

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Chemical Communications

COMMUNICATION

Polymerization of low molecular weight hydrogelators to form electrochromic polymers

Received 00th January 20xx,
Accepted 00th January 20xx

Peter S. Kubiak,^a Salmah Awhida,^b Christopher Hotchen,^a Wentao Deng,^a Ben Alston,^b Tom O. McDonald,^b Dave J. Adams,^{b,*} and Petra J. Cameron^{a,*}

DOI: 10.1039/x0xx00000x

www.rsc.org/

We present a method for the polymerization of low molecular weight hydrogelators to form polymers with unique structures. Carbazole-protected amino acids are shown to form hydrogels by self-assembly into fibrous structures. We show that is possible to directly electropolymerize the hydrogels. This results in the formation of microporous electrochromic polymers with distinctive structure. Polymers formed from the same gelator without the pregelation step show more compact structures. This method opens the possibility of creating polymers templated from pre-assembled gels that have the potential to be used in a wide range of applications.

Poly(carbazoles), poly(fluorenes) and other similar conjugated polymers have great potential as sensors, in light-emitting diodes, and in solar cells.^{1,2} Many of these polymers exhibit high quantum efficiencies, high thermal stabilities and tunable photoluminescence. They can be synthesized in solution by a range of coupling reactions, or electrochemically where polymerization is initiated by oxidation of the monomer.³ For many of the desired applications, the morphology of the polymers on a surface is important. As a result, there is considerable interest in preparing templated polymers with controlled morphology – for example an increase in porosity or incorporation of a desired structure such as polymer nanowires and nanotubes. As one example of an interesting morphology, conjugated polymer nanowires have many applications.⁴ Such nanowires often have properties that are different to those of the corresponding thin films or the bulk solids. There are many routes to polymer nanowires, including using hard templates, electrospinning and lithography.⁴ Another approach is to use the self-assembly of π -conjugated molecules.^{4,5} Low molecular weight gelators (LMWG), to give one example, self-assemble to form fibrous structures that immobilize the solvent.⁶ There are many examples of LMWG based on protected amino

acids or dipeptides.⁷⁻¹⁰ Many such LMWG have now been reported where the protecting group on the *N*-terminus is typically fluorenylmethoxycarbonyl (Fmoc), naphthalene, or another large aromatic group. Gelation can be triggered in water in many ways, including a pH change, temperature change, addition of ions, enzyme action, or shear flow. The resulting hydrogels typically contain a network of self-assembled fibers, with the gel properties being highly dependent on the nature of the amino acids in the gelator and how the gelation is carried out.¹¹ There is interest in cross-linking the LMWG to stabilize and strengthen the gel networks, which are often mechanically weak and sensitive to variations in their environment.¹² Chemical cross-linking in the gel state has been achieved by photo-crosslinking diacetylene or tyrosine groups on the LMWG.¹³⁻¹⁵

A number of Fmoc-amino acids can be used as LMWG.¹⁶⁻²¹ To the best of our knowledge, gels containing Fmoc-amino acids have never been cross-linked, but there is literature precedent for electropolymerising Fmoc-amino acids dissolved in an organic solution (i.e. not in a gel state). For example, Rault-Berthelot *et al.* grew brittle films of poly(Fmoc-Ala) and poly(Fmoc-Ile) electrochemically from solutions of the protected amino acid monomer in acetonitrile and used them as chiral sensors.²² He *et al.* electrosynthesised poly(Fmoc-Gly) using boron trifluoride diethyl etherate (BFEE) as the solvent.²³ This polymer retained the glycine side chain, was a good blue emitter, and had a conductivity of 0.4 S cm^{-1} . Finally Lai *et al.* prepared poly(Fmoc-Phe) electrochemically, also using BFEE as a solvent, creating a chiral polymer that was a good blue light emitter.²⁴


In this work, we postulated that the assembly of π -conjugated LMWG into fibers could be used as a pre-structuring step and that polymerization of the fibers could lead to novel microstructures such as conjugated polymer nanowires. To achieve this, we have prepared novel LMWGs based on a range of carbazole amino acids and polymerized the gels in an aqueous environment.²⁵ To the best of our knowledge this is the first example of the electrochemical polymerisation of a LMWG. By polymerizing pre-formed gels we have created redox polymers with unique microstructure. We have found that it is possible for π - π stacked gels to undergo a molecular reorganization during polymerization to form conjugated polymers

^a Department of Chemistry, University of Bath, Bath, BA2 7AY, United Kingdom

^b Department of Chemistry, University of Liverpool, Crown Street, Liverpool, L69 7ZD, United Kingdom

† Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: Synthetic details for Carbo-Ala, further electrochemical and other analysis. See DOI: 10.1039/x0xx00000x

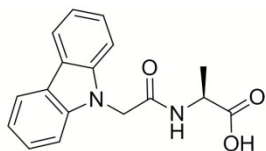

Scheme 1. Structure of Carb-Ala

As outlined above, we have chosen to electropolymerize gels prepared from carbazole protected amino acids. Carbazole-protected amino acids were chosen as poly(carbazole) is a well-known redox polymer.^{25,26} In addition, carbazole-protected amino acids were expected to be easier to polymerize compared to Fmoc protected amino acids as polymerization occurs at lower applied voltages (e.g. we found the oxidation onset for Carb-Ala was more than 400 mV less positive than that for Fmoc-Ala in acetonitrile, data not shown). Two carbazole-dipeptide gelators have been reported recently.²⁷ Here, we show that alanine protected at the *N*-terminus with a carbazole group (Carb-Ala, Scheme 1) is an effective LMWG. A number of other carbazole-protected amino acids form gels and can be polymerized, including valine, glycine and isoleucine, but we focus here on Carb-Ala for clarity. Similarly to other related LMWG (and the reported carbazole-dipeptides²⁷), Carb-Ala can form gels in the bulk via a pH switch in water. At high pH, a free-flowing solution is formed that gels when the pH is lowered, for example on addition of glucono- δ -lactone (GdL, which hydrolyses in situ to gluconic acid^{28,29}). These gels result from the self-assembly of Carb-Ala into fibres to give a transparent gel, with a storage modulus (G') of 6000 Pa and a loss modulus (G'') of 700 Pa. The gel was typical for this type of LMWG, with G' and order of magnitude greater than G'' and both being frequency independent.

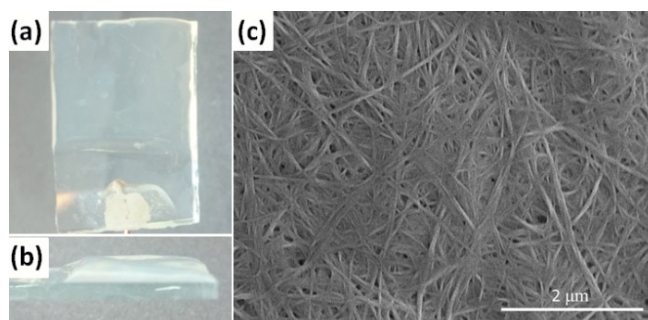


Figure 1. Photographs of a transparent Carb-Ala gel formed on an ITO-coated glass slide from (a) the top and (b) the side. (c) shows a SEM image of the xerogel formed by drying the gel in air.

Spatially resolved, surface supported Carb-Ala gels can also be prepared at an electrode surface via an electrochemically generated pH drop, as we have described previously (Fig. 1a and 1b).³⁰⁻³² Briefly, the electrochemical oxidation of hydroquinone to quinone results in a local pH drop at an electrode surface, and hence the gel only forms on the

electrode, rather than throughout the system. Again, the gel is a result of the assembly of Carb-Ala into fibres. On drying, an entangled network of fibers can be seen by microscopy, which is again typical for this type of gel (Fig. 1c).

We then attempted to directly polymerize Carb-Ala in the gel phase. A pre-formed gel layer was initially grown on an electrode surface as above. The gel was then removed from the Carb-Ala solution and placed into a 1 mol dm⁻³ perchloric acid electrolyte (note that there was no free monomer in the bulk solution at this point). The gel was polymerized by repeated cyclic voltammograms (CVs) between 0.2 and 1.1 V (versus Ag/AgCl, 3 mol dm⁻³). Oxidation of the monomer occurred above 0.8V. The polymerization process was videoed in real time (video at 16x speed is submitted as part of the ESI). Figure 2 shows stills taken from a video of the polymerization of a hemisphere of gel grown on the surface of a 1.6 mm diameter gold disc electrode. At $t=0$, there was a transparent hemi-sphere of gel on the electrode surface. As the polymerization progressed, the polymer grew out from the electrode surface and the gel collapsed to become part of the denser polymer film. A small amount of gel can still be seen away from the surface at $t=240$ s, but the majority has been incorporated into the polymer. The still at 240 seconds shows the polymer after approximately 8 CVs at 50 mVs⁻¹. Each CV lasted 34 seconds and they were started shortly after $t=0$ in the video.

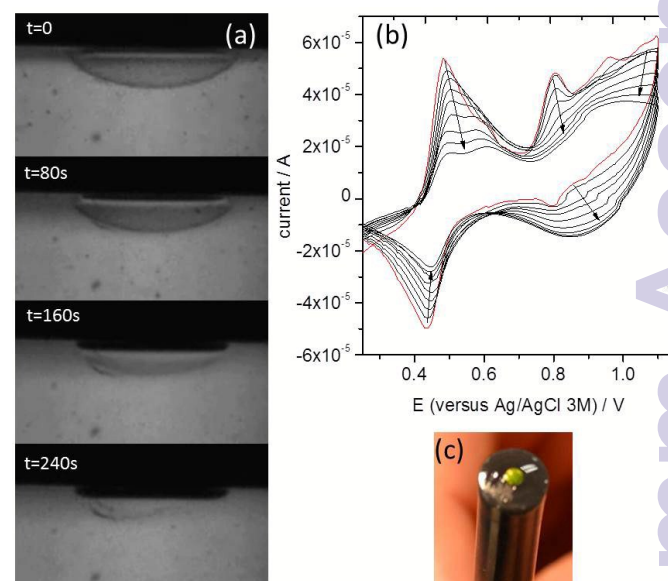


Figure 2. (a) In-situ polymerization of a pre formed gel on the surface of a gold disc electrode. At $t=0$, the gel is visible as a transparent hemi-sphere above the electrode surface. As the electrode was cycled above the oxidation potential for the monomer, the gel collapsed into a denser polymer layer on the electrode surface. The stills show the progression during the first 8 CVs at 50 mVs⁻¹ (34 seconds per scan). The surface attached polymer was electrochromic and cycled between green and colorless during successive scans. (b) Cyclic voltammograms taken during the polymerization of the gel shown in part (a). The peaks at 0.75 V are connected with the oxidation and reduction of the Carb-Ala monomer/polymer. The arrows show the evolution of the peaks with time. (c) photograph showing the green polymer grown on the gold disc electrode

The resulting small area poly(Carb-Ala) films were electrochromic and cycled between green (oxidized form) and colorless (reduced form) with each CV. The CVs taken as Carb-Ala gel was polymerized are shown in Figure 2b. The

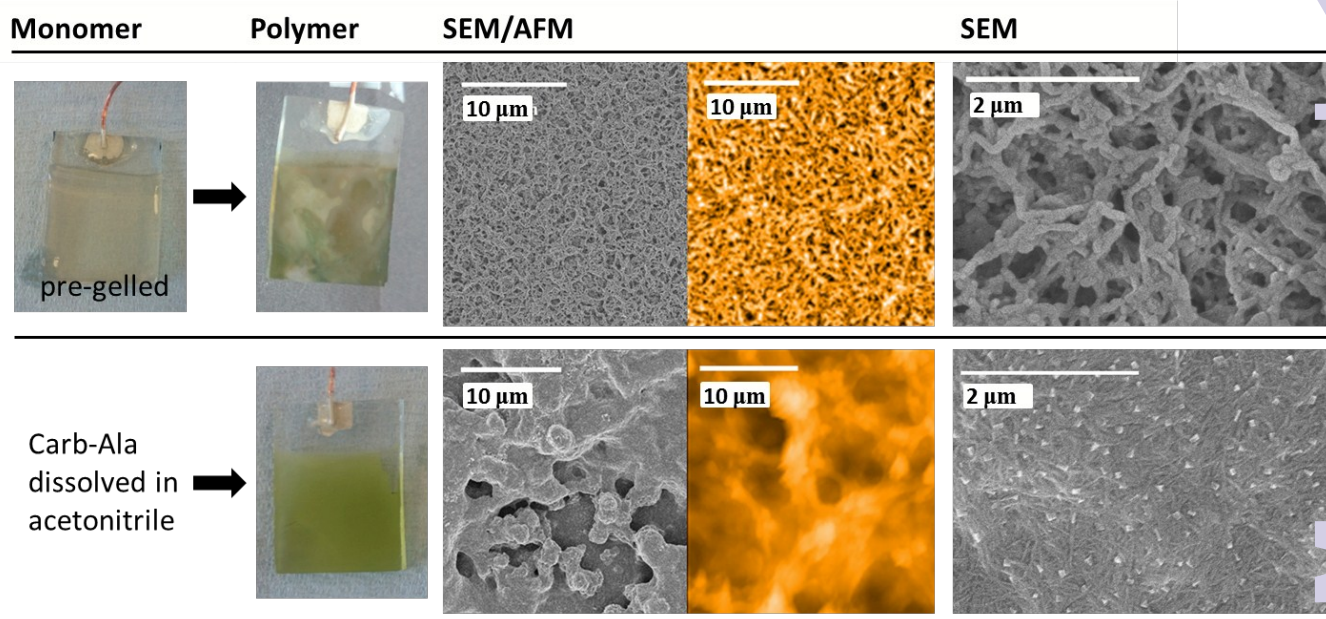


Figure 3. A comparison of the structures of large area polymer films grown on FTO glass electrodes. The top row shows the structure of the polymer formed when a gel is electropolymerized. The film grown from the pre-formed gel has a slight brown discoloration due to remaining hydroquinone/quinone within the polymer. The bottom row shows films obtained from the direct electropolymerization of Carb-Ala dissolved in acetonitrile. In both cases, the AFM (films grown from 2 mgmL⁻¹ Carb-Ala) and SEM (films grown from 2.5 mgmL⁻¹ Carb-Ala) images underline the large differences in the microstructures of polymer grown via the gel phase.

redox process centred on 0.46 V versus Ag/AgCl is due to the hydroquinone/quinone redox couple.

As described above, hydroquinone was used in the first step to create a pH drop at the electrode surface and to initiate gelation. The gel was subsequently removed from the hydroquinone solution and placed in 1 mol dm⁻³ perchloric acid. However, hydroquinone/quinone remains trapped within the gel and shows the quasi-reversible redox peaks centered on 0.46 V. The peaks decrease with increasing numbers of scans, probably due to the collapse of the gel into the polymer and the release of the hydroquinone/quinone back into solution. The peaks due to monomer and polymer oxidation and reduction occur above 0.75 V and are not as clearly defined as they are for polymerization of drop coated films in the same electrolyte (see Fig S1, ESI). However, a broad set of oxidation and re-reduction peaks are observed, centered on approximately 0.92 V. The thin films electropolymerised on 1.6mm diameter electrodes as shown in Fig. 2 were prepared from gels that were between 0.2mm to 0.5mm thick when wet. Thicker films which were several mm thick when wet were also polymerised on FTO slides (see Figure 3). In addition we have polymerised drop coated films which were much thinner and gave micrometre thick films of polymer (Fig. S5). While it is likely that there will be an upper limit to the thickness of the gel layer that can be polymerised, films more than a few mm thick were not investigated in this study.

As a control, polymers prepared from gels were compared to polymers prepared from Carb-Ala dissolved in acetonitrile (Fig. S2, ESI). The Carb-Ala does not pre-assemble into fibrous structures in acetonitrile, so polymerization occurs due to oxidation of free monomer in solution. These polymers were also compared to poly(carbazole) prepared by polymerizing carbazole dissolved in acetonitrile (Fig S3, ESI). FTIR

spectroscopy of the final polymers showed the presence of two peaks at 1660 cm⁻¹ and 1721 cm⁻¹ for the poly(Carb-Ala) films (from LMWGs and from acetonitrile), which were not present in spectra of poly(carbazole) films, showing the retention of the alanine group in the polymer (See Fig S4, ESI). Similarly, NMR showed the retention of the alanine group, as well as significant differences compared to the monomer. The spectra were similar for the polymer formed directly from acetonitrile and from the gel film (Fig. S5-S7, ESI). For both cases, residual monomer can be seen, with the amount varying depending on the polymerization process involved. Due to the polymers only dissolving in DMF and the lack of sufficient difference in refractive index between the polymer and solvent, all attempts at characterizing by GPC failed. Poly(Carb-Ala) produced by polymerization in acetonitrile showed a substantially different structure to poly(carbazole) (Fig. S8, ESI). Unfortunately, the two systems (polymerisation of a surface bound aqueous gel and or direct polymerisation of the monomer dissolved in acetonitrile) are too different to allow meaningful comparison of the reaction rates.

The structure of the polymers formed via the two-step gelation/ electropolymerization process is extremely interesting and quite different to the structure of polymers that did not pass through the templating gel phase. Imaging films where the gel had been polymerized for short times was difficult, as they remained soft and 'gel-like' (Fig. S9 shows photo of a partially polymerized gel on FTO glass). In order to obtain AFM images for the polymerized gels, the films were left in a covered container overnight to allow them to dry out slightly; it was therefore not possible to see the as-formed structure.

Figure 3 compares polymers grown from a pre-formed Carb-Ala gel and from Carb-Ala dissolved in acetonitrile. It can

be seen that polymers prepared from a pre-formed gel have an open fibrous structure, whereas polymers grown from acetonitrile are much denser. As an additional control, we drop-coated an electrode with Carb-Ala from a THF solution.³³ After evaporation of the organic solvent, polymerization of the Carb-Ala was also carried out in 1 mol dm⁻³ perchloric acid solution. The structure of polymers grown from drop-coated films was quite different to that of polymers grown from pre-formed gels (Fig. S8 compares the structures of drop coated poly(Carb-Ala) and poly(Carb-Ala) grown from acetonitrile with poly(carbazole) films grown under identical conditions). The drop-coated Carb-Ala polymerized to give needle shaped crystallites growing out from central nucleation points. Our results clearly show that we can use a gel to 'template' polymer structure to form unique structures by templating from the fibrous structures formed by the self-assembly of LMWG.

In conclusion, we have shown that Carb-Ala forms fibrous hydrogels in water. The gels can be polymerized by electrochemical oxidation of the carbazole end groups. Polymerized gels gave films with open porous structures, quite different to those prepared when films were grown from Carb-Ala-OH dissolved in MeCN or drop coated onto an electrode and polymerized in perchloric acid. Polymerization of gels was followed in real time; the gel collapsed as the Carb-Ala was incorporated into the polymers. Our data shows that it is possible for π - π stacked gels to undergo a molecular reorganization during polymerization to form conjugated polymers. The polymers were electrochromic (colourless to green) and retained the alanine functionality. These results open the possibility that a wide range of protected peptides could be fully or partially polymerized to form polymers with unique and useful microstructures. Patterning of the electrode could also allow selective polymerization of regions of gel. Overall, this process opens the possibility of using partially or completely polymerized hydrogels for a range of sensing and bioelectronics applications – introducing new properties while retaining an open porous structure and the amino acid functionality.

Acknowledgements

PJC acknowledges the University of Bath and the EPSRC (EP/H026304/1) for funding. SA thanks the Libyan government for a studentship. DJA thanks the EPSRC for a Fellowship (EP/L021978/1).

Notes and references

- 1 X. Guo, M. Baumgarten and K. Müllen, *Prog. Polym. Sci.* 2013, **38**, 1832.
- 2 R. C. Advincula, in *Functional Polymer Films*; Wiley-VCH Verlag GmbH & Co. KGaA: 2011, p 379.
- 3 J.-F. Morin, M. Leclerc, D. Adès and A. Siove, *Macromol. Rapid Commun.* 2005, **26**, 761.
- 4 F. S. Kim, G. Ren and S. A. Jenekhe, *Chem. Mater.*, 2011, **23**, 682.
- 5 S. S. Babu, V. K. Praveen and A. Ajayaghosh, *Chem. Rev.*, 2014, **114**, 1973.

- 6 P. Terech and R. G. Weiss, *Chem. Rev.* 1997, **97**, 3133.
- 7 M. de Loos, B. L. Feringa, and J. H. van Esch, *J. H. Eur. J. Org. Chem.* 2005, 3615.
- 8 D. J. Adams, *Macromolecular Bioscience* 2011, **11**, 160.
- 9 E. K. Johnson, D. J. Adams and P. J. Cameron, *J. Mater. Chem.* 2011, **21**, 2024.
- 10 S. Fleming and R. V. Ulijn, *Chem. Soc. Rev.* 2014, **43**, 8150.
- 11 J. Raeburn A. Zamith Cardoso and D. J. Adams, *Chem. Soc. Rev.* 2013, **42**, 5143.
- 12 D. J. Cornwell and D. K. Smith, *D. K. Mater. Horiz.* 2015.
- 13 S. R. Diegelmann, N. Hartman, N. Markovic and J. D. Tovar, *J. Am. Chem. Soc.* 2012, **134**, 2028.
- 14 M. de Loos, J. van Esch, I. Stokroos, R. M. Kellogg and B. L. Feringa, *J. Am. Chem. Soc.* 1997, **119**, 12675.
- 15 Y. Ding, Y. Li, M. Qin, Y. Cao and W. Wang, *Langmuir* 2013, **29**, 13299.
- 16 S. Sutton, N. L. Campbell, A. I. Cooper, M. Kirkland, W. J. Frith and D. J. Adams, *Langmuir* 2009, **25**, 10285.
- 17 Z. Yang, H. Gu, D. Fu, P. Gao, J. K. Lam and B. Xu, *Adv. Mater.* 2004, **16**, 1440.
- 18 D. M. Ryan, S. B. Anderson, F. T. Senguen, R. E. Youngman and B. L. Nilsson, *Soft Matter* 2010, **6**, 475.
- 19 D. M. Ryan, D. M.; Doran, T. M.; Anderson, S. B.; Nilsson, *Langmuir* 2011, **27**, 4029.
- 20 D. M. Ryan, T. M. Doran and B. L. Nilsson, *Chem. Commun.* 2011, **47**, 475.
- 21 D. M. Ryan and B. L. Nilsson *Polym. Chem.* 2012, **3**, 18.
- 22 J. Rault-Berthelot, E. Raoult, J. Tahri-Hassani, H. Le Deit and J. Simonet, *Electrochimica Acta* 1999, **44**, 3409.
- 23 Y. He, W. Guo, M. Pei and G. Zhang, *Chin. J. Chem.* 2012, **30**, 985.
- 24 C. Lai, W. Guo, X. Tang and M. Pei, *Chin. J. Chem.* 2012, **30**, 507.
- 25 K. Kawabata and H. Goto, *Synth. Metal*, 2010, **160**, 2290.
- 26 D.-X. Zhuang and P.-Y. Chen, *J. Electroanal. Chem.*, 2009, **62**, 197.
- 27 A. D. Martin, A. B. Robinson and P. Thordarson, *J. Mater. Chem. B*, 2015, **3**, 2277-2280.
- 28 Y. Pocker and E. Green, *J. Am. Chem. Soc.* 1973, **95**, 113.
- 29 D. J. Adams, M. F. Butler, W. J. Frith, M. Kirkland, L. Mullen and P. Sanderson, *Soft Matter* 2009, **5**, 1856.
- 30 E. K. Johnson, L. Chen, P. S. Kubiak, S. F. McDonald, D. J. Adams and P. J. Cameron, *Chem. Commun.* 2013, **49**, 869.
- 31 J. Raeburn, B. Alston, J. Kroeger, T. O. McDonald, J. R. Howse, P. J. Cameron and D. J. Adams, *Mater. Horiz.* 2014, **1**, 241.
- 32 E. K. Johnson, D. J. Adams and P. J. Cameron, *J. Am. Chem. Soc.* 2010, **132**, 5130.
- 33 G. Inzelt, *J. Solid State Electrochem.* 2003, **7**, 503.