

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

COMMUNICATION

## *In situ* production of silver nanoparticles on an aldehyde-equipped conjugated porous polymer and subsequent heterogeneous reduction of aromatic nitro groups at room temperature

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Jie Liu,<sup>a</sup> Jieshun Cui,<sup>a</sup> Filipe Vilela,<sup>b\*</sup> Jun He,<sup>c</sup> Matthias Zeller,<sup>d</sup> Allen D. Hunter<sup>d</sup> and Zhengtao Xu<sup>a\*</sup>


**In a metal-free procedure, chelating thiol groups and an electrophile react to assemble a robust, conjugated porous polymer with pendant aldehyde functionalities. These groups are able to reduce Ag(I) ions to generate, *in situ*, Ag(0) nanoparticles evenly dispersed in the polymer matrix. The Ag(0)-polymer composite enables selective reduction of aromatic nitro compounds as a heterogeneous catalyst, and can be conveniently recycled multiple times.**

Anthropogenic climate change as a result of our current energy demands is of great concern in today's society. The need for new sources of clean and renewable energy alongside with improved sustainable chemical processes has been the driving force behind the development of new materials. Conjugated Porous Polymers, (CPPs) as a growing class of advanced organic materials have received much attention due to their facile synthesis, low cost, and flexible chemical functionality. As the synthetic principles and structural studies continue to be extensively investigated, emphasis is being shifted to the properties and applications of these systems as novel organic zeolites. They have shown excellent performance in areas such as gas storage<sup>1</sup> and separation,<sup>1d</sup> by virtue of their high surface areas and porosity; metal-binding with high

selectivities;<sup>2</sup> and heterogeneous catalysis<sup>3</sup> including photocatalysis.<sup>4</sup> Furthermore, the combination of metal-binding ability with heterogeneous catalysis has the potential to develop materials with enhanced catalytic activity. Although underexplored, there are a few examples of this strategy.<sup>5</sup>

CPPs loaded with metal nanoparticles have also proven to be an efficient method in the development of novel heterogeneous photocatalysts. A conjugated microporous polymer was reported to photocatalyze Suzuki-Miyaura cross-coupling reactions when loaded with Pd nanoparticles.<sup>6</sup> Li *et al.* also reported that mesoporous g-C<sub>3</sub>N<sub>4</sub> can be used as photoactive anchoring support for Pd nanoparticles to perform the same chemical transformations.<sup>7</sup> These systems rely on the mixing of the CPP with a solution of nanoparticles leading to a cumbersome and wasteful process. By comparison, and to the best of our knowledge, there have been very few reports on nanoparticle synthesis *in situ* directly within a CPP network.<sup>8</sup>

Herein, we report a novel aldehyde-equipped porous polymer that can be easily synthesized in the absence of any metal catalyst, and can then be further post-modified to incorporate Ag nanoparticles (Ag NPs) via the use of Tollens' reagent. Our strategy allows for *in situ* formation of the Ag nanoparticles leading to a stable hybrid material that can be employed as a heterogeneous catalyst for the reduction of aromatic nitro compounds at room temperature. This application is particularly relevant to the pharmaceutical and agrochemical industries since synthesis of anilines or amines from the corresponding nitro compounds lead to versatile intermediates and precursors in the preparation of dyes, pharmaceuticals, pigments, agrochemicals and polymers.<sup>9</sup>

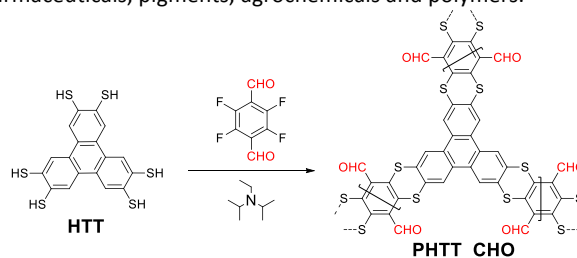

**Scheme 1.** Synthesis of the aldehyde-equipped CPP PHTT\_CHO. Conditions: dimethylacetamide (DMA), DIPEA, N<sub>2</sub>, 90 °C, 3 hours, then 140 °C, 12 hours.

<sup>a</sup>Ms. J. Liu, Dr. J. Cui and Prof. Z. Xu\*  
Department of Biology and Chemistry  
City University of Hong Kong  
83 Tat Chee Avenue, Kowloon, Hong Kong  
E-mail: zhengtao@cityu.edu.hk

<sup>b</sup>Dr. F. Vilela\*  
School of Engineering and Physical Sciences  
Heriot-Watt University  
Edinburgh, EH14 4AS, UK  
E-mail: f.vilela@hw.ac.uk

<sup>c</sup>Dr. J. He  
School of Chemical Engineering and Light Industry  
Guangdong University of Technology  
Guangzhou 510006, Guangzhou, China

<sup>d</sup>Dr. M. Zeller and Prof. A. D. Hunter  
Youngstown State University  
One University Plaza  
Youngstown, Ohio 44555, USA

Electronic Supplementary Information (ESI) available: Experimental procedures; network synthesis; elemental analysis, N<sub>2</sub> and CO<sub>2</sub> sorption, TGA, IR, NMR, and PXRD data. CCDC 1401125. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/x0xx00000x

CPPs are generally synthesized via metal catalyzed coupling reactions. Typically these include Suzuki-Miyaura,<sup>10</sup> Sonogashira-Hagihara,<sup>11</sup> Yamamoto and Glaser polycondensations.<sup>12</sup> Other strategies such as oxidative polymerizations also rely on metals (typically  $\text{FeCl}_3$ ).<sup>13</sup> Recently we reported a metal-free polymerization method simply by mixing two monomers in the presence of a mild base *N,N'*-diisopropylethylamine (DIPEA) that promoted C-N bond formation to produce a porous polymer framework in high yield.<sup>2</sup>


With regards to the synthesis of an aldehyde-equipped CPP, DIPEA was again employed to promote C-S bond formation via the use of a rigid monomer containing multiple chelating sites, triphenylene-2,3,6,7,10,11-hexathiol (HTT) (Scheme 1). This methodology offers great advantages: the most important being the absence of any metal catalysts. In general, thiols can easily undergo aromatic nucleophilic substitution without deactivating the substrate, thus facilitating the formation of the polymer framework. Utilizing this efficient aromatic nucleophilic substitution of thiol molecules we chose 2,3,5,6-tetrafluoroterephthalaldehyde (TFTA), as a linear bridge to connect the HTT moieties into a 3D-connected CPP, with TFTA being the source of aldehydes.

The assembly of the polymer simply involves heating a mixture of DMA, TFTA, HTT (which was freshly prepared by the deprotection of HBUtT<sup>14</sup>; see ESI), together with the mild base DIPEA (see Scheme 1, ESI) to produce a dark red solid in high yield (96.8%). To further demonstrate the simplicity of this polymerization, a model reaction between 1,2-benzenedithiol and TFTA is conducted under similar reaction conditions with high yield (88%). A single crystal structure is presented for this molecular system (Figure S9).

Elemental analysis of PHTT\_CHO is consistent with the calculated values for C, H, N (see ESI). Thermogravimetric analysis (TGA, Figure S1) reveals a stable weight region up to 300 °C, indicative of the non-volatile, and polymeric nature of the product. As expected, the peak at 1681  $\text{cm}^{-1}$  in the IR (Figure S2) confirms the presence of the aldehyde moiety. In addition, solid state <sup>13</sup>C NMR of a PHTT\_CHO sample confirms the polymer structure as shown in Scheme 1. As seen in Figure S3, the aromatic region of the solid state <sup>13</sup>C NMR spectrum of PHTT\_CHO is dominated by 3 distinct peaks (135.8, 129.2 and 123.8 ppm) corresponding to the aromatic carbon signals of the polymer backbone, the peak at 188.8 ppm is assigned to the aldehyde moieties in the PHTT\_CHO framework. Significant porous character of the activated sample of PHTT\_CHO was revealed in both  $\text{N}_2$  sorption (at 77 K) and  $\text{CO}_2$  sorption (at 273 K, see Figure S4) experiments. A typical type-I  $\text{N}_2$  gas adsorption isotherm (Figure 1A) was observed, with a Brunauer–Emmett–Teller (BET) surface area of 686  $\text{m}^2/\text{g}$ . QSDFT analysis on pore size distribution and pore volume indicated an average pore width of 1.03 nm and a pore volume of 0.374  $\text{cm}^3/\text{g}$  (Figure S6).


Aldehyde functionalized CPPs are rare.<sup>15</sup> The advantages of affixing the aldehyde functionality (e.g.,  $-\text{CHO}$ ) onto a CPP are obvious, since this moiety offers great versatility for facile and efficient post-modification reactions even in heterogeneous conditions. Aldehydes can readily undergo both reductions (e.g., to give alcohol  $-\text{CH}_2\text{OH}$  or halide  $\text{CH}_2\text{X}$  functions) and oxidation to form carboxyl groups, providing a convenient entry into diverse ranges of functional derivatives. An interesting post-modification

strategy, known as the silver mirror reaction, relies on Tollens' reagent, which is generally used to qualitatively detect the presence of aldehydes.

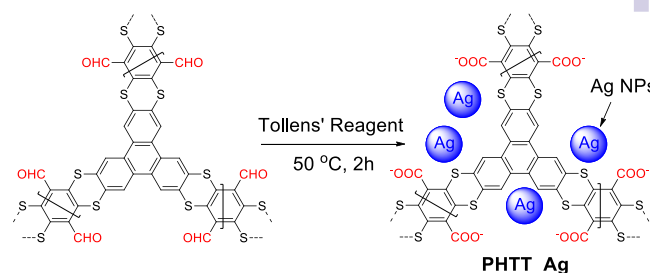


**Scheme 2.** The preparation of PHTT\_Ag from PHTT\_CHO with the *in situ* production of silver nanoparticles.

Upon stirring with a freshly prepared Tollens' reagent (see ESI) at 50 °C for 2 hours, the PHTT\_CHO powder turned from dark red to black to afford the PHTT\_Ag sample (Scheme 2). The strong PXRD peaks (Figure S10) of the silver loaded polymer sample indicate that the Ag NPs are evenly dispersed on the polymer support. The average particle size of Ag NPs is about 10 nm in diameter calculated based on the X-ray diffraction patterns.<sup>16</sup> Transmission electron microscopy (TEM) measurements were conducted on both PHTT\_CHO and PHTT\_Ag samples. Ag NPs can be readily seen in the Ag NPs loaded sample (PHTT\_Ag, Figure 2B) compared to the original dark red PHTT\_CHO polymer (Figure 2A). Scanning electron microscope (SEM) (Figure 2C) together with the corresponding elemental map of Ag atoms (Figure 2D) obtained by energy dispersive X-ray (EDX) technique on PHTT\_Ag, supported the notion of evenly distributed Ag throughout the polymer matrix. The amount of Ag NPs was quantified by ICP elemental analysis to be 33.5 wt%. As is consistent with previous studies, where Ag NPs and their aggregates was shown to block gas access to the pores,<sup>2</sup> the porosity of activated PHTT\_Ag is markedly suppressed, with  $\text{N}_2$  sorption revealing a decrease in surface area to 126  $\text{m}^2/\text{g}$  (686  $\text{m}^2/\text{g}$  before Ag NPs generation; Figure 1). Additionally, the PHTT\_Ag powder is more conductive (6.3 $\times 10^{-5}$  S/m; two-probe measurement) than PHTT\_CHO (4.9 $\times 10^{-6}$  S/m); the enhanced conductivity can be partly attributed to the formation of the Ag NPs, even though the polymer backbone also undergoes changes in electronic structure/properties with the pendant aldehyde groups oxidized into carboxylate units. Efforts to remove the Ag NPs from the polymer matrix are ongoing, so as to facilitate the characterization of such changes on the polymer backbone.

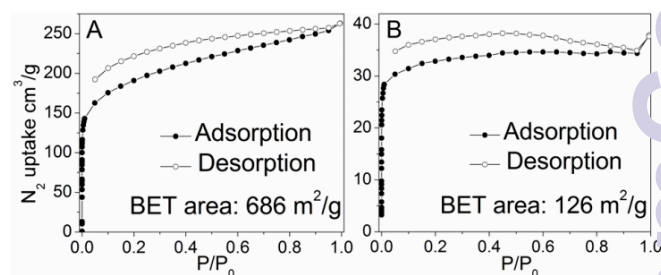

**Figure 1.**  $\text{N}_2$  sorption isotherms at 77 K for the activated solid samples of PHTT\_CHO (A) and PHTT\_Ag (B).

Nanoparticles of noble metals such as silver are very important due to their applications in catalysis.<sup>17</sup> Polymeric materials that support silver nanoparticles whilst retaining catalytic activity present distinct advantages over homogeneous systems, with regards ease of separation, recovery and reusability.

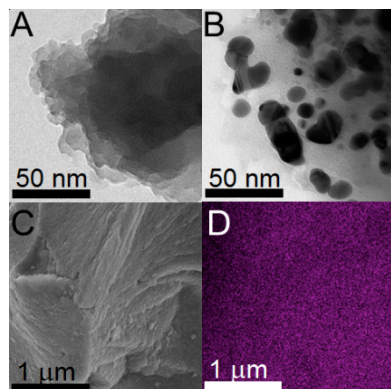

**Figure 2.** TEM images of (A) PHTT\_CHO, (B) PHTT\_Ag, (C) SEM image of PHTT\_Ag, and (D) the corresponding EDX mapping for Ag atom (purple indicates presence of Ag).

The catalytic activity of the PHTT\_Ag polymer was examined under especially mild conditions for the reduction of aromatic nitro groups, by simply stirring the substrates with NaBH<sub>4</sub> (an inexpensive, bench stable, stoichiometric reductant) and the polymer (Ag/substrate molar ratio: about 5%) in ethanol at room temperature and under air (see details in ESI). We tested the feasibility of PHTT\_Ag as a catalyst for the reduction of various nitroarenes, keeping all other reaction conditions unaltered. As shown in Table 1, the catalyst PHTT\_Ag was found to be very effective toward the reduction of nitro compounds to their corresponding anilines, regardless of the types and position of the substituents. Two control experiments were performed: i) in the absence of PHTT\_Ag there was no conversion of nitroaromatic compounds into amines; ii) a freshly prepared silver mirror with benzaldehyde showed reduced activity in the reduction of nitrobenzene when compared to PHTT\_Ag using similar conditions (followed by TLC). In particular, this reaction also showed high efficiency for the selective reduction of nitro groups in the presence of other reducible functional groups (*e.g.* alkenes, entry 6-8). The recyclability of the PHTT\_Ag solid was also investigated.

After the hydrogenation reaction, the catalyst can be conveniently recovered from the reaction mixture by centrifugation and subsequent washing with water and absolute ethanol. The reusability of the hybrid material was then tested after recovery. We observed no activity loss for the conversion of 1-allyloxy-3-nitrobenzene into 3-allyloxyaniline (entry 8 in Table 1). In fact, the conversion remained almost the same after 3 catalytic cycles, Figure S13. Furthermore, the isolated supernatant exhibited no catalytic activity under similar reaction conditions (as verified by the NMR data in Figure S14), which indicates that Ag NPs were not present in the reaction mixture proving that PHTT\_Ag does not leach Ag NPs under the conditions tested. This was also confirmed via ICP measurements where the amount of Ag within PHTT\_Ag was

found to be 33.4 wt% after the catalytic reactions, very close to the 33.5 wt% measured for PHTT\_Ag prior to catalysis. Further cycling of the PHTT\_Ag also showed no loss in activity (followed via TLC). However, PXRD experiments (Figure S15) at the 5<sup>th</sup> catalytic cycle started to reveal peaks of AgCl, which could have arisen from the Ag nanoparticles reacting with the residual NaCl trapped within the porous CPP during the earlier steps of synthesis (Scheme S1). Apart from the ease of recovery generally associated with polymer supports, catalyst recycling in the present case can also be attributed to the anionic form of the carboxylate units in the PHTT\_Ag composite (as a result of the alkaline conditions of aldehyde oxidation) – *i.e.*, the carboxylate anion minimizes the acid-base interaction with the (alkaline) amine products, and therefore facilitates their release from the polymer surface.

**Table 1.** Efficiencies of the PHTT\_Ag catalyst in the reduction of various nitroaromatics into amines.

Entry	Substrate	Product	Time (h)	Conversion <sup>b</sup> (%)
1			6	96
2			6	80
3			6	99
4			6	99
5			12	84
6			6	97
7			12	93
8			12	96
9			12	95
10			12	96

[a] Reaction conditions: substrate (0.084 mmol), NaBH<sub>4</sub> (0.67 mmol) and PHTT\_Ag (1.4 mg, Ag/substrate molar ratio: 5%) in 0.5 mL ethanol at RT. [b] Conversion is determined via <sup>1</sup>H NMR using 1,2,4,5-tetramethylbenzene as the internal standard. [c] See ESI for the cycling procedure.

To sum up, several major advantages of stability and functionality have been demonstrated for this aldehyde-equipped CPP system that is conveniently produced using a metal-free strategy under mild reaction conditions. The stability is highlighted by the aqueous, alkaline and oxidative conditions in the silver mirror reaction procedure, conditions that would readily destroy MOFs, COFs and other less robust porous polymers. The Ag nanoparticles produced *in situ* were found to be evenly blended with the polymer matrix, offering highly efficient heterogeneous catalysis for the reduction of aromatic nitro compounds at room temperature. The selectivity and reusability of the composite catalyst also further illustrate the *in situ* generation of metal particles as a potentially wide-scope, effective method for enhancing the materials properties of polymer/metal nanoparticle hybrids.

## Notes and references

General experimental details including CPP synthesis and post-modification reactions are given in the supporting information section.

**Typical conditions for heterogeneous catalytic reactions (reduction of aromatic nitro groups).** The substrate (0.084 mmol), NaBH<sub>4</sub> (25.4 mg, 0.672 mmol) and PHTT\_Ag (Ag/substrate molar ratio: 5%) were loaded into a 7.5-mL glass vial. Absolute ethanol (0.5 mL) was then added and the reaction mixture was stirred with a magnetic stirring bar at room temperature for several hours (see table 1). After the reaction was completed (monitored via TLC), PHTT\_Ag was removed by filtration, and washed with absolute ethanol (1 mL x 3), the filtrate was collected and the solvent was evaporated under reduced pressure. Conversions of the substrates were determined via <sup>1</sup>H NMR using 1,2,4,5-tetramethylbenzene as the internal standard.

This work was supported by City University of Hong Kong (Project 9667092), the Research Grants Council of HKSAR (GRF Project 103413) and the National Natural Science Foundation of China (21471037, 21201042). The X-ray diffractometer at YSU was funded by NSF Grant 1337296. We thank Mr. Yan Lung Wong for drawing Figure S9.

- (a) F. Su, C. L. Bray, B. Tan and A. I. Cooper, *Adv. Mater.*, 2008, **20**, 2663; (b) J.-Y. Lee, C. D. Wood, D. Bradshaw, M. J. Rosseinsky and A. I. Cooper, *Chem. Commun.*, 2006, 2670; (c) C. D. Wood, B. Tan, A. Trewin, H. Niu, D. Bradshaw, M. J. Rosseinsky, Y. Z. Khimyak, N. L. Campbell, R. Kirk, E. Stöckel and A. I. Cooper, *Chem. Mater.*, 2007, **19**, 2034; (d) N. B. McKeown, P. M. Budd, K. J. Msayib, B. S. Ghanem, H. J. Kingston, C. E. Tattershall, S. Makhseed, K. J. Reynolds and D. Fritsch, *Chem. Eur. J.*, 2005, **11**, 2610; (e) C. D. Wood, B. Tan, A. Trewin, F. Su, M. J. Rosseinsky, D. Bradshaw, Y. Sun, L. Zhou and A. I. Cooper, *Adv. Mater.*, 2008, **20**, 1916; (f) J. Germain, F. Svec and J. M. J. Fréchet, *Chem. Mater.*, 2008, **20**, 7069.
- J. Liu, K.-K. Yee, K. K.-W. Lo, K. Y. Zhang, W.-P. To, C.-M. Che and Z. Xu, *J. Am. Chem. Soc.*, 2014, **136**, 2818.
- F. Goettmann, A. Fischer, M. Antonietti and A. Thomas, *Angew. Chem. Int. Ed.*, 2006, **45**, 4467.
- (a) H. Urakami, K. Zhang and F. Vilela, *Chem. Commun.*, 2013, **49**, 2353; (b) K. Zhang, D. Kopetzki, P. H. Seeberger, M. Antonietti and F. Vilela, *Angew. Chem. Int. Ed.*, 2013, **52**, 1432; (c) K. Zhang, Z. Vobecka, K. Tauer, M. Antonietti and F. Vilela, *Chem. Commun.*, 2013, **49**, 11158; (d) D. Zheng, C. Pang, Y. Liu and X. Wang, *Chem. Commun.*, 2015, **51**, 9700; (e) J. Zhang, M. Zhang, C. Yang and X. Wang, *Adv. Mater.*, 2014, **26**, 4121; (f) G. Zhang, M. Zhang, X. Ye, X. Qiu, S. Li and X. Wang, *Adv. Mater.*, 2014, **26**, 805; (g) Y. Cui, Z. Ding, X. Fu and X. Wang, *Angew. Chem. Int. Ed.*, 2012, **51**, 11814; (h) Z. Lin and X. Wang, *Angew. Chem. Int. Ed.*, 2013, **52**, 1735; (i) X. Wang, K. Maeda, A. Thomas, K. Takanebe, G. Xi, J. M. Carlsson, K. Domen and M. Antonietti, *Nat. Mater.*, 2009, **8**, 76; (j) J. Sun, J. Zhang, M. Zhang, M. Antonietti, X. Fu and X. Wang, *Nat. Commun.*, 2012, 1139.
- (a) R. Palkovits, M. Antonietti, P. Kuhn, A. Thomas and F. Schüth, *Angew. Chem. Int. Ed.*, 2009, **48**, 6909; (b) P. M. Budd, B. Ghanem, K. Msayib, N. B. McKeown and C. E. Tattershall, *J. Mater. Chem.*, 2003, **13**, 2721.
- Z. J. Wang, S. Ghasimi, K. Landfester and K. A. I. Zhang, *Chem. Mater.*, 2015, **27**, 1921.
- (a) X.-H. Li, M. Baar, S. Blechert and M. Antonietti, *Sci. Rep.*, 2013, **3**; (b) X.-H. Li, X. Wang and M. Antonietti, *Chem. Sci.*, 2012, **3**, 2170.
- S. Rifai, C. A. Breen, D. J. Solis and T. M. Swager, *Chem. Mater.*, 2006, **18**, 21.
- (a) H.-U. Blaser, H. Steiner and M. Studer, *ChemCatChem*, 2009, **1**, 210; (b) J. P. Adams and J. R. Paterson, *J. Chem. Soc. Perkin Trans. 1*, 2000, 3695.
- L. Chen, Y. Honsho, S. Seki and D. Jiang, *J. Am. Chem. Soc.*, 2010, **132**, 6742.
- (a) J.-X. Jiang, F. Su, A. Trewin, C. D. Wood, H. Niu, J. T. Jones, Y. Z. Khimyak and A. I. Cooper, *J. Am. Chem. Soc.*, 2008, **130**, 7710; (b) J.-X. Jiang, F. Su, A. Trewin, C. D. Wood, N. L. Campbell, H. Niu, C. Dickinson, A. Y. Ganin, M. Rosseinsky, Y. Z. Khimyak and A. I. Cooper, *Angew. Chem. Int. Ed.*, 2007, **46**, 8574.
- (a) J. Schmidt, M. Werner and A. Thomas, *Macromolecules*, 2009, **42**, 4426; (b) J.-X. Jiang, F. Su, H. Niu, C. D. Wood, N. L. Campbell, Y. Z. Khimyak and A. I. Cooper, *Chem. Commun.*, 2008, 486.
- J. Schmidt, J. Weber, J. D. Epping, M. Antonietti and A. Thomas, *Adv. Mater.*, 2009, **21**, 702.
- J. Cui and Z. Xu, *Chem. Commun.*, 2014, **50**, 3986.
- V. Guillermin, L. J. Weselinski, M. Alkordi, M. I. H. Mohideen, M. Belmabkhout, A. J. Cairns and M. Eddaoudi, *Chem. Commun.*, 2014, **50**, 1937.
- H. Borchert, E. V. Shevchenko, A. Robert, I. Mekis, J. Kornowski, G. Grübel and H. Weller, *Langmuir*, 2005, **21**, 1931.
- (a) H. Cong, C. F. Becker, S. J. Elliott, M. W. Grinstaff and A. Porco, *J. Am. Chem. Soc.*, 2010, **132**, 7514; (b) N. Pradhan, A. Pal and T. Pal, *Colloids Surf., A*, 2002, **196**, 247; (c) B. Barua, G. J. Gabriel, M. J. Akbashev and M. E. Boohar, *Langmuir*, 2013, **29**, 4225.