

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Photocatalytic CO₂ reduction using visible light by metal-monocatecholato species in a metal-organic framework

Cite this: DOI: 10.1039/x0xx00000x

Yeob Lee,^a Sangjun Kim,^b Honghan Fei,^a Jeung Ku Kang,^{*b} and Seth M. Cohen^{*a}

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Metal-organic frameworks (MOFs) with isolated metal-monocatecholato groups have been synthesized via postsynthetic exchange (PSE) for CO₂ reduction photocatalyst under visible light irradiation in the presence of 1-benzyl-1,4-dihydropyridinamide and triethanolamine. The Cr-monocatecholato species are more efficient than the Ga-monocatecholato species.

The conversion of CO₂ into hydrocarbons has attracted great attention owing to global warming caused, in part, by CO₂ from fossil fuel combustion.^{1,2} Inspired by photosynthesis, development of an artificial system that catalytically regenerates hydrocarbon fuels from CO₂, H₂O, and sunlight is one very intriguing approach.³⁻⁵ Artificial photosynthesis would consist of two reactions: water oxidation to extract electrons from water and CO₂ reduction to generate carbonaceous radicals using electrons generated from water oxidation. CO₂ requires a large driving force to be transformed to other compounds due to the high kinetic and thermodynamic stability of CO₂.⁶⁻⁸ Several photocatalytic systems for CO₂ reduction, including heterogeneous semiconductor systems and homogeneous transition metal-based complexes have been investigated but some challenges still remains. For example, many metal oxides are active under only UV light, which represents only ~4% of the solar energy spectrum. This has encouraged research on extending the light absorption edge of metal oxides.⁹ Homogeneous metal complexes based on Ru, Re, and Ir have been investigated; however, an inability to recycle and reuse these precious metal compounds remains a limitation of these systems.¹⁰

Metal-organic frameworks (MOFs) are hybrid materials that consist of secondary building units (SBUs) and organic linkers. The rational design of MOFs with tunable properties through a selective combination of metal ions and organic ligands has produced materials useful for various applications. Photocatalytic applications of MOFs also have been studied.¹¹⁻¹⁵ Lin and co-workers reported a MOF photocatalyst doped with Re(bpy)(CO)₃Cl complexes that reduced

CO₂ to CO under UV light irradiation.¹¹ This pioneering work for MOF photocatalysts showed poor efficiency due, in part, to a low doping of the Re catalyst into the MOF. Fu et al. synthesized visible-light sensitive NH₂-MIL-125(Ti) with an amine-functionalized organic linker. This material reduced CO₂ to HCOO⁻ in the presence of triethanolamine (TEOA) under visible-light irradiation.¹² In addition, Li et al. developed a non-porous coordination polymer consisting of Y metal ions and Ir(ppy)₂(dcbpy) metalloligands; this material reduced CO₂ to HCOO⁻ under visible light irradiation.¹⁶ Despite these advances, the development of MOF photocatalysts for CO₂ reduction is still in its infancy.

Herein, we report a new MOF photocatalysts that incorporate catalytic metal sites, using postsynthetic modification methods, for CO₂ reduction to formic acid in the presence of 1-benzyl-1,4-dihydropyridinamide (BNAH) and triethanolamine (TEOA). The Zr(IV)-based MOF (UiO-66, UiO = University of Oslo) was subjected to postsynthetic exchange (PSE)¹⁷⁻²⁰ with a catechol-functionalized organic linker (catbdc, 2,3-dihydroxyterephthalic acid, to produce UiO-66-CAT).¹⁹ Two different trivalent metal ions, Cr(III) and Ga(III), were then incorporated into the catbdc sites to afford unprecedented Cr- and Ga-monocatecholato species in a robust UiO-66. The catbdc organic linkers are responsible for visible light absorption and metalation by Cr(III) and Ga(III) facilitates electron transfer within the MOFs.

PSE has become a facile and efficient strategy to functionalize MOFs under mild conditions (Fig. 1). UiO-66 was prepared solvothermally in DMF containing 1:1 molar ratio mixture of ZrCl₄ and H₂bdc with acetic acid as a modulator at 120 °C. UiO-66 was then exposed to DMF/H₂O solution containing 2 equiv catbdc²⁻ at 85 °C to achieve PSE into UiO-66.¹⁹ This gave a UiO-66 derivative that contained ~34% catbdc and ~66% bdc ligand. The metalation of the catechol functionality in UiO-66-CAT was conducted using aqueous K₂CrO₄ under weakly acidic conditions (pH = 3). After incubation at room temperature (1 h) the pale yellow UiO-66-CAT changed to a dark brown color. Similarly, an aqueous solution of Ga(NO₃)₃(H₂O)_x

was used to achieve metalation with Ga(III). After metalation, the MOFs were isolated by centrifugation, washed extensively with deionized water and MeOH, and dried under vacuum. Inductively coupled plasma mass spectrometry (ICP-MS, Table S1) confirmed the atomic ratio of 0.25 (Cr/Zr) and 0.26 (Ga/Zr), indicating that ~80% of the available catbdc ligands were metalated by both the Cr and Ga procedures based on three independent samples.

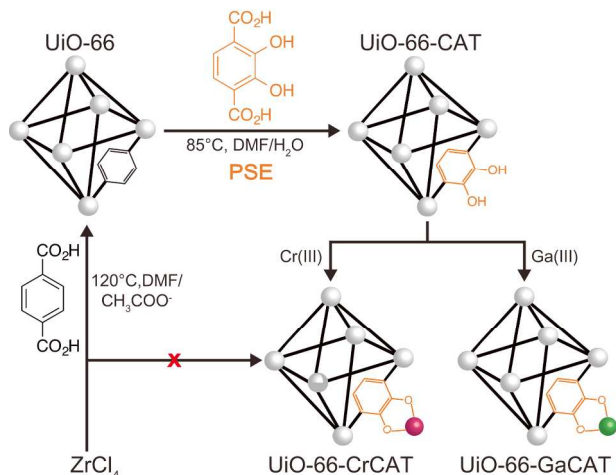


Fig. 1. Preparation of MOF photocatalysts through postsynthetic exchange (PSE) and metalation.

The MOFs formed as nanocrystallites ~150 nm on an edge, with an octahedral morphology. The crystallinity of the MOFs did not change upon PSE or metalation as evidenced by the PXRD patterns as shown in Fig. 2a. Scanning electron microscopy (SEM) images showed that the morphology and crystal size of UiO-66-CrCAT and UiO-66-GaCAT were also unchanged from the parent UiO-66 material (Fig. S1, S2). The characteristic M(III) signals were detected using energy dispersive X-ray spectroscopy (Fig. S1).

The UV-visible spectroscopy of the MOFs was altered upon PSE and metalation as illustrated in Fig. 2b. The diffuse reflectance of samples was measured and the reflectance values were subjected to the Kubelka-Munk function $((1-R)^2/2R)$ to quantify the light absorption ability of samples. $H_{2}bdc$ derivatives with electron donating functionality such as NH_2 , OH, and SH are known to increase the HOMO level of $H_{2}bdc$.²¹⁻²³ Thus, UiO-66-CAT is expected to absorb some visible light as a result of the catechol groups. A color change to dark brown was observed upon metalation with Cr(III). As expected, Cr(III) binding to catbdc results in the generation of ligand-to-metal charge transfer (LMCT).^{24,25} A similar color change was not observed upon metalation with Ga(III), as expected for this closed-shell ion.

X-ray photoelectron spectroscopy (XPS) of UiO-66-CrCAT and UiO-66-GaCAT was carried out to determine the oxidation states of Cr and Ga. The 2p orbital information was obtained and each spectrum exhibits two peak contributions. Chromium oxide (Cr_2O_3) and gallium oxide (Ga_2O_3) were selected as references for both UiO-66-M(III)CATs. UiO-66-CrCAT shows two peaks at 586.10 eV and 576.58 eV corresponding to $2p^{3/2}$ and $2p^{1/2}$ binding energies, respectively. These values compare well with energy levels in Cr_2O_3 (586.13 eV and 576.33 eV). This indicates that the Cr(VI) in K_2CrO_4 was reduced to Cr(III) upon metalation, as previously observed.¹⁹ The XPS for UiO-66-

GaCAT also consists of two peaks at 1144.79 eV and 1117.89 eV corresponding to $2p^{3/2}$ and $2p^{1/2}$ energy levels, respectively. These values match well to binding energies in Ga_2O_3 (1144.67 eV and 1117.79 eV). Therefore, XPS of UiO-66-CrCAT and UiO-66-GaCAT confirm the trivalent oxidation state of Cr and Ga in these MOFs.^{26,27}

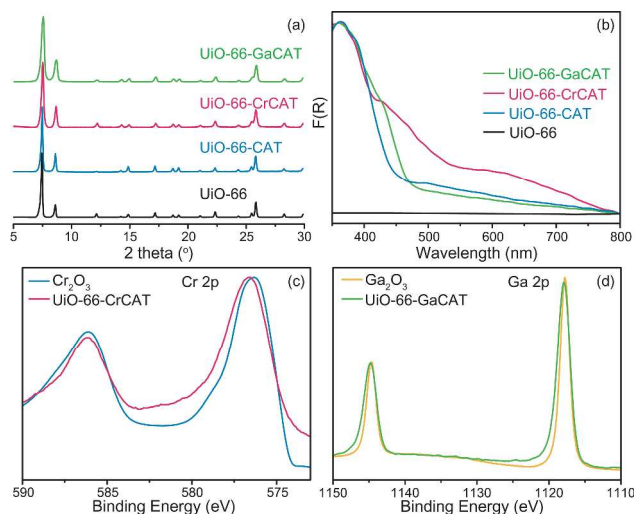


Fig. 2. (a) PXRD patterns of UiO-66 and functionalized UiO-66 derivatives; (b) UV-Vis spectroscopy for UiO-66, UiO-66-CAT, UiO-66-CrCAT, and UiO-66-GaCAT. $F(R)$ were calculated from diffuse reflectance measurement; X-ray photoelectron spectroscopy analysis of (c) UiO-66-CrCAT and (d) UiO-66-GaCAT.

These M(III)-monocatecholato functionalized MOFs were investigated for their photocatalytic CO_2 reduction activity. The MOFs were introduced into a mixed solution of 4:1 (v/v) MeCN and TEOA, which contained BNAH (0.1 M). In this photocatalytic reaction, BNAH serves as a reductant for CO_2 to produce carbonaceous radicals^{28,29} and TEOA acts as a sacrificial base to capture protons from BNAH.³⁰ The product solutions were found to consist of water, ethyl acetate, MeCN, and HCOOH. The photocatalytic activity of each UiO-66-M(III)CAT are shown in Fig. 3a. Turnover numbers were calculated from the amount of HCOOH produced versus the number of M(III)-catecholato sites in each MOF. Turnover numbers were calculated as 11.22 ± 0.37 for UiO-66-CrCAT and 6.14 ± 0.22 for UiO-66-GaCAT, respectively. UiO-66-CrCAT and UiO-66-GaCAT produced 51.73 ± 2.64 μ moles and 28.78 ± 2.52 μ moles of HCOOH from CO_2 photocatalysis, respectively (6 h of visible light irradiation). These numbers indicate that each Cr-catecholato species catalyzed the conversion of ~11 CO_2 molecules, while each Ga-catecholato species catalyzed the conversion of ~6 CO_2 molecules over the 6 h reaction time. UiO-66-CrCAT proved to be a more efficient catalyst than UiO-66-GaCAT under these reaction conditions. Both UiO-66-M(III)CATs produced negligible amount of H_2 and CO that can be generated from photocatalysis of CO_2 in the presence of TEOA and BNAH. This indicates that metalated catecholato species are suitably selective for CO_2 reduction to formate.

Both MOFs were tested over three catalytic cycles to investigate the stability and reusability of the MOF photocatalysts. Samples were recovered through isolation by centrifugation, washed with copious amounts of MeOH, and activated under vacuum after each cycle. The numbers of M(III)-catecholato sites were also redetermined for each cycle to obtain accurate turnover numbers. The catalytic activities of

both MOFs were relatively unchanged over the three cycles (Fig. 3a, Fig. S4). However, a small amount of M(III) ions leached from the MOFs based on an decreasing M(III)/Zr(IV) ratio as determined by ICP-MS (Table S1) after each reaction. The photocatalysis results in Fig. 3a were reproducible based on findings from three independent samples (Fig. S5). Quantum yields for both UiO-66-M(III)CAT MOFs were obtained under monochromatic light irradiation using a band-pass optical filter (450 nm). UiO-66-CrCAT showed a higher quantum yield value ($1.83 \pm 0.16\%$) when compared to UiO-66-GaCAT ($1.17 \pm 0.11\%$). The Fe(III) metalated UiO-66-CAT was also prepared following a previous report.¹⁹ Under identical photocatalytic conditions, UiO-66-FeCAT (Zr:Fe = 1:0.27, ~80% of catbdc was metalated) produced little HCOOH ($1.47 \mu\text{moles}$, Table S2). The redox potential for Fe(III) is not suitable (0.77 V vs. SHE) for CO_2 reduction (unlike Cr(III) and Ga(III)), and hence this MOF derivative is not a suitable photocatalyst.

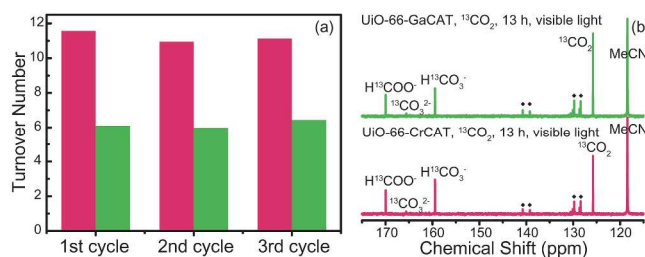


Fig. 3. (a) Photocatalytic ability of UiO-66-CrCAT (red) and UiO-66-GaCAT (green) over three cycles (6 h/cycle); (b) ^{13}C liquid NMR spectra of photocatalytic CO_2 reduction by UiO-66-CrCAT (red) and UiO-66-GaCAT (green) after 13 h reaction.

The use of UiO-66-CAT prior to metalation as a photocatalyst did not produce HCOOH as measured by GC-MS (and ^{13}C NMR, see below). This rules out the catbdc ligand alone or the Zr_6 SBU clusters as the catalytic sites for reduction. UiO-66-CAT is not suited to accept photo-generated electrons from the catbdc ligand because the redox potential of Zr_6 SBU is higher than the LUMO of bdc linkers.^{25,31} The control reactions with UiO-66-CAT support that photocatalytic reduction of CO_2 is dependent on the M(III)-catecholato species in the MOF.

^{13}C liquid NMR spectrum was acquired using a ^{13}C isotope of CO_2 as a substrate, in order to confirm the origin of the carbon source for HCOOH upon photocatalysis with MOFs. The photocatalytic conditions used were identical to those described above except for the use of CD_3CN and with the reactor purged by $^{13}\text{CO}_2$ (~99% of ^{13}C) before light irradiation. After 13 h, the reaction mixture was transferred to an NMR tube without further treatment (i.e. no H_2SO_4). Reference solutions were prepared for H^{13}COOH and the results are shown in Fig. S5. The chemical shift for H^{13}COOH in CD_3CN was found at 162.73 ppm; however, this value was increased to 169.86 ppm in 4:1 $\text{CD}_3\text{CN}:\text{TEOA}$ solution due to deprotonation to $\text{H}^{13}\text{COO}^-$.^{30,32} In addition, it was expected that $^{13}\text{CO}_2$ could form $^{13}\text{CO}_3^{2-}$ and $\text{H}^{13}\text{CO}_3^-$ under the alkaline reaction conditions.³³

Several signals corresponding to $\text{H}^{13}\text{COO}^-$, $^{13}\text{CO}_2$, $^{13}\text{CO}_3^{2-}$, $\text{H}^{13}\text{CO}_3^-$, MeCN, and other small signals were found in ^{13}C NMR spectrum of product solution from both UiO-66-M(III)CAT reaction mixtures (Fig. 3b). Small signals were also observed from BNAH isotopes and these signals were also found in reference solution of $\text{CD}_3\text{CN}:\text{TEOA}$ with BNAH. Moreover, ^{13}C NMR for experiment using unlabeled $^{12}\text{CO}_2$,

instead of $^{13}\text{CO}_2$, was also carried out but no $\text{H}^{13}\text{COO}^-$ peak was detected (Fig. S6). The strong resonance peaks observed for $\text{H}^{13}\text{COO}^-$ indicate that the carbon source is primarily from CO_2 gas, not from decomposition of the MOFs.

MOFs containing M(III)-monocatecholato species after three cycles of photocatalysis were characterized using PXRD and SEM measurements to evaluate their structural and chemical integrity, which is another essential characteristic feature for an optimal photocatalyst. Both UiO-66-CrCAT and UiO-66-GaCAT maintained their crystalline structure over 18 h of exposure to the photocatalysis conditions (although some Cr and Ga leaching was observed, Table S1). Crystal size, morphology, and surface (Fig. S7) remained intact throughout photocatalysis, indicating the SBUs and organic linkers were not significantly degraded. Furthermore, the crystallinity was maintained in both UiO-66 derivatives during 1 week of light irradiation (Fig. S8). Lastly, XPS results show that both Cr and Ga remained in their trivalent oxidation states after photocatalysis (Fig. S9). However, the BET specific surface area of both UiO-66-CrCAT and UiO-66-GaCAT was slightly decreased after three cycles of photocatalysis, which indicates that some pores were blocked or collapse occurred during intense photoradiation; however, the surface areas indicated that the MOFs were still highly porous (Fig. S10). The data suggest that isolated M(III)-monocatecholato functionalities residing in MOFs acted as independent photocatalytic sites.

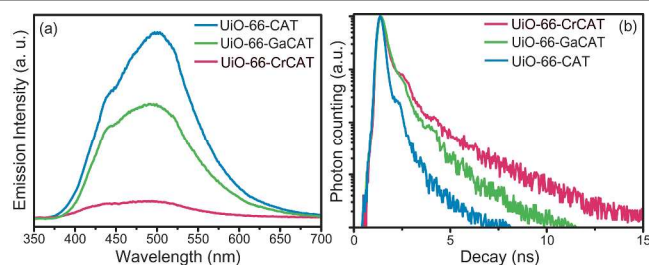


Fig. 4. (a) Photoluminescence (PL) spectra of UiO-66-CAT series; (b) Solid-state fluorescent lifetime of excited states by time-correlated single photon counting (TCSPC) method.

Photoluminescence (PL) spectroscopy was carried out to characterize the charge transfer between catbdc and M(III) in UiO-66-M(III)CAT. As shown in Fig. 4a, the emission intensity of UiO-66-CAT is significantly reduced after metalation. This indicates that the recombination rate of photogenerated electron-hole pairs in the organic linkers was markedly decreased upon metalation, suggesting that charges were transferred to other sites in the MOFs. The decreases in emission intensity were different for UiO-66-CrCAT and UiO-66-GaCAT, suggesting that the metalated catbdc centers are the acceptors. This indicates that LMCT occurred between the catechol units and metal elements, as expected.³⁴ In particular, UiO-66-CrCAT quenched ~80% of the photo-generated charges in catbdc and this value is close to the ratio of Cr-bound catechol ligands in UiO-66-CrCAT. This increased electron transfer ability may explain the greater photocatalytic efficiency of UiO-66-CrCAT over UiO-66-GaCAT. The charge accepting ability of these trivalent ions are expected to be quite different due to differences in their outer shell electronic configurations (Cr(III) $[\text{Ar}]3d^3$ versus Ga(III) $[\text{Ar}]3d^{10}$).^{35,36} More energy is needed to accept electrons for Ga-species because the

redox potential of Ga(III)/Ga(II) is higher than Cr(III)/Cr(II). This is consistent with the $\sim 2\times$ higher turnover number demonstrated by UiO-66-CrCAT when compared to UiO-66-GaCAT. Moreover, lifetimes of solid-state fluorescence, obtained by time-correlated single photon counting (TCSPC), confirmed that charge transfer between catbdc ligand and metals occurred through a LMCT mechanism (Fig. 4b, see details in ESI). This result also suggests that UiO-66-CrCAT holds charges longer than UiO-66-GaCAT for possible electron transfer to CO_2 .

The catalytic ability with respect to turnover frequency (TOF, h^{-1}) of the UiO-66-M(III)CAT MOFs were compared to other catalytic systems (Tables S4-S6). The turnover frequency of UiO-66-CrCAT (1.87 h^{-1}) and UiO-66-GaCAT (1.02 h^{-1}) were substantially greater than many reported heterogeneous systems that produce formate or formic acid as the photoproduct (Table S4). In contrast, the TOF of these MOFs was lower than that of many homogeneous systems reported (Table S5); however, the MOFs have the advantage of being both recyclable and not requiring an exogenous photosensitizer, which are both shortcomings of the homogeneous systems reported. Therefore, the MOF catalysts reported here balance the advantages of existing heterogeneous and homogeneous photoreduction catalysts. In addition, the UiO-66-M(III)CAT MOFs showed good photocatalytic ability when compared to other MOF-based CO_2 reduction photocatalytic systems studied to date (Table S6). When compared to other MOFs that do not use an added exogenous photosensitizer, TOF values for the UiO-66-M(III)CAT MOFs are noticeably better than previously studied MOFs that generate formate from CO_2 .

New MOF CO_2 reduction photocatalysts were prepared from isolated monocatecholato metal sites that were active under visible light irradiation. The catbdc²⁻ substituted UiO-66-CAT generated electron-hole pairs under visible light without light sensitizers. Both UiO-66-M(III)CAT-derivatives reduced CO_2 to HCOOH with the aid of BNAH and TEOA. The Cr-derivative showed better efficiency than Ga due to its open shell electronic structure. Further optimization of these systems may produce materials with the advantages of heterogeneous systems, but with activities comparable to homogeneous reduction catalysts.

These experiments were supported by a grant from the Department of Energy, Office of Basic Energy Sciences, Division of Materials Science and Engineering under Award No. DE-FG02-08ER46519 (Y.L., H.F., S.M.C.). Additional support for XPS, PL, and TCSPC studies were provided to S.K. and J.K.K. by the Korea Center for Artificial Photosynthesis (2009-0093881).

Notes and references

^a Department of Chemistry and Biochemistry, University of California, San Diego, La Jolla, California 92093, United States. E-mail: scohen@ucsd.edu

^b Graduate School of EEWS, Korea Advanced Institute of Science and Technology (KAIST), Daejeon, 305-701, Republic of Korea.

† Electronic Supplementary Information (ESI) available: experimental, supplementary figures and tables, details on comparison study]. See DOI: 10.1039/b000000x/

- N. S. Lewis and D. G. Nocera, *Proc. Natl. Acad. Sci. USA*, 2006, **103**, 15729-15735.
- G. Centi, E. A. Quadrelli and S. Perathoner, *Energy & Environ. Sci.*, 2013, **6**, 1711-1731.

- B. Kumar et al., *Annu. Rev. Phys. Chem.*, 2012, **63**, 541-569.
- P. D. Tran, L. H. Wong, J. Barber and J. S. C. Loo, *Energy & Environ. Sci.*, 2012, **5**, 5902-5918.
- Y. Izumi, *Coord. Chem. Rev.*, 2013, **257**, 171-186.
- T. Sakakura, J. C. Choi and H. Yasuda, *Chem. Rev.*, 2007, **107**, 2365-2387.
- C. Costentin, M. Robert and J. M. Saveant, *Chem. Soc. Rev.*, 2013, **42**, 2423-2436.
- W.-H. Wang et al., *Energy & Environ. Sci.*, 2012, **5**, 7923-7926.
- Y. Qu and X. Duan, *Chem. Soc. Rev.*, 2013, **42**, 2568-2580.
- A. J. Morris, G. J. Meyer and E. Fujita, *Acc. Chem. Res.*, 2009, **42**, 1983-1994.
- C. Wang, Z. Xie, K. E. deKrafft and W. Lin, *J. Am. Chem. Soc.*, 2011, **133**, 13445-13454.
- Y. Fu et al., *Angew. Chem. Int. Ed.*, 2012, **51**, 3364-3367.
- Y. Horiuchi et al., *J. Phys. Chem. C*, 2012, **116**, 20848-20853.
- T. Toyao et al., *Catal. Sci. Technol.*, 2013, **3**, 2092-2099.
- Y. Lee, S. Kim, J. K. Kang and S. M. Cohen, *Chem. Commun.*, 2015, **51**, 5735-5738.
- L. Li et al., *Chem. Sci.*, 2014, **5**, 3808-3813.
- M. Kim, J. F. Cahill, H. Fei, K. A. Prather and S. M. Cohen, *J. Am. Chem. Soc.*, 2012, **134**, 18082-18088.
- S. Pullen, H. Fei, A. Orthaber, S. M. Cohen and S. Ott, *J. Am. Chem. Soc.*, 2013, **135**, 16997-17003.
- H. Fei et al., *J. Am. Chem. Soc.*, 2014, **136**, 4965-4973.
- H. Fei, S. Pullen, A. Wagner, S. Ott and S. M. Cohen, *Chem. Commun.*, 2015, **51**, 66-69.
- C. H. Hendon et al., *J. Am. Chem. Soc.*, 2013, **135**, 10942-10945.
- H. Q. Pham et al., *J. Phys. Chem. C*, 2014, **118**, 4567-4577.
- L. Shen et al., *Phys. Chem. Chem. Phys.*, 2014, **17**, 117-121.
- D. E. Wheeler and J. K. McCusker, *Inorg. Chem.*, 1998, **37**, 2296-2307.
- A. J. Simaan et al., *Chem. Eur. J.*, 2005, **11**, 1779-1793.
- S. C. Ghosh, M. C. Biesinger, R. R. LaPierre and P. Kruse, *J. Appl. Phys.*, 2007, **101**, 114322.
- M. C. Biesinger et al., *Appl. Surf. Sci.*, 2011, **257**, 2717-2730.
- C. Pac et al., *J. Am. Chem. Soc.*, 1981, **103**, 6495-6497.
- X. Q. Zhu et al., *Chem. Eur. J.*, 2003, **9**, 3937-3945.
- Y. Tamaki, T. Morimoto, K. Koike and O. Ishitani, *Proc. Natl. Acad. Sci. USA*, 2012, **109**, 15673-15678.
- W. Liang, R. Babarao and D. M. D'Alessandro, *Inorg. Chem.*, 2013, **52**, 12878-12880.
- T. Reda, C. M. Plugge, N. J. Abram and J. Hirst, *Proc. Natl. Acad. Sci. USA*, 2008, **105**, 10654-10658.
- H. Takeda, H. Koizumi, K. Okamoto and O. Ishitani, *Chem. Commun.*, 2014, **50**, 1491-1493.
- G. Zhang, G. Kim and W. Choi, *Energy & Environ. Sci.*, 2014, **7**, 954-967.
- A. Hameed, M. A. Gondal and Z. H. Yamani, *Catal. Commun.*, 2004, **5**, 715-719.
- F. C. de Oliveira et al., *Chem. Phys. Lett.*, 2013, **585**, 84-88.