

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Journal Name

COMMUNICATION

Synthesis and Luminescence Modulation of Pyrazine-Based Gold(III) Pincer Complexes†

 Received 00th January 20xx,
 Accepted 00th January 20xx

 Julio Fernandez-Cestau,^a Benoît Bertrand,^a Maria Blaya,^a Garth A. Jones, Thomas J. Penfold*^b and Manfred Bochmann*^a

DOI: 10.1039/x0xx00000x

www.rsc.org/

The first examples of pyrazine-based gold(III) pincer complexes are reported; their intense photoemissions can be modified by protonation, N-alkylation or metal ions, without the need for altering the ligand framework. Emissions shift from red (77 K) to blue (298 K) due to thermally activated delayed fluorescence (TADF).

Gold(III) complexes with bis-cyclometallated ligands are characterized by their chemical stability and resistance to reduction. The ligand scaffold based on 2,6-diphenylpyridine¹ has proved particularly useful in gold(III) chemistry and forms (C^{^N^C})AuX pincer complexes of type **A** (Chart I). Such complexes have proved to be highly versatile and, in combination with strong carbon-based σ -donor ligands (e.g. X = N-heterocyclic carbene, alkynyl), display interesting photophysical^{2–4} properties. This C^{^N^C} ligand system has also been successful in stabilizing types of compounds that have frequently been invoked as unstable intermediates in catalytic cycles or postulated in computer modelling of catalytic processes, such as gold(III) hydrido, alkene, CO and peroxy complexes.⁵

Photoemissive materials as components of electronic devices such as flat screen displays should ideally be capable of covering the whole range of the visible spectrum. Such changes in emission colours can be induced by suitable modification of the ligand framework. For (C^{^N^C})Au(III) complexes a widely applied strategy for modulating the photoluminescence (PL) response and widening the range of emission wavelengths has been the introduction of electron donating or withdrawing substituents in the 4-position of the pyridine moiety.^{3,4} There are however limitations in this

approach: Firstly, the synthesis of C^{^N^C} gold complexes involves two C-H activation steps, each of which is sensitive to the ligand structure and needs to be optimized for each new ligand; secondly, the modulation of electronic characteristics of the central pyridine moiety that can be achieved by inductive or mesomeric substituent effects is limited.

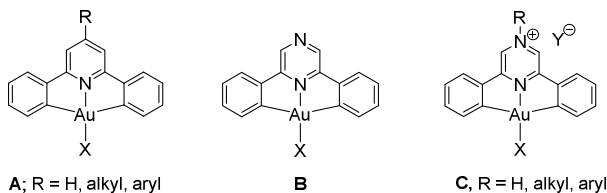


Chart I

Rather more profound electronic changes in C^{^N^C} ligands can be introduced by replacing the central pyridine ring by other heterocycles, such as pyrazine, to give compounds of type **B**. The lowest-energy π - π^* transition in pyrazine is about 0.95 eV smaller than in pyridine;^{6,7} pyrazine ligands are therefore much better electron acceptors and are likely to produce a red-shift of their UV and photoemission wavelengths. In addition, pyrazine complexes **B** offer scope for further derivatisation by protonation or quaternisation of the non-coordinating N atom, to give salts of type **C**.

Complexes of aryl-substituted pyrazines and quinoxalines are of course well-known for iridium(III) and platinum(II), since for these metals they are readily accessible by direct cyclometallation of the neutral ligand precursors by noble metal halides.⁸ By contrast, related gold(III) complexes have until now been inaccessible since the usual methods employed for the synthesis of pyridine complexes **A** fail for the analogous pyrazine derivatives. Here we report the first examples of cyclometallated Au(III) pyrazine complexes and the facile modification of their photoluminescence properties.

The mercuriation of the pro-ligand 2,6-bis(4'-t-BuC₆H₄)₂pz (pz = pyrazine) requires forcing conditions but proceeds using Hg(tfa)₂ in Htfa (tfa = CF₃CO₂) to give (C^{^N^Pz^C})HgCl₂·2Htfa (**1**). Transmetalation with KAuC₄ affords (C^{^N^Pz^C})AuCl (**2**) as a

^a School of Chemistry, University of East Anglia, Norwich, NR4 7TJ, UK. E-mail: m.bochmann@uea.ac.uk

^b Department of Chemistry, Newcastle University, Newcastle upon Tyne, NE1 7RU, UK. E-mail: Tom.Penfold@newcastle.ac.uk

† This work was supported by the European Research Council. M. B. is an ERC Advanced Investigator Award holder (grant no. 338944-GOCAT). Electronic Supplementary Information (ESI) available: Details of synthesis and characterization, X-ray crystallography, photophysical properties, theoretical calculations. See DOI: 10.1039/x0xx00000x

COMMUNICATION


yellow crystalline powder in good yield (Scheme 1). Substitution of the chloride ligand in **2** with KCN gives the cyanide complex **3**, while treatment with dimethylpyrazole affords the pyrazolato complex **4**. The reaction with AgC≡CR in CH₂Cl₂ affords the acetylides (C^{AN}^{PV}^C)AuC≡CR (**5a**, R = Ph; **5b**, R = Bu^t) in essentially quantitative yield.

Pyrazine is only weakly basic (pK_a 1.30, vs. 5.20 of pyridine).⁹ However, protonation of **2** by HBF₄·OEt₂ generated the corresponding salt **6**. Remarkably, the protonation by dry HCl in Et₂O proved to be reversible, and evaporation of the solvent from the HCl adduct regenerated neutral **2**. The alkylation of the non-coordinating pyrazine N-atom was achieved using Meerwein's salt [Me₃O]BF₄ to give **7** (Scheme 1) as a deep-red crystalline solid in 87 % yield. The molecular structures¹⁰ of **2**, **4**, **5a** and **5b** were determined by X-ray diffraction.[‡] The interatomic distances and angles are as expected for square-planar pincer complexes of this type (see S.I. for details).

All the complexes show moderate to intense luminescence in the solid state and in solution (for a detailed summary see the Supporting Information, Tables S2 and S3). Both the UV-vis spectra and the PL bands are characterized by the vibronic progression of the C^{AN}^{PV}^C pincer. As expected on the basis of the lower π-π* energy gap of the pyrazine compounds, the

bands are red-shifted by about 40–50 nm compared with their C^{AN}^{PV}^C analogues (see Figure S22).

Whereas in the case of diphenylpyridine-based complexes of type **A** strongly σ-donating ligands (such as aryls, acetylides or N-heterocyclic carbenes^{3,4}) are required to raise the d-orbital energy of Au(III) and increase the ³LLCT contribution to the emissive state, the pyrazine derivatives **2-7** reported here are emissive even if ligands X are weaker heteroatom donors. This is best exemplified by the chlorides: whereas (C^{AN}^{PV}^C)AuCl is non-emissive at room temperature,¹ complex **2** shows noticeable naked eye emission in fluid media (CH₂Cl₂ or 2-MeTHF) at 298 K that becomes very intense at 77 K (Figure S20). Similarly, the pyrazolato complex **4** is brightly emissive in the solid state or in fluid media at 298 K, while under identical conditions, the C^{AN}^{PV}^C analogue is only weakly emissive.¹¹ The pyrazine ligand framework of type **B** therefore significantly widens the range of photoemissive metal-ligand combinations. In solution, the neutral complexes **2-5** all emit in the yellow to green region of the spectrum, mainly due to a triplet state based on the diphenylpyrazine pincer ligand. The excited state lifetimes show biexponential decay, with the fast component in the range of 5–20 ns.

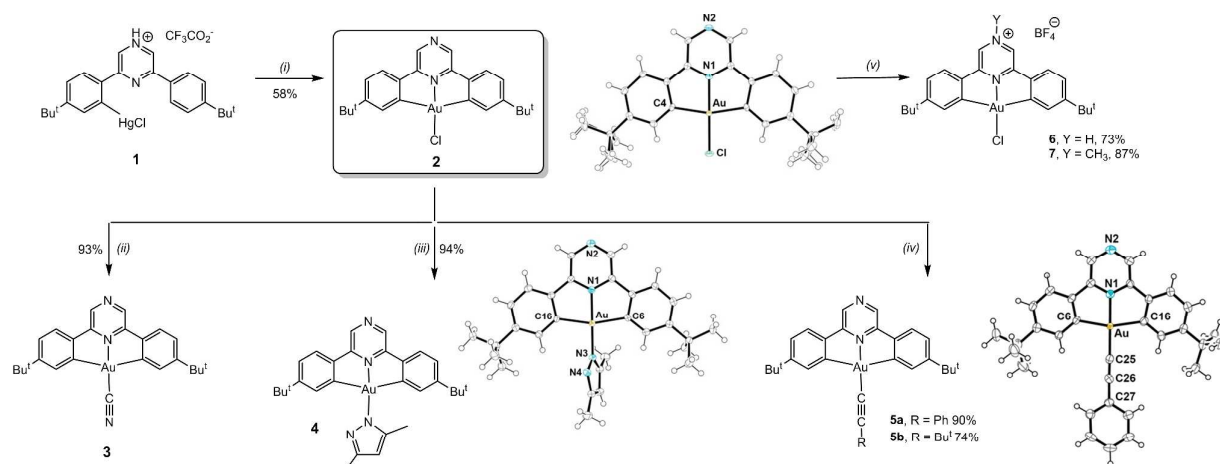

Scheme 1. Conditions: (i) KAuCl₄, CH₃CN/H₂O 1:1, reflux 72h. (ii) KCN, CH₂Cl₂, 20 °C, 24 h. (iii) KO^tBu, 3,5-dimethylpyrazole, toluene, 20 °C, 6 h. (iv) AgC≡CR, CH₂Cl₂, 20 °C, 24 h. (v) HBF₄·Et₂O, Et₂O, 20 °C, 30 min. (**6**), or [Me₃O]BF₄, toluene/1,2-C₆H₄F₂ (5:1 v/v), 12 h. (**7**). Molecular structures [selected bond distances (Å) and angles (°)]: **2:** Au-N1 1.976(4), Au-Cl 2.2653(12), Au-C4 2.078; N1-Au-C4 81.36(9), C4-Au-Cl 98.64(9), C4-Au-C4' 162.71(18), N1-Au-Cl 180. **4:** Au-N1 1.979(2), Au-C6 2.080(3), Au-C16 2.073(3), Au-N3 1.991(2); C6-Au-N1 81.39(10), C16-Au-N1 81.32(11), C6-Au-N3 98.88(10), C16-Au-N3 98.38(11), N1-Au-N3 178.33(9). **5a:** Au-N1 1.997(5), Au-C6 2.070(6), Au-C16 2.083(7), Au-C25 1.979(7), C25-C26 1.199(9); N1-Au-C6 80.4(2), N1-Au-C16 81.2(2), C6-Au-C25 99.3(3), C16-Au-C25 99.0(3), C6-Au-C16 161.6(3), Au-C25-C26 175.9(6), C25-C26-C27 177.4(7).

COMMUNICATION

At 77 K the emissions of **2**, both in the solid state ($\lambda_{\text{em}}^{\text{max}} = 563$ nm) and in solution ($\lambda_{\text{em}}^{\text{max}} = 532$ nm), agree reasonably well with the value calculated for a $T^1 \rightarrow S^0$ transition ($\lambda_{\text{em}}^{\text{calc}} = 541$ nm).⁵ However, at 298 K the emission shows a significant blue-shift, to 482 nm, a feature that is even more pronounced on addition of acid (*vide infra*).

One of the most important challenges in the design of photoluminescent devices is the ability to modulate the energy of the emitted light. In the pyrazine ligand system, the easiest way to achieve this is by making use of the non-coordinating nitrogen of the pyrazine ring. Strong Brønsted and Lewis acids do indeed produce dramatic changes in PL response. In order to eliminate any possible anion effects, initial protonation studies were carried out using the solid Brønsted acid $[\text{H}(\text{OEt}_2)_2][\text{H}_2\text{N}\{\text{B}(\text{C}_6\text{F}_5)_3\}_2]$ ("HNB₂"). As shown in Figure 1a, protonating **2** with this acid results in a blue-shift compared with the neutral complex, from 482 to 458 nm. On the other hand, at 77 K the emissions of both the neutral and protonated compounds are remarkable similar (as expected since both the HOMO and LUMO are based on the pyrazine ligand and are equally affected by protonation) and the emission is due to an intra-ligand charge transfer (³ILCT) process.

The temperature-dependence of the photoluminescence response is in agreement with a TADF process,¹³ where the energy difference between the T^1 and S^1 excited states is sufficiently small to allow thermally driven repopulation of the S^1 state from the T^1 state, with the faster decay occurring via the $S^1 \rightarrow S^0$ transition. In agreement with this mechanism, the quantum yields for the protonated pyrazine systems are about an order of magnitude higher than those of the neutral complexes. Photoemissions via a TADF mechanism are common for copper(I),¹⁴ but have not been previously reported for Au(III).

The alkynyl complexes **5a** and **5b** show similar behaviour: the gradual addition of triflic acid results in the progressive growth of a blue emission ($\lambda_{\text{em}}^{\text{max}} = 450$ nm for **5a**, Fig. 1b). Emissions involve a mixture of states, with both blue and green components, which combine to appear white.

The same effect can be achieved with the Lewis acid $\text{B}(\text{C}_6\text{F}_5)_3$. In this case the high energy component appears at slightly lower energy ($\lambda_{\text{em}}^{\text{max}} = 481$ nm), to give a more pronounced blue effect.

Whereas in the case of the chloride **2** both HOMO and LUMO were based on the pincer ligand, for **5a** the excitation involves metal-perturbed ligand-to-ligand $\pi(\text{C}\equiv\text{CPh}) \rightarrow \pi^*(\text{C}^{\wedge}\text{N}^{\text{Pz}}\text{A}^{\text{C}})$ charge transfer (³LLCT, also involving HOMO-2). The effect of adding H^+ or $\text{B}(\text{C}_6\text{F}_5)_3$ to the pyrazine N-atom is therefore pronounced. DFT calculations predict a strong red shift on

forming the **5a-H⁺** cation since on protonation the HOMO-LUMO gap is reduced (e.g. calculated HOMO-LUMO difference for **5a** = 5.963 eV, compared to 4.878 eV after H^+ addition). In agreement with this, solutions of **5a**· $\text{B}(\text{C}_6\text{F}_5)_3$ at 77 K display an intense emission at 569 nm (Figure S26) which is gradually deactivated on warming, while at the same time a high energy component increases, resulting in the blue emission at $\lambda_{\text{em}}^{\text{max}} = 481$ nm at 298 K. As can be seen (Fig. S29), these reactions also occur in the solid state.

Different metal ions also lead to distinctive modulations of the PL emission, arising from a mixture of states. The addition of ZnCl_2 , CdCl_2 and HgCl_2 (1:1 molar ratio) results in white, turquoise and light green emissions, respectively (Fig. 1c). The gradual addition of ZnCl_2 to a solution of the complex **5a** in 2-MeTHF, results in the activation of the blue TADF component at the expense of the green phosphorescence (see Fig. S27). Cooling to 77 K recovers the phosphorescent emission.

The addition of AgOTf or CuOTf also enhances the emission via the TADF mechanism (see Fig. 1d for Ag^+ and Fig. S28 for Cu^+). Freezing 2-MeTHF solutions of **5a**/ AgOTf to 77 K reveals the

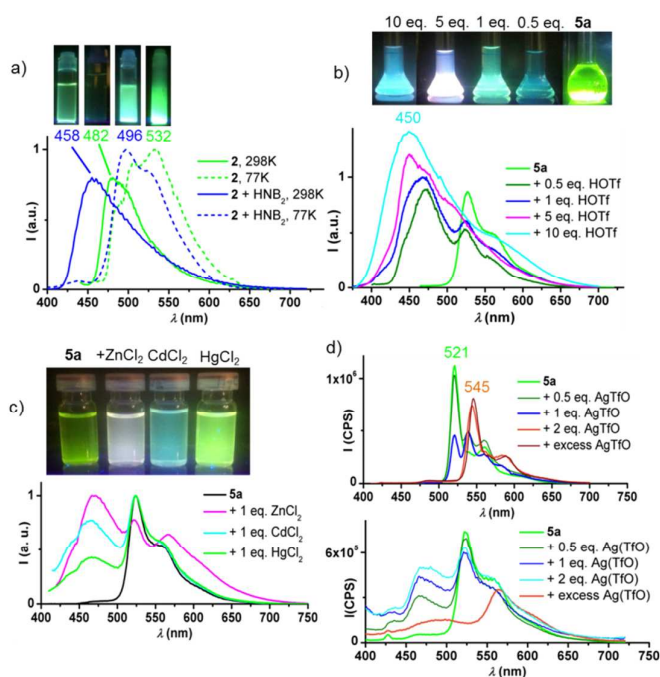


Fig. 1. (a) PL of **2** (CH_2Cl_2 , 1×10^{-4} M) in the absence and presence of two equivalents of $[\text{H}(\text{OEt}_2)_2][\text{H}_2\text{N}\{\text{B}(\text{C}_6\text{F}_5)_3\}_2]$ (HNB₂) at 298 and 77 K. (b) PL response of **5a** (CH_2Cl_2 , 1×10^{-4} M) to the addition of HOTf at 298 K. (c) PL of mixtures of **5a** (CH_2Cl_2 , 1×10^{-4} M) to the addition of MCl_2 ($\text{M} = \text{Zn}, \text{Cd}, \text{Hg}$) in THFMe-2 ($[\text{5a}] = 10^{-4}$ M) at 298 K. (d) PL response of **5a** (THFMe-2, 5×10^{-4} M) to the addition of AgTfO at 298 and 77 K.

presence of two different systems; complex **5a** ($\lambda_{\text{em}}^{\text{max}} = 521$ nm), and a second complex characterized by a band with maximum at 545 nm. The mixture of **5a** with two equivalents and with an excess of Ag^+ both show the same emission band, while 1 equivalent of Ag^+ gives two bands of about equal intensity. For these reasons, we tentatively suggest the formation of an aggregate of **5a** with two Ag^+ ions (e.g. coordination of two Ag^+ ions to the $\text{C}\equiv\text{C}$ bond and the pyrazine-N atom may be envisaged).

The N-methylated complex **7** mirrors the behaviour of the H^+ adducts and shows blue emission in solution ($\lambda_{\text{em}}^{\text{max}} = 460$ nm) but is dark-red in the solid state ($\lambda_{\text{em}} = 623_{\text{max}}, 680_{\text{sh}}$).

In summary, cyclometallated gold(III) pincer complexes based on pyrazine provide a new family of photoluminescent compounds which allow facile modulation of the emission characteristics by protonation, alkylation, Lewis acids or metal ions, without the need for modifying the pincer ligand framework. The modulation arises from the coexistence of high energy TADF and ^3IL ($\text{C}^{\wedge}\text{N}^{\text{pz}}\wedge\text{C}$) / $^3\text{LLCT}$ ($\text{X}\rightarrow\text{C}^{\wedge}\text{N}^{\text{pz}}\wedge\text{C}$) transitions.

Notes and references

‡ Crystallographic data for **2**, **4**, **5a** and **5b** are deposited as CCDC 1417819-1417822. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif

§ In the solid state at room temperature, complex **2** is non-emissive, most probably due to close intermolecular interactions in the crystal lattice which quench the luminescence. This notion is supported by the observed higher solid-state emission intensity of **5b** ($\lambda_{\text{max}} = 523$ nm, $\phi = 8.3$) compared to **5a** ($\lambda_{\text{max}} = 523$ nm, $\phi = 4.5$); the crystal packing shows that for **5b** intermolecular π -stacking is disfavoured on steric grounds. In solution at 298 K the PL intensities of **5a** ($\lambda_{\text{max}} = 526$ nm, $\phi = 0.462$) and **5b** ($\lambda_{\text{max}} = 526$ nm, $\phi = 0.512$) are essentially identical (see Fig. S19).

- 1 K.-H. Wong, K.-K. Cheung, M. C.-W. Chan, and C.-M. Che, *Organometallics* 1998, **17**, 3505.
- 2 Reviews: (a) C. Bronner and O. S. Wenger, *Dalton Trans.* 2011, **40**, 12409. (b) V. W.-W. Yam, K. M. C. Wong, *Chem. Commun.* 2011, **47**, 11579.
- 3 (a) V. K.-M. Au, D. P.-K. Tsang, Y.-C. Wong, M.-Y. Chan, V. W.-W. Yam, *J. Organomet. Chem.* 2015, **792**, 109; (b) M.-C. Tang, D. P.-K. Tsang, Y.-C. Wong, M.-Y. Chan, K. M.-C. Wong, V. W.-W. Yam, *J. Am. Chem. Soc.* 2014, **136**, 17861 and cited refs.
- 4 (a) G. Cheng, K. T. Chan, W.-P. To and C.-M. Che, *Adv. Mater.* 2014, **26**, 2540. (b) W.-P. To, K. T. Chan, G. S. M. Tong, C. S. Ma, W.-M. Kwok, X. G. Guan, K. H. Low and C.-M. Che, *Angew. Chem. Int. Ed.* 2013, **52**, 6648. (c) W.-P. To, G. S.-M. Tong, W. Lu, C.-S. Ma, J. Liu, A. L.-F. Chow, C.-M. Che, *Angew. Chem. Int. Ed.* 2012, **51**, 2654.
- 5 (a) D.-A. Roşca, D. A. Smith, D. L. Hughes, M. Bochmann, *Angew. Chem. Int. Ed.* 2012, **51**, 10643. (b) N. Savjani, D.-A. Roşca, M. Schormann, M. Bochmann, *Angew. Chem. Int. Ed.* 2013, **52**, 874. (c) D.-A. Roşca, J. A. Wright, D. L. Hughes, M. Bochmann, *Nat. Commun.* 2013, **4**, 2167. (d) D.-A. Roşca, J. Fernandez-Cestau, J. Morris, J. A. Wright, M. Bochmann, *Sci. Adv.* 2015, in press.
- 6 C. Walker, M. H. Palmer, A. Hopkirk, *Chem. Phys.* 1989, **141**, 365.
- 7 I. C. Walker, M. H. Palmer, *Chem. Phys.* 1991, **153**, 169.
- 8 See for example: (a) S. H. Wu, S. E. Burkhardt, J. Yao, Y. W. Zhong, H. D. Abruña, *Inorg. Chem.* 2011, **50**, 3959. (b) V. N. Kozhevnikov, M. C. Durrant, J. A. G. Williams, *Inorg. Chem.* 2011, **50**, 6304. (c) S. Culham, P.-H. Lanoë, V. L. Whittle, M. C. Durrant, J. A. G. Williams and V. N. Kozhevnikov, *Inorg. Chem.* 2013, **52**, 10992. (d) P.-H. Lané, C.-M. Tong, R. W. Harrington, M. R. Probert, W. Clegg, J. A. G. Williams and V. N. Kozhevnikov, *Chem. Commun.*, 2014, **50**, 6831.
- 9 H. J. Soscún Machado, A. Hinchliffe, *J. Mol. Struct. (Theochem)* 1995, **339**, 255.
- 10 S. J. Coles, P. Gale, *Chem. Sci.* 2012, **3**, 683.
- 11 D.-A. Roşca, D. A. Smith, M. Bochmann, *Chem. Commun.* 2012, **48**, 7247.
- 12 S. J. Lancaster, A. Rodríguez, A. Lara-Sanchez, M. D. Hannant, D. A. Walker, D. L. Hughes, M. Bochmann, *Organometallics* 2002, **21**, 451.
- 13 Reviews: (a) H. Yersin, A. F. Rausch, R. Czerwieniec, T. Hofbeck, T. Fischer, *Coord. Chem. Rev.* 2011, **255**, 2622. (b) Y. Tao, K. Yuan, T. Chen, P. Xu, H.-H. Li, R. F. Chen, C. Zheng, L. Zhang, W. Huang, *Adv. Mater.* 2014, **26**, 7931.
- 14 (a) M. J. Leitzl, V. Krylova, P. I. Djurovich, M. E. Thompson, H. Yersin, *J. Am. Chem. Soc.* 2014, **136**, 16032. (b) V. A. Krylova, P. I. Djurovich, B. L. Conley, R. Haiges, M. T. Whited, T. J. Williams, M. E. Thompson, *Chem. Commun.* 2014, **50**, 7176. (c) R. Marion, F. Sguerra, F. Di Meo, E. Sauvageot, J.-F. Lohier, R. Daniellou, J.-L. Renaud, M. Linares, M. Hamel, S. Gaillard, *Inorg. Chem.* 2014, **53**, 9181.