



Phosphonium-Containing Diblock Copolymers from Living Anionic Polymerization of 4-Diphenylphosphino Styrene

Journal:	<i>ChemComm</i>
Manuscript ID	CC-COM-10-2015-008699.R1
Article Type:	Communication
Date Submitted by the Author:	13-Nov-2015
Complete List of Authors:	Schultz, Alison; Virginia Polytechnic Institute and State University, Chemistry Fahs, Gregory; Virginia Tech, Chemistry Jangu, Chainika; Virginia Polytechnic Institute and State University, Macromolecules and Interface Institute Chen, Mingtao; Virginia Polytechnic Institute and State University Moore, Robert; Virginia Tech, Chemistry Long, Timothy; Virginia Polytechnic Institute and State University, Department of Chemistry



Journal Name

COMMUNICATION

Phosponium-Containing Diblock Copolymers from Living Anionic Polymerization of 4-Diphenylphosphino Styrene

Alison R. Schultz, Gregory B. Fahs, Chainika Jangu, Mingtao Chen, Robert B. Moore, and Timothy E. Long*

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Living anionic polymerization of 4-diphenylphosphino styrene (DPPS) achieved well-defined homopolymers, poly(DPPS-*b*-S) styrenic block copolymers, and poly(*l*-*b*-DPPS) diene-based diblock copolymers with predictable molecular weights and narrow polydispersities. *In situ* FTIR spectroscopy monitored the anionic polymerization of DPPS and tracked monomer consumption for kinetic analysis. Post-alkylation enabled controlled placement of phosphonium functionality in poly(*l*-*b*-DPPS) diblock copolymers, producing well-defined phosphonium-containing block copolymers with low degrees of compositional heterogeneity. Incorporating phosphonium charge disrupted the lamellar bulk morphology of the neutral diblock precursor and provided morphologies with interdigitated packing of alkyl chains on the phosphonium cation.

Styrenic block copolymers receive continued attention for the production of thermally stable compositions with tunable physical and mechanical properties, impacting technologies ranging from high performance adhesives^{1,2} and durable coatings^{3,4} to biomaterials^{5,6} and medical devices.⁷⁻¹⁰ Immiscible block sequences promote microphase separation, facilitating self-assembly into various nanostructured compositions with tailored sequence lengths and volume fractions, molecular weight distribution, and chemical compositions. Tuning structural composition and nanostructured morphologies engineers a vast array of styrenic block copolymers and enables predictable viscoelastic properties for targeted applications. Incorporating ion-containing extended sequences imparts electrostatic interactions for enhancing microphase separation and thermomechanical properties, and provides electromechanical properties suitable for additional technologies involving electro-active^{11,12} and ion exchange membranes.¹³⁻¹⁵

Sulfonated styrenic block copolymers represent exemplary ion-containing compositions, possessing fortified viscoelastic behavior and enhanced microphase separation due to synergistic properties of ionomers^{16,17} and block copolymers.¹⁸ Ionic association within these block compositions increases the Flory-Huggins interaction

parameter χ for microphase separation, allowing for lower block molecular weights and improved microphase separation.¹⁹ Previous investigations involving sulfonated block copolymers elucidated effects of sulfonation level on morphologies and electro-active properties, and earlier work predominately focused on Kraton[®] sulfonated poly(styrene-*b*-hydrogenated butadiene-*b*-styrene) [poly(SS-*b*-HB-*b*-SS)] and sulfonated poly(styrene-*b*-hydrogenated isoprene-*b*-styrene) [poly(SS-*b*-HI-*b*-SS)] triblock copolymers,^{20,21} and Kraton[®] sulfonated poly(tert-butyl styrene-*b*-hydrogenated isoprene-*b*-sulfonated styrene-*b*-hydrogenated isoprene-*b*-tert-butyl styrene) [poly(tBS-*b*-HI-*b*-SS-*b*-HI-*b*-tBS)] pentablock copolymers (0-50 mol% sulfonated polystyrene).²²⁻²⁵ Although these reports revealed sulfonated block copolymers as promising membranes for technologies ranging from fuel cells and water purification²⁶ to actuators²⁷ and nanofabrication²⁸, concern for thermal and charge stability due to low temperature degradation reactions poses an architectural design flaw and inspires new directions in polymerizing alternative charged monomers.^{25,29}

Recent studies reveal phosphorus-containing macromolecules as promising analogues to sulfonated polymers, revealing tunable oxidation states (phosphates, phosphines, phosphine oxides, and phosphoniums), high alkylation efficiency,^{30,31} thermal and base stability,^{30,31} high ionic conductivity,^{11,32} tailored structures and morphologies,³³ and ionic aggregation.³⁴ Phosphorus-containing monomers exhibiting vinylbenzyl-, acrylate-, and methacrylate-polymerizable units achieves a wide range of phosphorus-containing macromolecules including homopolymers,³⁵ random copolymers,³⁶ and block copolymers.³⁷ Although many of these synthetic methods involve controlled free radical strategies, anionic polymerization remains a commercially viable process for producing block copolymers with architectural precision and low degrees of compositional heterogeneity. Herein, we report the controlled anionic polymerization of 4-diphenylphosphino styrene (DPPS) as an unprecedented method for achieving novel phosphorus-containing styrenic block copolymers. DPPS does not contain β -hydrogens to the phosphorus atom that are susceptible for low temperature Hoffman elimination degradation pathways and, consequently, is structurally advantageous for achieving phosphonium-containing block copolymers with enhanced thermal and base stability in comparison to sulfonated styrenic block copolymers. Sequential monomer addition strategies enabled poly(*l*-*b*-DPPS) block copolymers for elucidating post-alkylation effects on structure-morphology


* Macromolecules and Interfaces Institute, Department of Chemistry, 80 Virginia Tech, Blacksburg, VA 24061, USA. E-mail: telong@vt.edu

† Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

behavior. As ion-containing polymers emerge for electro-active membranes, designing novel phosphonium-containing block copolymers with predictable structure-morphology-property relationships will facilitate commercial technologies.


Scheme 1 depicts anionic polymerization as a facile and controlled approach for achieving poly(DPPS) homopolymers in THF using *sec*-butyllithium as the initiator. The reaction proceeded at $-78\text{ }^{\circ}\text{C}$ to maintain stereochemical control of the propagating, deep red poly(styryl)lithium chains under the polar, aprotic solvent conditions. *In situ* FTIR spectroscopy monitored DPPS propagation, using the C=C vinyl vibrational frequency peak at 918 cm^{-1} and generating a normalized waterfall plot for peak absorbance vs. time (min). Tracking vinyl concentration disappearance over time indicated that complete monomer consumption occurred within 5 min (S1). Size exclusion chromatography (SEC) confirmed a 30,000 g/mol target M_n value for the homopolymer, and revealed monomodality in the chromatogram and a narrow polydispersity of 1.05 (Figure 1).

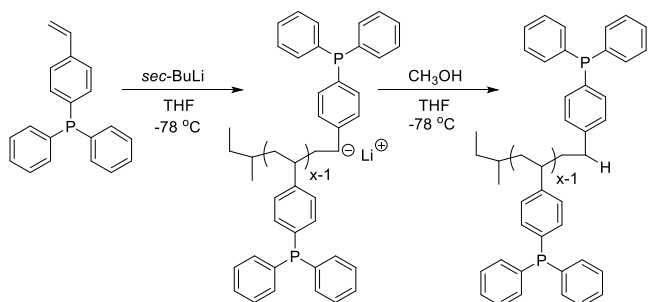

Scheme 1 Anionic polymerization achieves poly(DPPS).

Sequential monomer addition studies with styrene further verified the controlled polymerization of DPPS, revealing characteristics of a truly “living” polymerization (Scheme 2A). In these studies, *sec*-butyllithium initiated the anionic polymerization of DPPS and produced living propagating chains with target M_n of 30,000 g/mol. Sequential monomer addition enabled the anionic copolymerization with styrene, resulting in a poly(DPPS-*b*-S) block copolymer with final M_n of 60,000 g/mol (PDI = 1.06). SEC chromatograms in Figure 1 show the molecular weight shift during the sequential addition from poly(DPPS) to poly(DPPS-*b*-S) with narrow molecular weight distributions, which is indicative of living polymerization.

Living anionic polymerization with sequential monomer addition also produced a novel poly(*I-b*-DPPS) diblock copolymer in order to demonstrate the versatility in block composition and architecture (Scheme 2B). Moreover, this experiment elucidated DPPS propagation behavior in nonpolar solvent conditions suitable for targeting 1, 4-configuration *cis*-isomer diene microstructure. For this study, *sec*-butyllithium first initiated a living poly(isoprene) ($M_n = 30,000\text{ g/mol}$) due to the insoluble properties of poly(DPPS) in nonpolar solvents. After 2 h, isoprene monomer was completely consumed and DPPS was sequentially added to the living chain in order to produce a second block sequence ($M_n = 15,000\text{ g/mol}$) compatible with the polymer solution. The homogeneous, orange reaction mixture stirred for 30 min to complete DPPS propagation before quenching with acidic methanol. SEC analysis confirmed the total $M_n = 45,000\text{ g/mol}$ value for poly(*I-b*-DPPS) and revealed a narrow polydispersity of 1.04 (Figure 1).

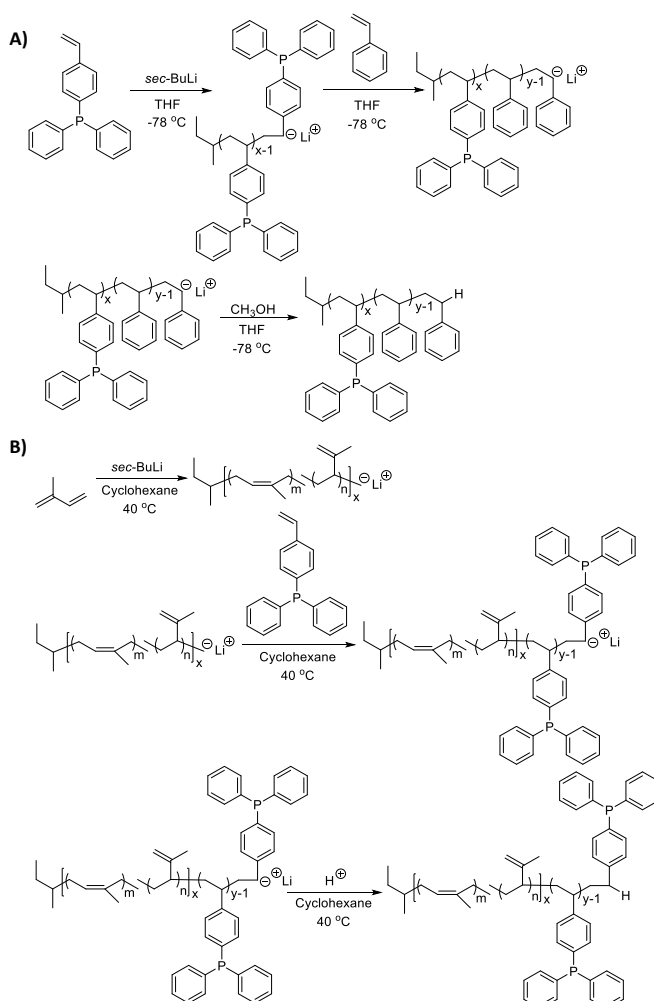

Scheme 2 Sequential monomer addition achieves copolymerization of diblocks (A) poly(DPPS-*b*-S) in polar solvent conditions and (B) poly(*I-b*-DPPS) in nonpolar solvent conditions.


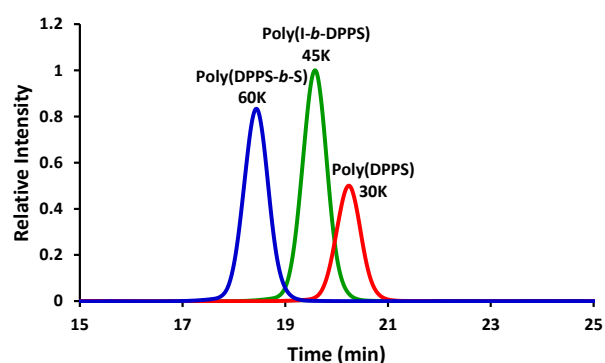


Figure 1 SEC characterization for poly(DPPS), poly(DPPS-*b*-S) after sequential addition of styrene, and poly(*I-b*-DPPS).

Poly(*I-b*-DPPS) diblock copolymer provided a balance of hard (DPPS, high $T_g = 120\text{ }^{\circ}\text{C}$) and soft (*I*, low $T_g = -50\text{ }^{\circ}\text{C}$) block sequences to fabricate a mechanically robust, free-standing film. Post-alkylation with bromohexane and bromododecane achieved phosphonium based derivatives (Scheme 3), poly(*I-b*-C₆DPPS)⁺Br⁻ and poly(*I-b*-C₁₂DPPS)⁺Br⁻, and small angle X-ray scattering analysis (SAXS) was employed to reveal the microphase-separated bulk morphologies of

the neutral and charged samples (Figure 2). All SAXS measurements were performed at room temperature, and all films were slowly cast from toluene and annealed at 120 °C under reduced pressure (5 mmHg) to achieve equilibrium or near-equilibrium morphologies. The neutral poly(*l*-*b*-DPPS) block copolymer sample exhibited an ordered scattering profile with peak maxima at q^* , $2q^*$, $3q^*$, and $4q^*$, indicating a lamellar morphology. Bragg's law was used to approximate lamellar spacing from the primary scattering maximum at q^* , revealing a Bragg distance of 22 nm. Strong scattering peaks were observed for all samples, indicating that microphase separation also existed post-alkylation. However, the scattering profile for both poly(*l*-*b*-C₆DPPS)⁺Br⁻ and poly(*l*-*b*-C₁₂DPPS)⁺Br⁻ failed to exhibit q -values characteristic to the traditional block copolymer morphology, presumably due to the incorporated ion associations that prohibit sufficient thermal annealing in these samples. Increasing the alkyl length also gave rise to a broad scattering peak near $q = 2.1 \text{ nm}^{-1}$, corresponding to the interdigitated packing of dodecyl chains on the phosphonium cation. A similar phenomenon was observed in earlier reports involving random copolymers containing trioctyl phosphonium styrenic ionic liquids.³⁶ Tuning film casting conditions and applying transmission electron microscopy (TEM) will further elucidate the morphology of phosphonium-containing diblock copolymers.

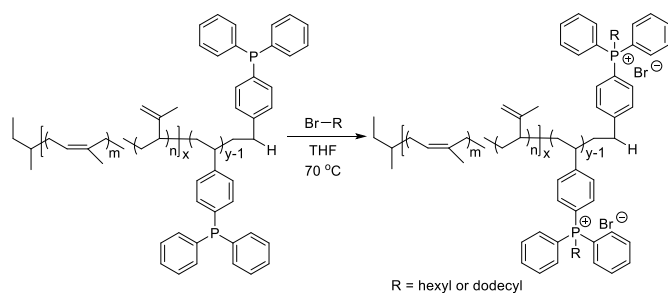

Scheme 3 Post-alkylation produces phosphonium containing diblock copolymers, poly(*l*-*b*-C₆DPPS)⁺Br⁻ and poly(*l*-*b*-C₁₂DPPS)⁺Br⁻.

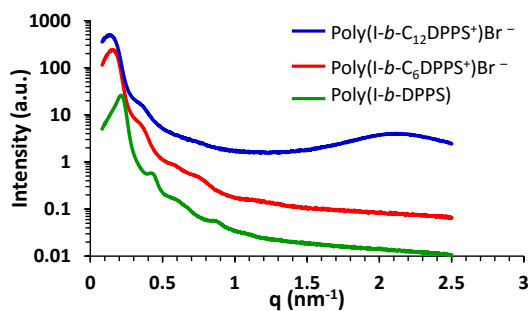


Figure 2 Small Angle X-Ray Scattering profiles reveal oriented bulk morphologies for poly(*l*-*b*-DPPS), poly(*l*-*b*-C₆DPPS)⁺Br⁻, and poly(*l*-*b*-C₁₂DPPS)⁺Br⁻ diblock copolymers. Appearance of broad peak in poly(*l*-*b*-C₁₂DPPS)⁺Br⁻ scattering profile corresponds to interdigitated bilayers.

Living anionic polymerization afforded novel phosphine-containing homopolymers and diblock copolymers with targetable molecular weights and narrow polydispersities. Sequential monomer addition strategies enabled poly(DPPS-*b*-S) and poly(*l*-*b*-DPPS) block copolymers for suitable polar and nonpolar solvent conditions. A balance of soft-hard volume fractions for poly(*l*-*b*-DPPS) block copolymers promoted self-assembly into highly ordered lamellar microphase separated morphologies. Post-alkylation efficiently converted the phosphine backbone to a phosphonium cation, achieving poly(*l*-*b*-C₆DPPS)⁺Br⁻ and poly(*l*-*b*-C₁₂DPPS)⁺Br⁻, which

disrupted the highly ordered bulk morphologies of the traditional neutral composition. Increasing the alkyl chain length gave rise to a new phase, corresponding to interdigitated packing of dodecyl chains on the phosphonium cation. Future studies will extend these novel phosphonium diblock compositions to ABA- and ABC- type triblock architectures, in order to evaluate these phosphonium-containing styrenic block copolymers as ion-containing thermoplastic elastomers.

We acknowledge the Institute for Critical Technology Applied Science (ICTAS) for laboratory support and we thank Dr. Carl Willis of Kraton Polymers for insightful discussions. This material is partially based upon work supported by the National Science Foundation under Grant No. DMR-0923107.

Notes and references

† Electronic supplementary information (ESI) available: Experimental details and *in situ* FTIR spectroscopy.

- 1 Tse, M. F. *Journal of Adhesion Science and Technology* 1989, **3**, 551.
- 2 Mauritz, K. A.; Blackwell, R. I.; Beyer, F. L. *Polymer* 2004, **45**, 3001.
- 3 Hashimoto, T.; Tsutsumi, K.; Funaki, Y. *Langmuir* 1997, **13**, 6869.
- 4 Ma, M.; Hill, R. M.; Lowery, J. L.; Fridrikh, S. V.; Rutledge, G. C. *Langmuir* 2005, **21**, 5549.
- 5 Kazunori, K.; Masayuki, Y.; Teruo, O.; Yasuhisa, S. *Journal of Controlled Release* 1993, **24**, 119.
- 6 Kwon, G. S.; Kataoka, K. *Advanced drug delivery reviews* 1995, **16**, 295.
- 7 Ranade, S. V.; Richard, R. E.; Helmus, M. N. *Acta Biomaterialia* 2005, **1**, 137.
- 8 Weiss, R. *Department of Polymer Engineering* 1992, **67**, 127.
- 9 Park, H. B.; Freeman, B. D.; Zhang, Z.-B.; Sankir, M.; McGrath, J. E. *Angew. Chem., Int. Ed.* 2008, **47**, 6019.
- 10 Brown, K.; Hooker, J. C.; Creton, C. *Macromolecular Materials and Engineering* 2002, **287**, 163.
- 11 Schultz, A. R.; Lambert, P. M.; Chartrain, N. A.; Ruohoniemi, D. M.; Zhang, Z.; Jangu, C.; Zhang, M.; Williams, C. B.; Long, T. E. *ACS Macro Letters* 2014, **3**, 1205.
- 12 Gao, R.; Zhang, M.; Dixit, N.; Moore, R. B.; Long, T. E. *Polymer* 2012, **53**, 1203.
- 13 Gao, R.; Wang, D.; Heflin, J. R.; Long, T. E. *Journal of Materials Chemistry* 2012, **22**, 13473.
- 14 Allen, M. H.; Green, M. D.; Getaneh, H. K.; Miller, K. M.; Long, T. E. *Biomacromolecules* 2011, **12**, 2243.
- 15 Allen, M. H., Jr.; Wang, S.; Hemp, S. T.; Chen, Y.; Madsen, L. A.; Winey, K. I.; Long, T. E. *Macromolecules*, 2013, **46**, 3037.
- 16 Page, K. A.; Cable, K. M.; Moore, R. B. *Macromolecules* 2005, **38**, 6472.
- 17 MacKnight, W.; DeMejo, L.; Vogl, O. *Acta Polymerica* 1980, **31**, 617.
- 18 Weiss, R.; Sen, A.; Pottick, L.; Willis, C. *Polymer* 1991, **32**, 2785.
- 19 Choi, J.-H.; Willis, C. L.; Winey, K. I. *Journal of Membrane Science* 2012, **394–395**, 169.
- 20 Choi, J.-H.; Ye, Y.; Elabd, Y. A.; Winey, K. I. *Macromolecules* 2013, **46**, 5290.
- 21 Elabd, Y. A.; Napadensky, E.; Walker, C. W.; Winey, K. I. *Macromolecules* 2006, **39**, 399.
- 22 Choi, J.-H.; Willis, C. L.; Winey, K. I. *J. membr. sci.* 2012, **394**, 169.

- 23 Elabd, Y. A.; Walker, C. W.; Beyer, F. L. *J. membr. sci.* 2004, **231**, 181.
- 24 Kim, J.; Kim, B.; Jung, B. *J. membr. sci.* 2002, **207**, 129.
- 25 Kim, B.; Kim, J.; Jung, B. *J. membr. sci.* 2005, **250**, 175.
- 26 Wang, X.; Goswami, M.; Kumar, R.; Sumpter, B. G.; Mays, J. *Soft Matter* 2012, **8**, 3036.
- 27 Shahinpoor, M.; Bar-Cohen, Y.; Simpson, J.; Smith, J. *Smart materials and structures* 1998, **7**, R15.
- 28 Bocharova, V.; Agapov, A. L.; Tselev, A.; Collins, L.; Kumar, R.; Berdzinski, S.; Strehmel, V.; Kisliuk, A.; Kravchenko, I. I.; Sumpter, B. G. *Advanced Functional Materials* 2015, **25**, 805.
- 29 Gao, R.; Zhang, M.; Dixit, N.; Moore, R. B.; Long, T. E. *Polymer* 2012, **53**, 1203.
- 30 Ren, H.; Sun, J.; Wu, B.; Zhou, Q. *Polym. Degrad. Stab.* 2007, **92**, 956.
- 31 Rana, U. A.; Vijayaraghavan, R.; Walther, M.; Sun, J.; Torriero, A. A. J.; Forsyth, M.; MacFarlane, D. R. *Chem Commun* 2011, **47**, 11612.
- 32 Hemp, S. T.; Zhang, M.; Allen, M. H., Jr.; Cheng, S.; Moore, R. B.; Long, T. E. *Macromol. Chem. Phys.* 2013, **214**, 2099.
- 33 Gu, Y.-Y.; Lodge, T. P. *Macromolecules* 2011, **44**, 1732.
- 34 Cheng, S.; Zhang, M.; Wu, T.; Hemp, S. T.; Mather, B. D.; Moore, R. B.; Long, T. E. *J. Polym. Sci., Part A: Polym. Chem.* 2012, **50**, 166.
- 35 Wang, K.; Zeng, Y.; He, L.; Yao, J.; Suresh, A. K.; Bellare, J.; Sridhar, T.; Wang, H. *Desalination* 2012, **292**, 119.
- 36 Cheng, S.; Zhang, M.; Wu, T.; Hemp, S. T.; Mather, B. D.; Moore, R. B.; Long, T. E. *J. Polym. Sci., Part A: Polym. Chem.* 2012, **50**, 166.
- 37 Borguet, Y. P.; Tsarevsky, N. V. *Polym. Chem.* 2012, **3**, 2487.