

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Journal Name

COMMUNICATION

Nanoelectrodes Reveal Electrochemistry of Single Nickelhydroxide Nanoparticles

 Received 00th January 20xx,
 Accepted 00th January 20xx

Jan Clausmeyer*, Justus Masa, Edgar Ventosa, Dennis Öhl, Wolfgang Schuhmann*

DOI: 10.1039/x0xx00000x

www.rsc.org/

Individual Ni(OH)₂ nanoparticles deposited on carbon nanoelectrodes are investigated in non-ensemble measurements with respect to their energy storage properties and electrocatalysis for the oxygen evolution reaction (OER). Charging by oxidation of Ni(OH)₂ is limited by diffusion of protons into the particle bulk and the OER activity is independent of particle size.

Electrochemical techniques have empowered to analyse single nanoparticles without averaging over large statistical ensembles. Stochastic collisions of individual particles with microelectrodes as demonstrated by Bard's¹ and Compton's² groups have provided information concerning particle size³ as well as physical⁴ and electrocatalytic properties.⁵ However, the particle collision method is an intrinsically transient method concerning the number of analysed particles at a given time, *i.e.* single particles cannot be studied over a long time in steady-state measurements. Alternatively, scanning electrochemical microscopy (SECM) or scanning electrochemical droplets allow for analysing particle size and detecting the products of a catalytic conversion.^{6,7} Deposition of electroactive materials on nanoelectrodes has allowed studying the activity of individual nanoparticles towards reactions relevant for electrochemical energy conversion such as the hydrogen evolution reaction (HER)⁸ or the oxygen reduction reaction (ORR).^{9,10} Here, we evaluate the oxygen evolution reaction (OER) as well as charge storage by proton insertion at single Ni(OH)₂ particle modified electrodes. In the quest to develop competitive technologies for the storage of electrical energy, Ni(OH)₂ has proved to be both a suitable catalyst for electrochemical water oxidation¹¹ as well as a material in aqueous batteries¹² and supercapacitors.¹³ Especially, nanostructured materials show superior performance compared to their bulk counterparts.^{14–17}

However, in understanding the nature of the enhanced electrocatalytic activity of nanoparticles, it is difficult to distinguish between the specific activity and geometric effects such as increased surface area or increased mass transport rates. Moreover, there is an ongoing debate concerning the mechanism of energy storage in nanomaterials for batteries and supercapacitors.^{13,18} As the dimensions of nanostructured materials decrease, electrochemical processes in proximity to the surface and thus capacitive and pseudo-capacitive contributions become more important due to the high surface area.

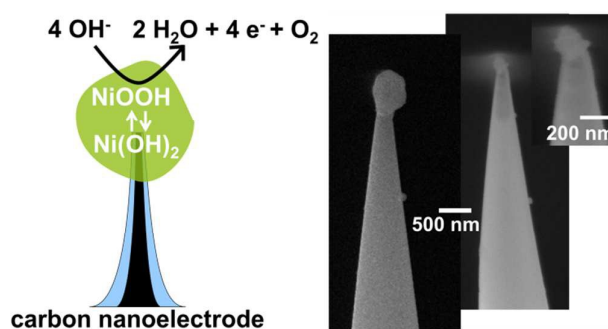


Figure 1. Nanoparticle-modified electrodes allow electrochemical characterization of individual Ni(OH)₂ nanoparticles. SEM images show two individual nanoparticles deposited on carbon nanoelectrodes and a magnified image of the smaller particle.

We use nanoelectrodes fabricated using a facile and effective method^{19,20} decorated with a single nanoparticle to demonstrate a range of dynamic experiments to assess size, composition and catalytic activity of nanoparticles at high mass transport rates. For the OER, we deduce novel but counterintuitive observations about the relation between size and activity of catalytic particles. Likewise unforeseen, we find that charge storage in single medium scale Ni(OH)₂ nanoparticles is limited by diffusion and thus does not show pseudo-capacitive behaviour.

Carbon nanoelectrodes are fabricated by pyrolytic decomposition of butane gas inside pulled quartz glass nanopipettes. This time-effective (ca. 1 min/electrode) method produces disk-

Analytical Chemistry - Center for Electrochemical Sciences (CES), Ruhr-Universität Bochum, Universitätsstrasse 150, D-44780, Bochum, Germany

*To whom correspondence should be addressed: jan.clausmeyer@rub.de; wolfgang.schuhmann@rub.de

Electronic Supplementary Information (ESI) available: [Experimental procedures, nanoelectrodes characterization, electrochemical estimation of particle sizes, additional SEM images and EDX analysis, OER polarization curves].

See DOI: 10.1039/x0xx00000x

shaped carbon electrodes with dimensions of a few nanometres surrounded by a thin glass sheath¹⁹ (see SI for fabrication and characterization of nanoelectrodes). Then, Ni(OH)₂ is cathodically deposited on the carbon nanoelectrodes from NiCl₂ solutions, yielding single Ni(OH)₂ nanoparticles attached to the nanoelectrodes. Due to the small dimensions of the carbon nanoelectrodes which are smaller or of comparable size to the deposited particles, the Ni(OH)₂ nanoparticles exhibit approximately spherical geometry as confirmed by SEM imaging (Figure 1). The radii of deposited particles range from 20 nm to 500 nm as determined electrochemically and confirmed by SEM (see SI).

The Ni(OH)₂/NiOOH redox couple has been widely used in highly dispersed materials for energy storage in aqueous batteries and pseudo-capacitors. The general paradigm is that surface or near-surface reactions, *i.e.* pseudo-capacitive contributions to the charge storage become more important with decreasing material dimensions. In contrast to previous studies,^{13,15} by investigating the oxidation of single Ni(OH)₂ particles we observe that the process is entirely limited by diffusion.

Voltammetric analysis of the Ni(OH)₂ → NiOOH + H⁺ + e⁻ transition reveals a linear dependence of the corresponding anodic peak currents with respect to the scan rate (Figure 2). The trend line of the log *i*_{pa} vs. log *v* plot shows a slope close to the theoretical value of 0.5 expected for a diffusion-controlled process, as opposed to a value of 1 for surface-confined species (*i.e.* a pseudo-capacitive process). It is very important to note that due to the small dimensions of the single particle electrode, diffusion of the involved species in the electrolyte occurs extremely fast. Hence, it is the diffusion of protons inside the bulk of the Ni(OH)₂ nanoparticle that limits the overall oxidation reaction. Due to the analogy to a macroscopic electrode with diffusion-limitation in the electrolyte, the Randles-Sevcik equation can be used to describe the voltammetric peak currents at the nanoelectrode with diffusion-limitation in the particle bulk.¹²

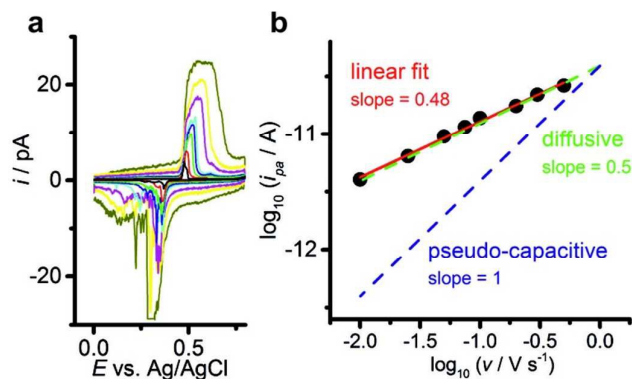


Figure 2. The oxidation of Ni(OH)₂ nanoparticles is limited by proton diffusion in the particle bulk. Cyclic voltammograms at a single Ni(OH)₂ nanoparticle (*r* = 75 nm) electrode at varying scan rates from 0.01 to 0.5 Vs⁻¹ in 0.1 M KOH (a) and analysis of anodic peak currents as a function of the scan rate (b).

Proton diffusion coefficients at single Ni(OH)₂ nanoparticles calculated from the Randles-Sevcik equation using the electrochemically estimated particle surface area and assuming stoi-

chiometric proton release (resulting in a bulk proton concentration of 44.7 M in Ni(OH)₂) range around 2 × 10⁻¹¹ cm²s⁻¹ for particles smaller than *r* = 75 nm. Slower apparent diffusion is observed for larger particles. This might be due to the contribution of poor electronic conductivity of Ni(OH)₂ which becomes more important for long electron-transfer paths inside larger particles. Values for the proton diffusion coefficient in Ni(OH)₂ observed by other authors range from 10⁻¹¹ to 10⁻⁷,^{12,21} which might be due to the difficulty in investigating thick porous film electrodes.

Upon sweeping the potential anodically to investigate the OER, single Ni(OH)₂ particle electrodes exhibit defined redox signals for the oxidation of Ni(OH)₂ to NiOOH which are well separated from the onset of the anodic current for OER (Figure 3a). The voltammetric peak for oxidation of Ni(OH)₂ (inset) is suitable for precise electrochemical determination of the catalyst amount.^{3,16} From the amount of deposited Ni(OH)₂ the particle size is calculated, assuming spherical geometry (see SI). To assess the catalyst activity, the turnover frequencies (TOF) for the OER at high overpotentials are analysed as a function of particle size (Figure 3b). The TOF indicates the rate of evolved oxygen molecules per catalyst active centre (see SI). Generally, single nanoparticle electrodes can be driven to high turnover frequencies at high potentials of 1.88 V vs. RHE (η = 0.65). Since no binders or conductive additives as typically used to formulate porous electrodes are necessary, degradation of those components at the high anodic potentials is excluded. Also, in contrast to thick porous films and powder electrodes, the particles are directly contacted by the nanoelectrodes to reduce the influence of electric resistance in the film. At single particles a relatively high variability of the TOF is observed, which may reflect information concerning the heterogeneity of individual particles that is normally lost when studying large ensembles of particles (Figure 3b).

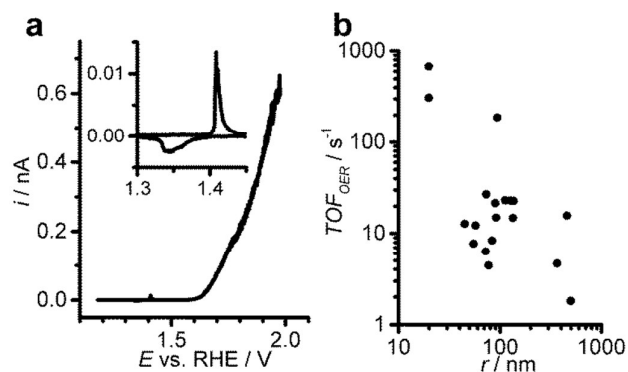


Figure 3. The OER is performed at single Ni(OH)₂ nanoparticles to investigate the relation between activity and particle size. Cyclic voltammogram (10 mV/s) at a single particle electrode (*r* = 83 nm) in 0.1 M KOH (a) and turnover frequencies for the OER at 1.88 V vs. RHE for differently sized particles (b).

Nevertheless, the analysis of the TOF with respect to the particle size shows a general decrease of the TOF with increasing particle radius. Since the TOF is considered an intrinsic material property this observation may be used to support the claim that smaller Ni(OH)₂ particles are intrinsically more active with

respect to the OER than larger particles. However, we attribute this finding to geometric effects, namely a higher surface-to-bulk ratio of the smaller particles that allows more precise quantification of active centres. Additionally, in the high overpotential region the poor electronic conductivity of the material may hamper the reaction rate at larger particles which have a longer electron path. We can exclude increased specific activity of small particles by comparing the electrode kinetics of small and large particles. Tafel analysis in the low overpotential region of the OER at single Ni(OH)₂ particles reveals that the electrode kinetics are largely invariant with the particle size (Figure 4). The Tafel plots for small and large particles all exhibit similarly low slopes in the low overpotential region between 1.57 and 1.66 vs. RHE ($\eta = 0.34$ and $\eta = 0.43$) followed by larger values at higher potentials (Figure 4a). Comparing the values for the Tafel slope over the whole population of individually analysed particles (Figure 4b) yields a slope of 0.05 ± 0.01 V dec⁻¹ as expected for highly active OER catalysts.^{14,16,17} This observation contradicts the assumption that small particles are intrinsically more active than large particles. The apparent increase in activity as concluded from the turnover frequencies is rather a result of geometric effects. At small particles the number of truly active sites can be estimated with higher precision because of the increased fraction of active centres located in direct contact between electrode and electrolyte solution. These findings highlight that the TOF is generally underestimated due to the difficulties in determining the number of active sites, especially at large particles or thick porous catalyst films on macroscopic electrodes. Also, in thick films or powder electrodes, electronic conductivity may have a detrimental influence on the reaction rate, which might be already observed for larger nanoparticles.

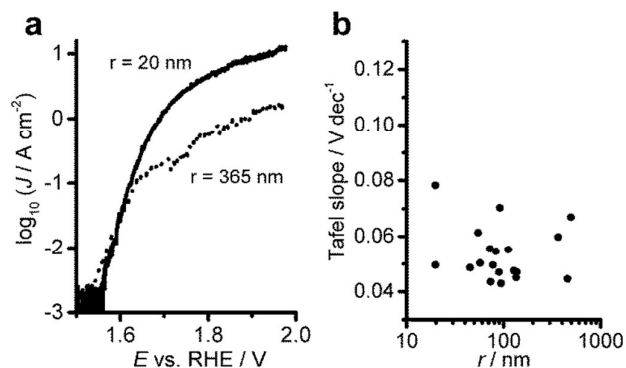


Figure 4. Electron transfer kinetics for the OER at single Ni(OH)₂ nanoparticles show no activity dependence on particle size. Tafel plots for two selected particles with radii of 20 nm (solid line) and 365 nm (dotted line) (a) and analysis of Tafel slopes between 1.57 and 1.66 vs. RHE as a function of particle size (b).

In conclusion, studying the electrochemistry of single nanoparticles deposited on carbon nanoelectrodes has several advantages: 1) Extremely fast mass transport rates are obtained which by far exceed those accessible in rotating ring-disk electrode experiments.⁹ 2) The particles are directly contacted with low resistance and in addition degradation of non-active components while applying high potentials necessary for the

OER can be excluded. 3) Characterization of individual particles provides precise knowledge of particle size and thus allows for deducing size-activity relations. Using these advantages, we find that the oxidation of Ni(OH)₂, a typical reaction representative for charge storage in aqueous batteries and supercapacitors, is entirely limited by proton diffusion inside the particle bulk even for relatively small particles. Capacitive behaviour due to charging of the electrochemical double layer or pseudo-capacitive contributions due to faradaic reactions at or near the surface are insignificant.

For the electrocatalytic evolution of oxygen we investigate the size-dependent catalytic turnover rate of individual Ni(OH)₂ particles. In contrast to the notion that a small particle size results in high catalytic activity we observe constant reaction kinetics for particles with radii between 20 nm and 500 nm. Analysis of single active nanoparticles using nanoelectrodes will develop to be a powerful tool to elucidate more size-specific phenomena in catalysis at the nanoscale and thus will help in understanding size-structure-activity relations.

Acknowledgements

The contribution of Sandra Schmidt for assistance with SEM/EDX measurements is acknowledged. This work was financially supported by the DFG (Cluster of Excellence RESOLV; EXC 1069) and by the BMBF (NeMeZu; FKZ 03SF0497B).

Keywords

nanoparticles; nanoelectrode, Ni(OH)₂, electrocatalysis; oxygen evolution

Notes and references

- X. Xiao and A. J. Bard, *J. Am. Chem. Soc.*, 2007, **129**, 9610; S. J. Kwon, F.-R. F. Fan and A. J. Bard, *J. Am. Chem. Soc.*, 2010, **132**, 13165.
- W. Cheng and R. G. Compton, *Trends Anal. Chem.*, 2014, **58**, 79.
- Y.-G. Zhou, N. V. Rees and R. G. Compton, *Angew. Chem. Int. Ed.*, 2011, **50**, 4219.
- K. Tschulik and R. G. Compton, *Phys. Chem. Chem. Phys.*, 2014, **16**, 13909.
- H. Zhou, J. H. Park, F.-R. F. Fan and A. J. Bard, *J. Am. Chem. Soc.*, 2012, **134**, 13212; P. Sun, F. Li, C. Yang, T. Sun, I. Kady, B. Hunt and J. Zhuang, *J. Phys. Chem. C*, 2013, **117**, 6120.
- M. A. O'Connell and A. J. Wain, *Anal. Chem.*, 2014, **86**, 12100.
- Y.-R. Kim, S. C. S. Lai, K. McKelvey, G. Zhang, D. Perry, T. S. Miller and P. R. Unwin, *J. Phys. Chem. C*, 2015, **119**, 17389; S. E. F. Kleijn, S. C. S. Lai, T. S. Miller, A. I. Yanson, M. T. M. Koper and P. R. Unwin, *J. Am. Chem. Soc.*, 2012, **134**, 18558.
- X. Shan, I. Díez-Pérez, L. Wang, P. Wiktor, Y. Gu, L. Zhang, W. Wang, J. Lu, S. Wang, Q. Gong, J. Li and N. Tao, *Nature Nanotechnol.*, 2012, **7**, 668; Q. Chen, L. Luo, H. Faraji, S. W. Feldberg and H. S. White, *J. Phys. Chem. Lett.*, 2014, **5**, 3539; Y. Yu, Y. Gao, K. Hu, P.-Y. Blanchard, J.-M. Noël, T. Nareshkumar, K. L. Phani, G. Friedman, Y. Gogotsi and M. V. Mirkin, *ChemElectroChem*, 2015, **2**, 58.
- S. Chen and A. Kucernak, *J. Phys. Chem. B*, 2004, **108**, 3262.

- 10 Y. Li, J. T. Cox and B. Zhang, *J. Am. Chem. Soc.*, 2010, **132**, 3047; Y. Li, Q. Wu, S. Jiao, C. Xu and L. Wang, *Anal. Chem.*, 2013, **85**, 4135.
- 11 R. D. L. Smith, M. S. Prévot, R. D. Fagan, Z. Zhang, P. A. Sedach, M. K. J. Siu, S. Trudel and C. P. Berlinguette, *Science*, 2013, **340**, 60; C. C. L. McCrory, S. Jung, J. C. Peters and T. F. Jaramillo, *J. Am. Chem. Soc.*, 2013, **135**, 16977.
- 12 M. A. Kiani, M. F. Mousavi and S. Ghasemi, *J. Power Sources*, 2010, **195**, 5794.
- 13 T. Brousse, D. Belanger and J. W. Long, *J. Electrochem. Soc.*, 2015, **162**, A5185–A5189.
- 14 M. Gao, W. Sheng, Z. Zhuang, Q. Fang, S. Gu, J. Jiang and Y. Yan, *J. Am. Chem. Soc.*, 2014, **136**, 7077.
- 15 H. B. Li, M. H. Yu, F. X. Wang, P. Liu, Y. Liang, J. Xiao, C. X. Wang, Y. X. Tong and G. W. Yang, *Nat. Commun.*, 2013, **4**, 1894.
- 16 D. Cibrev, M. Jankulovska, T. Lana-Villarreal and R. Gómez, *Int. J. Hydrogen Energy*, 2013, **38**, 2746.
- 17 L. Trotochaud, J. K. Ranney, K. N. Williams and S. W. Boettcher, *J. Am. Chem. Soc.*, 2012, **134**, 17253.
- 18 H.-S. Kim, T. Itoh, M. Nishizawa, M. Mohamedi, M. Umeda and I. Uchida, *Int. J. Hydrogen Energy*, 2002, **27**, 295.
- 19 P. Actis, S. Tokar, J. Clausmeyer, B. Babakinejad, S. Mikhaleva, R. Cornut, Y. Takahashi, A. López Córdoba, P. Novak, A. I. Shevchuk, J. A. Dougan, S. G. Kazarian, P. V. Gorelkin, A. S. Erofeev, I. V. Yaminsky, P. R. Unwin, W. Schuhmann, D. Klenerman, D. A. Rusakov, E. V. Sviderskaya and Y. E. Korchev, *ACS Nano*, 2014, **8**, 875.
- 20 J. Clausmeyer, P. Actis, A. López Córdoba, Y. Korchev and W. Schuhmann, *Electrochem. Commun.*, 2014, **40**, 28; Y. Takahashi, A. I. Shevchuk, P. Novak, Y. Zhang, N. Ebejer, J. V. Macpherson, P. R. Unwin, A. J. Pollard, D. Roy, C. A. Clifford, H. Shiku, T. Matsue, D. Klenerman and Y. E. Korchev, *Angew. Chem. Int. Ed.*, 2011, **50**, 9638.
- 21 J. W. Weidner and P. Timmermann, *J. Electrochem. Soc.*, 1994, **141**, 346; K. Watanabe, T. Kikuoka and N. Kumagai, *J. Appl. Electrochem.*, 1995, **25**; G. Briggs and P. R. Snodin, *Electrochim. Acta*, 1982, **27**, 565.

Table of Content Graphics/Graphical Abstract

