


# ChemComm

Accepted Manuscript

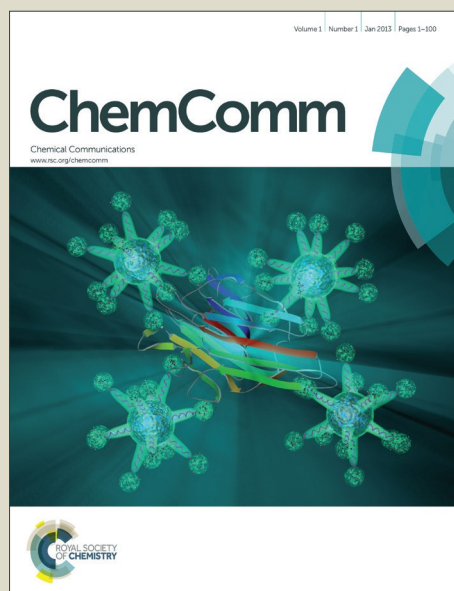

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## Determining the structural stability of UiO-67 with respect to time: A solid-state NMR investigation

Received 00th January 20xx,  
Accepted 00th January 20xx

M. C. Lawrence,<sup>a</sup> C. Schneider,<sup>a</sup> and M. J. Katz<sup>a,\*</sup>

DOI: 10.1039/x0xx00000x

www.rsc.org/

**The stability of UiO-67 has been questioned for some time. We have used solid-state NMR to investigate the temporal stability of this MOF. Proper activation is necessary to achieve optimal surface area. However, even with proper activation, the long-term (30+ days) fate of UiO-67 is hydrolysis of the linker-metal bonds and, ultimately, pore collapse.**

Metal-Organic Frameworks (MOFs) are porous materials formed via coordination of bridging organic ligands (linkers) with inorganic metal cations/clusters (nodes). With judicious choice of these components, MOFs with applications in gas-storage,<sup>1</sup> chemical separations,<sup>2</sup> light-harvesting,<sup>3</sup> sensing,<sup>2b, 4</sup> and catalysis<sup>5</sup> have been realized. One family of MOFs which are becoming ubiquitous in these applications is the Zr-cluster-containing family of MOFs, including, but not limited to, UiO's,<sup>6</sup> NU-1000,<sup>7</sup> PCN-222,<sup>8</sup> and MOF-808.<sup>9</sup> The interest in these MOFs stems from their thermal, chemical, and mechanic stability making them ideal for many applications.<sup>6d, 10</sup>

With respect to both anecdotal evidence as well as literature precedence, UiO-67 (Fig. 1) has had a precarious history. DeCoste et al. demonstrated that the internal surface area (SA) of UiO-67 decreased from 2145 m<sup>2</sup>g<sup>-1</sup> to 10 m<sup>2</sup>g<sup>-1</sup> after the MOF was exposed to 90 % relative humidity. Similarly, when soaked in water, UiO-67 was found to be unstable; powder x-ray diffraction data (pxrd) indicated the presence of ZrO<sub>2</sub>.<sup>11</sup> Although the instability is attributed to hydrolysis of the bonds between the linker and node, FTIR data showed no vibrational changes to corroborate this.

In a related manuscript, Mondloch et al. have proposed an alternate hypothesis. When UiO-67 was activated (i.e., the process of removing solvent from the porous frameworks) from water, then there was no notable porosity remaining. However, if water in the pore was replaced with acetone prior to activation, then the porosity remained; similar results were

obtained when UiO-67 was boiled in water prior to solvent exchange. Thus, rather than an inherent instability in the MOF it was proposed that capillary-force driven collapse, due to improper activation, is responsible for the proposed instability.<sup>12</sup>

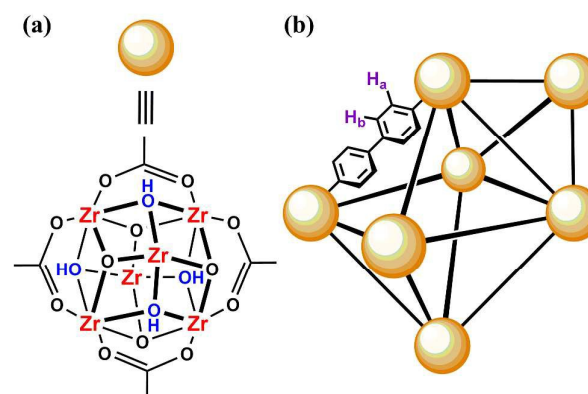


Fig. 1. (a) Zr<sub>6</sub>O<sub>4</sub>(OH)<sub>4</sub> cluster showing 4 of the 12 μ-BPDC units. (b) Schematic drawing of UiO-67 illustrating how the BPDC units link Zr<sub>6</sub>O<sub>4</sub>(OH)<sub>4</sub> clusters to one another to form both octahedral- and tetrahedral-shaped pores.

Given the utility of UiO-67,<sup>5b, 6h, 13</sup> we were interested in further probing its stability. Specifically, we are interested in investigating the long-term stability of UiO-67 with respect to time. We turned our attention to solid-state NMR (SS-NMR) as a probe for the potential structural changes that occur within this MOF. Unlike pxrd, which is sensitive to crystalline materials containing high Z nuclei, SS-NMR is equally sensitive to both amorphous and crystalline materials. Furthermore, SS-NMR has the potential to independently report on each nucleus.

UiO-67 was synthesized by the method of Katz et al. (See ESI for further details).<sup>6a</sup> UiO-67 was subsequently filter-dried (ca. 1 hour). The samples of DeCoste et al.<sup>11</sup> were similarly filtered.

As expected, despite the apparently dry UiO-67, the SS-NMR indicates that freshly-prepared UiO-67 (Fig. 2 red trace) shows remanence of methanol (3.05 ppm, 4.65 ppm) within

<sup>a</sup> Department of Chemistry, Memorial University of Newfoundland, St. John's, Newfoundland and Labrador, Canada.

\*Electronic Supplementary Information (ESI) available: [Experimental details, <sup>13</sup>C-NMR spectra, and <sup>1</sup>H-NMR spectra of CH<sub>2</sub>Cl<sub>2</sub>-activated UiO-67]. See DOI: 10.1039/x0xx00000x

the pores of the MOF; the remaining resonances at 7.82 and 8.29 ppm belong to the biphenyl protons (Fig. 1 H<sub>a</sub> and H<sub>b</sub>).

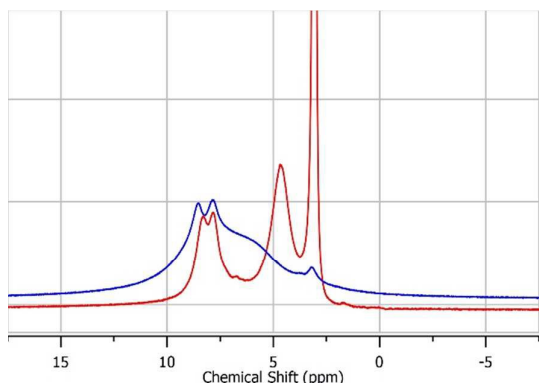


Fig. 2: (red) <sup>1</sup>H-NMR of UiO-67 immediately after vacuum filtration. (blue) <sup>1</sup>H-NMR of UiO-67 6 days after vacuum filtration. The corresponding <sup>13</sup>C-NMRs can be seen in Fig. S2.

When freshly-prepared UiO-67 was left out for 6 days, the SS-NMR indicated that the majority of the methanol signals were greatly diminished.<sup>14</sup> However, a new broad-featureless resonance upfield of the linker protons (6.29 ppm) with a concomitant broad resonance buried at 8.51 ppm was observed. This feature is indicative of the appearance of an amorphous material. Concomitantly, the Brunauer–Emmett–Teller (BET) SA of the 6-day old sample was a mere 500 m<sup>2</sup>g<sup>-1</sup> (Fig S1 in the ESI); this is in contrast with the SA of freshly-prepared and thermally activated UiO-67 which exhibited a BET SA of 2000 m<sup>2</sup>g<sup>-1</sup> (Fig S1 in the ESI). These results are consistent with the work by DeCoste et al.<sup>11</sup>

In order to further probe whether hydrolysis of the Zr-carboxylate bonds or capillary-force driven collapse is the culprit, we repeated the experiment with UiO-67 which was solvent exchanged (4 days) and subsequently filtered and thermally activated. As illustrated in Fig. 3, there are three distinct regions at ca. 0 ppm, 2.5 ppm, and 7.5 ppm; the latter two resonances have been attributed to the linker (7.5 ppm) and the bridging hydroxides (Fig. 1) on the node (2.5 ppm).<sup>15</sup> The remaining resonance at 0 ppm, which is only slightly visible in the spectra by Dolbecq et al.,<sup>15</sup> we attribute to linker deficiencies (i.e., defect sites comprised of Zr-bound OH and H<sub>2</sub>O moieties on the Zr<sub>6</sub>(OH)<sub>4</sub>O<sub>4</sub><sup>12+</sup> node) within the porous framework.<sup>6a,6h,16</sup>

Unlike the filter-dry sample which contains pore-bound solvent (Fig. 2), over the course of a month, the BET SA of activated UiO-67 merely decreased to 1500 m<sup>2</sup>g<sup>-1</sup> (Fig S1 in the ESI). The SS-NMR (Fig. 3) shows nearly no evidence for the broad featureless hump in Fig. 2 suggesting that the origin of the decrease in SA for filter-dried UiO-67 (Fig. 2) is due to capillary-force driven collapse.<sup>12</sup>

As a function of time however, the spectra in Fig. 3 show that the μ<sup>3</sup>-OH resonance (2.5 ppm) shifts with a concomitant increase in the intensity of the defect-based protons at 0 ppm. The latter implies that hydrolysis occurs over time leading to an increased defect density. Thus, in addition to capillary-force-driven collapse, the process of node-hydrolysis occurs slowly over time even in properly-activated UiO-67. However,

given the nominal decrease in SA over the course of a month, the MOF is clearly able to tolerate some hydrolysis of the linker-Zr bonds.

In order to probe the generality of our observations, we repeated the experiment with acetone and dichloromethane as the exchanged solvent (Fig. 4, Fig. S4 and S5 ESI).<sup>17</sup> Samples activated from dichloromethane (Fig. S5 ESI) showed evidence of amorphous material and was not further examined; we hypothesize that the low miscibility of water with dichloromethane, and thus a less-efficient solvent exchange, is responsible for the degradation of the MOF.

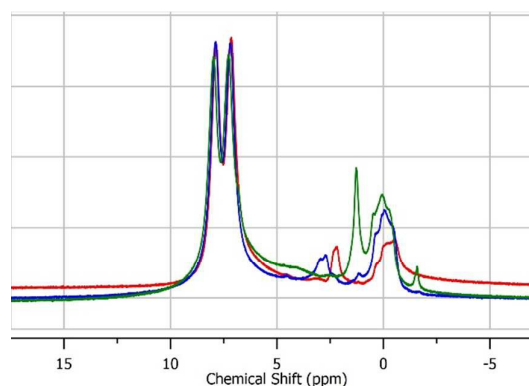


Fig. 3: (red) <sup>1</sup>H-NMR of UiO-67 immediately after thermal activation from methanol. (blue) <sup>1</sup>H-NMR of UiO-67 4 days after thermal activation. (green) <sup>1</sup>H-NMR of UiO-67 1 month after thermal activation. The corresponding <sup>13</sup>C-NMRs can be seen in Fig. S3.

However, when acetone was utilized (Fig. 4) the SS-NMR of the MOF initially indicated a more stable MOF with respect to hydrolysis (i.e., the peaks at 0 ppm do not shift or increase in intensity). However, after a month, the MOF was found to be completely amorphous with a BET SA of 500 m<sup>2</sup>g<sup>-1</sup> indicating that, eventually, the MOF succumbs to hydrolysis;<sup>18</sup> ultimately, we expect a similar fate to methanol-exchanged UiO-67.

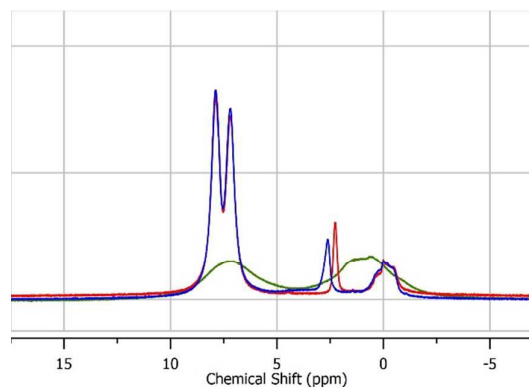


Fig. 4: (red) <sup>1</sup>H-NMR of UiO-67 immediately after thermal activation from acetone. (blue) <sup>1</sup>H-NMR of UiO-67 4 days after thermal activation. (green) <sup>1</sup>H-NMR of UiO-67 1 month after thermal activation. The corresponding <sup>13</sup>C-NMRs can be seen in Fig. S4.

As summarized in Table 1, SS-NMR in combination with SA measurements were used to examine the stability of UiO-67 with respect to time.<sup>19</sup> As evident by the changing chemical shift of the μ<sup>3</sup>-OH and defect-based resonance, SS-NMR is a key tool for the understanding of the dynamic behaviour

within MOFs. With respect to the stability of UiO-67, we observed that when solvent molecules remain inside the pore for a few days, then UiO-67 collapses rapidly. However, when solvent is removed at elevated temperatures, then UiO-67 remains stable for at least a month. Inevitably, hydrolysis, caused by the relative humidity, degrades the MOF beyond its structural integrity. In our hands, if kept dry or in solution, UiO-67 remains intact.

Table 1: Summary of SS-NMR observations correlated to BET SA and activation method and solvent.

Activation Method	Time (Days)	BET SA (m <sup>2</sup> /g)	SS-NMR observations
MeOH Wash	0	2000	MeOH present
	6	500	Crystalline and Amorphous
	0	2000	Defects present (0 ppm)
Thermal from MeOH	4	–	$\mu^3$ -OH shifts downfield, increased defect density
	30	1500	$\mu^3$ -OH shifts upfield, increased defect density, onset of amorphous material
	0	2000	Defects present (0 ppm)
Thermal from Acetone	4	–	$\mu^3$ -OH shifts downfield, no change in defect density,
	30	500	Completely amorphous
Thermal from DCM (ESI)	0	–	Amorphous material observed

## Acknowledgments


The 600 MHz SS-NMR was funded by CFI. The authors would like to acknowledge NSERC for financial support in the form of a Discovery Grant (MJK) and an Undergraduate Student Research Award (MCL). MJK would also like to acknowledge the RDC for an Ignite grant (MJK).

## Notes and references

- (a) J. A. Mason, M. Veenstra and J. R. Long, *Chem. Sci.*, 2014, **5**, 32-51; (b) B. Li, H.-M. Wen, W. Zhou and B. Chen, *J. Phys. Chem. Lett.*, 2014, **5**, 3468-3479; (c) O. K. Farha, A. Özgür Yazaydın, I. Eryazici, C. D. Malliakas, B. G. Hauser, M. G. Kanatzidis, S. T. Nguyen, R. Q. Snurr and J. T. Hupp, *Nat. Chem.*, 2010, **2**, 944-948; (d) J. B. DeCoste, M. H. Weston, P. E. Fuller, T. M. Tovar, G. W. Peterson, M. D. LeVan and O. K. Farha, *Angew. Chem. Int. Ed.*, 2014, **53**, 14092-14095; (e) Y. Liu, Z. U. Wang and H.-C. Zhou, *Greenhouse Gases Sci. Technol.*, 2012, **2**, 239-259.
- (a) D.-X. Xue, Y. Belmabkhout, O. Shekhah, H. Jiang, K. Adil, A. J. Cairns and M. Eddaoudi, *J. Am. Chem. Soc.*, 2015, **137**, 5034-5040; (b) L. E. Kreno, K. Leong, O. K. Farha, M. Allendorf, R. P. Van Duyne and J. T. Hupp, *Chem. Rev.*, 2012, **112**, 1105-1125; (c) E. Barea, C. Montoro and J. A. R. Navarro, *Chem. Soc. Rev.*, 2014, **43**, 5419-5430; (d) B. Van de Voorde, B. Bueken, J. Denayer and D. De Vos, *Chem. Soc. Rev.*, 2014, **43**, 5766-5788; (e) S. Qiu, M. Xue and G. Zhu, *Chem. Soc. Rev.*, 2014, **43**, 6116-6140.
- (a) C. Y. Lee, O. K. Farha, B. J. Hong, A. A. Sarjeant, S. T. Nguyen and J. T. Hupp, *J. Am. Chem. Soc.*, 2011, **133**, 15858-15861; (b) T. Zhang and W. Lin, *Chem. Soc. Rev.*, 2014, **43**, 5982-5993; (c) S. Jin, H.-J. Son, O. K. Farha, G. P. Wiederrecht and J. T. Hupp, *J. Am. Chem. Soc.*, 2013, **135**, 955-958; (d) K. Meyer, M. Ranocchiari and J. A. van Bokhoven, *Energy Environ. Sci.*, 2015, **8**, 1923-1937.
- (a) Z. Hu, B. J. Deibert and J. Li, *Chem. Soc. Rev.*, 2014, **43**, 5815-5840; (b) G. Lu and J. T. Hupp, *J. Am. Chem. Soc.*, 2010, **132**, 7832-7833; (c) Y. Cui, B. Chen and G. Qian, *Coord. Chem. Rev.*, 2014, **273-274**, 76-86.
- (a) J. Liu, L. Chen, H. Cui, J. Zhang, L. Zhang and C.-Y. Su, *Chem. Soc. Rev.*, 2014, **43**, 6011-6061; (b) C. M. McGuirk, M. J. Katz, C. L. Stern, A. A. Sarjeant, J. T. Hupp, O. K. Farha and C. A. Mirkin, *J. Am. Chem. Soc.*, 2015, **137**, 919-925; (c) J. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chem. Soc. Rev.*, 2009, **38**, 1450-1459; (d) L. Ma, C. Abney and W. Lin, *Chem. Soc. Rev.*, 2009, **38**, 1248-1256; (e) M. Yoon, R. Srirambalaji and K. Kim, *Chem. Rev.*, 2012, **112**, 1196-1231.
- (a) M. J. Katz, Z. J. Brown, Y. J. Colon, P. W. Siu, K. A. Scheidt, R. Q. Snurr, J. T. Hupp and O. K. Farha, *Chem. Commun.*, 2013, **49**, 9449-9451; (b) J. H. Cavka, S. Jakobsen, U. Olsbye, N. Guillou, C. Lamberti, S. Bordiga and K. P. Lillerud, *J. Am. Chem. Soc.*, 2008, **130**, 13850-13851; (c) S. J. Garibay and S. M. Cohen, *Chem. Commun.*, 2010, **46**, 7700-7702; (d) M. Kandiah, M. H. Nilsen, S. Usseglio, S. Jakobsen, U. Olsbye, M. Tilset, C. Larabi, E. A. Quadrelli, F. Bonino and K. P. Lillerud, *Chem. Mater.*, 2010, **22**, 6632-6640; (e) L. Valenzano, B. Civalieri, S. Chavan, S. Bordiga, M. H. Nilsen, S. Jakobsen, K. P. Lillerud and C. Lamberti, *Chem. Mater.*, 2011, **23**, 1700-1718; (f) M. J. Katz, J. E. Mondloch, R. K. Totten, J. K. Park, S. T. Nguyen, O. K. Farha and J. T. Hupp, *Angew. Chem. Int. Ed.*, 2014, **53**, 497-501; (g) S.-Y. Moon, G. W. Wagner, J. E. Mondloch, G. W. Peterson, J. B. DeCoste, J. T. Hupp and O. K. Farha, *Inorg. Chem.*, 2015, **54**, 10829-10833; (h) M. J. Katz, R. C. Klet, S.-Y. Moon, J. E. Mondloch, J. T. Hupp and O. K. Farha, *ACS Catal.*, 2015, **5**, 4637-4642; (i) J. M. Taylor, T. Komatsu, S. Dekura, K. Otsubo, M. Takata and H. Kitagawa, *J. Am. Chem. Soc.*, 2015, **137**, 11498-11506.
- (a) N. Planas, J. E. Mondloch, S. Tussupbayev, J. Borycz, L. Gagliardi, J. T. Hupp, O. K. Farha and C. J. Cramer, *J. Phys. Chem. Lett.*, 2014, **5**, 3716-3723; (b) J. E. Mondloch, W. Bury, D. Fairen-Jimenez, S. Kwon, E. J. DeMarco, M. H. Weston, A. A. Sarjeant, S. T. Nguyen, P. C. Stair, R. Q. Snurr, O. K. Farha and J. T. Hupp, *J. Am. Chem. Soc.*, 2013, **135**, 10294-10297.
- (a) D. Feng, Z.-Y. Gu, J.-R. Li, H.-L. Jiang, Z. Wei and H.-C. Zhou, *Angew. Chem.*, 2012, **124**, 10453-10456; (b) Z.-Y. Gu, J. Park, A. Raiff, Z. Wei and H.-C. Zhou, *ChemCatChem*, 2014, **6**, 67-75.
- (a) J. Jiang, F. Gándara, Y.-B. Zhang, K. Na, O. M. Yaghi and W. G. Klemperer, *J. Am. Chem. Soc.*, 2014, **136**, 12844-12847; (b) S.-Y. Moon, Y. Liu, J. T. Hupp and O. K. Farha, *Angew. Chem. Int. Ed.*, 2015, **54**, 6795-6799.
- (a) Y. Huang, W. Qin, Z. Li and Y. Li, *Dalton Trans.*, 2012, **41**, 9283-9285; (b) H. R. Abid, H. M. Ang and S. Wang, *Nanoscale*, 2012, **4**, 3089-3094.
- J. B. DeCoste, G. W. Peterson, H. Jasuja, T. G. Glover, Y.-g. Huang and K. S. Walton, *J. Mater. Chem. A*, 2013, **1**, 5642-5650.
- J. E. Mondloch, M. J. Katz, N. Planas, D. Semrouni, L. Gagliardi, J. T. Hupp and O. K. Farha, *Chem. Commun.*, 2014, **50**, 8944-8946.
- (a) S. Liu, Z. Yue and Y. Liu, *Dalton Trans.*, 2015, **44**, 12976-12980; (b) X. Zhu, B. Li, J. Yang, Y. Li, W. Zhao, J. Shi and J. Gu, *ACS Appl. Mater. Interfaces*, 2015, **7**, 223-231.
- Caution: desorption of solvent can cause damage to the rotor.
- W. Salomon, C. Roch-Marchal, P. Mialane, P. Rouschmeyer, C. Serre, M. Haouas, F. Taulelle, S. Yang, L. Ruhlmann and A. Dolbecq, *Chem. Commun.*, 2015, **51**, 2972-2975.
- (a) H. Wu, Y. S. Chua, V. Krungleviciute, M. Tyagi, P. Chen, T. Yildirim and W. Zhou, *J. Am. Chem. Soc.*, 2013, **135**, 10525-10532; (b) G. C. Shearer, S. Chavan, J. Ethiraj, J. G. Vitillo, S. Svelle, U. Olsbye, C. Lamberti, S. Bordiga and K. P. Lillerud, *Chem. Mater.*, 2014, **26**, 4068-4071; (c) P. Ghosh, Y. J. Colon and R. Q. Snurr, *Chem. Commun.*, 2014, **50**, 11329-11331; (d) M. J. Cliffe, W. Wan, X. Zou, P. A. Chater, A. K. Kleppe, M. G. Tucker, H. Wilhelm, N. P. Funnell, F.-X. Coudert and A. L. Goodwin, *Nat. Chem.*, 2014, **5**, 4176; (e) C. A. Trickett, K. J. Gagnon, S. Lee, F. Gándara, H.-B. Bürgi and O. M. Yaghi, *Angew. Chem. Int. Ed.*, 2015, **54**, 11162-11167.
- J. E. Mondloch, O. Karagiari, O. K. Farha and J. T. Hupp, *CryStEngComm*, 2013, **15**, 9258-9264.
- T. D. Bennett and A. K. Cheetham, *Acc. Chem. Res.*, 2014, **47**, 1555-1562.

19. Attempts to measure  $^{91}\text{Zr}$ -SS-NMR exhibited no discernible signal for UiO-67. NOESY-rfdr experiments showed signals between ligand protons, but no other interactions were observed.

**Table of Contents Graphic:**

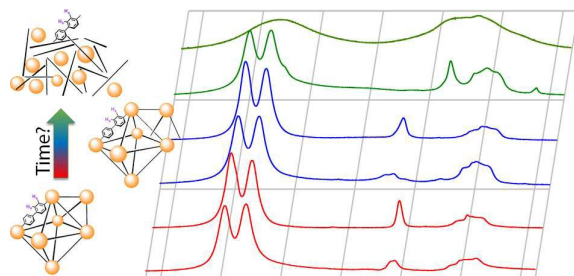

Revealing defects, the stability of UiO-67 was studied with SS-NMR as a function of time and activation method/solvent.