


# CrystEngComm

Accepted Manuscript

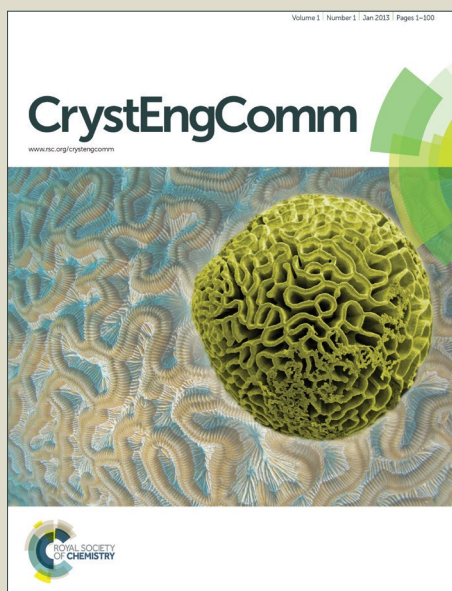

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



## Perfluorocarbon Liquid under Pressure: A Medium for Gas Delivery

Received 00th January 20xx,  
Accepted 00th January 20xx

Scott C. McKellar,<sup>a</sup> Jorge Sotelo,<sup>a</sup> John P. S. Mowat,<sup>b</sup> Paul A. Wright<sup>b</sup> and Stephen A. Moggach<sup>\*a</sup>

DOI: 10.1039/x0xx00000x

www.rsc.org/

**A novel method for CO<sub>2</sub> delivery to a porous material is reported, wherein a perfluorocarbon containing dissolved CO<sub>2</sub> has been used as a pressure-transmitting liquid in a high-pressure single-crystal X-ray diffraction experiment. Pressure causes the gas to be squeezed out of the liquid into the host crystal, monitored via a single-crystal to single-crystal phase transition on uptake of CO<sub>2</sub>.**

Perfluorocarbons (PFCs) are a family of liquids which have long been recognised as useful due to their capacity for dissolving large volumes of gas.<sup>1, 2</sup> They are colourless, odourless, chemically inert hydrocarbons in which the hydrogen atoms have been replaced with fluorine. First developed as corrosion inhibitors during World War II,<sup>3</sup> they now also have industrial applications as lubricants and coolants, with a wide range of linear, branched, cyclic or derivatised PFCs commercially available. The high solubility of respiratory gases such as CO<sub>2</sub> and O<sub>2</sub> in PFCs saw their usage expanded to biomedicine in the early 1990s with the launch of Flouso<sup>l</sup>, an emulsion of perfluorodecalin (C<sub>10</sub>F<sub>18</sub>) and perfluorotripropylene (C<sub>9</sub>F<sub>20</sub>). The solubility of O<sub>2</sub> in PFC liquids at 1 bar and 37°C is typically 40–50 % per volume of liquid, while that of CO<sub>2</sub> can exceed 200%. For comparison, the solubility of O<sub>2</sub> in water is 2.5 vol %.<sup>4</sup> PFCs attained ‘cult status’ in popular culture after the groundbreaking work of Clark demonstrated that mice could ‘breathe’ while submerged in oxygenated perfluorobutyltetrahydrofuran (C<sub>8</sub>F<sub>16</sub>O) liquid.<sup>1</sup> Solid porous materials with applications in gas storage and separation are of enormous interest across many disciplines of science, due in large part to current drives

towards clean energy and reduction of CO<sub>2</sub> emissions.<sup>5–8</sup> Inherent in such research is the requirement to optimise the quantity of gas that can be stored in the material. Evaluation of gas storage capacities is usually performed using gravimetric or calorimetric analysis over a range of temperatures and pressures. However, in the alternative method outlined here, we have used high-pressure, single-crystal X-ray diffraction to show for the first time how a PFC containing high concentrations of dissolved gas can be used as a pressure-transmitting medium, allowing us to literally squeeze gas into a host crystal from the surrounding liquid and calculate the gas uptake in a single experimental step at room temperature.

Previous work has shown that when surrounded by a pressure-transmitting liquid in the sample chamber of a modified Merrill-Bassett diamond anvil cell (DAC), the structural response of porous metal-organic frameworks (MOFs) to pressure can be highly sensitive to the liquid used to apply hydrostatic pressure to the sample.<sup>9</sup> For example, surrounded by a liquid small enough to penetrate the pores of the MOF, the framework can be super-filled, causing an expansion in unit cell volume as the liquid is squeezed into the void space. However, with larger media such as PFCs, the liquid is typically too large to penetrate the pore openings of most MOFs and thus direct compression of the framework occurs. These guest-dependant high-pressure results are an effective way to understand guest uptake and flexibility in porous MOFs, which have numerous potential related uses in applications such as gas storage<sup>10</sup>, molecular separation<sup>11</sup> and carbon capture.<sup>5</sup> In the work presented herein, the gas-dissolving capacity of PFCs has allowed us to investigate the application of these materials not just as media for compression experiments, but also as materials for pressure-induced gas delivery.


Our approach is fundamentally very simple; for a pressure-transmitting liquid, we selected Fluorinert<sup>TM</sup> FC-77 (Fig. 1a), a mixed PFC liquid comprised of perfluorooctane (C<sub>8</sub>F<sub>18</sub>) and perfluorooxacyclononane (C<sub>8</sub>F<sub>16</sub>O). FC-77 was chosen to demonstrate proof-of-concept since the liquid remains

<sup>a</sup> EaStCHEM School of Chemistry and the Centre for Science at Extreme Conditions, University of Edinburgh, Kings Buildings, West Mains Road, Edinburgh, EH9 3JJ, UK.

<sup>b</sup> EaStCHEM School of Chemistry, University of St Andrews, Purdie Building, St Andrews, KY16 9ST, UK. Address here.


\* email: s.moggach@ed.ac.uk

Electronic Supplementary Information (ESI) available: Experimental details on data collection, reduction and refinement, CO<sub>2</sub> dissolution and IR spectroscopy. See DOI: 10.1039/x0xx00000x. CCDC 1405820-1405822 contains the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data\_request/cif.

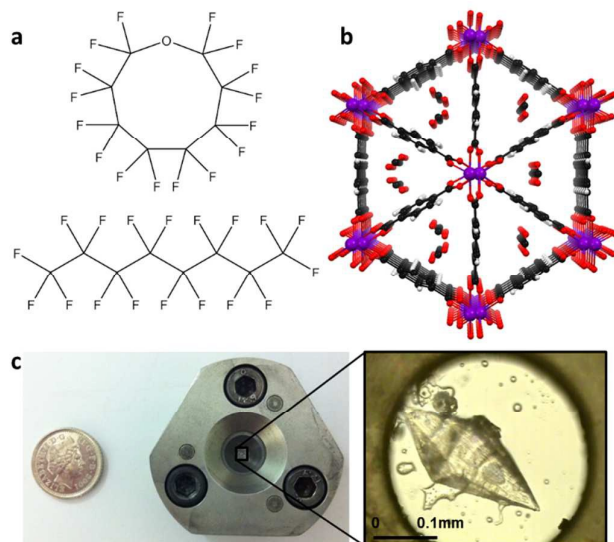

**Figure 1.** Materials used to perform high-pressure, single-crystal X-ray diffraction experiments. **a**, structure of Fluorinert™ FC-77; a mixed liquid consisting of perfluorooctane ( $C_8F_{18}$ ) and perfluorooxacyclononane ( $C_8F_{16}O$ ). **b**, six-channel portion of the previously-determined monoclinic  $Sc_2BDC_3$  crystal structure<sup>12</sup>, shown with partially-occupied adsorbed  $CO_2$  molecules in the framework pores. Purple, black, red and white spheres denote Sc, C, O and H atoms respectively. **c**, photograph of a modified Merrill-Bassett diamond anvil cell (DAC) (depicted beside a five-pence coin for scale), with an expanded photomicrograph of the sample chamber containing a single crystal of  $Sc_2BDC_3$  surrounded by  $CO_2$ -loaded FC-77 liquid.

hydrostatic up to GPa pressures<sup>13</sup> and because it has one of the highest gas-dissolving capacities of commercially available PFCs (56 ml  $O_2$ /100ml FC-77 and 224 ml  $CO_2$ /100ml FC-77 at 37°C).<sup>14</sup> As a host compound, the MOF  $Sc_2BDC_3$ <sup>15</sup> (Fig. 1b) (BDC = 1,4-benzenedicarboxylate) was used for two reasons. Firstly,  $Sc_2BDC_3$  has small (<4 Å diameter) hydrophobic pore openings that can adsorb a range of small gas molecules such as  $CO_2$ , carbon monoxide and methane, but the pores are too small to accommodate the bulky FC-77 molecules. Secondly, it has been shown previously that  $CO_2$  adsorption causes  $Sc_2BDC_3$  to

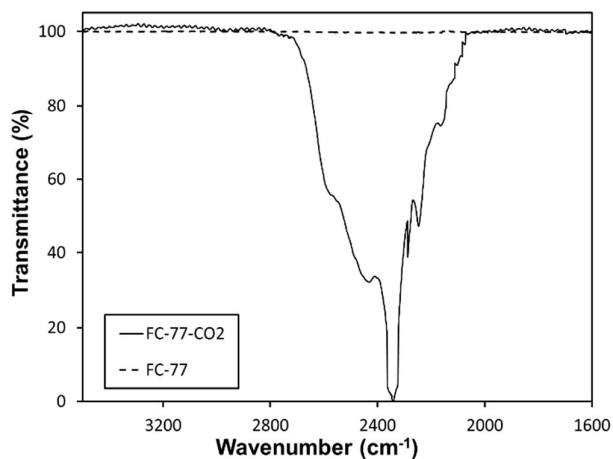

**Figure 2.** IR spectra of native FC-77 (dashed line) and  $CO_2$ -loaded FC-77 (solid line). The presence of  $CO_2$  in the liquid FC-77 is clearly visible from the characteristic asymmetric  $CO_2$  stretch at  $\sim 2385\text{ cm}^{-1}$ .

undergo a single-crystal-to-single-crystal phase transformation, characterised structurally by a slight rotation of the BDC linking molecules.<sup>12, 16</sup> Though the transition is subtle, it is easily detectable due to an associated change in crystal system from orthorhombic to monoclinic. No other guest species has been observed to trigger the phase transition. Therefore for the purposes of this work,  $Sc_2BDC_3$  has been used as a  $CO_2$  sensor with the phase change serving as an elegant indicator of  $CO_2$  uptake.  $CO_2$  was dissolved in the FC-77 by bubbling  $CO_2$  gas slowly through the liquid (see Supplementary Information). The presence of  $CO_2$  in the liquid was confirmed using IR spectroscopy (Fig. 2).

Initial X-ray diffraction data collected on a single crystal of  $Sc_2BDC_3$  at ambient temperature and pressure confirmed that the framework pores of the orthorhombic parent phase were free of any guest species (*i.e.* residual mother liquor solvent). Diffraction data were then collected on the same crystal whilst immersed in  $CO_2$ -loaded FC-77 at ambient pressure and temperature, using a bespoke method<sup>9</sup> whereby a  $Sc_2BDC_3$  crystal was stuck to the tip of a microloop inside a polyester capillary which was then filled with the PFC. This confirmed unambiguously that the face-centred orthorhombic symmetry of the as-prepared sample was maintained ( $Fddd$ ;  $a = 8.755(<1)\text{ \AA}$ ,  $b = 20.779(<1)\text{ \AA}$ ,  $c = 34.407(<1)\text{ \AA}$ <sup>15</sup>), indicating that the dissolved  $CO_2$  did not diffuse from the liquid into the crystal. A  $Sc_2BDC_3$  crystal was then loaded into a DAC at 1.7 kbar, with the  $CO_2$ -loaded FC-77 as a hydrostatic medium (Fig. 1c). At this pressure, crystal structure solution confirmed that the sample had adopted the monoclinic form indicative of  $CO_2$  uptake ( $C2/c$ ;  $a = 8.6929(18)\text{ \AA}$ ,  $b = 34.291(5)\text{ \AA}$ ,  $c = 11.0714(19)\text{ \AA}$ ,  $\beta = 111.014(13)^\circ$ ). Abridged crystallographic information for the ambient temperature/ambient pressure (1), ambient-pressure immersed (2) and high-pressure (3) crystal structures is provided in Table 1.

This result is, to the best of our knowledge, the first of its kind. It is known from previous work<sup>17</sup> that compression of  $Sc_2BDC_3$  in FC-77 causes the framework to experience direct compression with no change in the crystal symmetry. Therefore, the observed orthorhombic-to-monoclinic phase transition is due entirely to the  $CO_2$  uptake from the hydrostatic medium, and not due to structural rearrangement as a result of compression. This result (illustrated schematically in Fig. 3) shows that with the application of pressure, it is possible to squeeze gas from a PFC liquid into a porous framework as the system seeks to fill empty space and redistribute density upon contraction.

The  $CO_2$  guest molecules in the framework at 1.7 kbar were treated in the crystallographic model using the *PLATON SQUEEZE* algorithm. The calculated pore content was equivalent to 4.5 molecules of  $CO_2$  per  $Sc_2BDC_3$  unit cell; a calculated uptake of  $1.95\text{ mmol g}^{-1}$  at room temperature. This figure is somewhat lower than the maximum  $CO_2$  adsorption capacity measured independently for  $Sc_2BDC_3$  by Miller *et al.*<sup>12</sup> In this previous work, at 304 K, the Type 1 adsorption isotherm up to 50 bar showed a maximum  $CO_2$  adsorption of  $\sim 4.5\text{ mmol g}^{-1}$ . However, gas uptake increased significantly at lower


**Table 1.** Abridged crystallographic data and structure refinement parameters for  $\text{Sc}_2\text{BDC}_3$  at ambient temperature and ambient pressure (1), immersed in  $\text{CO}_2$ -loaded FC77 at ambient pressure (2) and at high-pressure in  $\text{CO}_2$ -loaded FC77 (3).

	1	2	3
Chemical formula	$\text{C}_{12}\text{H}_6\text{O}_6\text{Sc}$	$\text{C}_{12}\text{H}_6\text{O}_6\text{Sc}$	$\text{C}_{12}\text{H}_6\text{O}_6\text{Sc} \cdot 0.56(\text{CO}_2)$
Crystal system	Orthorhombic	Orthorhombic	Monoclinic
Space group	<i>Fddd</i>	<i>Fddd</i>	<i>C2/c</i>
<i>T</i> (K)	293.0	293.0	293.0
<i>a</i> (Å)	8.785 (6)	8.798 (2)	8.7007 (13)
<i>b</i> (Å)	20.810 (14)	20.865 (4)	34.271 (3)
<i>c</i> (Å)	34.480 (2)	34.551 (6)	11.0753 (12)
<i>V</i> (Å <sup>3</sup> )	6303 (7)	6342 (2)	3082.1 (7)
<i>Z</i>	16	16	8
<i>F</i> (000)	2352	2352	1176
Radiation type	Mo <i>K</i> α	Mo <i>K</i> α	Mo <i>K</i> α
$\mu$ (mm <sup>-1</sup> )	0.48	0.48	0.49
Crystal size (mm)	0.2 x 0.2 x 0.1	0.2 x 0.2 x 0.1	0.2 x 0.2 x 0.1
Reflections collected	5977	1914	4125
Independent reflections	831	771	972
Data / parameters	823 / 88	765 / 88	906 / 83
<i>R</i> <sub>int</sub>	0.059	0.109	0.093
$\sigma$ <sub>max</sub> (°)	20.8	20.8	22.7
$R[\overline{F}^2 > 2s(\overline{F}^2)]$ , <i>wR</i> ( <i>F</i> <sup>2</sup> )	0.031, 0.064	0.049, 0.111	0.121, 0.329
$\Delta\rho_{\text{max}} \Delta\rho_{\text{min}}$ (e Å <sup>-3</sup> )	0.35, -0.32	0.76, -0.67	0.89, -0.76

temperatures; the maximum uptake measured volumetrically was  $\sim 6.5 \text{ mmol g}^{-1}$ , achieved at 1 bar at 195 K and at 0.006 bar ( $p/p_0 = 1$ ) at 150 K. It is worth noting that use of the *SQUEEZE* algorithm is an estimate and is ideally performed on data sets with 100% completeness<sup>18</sup>, which is impossible in this instance due to shading by the DAC. However, we have previously shown that *SQUEEZE* can be used effectively in high-pressure datasets of MOFs to observe trends in pore content<sup>19</sup>, and accurately as a quantitative validation tool using guest species which can also be modelled crystallographically.<sup>20</sup>

The results obtained here would imply that there must be a barrier for diffusion of  $\text{CO}_2$  molecules into the framework when trapped within the PFC. However it has also been shown recently that particle size can play a significant role in the gas adsorption mechanics in MOFs,<sup>21</sup> which could explain the disparity between previous adsorption work, conducted using polycrystalline material, and the diffraction results reported here, performed using single crystals. Unfortunately, an atomistic model could not be obtained for localised  $\text{CO}_2$  sites within the MOF pores, therefore we could not determine whether the molecules retained the same geometry observed previously at 1 bar and 195 K. This is unsurprising considering the low data completeness and lower  $\text{CO}_2$  uptake at 1.7 kbar observed here. In previous measurements, only polarised infrared spectroscopy has been able to shed light on the orientation of  $\text{CO}_2$  molecules within  $\text{Sc}_2\text{BDC}_3$  at room temperature.<sup>22</sup>

The pressure in the DAC was then increased to 4.4 kbar in an attempt to push the limit of  $\text{CO}_2$  uptake from FC-77. At this pressure the  $\text{Sc}_2\text{BDC}_3$  crystal fractured and the resolution of the data decreased rapidly ( $\approx 1.3 \text{ \AA}$ ). Nevertheless, the sample could still be confirmed as being in the crystalline monoclinic phase. This work is the first example of a penetrating ( $\text{CO}_2$ ) and a non-penetrating (FC-77) medium being used simultaneously, so it is therefore interesting to speculate on the competing effect of the two given the different structural response that can be produced in porous frameworks. Previous work<sup>17</sup> has shown that native  $\text{Sc}_2\text{BDC}_3$  is not stable at pressures over  $\sim 4$  kbar whilst under direct compression in Fluorinert<sup>TM</sup>. However, super-filling of MOFs with penetrating guest molecules stabilises the frameworks to high pressures. It would therefore appear then, that even at low loadings of  $\text{CO}_2$ , the crystalline phase is stabilised to external pressure, preventing amorphisation. When comparing the unit cell parameters of the monoclinic  $\text{Sc}_2\text{BDC}_3$  at 1.7 kbar to the data collected at 4.4 kbar, contraction of all the unit cell axes takes place – as opposed to lengthening along the more flexible directions as is common in super-filled frameworks – suggesting that the direct compression at higher pressures exerted by the FC-77 outweighs any effect of possible super-filling with  $\text{CO}_2$ . Given the low uptake of  $\text{CO}_2$  previously calculated, and the fact that the sample is still crystalline at 4.4 kbar, it is easy to envisage that further filling of the pores with  $\text{CO}_2$  molecules may occur, further stabilising the crystalline monoclinic phase to amorphisation, but this requires further investigation.

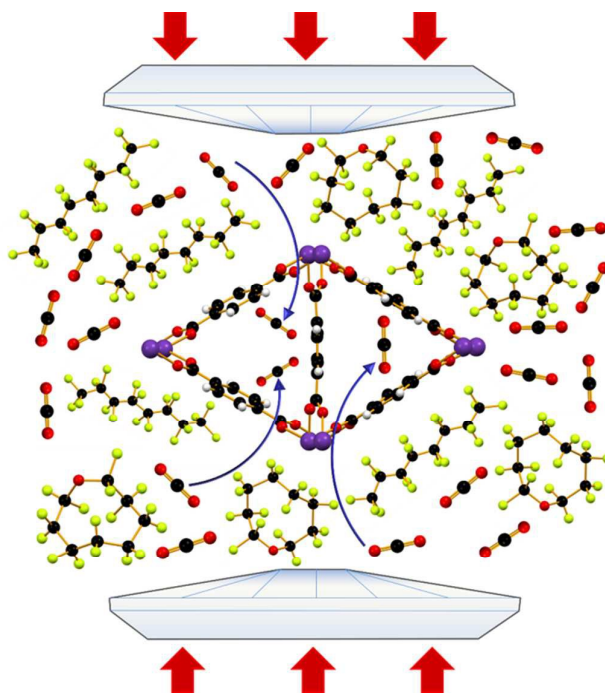

**Figure 3.** Cartoon schematic of pressure-induced  $\text{CO}_2$  loading of porous  $\text{Sc}_2\text{BDC}_3$  from liquid FC-77. Colour scheme as in Figure 1, with green spheres denoting F atoms. As pressure is applied to the  $\text{Sc}_2\text{BDC}_3$  crystal in the sample chamber between two diamond culets, dissolved  $\text{CO}_2$  in the liquid is squeezed into the previously empty framework. The molecules of the FC-77 are too large to penetrate the framework.

Though this method of using PFCs for gas-loading crystalline compounds under pressure is by no means limited to MOFs (nor is the gas necessarily limited to CO<sub>2</sub>), Sc<sub>2</sub>BDC<sub>3</sub> is a useful material


to demonstrate the application of the method since the use of porous MOFs as gas storage agents is currently a source of enormous interest in the research community.<sup>23</sup> This has been driven by advances in separation and carbon sequestration technologies<sup>5, 6</sup> in line with global government targets for cleaner energy and the reduction of CO<sub>2</sub> emissions.<sup>7, 24</sup> Innovative routes to CO<sub>2</sub> storage and the measurement of storage capacity is vital information for researchers considering scale-up and application of a particular MOF. Determination of the storage capacity *via* the construction of adsorption isotherms is usually performed using gravimetric or calorimetric

analyses over a range of different temperatures and pressures,<sup>12, 25-29</sup> often requiring gram-scale quantities of material. The results from our proof-of-concept study indicate that, in one experimental step, we can fill the pores with CO<sub>2</sub> and calculate the pore content with just one single crystal surrounded by FC-77 in a sample chamber of ~0.01 μL. Moreover, since our experiment is performed at room temperature, the structural response observed in the framework is more reflective of potential real-world gas storage material applications than the low temperatures used for adsorption isotherm construction, or indeed for standard X-ray diffraction experiments. We propose that as a method to quickly and efficiently probe the gas uptake and structural response of a material, pressure-induced gas loading from a PFC represents a unique approach and a complementary technique to classical gravimetric methods.

We thank the Royal Society of Edinburgh and the Scottish Government for a fellowship to Dr Stephen A. Moggach, and the Leverhulme Trust for financial support.

## References

1. L. C. Clark and F. Gollan, *Science*, 1966, 152, 1755-8.
2. J. G. Riess, *Chemical Reviews*, 2001, 101, 2797-2919.
3. K. C. Lowe, *Tissue Engineering*, 2003, 9, 389-399.
4. K. C. Lowe, *Journal of Materials Chemistry*, 2006, 16, 4189-4196.
5. P. Nugent, Y. Belmabkhout, S. D. Burd, A. J. Cairns, R. Luebke, K. Forrest, T. Pham, S. Ma, B. Space, L. Wojtas, M. Eddaoudi and M. J. Zaworotko, *Nature*, 2013, 495, 80-84.
6. S. Yang, J. Sun, A. J. Ramirez-Cuesta, S. K. Callear, W. I. F. David, D. P. Anderson, R. Newby, A. J. Blake, J. E. Parker, C. C. Tang and M. Schroeder, *Nature Chemistry*, 2012, 4, 887-894.
7. Z. Zhang, Y. Zhao, Q. Gong, Z. Li and J. Li, *Chemical Communications*, 2013, 49, 653-661.
8. R. E. Morris and P. S. Wheatley, *Angewandte Chemie-International Edition*, 2008, 47, 4966-4981.
9. S. C. McKellar, A. J. Graham, D. R. Allan, M. I. H. Mohideen, R. E. Morris and S. A. Moggach, *Nanoscale*, 2014, 6, 4163-4173.
10. P. L. Llewellyn, S. Bourrelly, C. Serre, A. Vimont, M. Daturi, L. Hamon, G. De Weireld, J.-S. Chang, D.-Y. Hong, Y. K. Hwang, S. H. Jung and G. Férey, *Langmuir*, 2008, 24, 7245-7250.
11. G. Lu and J. T. Hupp, *Journal of the American Chemical Society*, 2010, 132, 7832-+.
12. S. R. Miller, P. A. Wright, T. Devic, C. Serre, G. Férey, P. L. Llewellyn, R. Denoyel, L. Gaberova and Y. Filinchuk, *Langmuir*, 2009, 25, 3618-3626.
13. V. A. Sidorov and R. A. Sadykov, *Journal of Physics-Condensed Matter*, 2005, 17, S3005-S3008.
14. S. K. O. Ntwampe, C. C. Williams and M. S. Sheldon, *African Journal of Biotechnology*, 2010, 9, 1106-1114.
15. S. R. Miller, P. A. Wright, C. Serre, T. Loiseau, J. Marrot and G. Férey, *Chemical Communications*, 2005, DOI: 10.1039/b506677h, 3850-3852.
16. J. P. S. Mowat, S. R. Miler, J. M. Griffin, V. R. Seymour, S. E. Ashbrook, S. P. Thompson, D. Fairen-Jimenez, A.-M. Banu, T. Dueren and P. A. Wright, *Inorganic Chemistry*, 2011, 50, 10844-10858.
17. A. J. Graham, A.-M. Banu, T. Dueren, A. Greenaway, S. C. McKellar, J. P. S. Mowat, K. Ward, P. A. Wright and S. A. Moggach, *Journal of the American Chemical Society*, 2014, 136, 8606-8613.
18. A. L. Spek, *Acta Crystallographica Section C-Structural Chemistry*, 2015, 71, 9-18.
19. A. J. Graham, D. R. Allan, A. Muszkiewicz, C. A. Morrison and S. A. Moggach, *Angewandte Chemie-International Edition*, 2011, 50, 11138-11141.
20. S. C. McKellar, J. Sotelo, A. Greenaway, J. P. S. Mowat, O. Kvam, C. A. Morrison, P. A. Wright and S. A. Moggach, *in press*, 2015.
21. C. Zhang, J. A. Gee, D. S. Sholl and R. P. Lively, *Journal of Physical Chemistry C*, 2014, 118, 20727-20733.
22. A. Greenaway, B. Gonzalez-Santiago, P. M. Donaldson, M. D. Frogley, G. Cinque, J. Sotelo, S. Moggach, E. Shiko, S. Brandani, R. F. Howe and P. A. Wright, *Angewandte Chemie*, 2014, 126, 13701-13705.
23. N. R. Champness, *Dalton Transactions*, 2011, 40, 10311-10315.
24. J. D. Figueroa, T. Fout, S. Plasynski, H. McIlvried and R. D. Srivastava, *International Journal of Greenhouse Gas Control*, 2008, 2, 9-20.
25. A. R. Millward and O. M. Yaghi, *Journal of the American Chemical Society*, 2005, 127, 17998-17999.
26. S. J. Yang, T. Kim, J. H. Im, Y. S. Kim, K. Lee, H. Jung and C. R. Park, *Chemistry of Materials*, 2012, 24, 464-470.
27. H. Furukawa, N. Ko, Y. B. Go, N. Aratani, S. B. Choi, E. Choi, A. O. Yazaydin, R. Q. Snurr, M. O'Keeffe, J. Kim and O. M. Yaghi, *Science*, 2010, 329, 424-428.
28. C. Tan, S. Yang, N. R. Champness, X. Lin, A. J. Blake, W. Lewis and M. Schroeder, *Chemical Communications*, 2011, 47, 4487-4489.
29. L. Hamon, P. L. Llewellyn, T. Devic, A. Ghoufi, G. Clet, V. Guillerme, G. D. Pirngruber, G. Maurin, C. Serre, G. Driver, W. van Beek, E. Jolimaite, A. Vimont, M. Daturi and G. Férey, *Journal of the American Chemical Society*, 2009, 131, 17490-17499.

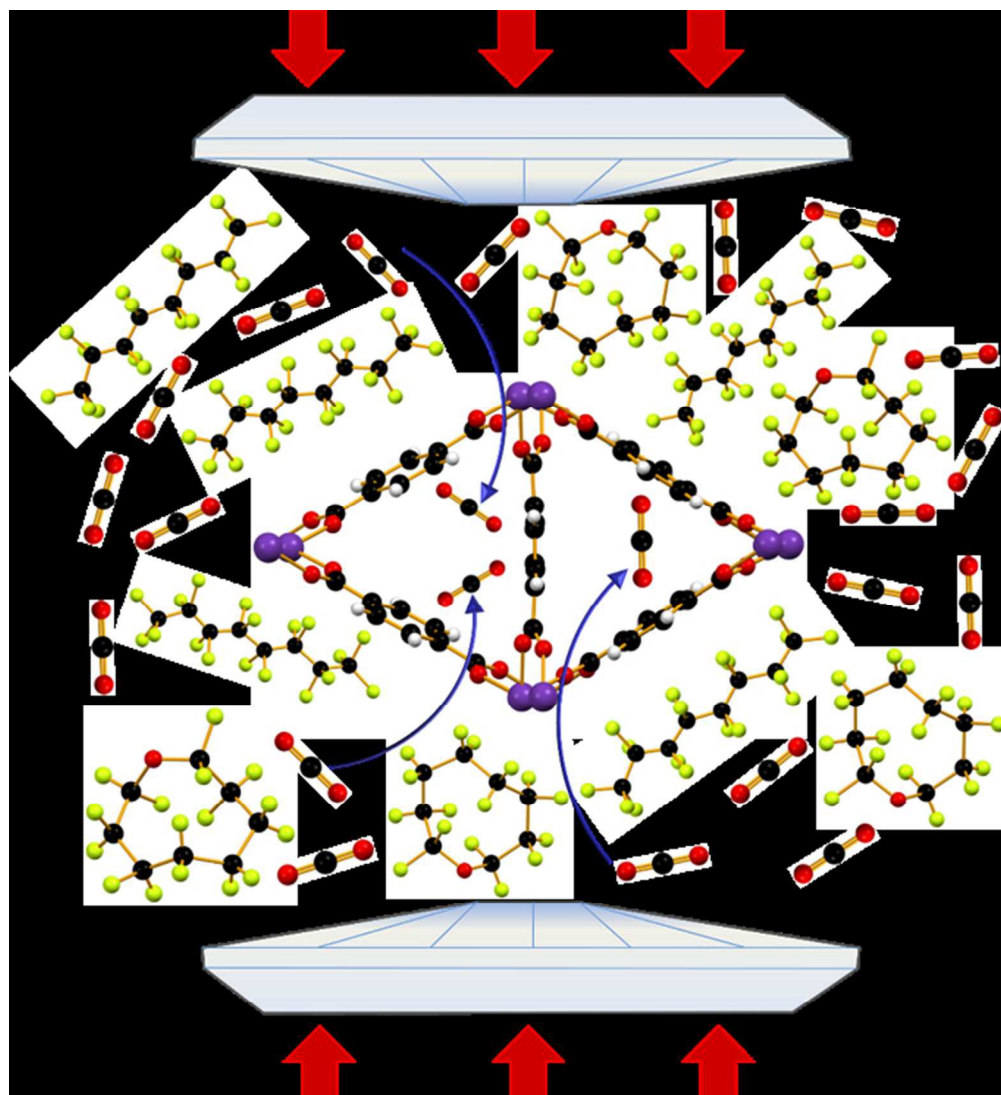

115x125mm (150 x 150 DPI)