

PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Thermally-induced chemical-order transitions in medium-large alloy nanoparticles predicted by a coarse-grained layer model

Micha Polak* and Leonid Rubinovich

A new coarse-grained layer model (CGLM) for efficient computations of axially symmetric elemental equilibrium configurations in alloy nanoparticles (NPs) is introduced and applied to chemical-order transitions in Pt-Ir truncated octahedrons (TOs) comprising up to tens of thousands atoms. The model is based on adaptation of the free energy concentration expansion method (FCEM) using as input coordination-dependent bond-energy variations (CBEV) that are extracted from DFT-computed elemental bulk and surface energies. Thermally induced quite sharp transitions from low- T asymmetric quasi-Janus and quasi ball-and-cup configurations to symmetric multi-shells furnish unparalleled core nanophase composite diagrams for 1289-, 2406- and 4033-atom NPs. At even higher temperatures entropic atomic mixing in the multi-shells gradually intensifies, as reflected in broad heat-capacity Schottky humps, which become sharper for much larger TOs (e.g., ~ 10 nm, $\sim 30,000$ atoms), due to transformation to solid-solution-like cores.

* Department of Chemistry, Ben-Gurion University of the Negev, Beer-Sheva 84105, Israel. E-mail: mpolak@bgu.ac.il

1. Introduction

In the extensive theoretical and experimental research devoted to alloy nanoparticles (NPs), considerable attention has been given recently to bi-metallic phase-separated (demixed) systems.¹ Such binary NPs are used in heterogeneous catalysis, and can find applications in other fields of technology, e.g., in biomedical drug delivery using core-shell configurations. Platinum-iridium nanoparticles are used as catalysts in organic molecule hydrogenation,² in oxygen reduction reactions,³ etc. The temperature dependent chemical order (or “compositional structure”), namely, the equilibrium atomic distribution of the two elements among the NP different surface and core sites, affects considerably its physical and chemical properties.¹

Previous theoretical-computational studies of NPs with separation tendency dealt mainly with cases of considerable size mismatch (>10%) between atoms of the two elements. Thus, in Cu, Ni or Co alloyed with Ag, the formation of side-separated “Quasi-Janus” configurations was attributed to near-surface elastic strain release using the Gupta potential and computational global optimization.^{4, 5} According to this and other methodologies (e.g., thermodynamics of spherical NPs) the tendency to form low- T asymmetric vs. symmetric configurations can depend on the composition, on the nanoparticle and core sizes, as predicted for a number of nanoalloy systems, such as Au-Pt,⁶ Cu-Ag,⁷⁻⁹ and Cu-Ni.¹⁰

Recently, atomic site-specific chemical order in fcc-based 201 and 586 atom Pt-Ir truncated-octahedron (TO) nanoparticles was studied¹¹ by us using near-surface coordination-dependent bond-energy variations (CBEV)¹² as input to the statistical-mechanical free-energy concentration expansion method (FCEM),¹³ which takes into account analytically short-range order. Thus, in this weakly miscible bi-metallic alloy having relatively small atomic-size mismatch, axially-symmetric quasi-Janus configurations were found to be stabilized at low temperatures mainly due to CBEV-induced preferential strengthening of Pt-surface/Ir-subsurface bonds, and the greatly reduced number of energetically unfavorable hetero-atomic bonds. At higher temperatures, the Pt-Ir quasi-Janus configurations transform into partially mixed central-symmetric multi-shell structures.

While this previous atomistic version of the FCEM could cope with structures comprising hundreds of atoms at the most, the present study aims at elucidating phase separation phenomena in significantly larger, more practical, NPs. For this goal, the FCEM has to become computationally more efficient by devising a model that facilitates a reduction in the number of compositional degrees of freedom via “mapping” atomic sites into groups. A similar principle was used, for example, in mesoscale molecular-dynamics simulations of polymers, proteins and carbon nanomaterials etc.^{14, 15} Pt-Ir has been chosen as a nanosystem model for the new “coarse-grained” FCEM version described below, while employing refined CBEV energetics, in an attempt to predict chemical-order transitions in thousands and tens thousands atom nanoparticles, with the ultimate goal of constructing the corresponding nanophase diagrams. The latter turn out to be highly involved and substantially distinct from our above-mentioned previous study for smaller NPs, as well as from the Pt-Ir bulk diagram.

2. Methodology

The FCEM expression for predicting alloy bulk and nanoparticle chemical order, was derived on the basis of nearest neighbor (NN) pair-interaction Hamiltonian within the rigid-lattice Ising model. Expanding the free energy in powers of constituent concentrations gives,¹⁶

$$F = kT \sum_p \left(N_p \sum_I c_p^I \ln c_p^I \right) + \sum_{p \leq q} N_{pq} \left(\frac{1}{2} \sum_I w_{pq}^I (c_p^I + c_q^I) - \sum_{\{IJ\}} \left(V_{pq}^{IJ} (c_p^I c_q^J + c_p^J c_q^I) + kT c_p^I c_p^J c_q^I c_q^J \frac{1}{b} \ln \left(\cosh \left(b \frac{2V_{pq}^{IJ}}{kT} \right) \right) \right) \right)$$

When applied to NPs consisting of geometrically nonequivalent atomic groups, numerical minimization of F (e.g., by MATLAB) yields all I -constituent equilibrium concentrations for group number p , c_p^I . Geometric input parameters include the number of atoms in each group, N_p , and the number of NN pairs belonging to p - and q - groups, N_{pq} . The first term stands for most of the configurational entropy, the second involves the elemental (homoatomic) interactions, w_{pq}^{II} , the third term includes the heteroatomic effective pair-interactions, V_{pq}^{IJ} , between constituents I and J ($V_{pq}^{IJ} = \frac{1}{2}(w_{pq}^{II} + w_{pq}^{JJ} - 2w_{pq}^{IJ})$), and the last term in F involves short-range order contributions ($b \approx 0.6$ is a constant obtained from a best fit of FCEM predictions to Monte Carlo simulations¹⁷). The FCEM is advantageous compared to the simplistic Bragg-Williams approach that neglects short-range order. In spite of its limitations, the FCEM has at least one major advantage over numeric computer simulations, namely, its much higher efficiency due to the use of the above explicit analytical expression, which can furnish the full temperature-dependence of chemical order and thermodynamic properties even for large NPs. Furthermore, FCEM computations exhibited reasonable accuracy when combined with energetics input based on the CBEV method (described below), expected especially for alloys with small atomic-size mismatch (for Pt-Ir NPs the roles of local strain and vibrational entropy were estimated to be minor¹¹). Thus, computational results were found to be in general agreement with direct DFT computations for small-size TO clusters of Pt-Pd¹⁸ and Pd-Ir,¹⁹ as well as with MEIS experimental data for Pt₂₅Rh₇₅(111).²⁰

In the previous version, referred to here as “fully atomistic FCEM” (FA-FCEM), the free-energy expression was minimized with respect to the number of all concentration variables, c_p^I , which amounts to the number of geometrically nonequivalent sites in central-symmetric or axially-symmetric nanostructures. Because of the rapid increase of this number with the NP size, making the computations extremely tedious (and feasible up to ~ 1000 atoms), we decided to devise a method to reduce the number of FCEM variables without losing too much accuracy. The attainable size is significantly extended here by a coarse-grained layer model (CGLM), in which similar adjacent atomic sites within a layer are grouped together with a single assigned concentration variable. In particular, as demonstrated by Fig.1, the method evaluates layer-by-layer subsurface and inner core “average concentrations”. (It should be noted that this grouping together of similar adjacent atomic sites differs substantially from a recently reported approach that puts atoms in equivalence sets defined on the basis of point group symmetry.²¹) For the 1289 atom TO core the number of concentration variables goes down to 28 from hundreds variables that have to be employed in the corresponding FA-FCEM. Due to the strong Pt surface segregation in this alloy, only four surface concentration variables, corresponding to sites having different coordinations, are used (namely, vertexes, edges, (100) and (111) faces). It can be noted that although a common variable is assigned to every layer-specific subsurface entity (Fig.1), its value is affected by an “integral” CBEV effect depending on the coordination of all neighboring surface sites. As an illustration, strong CBEV effects are expected to be associated with the NP central (layer #0) subsurface adjacent to many low-coordinated edge and vertex surface sites, as compared to layers #5 or #6 which intersect the surface mainly via (111) faces (Fig.1).

Although this computationally advantageous method provides concentration variations along a chosen axis only, this information can be valuable, for example in finding nanophase transitions involving symmetry breaking. (In some sense the CGLM resembles certain experimental methods providing insights of concentration gradients along a chosen direction.)

The CBEV approach, introduced by us several years ago,²⁰ derives the near-surface energetics input compatible with the FCEM by searching for a functional dependence of elemental bond-energy variations (δw_{pq}) on the corresponding pair coordinations. This is done for intra-surface and surface-subsurface bonds (two-layer model) by employing DFT computed surface energies in the pair-interaction expression,

$$\sigma = \sum_p \frac{1}{2} \left(\sum_{q(q \neq p)} \delta w_{pq} - \Delta Z_p w_b \right),$$

where w_b denotes the bulk bond-energy, related to the bulk energy per atom $w_b = E_b / 6$ (and $w_{pq} = w_b + \delta w_{pq}$). In particular, CBEV was approximated by a polynomial with coefficients fitted to (111), (110), (100), (311), (331), and (210) surface energies for each metallic element. For a $p-q$ pair bond with ΔZ_p and ΔZ_q broken bonds, δw_{pq} is considered as a function of symmetric, $x_{pq} = \Delta Z_p + \Delta Z_q$ and anti-symmetric, $y_{pq} = \Delta Z_p - \Delta Z_q$, coordination variables (y_{pq} takes into account the possible non-equivalence of two sites),

$$\delta w_{pq} = a_{1,0} x_{pq} + a_{2,0} x_{pq}^2 + a_{0,2} y_{pq}^2 + a_{3,0} x_{pq}^3 + a_{1,2} x_{pq} y_{pq}^2 + a_{4,0} x_{pq}^4$$

In this way, bond-energy variations are treated as coordination-dependent functions rather than numerical values. The implied basic assumption concerning the dominant effect of coordination, reflected in the use of common polynomials with element-specific coefficients, helps to circumvent transferability problems, namely, the need to repeat fitting of interactions for every site in a given nanoparticle surface structure. This makes the FCEM/CBEV combination highly efficient. Furthermore, as demonstrated below the high transparency of the CBEV helps to elucidate the origin of the distinct bond-energy variation effects on site-specific segregation in alloy nanoclusters.

Compared to our recent work,¹¹ elemental CBEV data are obtained here from refined DFT-computed elemental bulk and surface energies, as outlined elsewhere.¹⁹ According to both sets of energetics, surface sites are unfavorable for Ir atoms, which tend to segregate at the subsurface atomic sites since the strengthening of surface-subsurface Ir–Ir bonds (and presumably also Pt–Ir) is consistently larger than Pt–Pt bonds (Fig.2). This trend is stronger under the present energetics compared to our previous study of 923 Pt–Ir cuboctahedra,¹² and is qualitatively consistent with DFT studies of segregated structures in Pt₃Ir (211) surface²² and with a (slight) subsurface preference for a single Ir dopant atom in a 201-atom Pt TO.²³

3. Results and discussion

Since Pt atoms practically do not desegregate from the surface (<1% at ~ 1200 K), the study is focused on the NP-core chemical order and its variations. First, the CGLM is tested by comparison with predictions of our previous FA-FCEM computations¹¹ for the largest TO size accessible to it (586 atoms). Secondly, we present detailed comparative computations for several thousand atoms NPs having various compositions. Finally, the CGLM-FCEM/CBEV is applied to a single-composition 29881-atom Pt–Ir TOs revealing additional features.

3.1 Testing the CGLM (586-atom TO)

According to FA-FCEM computations (based on the former energetics)¹¹ made along the [111] symmetry axis in Pt₃₇₆Ir₂₁₀ TO, low- T asymmetric quasi-Janus structure transforms to symmetric multi-shell structure when concentrations of the corresponding front and back (or left/right) (111) layers in the QUASI-JANUS coincide at the transition temperature, T_{sym} (Fig.3a). Concentrations of the three chosen distinct subsurface sites are very close at all temperatures. Hence, the subsurface site concentration variables can be substituted by a single CGLM subsurface concentration, which, indeed, turns out to be close to the FA values, and so the transition temperature is quite accurately reproduced (Fig.3a). Thus, the two differently computed phase diagrams almost coincide for most of the NP compositions (Fig.3b). Since the 68 distinct sites (below the Pt surface) involved in the FA computations constitute only 8 layers, the number of corresponding concentration variables is significantly decreased to 14 in the CGLM. Although the CGLM output is somewhat less detailed, this advantage becomes crucial for large NPs. Moreover, for larger NPs the CGLM approximation, assigning one concentration

to all inner sites of each layer (Fig.1), becomes more and more justified, since the exact geometrical intra-layer position becomes then insignificant.

3.2 CGLM computations for 1289 atom TOs

Larger Pt-Ir TOs were studied using the CGLM for separation along the [100] axis (along which the layer density is lower and is preferred when using the refined energetics over the [111] axis used in sec. 3.1).

3.2.1 Low-Pt core

Computation results for ~28 at. % Pt core below the Pt-segregated surface are shown in Fig.4. The plots of inner-core layer concentrations vs. temperature exhibit a transition from quasi-Janus-like configurations to a symmetric configurations, reflected by the joining of the six Pt-side with the corresponding six Ir-side concentration curves at T_{sym} (Fig.4a). Above it the symmetric configuration comprises 7 core layer concentrations, including the central layer 0 (see Fig.1). The corresponding configurational heat-capacity curve (Fig.4b) exhibits a wide λ -peak²⁴ that reflects the pre-transition concentration variations (gradual mixing of Pt and Ir, Fig.4a). Fig.4c further demonstrates the symmetry-breaking character of the transition, namely, at 900 K the concentration profile across the inner-core is still asymmetric with a peaked Pt-rich region (adjacent to Ir-rich one) and becomes symmetric and wider at 1040 K. In other words, at $T < T_{sym}$ the alloy separation tendency breaks the symmetry in forming almost pure Ir layers by off-center shift of the Pt-rich region. At $T > T_{sym}$ more dominant configurational entropy effects establish symmetry by making equal the layer composition of geometrically-equivalent opposite pairs. Since the concentration profile should be symmetric with respect to *all* three [100] directions, a multi-shell concentric structure is anticipated. Thus, the thermally-induced changes in the concentration profile are consistent with transition from quasi-Janus to partially-mixed multi-shell configurations predicted in our FA-FCEM computations for the smaller 201- and 586-atom TOs.¹¹

At higher Pt content (38 at. % Pt core) the transition from quasi-Janus to multi-shell configurations is quite minor and occurs at significantly lower T_{sym} followed by thermally induced gradual mixing of the multi-shell structure (Fig.5a). The latter contributes to a more significant heat capacity hump (Fig.5b) with a shape characteristic of a ‘‘Schottky anomaly’’.²⁵ The hump maximum at T_{Sck} indicates the most intensive Pt-Ir mixing process. The T_{sym} lowering stems from geometric constraints that hamper formation of significantly asymmetric nanophase at this composition, namely, the corresponding broader Pt maximum can shift only slightly upon approaching the transition (Fig.5c). (This prediction is consistent with statistical arguments concerning the tendency to form asymmetric configurations when the separated region is small, while for large one off-center preference should disappear.⁵) The shift is not accompanied by significant mixing and energy change, and therefore the heat-capacity exhibits just a weak feature at T_{sym} (Fig.5b). It can be noted that in the previous case of 28 at. % Pt core actually T_{sym} and T_{Sck} coincide (Fig.4). Furthermore, for both NP compositions the thermally-induced changes are accompanied by increase in the number of Pt-Ir bonds (Table 1). However, this increase amounts to 284 bonds in a pre-transition range of 140 K for the 28 at. % Pt core due to intense mixing that appears to be associated mainly with interphase broadening (Fig.4c), whereas in the case of the 38 at. % Pt core the corresponding increase amounts to only 69 Pt-Ir bonds, since the latter transition is associated mainly with weak mixing of the slightly shifted nanophase boundaries (Fig.5c). Above the transitions multi-shell mixing is manifested in decreased/increased amounts of extra Pt-Ir bonds (per degree) in the case of 28 % vs. 38 % Pt cores (Table 1).

3.2.2. Medium-Pt core

In this range, Pt gradually fills sub-surface layers until a ‘‘magic composition’’, with pure Pt inner-core and Ir subsurface, is formed. Now the concentration profile is symmetric even at

$T = 0$ (no transition) exhibiting an ideal multi-shell structure (Fig.6a, inset). This is closely associated with the above-mentioned CBEV-induced strong tendency of Ir to preferentially populate all subsurface sites. Correspondingly, the Pt concentrations are very low even at $T = 300$ K, and the subsurface profile deviates only slightly from the ideal multi-shell, namely it exhibits two very shallow Pt peaks, divided by a minimum at the central layer, which start to grow with temperature due to entropic mixing (Fig.6a). The minimum originates from the enhanced Ir population in sub-edge sites of this layer (Fig.1) due to their larger surface-subsurface CBEV effects.

3.2.3 High-Pt core

In particles with Pt content exceeding the number of inner-core sites, so it occupies some subsurface sites, Ir accumulates asymmetrically at low-temperatures, forming quasi ball-and-(subsurface)-cup structure (Fig.6b). These configurations transform to symmetric subsurface concentration profiles having again a central minimum. The transition temperatures are generally lower than in the low-Pt core region, as described below.

3.3 Nanophase diagrams (1289, 2406 and 4033 atom TOs)

The same computations done for 2406- and 4033-atom TOs furnish all the asymmetry-symmetry transition temperatures. Plotting T_{sym} vs. composition gives the corresponding nanophase diagrams (Fig.7). As indicated above, three composition ranges can be distinguished in the diagrams:

(I) The low-Pt-core separation-coexistence line (dome) marks inner-core transitions from quasi-Janus to partially-mixed multi-shell configurations. With increase of NP size the dome widens, shifts to higher temperatures and its apex starts to turn towards the center in the direction of the bulk diagram. These variations are associated with the increase in the fraction of inner-core atoms with NP size, namely, $\sim 57\%$, $\sim 65\%$ and $\sim 70\%$ of the core atoms in 1289-, 2406- and 4033-atom TOs, respectively. It can be noted that T_{sym} and T_{Sck} coincide for all compositions up to the apex (see Fig.4), whereas above it $T_{sym} < T_{Sck}$, since, as noted above, geometric constraints hamper significant asymmetric shift of the broad Pt-rich region, and most of the mixing takes place gradually at higher temperatures (see Fig.5).

(II) This intermediate Pt concentration region below the magic-composition (Ir-subsurface@Pt-inner-core) is characterized by greatly size-dependent, somewhat irregular variations in the quite low transition temperatures. For the 1289 TO in addition to the magic composition (57% Pt core) $T_{sym} = 0$ also for 44% Pt core that is another fully symmetric configuration, which involves Ir in sub-subsurface sites, and reflects again the subtle interplay of geometric constraints, composition and near-surface energetics.

(III) The high-Pt-core dome that corresponds to intra-subsurface separation is lower than the dome in region I since this 2D “cup” configuration is naturally less stable than the 3D quasi-Janus separated structure. In addition, it gradually becomes narrower and shifts to the right with the NP size increase due to geometrical-compositional factors. Ultimately, this portion of the nanophase diagram is expected to disappear for very large particles (in the bulk limit). It can be noted that the predicted intra-subsurface separation, reflected in this second dome, occurs due to a strong CBEV-induced uniform tendency of Ir atoms to segregate at all subsurface sites. With the former energetics this tendency is weaker and a side-separated Ir cluster starts to grow preferentially from one of the (111) subsurfaces¹¹ and hence the diagram has just a single dome (Fig.3).

3.4 6266 and 29881 atom TOs

Due to the significant reduction of the number of concentration variables, the CGLM can cope even with much larger NPs. Compared to the variations shown in Fig.5a, the most prominent new feature for these sizes is the sharpening of the smeared region of intensive atomic mixing near T_{Sck} . Thus, a rather distinct transition to a solid-solution-like nanophase is obtained, especially for the 29881-atom NP (Fig.8a-b), which starts to approach ($T_{Sck} = 1390$ K) the bulk value for this composition (~ 1490 K, Fig.7). Correspondingly, the shape of Schottky anomaly

(Fig.8c) starts to resemble somewhat a heat-capacity feature characteristic of a “mean-field” computed bulk phase transition. Similarly to the case illustrated in Fig.5, the low- T symmetry-breaking transition ($T_{sym} \ll T_{Sck}$) is not accompanied by substantial mixing and energy change, but mainly by a small shift of nanophase boundaries, which, as shown in Fig.8c is only slightly reflected in the heat-capacity plots. In agreement with the above and earlier results,^{6, 8} the predicted sequence of nanophases for the 29881-atom NP starts with the more stable Janus-like asymmetric core configurations as compared to the multi-shell structures, followed by solid-solution-like cores that are thermodynamically the least stable.

4. Conclusions

Transitions between asymmetric and symmetric configurations in relatively large alloy nanoparticles with separation tendency were studied by a new coarse-grained layer model (CGLM) in the framework of the free energy concentration expansion method (FCEM). The input energetics is based on coordination-dependent bond-energy variations (CBEV) extracted from newly refined DFT-computed elemental bulk and surface energies. Thus, the highly efficient combination of FCEM/CBEV and CGLM enables extensive computations of temperature-induced nanophase symmetry-breaking transitions in Pt-Ir truncated octahedrons consisting of thousands and tens thousands of atoms. Although the CGLM output is inherently somewhat less detailed than site-by-site fully atomistic calculations, it is proven to be a reasonably accurate approximation even for several hundred atom NPs. The advantage in reducing the numbers of concentration variables becomes crucial for larger NPs, for which the accuracy is expected to further increase with size.

The vast amount of output data enable to construct a unique, perhaps the first of its kind, nanophase composite diagram comprising distinct composition ranges where inner-core (quasi-Janus) and intra-subsurface (quasi ball-and-cup) configurations are stabilized at low T and transform to partially mixed multi-shells, which gradually mix further to form ultimately solid-solution-like cores. The third (intermediate) region includes low- T “magic composition” multi-shell structures that do not undergo any thermally-induced nanophase transition.

According to preliminary computations for complementary TOs comprising up to tens of thousands atoms, the critical temperature (at the diagram apex) vs. NP size exhibits finite size scaling behavior,²⁶ to be reported elsewhere. In addition to Pt-Ir that was chosen as a model system, the CGLM should be appropriate for medium-large nanoparticles of other weakly-miscible alloys and is not limited to small-size-mismatch ones or to the use of CBEV energetics.

Acknowledgments

This work was supported by the Israel Science Foundation (grant No. 391/12). L.R. is thankful to the Israel Ministry of Immigrant Absorption, for the continued financial support under the KAMEA program. The authors would like to thank the European Cooperation in the field of Scientific and Technical Research (COST) Action MP0903 “Nanoalloys as advanced materials: from structure to properties and applications”. We are grateful to Jack B. A. Davis from the University of Birmingham in the UK for providing DFT-computed Pt bulk and surface energy data.

1. R. Ferrando, J. Jellinek and R. L. Johnston, *Chemical Reviews*, 2008, **108**, 845-910.
2. J. A. Toledo-Antonio, C. Angeles-Chavez, M. Antonia Cortes-Jacome, I. Cuauhtemoc-Lopez, E. Lopez-Salinas, M. Perez-Luna and G. Ferrat-Torres, *Applied Catalysis a-General*, 2012, **437**, 155-165.

3. S. J. Hwang, S. J. Yoo, T.-Y. Jeon, K.-S. Lee, T.-H. Lim, Y.-E. Sung and S.-K. Kim, *Chemical Communications*, 2010, **46**, 8401-8403.
4. D. Bochicchio and R. Ferrando, *Physical Review B*, 2013, **87**.
5. R. Ferrando, *J. Phys.: Condens. Matter*, 2015, **27**, 013003.
6. Y. Wang and M. Hou, *Journal of Physical Chemistry C*, 2012, **116**, 10814-10818.
7. A. Christensen, P. Stoltze and J. K. Nørskov, *Journal of Physics-Condensed Matter*, 1995, **7**, 1047-1057.
8. F. Delogu, *Journal of Physical Chemistry C*, 2010, **114**, 19946-19951.
9. I. Atanasov, R. Ferrando and R. L. Johnston, *Journal of Physics-Condensed Matter*, 2014, **26**.
10. G. Guisbiers, S. Khanal, F. Ruiz-Zepeda, J. R. de la Puente and M. Jose-Yacamán, *Nanoscale*, 2014, **6**, 14630-14635.
11. M. Polak and L. Rubanovich, *Physical Chemistry Chemical Physics*, 2014, **16**, 1569-1575.
12. H. Tigger, L. Rubanovich and M. Polak, *Journal of Physical Chemistry C*, 2012, **116**, 26000-26005.
13. M. Polak and L. Rubanovich, *Surface Science Reports*, 2000, **38**, 127-194.
14. J. A. Elliott, *International Materials Reviews*, 2011, **56**, 207-225.
15. L. Ruiz, W. Xia, Z. Meng and S. Keten, *Carbon*, 2015, **82**, 103-115.
16. M. Polak and L. Rubanovich, *Surface Science*, 2005, **584**, 41-48.
17. J. M. Roussel, A. Saul, L. Rubanovich and M. Polak, *Journal of Physics-Condensed Matter*, 1999, **11**, 9901-9906.
18. L. RUBINOVICH, *Nano Letters*, 2011, **11**, 1766-1769.
19. J. B. A. Davis, R. L. Johnston, L. Rubanovich and M. Polak, *Journal of Chemical Physics*, 2014, **141**, 224307.
20. L. Rubanovich and M. Polak, *Physical Review B*, 2009, **80**.
21. G. Barcaro, L. Sementa and A. Fortunelli, *Physical Chemistry Chemical Physics*, 2014, **16**, 24256-24265.
22. R. Callejas-Tovar and P. B. Balbuena, *Surface Science*, 2008, **602**, 3531-3539.
23. J. B. A. Davis, *private communication*, 2014.
24. Y. Mnyukh, *arXiv*, 2011, **1104.4637**.
25. M. Polak and L. Rubanovich, *Physical Review B*, 2005, **71**.
26. J. C. Lee, *Thermal Physics: Entropy and Free Energies.*, World Scientific Publishing, Singapore, 2002.

Table 1 Thermally-induced variations in the number of heteroatomic bonds in 1289 atom TO: comparison between two compositions

% Pt core	Temperature, K	Number of Pt-Ir bonds
28	900	2442
	1040^a	2726
	1200	2827
38	450	2169
	590^a	2238
	1040	2495

^a Transition temperature, T_{sym} .

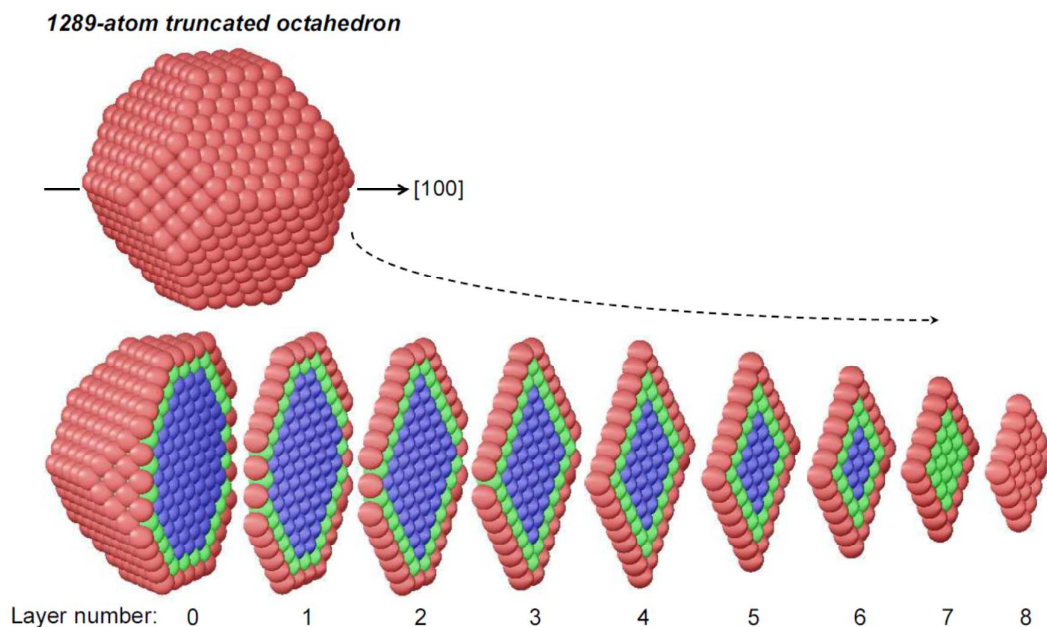


Fig.1. Illustration of the coarse-grained layer model (CGLM): the number of concentration variables is reduced by grouping together atomic sites within layers perpendicular to a chosen axis. Distinct concentration variables correspond to: (a) surface sites (red) having four different coordinations (vertexes, edges, (100) and (111) faces), (b) core sites in two locations: the inner-core (blue) and the subsurface (green).

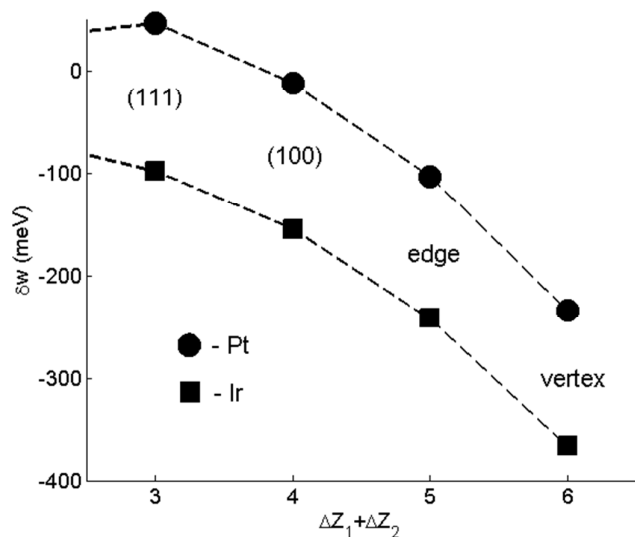


Fig.2. The dependence of surface-subsurface bond-energy variations, δw , on the number of pair broken bonds, $\Delta Z_1 + \Delta Z_2$, as extracted from DFT-computed surface energies (bulk bond energies are: $w_b^{Pt} = -1.160$ eV, $w_b^{Ir} = -1.635$ eV).

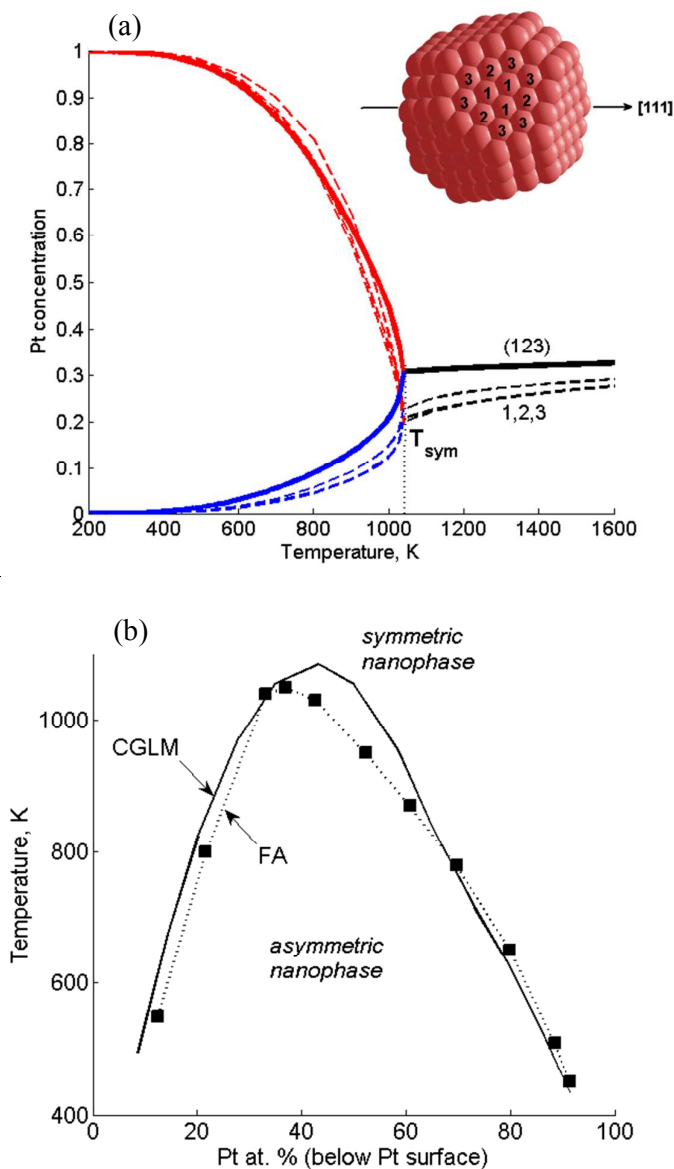


Fig.3. Verification of the coarse-grained layer model (CGLM): Asymmetric-symmetric transitions along the [111] axis in Pt₃₇₆Ir₂₁₀ TOs computed with the CGLM-FCEM vs. the fully-atomistic (FA)-FCEM. (a) Three distinct subsurface site concentrations (thin dashed lines) vs. one subsurface layer concentration computed using the CGLM (thick solid lines). Below the transition at T_{sym} , Pt-side - red, Ir-side - blue. The site positions are marked in the subsurface schematics (inset); (b) Nanophase diagram computed in the CGLM (thick solid line), compared to the diagram obtained by the FA computation¹¹ (■ - magic-number compositions).

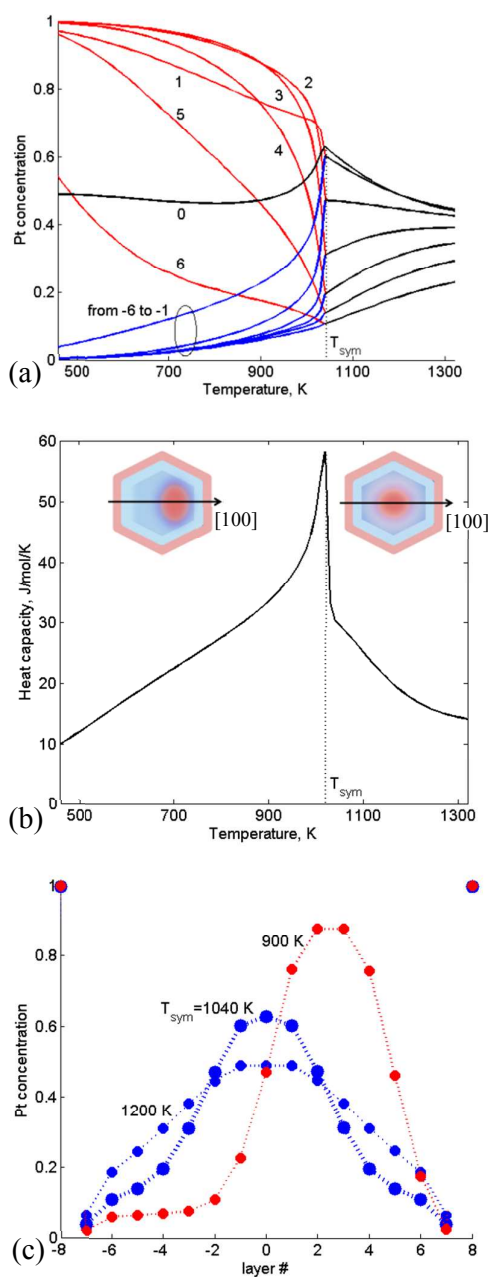


Fig.4. CGLM-FCEM computation results for 1289-atom TO with 28 at. % Pt core: (a) Thermally-induced variations of the Pt-side (red) and Ir-side (blue) inner core layer concentrations, which coincide (black) at the transition temperature T_{sym} . Inset: schematics of asymmetric (quasi-Janus) and symmetric (multi-shell) configurations below and above T_{sym} . (b) The corresponding configurational heat-capacity λ -peak. (c) Layer concentration profiles for $T < T_{sym}$, $T = T_{sym}$ and $T > T_{sym}$. Layer numbering corresponds to Fig.1.

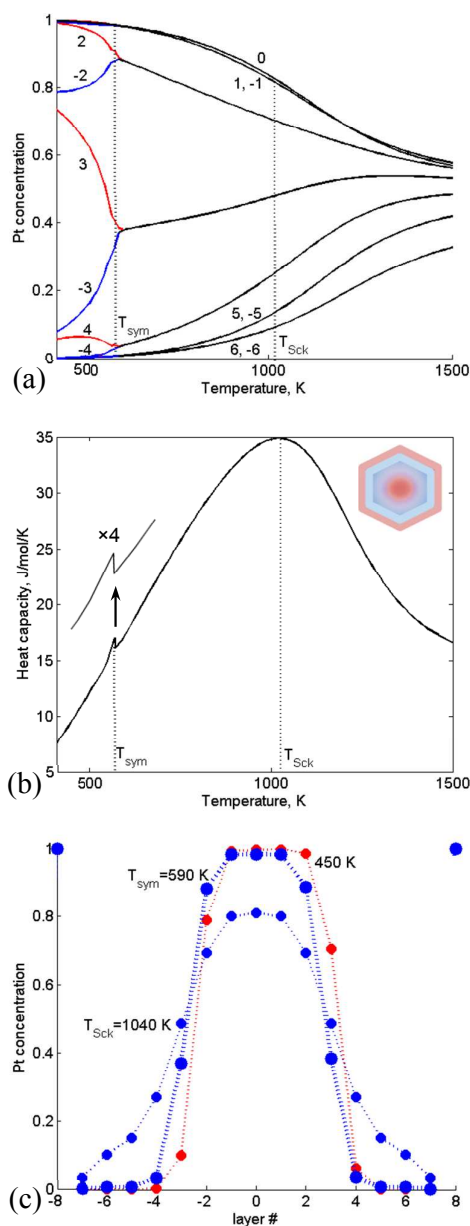


Fig.5. CGLM-FCEM results for 1289-atom TO with 38 at. % Pt core (along the [100] axis): (a) Thermally-induced variations of the Pt-side (red) and Ir-side (blue) inner core layer concentrations, which coincide (black) at the transition temperature T_{sym} . (b) The corresponding configurational heat-capacity Schottky hump with maximum at $T_{Sck} \gg T_{sym}$ and a weak sharp feature related to the symmetry-breaking minor transition. Inset: schematics of a symmetric (multi-shell) configuration above T_{sym} . (c) Layer concentration profiles for $T < T_{sym}$, $T = T_{sym}$ and $T > T_{sym}$. Layer numbering corresponds to Fig.1.

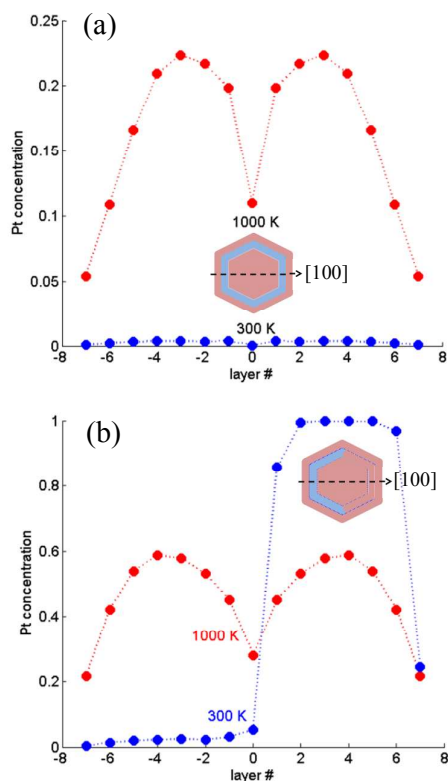


Fig.6. Subsurface layer concentration profiles computed for 1289-atom TO. (a) Magic composition (~ 57 at. % Pt core): multi-shell structure without a transition; (b) ~ 75 at. % Pt core: asymmetric quasi ball-and-(subsurface)-cup at 300 K and symmetric profile at 1000 K. Layer numbering corresponds to Fig.1.

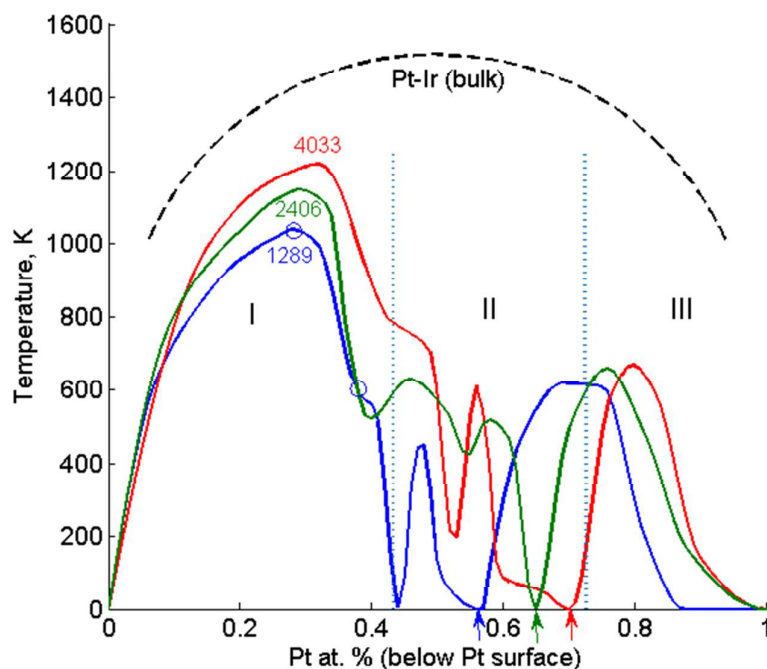


Fig.7. Nanophase diagram of symmetry-breaking transitions in Pt-Ir TO NPs (with marked sizes) computed by the CGLM-FCEM. The left (I) and right (III) domes correspond to inner-core quasi-Janus and subsurface quasi ball-and-cup transitions to multi-shell configurations, respectively. The intermediate region (II) involves ideal multi-shell (no transitions) at “magic compositions” indicated by arrows (Pt-surface@Ir-subsurface@Pt-inner-core). The transitions presented in Figs. 4 and 5 are marked by small circles on the separation-coexistence dome of the 1289-atom TO. FCEM-computed bulk diagram miscibility gap is shown for comparison.

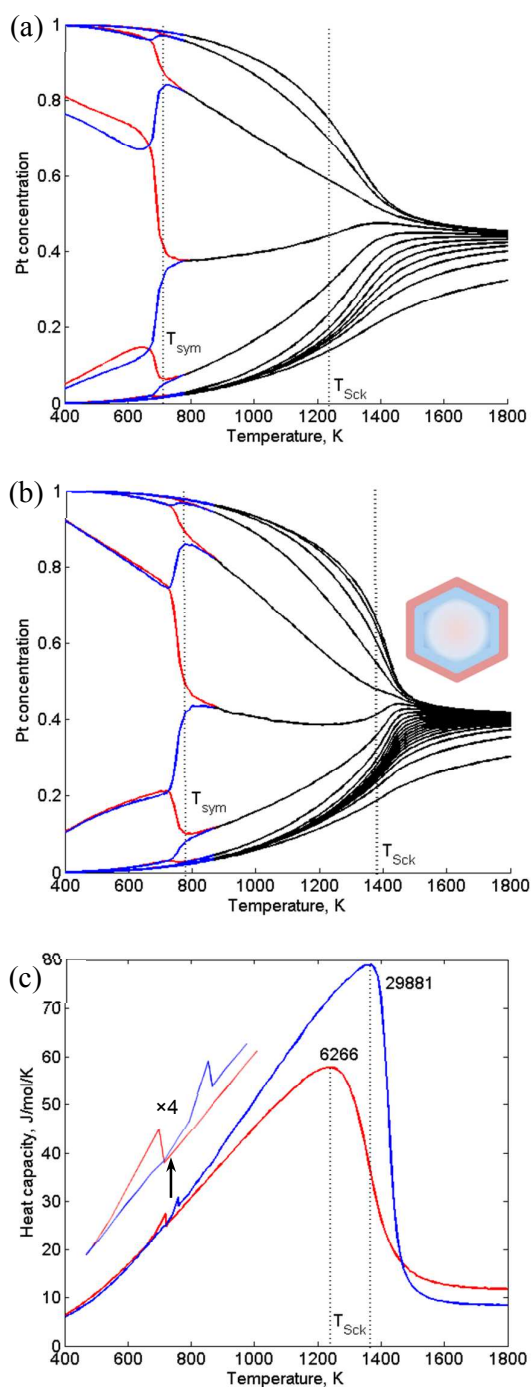


Fig.8. Variations with temperature of the inner core layer concentrations in 6266-atom (a) and 29881-atom (b) TOs (37 at. % Pt core); (c) Heat-capacity Schottky humps corresponding to the indicated TO sizes. The weak features around 700 K correspond to symmetry-breaking transitions accompanied by nanophase boundary small shifts.