

PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Connecting Defects and Amorphization in UiO-66 and MIL-140 Metal-organic Frameworks: A Combined Experimental and Computational Study

Thomas D. Bennett^{a*}, Tanya K. Todorova^b, Emma F. Baxter^a, David G. Reid^c, Christel Gervais^d, Bart Bueken^e, B. Van de Voorde^e, Dirk De Vos^e, David A. Keen^f and Caroline Mellot-Draznieks^{b*}

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

The mechanism and products of the structural collapse of the metal-organic frameworks (MOFs) **UiO-66**, **MIL-140B** and **MIL-140C** upon ball-milling are investigated through solid state ¹³C NMR and pair distribution function (PDF) studies, finding amorphization to proceed by the breaking of a fraction of metal-ligand bonding in each case. The amorphous products contain inorganic-organic bonding motifs reminiscent of the crystalline phases. Whilst the inorganic Zr₆O₄(OH)₄ clusters of **UiO-66** remain intact upon structural collapse, the ZrO backbone of the **MIL-140** frameworks undergoes substantial distortion. Density functional theory calculations have been performed to investigate defective models of **MIL-140B** and show, through comparison of calculated and experimental ¹³C NMR spectra, that amorphization and defects in the materials are linked.

Introduction

Crystalline metal-organic frameworks (MOFs) continue to be of interest to the scientific community due to their high surface areas and related potential for gas sorption, separations, drug delivery and catalysis.^{1, 2} Comparatively little attention is however focused on their amorphous counterparts, i.e. those which do not exhibit long range crystallographic order, yet still consist of three-dimensional arrays of connected inorganic nodes and organic ligands.³⁻⁵ The use of pressure, temperature or shear stress to induce transitions between crystalline and amorphous states is of particular intrigue,⁶⁻⁸ due to possible uses in reversible sorption, conductive and multiferroic applications.⁹ Whilst computational or experimental characterization of purely inorganic¹⁰ or organic¹¹ amorphous frameworks is known, structural insight into amorphous MOFs (*a*MOFs) is largely limited to those which adopt similar network topologies to the zeolite family.¹²

50

Mechanochemistry, or ball-milling is increasingly utilized to synthesize crystalline MOFs in relatively large quantities with minimal solvent use.¹³ Curiously, and unlike other inorganic porous materials, MOFs are highly susceptible to collapse using the same treatment.¹⁴ Whilst this can be mitigated by pore-filling prior to treatment, it remains problematic given the use of ball-milling as a common post-processing method to increase external surface area.^{15, 16} This propensity for collapse has previously been linked to the low shear moduli of the family,¹⁷ although recent reports have emerged that appear to contradict this argument.^{18, 19}

The zirconium-based MOF **UiO-66** [Zr₆O₄(OH)₄(O₂C-C₆H₄-CO₂)₆]²⁰ crystallizes in the space group *Fm* $\bar{3}$ *m*, and consists of Zr₆O₄(OH)₄ octahedra connected together by benzene-1,4-dicarboxylate (**bdc**) linkers in three dimensions.²¹ The inorganic cluster has a twelve-fold coordination and each Zr⁴⁺ ion is connected to four intra-cluster oxygen atoms, and four distinct carboxylate linkers (Figs. 1a, 1b).²² The presence of such high coordinate inorganic centers is thought to confer a large shear modulus upon the framework, though rapid amorphization upon ball-milling is still observed.¹⁸

The two related MOFs, **MIL-140B** [ZrO(O₂C-C₁₀H₆-CO₂)] and **MIL-140C** [ZrO(O₂C-C₁₂H₈-CO₂)], also collapse relatively quickly upon ball-milling. Respectively crystallizing in the space groups *Cc* and *C2/c*, each contains seven-coordinate Zr⁴⁺ ions, which are connected to four 2,6-naphthalene dicarboxylate (**ndc**) and 4,4'-biphenyldicarboxylate (**bpdc**) ligands respectively. Purely inorganic ZrO chains line the *c*-axis of the cells and delimit triangular channels (Fig. 1c), which are larger in **MIL-140C** due to the larger **bpdc** organic

^a Department of Materials Science and Metallurgy, University of Cambridge, Cambridge CB3 0FS, United Kingdom.

^b Laboratoire de Chimie des Processus Biologiques, UMR 8229 CNRS, UPMC Univ Paris 06, Collège de France, 11 Marcelin Berthelot, 75231 Paris Cedex 05, France.

^c Department of Chemistry, University of Cambridge, Lensfield Road, Cambridge, CB2 1EW, UK.

^d Sorbonne Universités, UPMC Univ Paris 06, CNRS, Collège de France, UMR 7574, Chimie de la Matière Condensée de Paris, Paris, France.

^e Centre for Surface Chemistry and Catalysis, Leuven Chem&Tech, KULeuven, Celestijnenlaan 200F, 3001 Heverlee, Belgium.

^f ISIS Facility, RAL, Harwell Oxford, Didcot, Oxon, OX11 0QX, UK.

† Electronic Supplementary Information (ESI) available: ¹³C NMR, DFT, PDF analysis. See DOI:

linker used (Fig. 1e). Whilst π -stacking along the c -axis between all **bpdc** ligands (i.e. those bisecting the lozenge-shaped channels) is observed in **MIL-140C**, only 50% of the corresponding **ndc** ligands in **MIL-140B** participate in this stabilization (Fig. 1d, 1f).²³

Connections between the mechanical properties of MOFs and their defect content are of interest. **UiO-66** has previously been demonstrated to be prone to linker vacancies,^{22, 24} the extent of which can be tuned to yield differential adsorption and thermo-mechanical properties.^{25, 26} Specifically, recent work has pointed to the direct coordination of H₂O and solvent molecules to Zr⁴⁺ nodes in defective UiO-type structures.^{27, 28} Differences between simulated and experimental cell parameters of solvothermally synthesized **MIL-140B** point towards the presence of defects in this framework, though microwave based syntheses are recorded as producing a defect free material.^{29, 30} Potential links between defects and amorphization mechanisms are therefore of much interest, alongside the structure and properties of the resultant amorphous products.

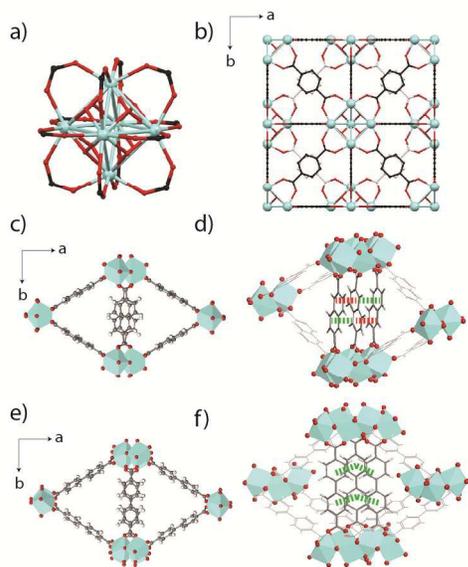


Figure 1. (a) The Zr₆O₄(OH)₄ inorganic node present in **UiO-66**. (b) Unit cell of **UiO-66** viewed along a cubic axis. Carbon atoms behind those shown in the foreground are coloured off-white for clarity. (c) The **MIL-140B** crystal structure proposed in ref²³, viewed along the c -axis, along with (d) π -stacking distances along the c -axis between the **ndc** ligands. Red – 4.46 Å, green – 3.63 Å. (e) The **MIL-140C** crystal structure proposed in ref²³, with (f) corresponding π -stacking distances (green – 3.94 Å) along the c -axis between the **bpdc** linkers. Zr atoms are depicted as light blue polyhedra, O is red, C is gray and H is white.

We use infrared spectroscopy and pair distribution function (PDF) measurements to structurally characterize the products of the ball-milling induced collapse of the rigid **UiO-66**, **MIL-140B** and **MIL-140C** frameworks. Density functional theory (DFT) calculations reveal the presence of defects in **MIL-140B**. We build defective models, and alongside ¹³C solid state magic angle spinning (MAS) nuclear magnetic resonance (NMR), use these to suggest the likely nature of the defects in

the framework. Overall, we find a quantifiable partial breakage of metal-ligand bonding in each case, though, perhaps surprisingly, the backbone ZrO chains of the **MIL-140** frameworks are also damaged in the process. The [Zr₆O₄(OH)₄] clusters of **UiO-66** however remain intact.

Experimental

Materials selection and synthesis: Samples were synthesized according to previous procedures.^{18, 23}

Ball Milling: 50 mg of each sample was placed in a 10 mL stainless steel jar along with one 9 mm diameter stainless steel ball. The material was then ball-milled for the specified time in a Retsch MM400 grinder mill operating at 20 Hz.

Computational Details

All geometry optimization calculations are based on density functional theory (DFT) and performed using the Vienna *Ab-initio* Simulation Package (VASP).³¹ Lattice parameters and atomic positions were optimized until the forces on all atoms were smaller than 0.01 eV Å⁻¹ and the SCF convergence criteria is below 1×10^{-5} hartree.

A plane-wave basis set with an energy cutoff of 600 eV was employed, along with the Perdew-Burke-Ernzerhof (PBE) exchange-correlation functional.³² The long-range weak dispersion interactions were taken into account by different schemes: 1) the DFT-D method of Grimme (DFT-D2³³ and DFT-D3³⁴) and 2) one of the non-local van der Waals functionals of Langreth and Lunquist, namely the optB88-vdW functional.^{35, 36} The electron-ion interactions were described by the projector augmented wave (PAW) method³⁷ in the implementation of Kresse and Joubert.³⁸ The Brillouin zone integration was performed using a (1×1×2) Monkhorst-Pack grid.³⁹

The NMR chemical shift calculations were performed at the VASP optimized geometries using the QUANTUM-ESPRESSO software.⁴⁰ The PBE generalized gradient approximation³² was used and the valence electrons were described by norm conserving pseudopotentials in the Kleinman-Bylander form.⁴¹ The wave functions are expanded on a plane wave basis set with a kinetic energy cut-off of 816 eV and the convergence threshold for the SCF energy was set to 1.36×10^{-9} eV. The integrals over the first Brillouin zone are performed at the Γ point for the charge density and chemical shift tensor calculations.

The shielding tensor is computed using the GIPAW⁴² approach which permits the reproduction of the results of a fully converged all-electron calculation. The isotropic chemical shift δ_{iso} is defined as $\delta_{\text{iso}} = -[\sigma - \sigma^{\text{ref}}]$ where σ is the isotropic shielding and σ^{ref} is the isotropic shielding of the same nucleus in a reference system. In the present case, the comparison between the experimental δ_{iso} and calculated δ_{iso} ¹³C chemical shift values for carboxylate of benzoic acid⁴³ ($\delta_{\text{iso}} = 172.0$ ppm)⁴⁴ allowed to determine σ^{ref} for this nucleus.

Characterization of materials

Powder X-ray Diffraction: Room temperature PXRD data ($2\theta = 5-30^\circ$) were collected with a Bruker-AXS D8 diffractometer using $\text{Cu K}\alpha_1$ ($\lambda = 1.540598 \text{ \AA}$) radiation and a LynxEye position sensitive detector in Bragg-Brentano parafocusing geometry.

Nuclear Magnetic Resonance Spectroscopy: Solid state ^{13}C NMR spectra were acquired on a Bruker Avance I, 9.4T spectrometer operating at 400 MHz for ^1H and 100 MHz for ^{13}C with the following acquisition parameters: magic angle spinning (MAS) frequency 10 kHz, 4 mm outer diameter zirconia rotors, ^1H $\square/2$ pulse 2.5 \square s, ramped cross polarization from ^1H to ^{13}C (CP) 2.5 ms at 70 kHz matching RF fields, 100 kHz ^1H spinlock decoupling during acquisition, repetition time 30 s, chemical shifts referenced relative to external \square -glycine methylene signal at 43.1 ppm.

Total Scattering Measurements: Room temperature X-ray data were collected at the I15 beamline at Diamond Light Source, UK, at a wavelength of $\lambda=0.1722 \text{ \AA}$ (72 keV). Finely powdered samples (crystalline and amorphous) of **UiO-66**, **MIL-140B** and **MIL-140C** were carefully loaded into 1.0 mm diameter fused silica capillaries. Data were collected in the range $\sim 0.5 < Q < \sim 22 \text{ \AA}^{-1}$ and data from an empty instrument and capillary were also collected for background subtraction.

Corrections for background, multiple scattering, container scattering, Compton scattering and absorption were applied using the GudrunX program.⁴⁵ The corrected and normalized reciprocal space data were then converted to the PDFs using Fourier transform within GudrunX.

Results and Discussion

Powder X-ray Diffraction and Infrared Spectroscopy

Consistent with prior work, ball-milling of crystalline samples of **UiO-66** (10 mins), **MIL-140B** (15 mins) and **MIL-140C** (20 mins) resulted in the disappearance of Bragg peaks from the powder X-ray diffraction patterns (Fig. 2). We term the products ***a_m*UiO-66** and ***a_m*MIL-140C**, where the subscript m refers to amorphization by mechanochemical means. An asterisk denotes the retention of some Bragg peaks in the diffraction pattern of **MIL-140B** after milling (***a_m*MIL-140B***, Fig. 2b inset). Infrared spectroscopy revealed the emergence of a band centered at ca. 1700 cm^{-1} upon amorphization of the **MIL-140** samples, which is assigned to the uncoordinated carbonyl stretching frequency (Fig. 2). An increase in intensity of this band was also noted upon collapse of **UiO-66**, where uncoordinated **bdc** ligands within the pores result in a small feature at 1700 cm^{-1} in the crystalline sample.⁴⁶

Nuclear Magnetic Resonance Spectroscopy

NMR has proven a valuable tool in the detailed structural characterization of MOFs.⁴⁷⁻⁵² The qualitative observation of partial destruction of metal-ligand bonding motivated us to perform solid-state ^{13}C MAS NMR on the compounds. The experimental spectrum of **UiO-66** (Fig. 3a) contains three peaks. Based on prior work,⁴⁶ resonances at 128 ppm and 137 ppm are assigned to the two types of carbon on the **bdc** aromatic ring, whilst the carboxylate-binding group gives rise

to the signal at 170 ppm. The ^{13}C NMR spectrum of **MIL-140B** (Fig. 3b) is significantly more complicated, containing multiple signals in the 120 ppm – 140 ppm region and two distinct resonances at 173.5 ppm and 175 ppm. A further increase in complexity is noted in the ^{13}C MAS NMR spectrum of **MIL-140C** (Fig. 3c), which now contains three resonances in the region 170-175 ppm.

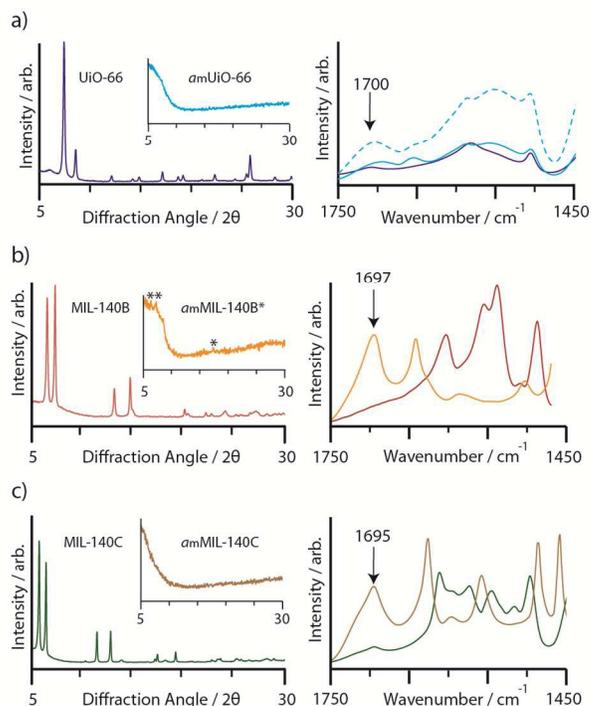


Figure 2. $\text{CuK}\alpha_1$ powder X-ray diffraction patterns, and IR spectra, of crystalline and (inset) amorphous samples (left hand plots), complete with IR spectra of the region 1450 – 1750 cm^{-1} (right hand plots). (a) **UiO-66**: dark blue, ***a_m*UiO-66**: light blue, ***a_m*UiO-66** after 20 minutes ball milling: broken light blue, (b) **MIL-140B**: red, ***a_m*MIL-140B***: orange, (c) **MIL-140C**: green, ***a_m*MIL-140C**: brown.

Upon amorphization, significant peak broadening of all signals is observed in the experimental spectra, though an indication of retention of the **bdc** ligand in ***a_m*UiO-66** is given by the two identifiable signals which make up the broad peak at low chemical shift (Fig. 3a). Coalescence of the signals belonging to non-carboxylate carbon atoms in ***a_m*MIL-140B*** is observed (Fig. 3b), while three distinct features in the 120-145 ppm ^{13}C spectrum of ***a_m*MIL-140C** remain apparent (Fig. 3c). Loss of chemically distinct ligand environments in the **MIL-140** frameworks was confirmed by coalescence of carboxylate peaks at ca. 170 ppm in each case.

A small additional feature at ca. 182.5 ppm appears upon amorphization for all three samples (Fig. 3d). The higher chemical shift of this peak is consistent with loss of carboxylate coordination to the Zr^{4+} ions upon structural collapse. Integration traces of the carboxylate signals in the amorphous samples yielded the approximate ratio of this emergent peak to the main peak. In ***a_m*UiO-66**, the new feature was found to account for ca. 6.8 % of the total intensity from the carboxylate carbon, suggesting a low degree of Zr-OOC bond breaking. This is raised to ca. 13.2 % and 11.0 % respectively in **MIL-**

140B and **MIL-140C**, implying a higher degree of coordinate bond breaking in these samples upon amorphization.

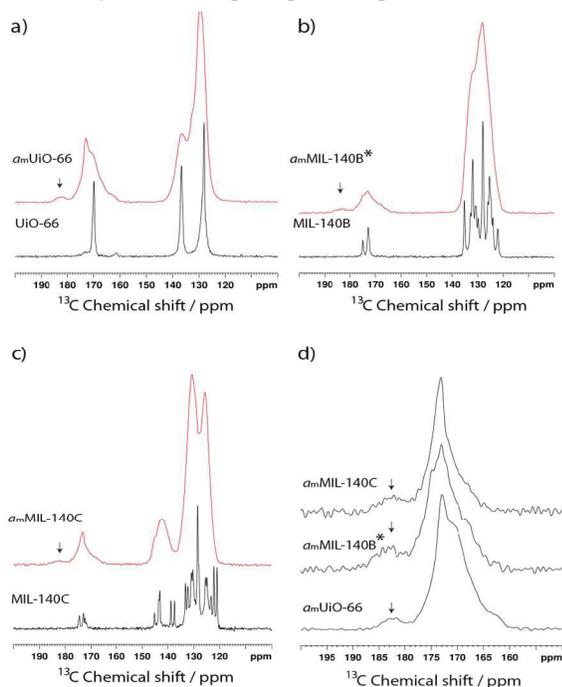


Figure 3. ^{13}C MAS NMR spectra of crystalline (black) and amorphous (red) samples of (a) **UiO-66**, (b) **MIL-140B** and (c) **MIL-140C**. (d) Magnified view of the 150-200 ppm region of the amorphous samples. Acquisition parameter details are given in the SI.

Non-defective modeling of **MIL-140B**

In order to understand and better assign individual features in the experimental ^{13}C NMR spectra of **MIL-140B** and **MIL-140C**, DFT calculations were performed using their previously reported crystal structures,²³ which were derived using a computationally assisted strategy from the crystal structure of **MIL-140A** (the bdc-based isorecticular structure); the only one solved by Rietveld refinement of X-ray powder diffraction data.²³ Simulated cell parameters and volumes for **MIL-140B** and **MIL-140C** were obtained in the present work upon fully relaxing coordinates and cell parameters, using four different DFT approaches; one with no dispersion correction (PBE), two with dispersion correction using the DFT-D approach of Grimme by means of D2 and D3 corrections (PBE-D2³³ and PBE-D3³⁴), and a second one employing one of the non-local van der Waals functionals (optB88-vdW).^{35, 36} We first discuss attempts at structural optimization of alternative, non-defective **MIL-140B** structures, before considering defective **MIL-140B** models and their relative energetics, and then their respective calculated ^{13}C NMR responses.

Upon comparison of DFT results with the experimental values for **MIL-140B** (Table 1), all employed DFT methods converge systematically to a larger cell volume than the experimental one (7.5 % error). This mainly emanates from the recurrent overestimation of the lattice constant a found at ~ 28 Å (4.8 % error), while b and c are predicted with excellent accuracy (within 1.5 % error). This cell expansion occurs when dispersion corrections are omitted (PBE entry), and is surprisingly maintained when they are taken into account, a

result which is not sensitive to the methodology by which the dispersion is calculated (PBE-D2, -D3 and optB88-vdW entries). A further geometry optimization of **MIL-140B**, constraining its cell parameters to the experimentally determined values (PBE-D3//exp entry), reveals it is much less stable by 1.57 eV than its relaxed **MIL-140B** counterpart (PBE-D3 entry), pointing towards an inconsistency between the structural model used and the experimentally determined cell parameters. Expectedly, the simulated ^{13}C spectrum of **MIL-140B** is in very poor agreement with the experimental one, in both regions of carboxylate and aromatic carbons (Fig. S1a), supporting a hypothesis of a different, or defective **MIL-140B** structure not captured in the initial model of ref²².

The situation is markedly different with **MIL-140C**, with excellent predictions from DFT structure optimizations (Table 1 and Fig. S2). While dispersion correction-free DFT calculations slightly overestimate the a cell parameter (1.6% error) and cell volume, V (4.3% error), all dispersion-corrected DFT calculations yield excellent agreement when compared to experiment, particularly the optB88-vdW entry with errors reduced to 0.4 % and 0.6% for a and V , respectively. As in all **MIL-140B** calculations, the c parameter is systematically very well predicted. This reflects the structural rigidity associated with the inorganic subunit of the zirconium oxide chains along that direction. Taking the dispersion effects into account improves the simulation of the **MIL-140C** crystal structure and highlights the importance of the π -stacking stabilizing interactions along the c -axis, which take place with the involvement of all **bpdc** ligands at regular center-to-center distances of 3.9 Å (Fig. 1f). The simulated NMR spectra provide significantly better agreement with observed NMR shifts, supporting a consistent initial structural model (Fig. S2).

The failure of DFT calculations to predict the correct cell volume and lattice parameters for **MIL-140B** reveals that its stabilization at the smaller observed cell parameters emanates from additional structural features. This together with NMR discrepancies prompted us to an in-depth investigation of the structure and defects in **MIL-140B**, as a case study.

Enhanced π Stacking in **MIL-140B**

A first variant of the reported **MIL-140B** structure, hereby referred to as **MIL-140B(r)**, where (r) indicates the partial rotation of linkers, was therefore constructed by imposing a 180° rotation around the b -axis to the **ndc** linkers not participating in the π -stacking (Fig. 4a). The resultant **MIL-140B(r)** model is hence one in which a full π -stacking of **ndc** linkers along the c -axis occurs. As a result, the fully relaxed **MIL-140B(r)** model is 0.38 eV lower in energy than the parent **MIL-140B**, compared at the same level of theory (Table 1, PBE-D3 entry). This stabilization is assigned mainly to the now enhanced π -stacking along c . In addition, the sole rotation of these **ndc** linkers induces a large contraction along the a -axis, of 0.4-0.7 Å depending on the level of theory, with an error reduced to 2-3%.

Table 1. Cell parameters of experimental and optimized crystal structures of MIL-140B, MIL-140B(r) and MIL-140C. MIL-140B(r) refers to a defective model imposing a 180° rotation around the *b*-axis to **ndc** linkers (see text for details). PBE-D2, PBE-D3, optB88-vdW represent dispersion corrected schemes. PBE-D3//exp entry refers to a geometry optimization of MIL-140B at the experimental lattice parameters.

MIL-140B	<i>a</i> (Å)	<i>b</i> (Å)	<i>c</i> (Å)	α (°)	β (°)	γ (°)	<i>V</i> (Å ³)	E (eV)
Exp. Ref 22	26.71	13.30	7.79	90	92.56	90	2763.2	
PBE	28.05	13.49	8.02	90	94.26	90	3024.7	
PBE-D2	28.05	13.46	7.87	90	93.40	90	2964.7	
PBE-D3	27.95	13.46	7.91	90	93.34	90	2970.7	0
PBE-D3//exp	26.71	13.30	7.79	90	92.56	90	2763.2	+1.57
optB88-vdW	28.00	13.44	7.89	90	93.82	90	2963.3	0
MIL-140B(r)								
PBE-D2	27.65	13.41	7.84	89.32	90.12	88.86	2906.1	
PBE-D3	27.56	13.41	7.88	89.50	90.34	88.81	2909.8	-0.38
optB88-vdW	27.28	13.38	7.85	91.06	88.66	88.16	2864.8	-0.47
MIL-140C	<i>a</i> (Å)	<i>b</i> (Å)	<i>c</i> (Å)	α (°)	β (°)	γ (°)	<i>V</i> (Å ³)	
Exp. Ref 22	31.03	15.51	7.82	90	93.26	90	3756.6	
PBE	31.52	15.63	7.97	90	87.06	90	3918.3	
PBE-D2	31.29	15.58	7.78	90	89.67	90	3794.7	
PBE-D3	31.25	15.59	7.82	90	89.32	90	3810.9	
optB88-vdW	31.16	15.59	7.78	90	89.90	90	3778.8	

Addition of uncoordinated H₂O

While being closer to experimental findings, MIL-140B(r) still exhibits overestimated cell parameters. Given recent reports of the defects in UiO-materials being caused by H₂O or solvent molecules,^{27, 53} we thus further constructed several non-defective structures, where low concentrations of water are introduced as adsorbed molecules. Table 2 summarizes the optimized cell parameters and their relative energies obtained at the PBE-D3 level of theory.

Two hydrated models were derived from MIL-140B and MIL-140B(r), respectively (labelled “•H₂O”), by adding one adsorbed water molecule per cell (Fig. 4b, 4d). Upon full relaxation, the water molecule preferentially forms hydrogen bonds with two carboxyl oxygen atoms (1.99 and 1.95 Å) of two neighbouring **ndc** linkers stacked along *c*, with minor change in cell volumes. The rotated hydrated model was found to be of lower energy (by 0.35 eV) than the non-rotated one, which is ascribed entirely due to the enhanced π -stacking in MIL-140B(r) (see Table 1). Addition of a second uncoordinated water to both models (labelled •2H₂O), to a site at the opposite end of the organic linker to the first molecule, did not result in any cell modification nor further stabilization.

Defect Modelling

H₂O coordination to Zr combined with linker displacement

In further models, H₂O was allowed to coordinate to Zr⁴⁺ ions, forming defective MIL-140B structures. Four possible defect incorporation pathways, (a)-(d) were considered (Figure 5), respectively leading to models **A-D** (Fig. S3). Models arising from the original MIL-140B structure are given the subscript ‘0’, and those arising from MIL-140B(r), are given the

subscript ‘r’, e.g. **A₀** and **A_r**, respectively for pathway ‘a’.

In pathway ‘a’, one end of an **ndc** linker was displaced into a monodentate state, allowing coordination of one H₂O molecule to the newly created defect site. Upon relaxation, the chemisorbed water remained bound to Zr and established hydrogen bonds with its two surrounding carboxyl oxygen atoms (1.80 Å). Interestingly, model **A_r** is isoenergetic to the relative ground state MIL-140B•H₂O structure (0.02 eV): the energy penalty for breaking Zr-O(linker) bond (~0.3 eV) and altering the π -stacking is compensated by the coordination of the water molecule to Zr. In addition, unlike the (non-coordinating) adsorption of water, the chemisorption of water on the Zr-center in **A_r** leads to a significant cell contraction along *a* (up to ~0.3 Å) when compared to the water-free model, making **A_r** a promising defective model candidate.

Extension of this defect with a second coordinated H₂O molecule along the *a*-axis (model **A_re**) induces a relatively low energetic penalty (+0.40 eV). More importantly, this results in a further cell contraction of this defective MIL-140B model of the *a* lattice constant (*a* = 26.63 Å), in excellent agreement with the experimentally determined value for the MIL-140B structure of 26.71 Å.

Identical treatment of MIL-140B•H₂O, the non-rotated system, gave rise to models **A₀** and **A_{0e}**, which are only 0.21 eV and 0.37 eV higher in energy than the reference ground state of MIL-140B with uncoordinated water molecule, respectively, with however again poor agreement in lattice parameters.

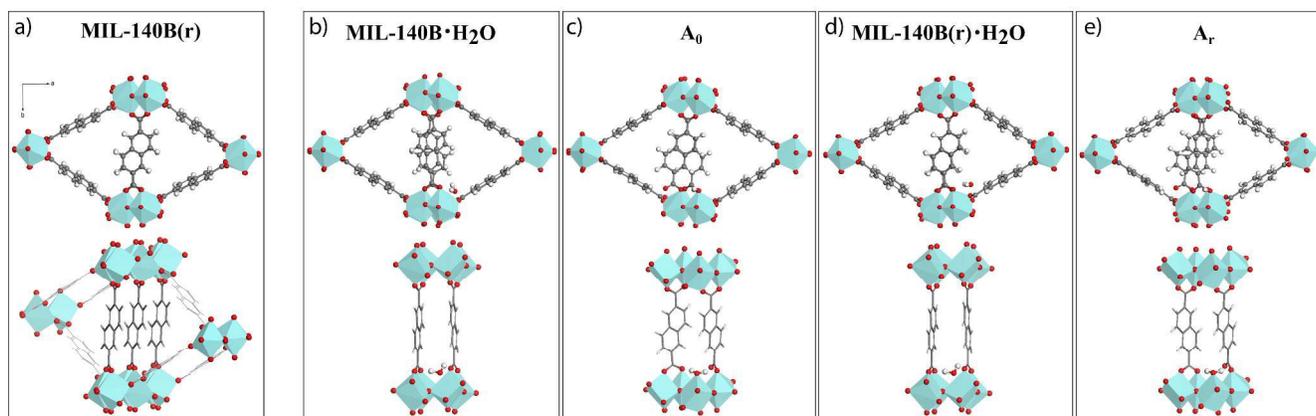


Figure 4. Crystal structure of **MIL-140B(r)**, formed by rotating 50% of the **ndc** linkers which lie along the *a*-axis, around the *b*-axis by 180° . Structures of **MIL-140B** contain one H_2O molecule per unit cell viewed along the *c*-axis. Models called **MIL-140B·H₂O** and **MIL-140B(r)·H₂O** contain an uncoordinated water molecule, while **A₀** and **A_r**, are defective models and are built with a H_2O molecule coordinates directly to a Zr-center. The latter displaces the linker which becomes monodentate on one its carboxylate end. Zr atoms are depicted as light blue polyhedra, O is red, C is gray and H is white.

Turning to defect B, we considered translation of the entire **ndc** linker induced by the chemisorption of two water molecules on the opposite Zr-centers (pathway ‘b’ in Figure 5). As a result, the linker becomes monodentate on one side and bidentate on the other. The resultant models, **B_r** and **B₀**, are +0.26 and +0.54 eV higher in energy than the reference model.

A third type of defect yielded model **C₀** (pathway ‘c’, in Figure 5). Whilst the defect resembles that in pathway ‘b’, the linker binds to two neighbouring Zr-centers along the *c* direction. This structure was deemed unfavourable by +0.82 eV with respect to the reference defect-free model **MIL-140B·2H₂O**.

A fourth defect structure, modelled by following pathway ‘d’ in Figure 5, yields **D_r**. In this structure both ends of an **ndc** linker were displaced into a monodentate position, allowing coordination of a H_2O molecule to each of the two newly created defective Zr sites. It can form with an energy cost of 0.37 eV and shows significant shrinking of the lattice vector *a* to 27.10 Å.

Overall, this series of calculations tend to suggest that the formation of defects in **MIL-140B** may occur through the coordination of water molecules to Zr centers together with the displacement of the linker and that such defects are associated with relatively low energy penalties. They also indicate that defect pathways allowing the enhancement of π -stacking of **ndc** linkers along *c* direction might be favoured, exemplified in ‘r’ type models.

Comparison of predicted ¹³C NMR shifts from defective models

¹³C NMR chemical shift calculations were performed on our defective **MIL-140B** variants in order to evaluate the pertinence of these models with respect to available experimental data. Calculation of the ¹³C NMR chemical shifts for the **MIL-140B(r)** model yielded significantly better agreement with the experimentally observed shifts than those

attained directly from **MIL-140B** (Fig. S1b).

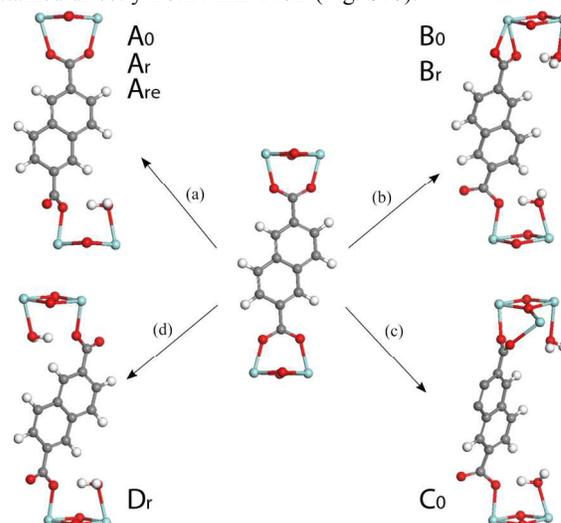


Figure 5. Formation of different types of defective structures upon direct binding of water on a Zr-center. The names of the defective models derived from each pathway are included for clarity. Zr – light blue, O – red, C – gray, H – white.

This is most notable in the increased complexity of the splitting pattern in the aromatic carbon region that covers more consistently the whole range of observed peaks. The concordance of such splitting between the experimental data and this **MIL-140B(r)** model suggests that rotation of **ndc** linkers might indeed occur so as to favor π -stacking locally. This improved agreement in the 120-140 ppm aromatic region is retained in hydrated models, i.e. **A_{re}**, **B_r** and **D_r**, in which H_2O is introduced directly to the Zr coordination sphere. The region of the NMR spectra attributed to carboxylate shifts (170-190 ppm) of **A_{re}**, **B_r** and **D_r**, however, shows a lower level of agreement with the experimental spectra of **MIL-140B** with a large dispersion of the calculated values compared to the experimental ones.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Table 2. Optimized cell parameters (PBE-D3 level of theory) of MIL-140B defective variants containing different amount of adsorbed or coordinated water molecules per unit cell. Energies are given in eV with respect to the structures with adsorbed (not coordinated) water molecules. ‘r’ refers to models constructed with rotated linkers for π -stacking enhancement while ‘0’ refers to models constructed from the parent MIL-140B. A, B, C and D refer to the various defect pathways (a, b, c, d) in Figure 5. ‘e’ refers to models with extended coordination of water molecules along the *a*-axis.

	Uncoordinated Water	<i>a</i> (Å)	<i>b</i> (Å)	<i>c</i> (Å)	α (°)	β (°)	γ (°)	<i>V</i> (Å ³)	E (eV)
	MIL-140B•H ₂ O	27.84	13.47	7.89	90.57	92.79	90.02	2957.5	0
	MIL-140B •2H ₂ O	27.82	13.48	7.90	89.96	93.01	90.54	2955.5	0
	MIL-140B(r)•H ₂ O	27.52	13.42	7.87	89.49	90.15	88.94	2905.4	-0.35
	MIL-140B(r)•2H ₂ O	27.51	13.44	7.86	89.26	90.24	89.15	2905.4	-0.37
	Coordinated Water								
	A _r	27.28	13.42	7.86	90.07	88.28	89.20	2875.1	+0.02
	A _{re}	26.63	13.45	7.83	90.36	84.44	89.91	2789.4	+0.40
	A ₀	27.79	13.46	7.87	90.34	92.13	90.52	2944.2	+0.21
	A _{0e}	27.56	13.49	7.85	90.79	90.12	91.10	2918.8	+0.37
	B _r	27.40	13.41	7.85	90.67	89.54	87.65	2882.5	+0.26
	B ₀	27.69	13.47	7.85	89.43	92.26	89.51	2925.6	+0.54
	C ₀	27.77	13.46	7.85	90.18	93.30	89.41	2930.2	+0.82
	D _r	27.10	13.45	7.86	89.45	87.19	89.77	2861.3	+0.37

Whilst possible, defect-incorporating models (A_{re}, B_r and D_r), for the reported MIL-140B structure have been suggested, it is equally interesting that some of the features in the predicted NMR shifts agree well with those of a_mMIL-140B. The range of chemical shifts across the spectra observed shows excellent agreement with those for the amorphized MIL-140B sample. The predicted ¹³C NMR spectrum of model B_r however, is the only one to exhibit a peak in the region 185 ppm – 190 ppm, which is identified to be a fingerprint of one carboxylate end being bound in a bidentate fashion to Zr⁴⁺. Since this is closely reminiscent of the feature which appears upon amorphization, it provides some evidence as to the introduction of defects upon ball-milling of the structure.

Pair Distribution Function Studies

Analysis of the pair distribution function, or the weighted histogram of atom-atom distances,⁵⁴ of amorphous inorganic zeolites⁵⁵ and MOFs,¹² has in the past yielded useful information on the chemical structure of complex amorphous systems. Room temperature total scattering data were therefore collected on crystalline and amorphous samples using synchrotron radiation ($\lambda = 0.1722$ Å, $Q_{\max} = 22$ Å⁻¹). The resultant structure factors *S*(*Q*) (Figs. S4-S6) of a_mUiO-66 and a_mMIL-140C are devoid of Bragg peaks, confirming the amorphous sample nature. Expectedly, that of a_mMIL-140B* contains some features due to Bragg scattering. After suitable corrections using the GudrunX software,⁴⁵ the data were converted to the corresponding PDFs by Fourier Transform.⁵⁶

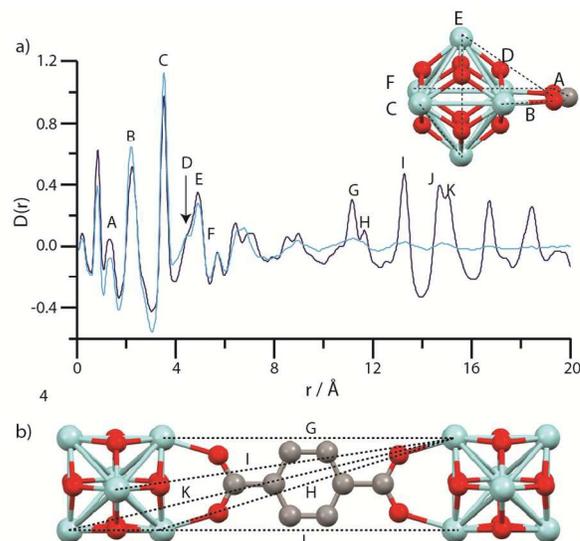


Figure 6. (a) PDF data for UiO-66 (dark blue) and a_mUiO-66 (light blue). A-F labels of peaks below 8 Å correspond to the indicated correlations in the Zr₆O₄(OH)₄ cluster (Inset). (b) Two Zr₆O₄(OH)₄ units linked by a bdc ligand, and some of the significant distances corresponding to the longer *r* features (G-K) in (a). Zr – light blue, O – red, C – gray, H – omitted.

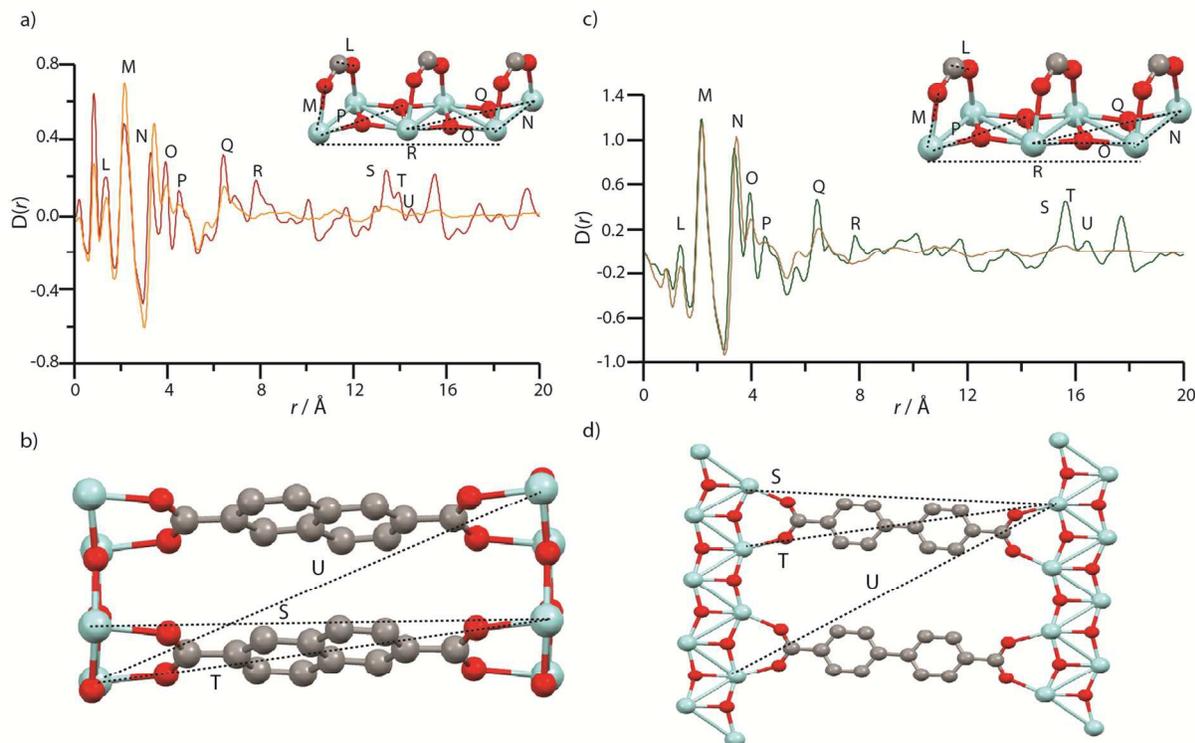


Figure 7. (a) PDF data for **MIL-140B** and a_m **MIL-140B***. Labels of peaks below 8 Å correspond to the indicated correlations in the ZrO inorganic chains (Inset). (b) Two ZrO chains linked by 2,6-**ndc**, and the distances corresponding to the longer r features in (a). (c) PDF data for **MIL-140C** and a_m **MIL-140C**. Labels of peaks below 8 Å correspond to the indicated correlations in the ZrO inorganic chains, as in **MIL-140B** (Inset). (d) Two ZrO chains linked by **bpdc**, and the distances corresponding to the longer r features in (a). Zr – light blue, O – red, C – gray, H – omitted. To facilitate assignment of features, partial PDFs were calculated using the PDFgui software (Figs. S7-S9).⁵⁷ All PDFs of crystalline species are, as expected, dominated by correlations involving Zr, due to the larger X-ray scattering cross section of Zr relative to C, O and H.

Due to the difficulties in obtaining reliable data below ~ 1 Å from X-ray total scattering instruments, the first peak in the PDF of crystalline **UiO-66** belonging to a physical atom-atom correlation appears at ~ 1.3 Å, which corresponds to C-C or C-O direct linkages (A, Fig. 6a). Other features below 6 Å (B-F) are assigned to various Zr-Zr and Zr-O inter-cluster separations. At longer distances, overlapping contributions from similarly spaced Zr-C atom pairs results in peak broadening and renders precise assignment of the features at ~ 6.5 Å and ~ 8.6 Å challenging. The large relative scattering cross-section of Zr results in sharp features above 10 Å (G-K) in the PDF of **UiO-66**, which can be ascribed to Zr atom pairs joined through a **bdc** linker (Fig. 6b).

Below 6 Å, the PDF of a_m **UiO-66** is very similar to **UiO-66**, with peaks A-F appearing invariant in position between the two and thus confirming the presence of the $Zr_6O_4(OH)_4$ structural building unit in a_m **UiO-66**. Coalescence of the double peaks centered at ~ 6.5 Å and ~ 8.6 Å occurs upon amorphization, yielding two broad features in the PDF of a_m **UiO-66**. The reduction in intensity and severe broadening of these peaks, and those labelled G-K, in a_m **UiO-66** is indicative of the loss in long range-order of the framework. The presence however of some intensity does suggest at least the partial retention of the structural linkage, though substantial changes to Zr-Zr correlations would be expected upon breaking if only one Zr-O bond were to break. The observable extent of order in a_m **UiO-66** may extend beyond 15.9 Å, though this is the last distance

which correlations can be unambiguously assigned to Zr-Zr atoms separated by the organic linker.

The PDF of **MIL-140B** (Fig. 7a) contains the expected peaks (L-N) belonging to nearest neighbour C-C/C-O, Zr-O and Zr-Zr distances at ca. 1.3 Å, 2 Å and 3.3 Å, whilst at further distances below 8 Å (O-R), non nearest neighbour correlations of Zr-Zr and Zr-O atoms also elicit sharp features. These corresponding chemical distances relating to L-R are indicated in the inset of Figure 7a, and all relate to the inorganic ZrO backbone chain. Sharp features associated with crystalline order continue to be observed in the PDF of **MIL-140B** to distances up to 20 Å, as expected. Key features (S-U) at these longer r values agree well with Zr-Zr distances separated by the 2,7-**ndc** linker (Fig. 7b).

Features L and M are located in the same position in the PDF of a_m **MIL-140B*** (Fig. 7a), though N, which corresponds to the nearest Zr-Zr distance in the inorganic backbone appears to lengthen from 3.3 Å to 3.5 Å upon amorphization. Another noticeable change in the PDF of a_m **MIL-140B*** is the loss in intensity of peaks O-Q, which, correspond to non-nearest neighbour Zr and O distances in the ZrO backbone chains. Somewhat surprisingly, the peak at 7.8 Å, labelled R, disappears entirely on going from **MIL-140B** to a_m **MIL-140B***, suggesting the rigid ZrO inorganic chain no longer remains intact when longer Zr-Zr correlations are considered. Indeed, changes are apparent at even shorter Zr-Zr length scales, with substantial deterioration of the intensity of the Zr-O-Zr (O) peak intensity at 4.5 Å, which suggests that some Zr-

O bonds have been broken during the ball-milling process, causing the chain to twist. Given this partial destruction of the continuous ZrO backbone, it is surprising that pair correlations relating to Zr atoms separated by the organic linker (S, T and U) persist in a_m MIL-140B*, with some degree of correlated order extending to ca 15.9 Å. Above this distance, the PDF of a_m MIL-140B* is featureless, in sharp contrast to its crystalline counterpart.

The near-identical nature of the MIL-140C framework, aside from the slightly longer organic linker, led to the labelling of corresponding distances in the PDFs with the same notation as that used in the MIL-140B PDF. Similar differences between amorphous and crystalline frameworks are observed in the PDFs of MIL-140C and a_m MIL-140C (Fig. 7c, d). In particular, the same lengthening of nearest Zr-Zr distances (N) upon amorphization is witnessed. In addition, very similar reductions in the intensity of the peak belonging to nearest neighbour Zr-O correlations at 4.5 Å (O) are also observed whilst there is very little intensity in further Zr-O correlations (P-R).

This observation provides confidence that the ZrO backbone shared by both MIL-140B and MIL-140C, undergoes significant distortion during ball-milling, though some order persists in the PDF of a_m MIL-140C, to 17.6 Å (S, T and U). These distances, as in a_m MIL-140B*, correspond to two Zr atoms separated by the larger bpdc organic linker (Fig. 7d).

Conclusions

The results further contribute to the area of non-crystalline metal-organic frameworks and provide insight into the relationship between defects and amorphization. We have identified possible modes of defect incorporation into the structure of MIL-140B; Defects investigated include coordinated water to Zr centers combined with linker displacement. Such defective models provide significantly better agreement with the experimentally observed structural cell parameters than the defect free ones. DFT calculations of the chemical shifts of some models also show similar features to those witnessed experimentally upon amorphization of MIL-140B. We anticipate that the occurrence of such defects might be applicable to other MOFs, given the prevalence of carboxylate linkers in this family.

In addition to solid state NMR, we have used pair distribution function analysis to show that the amorphization of the prototypical UiO-66 framework proceeds via partial breakage of Zr-carboxylate bonds, though the rigid $Zr_6O_4(OH)_4$ inorganic building unit appears to remain intact. This is in stark contrast to MIL-140B and MIL-140C, where in addition to metal-carboxylate bond breaking, the inorganic backbone is also heavily damaged during the ball-milling process. This mechanism bears a large similarity to the changes seen in the ball-milling of zeolites, where M-O (M = Si, Al) bonds are observed to be broken,⁵⁸ whilst the inorganic distortions are to be expected given that pure Zirconia undergoes phase transitions and eventual amorphization when subjected to ball-milling.⁵⁹

The different behaviour of the two inorganic units is ascribed to the larger interconnected nature of the inorganic

clusters in UiO-66, where 24 Zr-O bonds hold the unit together. This is in contrast to the ZrO chains of the MIL-140 frameworks, where in a unit containing the same number of Zr ions, only 16 Zr-O bonds hold the chain together. Whilst structural defects will also play a role in determining mechanical stability, the research here may be combined with increasing metal-ligand bond strengths,²⁰ to yield 'strong' MOFs capable of resisting external stresses

Notes and references

The manuscript was written through contributions of all authors. TDB conceived the initial project. T.D.B. acknowledges Trinity Hall (University of Cambridge) and Professor Anthony K. Cheetham for use of lab facilities. D.G.R. acknowledges the UK MRC for financial support. The authors acknowledge Diamond Light Source for the provision of synchrotron access to Beamline I15 (exp. EE9691) and Philip A. Chater and Andrew Cairns for assistance with data collection. T.K.T. and C.M.D. thank the French National Research Agency (ANR project: HOPFAME ANR-13-BS07-0002-01) and the Foundation de l'Orangerie for funding. The calculations have been performed using the HPC resources from GENCI (CINES/TGCC/IDRIS) through Grant (2015-097343 and -091461). B.B., B.V.d.V. and D.D.V. gratefully acknowledge the FWO for funding (aspirant grant).

1. H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 974-986.
2. J. E. Mondloch, M. J. Katz, W. C. Isley III, P. Ghosh, P. Liao, W. Bury, G. W. Wagner, M. C. Hall, J. B. DeCoste, G. W. Peterson, R. Q. Snurr, C. J. Cramer, J. T. Hupp and O. K. Farha, *Nat. Mater.*, 2015, **14**, 512-516.
3. T. D. Bennett and A. K. Cheetham, *Acc. Chem. Res.*, 2014, **47**, 1555-1562.
4. S. R. Batten, N. R. Champness, X. M. Chen, J. Garcia-Martinez, S. Kitagawa, L. Ohrstrom, M. O'Keeffe, M. P. Suh and J. Reedijk, *CrystEngComm*, 2012, **14**, 3001-3004.
5. T. D. Bennett, J. C. Tan, Y. Z. Yue, E. Baxter, C. D. Ducati, N. Terril, H. Y. Yeung, Z. Zhou, W. Chen, S. Henke, A. K. Cheetham and G. N. Greaves, *Nat Commun*, 2015, **6**, 10.1038/NCOMMS9079.
6. K. W. Chapman, D. F. Sava, G. J. Halder, P. J. Chupas and T. M. Nenoff, *J. Am. Chem. Soc.*, 2011, **133**, 18583-18585.
7. F. X. Coudert, *Chem. Mater.*, 2015, **27**, 1905-1916.
8. D. Umeyama, S. Horike, M. Inukai, T. Itakura and S. Kitagawa, *J. Am. Chem. Soc.*, 2015, **137**, 864-870.
9. G. Givaja, P. Amo-Ochoa, C. J. Gomez-Garcia and F. Zamora, *Chem. Soc. Rev.*, 2012, **41**, 115-147.
10. J. Haines, C. Levelut, A. Isambert, P. Hebert, S. Kohara, D. A. Keen, T. Hammouda and D. Andraut, *J. Am. Chem. Soc.*, 2009, **131**, 12333-12338.
11. S. Jiang, K. E. Jelfs, D. Holden, T. Hasell, S. Y. Chong, M. Haranczyk, A. Trewin and A. I. Cooper, *J. Am. Chem. Soc.*, 2013, **135**, 17818-17830.
12. T. D. Bennett, A. L. Goodwin, M. T. Dove, D. A. Keen, M. G. Tucker, E. R. Barney, A. K. Soper, E. G. Bithell, J. C. Tan and A. K. Cheetham, *Phys. Rev. Lett.*, 2010, **104**, 115503.
13. S. L. James and T. Friscic, *Chem. Soc. Rev.*, 2013, **42**, 7494-7496.
14. A. D. Katsenis, A. Puskaric, V. Strukil, C. Mottillo, P. A. Julien, K. Uzarevic, M. H. Pham, T. O. Do, S. A. J. Kimber, P. Lazić, O. Magdysyuk, R. E. Dinnebier, I. Halasz and T. Friscic, *Nat Commun*, 2015, **6**, 10.1038/ncomms7662.
15. T. D. Bennett, J. Sotelo, J. C. Tan and S. A. Moggach, *CrystEngComm*, 2015, **17**, 286-289.
16. A. U. Ortiz, A. Boutin, A. H. Fuchs and F. X. Coudert, *J. Phys. Chem. Lett.*, 2013, **4**, 1861-1865.
17. J. C. Tan, B. Civalieri, C. C. Lin, L. Valenzano, R. Galvelis, P. F. Chen, T. D. Bennett, C. Mellot-Draznieks, C. M.

- Zicovich-Wilson and A. K. Cheetham, *Phys. Rev. Lett.*, 2012, **108**, 095502.
18. B. Van de Voorde, I. Stassen, B. Bueken, F. Vermoortele, D. De Vos, R. Ameloot, J. C. Tan and T. D. Bennett, *J Mater Chem A*, 2015, **3**, 1737-1342.
- 5 19. H. Wu, T. Yildirim and W. Zhou, *J. Phys. Chem. Lett.*, 2013, **4**, 925-930.
20. J. H. Cavka, S. Jakobsen, U. Olsbye, N. Guillou, C. Lamberti, S. Bordiga and K. P. Lillerud, *J. Am. Chem. Soc.*, 2008, **130**, 13850-13851.
- 10 21. L. Valenzano, B. Civalieri, S. Chavan, S. Bordiga, M. H. Nilsen, S. Jakobsen, K. P. Lillerud and C. Lamberti, *Chem. Mater.*, 2011, **23**, 1700-1718.
22. H. Wu, Y. S. Chua, V. Krungleviciute, M. Tyagi, P. Chen, T. Yildirim and W. Zhou, *J. Am. Chem. Soc.*, 2013, **135**, 10525-10532.
- 15 23. V. Guillerm, F. Ragon, M. Dan-Hardi, T. Devic, M. Vishnuvarthan, B. Campo, A. Vimont, G. Clet, Q. Yang, G. Maurin, G. Férey, A. Vittadini, S. Gross and C. Serre, *Angew. Chem. Int. Ed.*, 2012, **51**, 9267-9271.
- 20 24. Z. L. Fang, B. Bueken, D. E. De Vos and R. A. Fischer, *Angew. Chem. Int. Ed.*, 2015, **54**, 7234-7254.
- 25 25. G. C. Shearer, S. Chavan, J. Ethiraj, J. G. Vitillo, S. Svelle, U. Olsbye, C. Lamberti, S. Bordiga and K. P. Lillerud, *Chem. Mater.*, 2014, **26**, 4068-4071.
- 26 26. M. J. Cliffe, W. Wan, X. D. Zou, P. A. Chater, A. K. Kleppe, M. G. Tucker, H. Wilhelm, N. P. Funnell, F. X. Coudert and A. L. Goodwin, *Nat Commun*, 2014, **5**.
- 27 27. C. A. Trickett, K. J. Gagnon, S. Lee, F. Gandara, H. B. Bürgi and O. Yaghi, *Angew. Chem. Int. Ed.*, 2015, **54**, 1-7.
- 30 28. P. Ghosh, Y. J. Colon and R. Q. Snurr, *Chem. Commun.*, 2014, **50**, 11329-11331.
- 29 29. W. B. Liang, R. Babarao, T. L. Church and D. M. D'Alessandro, *Chem. Commun.*, 2015, **51**, 11286-11289.
- 35 30. W. B. Liang and D. M. D'Alessandro, *Chem. Commun.*, 2013, **49**, 3706-3708.
- 31 31. G. Kresse and J. Furthmuller, *Comp Mater Sci*, 1996, **6**, 15-50.
- 32 32. J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865-3868.
- 40 33. S. Grimme, *J Comput Chem*, 2006, **27**, 1787-1799.
- 34 34. S. Grimme, J. Antony, S. Ehrlich and H. Krieg, *J Chem Phys*, 2010, **132**.
- 35 35. J. Klimes, D. R. Bowler and A. Michaelides, *Phys. Rev. B.*, 2011, **83**.
- 45 36. D. C. Langreth, B. I. Lundqvist, S. D. Chakarova-Kack, V. R. Cooper, M. Dion, P. Hyldgaard, A. Kelkkanen, J. Kleis, L. Z. Kong, S. Li, P. G. Moses, E. Murray, A. Puzder, H. Rydberg, E. Schroder and T. Thonhauser, *J. Phys.-Condens. Mat.*, 2009, **21**.
- 50 37. P. E. Blochl, *Phys. Rev. B.*, 1994, **50**, 17953-17979.
- 38 38. G. Kresse and D. Joubert, *Phys. Rev. B.*, 1999, **59**, 1758-1775.
- 39 39. H. J. Monkhorst and J. D. Pack, *Phys. Rev. B.*, 1976, **13**, 5188-5192.
- 55 40. P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari and R. M. Wentzcovitch, *J. Phys.-Condens. Mat.*, 2009, **21**.
- 60 41. L. Kleinman and D. M. Bylander, *Phys. Rev. Lett.*, 1982, **48**, 1425-1428.
- 42 42. C. J. Pickard and F. Mauri, *Phys. Rev. B.*, 2001, **63**.
- 43 43. G. Bruno and L. Randaccio, *Acta Crystallogr B*, 1980, **36**, 1711-1712.
- 70 44. F. Babonneau, L. Yeung, N. Steunou, C. Gervais, A. Ramila and M. Vallet-Regi, *J Sol-Gel Sci Techn*, 2004, **31**, 219-223.
- 45 45. A. K. Soper, *Tech. Rep. RAL-TR-2011-013*, 2011.
46. S. Devautour-Vinot, G. Maurin, C. Serre, P. Horcajada, D. P. da Cunha, V. Guillerm, E. D. Costa, F. Taulelle and C. Martineau, *Chem. Mater.*, 2012, **24**, 2168-2177.
- 75 47. S. B. Kalidindi, S. Nayak, M. E. Briggs, S. Jansat, A. P. Katsoulidis, G. J. Miller, J. E. Warren, D. Antypov, F. Cora, B. Slater, M. R. Prestly, C. Marti-Gastaldo and M. J. Rosseinsky, *Angew. Chem. Int. Ed.*, 2015, **54**, 221-226.
- 80 48. P. He, B. E. G. Lucier, V. V. Tersikh, Q. Shi, J. X. Dong, Y. Y. Chu, A. M. Zheng, A. Sutrisno and Y. N. Huang, *J Phys Chem C*, 2014, **118**, 23728-23744.
- 49 49. G. Mali, J. Trebosc, C. Martineau and M. Mazaj, *J Phys Chem C*, 2015, **119**, 7831-7841.
- 85 50. P. He, J. Xu, V. V. Tersikh, A. Sutrisno, H. Y. Nie and Y. N. Huang, *J Phys Chem C*, 2013, **117**, 16953-16960.
- 51 51. H. C. Hoffmann, M. Debowski, P. Muller, S. Paasch, I. Senkowska, S. Kaskel and E. Brunner, *Materials*, 2012, **5**, 2537-2572.
- 90 52. M. Baias, A. Lesage, S. Aguado, J. Canivet, V. Moizan-Basle, N. Audebrand, D. Farrusseng and L. Emsley, *Angew. Chem. Int. Ed.*, 2015, **54**, 5971-5976.
- 53 53. S. Oien, D. Wragg, H. Reinsch, S. Svelle, S. Bordiga, C. Lamberti and K. P. Lillerud, *Cryst. Growth. Des.*, 2014, **14**, 5370-5372.
- 95 54. P. K. Allan, K. W. Chapman, P. J. Chupas, J. A. Hriljac, C. L. Renouf, T. C. A. Lucas and R. E. Morris, *Chem. Sci.*, 2012, **3**, 2559-2564.
- 55 55. J. E. Readman, P. M. Forster, K. W. Chapman, P. J. Chupas, J. B. Parise and J. A. Hriljac, *Chem. Commun.*, 2009, 3383-3385.
- 100 56. D. A. Keen, *J Appl Crystallogr*, 2001, **34**, 172-177.
- 57 57. C. L. Farrow, P. Juhas, J. W. Liu, D. Bryndin, E. S. Bozin, J. Bloch, T. Proffen and S. J. L. Billinge, *J. Phys.-Condens. Mat.*, 2007, **19**, 335219.
- 105 58. C. Kosanovic, J. Bronic, B. Subotic, S. I. M. Stubicar, A. Tonejc and T. Yamamoto, *Zeolites*, 1993, **13**, 261-268.
- 59 59. T. Puclin and W. A. Kaczmarek, *Colloid Surface A*, 1997, **129**, 365-375.
- 110