

# Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

**Magnetic colloidal superparticles of Co, Mn and Ni ferrite featured with comb-type and/or linear amphiphilic polyelectrolytes; NMR and MRI relaxometry**

Melita Menelaou,<sup>1</sup> Zacharoula Iatridi,<sup>2</sup> Ioannis Tsougos,<sup>3</sup> Katerina Vasiou,<sup>4</sup> Catherine Dendrinou-Samara<sup>1\*</sup> and Georgios Bokias<sup>2\*</sup>

<sup>1</sup>*Department of Chemistry, Aristotle University of Thessaloniki, GR-54124 Thessaloniki, Greece*

<sup>2</sup>*Department of Chemistry, University of Patras, GR-26504 Patras, Greece*

<sup>3</sup>*Department of Medical Physics, University Hospital of Larissa, University of Thessaly, Biopolis, GR-41110 Larisa, Greece*

<sup>4</sup>*Department of Radiology, University Hospital of Larissa, University of Thessaly, Biopolis, GR-41110 Larisa, Greece*

\*Corresponding Authors

C. Dendrinou-Samara, Phone (+30) 2310-997876; Fax (+30) 2310-997876; E-mail [samkat@chem.auth.gr](mailto:samkat@chem.auth.gr)

G. Bokias, Phone (+30) 2610-997102; Fax (+30) 2610-997122; E-mail [bokias@upatras.gr](mailto:bokias@upatras.gr)

## Abstract

The ability to encapsulate hydrophobic ferrites in colloidal superparticle structures of an  $\alpha$ -telechelic hexadecyl-functionalized poly(methacrylic acid) ( $C_{16}H_{33}$ -PMAA) polymer of linear architecture was investigated and compared to that of two amphiphilic comb-type water-soluble copolymers, namely P(ANa-co-DAAm) and P(MANa-co-DMA), comprised by a poly(sodium acrylate) or poly(sodium methacrylate) backbone and pendent dodecyl acrylamide or dodecyl methacrylate chains, respectively. In the case of  $C_{16}H_{33}$ -PMAA, the pH-sensitive self-assembly behavior, studied through Nile Red probing and TEM, was related to its encapsulation properties. Hydrophobic  $MFe_2O_4$  nanoparticles coated with oleylamine ( $MFe_2O_4@OAm$  MNPs where  $M=Co, Mn, Ni$ ) of similar shape and size ( $\sim 9$  nm) with magnetization values 87.4, 63.1 and 55.0 emu/g for  $CoFe_2O_4@OAm$ ,  $MnFe_2O_4@OAm$  and  $NiFe_2O_4@OAm$  respectively, were successfully encapsulated into the hydrophobic cores of the spherical micellar structures formed by the copolymers in aqueous solution, through a solvent mixing procedure. The synthesized magnetic colloidal superparticles fall in the static dephasing regime (SDR). NMR relaxivity measurements of  $MFe_2O_4@P(ANa-co-DAAm)$ ,  $MFe_2O_4@P(MANa-co-DMA)$  and  $MFe_2O_4@C_{16}H_{33}$ -PMAA at pH=4.5 and pH=7 (where  $M=Co, Mn, Ni$ ) at 11.7 T were recorded and transverse relaxivity ( $r_2$ ) ( $mM^{-1}s^{-1}$ ) was determined. Among all,  $CoFe_2O_4@$ polymers demonstrated the highest  $r_2$  relaxivity values, ranging from 61.6 for  $CoFe_2O_4@C_{16}H_{33}$ -PMAA (pH=7) to 316.0  $mM^{-1}s^{-1}$  for  $CoFe_2O_4@P(ANa-co-DAAm)$ . The relaxation efficiency ( $r_1$  and  $r_2$ ) of  $CoFe_2O_4@P(ANa-co-DAAm)$  was further investigated at 1.5 T and 3 T in magnetic resonance imaging (MRI) and the  $r_2/r_1$  ratio was found 16.5 and 18.2 respectively, indicating its potential use as  $T_2$  contrast agent.

## Introduction

Magnetic nanoparticles (MNPs) such as spinel ferrites with the general formula  $MFe_2O_4$  (where  $M=Mn, Co, Fe, Ni$ ) have attracted great attention due to their composition, size and shape dependent magnetic properties in various fields, spanning from electronics to bioapplications.<sup>1</sup> Although great progress has been done in the past few decades and even iron oxides have been commercialized for medical diagnosis, the successful use of MNPs in biomedical applications is complicated and MNPs are still being developed to improve enhanced magnetic properties and specificity to biological functions. On that basis, a new family of nanomaterials is generated by clustering small MNPs to larger particles in a colloidal phase, namely magnetic colloidal superparticles (MSPs).<sup>2</sup> These subsidiary functional materials exhibit collective chemical and physical properties inherited from their constituent nanoparticles and are proposed to overcome the limitations of primary MNPs.<sup>2</sup> For example, cooperative magnetic behavior within highly crystalline iron oxide into raspberry like or spherical superparticles<sup>2</sup> was found, which can improve diagnosis effectiveness and/or to be simultaneously therapeutic agents over existing nanostructures, while preserving biocompatibility. Fundamentally, the efficacy of magnetic nanoparticles either as single particles or superparticles, to act as  $T_2$ -contrast agents for Magnetic Resonance Imaging (MRI) is related to the transverse relaxivity ( $r_2$ ) which depends on their size and the square of the saturation magnetization ( $R_2 = 1/T_2 \propto \mu^2$ ).<sup>3</sup> Moreover, the nature of the surface coating around the magnetic core is crucial, since it controls the diffusion of water protons and the assembly of magnetic nanoparticles.<sup>4</sup> In fact, three different regimes have been predicted, where such factors can influence the relaxivity and therefore the contrast enhancement; the

motional average regime (MAR), the static dephasing regime (SDR) and the echo-limiting regime (ELR).<sup>5</sup>


The preparation of MSPs is based on colloidal assemblies, arisen through one step solvothermal route, microwave assisted synthesis or post transformation routes, where the involved evaporation-induced preparations, offer precise control of the superparticle size.<sup>6</sup> Synthesis of new polymers with specific properties for the encapsulation of MNPs is of great importance nowadays, as the resulted MSPs can improve the targeting efficiency in bioapplications, meanwhile degraded into small particles which can be subsequently less harmful for the body.<sup>7</sup>

The dispersion of hydrophobic MNPs in water through polymer encapsulation for potential MRI applications, is a major intriguing challenge for us and other groups, as it is a prerequisite for *in vitro* and *in vivo* applications. Within this context, a variety of amphiphilic diblock copolymers<sup>8,9,10,11,12</sup> as well as alkyl-functionalized comb-type copolymers<sup>13,14,15,16,17</sup> (often called hydrophobically modified water-soluble polymers (HMWSP)) have been explored, where monodispersed or superparticle structures can be formed through hydrophobic interactions and Van der Waals forces, depending on the type of the grafted tail and the grafting density. For example, the hydrophilization of iron oxide nanoparticles has been successfully applied using poly(maleic anhydride-alt-1-octadecene) modified with 5000Da polyethylene glycol (PEG) or short ethylene glycol (EG) chains.<sup>14</sup> In another study, Peng et al.<sup>17</sup> demonstrated the ability of poly(maleic anhydride-alt-1-octadecene)-g-poly(ethylene glycol) amphiphilic copolymers (PMAO-g-PEG) to form water soluble manganese ferrite MSPs. Recently, we have demonstrated that solvothermally prepared hydrophobic  $\text{CoFe}_2\text{O}_4$  MNPs coated with oleylamine ( $\text{CoFe}_2\text{O}_4@\text{OAm}$ ) were successfully encapsulated above the critical micellization concentration (CMC)

of the HMWSPs used, to form spherical hydrophilic superparticles.<sup>18</sup> These HMWSPs were comprised by a poly(sodium methacrylate) (PMANa) or poly(sodium acrylate) (PANa) backbone and pendent dodecyl methacrylate (DMA) or dodecyl acrylamide (DAAm) chains, respectively. However, to our knowledge reports on the use of alkyl modified amphiphilic copolymers with a linear architecture for such applications are very rare.<sup>19</sup> Nevertheless, alkyl thioether end-functionalized polymers usually bearing poly(acrylic acid) (PAA), poly(methacrylic acid) (PMAA) or poly(vinyl acetate) (PVAc), with 1-dodecane thiol, have been recently exploited in the synthesis of size-controlled Au NPs, Co NPs or Fe<sub>3</sub>O<sub>4</sub> NPs.<sup>19,20,21,22,23</sup>

Herein, we extend our studies on HMWSPs while we exploit the amphiphilic nature of an alkyl-functionalized copolymer with linear architecture for the hydrophilization of hydrophobic primary building units; namely, oleylamine-coated MFe<sub>2</sub>O<sub>4</sub> (M=Co, Mn, Ni) MNPs of different magnetization values. Thus, an a-telechelic hexadecyl-functionalized poly(methacrylic acid) (C<sub>16</sub>H<sub>33</sub>-PMAA, see Scheme 1) was tested as potential encapsulating polymeric agent and compared with the comb-type HMWSPs, denoted P(MANa-co-DMA) and P(ANa-co-DAAm) (see Scheme 1), respectively. We choose to keep constant the size and shape of the primary building units, since size and shape of the MNPs have been previously shown to affect relaxivities, while polymers of different architecture are tested; to our knowledge, such comparison is studied for the first time. Also, since (meth)acrylic units are weakly acidic in the case of C<sub>16</sub>H<sub>33</sub>-PMAA, the pH-sensitive encapsulating ability was explored at both pH=4.5 and pH=7. Relaxometric properties of the colloidal superparticles among MFe<sub>2</sub>O<sub>4</sub> (M= Co, Mn, Ni) MNPs and the synthesized copolymers have been pre-evaluated by NMR relaxivity ( $r_2$ ) studies, while MRI

measurements at 1.5 T and 3 T have been achieved for the most promising material; namely,  $\text{CoFe}_2\text{O}_4$  MSPs.

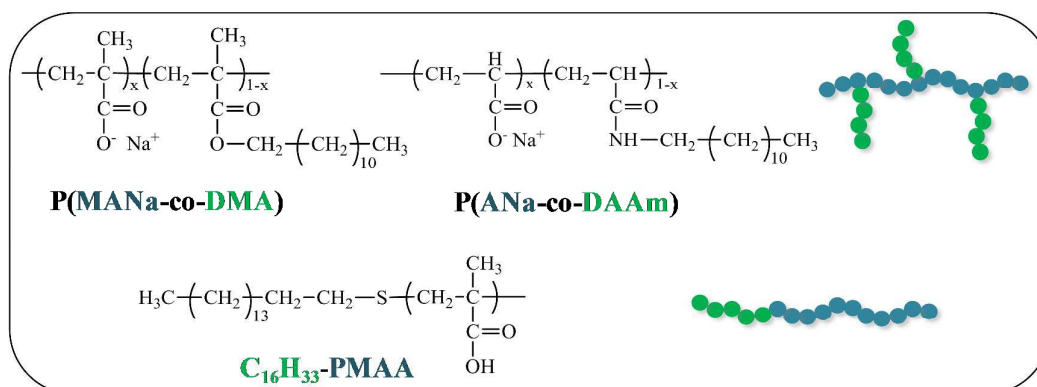

**Scheme 1.** Chemical structure and schematic depiction of the comb-type and linear architecture of the copolymers used in the present work.

## Experimental Part

### Materials

The monomer methacrylic acid (MAA) and the fluorescent probe Nile Red were purchased from Fluka. 1-Hexadecanethiol was purchased from Alfa Aesar. The initiator azobisisobutyronitrile (AIBN), cobalt(III) acetylacetonate ( $\geq 99.9\%$ ,  $\text{Co}(\text{acac})_3$ ), manganese(III) acetylacetonate ( $\geq 99.9\%$ ,  $\text{Mn}(\text{acac})_3$ ), oleylamine (OAm), diphenyl ether ( $\geq 99\%$ , DPHE) and the solvents tetrahydrofuran (THF), dioxane, petroleum ether and deuterated dimethyl sulfoxide ( $d_6$ -DMSO) were all purchased from Aldrich. Nickel(II) acetylacetonate ( $\geq 99.9\%$ ,  $\text{Ni}(\text{acac})_2$ ) was purchased from Riedel-de Haën. Ultrapure 3D-water was obtained by means of a SG Waters apparatus.

### Synthesis of $\alpha$ -telechelic hexadecyl-functionalized copolymer (C<sub>16</sub>H<sub>33</sub>-PMAA)

C<sub>16</sub>H<sub>33</sub>-PMAA was synthesized by the chain-transfer method utilizing 1-hexadecanethiol as the chain transfer agent. Typically, MAA, 1-hexadecanethiol and AIBN were dissolved in dioxane in a round-bottom flask equipped with a reflux

condenser. The reaction mixture was degassed with nitrogen for 2 hours and then was left overnight under stirring at 60 °C. The final polymer was recovered through precipitation in petroleum ether and dried under vacuum at 40 °C. After purification, it was characterized by <sup>1</sup>H-NMR, as far as the composition is concerned. The molecular weights and polydispersity were determined through GPC.

### Synthesis of comb-type copolymers

The synthesis of the P(MANa-co-DMA) and P(ANa-co-DAAm) copolymers has been described elsewhere.<sup>18</sup> Briefly, P(MANa-co-DMA) copolymer was prepared through free radical copolymerization of methacrylic acid and dodecylmethacrylate in THF at 70°C, using AIBN as initiator. This product was transformed to the sodium salt form, P(MANa-co-DMA), through neutralization with NaOH and recovered through freeze-drying, after purification through dialysis. For the synthesis of P(ANa-co-DAAm), PAA ( $M_w=5000$  g/mol) was grafted with dodecylamine in DMF at 60 °C, using DCC as condensing agent. After 24 hours, the solution was vacuum filtered to remove the unwanted dicyclohexyl urea byproduct and finally the sodium salt form was precipitated upon addition of a quantity of 1M NaOH aqueous solution. The final product was washed with DMF and methanol, vacuum filtered and dried in vacuum oven at 60 °C.

### Solvothermal synthesis of $MFe_2O_4@OAm$ nanoparticles

Based on our previous results,  $MFe_2O_4@OAm$  MNPs (where M= Co, Mn, Ni) were prepared by solvothermal route.<sup>18,24,25</sup> Briefly, 1.8 mmol of  $Fe(acac)_3$  and 0.9 mmol of  $M(acac)_2$  (M=Ni)/ $M(acac)_3$  (M=Co, Mn) were dissolved either in only OAm (M=Co) or in a mixture of OAm and DPHE (M=Mn,Ni). The resulting solution was stirred thoroughly and then transferred into a 23 mL Teflon-lined stainless-steel autoclave. The autoclave was placed in an electrical oven and temperature was raised



up to 200 °C for 24 h. The autoclave was then cooled to room temperature and the resulted product was washed with ethanol; thus, hydrophobic  $\text{MFe}_2\text{O}_4@\text{OAm}$  MNPs were obtained.

### **Preparation of magnetic colloidal superparticles $\text{MFe}_2\text{O}_4@\text{polymer}$**

Aqueous solutions of P(MANa-co-DMA), P(ANa-co-DAAm) and  $\text{C}_{16}\text{H}_{33}$ -PMAA at specific polymer concentrations were prepared in 3D water and left under stirring overnight. A small volume of a THF dispersion of  $\text{CoFe}_2\text{O}_4@\text{OAm}$ ,  $\text{MnFe}_2\text{O}_4@\text{OAm}$  or  $\text{NiFe}_2\text{O}_4@\text{OAm}$  MNPs was added in the aqueous polymer solutions. The polymer/MNPs mixing ratio was adjusted to 10/1 by weight. The mixtures were sonicated in a Branson 1510 70W, 40 kHz sonicator and then left at 40°C until full evaporation of THF. After THF removal, precipitation of a fraction of MNPs was observed. This fraction was discarded and the supernatant was used for further studies.

### **Characterization Techniques**

$^1\text{H}$ -NMR spectra of the copolymers in  $\text{d}_6$ -DMSO or  $\text{D}_2\text{O}$  were obtained on a Bruker Advance DPX 400 MHz spectrometer. The acid form of the copolymers, soluble in THF, was used for the Gel Permeation Chromatography (GPC) characterization. Two PLgel MiniMix columns “C” and “D” (molecular range 4000-340000 g/mol) were used and calibrated with polystyrene standards. THF was used as eluent. The elution rate was 0.5 mL/min. Powder X-ray diffraction (XRD) diagram was obtained by using a 2-cycle Rigaku Ultima + diffractometer (40 kV, 30 mA, CuK $\alpha$  radiation) with Bragg-Brentano geometry (detection limit 2% approximately). The elemental composition of the samples was tested by inductively coupled plasma atomic emission spectroscopy (ICP-AES), Perkin-Elmer Optima 3100XL. Fourier-Transform Infrared Spectroscopy was recorded using a Nicolet

FTIR 6700 spectrometer with KBr pellets in the range 350-4000  $\text{cm}^{-1}$ . Thermogravimetric Analysis (TGA) was performed using SETA-RAM SetSys-1200 and carried out in the range from room temperature to 850  $^{\circ}\text{C}$  at a heating rate of 10  $^{\circ}\text{C min}^{-1}$  under  $\text{N}_2$  atmosphere. Magnetic measurements were performed at 300K in a 1.2H/CF/HT Oxford Instruments VSM as function of the applied field (1 T).

### **Physicochemical characterization**

**Nile Red fluorescence probing.** Steady-state fluorescence spectra of Nile Red were recorded on a Perkin Elmer LS50B luminescence spectrometer. A small volume (5  $\mu\text{L}$ ) of a stock THF solution, containing  $1 \cdot 10^{-3}$  M Nile Red, was added in 3 mL of the aqueous polymer solution. The final concentration of the probe was, thus, fixed at  $1.7 \cdot 10^{-6}$  M. The maximum intensity of the emission peak of Nile Red in the region 600-650 nm, after excitation at 550 nm, was used to detect the formation of hydrophobic microdomains. The excitation and emission slits were fixed at 10 nm.

**Transmission Electron Microscopy (TEM).** TEM experiments were carried out using a JEM 2100 microscope operating at 200 kV. For the TEM investigation of pure MNPs, diluted THF dispersions were used, whereas aqueous solutions/dispersions were used for the TEM investigation of pure polymers and colloidal superparticles.

**Dynamic light scattering (DLS) and electrophoresis measurements** were carried out at 25  $^{\circ}\text{C}$  by means of a NanoZetasizer, Nano ZS Malvern apparatus. The incident light source was a 4 mW He-Ne laser at 633 nm and the intensity of the scattered light was measured at  $173^{\circ}$ . The mean hydrodynamic diameter was determined from the obtained apparent diffusion coefficient through the Stokes-Einstein equation.

**NMR Relaxivity Measurement.**  $T_2$  relaxation times were measured using a 500-MR NMR Spectrometer (500 MHz, Agilent Technologies) and at a temperature of 25  $^{\circ}\text{C}$  using a Carr-Purcell-Meiboom-Gill (CPMG) pulse sequence. The metal ion

concentration ( $\text{Fe} + \text{M}^{\text{II}}$ ) ( $\text{M}=\text{Co}, \text{Mn}, \text{Ni}$ ) of each aqueous solution was measured by inductively coupled plasma optical emission spectroscopy (ICP-OES).  $T_2$  was measured for a range of concentrations (0.05-0.8 mM) of metal ions ( $\text{Fe} + \text{M}^{\text{II}}$ ). The initial polymer concentration was in all cases 0.2 wt%. Moreover, care was taken during the dilutions, in order to preserve the final polymer concentration well above or close to CMC.

**MR Relaxivity Measurement.** The longitudinal ( $T_1$ ) and transverse ( $T_2$ ) relaxation times at different concentrations (0.0125-0.8 mM) of the metal ions were performed on two clinical MRI Scanners (a 1.5 T Siemens Aera and a 3T General Electric Signa) using a Head/Neck coil. The  $T_1$ -weighted images were obtained by an inversion recovery (IR)  $T_1$  pulse sequence with variable inversion values (IR=25 - 4000 ms) and an echo time (TE) of 12 ms (1.5 T)/43 ms (3 T). Imaging parameters were as follows: (a) 1.5 T; field of view (FOV)=250:250 mm<sup>2</sup>, matrix size (MTX)=128:128, number of axial slices=1, slice thickness=20 mm, and number of averages (NEX)=1 and (b) 3 T; field of view (FOV)=240:240 mm<sup>2</sup>, matrix size=416:320, number of axial slices=1, slice thickness=4 mm, and number of averages (NEX)=1.  $T_2$ -weighted images were obtained by a multi-echo spin-echo  $T_2$  pulse sequence (5 echoes; 25-50-75-100-125 ms, and static TR (2000 ms) for 1.5 T and 8 echoes; 50, 72, 94, 106, 139, 173, 206, 212 ms, and static TR (1560 ms) for 3 T). Imaging parameters were as follows: (a) 1.5 T; FOV=250:250 mm<sup>2</sup>, MTX=256:128, number of axial slices=1, slice thickness=5.0 mm, and NEX=1 and (b) 3 T; FOV=240:240 mm<sup>2</sup>, MTX=416:320, number of axial slices=1, slice thickness=4.0 mm, and NEX=1. The resulting set of images was processed off line using an image sequence analysis tool developed in IDL (IDL 8.2, Boulder, USA).  $T_1$  and  $T_2$  analyses were carried out by fitting a monoexponential curve

on the image intensities measured on the selected regions of interest (ROIs) for each axial slice.

## Results and Discussion

In the present study we select to use ~9 nm building units of MNPs, since previously it has been shown that small sizes (often lower than 7 nm) cannot influence positively the  $r_2$  values, while slightly bigger sizes can lead to optimized results.<sup>26</sup> For that reason, we adopted a previously reported by us solvothermal synthesis to isolate ferrite MNPs of similar size and shape.<sup>18,24,25</sup> In brief, fine cubic spinel structures Fd3m of ferrite nanoparticles  $MFe_2O_4$  (where M=Co, Mn, Ni) were solvothermally synthesized through metal acetylacetonates precursors in the presence of oleylamine (OAm). The crystal structures of the primary units were verified by XRD patterns (**Fig. S1a**) while crystallite sizes were calculated using Scherrer's formula at 9.2 nm for  $CoFe_2O_4@OAm$ , 9.0 nm for  $MnFe_2O_4@OAm$  and 9.3 nm for  $NiFe_2O_4@OAm$ , respectively; almost identical sizes compared to those found by TEM images (**Fig. 1a-c**). The presence of OAm was certified by FT-IR spectroscopy (**Fig. S1b**) and the total amount of weight loss was found by thermogravimetric analysis (TGA) which is equal to 27.5 wt %, 23.0 wt % and 29.5 wt % for  $CoFe_2O_4@OAm$ ,  $MnFe_2O_4@OAm$  and  $NiFe_2O_4@OAm$ , respectively (**Fig. S1b and S1c**). Additionally, using TGA results the coverage of OAm molecules surrounding each nanoparticle has been quantified; based on the assumption that all nanoparticles are spherical, the number of OAm ligands (N) for each  $MFe_2O_4$  system, was calculated according to equation (1);<sup>27</sup> 1338.2 ( $CoFe_2O_4@OAm$  NPs), 1029.2 ( $MnFe_2O_4@OAm$  MNPs) and ~1352.5 ( $NiFe_2O_4@OAm$  NPs), respectively. Also, based on Eq. (1)<sup>27</sup>, the number of molecules per area ( $A=4\pi R^2$ ) was calculated;  $5.03\cdot 10^{14}$  ( $CoFe_2O_4@OAm$  MNPs),  $4.04\cdot 10^{14}$  ( $MnFe_2O_4@OAm$  MNPs) and  $5.20\cdot 10^{14}$  ( $NiFe_2O_4@OAm$  MNPs),

respectively. These results can further provide a stronger evidence of the thickness of the organic coating around the metal core for each of the three studied systems.

$$N = \frac{\omega N_A \rho \frac{4}{3} \pi R^3 10^{-23}}{MM} \quad (1)$$

where:  $N$  is the number of ligands on each particle,  $R$  is the mean radius of the  $MFe_2O_4$  NPs,  $\rho$  is the density of the  $MFe_2O_4$  MNPs ( $M=Co, Mn, Ni$ ; 5.304 g/cm<sup>3</sup>, 5.21 g/cm<sup>3</sup> and 5.164 g/cm<sup>3</sup>, respectively),  $N_A$  is Avogadro's number,  $MM$  is the mean molar mass of the OAm molecules (g/mol), and  $\omega$  is the mass loss (%).


The resulted ferrite MNPs displayed enhanced  $M_s$  values depending on the nature of the divalent ion, with absolute magnetization values at 87.4 emu/g for  $CoFe_2O_4@OAm$ , 63.1 emu/g for  $MnFe_2O_4@OAm$  and 55.0 emu/g for  $NiFe_2O_4@OAm$  (**Fig. S1d**).

#### Formation of magnetic colloidal superparticles with comb-type copolymers

For the formation of colloidal superparticles of  $MFe_2O_4@OAm$  ( $M= Co, Mn, Ni$ ) MNPs, two comb-type HMWSPs based on a carboxylate backbone and dodecyl- side chains, namely P(MANa-co-DMA) and P(ANa-co-DAAm), were explored. The chemical structure and the depiction of the architecture of the comb-type copolymers are shown in **Scheme 1**, while the characterization results of the copolymers are tabulated in **Table 1**.<sup>18</sup> In our previous report,  $CoFe_2O_4@HMWSPs$  nano hybrids were effectively stabilized in water through a solvent mixing procedure.<sup>18</sup> In the present work we further extend this concept and we utilize comb-type copolymers to disperse hydrophobic  $MnFe_2O_4@OAm$  and  $NiFe_2O_4@OAm$  MNPs.

Representative TEM images of the spherical nanostructures stabilized in water, and the intensity-weighted distribution of the hydrodynamic diameter (determined through DLS) of  $MFe_2O_4@P(MANa-co-DMA)$  and  $MFe_2O_4@P(ANa-co-DAAm)$  (where  $M= Mn, Ni, Co$ ) are shown in **Fig. 1**. The hydrodynamic diameter is ~180 nm

and  $\sim 140$  nm for  $\text{MnFe}_2\text{O}_4@\text{P}(\text{MANa-co-DMA})$  (inset of **Fig. 1d**) and  $\text{MnFe}_2\text{O}_4@\text{P}(\text{ANa-co-DAAm})$  (inset of **Fig. 1g**), respectively. The estimated diameter from TEM images varied in the range 90-100 nm (**Fig. 1d**) and 45-65 nm (**Fig. 1g**), for the  $\text{MnFe}_2\text{O}_4@\text{P}(\text{MANa-co-DMA})$  and  $\text{MnFe}_2\text{O}_4@\text{P}(\text{ANa-co-DAAm})$  nanohybrids, respectively. A similar behavior was exhibited by the  $\text{NiFe}_2\text{O}_4@\text{copolymer}$  samples;  $\text{NiFe}_2\text{O}_4@\text{P}(\text{MANa-co-DMA})$  nanohybrids form nanostructures (**Fig. 1e**) with a diameter of  $\sim 180$  nm (from DLS) and 70-90 nm (from TEM), while  $\text{NiFe}_2\text{O}_4@\text{P}(\text{ANa-co-DAAm})$  form nanostructures (**Fig. 1h**) with a diameter of  $\sim 185$  nm (from DLS) and 150-170 nm (from TEM). Finally, the size of the  $\text{CoFe}_2\text{O}_4@\text{P}(\text{MANa-co-DMA})$  was  $\sim 150$  nm (from DLS) and 65-90 nm (from TEM) (**Fig. 1f**) and  $\sim 140$  nm (from DLS) and 45-90 nm (from TEM) for  $\text{CoFe}_2\text{O}_4@\text{P}(\text{ANa-co-DAAm})$  (**Fig. 1i**). Although there are not such big numerical differences of the organic coating of the primary building MNPs, taking into account the similar sizes of the metal core and the same surfactant, we assume that the way of bounding and/or small differences of the thickness of the organic coating, influences the uniform supramolecular structures formation.

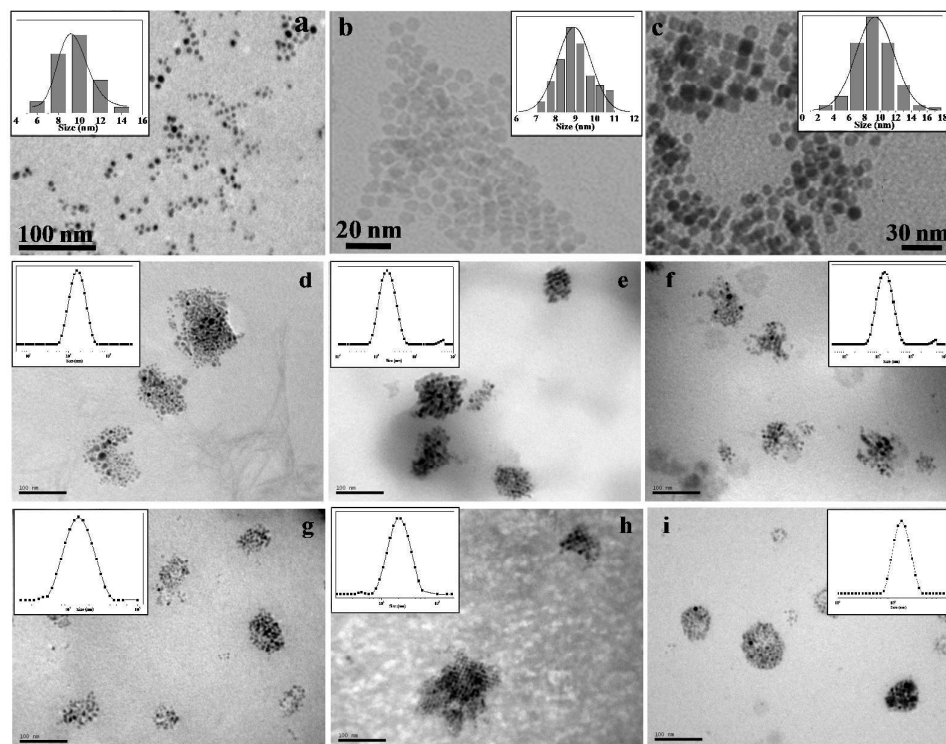

**Fig. 1.** TEM images of single particles (a)  $\text{CoFe}_2\text{O}_4@\text{OAm}$ , (b)  $\text{MnFe}_2\text{O}_4@\text{OAm}$  and (c)  $\text{NiFe}_2\text{O}_4@\text{OAm}$  as well as  $\text{MFe}_2\text{O}_4@\text{P(MANa-co-DMA)}$  where (d)  $\text{M}=\text{Mn}$ , (e)  $\text{M}=\text{Ni}$ , (f)  $\text{M}=\text{Co}$ , and  $\text{MFe}_2\text{O}_4@\text{P(ANa-co-DAAM)}$  where (g)  $\text{M}=\text{Mn}$ , (h)  $\text{M}=\text{Ni}$  and (i)  $\text{M}=\text{Co}$ . The copolymer concentration is 0.3 wt% (above CMC for both polymers). Scale bar in (d)-(i): 100 nm. Inset: distribution of the hydrodynamic diameter as determined by DLS.

### Formation of magnetic colloidal superparticles (MSPs) with the linear copolymer $\text{C}_{16}\text{H}_{33}\text{-PMAA}$

Synthesis and characterization of linear polymer  $\text{C}_{16}\text{H}_{33}\text{-PMAA}$  Thiol-containing molecules are efficient chain transfer agents and, in combination with adequate initiators like azobisisobutyronitrile (AIBN)<sup>19-23</sup> or ammonium persulfate,<sup>28</sup> they are applied for chain transfer polymerizations in organic or aqueous media, respectively. As a consequence of the chain transfer polymerization mechanism, the thiol group is

attached at the one end of the polymer chain, through a thioether bond, leading to products of low molecular weights and narrow polydispersity.<sup>22</sup> The synthesis of functional thioether polymers using monomers like acrylic acid (AA) or methacrylic acid (MAA) and dodecanethiol as chain transfer agent has already been reported in literature.<sup>19-23</sup> Herein, we apply this methodology for the synthesis of an  $\alpha$ -telechelic amphiphilic copolymer, namely poly(methacrylic acid), PMAA, end-functionalized with a more hydrophobic, longer alkylthiol, namely 1-hexadecanethiol. Dioxane was chosen as a desirable reaction solvent for the monomer MAA, the chain transfer agent 1-hexadecanethiol and the initiator AIBN. The chemical structure and schematic depiction of the architecture of C<sub>16</sub>H<sub>33</sub>-PMAA are shown in **Scheme 1**. The copolymer was characterized by <sup>1</sup>H-NMR, using d<sub>6</sub>-DMSO as deuterated solvent, and GPC in THF. The characterization results are summarized in **Table 1**. From the <sup>1</sup>H-NMR characterization, the MAA content of the copolymer is found to be 94 mol%. This suggests that ~ 16 MAA units are polymerized at each hexadecanethiol group, leading to an estimated number-average molecular weight, M<sub>n</sub> ~ 1630 g/mol. This value is in a rather good agreement with the value M<sub>n</sub>=2600 g/mol determined through GPC, using polystyrene standards. Moreover, from GPC characterization the weight-average molecular weight M<sub>w</sub> is determined to be M<sub>w</sub>=3600 g/mol. Thus, the obtained low molecular weight together with the observed narrow polydispersity index (PI=1.38) suggests that the chain transfer polymerization mechanism is indeed effective.

Since the PMAA block of C<sub>16</sub>H<sub>33</sub>-PMAA is a weak polyacid, i.e. the degree of dissociation depends on the pH of the solution, this copolymer is expected to exhibit a pH-sensitive self-association behavior in aqueous media. In fact, this is shown in Fig. 2a, where the influence of pH on the CMC of C<sub>16</sub>H<sub>33</sub>-PMAA is investigated in



aqueous buffer solutions ( $4.5 < \text{pH} < 7$ ) through fluorescence probing with Nile Red. Nile Red is poorly soluble in water but its solubility increases in a less polar environment. In addition, it is almost non-fluorescent in water and other polar solvents, while it is strongly fluorescent in less polar environments, showing an intense emission peak in the region of 600-650 nm. The CMC is the polymer concentration above which the amphiphilic copolymers form micellar-like structures with hydrophobic cores consisted of the pendant alkyl chains and hydrophilic coronas consisted of the anionic polyelectrolyte backbones. As it can be observed, the copolymer exhibits a similar behavior in all buffer solutions for  $\text{pH} \leq 5.5$ . Within this pH region, the PMAA block is just slightly ionized, as suggested by the low absolute  $\zeta$ -potential value (**Table 1**) of the formed micellar aggregates, since the  $\text{pK}_a$  of pure PMAA is estimated to be  $\text{pK}_a \sim 5.5$ .<sup>29</sup> As a result, the CMC of the copolymer, determined as the polymer concentration at the onset of the fluorescence intensity of the probe, is  $\sim 0.001$  wt% for  $\text{pH} \leq 5.5$ . For pH higher than the  $\text{pK}_a$  of pure PMAA, the carboxylic groups of PMAA block become gradually ionized, the polyacid blocks are more extended and a higher polymer concentration is necessary in order to detect micellar nanostructures in aqueous media. Thus, the CMC is detected at a polymer concentration of 0.01 and 0.03 wt% for the buffer solutions with  $\text{pH}=6$  and  $\text{pH}=7$ , respectively, while the formed micellar aggregates are characterized by a higher absolute  $\zeta$ -potential value (**Table 1**). Finally, when the copolymer is dissolved in pure water, the solution is slightly acidic,  $\text{pH} \sim 4.5$ , as expected. However, as compared to the behavior observed in the buffer solution with  $\text{pH}=4.5$ , the CMC of the copolymer in pure water is higher,  $\text{CMC} \sim 0.002$  wt%. This slight CMC difference is attributed to the presence of salt in the buffer solution, enabling self-association, as a consequence of the screening of the (low) fraction of charges along the polyacid block.

**Table 1.** Physicochemical characterization of the amphiphilic copolymers.


Copolymer	Composition ( <sup>1</sup> H-NMR) <sup>a</sup>	Mn, g/mol (GPC)	Mw, g/mol (GPC)	ζ-potential, mV	CMC <sup>c</sup> , wt%
P(MANa-co-DMA)*	75	27800	73600	-40.7	0.002
P(ANa-co-DAAm)*	90	-	7500 <sup>b</sup>	-46.8	0.100
C <sub>16</sub> H <sub>33</sub> -PMAA	94	2600	3600	-15.9 (at pH 7.5)	0.020
				-10.0 (at pH 4.5)	0.002

\* From ref. 18.

<sup>a</sup> % moles of MANa, ANa or MAA units; <sup>b</sup> calculated from the nominal mass of PAA and the composition of the copolymer, as found through <sup>1</sup>H-NMR; <sup>c</sup> from Nile Red probing.

In order to get a visual confirmation of the nanostructures formed by the C<sub>16</sub>H<sub>33</sub>-PMAA copolymer in aqueous media, we proceeded in TEM characterization at polymer concentrations above CMC at two pH values, pH=4.5 and pH=7.5. Representative results are shown in **Fig. 2**. The size of the aggregates formed at lower pH values is generally smaller compared to that of the aggregates formed at a more basic environment. More specifically, the copolymer forms micellar nanostructures with a diameter of 25-50 nm at pH=4.5 (**Fig. 2b**) and 125-325 nm at pH=7.5 (**Fig. 2c**). The formed micelles at pH=4.5 are probably multichain aggregates with a spherical shape where the hydrophobic hexadecane units are located in the center, while the hydrophilic PMAA blocks provide water solubility and stability of the formed micelles in the aqueous solution. When pH increases to higher values, the formed aggregates display an expansion in size, due to the enhanced osmotic pressure of the counter-ions trapped inside the polymeric network by the electrostatic attraction exerted by the charged carboxylate groups.<sup>29,30</sup> As a consequence, the multichain aggregates formed at low pH probably change to large-compound micelles at pH=7.5,


as it has been shown in the case of amphiphilic P(MANa-co-DMA) and P(ANa-co-DAAm) comb-type copolymers.<sup>18</sup>

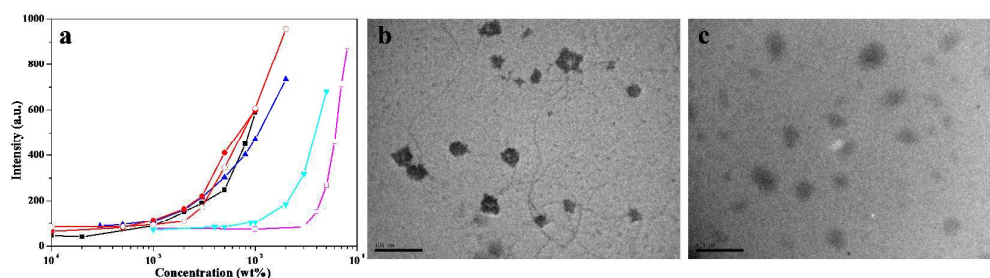

**Fig. 2.** (a) Dependence of the maximum fluorescence intensity of Nile Red at 600-650 nm on the C<sub>16</sub>H<sub>33</sub>-PMAA concentration in buffer solutions (pH=2 (■), pH=4.5 (●), pH=5.5 (▲), pH=6 (▼) and pH=7 (□) or at pure water (pH~4.5) (○)), TEM images of aqueous C<sub>16</sub>H<sub>33</sub>-PMAA solutions at (b) 0.01 wt% and pH=4.5 (above CMC, scale bar: 100 nm) and (c) 0.3 wt% and pH=7.5 (above CMC, scale bar: 500 nm).

Encapsulation of hydrophobic MNPs by the linear C<sub>16</sub>H<sub>33</sub>-PMAA copolymer. End-telomerized polymers with dodecyl groups have been previously reported to disperse Au NPs, Co NPs or iron oxide NPs in aqueous media.<sup>19-23</sup> In all cases, the nanoparticles are *in situ* synthesized, using either reduction agents or basic solutions in the presence of the polymer. In contrast, in the present study a post synthetic procedure is applied to form the colloidal superparticles between the already prepared hydrophobic MNPs, taking advantage of the ability of the polymer to form water soluble micellar-type structures. Representative TEM images and the distribution of the hydrodynamic diameter measured by DLS of the colloidal superparticles (MFe<sub>2</sub>O<sub>4</sub>@C<sub>16</sub>H<sub>33</sub>-PMAA (M= Co, Mn, Ni)) are shown in **Fig. 3**. It should be noted that the assemblies formed are generally seen smaller in TEM with respect to the DLS results, due to evaporation of the solvent and the shrinkage or the dehydration of the micellar aggregates. In the TEM images, only the hydrophobic cores with the

incorporated  $\text{MFe}_2\text{O}_4@OAm$  MNPs are observable and not the hydrophilic part of the micelles, as a consequence of the high contrast of the MNPs. Thus, although similar hydrodynamic sizes of  $\sim 125$ - $160$  nm are found through DLS, from TEM investigation the importance of pH and/or the nature of MNPs is more clearly evidenced. The supramolecular structures formed by the  $\text{MFe}_2\text{O}_4@C_{16}H_{33}\text{-PMAA}$  seem more uniform in the case of Co and Mn ferrite MNPs while in the case of Ni they are less uniform, possibly due to dispersibility limitations. The mean size of the aggregates seems to increase with pH, in a qualitative agreement with the behavior of the pure copolymer above CMC (Fig. 2). This is more clear in the cases of  $\text{CoFe}_2\text{O}_4@C_{16}H_{33}\text{-PMAA}$  (the mean size increases from  $\sim 40$ - $60$  nm at  $\text{pH}=4.5$  to  $100$ - $120$  nm at  $\text{pH}=7.5$ ) and  $\text{NiFe}_2\text{O}_4@C_{16}H_{33}\text{-PMAA}$  (at  $\text{pH}=4.5$  the smaller objects with sizes of  $\sim 30$ - $40$  nm seem to disappear and to be replaced by objects with a more uniform size of  $\sim 90$ - $100$  nm at  $\text{pH}=7.5$ ). Also, uniformity at the same pH between the different MNPs may be explained, as stated before, to the organic coating of the primary building MNPs.

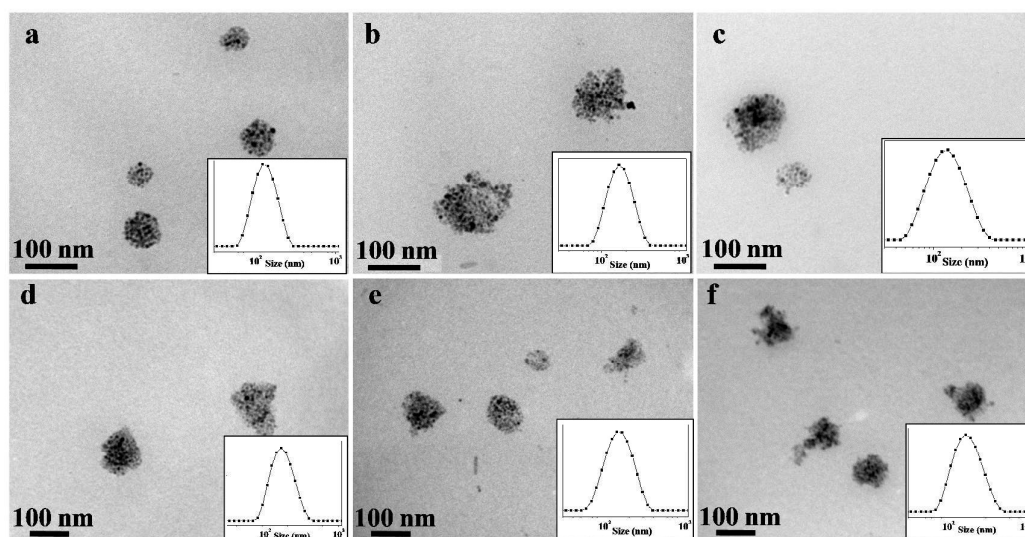

**Fig. 3.** TEM images of  $\text{MFe}_2\text{O}_4@C_{16}H_{33}\text{-PMAA}$  where (a and d)  $M=\text{Co}$ , (b and e)  $M=\text{Mn}$  and (c and f)  $M=\text{Ni}$  above CMC (0.3 wt%) at  $\text{pH}=4.5$  (a, b, c) and  $\text{pH}=7.5$  (d,

e, f). Scale bar: 100 nm. Inset: distribution of the hydrodynamic diameter, as determined by DLS.

Based on the hydrodynamic diameters of the MSPs formed either by the linear or the two comb-type amphiphilic copolymers, the maximum number of single nanoparticles in a superparticle ( $N_{Sup}$ ) was calculated through Eq. 2.<sup>5</sup> The results are listed in Table 2; roughly ~15-20 MNPs may fit in one MSP for all systems.

$$\frac{4}{3}\pi R_{Sup}^3 = N_{Sup} \frac{4}{3}\pi R^3 \quad (2)$$

where:  $R_{Sup}$  is the superparticle radius (determined by DLS),  $R$  is the radius of the nanoparticle, and  $N_{Sup}$  is the number of nanoparticles in the superparticle.

### NMR and MR Relaxivity Measurements

The efficiency of magnetic nanoparticles to act as  $T_2$ -contrast agents for MRI is related to the transverse relaxivity ( $r_2$ ) which occurs in three different regions while theoretical models have been described in order to predict relaxivity in each regime.<sup>31</sup> In the first regime which is called motional average regime (MAR) or outer sphere,  $r_2$  increases with the size of the MSPs while in the second regime, called static dephasing regime (SDR) which is the most interesting from the MRI point of view, the highest relaxivities occur and depend on the magnetization properties of the MSPs and not on the shape or density of the MSPs.<sup>31</sup> In the third regime, called echo-limiting regime (ELR), an echo-dependant decrease of relaxation is observed and is expected to be independent from the shape of the MSPs.<sup>31</sup>

The size dependence of the  $r_2$  in MAR originates from the diffusion of water molecules and the regime is reached only when Redfield condition is fulfilled ( $\gamma B_{eq} \tau_D < 1$  or  $\Delta \omega \tau_D < 1$ );<sup>1,31</sup> thus the condition can be expressed by calculating the

diffusion time ( $\tau_D$ ) and the equatorial magnetic field ( $B_{eq}$ ) (Eq. 3). At a certain size,  $r_2$  no longer increases with increasing size, since the SDR is reached ( $\gamma B_{eq}\tau_D \gg 1$  or more precisely  $5 < \Delta\omega\tau_D < 20$ ).<sup>1,31</sup>

$$\tau_D = \frac{d^2}{4D} \quad B_{eq} = \frac{\mu_0}{3} M_s \quad \Delta\omega = \gamma B_{eq} \quad (3)$$

where:  $\tau_D$  is the diffusion time,  $d$  is the hydrodynamic diameter (determined by DLS), and  $D$  is the water diffusion coefficient ( $D=3 \cdot 10^{-9} \text{ m}^2\text{s}^{-1}$ );  $B_{eq}$  is the equatorial magnetic field of the MNPs,  $\mu_0$  is the vacuum magnetic permeability ( $4\pi \cdot 10^{-4} \text{ T emu}^{-1}\text{cm}^{-3}$ ),  $M_s$  is the normalized magnetization of the MNPs;  $\Delta\omega$  is the Larmor frequency shift and  $\gamma$  is the proton gyromagnetic ratio.

When SDR is reached, the transverse relaxation rate,  $R_2$  and  $R_2^*$ , are equal and given by:<sup>1</sup>  $R_2^* = \frac{1}{T_2^*} = \frac{2\pi}{3\sqrt{3}} \nu \gamma B_{eq} = \frac{2\pi}{3\sqrt{3}} f \Delta\omega \approx R_2$


In this respect, at first we examine in which regime the synthesized superparticles fall;  $\Delta\omega\tau_D$  was calculated for all formed MSPs. The values for all the systems were in the range of 6.5 to 17.5 as it is depicted in **Table 2** and SDR regime identified. A linear concentration dependence of the transverse relaxation rate [ $R_2$  ( $1/T_2$ )] with respect to the metal ions concentration ( $C$ ) was observed by NMR relaxometric measurements for all samples, permitting therefore the determination of transverse relaxivity ( $r_2$ ) value based on Eq. 4 (**Fig. 4**).<sup>32</sup> The calculated  $r_2$  values are listed in **Table 2**.

$$R_2 = \frac{1}{T_2} = \frac{1}{T_2^0} + r_2 C \quad (4)$$


where:  $T_2$  is the proton relaxation time in the presence of MNPs,  $T_2^0$  is the proton relaxation time of pure water and  $C$  is the concentration of the metal ions ( $\text{Fe}+\text{M}^{\text{II}}$ ).

The results as depicted in **Fig. 4**, were indicative of the importance of the difference in the magnetic properties ( $M_s$ ) of the single ferrite particles ( $M_{s \text{ Co}} > M_{s \text{ Mn}}$

$> M_{s, Ni}$ ) as well as the difference in the architecture of the amphiphilic polymers (comb-type and linear); the highest  $r_2$  values among the synthesized colloidal superparticles of all samples were obtained when  $CoFe_2O_4$  MNPs were used as single particles attributed to the collective magnetic properties of the building units. Moreover, encapsulation of the single particles in the copolymers with comb-type architecture featured higher  $r_2$  values for all systems compared with the one with linear architecture (**Fig. 5**); in particular the highest  $r_2$  value was obtained for  $CoFe_2O_4$  and  $NiFe_2O_4$  MSPs in the presence of P(ANa-co-DAAm) ( $316.0 \text{ mM}^{-1}\text{s}^{-1}$  and  $110.4 \text{ mM}^{-1}\text{s}^{-1}$ , respectively). However, the presence of P(ANa-co-DAAm) for  $MnFe_2O_4$  MSPs, led to lower  $r_2$  value ( $128.9 \text{ mM}^{-1}\text{s}^{-1}$ ). In this case, the  $\Delta\omega\tau_D$  value is at  $\sim 8$ , close to the lower limit of the regime. Thus, we can assume that  $MnFe_2O_4@P(ANa-co-DAAm)$  is neither in the MAR nor completely in the SDR regime as was also previously found.<sup>1</sup> Nevertheless, the highest relaxivity was shown by the comb-type polymer  $MnFe_2O_4@P(MANa-co-DMA)$  ( $152.5 \text{ mM}^{-1}\text{s}^{-1}$ ). In the case of the linear polymer, pH values also affected the resulted relaxivities since at pH=4.5 all MSPs showed increased values compared to those found at pH=7, indicative of the pH dependence (**Table 2**). Based on the above results, the difference in the architecture of the polymers is proven to be a crucial factor for differentiating the  $r_2$  values of the MSPs. In addition to the different topology, the relatively higher hydrophobic content and higher molecular weight (**Table 1**) also favor the encapsulation efficiency of the comb-type copolymers as compared to that of the linear one. To fully elucidate this behavior, further information is needed, concerning the relation of the encapsulation ability with the polymer architecture (comb-type or linear one), the hydrophilic-lipophilic balance of the copolymers and the respective variation of the aggregation numbers of the resulting polymeric micelles.

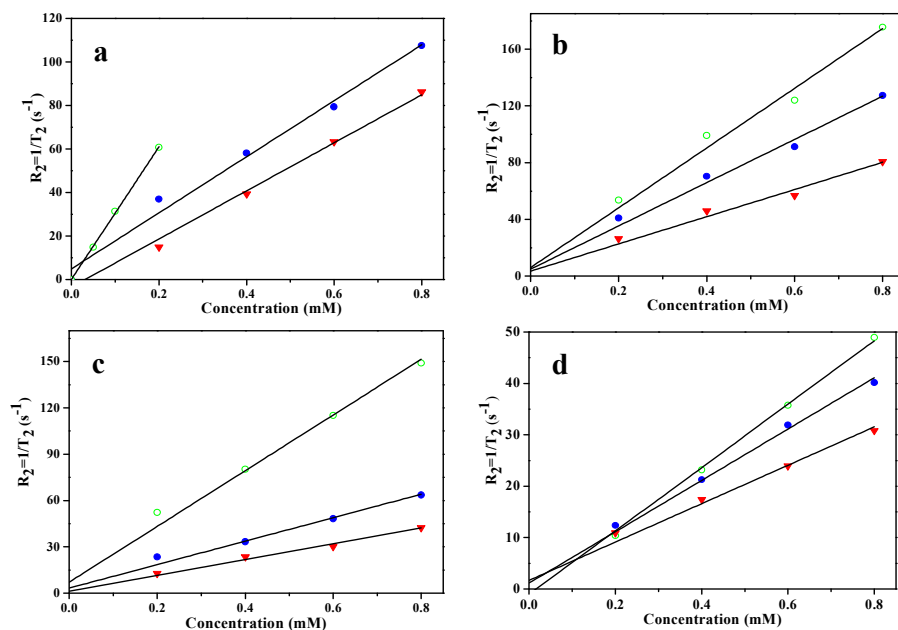

**Fig. 4.** NMR Relaxometric properties of (a)  $\text{MFe}_2\text{O}_4@\text{P(ANa-co-DAAm)}$ , (b)  $\text{MFe}_2\text{O}_4@\text{P(MANa-co-DMA)}$ , (c)  $\text{MFe}_2\text{O}_4@\text{C}_{16}\text{H}_{33}\text{-PMAA}$  at  $\text{pH}=4.5$  and (d)  $\text{MFe}_2\text{O}_4@\text{C}_{16}\text{H}_{33}\text{-PMAA}$  at  $\text{pH}=7$ , where  $\text{M}=\text{Co}$  ( $\circ$ ),  $\text{Mn}$  ( $\bullet$ ) and  $\text{Ni}$  ( $\blacktriangledown$ ), respectively.

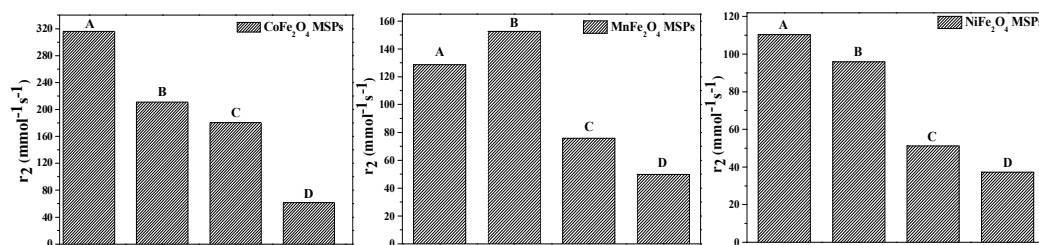


**Fig 5.** Transverse relaxivity ( $r_2$ ) values of Co, Mn, and Ni ferrite MCSs (where: A:  $\text{P(ANa-co-DAAm)}$ ; B:  $\text{P(MANa-co-DMA)}$ ; C:  $\text{C}_{16}\text{H}_{33}\text{-PMAA}$  at  $\text{pH}=4.5$  and D:  $\text{C}_{16}\text{H}_{33}\text{-PMAA}$  at  $\text{pH}=7$ ).

Furthermore, the performance of the  $\text{CoFe}_2\text{O}_4@\text{P(ANa-co-DAAm)}$ , that exhibited the highest  $r_2$  value, was examined at 1.5 T and 3 T MRI scanners to explore the effectiveness of the system under different magnetic field. The MR  $T_1$ -weighted and



$T_2$ -weighted phantom images in **Fig. 6** demonstrated the concentration-dependent  $T_1$  brightening effect and  $T_2$  darkening effect. The relaxivity values ( $r_1$  and  $r_2$ ) were determined through the curve fitting of the linear relationship according to Eq. 4 (**Fig. 6**).  $r_1$  and  $r_2$  were found 0.58 (1.5 T)/0.7 (3 T) and 9.6 (1.5 T)/12.7 (3 T), respectively. These values are lower compared to those of the commercially available contrasts agents such as Magnevist (3.3 (1.5 T)/3.1 (3 T) and 3.9 (1.5 T)/3.7 (3 T)), Resovist (8.7 (1.5 T)/4.1 (3 T) and 61 (1.5 T)/143 (3 T)) and Feridex (4.6 (1.5 T)/4.1 (3 T) and 41 (1.5 T)/93 (3 T))<sup>33</sup> which can be attributed to various factors including the different structure of the surface coating and the hydrodynamic diameter. However,  $r_2/r_1$  ratio which is very important to determine whether a contrast agent has mainly a  $T_1$ -reducing or  $T_2$ -reducing effect, was found 16.5 at 1.5 T and 18.2 at 3 T. These values are close to previous reports for the iron oxide MNPs - Feridex/Endorem (8.9 at 1.5 T and 22.7 at 3 T).<sup>33</sup>

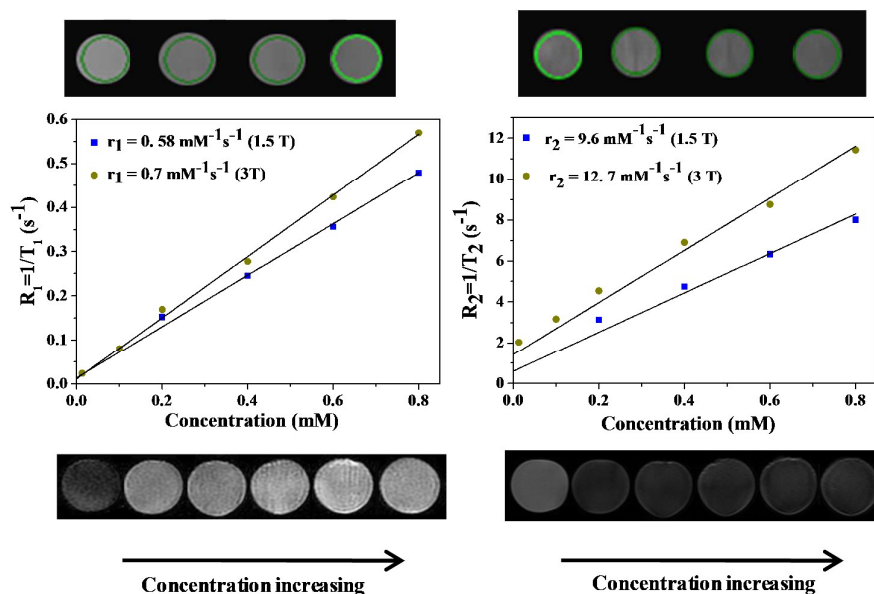

**Fig. 6.**  $T_1$ -weighted and  $T_2$ -weighted MR images as well as  $T_1$  and  $T_2$  relaxivity plots of  $\text{CoFe}_2\text{O}_4@P(\text{ANa-co-DAAm})$  at 1.5 T (■) and 3 T (●), respectively.

**Table 2.**  $D_{hydro}$ : the hydrodynamic diameter (DLS) of the superparticles,  $N_{Sup}$ : number of single nanoparticles in the superparticle;  $\zeta$ -potential;  $\Delta\omega$ : the Larmor frequency shift;  $\tau_D$ : the translational time and  $r_2$ : relaxivity values of the MSPs in the presence of the copolymers.

Polymer employed in the encapsulation process	$D_{hydro}$ (nm)	$N_{Sup}$	$\zeta$ -potential (mV)	$\Delta\omega\tau_D$	$r_2$ ( $\text{mM}^{-1}\text{s}^{-1}$ )	Regime
$\text{CoFe}_2\text{O}_4@\text{OAm}$ / 9.2 nm / 87.4 $\text{emu g}^{-1}$						
P(ANa-co-DAAm)	140	16	-57.1	12.5	316.0	SDR <sup>a</sup>
P(MANa-co-DMA)	150	17	-45.7	15.2	210.7	SDR
$\text{C}_{16}\text{H}_{33}$ -PMAA (pH=4.5)	125	14	-23.8	10.3	180.3	SDR
$\text{C}_{16}\text{H}_{33}$ -PMAA (pH=7)	160	18	-58.7	17.5	61.60	SDR
$\text{MnFe}_2\text{O}_4@\text{OAm}$ / 9.0 nm / 63.1 $\text{emu g}^{-1}$						
P(ANa-co-DAAm)	130	14	-43.3	8.30	128.7	SDR/MAR <sup>b</sup>
P(MANa-co-DMA)	180	20	-35.9	16.6	152.5	SDR
$\text{C}_{16}\text{H}_{33}$ -PMAA (pH=4.5)	160	18	-21.0	12.9	75.90	SDR
$\text{C}_{16}\text{H}_{33}$ -PMAA (pH=7)	140	16	-54.7	10.0	49.90	SDR
$\text{NiFe}_2\text{O}_4@\text{OAm}$ / 9.1 nm / 55.0 $\text{emu g}^{-1}$						
P(ANa-co-DAAm)	185	21	-42.2	13.9	110.4	SDR
P(MANa-co-DMA)	180	20	-35.6	13.0	95.90	SDR
$\text{C}_{16}\text{H}_{33}$ -PMAA (pH=4.5)	125	14	-21.6	6.50	51.20	SDR
$\text{C}_{16}\text{H}_{33}$ -PMAA (pH=7)	160	18	-57.3	10.8	37.30	SDR

<sup>a</sup>SDR: Static Dephasing Regime; <sup>b</sup>MAR: Motional Average Regime

## Conclusions

Hydrophobically modified magnetic superparticles (MSPs) can be challenging candidates for biomedical applications including magnetic resonance imaging (MRI). Polymer addition led to a controlled manner clustering and water dispersity while the successful encapsulation can be considered as a host-guest process. The architecture of amphiphilic polymers is found to be crucial to the relaxivity properties of MSPs. Thus, among the tested polymers for the encapsulation of the same primary building blocks of  $\text{MFe}_2\text{O}_4@\text{OAm}$  MNPs (M=Co, Mn, Ni), comb-type copolymers exhibit higher  $r_2$  relaxivity values compared to the linear one. The importance of pH on the relaxivity properties has been evaluated using MSPs formed by the linear copolymer. However, collective magnetic properties are based on the magnetization of the

primary building nanoparticles, since a linear correlation with  $r_2$  relaxivity was found in all cases (Co>Mn>Ni). CoFe<sub>2</sub>O<sub>4</sub>@P(ANa-co-DAAm) with the highest NMR  $r_2$  value (316.0 mm<sup>-1</sup>s<sup>-1</sup>), exhibited signal decreased as MRI T<sub>2</sub>-contrast agent with the  $r_2/r_1$  ratio (18.2 at 3 T) in a similar range to that of a commercially available T<sub>2</sub>-contrast agent. The assembled of small particles in a large one with good response to the magnetic field, gives further options for specific targeting in bioapplications since accumulation and disassemble in the body differentiated.

### Acknowledgements

This research was co-financed by the European Union (European Social Fund-ESF) and Greek national funds through the Operational Program “Education and Lifelong Learning” of the National Strategic Reference Framework (NSRF)-Research Funding Program: THALES. Investing in knowledge society through the European Social Fund. The authors thank the Royal Marsden NHS Foundation Trust for the 1.5 T MRI measurements as well as Dr Maria Kollia and Mr Vasilis Kotsopoulos from the Lab of Electron Microscopy and Microanalysis at the University of Patras for the TEM images.

### References

- 1 Q. L. Vuong, J.-F. Berret, J. Fresnais, Y. Gossuin and O. Sandre, *Adv. Healthcare Mater.*, 2012, **1**, 502-512.
- 2 T. Wang, X. Wang, D. LaMontagne, Z. Wang, Z. Wang and Y. C. Cao, *J. Am. Chem. Soc.*, 2012, **134**, 18225-18228.

- 3 A. Kostopoulou, S. K. P. Velu, K. Thangavel, F. Orsini, K. Brintakis, S. Psycharakis, A. Ranella, L. Bordonali, A. Lappas and A. Lascialfari, *Dalton Trans.*, 2014, **43**, 8395-8404.
- 4 Y. Hu, L. Meng, L. Niu and Q. Lu, *Langmuir*, 2013, **29**, 9156-9163.
- 5 A. Roch, Y. Gossuin, R. N. Muller and P. Gillis, *J. Magn. Magn. Mat.*, 2005, **293**, 532-539.
- 6 J. Guo, W. Yang and C. Wang, *Adv. Mater.*, 2013, **25**, 5196-5214.
- 7 T. Sun, Y. S. Zhang, B. Pang, D. C. Hyun, M. Yang and Y. Xia, *Angew. Chem. Int. Ed.*, 2014, **53**, 12320-12364.
- 8 B.-Su. Kim, J.-M. Qiu, J.-P. Wang and T. A. Taton, *Nano Lett.*, 2005, **5**, 1987-1991.
- 9 S. Lecommandoux, O. Sandre, F. Checot and R. Perzynski, *Prog. Solid State Chem.*, 2006, **34**, 171-179.
- 10 A. Bakandritsos, G. Mattheolabakis, R. Zboril, N. Bouropoulos, J. Tucek, D. G. Fatouros and K. Avgoustakis, *Nanoscale*, 2010, **2**, 564-572.
- 11 A. M. Budgin, Y. A. Kabachii, Z. B. Shifrina, P. M. Valetsky, S. S. Kochev, B. D. Stein, A. Malyutin and L. M. Bronstein, *Langmuir*, 2012, **28**, 4142-4151.
- 12 S. Mahajan, V. Koul, V. Choudhary, G. Shishodia and A. C. Bharti, *Nanotechnology*, 2013, **24**, 015603.
- 13 E. V. Shtykova, X. Huang, X. Gao, J. C. Dyke, A. L. Schmucker, B. Dragnea, N. Remmes, D. V. Baxter, B. Stein, P. V. Konarev, D. I. Svergun and L. M. Bronstein, *J. Phys. Chem. C*, 2008, **112**, 16809-16817.
- 14 E. V. Shtykova, A. Malyutin, J. Dyke, B. Stein, P. V. Konarev, B. Dragnea, D. I. Svergun and L. M. Bronstein, *J. Phys. Chem. C*, 2010, **114**, 21908-21913.

- 15 Y. Ning, H. Zhang, J. Han, C. Yang, Y. Liu, D. Zhou and B. Yang, *J. Mater. Chem.*, 2011, **21**, 6837-6843.
- 16 X. Li, H. Li, G. Liu, Z. Deng, S. Wu, P. Li, Z. Xu, H. Xu and P. K. Chu, *Biomaterials*, 2012, **33**, 3013-3024.
- 17 E. Peng, E. S. G. Choo, Y. Sheng and J. M. Xue, *New J. Chem.*, 2013, **37**, 2051-2060.
- 18 Z. Iatridi, V. Georgiadou, M. Menelaou, C. Dendrinou-Samara and G. Bokias, *Dalton Trans.*, 2014, **43**, 8633-8643.
- 19 M. I. Majeed, Q. Lu, W. Yan, Z. Li, I. Hussain, M. N. Tahir, W. Tremel and B. Tan, *J. Mater. Chem. B*, 2013, **1**, 2874-2884.
- 20 S. Graham, P. A. G. Cormack and D. C. Sherrington, *Macromolecules*, 2005, **38**, 86-90.
- 21 X. Huang, B. Li, H. Zhang, I. Hussain, L. Liang and B. Tan, *Nanoscale*, 2011, **3**, 1600-1607.
- 22 L. Zhu, D. Xue and Z. Wang, *Langmuir*, 2008, **24**, 11385-11389.
- 23 L. T. Lu, L. D. Tung, I. Robinson, D. Ung, B. Tan, J. Long, A. I. Cooper, D. G. Fernig and N. T. K. Thanh, *J. Mater. Chem.*, 2008, **18**, 2453-2458.
- 24 M. Menelaou, K. Georgoula, K. Simeonidis and C. Dendrinou-Samara, *Dalton Trans.*, 2014, **43**, 3626-3636.
- 25 K. Vamvakidis, M. Katsikini, D. Sakellari, E. C. Paloura, O. Kalogirou and C. Dendrinou-Samara, *Dalton Trans.*, 2014, **43**, 12754-12765.
- 26 E. Pösel, H. Kloust, U. Tromsdorf, M. Janschel, C. Hahn, C. Maßlo and H. Weller, *ACS Nano*, 2012, **6**, 1619-1624.
- 27 R. De Palma, S. Peeters, M. J. Van Bael, H. Van den Rul, K. Bonroy, W. Laureyn, J. Mullens, G. Borghs and G. Maes, *Chem. Mater.*, 2007, **19**, 1821-1831.

- 28 G. Bokias, A. Durand and D. Hourdet, *Macromol. Chem. Phys.*, 1998, **199**, 1387-1392.
- 29 B. H. Tan, P. Ravi and K. C. Tam, *Macrom. Rapid Commun.*, 2006, **27**, 522-528.
- 30 Z. Wang, B. H. Tan, H. Hussain and C. He, *Col. Polym. Sci.*, 2013, **291**, 1803-1815.
- 31 Q. L. Vuong, P. Gillis and Y. Gossuin, *J. Magn. Reson.*, 2011, **212**, 139-148.
- 32 H. Yang, H. Zhou, C. Zhang, X. Li, H. Hu, H. Wu and S. Yang, *Dalton Trans.*, 2011, **40**, 3616-3621.
- 33 M. Rohrer, H. Bauer, J. Mintorovitch, M. Requardt and H.-J. Weinmann, *Invest. Rad.*, 2005, **40**, 715-724.

## Table of contents

### Magnetic colloidal superparticles of Co, Mn and Ni ferrite featured with comb-type and/or linear amphiphilic polyelectrolytes; NMR and MRI relaxometry

Melita Menelaou,<sup>1</sup> Zacharoula Iatridi,<sup>2</sup> Ioannis Tsougos,<sup>3</sup> Katerina Vasiou,<sup>4</sup> Catherine Dendrinou-Samara<sup>1\*</sup> and Georgios Bokias<sup>2\*</sup>

Hydrophobically modified magnetic superparticles (MSPs) of  $MFe_2O_4$  NPs were synthesized in the presence of amphiphilic polymers with different architecture and evaluated through NMR and MRI Relaxivity measurements.

