

Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

COMMUNICATION

Controllable explosion: Fine-tuning the sensitivity of high-energy complexes

Kun Wang^{a,b}, Dihao Zeng^b, Jian-Guo Zhang^{*a}, Yan Cui^c, Tong-Lai Zhang^a, Zhi-Min Li^d, Xin Jin^b

Received (in XXX, XXX) Xth XXXXXXXXX 2015, Accepted Xth XXXXXXXXX 2015

DOI: 10.1039/b000000x

Tuning the sensitivity of energetic materials has always been a research topic of interest. A lot of attention has been paid on changing the ligands previously in traditional high energy density materials (HEDMs). Recently, we have stepped further along this path by thinking from another angle—changing the metal centre. Herein, we report 4 transition metal complexes with the ligands 1,5-diaminotetrazole, which have similar structures but drastically different sensitivities. These differences are apparently due to different metal centres.

High energy density materials (HEDM) based on nitrogen-rich complexes¹ have been used as energy-storage materials, propellants and explosives². Current interest mainly lies in the development of HEDMs with increased energetic performance and decreased sensitivity^{1f,3,4}. Most previous research focused on tuning the ligands or anions to improve the sensitivity on the basis of these backbones, such as protonated ligands by strong acid (nitric acid or perchloric acid)^{5,6}, methylated in acetonitrile⁶ or other azo groups^{1c,7}. However, little attention has been paid to the relationship between the metal centre and the impact sensitivity. Recently, we have found that the sensitivity can be controlled by changing the metal centres of the metal 1,5-diaminotetrazole (DAT) perchlorate complexes.

1,5-diaminotetrazole (DAT)^{4e, 5a, 8} and its derivatives have been described as a typical representation of highly energetic compounds. In the development of the lead-free primary explosives^{4e, 9}, adding the DAT ligand introduces a new way of designing energetic materials. We have reported two crystalline perchlorate salts of Co and Cd DAT complexes before¹⁰, which are quite sensitive towards impact and friction stimuli¹¹. The lack of crystal water in the structures makes them promising primary explosives. However, due to the environmental unfriendliness of the heavy metal elements, we moved to investigate the first-row transition metals, by synthesizing [Mn(DAT)₆](ClO₄)₂ and [Zn(DAT)₆](ClO₄)₂, which have lower toxicity than [Cd(DAT)₆](ClO₄)₂ but have higher sensitivity. It is noticeable that the four complexes have similar octahedron structures but exhibit very different sensitivities. Here we present the newly synthesized complexes, [Mn(DAT)₆](ClO₄)₂(1), [Co(DAT)₆](ClO₄)₂(2), [Zn(DAT)₆](ClO₄)₂(3) and [Cd(DAT)₆](ClO₄)₂(4). The synthesis method and the structures of these complexes are summarized in Figure 1.

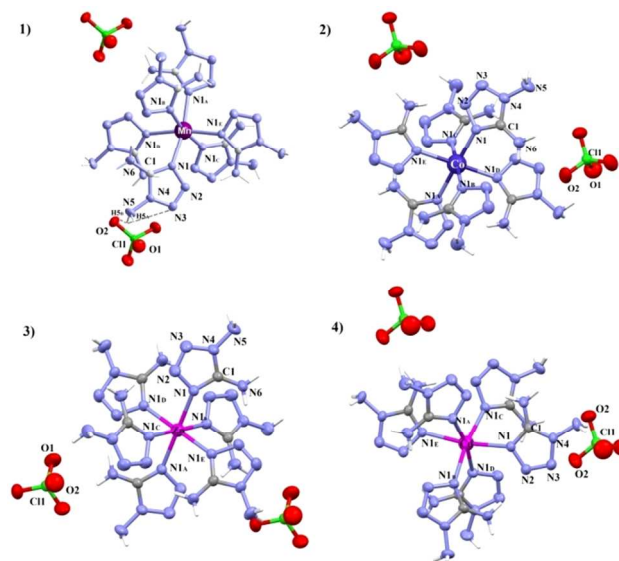


Figure 1. Structures of metal 1,5-diaminotetrazole perchlorate complexes ([M(DAT)₆](ClO₄)₂). 1) Crystal structure of [Mn(DAT)₆](ClO₄)₂ where hydrogen atoms are shown in capped sticks style. Selected bond lengths [Å]: Mn-N1 2.290(10), N1-C1 1.336(15), N1-N2 1.379(14), N2-N3 1.284(15), N3-N4 1.365(14), N4-C1 1.343(15), N4-N5 1.389(14), N6-C1 1.332(16). 2) Crystal structure of [Co(DAT)₆](ClO₄)₂. Selected bond lengths [Å]: Co-N1 2.205(14), N1-C1 1.335(2), N1-N2 1.376(2), N2-N3 1.278(2), N3-N4 1.359(3), N4-C1 1.343(2), N4-N5 1.393(2), N6-C1 1.323(3). 3) Crystal structure of [Zn(DAT)₆](ClO₄)₂. Selected bond lengths [Å]: Zn-N1 2.218(11), N1-C1 1.332(2), N1-N2 1.373(2), N2-N3 1.274(2), N3-N4 1.355(3), N4-C1 1.339(2), N4-N5 1.386(2), N6-C1 1.317(3). 4) Crystal structure of [Cd(DAT)₆](ClO₄)₂. Selected bond lengths [Å]: Cd-N1 2.371(1), N1-C1 1.326(2), N1-N2 1.373(2), N2-N3 1.280(2), N3-N4 1.361(2), N4-C1 1.334(2), N4-N5 1.390(2), N6-C1 1.333(2).

The single-crystal X-ray diffraction study was performed for the crystals obtained through hydrothermal method. All the four crystals belong to the trigonal syngony. **1** and **4** crystallize in the space group $P\bar{3}c1$ while **2** and **3** crystallize in $P\bar{3}$. All the metal centres are hexa-coordinated through a strong electrostatic interaction with the nitrogen atom of of DAT. Hexa-coordinated energetic complexes are unusual and are only found in the structures of traditional CP/BNCP (2-(5-Cyanotetrazolato) pentaammine cobalt/tetraammine-*cis*-bis(5-nitro-2*H*-tetrazolato-*N*) cobalt) primary explosives.¹²

All the four complexes are shown in Figure 1. [Mn(DAT)₆]²⁺ has a distorted octahedron geometry. All the six Mn-N bond lengths are the same (2.290(10) Å). The dihedral angle between different tetrazole planes is close to 31.7°, resulting from the

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

COMMUNICATION

steric effect from the bulky DAT groups.

The cases are similar for the other three structures of $[\text{Co}(\text{DAT})_6]^{2+}$, $[\text{Zn}(\text{DAT})_6]^{2+}$ and $[\text{Cd}(\text{DAT})_6]^{2+}$, which are distorted octahedrons as well (SI-Table S2). It should be noticed that hydrogen bonds play a quite important role in stabilizing the structures: the intermolecular hydrogen bonds form between amino groups and apical nitrogen atoms of DAT, while the intramolecular ones form between $-\text{NH}_2$ and ClO_4^- , which is similar to the structure of $[\text{Mn}(\text{DAT})_6](\text{ClO}_4)_2$. The DAT ligands interact with each other through different types of hydrogen bonds (see the packing diagrams in Figure S1), which leads to 2-D layered structures. (SI-Figure S2).

The decomposition of the four $[\text{M}(\text{DAT})_6](\text{ClO}_4)_2$ samples was investigated using DSC and TG-DTG techniques (Figure 2 and SI-Figure S4).

The decomposition of **1** is a three-step process. The first and most rapid of decomposition occurs from 200.4 to 279.9 °C where the peak is at 242.8 °C. TG-DTG measurements show that about 65.6 wt% DAT decomposes in this period which is close to its theoretical capacity of 70.3 wt%. (The IR spectrum of **1**'s residue at 279.9 °C: $\nu_{\text{N-H}}$: 3324, 3256 cm^{-1} ; $\nu_{\text{C=N}}$: 1322 cm^{-1} ; $\delta_{\text{N-H}}$: 1600 cm^{-1} suggesting the cleavage of tetrazole ring.) New bands at 1620, 1514, 1423, 1097 and 628 cm^{-1} indicate the existence of $[-\text{CO-NH-}]$ polymer and $\text{Mn}(\text{ClO}_4)_2$. At the same time, $\text{Mn}(\text{ClO}_4)_2$ ($\nu_{\text{Cl-O}}$: 1097 cm^{-1}) and MnCO_3 ($\nu_{\text{C=O\&C-O}}$: 1620, 1250 cm^{-1}) are detected. The continuous decomposition stage from 279.9 to 388.8 °C is possibly related to the formation (2117 cm^{-1}) of $\text{Mn}(\text{NCO})_2$ and the decomposition of $\text{Mn}(\text{ClO}_4)_2$ with the mass loss of 21.4 wt%. Upon further heating to 600 °C, some black residue can be observed with some gas products. The black residue is identified as a mixture of MnO and MnO_2 based on IR data (SI-Figure S3, IR bands between 500 and 750 cm^{-1}).

There are three steps in the whole decomposition of **2** as well. The first stage is exothermic, from 213.8 to 250.9 °C, with the peak at 229.9 °C. The weight loss is 58.8 wt% corresponds to the ring opening activity. The next two stages are exothermic at a temperature range from 250.9 to 347.2 °C and 502 to 600 °C where the corresponding mass loss is 26.8 wt% and 8.57 wt%, respectively. The final products (9.31 wt%) is Co_3O_4 based on IR spectra of the residue.

For **3**, a melting process starts at 170.5 °C. **3** starts to decompose at 185.6 °C and stops at 305.9 °C with the peak at 235.6 °C (56.0 wt% mass loss in total). This corresponds to a process of DAT ring opening and the formation of $\text{Zn}(\text{ClO}_4)_2$. The next two steps are both exothermic at the temperature range of 305.9-442.3 °C and 442.3-600 °C with the weight loss of 6.4 wt% and 10.8 wt%, respectively. The final residue (9.6 wt%) is ZnO .


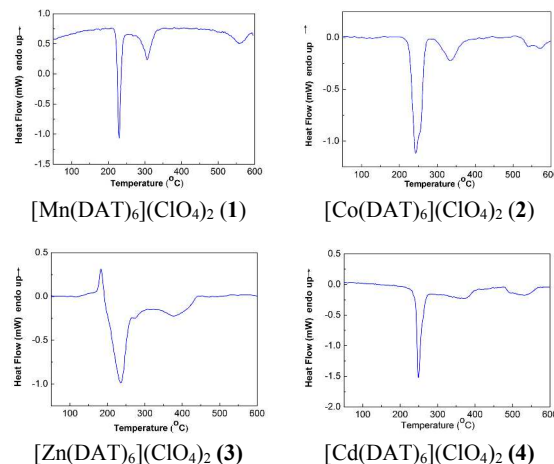


Figure 2. DSC traces of $[\text{M}(\text{DAT})_6](\text{ClO}_4)_2$ (measured at 5°C/min to 600°C in nitrogen gas flowing with the rate of 20mL/min).

The decomposition of **4** is similar to the other three. The three stages occur at the temperature ranges of 230.0-281.8 °C (weight loss: 71.7 wt%), 301.7-476.9 °C (weight loss: 20.21 wt%) and 476.9-600 °C (weight loss: 20.21 wt%), respectively. The overall peak is at 249.3 °C. The final residue is CdO . Therefore, the decomposition processes of the four complexes should be described as follows (The IR spectrum of the corresponding products have been listed in the SI-Figure S3):

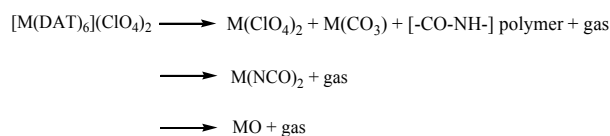

We further applied Kissinger's and Ozawa-Doyle's method¹³ (shown in equation (1) and (2)) to explore the activation energy of the first stage of the decomposition. In the equations, T_p means the peak temperature, R equals to 8.314 J/(mol·K), β is the linear heating rate set as 2, 5, 10 and 20 K/min. C represents a constant. A (s^{-1}) and E (kJ/mol) refer to pre-exponential factor and activation energy, respectively. The results have been listed in SI-Table S2. By averaging the results of K-method and O-method, the values of activation energy of the four complexes are 32.6, 37.2, 29.5 and 47.8 kcal/mol.

$$\ln \frac{\beta}{T_p^2} = \frac{RA}{E} - \left(\frac{E}{R} \right) \left(\frac{1}{T_p} \right) \quad (1) \quad \ln \beta + \frac{0.4567 E}{RT_p} = C \quad (2)$$

The sensitivity is analyzed by the sensitivity test (Table 1). Impact and friction sensitivity measurements were performed according to the standard BAM method.^{14a} The measurement of flame sensitivity^{14b} has been described in the supplementary information. Wherein **2** is sensitive to all the impact, friction and flame, **4** is sensitive to both the impact and friction while **3** is the most insensitive among the four complexes. The impact sensitivity suggests **2** and **4** are very sensitive (< 3J), while **1** is

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

COMMUNICATION

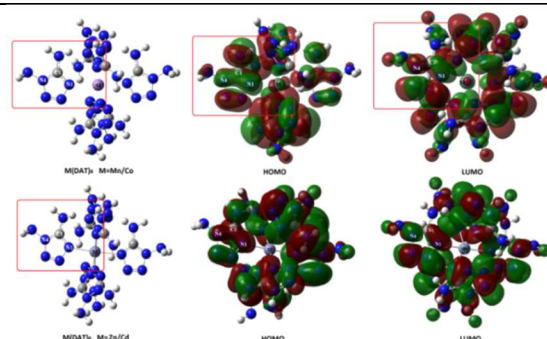
sensitive (<4 J, >3 J)^{5a}. For **3**, it is highly stable because it is insensitive to the stimulation of all three factors. The friction sensitivities show the same trend as the impact sensitivities, while **2** is extremely sensitive to friction and should be handled carefully.

Table 1. The sensitivity of the four complexes

Complexes	Impact(J)	Friction (N) ^a	Flame (cm)
1	3.6	252	18.63
2	0.6	9 (+)	21.75
3	-	> 360	-
4	1.2	20 (+)	33.93

^a: According to the *UN Recommendations on the Transport of Dangerous Goods, Manual of Tests and Criteria*^{14a}, (+) indicates not safe for transport

Further insights into the electronic structures and HOFs (Heat of Formation) come from the studies with DFT. All structures were computed using the Gaussian 09^{15a} with the method of unrestricted B3LYP^{15b,c}. For the non-metal elements we used the Gaussian basis set¹⁶ of 6-31+G*. For the metal elements, pseudo potential basis sets of LanL2DZ with f polarization corrections¹⁷ have been used (2.195 for Mn, 2.780 for Co, 3.031 for Zn and 1.495 for Cd). The optimized structures are shown in SI-Figure S4. High spin and low spin states have been compared for the metal centres in **1** and **2** to confirm the electronic configurations. For Mn²⁺, the electronic configuration is (t_{2g})³(e_g)² which is 39.4 kcal/mol lower than the low-spin state of (t_{2g})⁵. While for Co²⁺ it is (t_{2g})⁵(e_g)² which is 16.1 kcal/mol lower than that of (t_{2g})⁶(e_g)¹. Therefore, these two metal centres are both at high-spin states here. NBO analysis of the interactions between the DAT units and the transition metal centre at the ground states confirms that the dominant interactions are donation of electron density (i) from N1-C1 π orbital localized on N1 to the σ^* orbital of Mn-N1/Co-N1 or *non-bonding* (*n*) orbital of Zn/Cd localized on the metal and (ii) from metal σ/n orbital to N1-C1 π^* orbital localized on N1. (Figure 3). The second order stabilization energy (*E2*) shows that the strength of the interactions of (i) and (ii) increases in the order of **2**<**4**<**1**<**3**, which results in the different stabilities of the compounds (SI-Table S3). This order of stability is consistent with the observed impact and friction sensitivities of the complexes together with our previous study of many energetic complexes¹⁸ (SI-Table S4), we see that the sensitivities vary with different transition metal centres. Simply put, we believe that the metal with the electronic configuration of 3d⁶-3d⁹ makes the complex more sensitive. To further confirm this conclusion, we also explored the *E2* of [Fe(DAT)₆](ClO₄)₂ and [Ni(DAT)₆](ClO₄)₂. The order of *E2* is [Fe(DAT)₆](ClO₄)₂<**2**<[Ni(DAT)₆](ClO₄)₂<**4**<**1**<**3**.

**Figure 3.** NLMOs of [M(DAT)₆]²⁺ are boxed at the best view.**Table 2.** Physical properties of the four complexes

Complexes	$\Delta_f H^\ominus$ [a]	$\Delta_r H^\ominus$ [b]	Band gap [c]	Density [d]	E_k [e]	Impact sensitivity	Ti(°C) [f]
1	915.33	0.202	43.4	1.786	32.6	3.6	200.4
2	931.46	0.196	28.3	1.777	37.2	0.6	213.8
3	946.46	0.203	86.0	1.801	29.5	-	185.6
4	958.13	0.172	84.8	1.855	47.8	1.2	230.0

⁴⁵ [a] Heat of formation (kcal/mol, Gaussian09 results); [b] Reactive enthalpy (kcal/mol, Gaussian09 results); [c] Band gap (kcal/mol, CASTEP results) [d] experimental densities (g/cm³); [e] The activation energy of the first exothermic stage by Kissinger's method (kcal/mol) [f] Thermal decomposition temperature under nitrogen gas (DSC, 5 °C/min)

⁵⁰ Ochterski's methods¹⁹ were used to calculate the HOFs ($\Delta_f H^\ominus$). The reaction enthalpies ($\Delta_r H^\ominus$) of **1-4** are listed in Table 2.

The 0 K HOF of metals are used as follows: 67.02 kcal/mol for Mn²⁰, 101.60 kcal/mol for Co²¹, 31.04 kcal/mol for Zn²⁰ and 28.20 kcal/mol for Cd²¹. All the complexes have positive HOFs. Furthermore, the positive theoretical enthalpy of reaction implies that all the reactions are endothermic. The crystal structures and electronic structures of **1-4** were investigated using the MS CASTEP²² package with the GGA-PBE functional. The optimized crystal structures are very similar to the previously reported crystallographic data for **1-4**. (SI-Figure S5). The band gaps of **1** to **4** are 43.4, 28.3, 86.0 and 84.8 kcal/mol, respectively. The DOS and *pDOS* are shown in SI-Figure S6. For **1** and **2**, the top of the valence band consists of Mn/Co 3d states, while for **3** and **4**, it consists of N/O 2p states. Combined with our results (Table 2 and SI-Table S5)¹⁸, it is reasonable to conclude that the impact sensitivities are inversely proportional to the band gaps of the complexes [M(DAT)₆](ClO₄)₂, (M= Mn, Fe, Co, Ni, Cu, Zn). The density of most of the new perchlorate DAT complexes ranges between 1.77 and 1.85 g/cm³. The decomposition temperatures lie in the range of 185-242 °C.

Conclusions

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

COMMUNICATION

We have reported four transition metal 1,5-diaminotetrazole complexes with similar structures but different explosive properties. DFT calculations confirm that the first row transition metal elements with electronic configuration of $3d^6-3d^9$ make the explosive more sensitive than those with the electronic configuration of $3d^5$ or $3d^{10}$. Last but not least, across the period, the impact sensitivities of this series of transition metal DAT complexes are inversely proportional to their band gaps.

Notes and references

- ¹⁰ ^aState Key Laboratory of Explosion Science and Technology, Beijing Institute of Technology, Beijing 100081 P. R. China. Tel & Fax: +86 10 68918091, E-mail: zjgbt@bit.edu.cn
- ^bPhysical and Theoretical Chemistry Laboratory, University of Oxford, Oxford OX1 3QR, United Kingdom, E-mail: dihao.zeng@chem.ox.ac.uk
- ¹⁵ ^cThe 6th Department of Research Institute of Chemical Defense, Beijing 102205, China
- ^dBeijing Key Laboratory of Ionic Liquids Clean Process, State Key Laboratory of Multiphase Complex Systems, Institute of Process Engineering, Chinese Academy of Sciences, 1 North 2nd Street, Zhongguancun, Haidian District, Beijing 100190, China
- † Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI:10.1039/b000000x/
- ‡ Financial support by NSFC 10776002 and SKLST (BIT) YBKT-16-04 & ZDKT-12-03 is acknowledged.
- 1 a) J. Zhang, J. Shreeve, *J. Am. Chem. Soc.* 2014, **136**, 4437; b) Q. Wu, W. Zhu, H. Xiao, *J. Mater. Chem. A* 2014, **2**, 13006; c) T. M. Klapötke, F. A. Martin, J. Stierstorfer, *Chem. Eur. J.* 2012, **18**, 1487; d) Q. Zhang, J. M. Shreeve, *Angew. Chem. Int. Ed.* 2013, **52**, 8792; e) D. Fischer, T. M. Klapötke, D. G. Piercey, J. Stierstorfer, *Chem. Eur. J.* 2013, **19**, 4602; f) M. H. V. Huynh, M. A. Hiskey, D. E. Chavez, D. L. Naud, R. D. Gilardi, *J. Am. Chem. Soc.* 2005, **127**, 12537; g) R. Wang, H. Xu, Y. Guo, R. Sa, J. M. Shreeve, *J. Am. Chem. Soc.* 2010, **132**, 11904; h) J. P. Agrawal, *Progress in Energy and Combustion Science* 1998, **24**, 1.
- 2 H. Gao, J. Shreeve, *Chem. Rev.* 2011, **111**, 7377.
- 3 a) H. Brand, P. Mayer, A. Schulz, J. J. Weigand, *Angew. Chem. Int. Ed.* 2005, **44**, 3929; b) Y. H. Joo, J. M. Shreeve, *Angew. Chem. Int. Ed.* 2009, **48**, 564.
- 4 a) C. Qi, S. H. Li, Y. C. Li, Y. Wang, X. K. Chen, S. P. Pang, *J. Mater. Chem.* 2011, **21**, 3221; b) C. Ye, H. Gao, J. A. Boatz, G. W. Drake, B. Twamley, J. M. Shreeve, *Angew. Chem. Int. Ed.* 2006, **45**, 7262; c) M. H. V. Huynh, M. A. Hiskey, E. L. Hartline, D. P. Montoya, R. Gilardi, *Angew. Chem. Int. Ed.* 2004, **43**, 4924; d) M. H. V. Huynh, M. A. Hiskey, J. G. Archuleta, E. L. Roemer, R. Gilardi, *Angew. Chem. Int. Ed.* 2004, **43**, 5658; e) Y. H. Joo, B. Twamley, S. Garg, J. M. Shreeve, *Angew. Chem. Int. Ed.* 2008, **47**, 6236; f) T. M. Klapötke, D. G. Piercey, *Inorg. Chem.* 2011, **50**, 2732.
- 5 a) J. C. Gálvez-Ruiz, G. Holl, K. Karaghiosoff, T. M. Klapötke, K. Löhnwitz, P. Mayer, H. Nöth, K. Polborn, C. J. Rohbogner, M. Suter, J. J. Weigand, *Inorg. Chem.* 2005, **44**, 4237; b) T. M. Klapötke, C. M. Sabaté, J. M. Welch, *Z. Anorg. Allg. Chem.* 2008, **634**, 857; c) R. P. Singh, R. D. Verma, D. T. Meshri, J. M. Shreeve, *Angew. Chem. Int. Ed.* 2006, **45**, 3584; d) E. Sebastiao, C. Cook, A. Hu, M. Murugesu, *J. Mater. Chem. A* 2014, **2**, 8153.
- 6 T. M. Klapötke, J. Stierstorfer, *Euro. J. Inorg. Chem.* 2008, **26**, 4055.
- 7 a) M. B. Frankel, D. O. Woolery, *J. Org. Chem.* 2002, **48**, 611; b) T. M. Klapötke, D. G. Piercey, J. Stierstorfer, *Dalton Trans.* 2012, **41**, 9451.
- 8 a) R. Stollé, R. Bergdoll, M. Luther, A. Auerhahn, W. Wacker, *Journal für Praktische Chemie* 1930, **128**, 1; b) R. Raap, *Can. J. Chem.* 1969, **47**, 3677.
- 9 a) Y. Tang, H. Yang, X. Ju, H. Huang, C. Lua, G. Cheng, *J. Mater. Chem. A* 2014, **2**, 4127; b) V. P. Sinditskii, V. Y. Egorshv, T. Y. Dutova, M. D. Dutov, T.-L. Zhang, J.-G. Zhang, *Combustion, Explosion, and Shock Waves* 2011, **47**, 36; c) Y.-H. Joo, J. M.

Shreeve, *Angew. Chem. Int. Ed.* 2010, **49**, 7320; d) M. H. V. Huynh, *US Patent: 7592462 B2*, US, 2009.

- 10 a) Y. Cui, J. Zhang, T. Zhang, L. Yang, J. Zhang, X. Hu, *J. Hazard. Mater.* 2008, **160**, 45; b) S. Y. Qi, Z. M. Li, Z. N. Zhou, Y. Cui, G. T. Guo, T. Zhang, J. Zhang, L. Yang, *Chin. J. Chem.* 2011, **29**, 59. c) S. Y. Qi, J. Zhang, T. Zhang, Y. Cui, L. Yang, K. Yu, Y. Shu, *Chem. J. Chinese U.* 2009, **10**, 1935. d) J. Shang, J. Zhang, Y. Cui, T. Zhang, Y. Shu, L. Yang, *Acta. Chim. Sinica.* 2010, **68**, 233.
- 11 T. S. Kon'kova, Y. N. Matyushin, E. A. Miroshnichenko, A. B. Vorob'ev, *Russ. J. Phys. Chem. B* 2009, **3**, 987.
- 12 a) M. B. Talawar, A. P. Agrawal, S. N. Asthana, *J. Hazard. Mater.* 2005, **120**, 25; b) M. B. Talawar, A. P. Agrawal, M. Anniyappan, D. S. Wani, M. K. Bansode, G. M. Gore, *J. Hazard. Mater.* 2006, **137**, 1074.
- 13 a) A. E. Kissinger, *Anal. Chem.* 1957, **29**, 1702; b) T. Ozawa, *Bull. Chem. Soc. Jpn.* 1965, **38**, 1881. c) C. D. J. Doyle, *J. Appl. Polym. Sci.* 1961, **5**, 285.
- 14 a) Test methods according to the *UN Recommendations on the Transport of Dangerous Goods, Manual of Tests and Criteria*, United Nations Publication, New York, 4th edn, 2003. b) Z. T. Liu, Y. L. Lao, *Initiating Explosive Experimental*, Beijing Institute of Technology, China, 1995.
- 15 a) M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, B. Mennucci, G. A. Petersson, H. Nakatsuji, M. Caricato, X. Li, H. P. Hratchian, A. F. Izmaylov, J. Bloino, G. Zheng, J. L. Sonnenberg, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, J. A. Montgomery, Jr., J. E. Peralta, F. Ogliaro, M. Bearpark, J. J. Heyd, E. Brothers, K. N. Kudin, V. N. Staroverov, R. Kobayashi, J. Normand, K. Raghavachari, A. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, N. Rega, J. M. Millam, M. Klene, J. E. Knox, J. B. Cross, V. Bakken, C. Adamo, J. Jaramillo, R. Gomperts, R. E. Stratmann, O. Yazyev, A. J. Austin, R. Cammi, C. Pomelli, J. W. Ochterski, R. L. Martin, K. Morokuma, V. G. Zakrzewski, G. A. Voth, P. Salvador, J. J. Dannenberg, S. Dapprich, A. D. Daniels, Ö. Farkas, J. B. Foresman, J. V. Ortiz, J. Cioslowski, D. J. Fox, *Gaussian, Inc.*, Wallingford CT, 2009. b) A. D. Becke, *J. Chem. Phys.* 1993, **98**, 5648-5652; c) C. Lee, W. Yang, R. G. Parr, *Phys. Rev. B* 1988, **37**, 785.
- 16 S. F. Boys, *Proceedings of the Royal Society A* 1950, **200**, 542.
- 17 a) A. Hollwarth, M. Bohme, S. Dapprich, A. W. Ehlers, A. Gobbi, V. Jonas, K. F. Kohler, R. Stegmann, A. Veldkamp, G. Frenking, *Chem. Phys. Lett.* 1993, **208**, 237; b) A. W. Ehlers, M. Bihme, S. Dapprich, A. Gobbi, A. Hollwarth, V. Jonas, K. F. Kohler, R. Stegmann, A. Veldkamp, G. Frenking, *Chem. Phys. Lett.* 1992, **208**, 111.
- 18 a) B. D. Wu, *Studies on Synthesis, Characterization and Properties of the Novel Azide and Diazo Energetic Compounds*, Beijing Institute of Technology, 2014. b) H. S. Huang, T. L. Zhang, J. G. Zhang, L. Q. Wang, *J. Hazard Mater.* 2010, **179**, 21. c) H. S. Huang, T. L. Zhang, J. G. Zhang, L. Q. Wang, *Chem Phys Lett*, 2010, **487**, 200.
- 19 J. W. Ochterski, http://www.gaussian.com/g_whitepap/thermo/thermo.pdf, 2000. **6.2**.
- 20 M. W. Chase, C. A. Davies, J. R. Downey, D. J. Frurip, R. A. McDonald, A. N. Syverud, *J. Phys. Ref. Data* 1985, **14**, suppl. 1.
- 21 a) J. D. Cox, D. D. Wagman, V. A. Medvedve, Co DATA key values for thermodynamics. Hemisphere Publishing Corp., New York, 1989; b) B. C. Shepler, K. A. Peterson, *J. Phys. Chem. A* 2006, **110**, 12321.
- 22 M. Segall, P. J. Lindan, M. J. Probert, C. J. Pickard, P. J. Hasnip, S. J. Clark, M. C. Payne, *J. Phys.: Condensed. Matt.* 2002, **14**, 2717.
- 25

Graphical Abstract

The sensitivities are controllable just by tuning the centre metal centres in the energetic complexes of $[M(\text{DAT})_6](\text{ClO}_4)_2$.

