

Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

A new family of high nuclearity Co^{II}/Dy^{III} coordination clusters possessing robust and unseen topologies

Benjamin Berkoff,^a Kieran Griffiths,^a Alaa Abdul-Sada,^a Graham J. Tizzard,^b Simon J. Coles,^b Albert Escuer,^{*c} and George E. Kostakis ^{*a}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

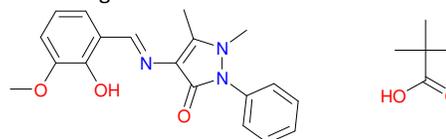
Mixing Co(NO₃)₂·6H₂O / Dy(NO₃)₃·6H₂O / (E)-4-(2-hydroxy-3-methoxybenzylideneamino)-2,3-dimethyl-1-phenyl-1,2-dihydropyrazol-5-one (HL) / pivalic acid / Et₃N in various solvents results in the synthesis of seven compounds formulated as [Co^{II}Dy^{III}]₂(μ₃-MeO)₂(L)₂(piv)₄(NO₃)₂ (**3**), [Co^{II}Dy^{III}]₃(μ₃-MeO)₂(μ₂-MeO)₂(L)₂(piv)₂(NO₃)₃·2(CH₃OH) (**4**·2CH₃OH), 2[Co^{II}Dy^{III}]₄(μ₂-O)₂(μ₃-OH)₄(L)₄(piv)₈][Co^{II}Dy^{III}]₅(μ₃-OH)₆(L)₂(piv)₈(NO₃)₄ (**5**), [Co^{II}Dy^{III}]₄(μ₂-O)₂(μ₃-OH)₄(L)₄(piv)₈·2(CH₃CN) (**6**·2CH₃CN), [Co^{II}Dy^{III}]₅(μ₃-OH)₆(L)₂(piv)₈(NO₃)₄·4(CH₃CN) (**7**·4CH₃CN), [Co^{II}Dy^{III}]₂(μ₃-OH)₂(L)₂(piv)₂(NO₃)₂(EtOH)₂(H₂O)₂(NO₃)₂(EtOH) (**8**·EtOH) and [Co^{II}Dy^{III}]₄(μ₂-O)₂(μ₃-OH)₄(L)₄(piv)₈ (**9**) with robust and unseen topologies. These show that the temperature and reaction time influence the formation of the final product. Preliminary magnetic studies, have been performed for **6** and **7** in the temperature range 2 – 300K, are indicative of Single Molecule Magnet (SMM) behaviour. Moreover, the catalytic properties of compound **3** as efficient catalyst for the synthesis of trans-4,5-diaminocyclopent-2-enones from 2-furaldehyde and primary amines have been carried out.

Introduction

In recent years, 3d/4f coordination cluster chemistry has received attention due to the fascinating structures^{1–5} and properties that these materials display.^{6–9} The simple preparative procedure and the wide range of 3d, 4f elements and organic ligands that can be used have led to numerous compounds with unprecedented structures.¹⁰ The high coordination numbers that lanthanides favour make prediction and description of the final product difficult. Recognizing the importance of topology in the development of coordination polymer chemistry,¹¹ and aiming to create order in the fast-expanding group of polynuclear coordination clusters (CCs), we developed a methodology which simplifies the description of the complicated structures of such species.^{12,13} This methodology classifies^{14,15} and compares polynuclear CCs of defined nuclearity and topology¹⁴ and allows a graphical search of structural motifs.¹⁶

We recently employed (E)-4-(2-hydroxy-3-methoxybenzylideneamino)-2,3-dimethyl-1-phenyl-1,2-dihydropyrazol-5-one (HL, Scheme 1) in Co/Ln chemistry, in the absence of co-ligand to give two isoskeletal Co^{II}₃Dy^{III}₄ CCs

formulated as ([Co^{II}₃Dy^{III}₄(μ₃-OH)₆(CF₃SO₃)₃](ClO₄)₅ (**1**) and [Co^{II}₃Dy^{III}₄(μ₃-OH)₆(CF₃SO₃)₃](ClO₄)₃(CF₃SO₃)₂ (**2**) possessing a disk-like or **3,6M7-1** topology, previously unseen in Co/Ln chemistry and exhibiting interesting magnetic properties.¹⁷ The two different coordination pockets, the limited degree of flexibility of the ligand, the unusual Co/Dy topology and the higher nuclearity afforded in comparison with compounds containing similar ligands,¹⁸ lead us to explore the coordination chemistry of HL in more detail and to undertake a systematic investigation.



Scheme 1 (left) The protonated form of (E)-4-(2-hydroxy-3-methoxybenzylideneamino)-2,3-dimethyl-1-phenyl-1,2-dihydropyrazol-5-one (HL) ligand used in this work, (right) Pivalic acid (pivH) used as co-ligand in this study.

Since pivalic acid (pivH) has been shown to be an excellent co-ligand, preventing extensive hydrolysis of the metal centres, for the synthesis of 3d/4f polynuclear CCs,^{19–25} we decided to incorporate it in the reaction system that afforded the two isoskeletal Co^{II}₃Dy^{III}₄ CCs (**1** and **2**), resulting in the synthesis of seven new compounds formulated as [Co^{II}Dy^{III}]₂(μ₃-MeO)₂(L)₂(piv)₄(NO₃)₂ (**3**), [Co^{II}Dy^{III}]₃(μ₃-MeO)₂(μ₂-MeO)₂(L)₂(piv)₂(NO₃)₃·2(CH₃OH) (**4**·2CH₃OH), 2[Co^{II}Dy^{III}]₄(μ₂-O)₂(μ₃-OH)₄(L)₄(piv)₈][Co^{II}Dy^{III}]₅(μ₃-OH)₆(L)₂(piv)₈(NO₃)₄ (**5**), [Co^{II}Dy^{III}]₄(μ₂-O)₂(μ₃-OH)₄(L)₄(piv)₈·2(CH₃CN) (**6**·2CH₃CN), [Co^{II}Dy^{III}]₅(μ₃-OH)₆(L)₂(piv)₈(NO₃)₄·4(CH₃CN) (**7**·4CH₃CN), [Co^{II}Dy^{III}]₂(μ₃-OH)₂(L)₂(piv)₂(NO₃)₂(EtOH)₂(H₂O)₂(NO₃)₂(EtOH) (**8**·EtOH) and [Co^{II}Dy^{III}]₄(μ₂-O)₂(μ₃-OH)₄(L)₄(piv)₈ (**9**) with robust and unseen topologies.

^a Department of Chemistry, School of Life Sciences, University of Sussex, Brighton BN1 9QJ, United Kingdom, G.Kostakis@sussex.ac.uk

^b EPSRC National Crystallography Service, School of Chemistry, University of Southampton, Highfield, Southampton SO17 1BJ, UK.

^c Department de Química Inorgànica, Universitat de Barcelona, Diagonal 645, 08028 Barcelona, Spain, e-mail: albert.escuer@qi.ub.es

† Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: [IR, ESI-MS, ¹H-NMR, Magnetic data, CIF files]. See DOI: 10.1039/x0xx00000x

(8·EtOH) and $[\text{Co}_4^{\text{II}}\text{Dy}^{\text{III}}_4(\mu_2\text{-O})_2(\mu_3\text{-OH})_4(\text{L})_4(\text{piv})_8]$ (**9**) with robust and unprecedented topologies. These show that the temperature and reaction time influence the formation of the final product. Preliminary magnetic studies, have been performed for **6** and **7** in the temperature range 2 – 300K, are indicative of Single Molecule Magnet (SMM) behaviour. Moreover, compound **3** has been tested as efficient catalyst for the synthesis of trans-4,5-diaminocyclopent-2-enones from 2-furaldehyde and primary amines.

Experimental

Materials and methods

Materials. Chemicals (reagent grade) were purchased from Sigma Aldrich and Alfa Aesar. All experiments were performed under aerobic conditions using materials and solvents as received.

Instrumentation. NMR spectra were measured on a Varian VNMRS solution-state spectrometer at 500 MHz at 30°C using residual isotopic solvent (DMSO, $\delta_{\text{H}} = 2.50$ ppm) as internal reference. Chemical shifts are quoted in ppm. Coupling constants (J) are recorded in Hz. IR spectra of the samples were recorded over the range of 4000–650 cm^{-1} on a Perkin Elmer Spectrum One FT-IR spectrometer fitted with an UATR polarization accessory. EI-MS was performed on a VG Autospec Fissions instrument (EI at 70 eV).

Synthetic procedures.

Ligand synthesis. The synthesis of HL has been carried out according to the reported synthetic procedure.¹⁷

Synthesis of $[\text{Co}^{\text{II}}\text{Dy}^{\text{III}}_2(\mu_3\text{-MeO})_2(\text{L})_2(\text{piv})_4(\text{NO}_3)_2]$ (3**).** 0.075 g (0.22 mmol) of L and 0.036 g (0.35 mmol) of pivalic acid were added to 20ml of MeOH and stirred. To this 118 μl (0.84 mmol) of 99% NEt_3 were added and the resultant mixture brought to 40 °C and stirred for 10 minutes. To this 0.068 g (0.23 mmol) of $\text{Co}^{\text{II}}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and 0.104 g (0.23 mmol) of $\text{Dy}^{\text{III}}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ were added and the resultant mixture stirred at 40 °C for a further hour. This was then filtered and left undisturbed for slow evaporation, orange diamond shaped plate-like crystals of **3** formed 7 days later. Yield: 35.5 mg (18.3% based on Co) Selected IR peaks (cm^{-1}): 2960.53 (br), 1608.15 (s), 1467.22 (s), 1312.43 (m), 1215.08 (m), 736.21 (m). Attempts to characterize, via X-Ray crystallography, the residue on the filter were not successful

Synthesis of $[\text{Co}^{\text{II}}\text{Dy}^{\text{III}}_3(\mu_3\text{-MeO})_2(\mu_2\text{-MeO})_2(\text{L})_2(\text{piv})_2(\text{NO}_3)_3] \cdot 2(\text{CH}_3\text{OH})$ (4**).** 0.075 g (0.22 mmol) of L and 0.036 g (0.35 mmol) of pivalic acid were added to 20ml of MeOH and stirred. To this 118 μl (0.84 mmol) of 99% NEt_3 were added and the resultant mixture brought to reflux and stirred for 10 minutes. To this 0.068 g (0.23 mmol) of $\text{Co}^{\text{II}}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and 0.130 g (0.29 mmol) of $\text{Dy}^{\text{III}}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ were added and the resultant mixture refluxed for an hour. This was then filtered and left undisturbed for slow evaporation, orange needle like crystals of **4** formed within 48 hours. Yield: 23 mg (16.9% based on Dy) Selected IR peaks (cm^{-1}): 2955.32 (br), 1595.00 (m), 1551.31 (m), 1459.74 (s), 1420.58 (s), 1300.85 (s), 1211.06 (s), 1014.61 (m), 747.41 (m), 700.82 (m).

Synthesis of $2[\text{Co}_4^{\text{II}}\text{Dy}^{\text{III}}_4(\mu_2\text{-O})_2(\mu_3\text{-OH})_4(\text{L})_4(\text{piv})_8][\text{Co}_2^{\text{II}}\text{Dy}^{\text{III}}_5(\mu_3\text{-OH})_6(\text{L})_2(\text{piv})_8(\text{NO}_3)_4]$ (5**).** 0.075 g (0.22 mmol) of L and 0.036 g (0.35 mmol) of pivalic acid were added to 20ml of MeCN and stirred. To this 118 μl (0.84 mmol) of 99% NEt_3 were added and the resultant mixture brought to 40 °C and stirred for 10 minutes. To this 0.068 g (0.23 mmol) of $\text{Co}^{\text{II}}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and 0.104 g (0.23 mmol) of $\text{Dy}^{\text{III}}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ were added and the resultant mixture stirred at 40 °C for a further hour. This was then filtered and left undisturbed for slow evaporation. Crystals of **5** were formed within 72 hours Yield: 28mg (17% based on Dy).

Synthesis of $[\text{Co}_4^{\text{II}}\text{Dy}^{\text{III}}_4(\mu_2\text{-O})_2(\mu_3\text{-OH})_4(\text{L})_4(\text{piv})_8] \cdot 2(\text{CH}_3\text{CN})$ (6**).** 0.075 g (0.22 mmol) of L and 0.036 g (0.35 mmol) of pivalic acid were added to 20ml of MeCN and stirred. To this 118 μl (0.84 mmol) of 99% NEt_3 were added and the resultant mixture brought to reflux and stirred for 10 minutes. To this 0.068g (0.23 mmol) of $\text{Co}^{\text{II}}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and 0.104 g (0.23 mmol) of $\text{Dy}^{\text{III}}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ were added and the resultant mixture refluxed for a further hour. This was then filtered and left undisturbed for slow evaporation, red hexagonal plate like crystals of **6** formed within 48 hours. Yield: 18.2 mg (10.4% based on Co) Selected IR peaks (cm^{-1}): 2958.46 (br), 1603.96 (s), 1544.31 (s), 1419.35 (s), 1219.56 (s), 1104.31 (m), 967.74 (m), 742.29 (m), 705.04 (m).

Synthesis of $[\text{Co}_2^{\text{II}}\text{Dy}^{\text{III}}_5(\mu_3\text{-OH})_6(\text{L})_2(\text{piv})_8(\text{NO}_3)_4] \cdot 4(\text{CH}_3\text{CN})$ (7**).** 0.075 g (0.22 mmol) of L and 0.036 g (0.35 mmol) of pivalic acid were added to 20ml of MeCN and stirred. To this 118 μl (0.84 mmol) of 99% NEt_3 were added and the resultant mixture brought to reflux and stirred for 10 minutes. To this 0.068 g (0.23 mmol) of $\text{Co}^{\text{II}}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and 0.104 g (0.23 mmol) of $\text{Dy}^{\text{III}}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ were added and the resultant mixture refluxed for a further 24 hours. This was then filtered and left undisturbed for slow evaporation, orange rectangular plate like crystals of **7** formed within 72 hours. Yield: 16 mg (13.0% based on Dy) Selected IR peaks (cm^{-1}): 2958.26 (m, br), 1605.7 (m), 1556.13 (s), 1485.01 (s), 1423.04 (s), 1221.42 (m), 1033.26 (m)

Synthesis of $[\text{Co}^{\text{II}}_2\text{Dy}^{\text{III}}_2(\mu_3\text{-OH})_2(\text{L})_2(\text{piv})_2(\text{NO}_3)_2(\text{EtOH})_2(\text{H}_2\text{O})_2] (\text{NO}_3)_2 (\text{EtOH})$ (8**).** 0.075 g (0.22 mmol) of L and 0.036 g (0.35 mmol) of pivalic acid were added to 20ml of EtOH and stirred. To this 118 μl (0.84 mmol) of 99% NEt_3 were added and the resultant mixture brought to reflux and stirred for 10 minutes. To this 0.068 g (0.23 mmol) of $\text{Co}^{\text{II}}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and 0.104 g (0.23 mmol) of $\text{Dy}^{\text{III}}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ were added and the resultant mixture refluxed for a further hour. This was then filtered and left undisturbed for slow evaporation, large red crystals of **8** formed within 48 hours. Yield: 91 mg (46.9% based on Co) Selected IR peaks (cm^{-1}): 3242.7 (br), 2971.00 (w), 1483.94 (s), 1454.42 (s), 1420.39 (s), 1300.92 (s), 1036.49 (s), 961.76 (m), 745.43 (s), 706.18 (m)

Synthesis of $[\text{Co}_4^{\text{II}}\text{Dy}^{\text{III}}_4(\mu_2\text{-O})_2(\mu_3\text{-OH})_4(\text{L})_4(\text{piv})_8]$ (9**).** 0.075 g (0.22 mmol) of L and 0.036 g (0.35 mmol) of pivalic acid were added to 20ml of EtOH and stirred. To this 118 μl (0.84 mmol) of 99% NEt_3 were added and the resultant mixture brought to reflux and stirred for 10 minutes. To this 0.068 g (0.23 mmol) of $\text{Co}^{\text{II}}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and 0.104 g (0.23 mmol) of $\text{Dy}^{\text{III}}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ were added and the resultant mixture refluxed for a further 24

hours. This was then filtered and left undisturbed for slow evaporation, red hexagonal plate like crystals of **9** formed within 48 hours. Yield: 24.5 mg (14.0% based on Co) Selected IR peaks (cm^{-1}): 2958.46 (br), 1603.96 (s), 1544.31 (s), 1419.35 (s), 1219.56 (s), 1104.31 (m), 967.74 (m), 742.29 (m), 705.04 (m).

Conversion of **8 to **6**.** 10 mg (0.00623 mmol) of **8** was added along with 1.27 mg (0.01246 mmol) of pivalic acid to 5ml MeCN. To this 0.86 μl (0.00623 mmol) of 99% NEt_3 were added and the resultant mixture stirred and refluxed for 24 hours. Crystals of **6** were formed within 72 hours. **Conversion of **8** to **9**.** 10 mg (0.00623 mmol) of **8** was added along with 1.27 mg (0.01246 mmol) of pivalic acid to 5ml EtOH. To this 0.86 μl (0.00623 mmol) of 99% NEt_3 were added and the resultant mixture stirred and refluxed for 24 hours. Crystals of **9** were formed within 72 hours.

Magnetic studies. Magnetic susceptibility measurements were carried out on polycrystalline samples with a MPMS5 Quantum Design susceptometer working in the range 30-300 K under external magnetic field of 0.3 T and under a field of 0.03T in the 30 – 2 K range to avoid saturation effects. Diamagnetic corrections were estimated from Pascal Tables.

Crystallography. Data for **4** and **8** were collected (ω - scans) at the University of Sussex using an Agilent Xcalibur Eos Gemini Ultra diffractometer with CCD plate detector under a flow of nitrogen gas at 173(2) K using Mo K α radiation ($\lambda = 0.71073 \text{ \AA}$). CRYSLIS CCD and RED software was used respectively for data collection and processing. Reflection intensities were corrected for absorption by the multi-scan method. Data for **3**, **5**, **6**, **7**, **8'** and **9** were collected at the National Crystallography Service, University of Southampton²⁶ using a Rigaku Saturn 724+ area detector mounted at the window of an FR-E+ rotating anode generator with a Mo anode ($\lambda=0.71075 \text{ \AA}$) under a flow of nitrogen gas at 100(2) K. All structures were determined using Olex2,²⁷ solved using either Superflip²⁸ or SHELXT^{29,30} and refined with SHELXL-2014.³¹ All non-H atoms were refined with anisotropic thermal parameters, and H-atoms were introduced at calculated positions and allowed to ride on their carrier atoms. Geometric/crystallographic calculations were performed using PLATON,³² Olex2,²⁷ and WINGX²⁹ packages; graphics were prepared with Crystal Maker.³³ Crystallographic details for **3** – **9** are given in Table S1. CCDC 1055917-1055924.

Results and discussion

Some general observations for all compounds, are: (a) except **4**, each L^- is chelated to an Co^{II} centre, forming a cationic metalloligand, $(\text{CoL})^+$, which in turn is linked to other metal centres, (b) L^- is coordinated to three metal centres exhibiting two different coordination modes (modes I and II, Scheme 2, above), (c) two coordination modes can be found for the co-ligand (Scheme 2, below), (d) Co^{II} centres are six coordinate in essentially regular octahedral coordination and (e) the coordination spheres of the Dy centres are completed by the carboxylate and the nitrate groups.

By changing the reaction conditions that afforded **1**, introducing pivalic acid as co-ligand, and heating at 40°C for one hour (Table 1, entry 1), we obtained orange diamond-shaped crystals of compound **3** (Fig. 1a). The structure, confirmed by X-Ray studies,²⁶ possesses the well-known defect dicubane³⁴ or, according to our nomenclature, **2,3M4-1**¹³ topology. The coordination number of the two Dy^{III} ions is 8. Using Shape software,³⁵ the geometry of Dy(1) can be best described as biaugmented trigonal prism or square antiprism [S(P) values 1.767 and 1.968, respectively] and of Dy(2) as biaugmented trigonal prism [S(P) = 2.372].


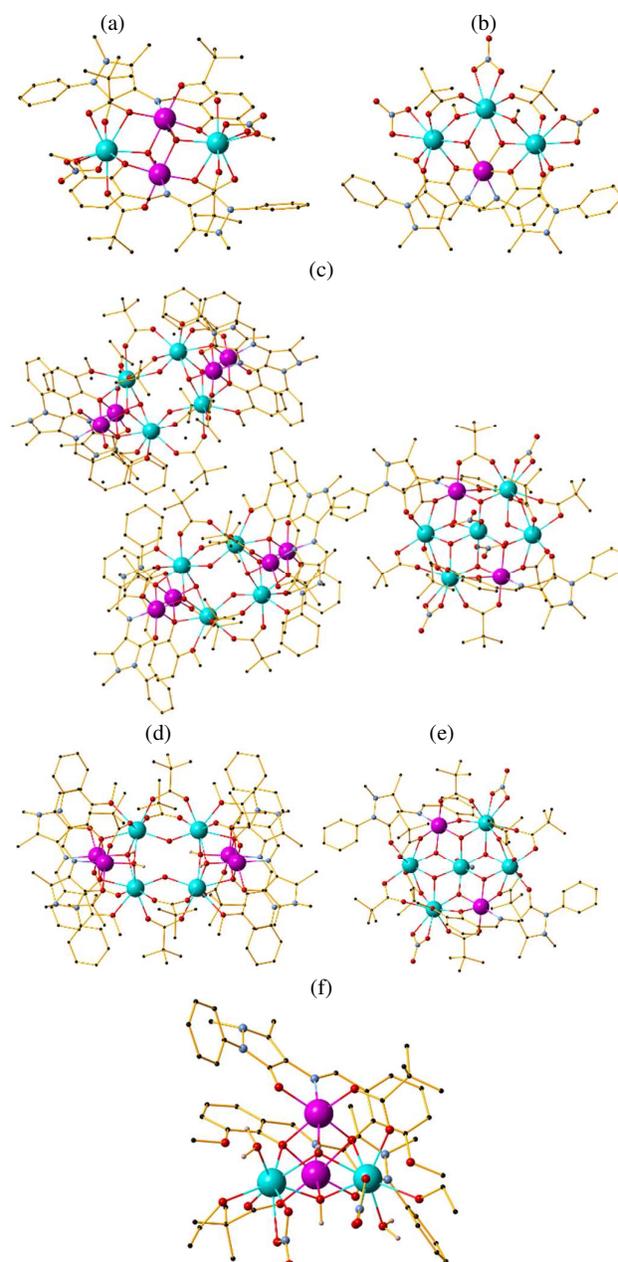


Fig. 1 Molecular structures of **3** (a), **4** (b), **5** (c), **6** (d), **7** (e) and **8** (f). Colour code: Co^{II} , pink; Dy^{III} , light blue; O, red; N, blue; C, black. Hydrogen atoms are omitted for clarity

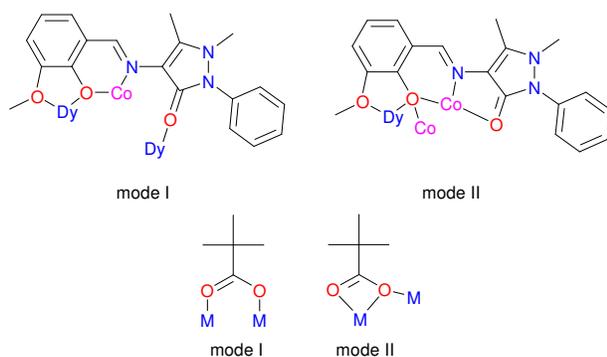The orange needles obtained under reflux (Table 1, entry 2) were found to be **4** $2(\text{CH}_3\text{OH})$, (Fig. 1b) also possessing the defect dicubane or **2,3M4-1** topology. In this compound, two L^- are chelated to a Co^{II} centre, forming a neutral metalloligand, (CoL_2) , which in turn is linked to the Dy^{III} centres. The coordination number of all Dy^{III} ions is 8. Using Shape software,³⁵ the geometry of $\text{Dy}(1)$ can be best described as intermediate between heptagonal pyramid and Johnson elongated triangular bipyramid, and the geometry of $\text{Dy}(2)$ can be best described as an intermediate of Johnson gyrobifastigium,³⁶ biaugmented trigonal prism and elongated trigonal bipyramid. The lattice methanol is hydrogen bonded to the chelated nitrate group of $\text{Dy}(2)$. Reaction for a longer time (Table 1, entry 3) again gave **4**, confirmed by a unit cell check. To the best of our knowledge, such defect dicubane $\text{Co}^{\text{II}}\text{Dy}^{\text{III}}_3$ topology has not previously been reported. In both **3** and **4**, MeO groups, arising from solvent deprotonation, bridge the metal centres μ_2 - or μ_3 - fashion and, the structure is unchanged, even after prolonged heating under reflux.











Scheme 2 (above) The two coordination modes of the ligand. Mode I is seen in compounds **3**, **4**, **5** and **7**, mode II is seen in **5**, **6**, **8**, **8'** and **9**. (below) The two coordination modes seen in **3** – **9**, for the pivalate anion.

As the complexes required bridging MeO groups to give a defect dicubane geometry it would be reasonable to suggest that a non-coordinating solvent may result in different topologies. Indeed, repetition of the reaction that afforded **3** in CH_3CN instead of CH_3OH (Table 1, entry 4), results in orange hexagonal crystals of **5** (Fig. 1c), the lattice of which contains two octanuclear and one heptanuclear $\text{Co}^{\text{II}}/\text{Dy}^{\text{III}}$ units. The octanuclear one can be considered as two $\text{Co}^{\text{II}}_2\text{Dy}^{\text{III}}_2$ cubanes joined by two oxo bridges, and bridged by four pivalates, possessing a **3,4M8-3** topology (Table 1, entry 4) and the heptanuclear fragment possesses a disk-like or **3,6M7-1** topology. According to our survey, both topologies are unprecedented in Co/Ln chemistry, and mixed nuclearity CCs are very rare in coordination chemistry as a whole.³⁷ The unusual **3,4M8-3** topology can be found in compounds containing solely Fe,^{38,39} Zn⁴⁰ and Dy⁴¹ but not in mixed metal species. Additionally, the **3,6M7-1** topology has been seen in mixed valence $\text{Co}^{\text{II/III}}_{42-44}$ and $\text{Dy}^{\text{III}}_{45}$ compounds, in a $\text{Mn}^{\text{II}}_3\text{Dy}^{\text{III}}_{46}$ compound and in the heptanuclear $\text{Co}^{\text{II}}_3\text{Dy}^{\text{III}}_4$ compound.¹⁷ Moreover, the existence of two bridging $\mu_2\text{-O}$

atoms is very rare in lanthanide chemistry. Only eight compounds are known with double bridging oxygen atoms; the Dy-O and the O-Dy-O values are in line with the previous reported examples.^{47,48} Triply bridging hydroxyl groups further support the formation of both species. In the reaction in CH_3CN under reflux conditions for an hour (Table 1, entry 5), only compound **6** $2\text{CH}_3\text{CN}$ was isolated and characterized (Fig. 1d). Compound **6** is identical to the octanuclear species found in **5**. The coordination number of the four Dy^{III} ions is 8. Using Shape software,³⁵ the geometry of both Dy^{III} ions can be best described as triangular dodecahedron, $S(P) = 0.790$.


Table 1 A summary of the reaction conditions for the formation of **3** – **9**

Entry	Solvent	Temperature / Time (h)	Topology	Product
1	MeOH	40°C / 1	2,3M4-1	 3
2	MeOH	Reflux (65°C) / 1	2,3M4-1	 4
3	MeOH	Reflux (65°C) / 24	2,3M4-1	 4
4	MeCN	40°C / 1	2 (3,4M8-3) + 3,6M7-1	 5
5	MeCN	Reflux (82°C) / 1	3,4M8-3	 6
6	MeCN	Reflux (82°C) / 24	3,6M7-1	 7
7	EtOH	40°C / 1	3M4-1	 8
8	EtOH	Reflux (79°C) / 1	3M4-1	 8'
9	EtOH	Reflux (79°C) / 24	3,4M8-3	 9

A further increase of the reaction time, to 24 hours (Table 1, entry 6), results in the isolation of only compound **7** $4\text{CH}_3\text{CN}$

(Fig. 1e) which is identical to the heptanuclear species found in **5**. This indicates a rearrangement to a species in which the Co/Dy ratio is different. The coordination numbers of the three peripheral and the central Dy^{III} ions are 8 and 7, respectively. The geometry of the central Dy^{III} ion can be best described as capped octahedron and of the four wheel Dy^{III} as bicapped trigonal prism. Thus, the solvent has a major effect on the adopted topology in this family of CCs. The use of CH₃CN does not provide linking between the metal centres; instead it promotes hydrolysis of the metal salts, to give CCs of higher nuclearity. The differences in temperature and reaction time in the synthesis of **5–7** influence the final product. A unit cell check of twenty random samples selected from three different vials gave identical unit cells, indicating that formation of **5–7** was reproducible.

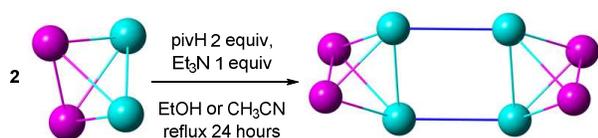The next step was to incorporate a protic solvent that has similar coordination ability to MeOH but is more bulky. The additional bulk should prevent the formation of bridges to give the defect dicubane geometry. Indeed, a reaction in EtOH at 40°C for 1 hour (Table 1, entry 7) resulted in the formation of a dicationic tetranuclear compound **8**·EtOH possessing a cubane (Fig. 1f) or **3M4-1** topology (Table 1, entry 7). Two triply bridging hydroxyl groups further enhance the formation of the cubane topology, while ethanol and water molecules fill the vacant positions on the two Dy^{III} centres. The coordination number of the two Dy^{III} ions is 10. Using Shape software,³⁵ the geometry of both Dy^{III} ions can be best described as sphenocorona, [S(P) = 10.948] and is very close to bicapped square antiprism [S(P) = 12.332] or augmented tridiminished icosahedron [S(P) = 12.234].³⁶ This cubane topology has reported previously only once in Co/Ln chemistry.⁴⁹ Most of the known tetranuclear Co₂Dy₂ compounds possess a defect dicubane topology.



Scheme 3 A proposed transformation of **8** or **8'** to **9** (EtOH) or **6** (CH₃CN) using

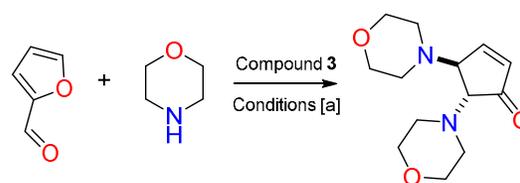
Thus, the employment of EtOH as solvent prevents the formation of EtO bridges and promotes partial hydrolysis of the metal centres to give a cubane unit. From the decorated topologies¹² (Table 1, entries 7 or 8 and 5) compound **8** can be considered as half the octanuclear species found in **6**. The formation of **6** could be formed by linking two cubane units by double deprotonation of a coordinated H₂O molecule occurs, to form a μ₂-O bridge. At the same time, replacement of two coordinated NO₃, two EtOH and the remaining coordinated H₂O molecules in each cubane by pivalate groups further stabilizes the octanuclear species. The formation of **8** was achieved in one hour at 40°C, thus the next step is to confirm that **8** is indeed an intermediate in the formation of **6**. This could be done in two ways: a) by showing that an increase in

temperature or time affords an octanuclear specie isoskeletal to **6** and b) by converting **8** to **6** in an independent reaction.

Reaction under reflux conditions for an hour (Table 1, entry 8) afforded a compound **8** (EtOH), which crystallized in a different space group. However, reaction for 24 hours under reflux (Table 1, entry 9) afforded, a compound **9**, isoskeletal to **6**. Furthermore, heating **8** for 24 hours under reflux in EtOH or CH₃CN, in the presence of 2 equivalents of pivalic acid and 1 equivalent of Et₃N, resulted in the formation of **9** or **6**, respectively (Scheme 3), as confirmed by unit cell check and IR.

To confirm the identity of those compounds in solution, we made use of broad electrospray ionization mass spectrometry (ESI-MS). However only for compounds **3** and **8** were we able to ascertain the identities of the species in solution. For **3**, we observed two peaks in the MS (positive-ion mode) at *m/z* 1644.6395 and at *m/z* 791.3097 which correspond to the fragments, [Co^{II}₂Dy^{III}₂(MeO)₂(C₁₉H₁₈N₃O₃)₂(C₅H₉O₂)₄(NO₃)]⁺ and [Co^{II}₂Dy^{III}₂(MeO)₂(C₁₉H₁₈N₃O₃)₂(C₅H₉O₂)₄-H]²⁺, respectively (see Fig. S7). For **8**, we observed two peaks in the MS (positive-ion mode) at *m/z* 1709.3351 and at *m/z* 1644.2554 which correspond to two monocationic fragments, [Co^{II}₂Dy^{III}₂(OH)₂(L)₂(piv)₂(NO₃)₄(EtOH)₂(H₂O) + H]⁺ and [Co^{II}₂Dy^{III}₂(OH)₂(L)₂(piv)₂(NO₃)₄(EtOH)]⁺, respectively, (see Fig. S8). Assignments were confirmed by the Dy isotope patterns (the weaker patterns from Co were masked) and showed that the clusters identified in the solid state were preserved in solution.

Since a tetranuclear Co^{II}Dy^{III}₂ compound⁹ is an efficient catalyst for the synthesis of trans-4,5-diaminocyclopent-2-enones from 2-furaldehyde and primary and secondary amines, we used compound **3** as catalyst in this domino reaction (Scheme 2, Table 2). Loadings of 1% and 2.5% for 2 h resulted in 43% and 73% yields, respectively. A loading of 10% for 8 h showed the highest yield of 95%. No significant improvement in yield was observed for any % loading over 8 hours. A fourfold decrease in catalyst loading for 8 h (2.5%) still shows good yields (85%), however these are lower than to the previously mentioned Co^{II}Dy^{III}₂ compound,⁹ suggesting catalytic efficiency is highly dependent on the coordination environment of the Dy^{III} centres. Efforts to recover the catalyst were not successful, while theoretical studies on this aspect are in progress.




Scheme 4 The catalytic reaction tested for compound **3**

Table 2 Comparison of catalytic activity for compound 3.

Entries	Catalyst Loading (%) ^[b]	2 h (Yield %) ^[c]	8 h (Yield %) ^[c]
1	10	92	95
2	5	86	90
3	2.5	73	85
4	1	43	66

[a] Reaction conditions: Morpholine 1 mmol; 2-furaldehyde 0.5 mmol; 4 Å MS 100 mg; catalyst; anhydrous MeCN 4mL; room temperature [b] Catalyst loading calculated per equivalent of Dy [c] Determined by ¹H NMR spectroscopy

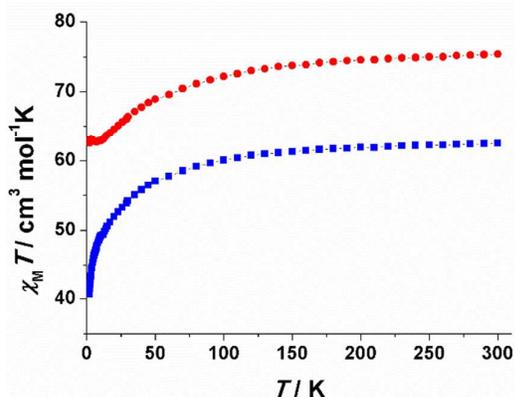The room temperature χ_{MT} values for **6** and **7** (62.5 and 75.4 cm³ K mol⁻¹, respectively) are in agreement with the expected values of 64.18 and 74.60 cm³ K mol⁻¹ for four non-interacting Dy^{III} (⁶H_{15/2} free ion; $S = 5/2$; $L = 5$; $g_J = 4/3$) centres, and four Co^{II} ions or five non-interacting Dy^{III} and two Co^{II} respectively (Fig 2). Upon cooling, the χ_{MT} products decrease monotonically for **6** reaching 40.7 cm³ K mol⁻¹ at 2 K and down to a quasi constant value around 63 cm³ K mol⁻¹ for **7**. This decrease is mainly due to the progressive depopulation of the Dy^{III} excited Stark sublevels. The relativity high χ_{MT} value and the absence of decay at low temperature for **7**, as well its fast magnetization, (Fig S10), may also suggest weak intramolecular ferromagnetic coupling. In the light of the susceptibility responses, alternating-current (ac) preliminary magnetic susceptibility measurements were performed on polycrystalline samples of **6** and **7** (Fig S11). In a zero applied dc field and a 4 G ac field oscillating at 1000 and 10 Hz. frequency-dependent out-of-phase (χ''_M) weak tails were observed, but no peaks were seen even under an dc field of 0.1 T, suggesting weak single-molecule magnet response



clearly below K.

Fig. 2 χ_{MT} vs T plots for complexes **6** (blue) and **7** (red). Solid lines are guides for the eye.

The CCs presented here show how major differences in core motif are caused by subtle changes in reaction conditions. The employment of HL in Co/Dy chemistry compounds a) with Co in oxidation state II and b) with hitherto unobserved topologies that are preserved in alcoholic solvents. The most important feature of HL is that despite, being monoanionic and showing a coordination environment similar to those in other ligands,¹⁸ gives CCs with higher nuclearity. Two different coordination modes are seen for HL in compounds **3–9**

(Scheme 2), however despite the increase in reaction temperature no increase in the number of bridging metal centres is observed. In protic solvents, the ligand coordinates differently, but this can be attributed to the existence of further MeO bridges. The final products are influenced by the temperature and the reaction time. When CH₃CN is used as solvent, a mixed octanuclear and heptanuclear CC product is obtained (Table 1, entry 4) and when reaction takes place under reflux (Table 1, entries 5 and 6), distinct octanuclear (Table 1, entry 5) and heptanuclear (Table 1, entry 6) CCs are obtained. Even with changes of solvents viz to CH₃CN (Table 1, entry 5) and EtOH (Table 1, entry 9) and reaction times, isoskeletal products are obtained. For this specific reaction system, an increase in the reaction temperature enhances deprotonation of water molecules to form OH⁻ and/or O²⁻ species leading to CCs clusters of higher nuclearity in CH₃CN and EtOH.

Conclusions

The formation of the double cubane **9** either from the single cubane **8** or by increased reaction time and temperature (Table 1, entry 9) represents an interesting example in coordination chemistry. The structural relationship of compounds **6**, **9** and **8** can immediately be visualized (Scheme 3) from topological analysis. Since the coordination chemistry of HL is still insufficiently delineated, further studies are required that will reveal its coordination behaviour and lead to a library of CCs. We are extending this study to: a) more complicated systems to explore synthesis of CCs with higher nuclearity and b) compounds of other 3d and 4f elements to investigate their magnetic and photoluminescent properties.

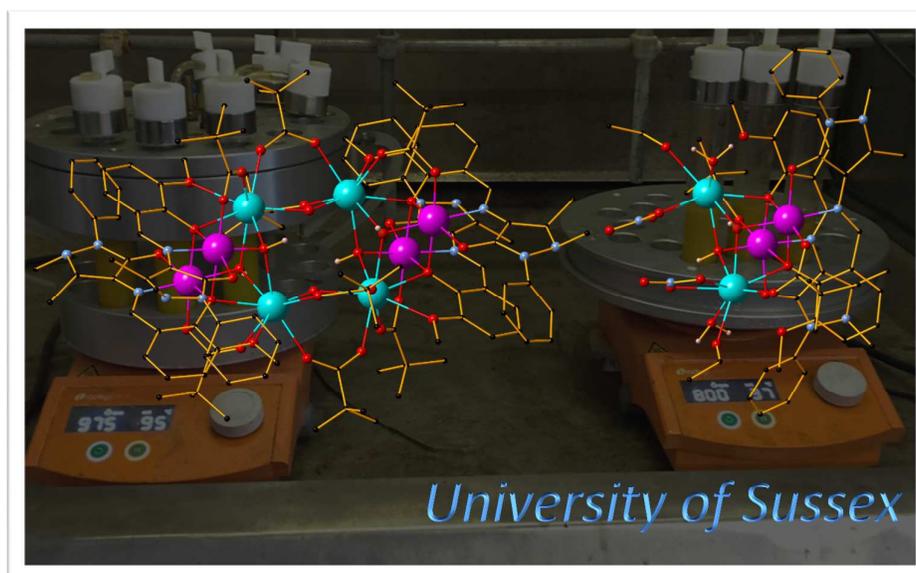
Acknowledgements

We thank the University of Sussex for offering a PhD position to K.G., the EPSRC UK National Crystallography Service at the University of Southampton for the collection of the crystallographic data for compounds **3**, **5**, **6**, **7**, **8'** and **9** and Dr. David Smith (University of Sussex) for helpful discussions

References

- D. I. Alexandropoulos, T. N. Nguyen, L. Cunha-Silva, T. F. Zafiroopoulos, A. Escuer, G. Christou, and T. C. Stamatatos, *Inorg. Chem.*, 2013, **52**, 1179–1181.
- J.-B. Peng, Q.-C. Zhang, X.-J. Kong, Y.-Z. Zheng, Y.-P. Ren, L.-S. Long, R.-B. Huang, L.-S. Zheng, and Z. Zheng, *J. Am. Chem. Soc.*, 2012, **134**, 3314–3317.
- C. Papatriantafyllopoulou, T. C. Stamatatos, C. G. Efthymiou, L. Cunha-Silva, F. A. A. Paz, S. P. Perlepes, and G. Christou, *Inorg. Chem.*, 2010, **49**, 9743–9745.
- Y.-Z. Zheng, M. Evangelisti, and R. E. P. Winpenny, *Chem. Sci.*, 2011, **2**, 99–102.
- S. Hossain, S. Das, A. Chakraborty, F. Lloret, J. Cano, E. Pardo, and V. Chandrasekar, *Dalton Trans.*, 2014, **43**, 10164–10174.
- G. Maayan and G. Christou, *Inorg. Chem.*, 2011, **50**, 7015–7021.
- K. Liu, W. Shi, and P. Cheng, *Coord. Chem. Rev.*, 2014.
- E. C. Sañudo and L. Rosado Piquer, *Dalton Trans.*, 2015.

9. K. Griffiths, C. W. D. Gallop, A. Abdul-Sada, A. Vargas, O. Navarro, and G. E. Kostakis, *Chem. Eur. J.*, 2015, **21**, 6358–6361.
10. R. E. P. Winpenny, *J. Chem. Soc. Dalton Trans.*, 2002, 1–10.
11. M. O’Keeffe, M. A. Peskov, S. J. Ramsden, and O. M. Yaghi, *Acc. Chem. Res.*, 2008, **41**, 1782–1789.
12. G. E. Kostakis and A. K. Powell, *Coord. Chem. Rev.*, 2009, **253**, 2686–2697.
13. G. E. Kostakis, V. A. Blatov, and D. M. Proserpio, *Dalton Trans.*, 2012, **41**, 4634–4640.
14. G. E. Kostakis, S. P. Perlepes, V. A. Blatov, D. M. Proserpio, and A. K. Powell, *Coord. Chem. Rev.*, 2012, **256**, 1246–1278.
15. P. Wix, G. E. Kostakis, V. A. Blatov, D. M. Proserpio, S. P. Perlepes, and A. K. Powell, *Eur. J. Inorg. Chem.*, 2013, **2013**, 520–526.
16. G. E. Kostakis and A. K. Powell, *Chem. Eur. J.*, 2010, **16**, 7983–7987.
17. E. Loukopoulos, B. Berkoff, A. Abdul-Sada, G. J. Tizzard, S. J. Coles, A. Escuer, and G. E. Kostakis, *Eur. J. Inorg. Chem.*, 2015, n/a–n/a.
18. K. C. Mondal, A. Sundt, Y. Lan, G. E. Kostakis, O. Waldmann, L. Ungur, L. F. Chibotaru, C. E. Anson, and A. K. Powell, *Angew. Chem. Int. Ed.*, 2012, **51**, 7550–7554.
19. E. V. Orlova, A. E. Goldberg, M. A. Kiskin, P. S. Koroteev, A. L. Emelina, M. A. Bykov, G. G. Aleksandrov, Z. V. Dobrokhotova, V. M. Novotortsev, and I. L. Eremenko, *Russ. Chem. Bull.*, 2012, **60**, 2236–2250.
20. N. P. Burkovskaya, E. V. Orlova, M. A. Kiskin, N. N. Efimov, A. S. Bogomyakov, M. V. Fedin, S. V. Kolotilov, V. V. Minin, G. G. Aleksandrov, A. A. Sidorov, V. I. Ovcharenko, V. M. Novotortsev, and I. L. Eremenko, *Russ. Chem. Bull.*, 2012, **60**, 2490–2503.
21. N. Gogoleva, E. Zorina-Tikhonova, G. Aleksandrov, A. Lermontov, N. Efimov, A. Bogomyakov, E. Ugolkova, S. Kolotilov, A. Sidorov, V. Minin, V. Novotortsev, and I. Eremenko, *J. Clust. Sci.*, 2014, **26**, 137–155.
22. E. N. Egorov, E. A. Mikhalyova, M. A. Kiskin, V. V. Pavlishchuk, A. A. Sidorov, and I. L. Eremenko, *Russ. Chem. Bull.*, 2014, **62**, 2141–2149.
23. S. Schmidt, D. Prodius, G. Novitchi, V. Mereacre, G. E. Kostakis, and A. K. Powell, *Chem. Commun.*, 2012, **48**, 9825–9827.
24. V. Mereacre, A. M. Ako, R. Clérac, W. Wernsdorfer, I. J. Hewitt, C. E. Anson, and A. K. Powell, *Chem. Eur. J.*, 2008, **14**, 3577–3584.
25. G. Peng, G. E. Kostakis, Y. Lan, and A. K. Powell, *Dalton Trans.*, 2013, **42**, 46–49.
26. S. J. Coles and P. A. Gale, *Chem. Sci.*, 2012, **3**, 683–689.
27. O. V Dolomanov, A. J. Blake, N. R. Champness, and M. Schröder, *J. Appl. Crystallogr.*, 2003, **36**, 1283–1284.
28. L. Palatinus and G. Chapuis, *J. Appl. Crystallogr.*, 2007, **40**, 786–790.
29. L. J. Farrugia, *J. Appl. Crystallogr.*, 1999, **32**, 837–838.
30. G. M. Sheldrick, *Acta Crystallogr. Sect. A Found. Adv.*, 2015, **71**, 3–8.
31. G. M. Sheldrick, *Acta Crystallogr. Sect. A*, 2008, **64**, 112–122.
32. A. L. Spek, *J. Appl. Crystallogr.*, 2003, **36**, 7–13.
33. C. F. Macrae, P. R. Edgington, P. McCabe, E. Pidcock, G. P. Shields, R. Taylor, M. Towler, and J. Van De Streek, *J. Appl. Crystallogr.*, 2006, **39**, 453–457.
34. P. King, R. Clerac, W. Wernsdorfer, C. E. Anson, and A. K. Powell, *Dalton Trans.*, 2004, 2670–2676.
35. S. A. M. Llunell, D. Casanova, J. Cirera, P. Alemany, *SHAPE version 2.0.*, 2010, **Barcelona**.
36. N. W. Johnson, *Canad. J. Math.*, 1966, **18**, 169–200.
37. A. K. Powell, S. L. Heath, D. Gatteschi, L. Pardi, R. Sessoli, G. Spina, F. Del Giallo, and F. Pieralli, *J. Am. Chem. Soc.*, 1995, **117**, 2491–2502.
38. L. C. Roof, W. T. Pennington, and J. W. Kolis, *Angew. Chemie Int. Ed. English*, 1992, **31**, 913–915.
39. L. Cai, B. M. Segal, J. R. Long, M. J. Scott, and R. H. Holm, *J. Am. Chem. Soc.*, 1995, **117**, 8863–8864.
40. A. F. Armstrong, T. Chivers, M. Krahn, and M. Parvez, *Can. J. Chem.*, 2005, **83**, 1768–1778.
41. A. S. R. Chesman, D. R. Turner, B. Mobaraki, K. S. Murray, G. B. Deacon, and S. R. Batten, *Dalton Trans.*, 2012, **41**, 3751–3757.
42. A. A. Kitos, C. G. Efthymiou, C. Papatriantafyllopoulou, V. Nastopoulos, A. J. Tasiopoulos, M. J. Manos, W. Wernsdorfer, G. Christou, and S. P. Perlepes, *Polyhedron*, 2011, **30**, 2987–2996.
43. R. Pattacini, P. Teo, J. Zhang, Y. Lan, A. K. Powell, J. Nehrkor, O. Waldmann, T. S. A. Hor, and P. Braunstein, *Dalton Trans.*, 2011, **40**, 10526–10534.
44. L. F. Chibotaru, L. Ungur, C. Aronica, H. Elmoll, G. Pilet, and D. Luneau, *J. Am. Chem. Soc.*, 2008, **130**, 12445–12455.
45. J. W. Sharples, Y.-Z. Zheng, F. Tuna, E. J. L. McInnes, and D. Collison, *Chem. Commun.*, 2011, **47**, 7650–7652.
46. J. Liu, C. Ma, H. Chen, M. Hu, H. Wen, H. Cui, and C. Chen, *Dalton Trans.*, 2013, **42**, 3787–3790.
47. A. J. Wooles, O. J. Cooper, J. McMaster, W. Lewis, A. J. Blake, and S. T. Liddle, *Organometallics*, 2010, **29**, 2315–2321.
48. M. P. Coles, P. B. Hitchcock, A. V Khvostov, M. F. Lappert, Z. Li, and A. V Protchenko, *Dalton Trans.*, 2010, **39**, 6780–6788.
49. X.-Q. Zhao, Y. Lan, B. Zhao, P. Cheng, C. E. Anson, and A. K. Powell, *Dalton Trans.*, 2010, **39**, 4911–4917.



Mixing $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ / $\text{Dy}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ / (E)-4-(2-hydroxy-3-methoxybenzylideneamino)-2,3-dimethyl-1-phenyl-1,2-dihydropyrazol-5-one (HL) / pivalic acid / Et_3N in various solvents gives products with robust and unseen topologies. These show that the temperature and reaction time influence the formation of the final product. Magnetic and catalytic studies are presented as well.