

Faraday Discussions

Accepted Manuscript



This manuscript will be presented and discussed at a forthcoming Faraday Discussion meeting. All delegates can contribute to the discussion which will be included in the final volume.

Register now to attend! Full details of all upcoming meetings: <http://rsc.li/fd-upcoming-meetings>



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Synthesis of ammonia directly from wet air using $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ as the catalyst

Rong Lan ^a, Khaled A. Alkhazmi ^a, Ibrahim A. Amar ^a and Shanwen Tao ^{a,b,*}

^a Department of Chemical & Process Engineering, University of Strathclyde, Glasgow G1 1XJ, UK

^b School of Engineering, University of Warwick, Coventry, CV4 7AL, UK

Ammonia was directly synthesised from wet air at 400 °C at atmospheric pressure. A new perovskite $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ was used as electrocatalyst for electrochemical synthesis of ammonia. Ammonia formation rates of $9.19 \times 10^{-7} \text{ mol s}^{-1} \text{ m}^{-2}$ and $1.53 \times 10^{-6} \text{ mol s}^{-1} \text{ m}^{-2}$ were obtained at 400 °C when wet air and wet N_2 were introduced into a simple single chamber reactor respectively. The perovskite catalyst is low cost compared to the previously reported Ru/MgO and Pt/C catalysts. This experiment indicates that ammonia can be directly synthesised from wet air, a very promising simple technology for sustainable synthesis of ammonia in the future.

* Corresponding author:
Department of Chemical and Process Engineering
University of Strathclyde
Glasgow G1 1XJ UK
Tel.: +44 (0) 141 548 2361; fax: +44 (0) 141 548 2539
E-mail address: shanwen.tao@strath.ac.uk

1. Introduction

Nitrogen fertiliser has supported approximately 27% of the world's population over the last century, equivalent to around 4 billion people born (or 42% of the estimated total births) since 1908.¹ Although over 78% of the atmosphere is composed of nitrogen, it is difficult to use N₂ directly by plants as plants can only use fixed nitrogen. The breakthrough in nitrogen fixation took place a century ago, the well-known Haber-Bosch process, operating at high temperature (~ 500 °C) and high pressure (150-300 bar).² Fritz Haber and Carl Bosch won Nobel Prize in Chemistry in 1918 and 1931 respectively for their contributions in industrial production of ammonia. This innovation became a key driver in the development of the industrialized society and is still securing the nutrition of billions of people today. In 2007, The Nobel Prize in Chemistry 2007 was awarded to Gerhard Ertl for his studies of chemical processes on solid surfaces while understanding of the reaction mechanism of H₂ and N₂ on solid ammonia synthesis catalysts is a major achievement of Gerhard Ertl for this prize.³

In the Haber-Bosch process, the required hydrogen is produced through the steam reforming of natural gases or coal by which consumed more than 1% of world power generation.⁴ In addition, CO₂ emitted from ammonia industry is equivalent to 0.77 % of the world total CO₂ emission. In order to reduce the current dependency on the fossil fuels and to reduce carbon emissions associated with their use, it is essential to introduce new ammonia synthesis process and break the link between fossil fuels and ammonia industry.⁵

To reduce global CO₂ emission, renewable electricity generated from solar, wind, marine and other sources are becoming more and more important. Due to the intermittent nature of those renewable resources, energy storage, particularly renewable electricity storage becomes a big challenge. One of the possible solutions for renewable electricity storage is to produce basic chemical feedstock such as ammonia. The electrochemical synthesis processes are among the promising alternatives in particular if the hydrogen required for ammonia synthesis is produced from non-fossil fuel resources.⁶⁻⁸ Recently, it has been reported that ammonia can be directly synthesised from air and water at ambient conditions.² It has been widely reported

that ammonia can be synthesised from N_2 and H_2 (or steam) at a temperature around $500\text{ }^\circ\text{C}$.⁹
¹⁵ The possible reason is that, the decomposition of ammonia at high temperature is kinetically slow thus ammonia can still be collected if it is removed from the reactor in time. Ammonia will be able to be synthesised from air and water at elevated temperatures if the oxidation of ammonia is also kinetically slow.

In our previous papers, we reported electrochemical synthesis of ammonia based on electrochemical cells using $Ce_{0.8}Sm_{0.2}O_{2-\delta}$ - $(Li,Na,K)_2CO_3$ composite electrolyte.¹² The eutectic point of $(Li,Na,K)_2CO_3$ ternary molten salts is $396\text{ }^\circ\text{C}$.^{16,17} The low melting point of mixed $(Li,Na,K)_2CO_3$ salts makes the composite to exhibit high ionic conductivity at relatively low temperature which can minimise the operating temperature of the cell, reducing the thermal decomposition and oxidation of ammonia. It has been reported that the ionic conductivity of $Ce_{0.8}Sm_{0.2}O_{2-\delta}$ - $(Li,Na,K)_2CO_3$ composite reached 0.1 S/cm at a temperature around $400\text{ }^\circ\text{C}$.¹⁸ The total ionic conductivity includes those from Li^+ , Na^+ , K^+ , H^+ , HCO_3^- , CO_3^{2-} and O^{2-} ions. Good fuel cell performance based on $Ce_{0.8}Sm_{0.2}O_{2-\delta}$ - $(Li,Na,K)_2CO_3$ composite electrolyte indicates higher H^+/O^{2-} ionic conductivity in this type of composite materials.¹⁸⁻²⁰ Either H^+ or O^{2-} ionic conduction can be used for electrochemical synthesis of ammonia.⁶ Therefore a similar composite electrolyte $Ce_{0.8}Gd_{0.2}O_{2-\delta}$ - $(Li,Na,K)_2CO_3$ was used as electrolyte in this study for ammonia synthesis. Recently, it has been reported that ammonia was successfully synthesised directly from wet air using $La_{0.8}Cs_{0.2}Fe_{0.8}Ni_{0.2}O_{3-\delta}$ ²¹ or $Pr_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-\delta}$ ²² as the catalyst. It has been reported that Cu and Ni co-doped $SmFeO_3$, $SmFe_{0.7}Cu_{0.1}Ni_{0.2}O_{3-\delta}$ is a very good ammonia synthesis catalyst and an ammonia formation rate of $1.13 \times 10^{-8}\text{ mol}\cdot\text{cm}^{-2}\cdot\text{s}^{-1}$ was observed at $80\text{ }^\circ\text{C}$ when N_2 and H_2 were used as the reactants.²³ This inspired us to use doped $SmFeO_3$ catalysts for electrochemical synthesis of ammonia. On the other hand, BaO is a typical promoter of ammonia synthesis catalysts.^{24,25} However, BaO itself is unstable in wet air because of the reaction between BaO and H_2O to form $Ba(OH)_2$. Therefore, in this paper, we introduce some Ba at the A-site of perovskite oxide $SmFeO_3$. New perovskite $Sm_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-\delta}$ (SBFCu) was synthesised as electro-catalyst for synthesis of ammonia from air/ N_2 and water. $Sm_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-\delta}$ was used as both cathode and anode and a single chamber reactor was used for the synthesis.

2. Experimental

Materials synthesis

Calculated amounts of Gd_2O_3 were dissolved hot dilute nitric acid to form gadolinium nitrate aqueous solution. Then an appropriate amount of $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ was added into the solution. 1M $(\text{NH}_4)_2\text{CO}_3$ solution was added dropwise with vigorous stirring until pH value reached 7-8, after that vigorous stirring was continued for another 30 min. The formed precipitate was then collected by vacuum filtration and washed several times with deionised water then dried at 100 °C overnight. The obtained powder was calcined in air at 650 °C for 2 hours with a heating/cooling rate of 2 °C min^{-1} . Finally, ultrafine powder of (GDC) was obtained.

$\text{Ce}_{0.8}\text{Gd}_{0.2}\text{O}_{2.8}$ and ternary carbonate mixture $(\text{Li,Na,K})_2\text{CO}_3$ (32.1 wt% Li_2CO_3 ; 34.5 wt% K_2CO_3 ; 33.4 wt% Na_2CO_3) powders were mixed together with weight ratio of oxide to carbonate 7:3. The mixture was mixed and grounded with the use of 25 ml isopropanol. Then the mixture was put in ball miller (Planetary Mono Mill Pulverisette 6) for mixing with speed of 400 rpm for 4 hours. The weight ratio of balls to powders was roughly 1:1. Then the mixture was heated at hot plate magnetic stirrer at 150 °C to release and get rid of isopropanol. The powder was then heated at 600 °C for one hour then quench in air to room temperature. The as-prepared oxide-carbonate composite electrolyte will be used for ammonia synthesis.

Samarium (III) oxide was dissolved in diluted nitric acid to form samarium nitrate under heating and stirring. Calculated amounts of nitrates $\text{Ba}(\text{NO}_3)_2$, $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ and $\text{Cu}(\text{NO}_3)_2 \cdot 2.5\text{H}_2\text{O}$ were dissolved in deionised water and were added to the above prepared solution. Appropriate amounts of citric acid and EDTA (ethylenediaminetetraacetic acid) were then added as complexing agents with a molar ratio of citric acid: EDTA: metal cations of 1.5:1: 1. Dilute aqueous ammonia solution was then added to the mixed solution to adjust the pH value to around 6 and a dark green clear solution was obtained. The mixed solution

was evaporated on a hot-plate at 200-250 °C under stirring and then gradually changed into a dark sticky gel before complete drying. By further heating the gel converted to black. The brown ash was grounded and subsequently calcined in air at 900 °C for 2 hours with heating/cooling rates of 5 °C min⁻¹ to obtain a single phase of Sm_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-δ}.

Materials characterisation

X-ray data were collected on a PANanalyticalX'Pert Pro in the Bragg-Brentano reflection geometry with a Ni-filtered Cu K α source (1.5405 Å), fitted with a X'Celerator detector and an Empyrean CuLFF xrd tube. Absolute scans in the 2 θ range of 5-100° with step sizes of 0.0167° were used during data collection. The surface area of Sm_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-δ} powder was measured by a N₂ adsorption method using Micromeritics ASAP 2420.

TG/DSC analyses were performed using a Stanton Redcroft STA/TGH series STA 1500 operating through a Rheometric Scientific system interface controlled by the software RSI Orchestrator in flowing air or N₂ at a flow rate of 50 ml min⁻¹.

Total conductivity measurements were carried out by a pseudo-four-terminal method using a computer-controlled SolartronAnalytical[®] SI 1470A electrochemical interface by applying a constant current. The Sm_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-δ} powder fired at 900 °C was pressed into pellets with diameter of 13 mm and thickness around 2 mm then fired at 1100 °C for 5 hours. A silver coated pellet was fitted into the measuring apparatus and the conductivity measurement was carried out in air between room temperature and 750 °C.

Fabrication of the single cell and ammonia synthesis measurements

The cell was placed in a self-designed single chamber reactor as described elsewhere.²² Electrolytic cell for ammonia synthesis was a tri-layer single cell which fabricated by a cost-effective one-step dry-pressing and co-firing process. The anode and cathode material was

0.8 g $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ plus 0.2 g composite electrolyte to form a composite electrode materials. The composite anode, composite electrolyte and composite cathode (SBFCu/CGO/SBFCu) were fed into the die, layer by layer, with the aid of a sieve to ensure uniform powder distribution, and then uniaxially pressed at pressure of 300 MPa by cold pressing into 13 mm pellets. The pellets were sintered at 600 °C for 2 h. The thickness of the anode, electrolyte and cathode was approximately 0.6, 1.0 and 0.6 mm respectively. The catalyst surface area of the cathode and anode was 1.281 cm². Silver paste was painted on each electrode surface of the cell as a current collector. Ag wires were used as output terminals for both electrodes. It has been reported that silver itself have negligible catalytic effects on ammonia synthesis.⁹

Compressed air or N₂ was passing through room temperature water before imputing to the single chamber reactor as described in previous reports.^{21,22} The flow rate of air (or N₂) was 50ml/min. The steam concentration in air (or N₂) was 3mol%. A dc voltage was applied to the cell using a Solartron 1287A electrochemical interface. The synthesised ammonia was absorbed by 25 ml of diluted sulphuric acid (0.001 M) for 30 min as described before.^{2,12} The concentration of NH₄⁺ in the absorbed solution was analysed using Orion Application solution for low adjusting ISA. The produced ammonia was detected using an ammonia meter (ISE Thermo Scientific Orion Star A214) and the rate of ammonia formation was calculated using the following equation².

$$r_{\text{NH}_3} = \frac{[\text{NH}_4^+] \times V}{t \times A} \quad (1)$$

Where:

[NH₄⁺] = is the measured NH₄⁺ ion concentration

V = is the volume of the dilute H₂SO₄ for ammonia collection

t = is the adsorption time.

A = is the effective area of the cell.

3. Results and discussion

Thermal analysis of the brown ash was carried out in air (Fig. 1A). It was found a weight loss of $\sim 52\%$ occurred at a temperature between 300 and 430 °C. This is due to the decomposition of the ash and loss of organic components. The sample weight became stable at a temperature above 800 °C indicating the minimum formation temperature for $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ is 800 °C. To guarantee the formation of single phase, we choose 900 °C as the firing temperature for $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$. The ash was fired at 900 °C for 2 hours to form perovskite phase. XRD analysis of the powder after firing at 900 °C indicates it is a single phase (Fig. 2). It exhibits a cubic structure with space group $Pm\bar{3}m(221)$; $a = 3.9148(1)$ Å, $V = 60.00(1)$ Å³ (Table 1). In our previous report, perovskite oxide $\text{La}_{0.6}\text{Sr}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ exhibits a cubic structure with space group $Pm\bar{3}m(221)$.¹² SEM pictures indicate that the prepared $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ powders agglomerated together with secondary particle size of ~ 0.1 μm (Fig. 3). The surface area of the $\text{La}_{0.6}\text{Sr}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ prepared at 900 °C was 7.94(1) m²/g.

The electronic conductivity of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ is very important in order to be used as both cathode and anode for the electrochemical cells for ammonia synthesis. Dc conductivity measurement indicated that the conductivity increased before 550 °C, reached a value of 2.29 S/cm then started to decrease (Fig. 4). This is probably due to the semiconductor to metal transition which is a common phenomenon in perovskite oxides.²⁶ The conductivity of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ was 1.88 S/cm at 400 °C. Regarding the operating temperature of the cell, the lowest working temperature of the CGO-(Li,Na,K)₂CO₃ composite electrolyte (400 °C) was used in order to minimise possible ammonia decomposition and oxidation.

During the ammonia synthesis process, $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ was exposed wet N₂ or wet air. Therefore the stability of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ in N₂ is very important. The STA analysis of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ in N₂ is shown in Fig. 1B. It was found that the sample kept losing weight until the measured 600 °C. The initial weight loss below is due to the

desorption of adsorbed water and gases. Further weight loss at higher temperature is probably due to the lattice oxygen, forming oxygen vacancies. No obvious thermal effect was observed on the DSC curve indicating that there is no obvious chemical reaction between $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ and N_2 at a temperature below 600 °C.

For ammonia synthesis, wet air was fed into the single chamber reactor as described elsewhere.²² The gas composition was approximately 3mol% H_2O , 97mol% air. The effect of the applied potential on ammonia formation rate was investigated at 400 °C and the order for applied voltage was from low to high, between 1.2 and 1.7V with 0.1 V interval. Fig. 5A shows the recorded current change against time for electrolytic cell during the ammonia synthesis process at different potentials at 400 °C over a period of 3600 seconds (was 3300 seconds due to interruption when applied 1.6V). As can be seen, the current density decreased at the beginning but tended to become stable. The ammonia produced in the single chamber reactor was absorbed by 20 ml of dilute H_2SO_4 (0.001M) for 60 minutes. It is surprising that ammonia was successfully synthesised at atmospheric pressure from wet air (~3% H_2O). As can be seen in Fig. 6A the ammonia formation rate increased significantly with increasing the applied potential and reached a maximum value at 1.4 V ($9.19 \times 10^{-7} \text{ mol s}^{-1} \text{ m}^{-2}$ at 400 °C), showing that 1.4 V was the optimum potential for ammonia synthesis in this study. In terms of catalyst weight, the ammonia formation rate was $1.48 \times 10^{-10} \text{ mol/s} \cdot \text{g}_{\text{cat}}$. This is two orders of magnitudes higher than the reported ammonia formation rates (around $1.0 \times 10^{-12} \text{ mol/s} \cdot \text{g}_{\text{cat}}$ at ~ 600 °C) when either a H^+ ($\text{SrCe}_{0.95}\text{Yb}_{0.05}\text{O}_{3-\delta}$) or O^{2-} (8 mol% yttria-stabilized zirconia) conductor was used as electrolyte with an industrial Ru/MgO catalyst used at the cathode.⁹ It was 400 °C in our experiment which is roughly 200 °C lower than that reported by Skodra.⁹ Higher working temperature may cause the thermal decomposition or oxidation of produced ammonia, particularly at a temperature above 500 °C.² The $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ catalyst used in this study is much cheaper than the Ru/MgO catalyst reported by Skodra and Stoukides⁹ and, the Pt/C catalyst used for low temperature synthesis of ammonia from air and water.^{2,4}

For comparison, ammonia was synthesised from wet nitrogen using the same cell. Fig. 5B shows the recorded current change against time for electrolytic cell during the ammonia synthesis process at different potentials at 400 °C over a period of 60 minutes. As can be seen, the electrolytic cell was stable when applied voltages was over 1.4 V. As expected, ammonia was also successfully synthesised at 400 °C under atmospheric pressure from ~3% H_2O and N_2 (Fig. 6A). Again the ammonia formation rate increased significantly with increasing the

applied potential and reached a maximum value at 1.4 V (1.53×10^{-6} mol s⁻¹ m⁻² at 400 °C), showing that 1.4 V was the optimum potential for ammonia synthesis in this study. The same tendency was observed for both wet air and wet N₂. This could be attributed to nitrogen chemisorption hindered by the high rate of electrochemically supplied H⁺, which in turn poisoned the catalyst (cathode surface).^{6, 27} In terms of catalyst weight, the ammonia formation rate was 2.45×10^{-10} mol/s·g_{cat} which is more than two orders of magnitude higher than the values reported by Skodra.⁹ When applied 1.7V, the ammonia formation rates for wet air and wet N₂ are comparable (Fig. 6A) while slightly more ammonia was produced at lower voltages when wet N₂ was introduced into the single chamber reactor. The observed ammonia formation rates in this study were lower than the reported value when SmFe_{0.7}Cu_{0.1}Ni_{0.2}O_{3-δ} was used as the cathode catalyst but the experiments were operated under different conditions.²³ H₂ and N₂ were used as the reactant while we used wet N₂/air as the precursor. The cell operating temperature was 400 °C while was nearby room temperature in a previous report.²³

The Faraday efficiencies of the electrochemical synthesis process under different conditions are also calculated. As shown in Fig. 6B, when wet air was used, the highest Faraday efficiency was 0.74% when a voltage of 1.7V was applied. In the case of wet N₂, the highest Faraday efficiency was 1.19% at a voltage of 1.7V. At lower applied voltages, the Faraday efficiencies were comparable for wet air and wet N₂, indicating the possibility to use wet air instead of wet N₂ for direct synthesis of ammonia at a temperature at or below 400 °C. Although the Faraday efficiencies in our experiments are lower than the high efficiency of 78% when H₂ and N₂ was used as the precursor¹³ but steam instead of H₂, air instead of N₂ were used as the precursors in this study. It is believed that both the formation rate and Faraday efficiency can be improved when better electro-catalysts are identified.

4. Conclusion

In conclusion, after our previous reports on ammonia synthesis directly from air and water at ambient temperature and up to 80 °C,^{2,4} ammonia was also synthesised directly from wet air at high temperature (400 °C). Perovskite oxide Sm_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-δ} was successfully synthesised, showed a conductivity of 1.88 S/cm at 400 °C. Ammonia was successfully synthesised at 400 °C under atmospheric pressure from both wet air and wet nitrogen using

Sm_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-δ} as anode and cathode catalyst. Ammonia formation rates of 9.19×10^{-7} mol s⁻¹ m⁻² and 1.53×10^{-6} mol s⁻¹ m⁻² were obtained at 400 °C when wet air and wet N₂ were introduced into a simple single chamber reactor. These values are more than two orders of magnitude higher than the reported ammonia formation rates when synthesised from N₂ and H₂O at 600 °C.⁹ Our perovskite catalyst is also low cost compared to the Ru/MgO catalyst in previous report⁹ and Pt/C catalysts in our previous study on ammonia synthesis from air and water.^{2, 4} Although the ammonia formation rates were not high enough for mass production, this is a very simple process using low-cost materials. After further investigation and optimisation, we believe ammonia can be synthesised directly from wet air on a large scale to feed the growing world population in the future.

Acknowledgements

The authors thank EPSRC SuperGen XIV 'Delivery of Sustainable Hydrogen' project (Grant No EP/G01244X/1) for funding.

References:

- 1 J. W. Erisman, M. A. Sutton, J. Galloway, Z. Klimont and W. Winiwarter, *Nat. Geosci.*, 2008, **1**, 636-639.
- 2 R. Lan, J. T. S. Irvine and S. W. Tao, *Sci. Repts*, 2013, **3**, 1145.
- 3 http://www.nobelprize.org/nobel_prizes/chemistry/laureates/2007/.
- 4 R. Lan and S. W. Tao, *RSC Adv.*, 2013, **3**, 18016-18021.
- 5 R. Lan, J. T. S. Irvine and S. W. Tao, *Inter. J. Hydrogen Energy*, 2012, **37**, 1482-1494.
- 6 I. A. Amar, R. Lan, C. T. Petit and S. W. Tao, *J. Solid State Electrochem.*, 2011, **15**, 1845-1860.
- 7 S. Giddey, S. P. S. Badwal and A. Kulkarni, *Inter. J. Hydrogen Energy*, 2013, **38**, 14576-14594.
- 8 I. Garagounis, V. Kyriakou, A. Skodra, E. Vasileiou and M. Stoukides, *Front. Energy Res.*, 2014, **2**, 1-10.
- 9 A. Skodra and M. Stoukides, *Solid State Ionics*, 2009, **180**, 1332-1336.
- 10 C. Chen and G. L. Ma, *J. Mater. Sci.*, 2008, **43**, 5109-5114.
- 11 I. A. Amar, R. Lan, C. T. Petit, V. Arrighi and S. W. Tao, *Solid State Ionics*, 2011, **182**, 133-138.
- 12 I. A. Amar, C. T. Petit, L. Zhang, R. Lan, P. J. Skabara and S. W. Tao, *Solid State Ionics*, 2011, **201**, 94-100.
- 13 G. Marnellos and M. Stoukides, *Science*, 1998, **282**, 98-100.
- 14 G. Marnellos, S. Zisekas and M. Stoukides, *J. Catal.*, 2000, **193**, 80-87.
- 15 I. A. Amar, C. T. G. Petit, G. Mann, R. Lan, P. J. Skabara and S. W. Tao, *Inter. J. Hydrogen Energy*, 2014, **39**, 4322-4330.
- 16 G. J. Janz and M. R. Lorenz, *J. Chem. & Eng. Data*, 1961, **6**, 321-323.
- 17 R. I. Olivares, C. Chen and S. Wright, *J. Solar Energy Eng.-Trans. Asme*, 2012, **134**.
- 18 C. Xia, L. Li, Y. Tian, Q. Liu, Y. Zhao, L. Jia and Y. Li, *J. Power Sources*, 2009, **188**, 156-162.
- 19 L. Fan, C. Wang, M. Chen and B. Zhu, *J. Power Sources*, 2013, **234**, 154-174.
- 20 L. Zhang, R. Lan, A. Kraft and S. W. Tao, *Electrochem. Commun.*, 2011, **13**, 582-585.

- 21 R. Lan, K. A. Alkhazmi, I. A. Amar and S. W. Tao, *Electrochim. Acta*, 2014, **123**, 582-587.
- 22 R. Lan, K. A. Alkhazmi, I. A. Amar and S. W. Tao, *Appl. Catal. B: Environ.*, 2014, **152–153**, 212-217.
- 23 G. Xu, R. Liu and J. Wang, *Sci. China Ser. B: Chem.*, 2009, **52**, 1171-1175.
- 24 C. H. Liang, Z. B. Wei, Q. Xin and C. Li, *Appl. Catal. A-General*, 2001, **208**, 193-201.
- 25 W. Rarog-Pilecka, E. Miskiewicz, L. Kepinski, Z. Kaszukur, K. Kielar and Z. Kowalczyk, *J. Catal.*, 2007, **249**, 24-33.
- 26 T. Sugahara and M. Ohtaki, *Appl. Phys. Lett.*, 2011, **99**, 062107.
- 27 W. Wang, X. Cao, W. Gao, F. Zhang, H. Wang and G. Ma, *J. Memb. Sci.*, 2010, **360**, 397-403.

Figure captions

Table 1 Structure parameters of $\text{Sm}_{0.6}\text{Sr}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$.

Fig. 1 The STA analysis of the $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ ash (A) and the $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ powder in N_2 (B).

Fig. 2 XRD pattern of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ at room temperature.

Fig. 3 SEM images of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ powder after calcining at 900 °C for 2 hours. (A) at $\times 2,000$ magnification, (B) at 10,000 magnification.

Fig. 4 The d.c. conductivity of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ in air.

Fig. 5 The current density across the cell in wet air (A) and wet N_2 (B) when applied with different voltages.

Fig. 6 The ammonia formation rate (A) and Faraday efficiency (B) at 400 °C in wet air and wet N_2 when applied with different voltages.

Table 1 Structure parameters of $\text{Sm}_{0.6}\text{Sr}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$.

Atom	Site	Occupancy	x	y	z	$U_{\text{iso}}/\text{\AA}^2$
Sm	1a	0.6	0	0	0	0.0181(5)
Ba	1a	0.4	0	0	0	0.0181(5)
Fe	1b	0.8	0.5	0.5	0.5	0.0171(9)
Cu	1b	0.2	0.5	0.5	0.5	0.0171(9)
O	3c	1	0	0.5	0.5	0.796(27)

Note: Space group $Pm\bar{3}m(221)$; $a = 3.9148(1) \text{ \AA}$, $V = 60.00(1) \text{ \AA}^3$. $R_{\text{wp}} = 6.11\%$, $R_{\text{p}} = 4.48\%$, $\chi_{\text{red}}^2 = 2.52$.

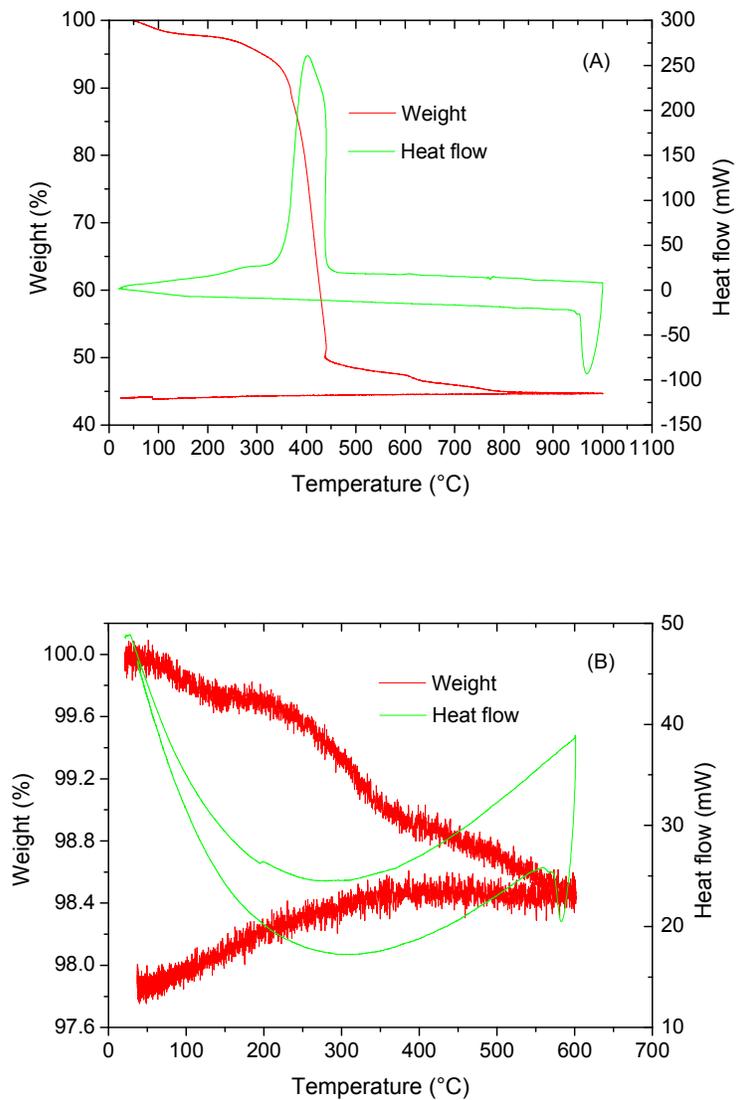


Fig. 1 The STA analysis of the $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ ash (A) and the $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ powder in N_2 (B).

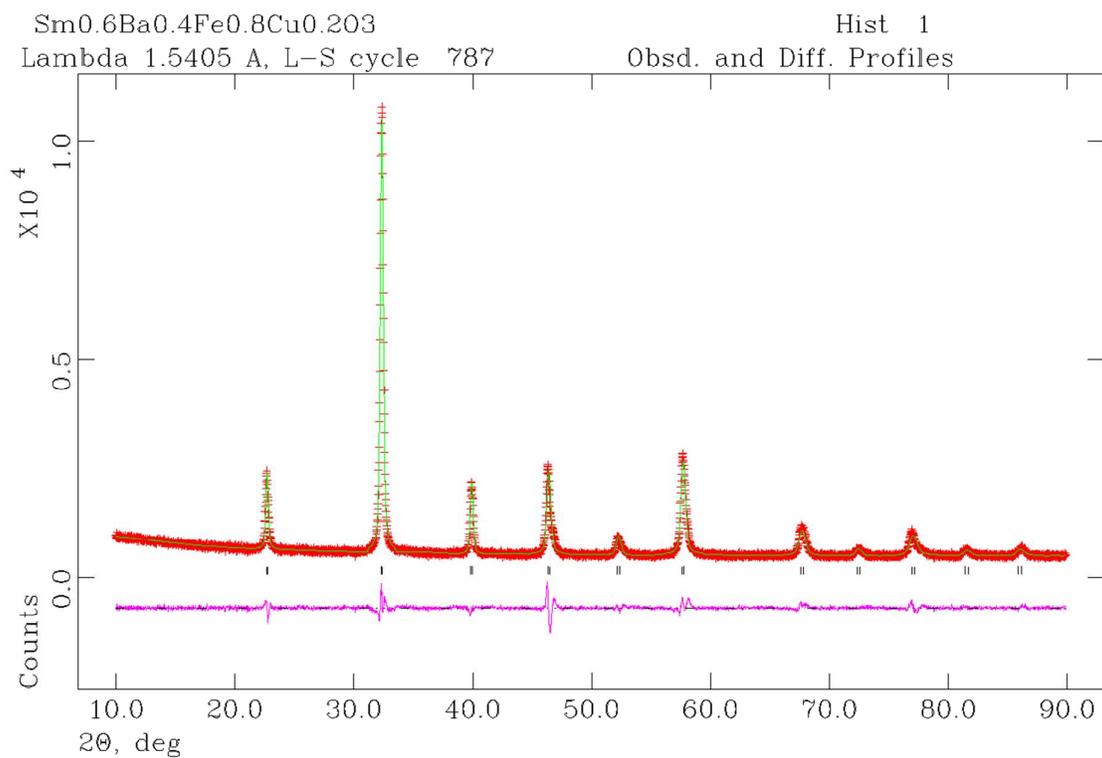


Fig. 2 XRD pattern of Sm_{0.6}Ba_{0.4}Fe_{0.8}Cu_{0.2}O_{3-δ} at room temperature.

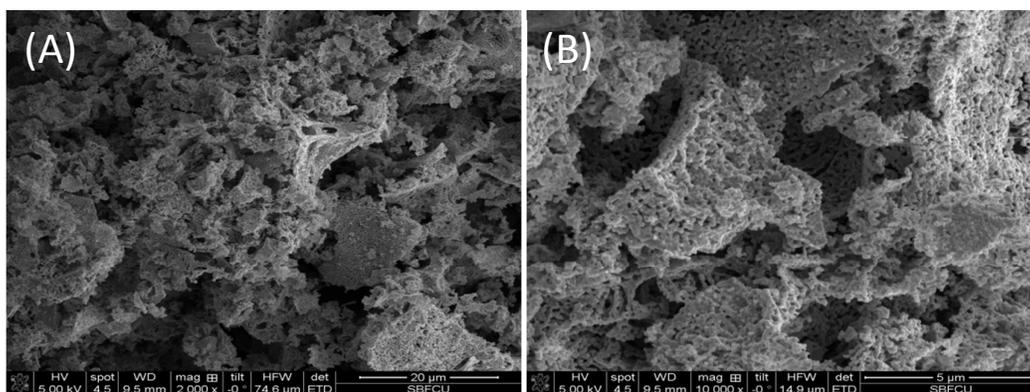


Fig. 3 SEM images of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ powder after calcining at 900 °C for 2 hours. (A) at $\times 2,000$ magnification, (B) at 10,000 magnification.

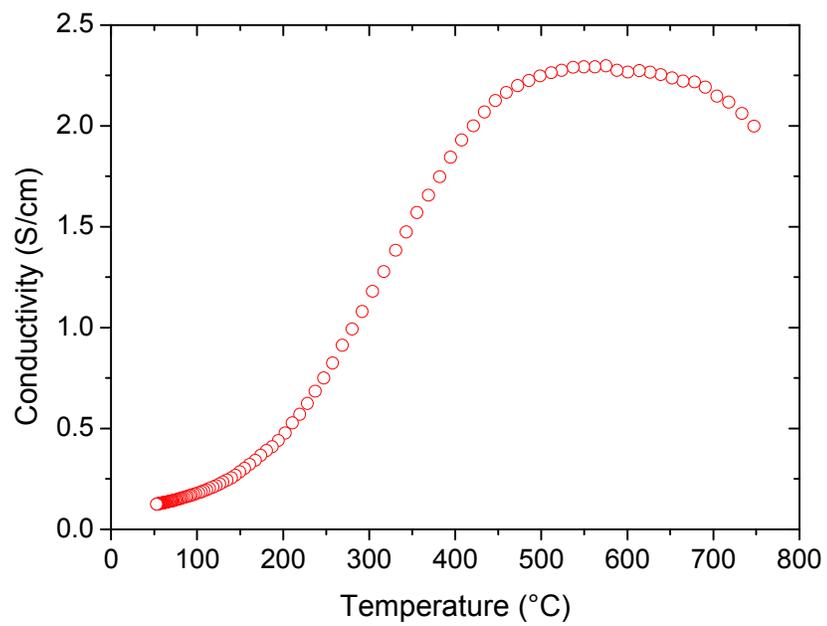


Fig. 4 The d.c. conductivity of $\text{Sm}_{0.6}\text{Ba}_{0.4}\text{Fe}_{0.8}\text{Cu}_{0.2}\text{O}_{3-\delta}$ in air.

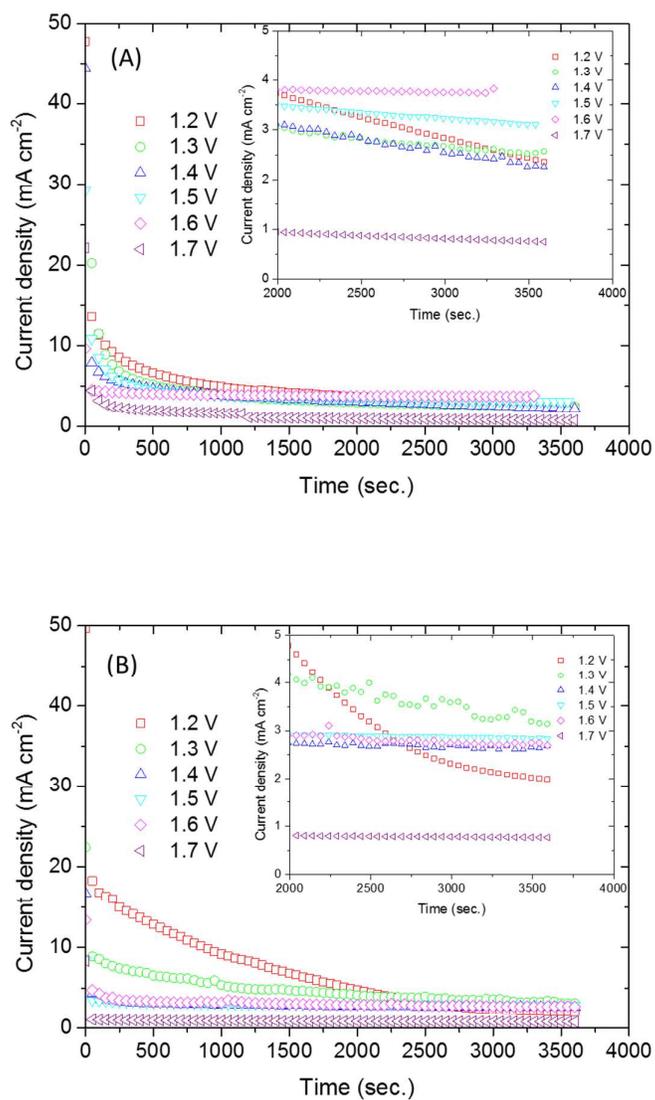


Fig. 5 The current density across the cell in wet air (A) and wet N₂ (B) when applied with different voltages.

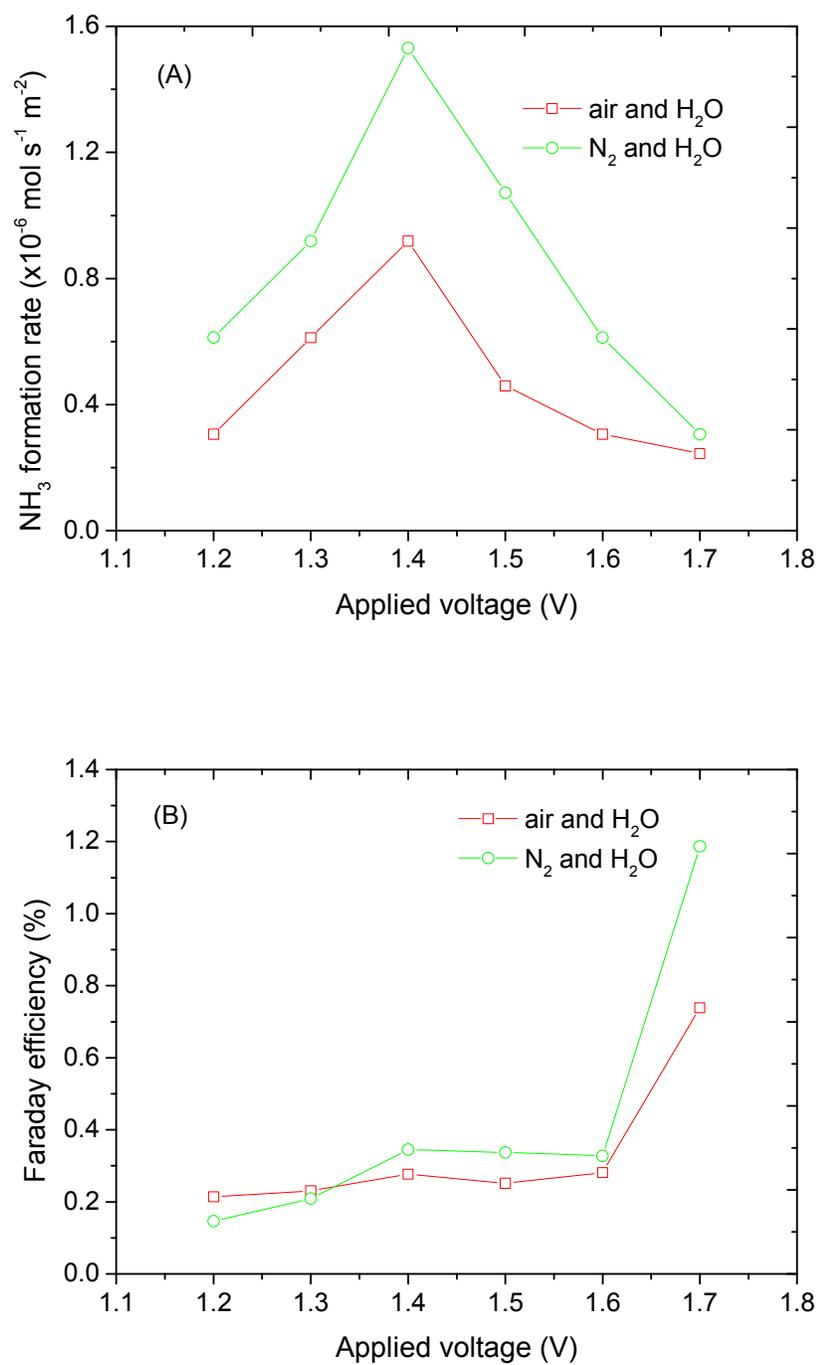


Fig. 6 The ammonia formation rate (A) and Faraday efficiency (B) at 400 °C in wet air and wet N₂ when applied with different voltages.