



**Lewis Acid Zeolites for Tandem Diels-Alder Cycloaddition  
and Dehydration of Biomass-Derived Dimethylfuran and  
Ethylene to Renewable p-Xylene**

Journal:	<i>Green Chemistry</i>
Manuscript ID	GC-ART-09-2015-002164.R1
Article Type:	Paper
Date Submitted by the Author:	06-Oct-2015
Complete List of Authors:	Chang, Chun-Chih; University of Massachusetts, Chemical Engineering Cho, Hong Je; University of Massachusetts, Chemical Engineering Yu, Jingye; University of Pennsylvania, Chemical and Biomolecular Engineering Gorte, Raymond; Structure of Matter (LRSM), Laboratory for Research on the Gulbinski, Jason; University of Delaware, Chemical Engineering Dauenhauer, Paul; University of Minnesota, Chemical Engineering and Materials Science; Fan, Wei; University of Massachusetts, USA, Chemical Engineering

## Lewis Acid Zeolites for Tandem Diels—Alder Cycloaddition and Dehydration of Biomass-Derived Dimethylfuran and Ethylene to Renewable *p*-Xylene†

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Chun-Chih Chang<sup>a,d</sup>, Hong Je Cho<sup>a,d</sup>, Jingye Yu<sup>b,d</sup>, Ray J. Gorte<sup>b,d</sup>, Jason Gulbinski<sup>e,d</sup>, Paul Dauenhauer<sup>c,d</sup> and Wei Fan<sup>\*a,d</sup>


Lewis acid zeolites including Zr-, Sn-, and Ti-BEA were examined for tandem [4+2] Diels—Alder cycloaddition of 2,5-dimethylfuran (DMF) and ethylene to oxanobornene with subsequent dehydration to produce biorenewable *p*-xylene. Zr-BEA (Si/Zr=168) exhibited superior performance with improved recalcitrance to deactivation, which was attributed to its low activity for the hydrolysis of DMF to 2,5-hexanedione and subsequent condensation. Zr-BEA also achieved the highest selectivity to *p*-xylene of 90% at 99% conversion of DMF. For low catalyst loading within a three-phase reactor, the reaction rate to form *p*-xylene was linearly proportional to the number of Lewis acid sites, while high catalyst loading exhibited zero order dependence on Lewis acid sites. A maximum achievable reaction rate was shown consistent with a transition in rate-limiting reactions from dehydration of oxanobornene, the Diels—Alder product, to the Diels—Alder cycloaddition of DMF and ethylene.

### Introduction

*p*-Xylene is an important commodity chemical for the synthesis of terephthalic acid, which is the monomer for the manufacture of polyethylene terephthalate (PET). PET has been widely utilized to commercially manufacture synthetic fibers and plastic bottles due to their outstanding mechanical and chemical properties.<sup>1–3</sup> As the third largest chemical by volume in the world produced from petroleum (catalytic reforming of naphtha) with increasing demand (6–8 % per year),<sup>4</sup> there are now ongoing efforts worldwide for developing alternative routes to produce *p*-xylene from renewable biomass resources.<sup>5–14</sup> For example, Lyons et al. demonstrated that *p*-xylene can be synthesized from ethylene (from dehydration of bio-ethanol) by a multi-step reaction pathway including trimerization of ethylene, Diels—Alder

reaction of 2,4-hexadiene with ethylene and dehydrogenation of 3,6-dimethylcyclohexene; Shiramizu and Toste also reported that *p*-xylene can be selectively produced from 2,5-dimethylfuran (DMF, from hydrogenolysis of cellulosic biomass-derived 5-hydroxymethylfurfural (HMF)) and acrolein (from glycerol, a biodiesel byproduct).<sup>10,12</sup>

In previous studies, we have reported a renewable reaction pathway to produce *p*-xylene from lignocellulosic biomass over solid Brønsted acid catalysts. The Diels—Alder dehydration reaction includes the cycloaddition of biomass-derived dimethylfuran (DMF) with ethylene, and subsequent dehydration of the formed Diels—Alder adduct to *p*-xylene (Scheme 1).<sup>7,8,15–17</sup> Competing reactions include hydrolysis of

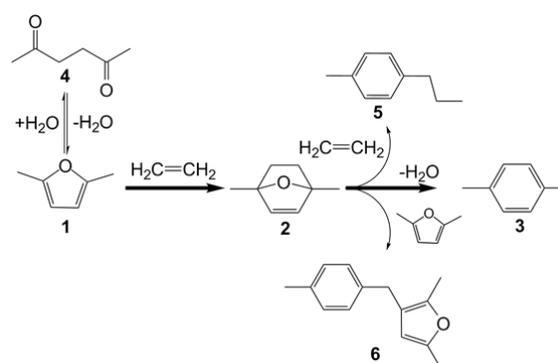

**Scheme 1.** Simplified reaction scheme for synthesis of *p*-xylene from DMF and ethylene. **1**: DMF; **2**: cycloadduct; **3**: *p*-xylene; **4**: 2,5-hexanedione; **5**: representative alkylated product; **6**: representative oligomer.

<sup>a</sup> Department of Chemical Engineering, University of Massachusetts Amherst, 686 N. Pleasant Street, Amherst, MA 01002.

<sup>b</sup> Department of Chemical and Biomolecular Engineering, University of Pennsylvania, 220 S. 33<sup>rd</sup> St., Philadelphia, PA 19104.

<sup>c</sup> Department of Chemical Engineering and Materials Science, University of Minnesota, 421 Washington Ave. SE, Minneapolis, MN, 55455.

<sup>d</sup> Catalysis Center for Energy Innovation, a U.S. Department of Energy – Energy Frontier Research Center. <http://www.efrc.udel.edu/>.

<sup>e</sup> Department of Chemical Engineering, University of Delaware, 150 Academy Street, Newark, Delaware 19716.

\*Corresponding author: Phone: (+1) 413-545-1750. Fax: (+1) 413-545-1647. E-mail: wfan@ecs.umass.edu.

†Electronic Supplementary Information (ESI) available: XRD patterns and diethylether TPD data for Lewis acid zeolites, reaction kinetics from metal oxides, GC/MS data for cycloadduct of DMF and ethylene, data for dehydration of cyclohexanol, and DMF and byproduct distribution of 2,5-hexanedione added reactions for Zr-BEA and Al-BEA. See DOI: 10.1039/x0xx00000x

DMF to 2,5-hexanedione and reactions between the cycloadduct, DMF (oligomers) and ethylene (alkylated products).<sup>16</sup> The proposed process to *p*-xylene can be completely based on biomass resources. DMF can be produced from the hydrolysis of cellulose followed by dehydration of glucose or fructose to HMF, and hydrodeoxygenation of HMF to DMF.<sup>18</sup> Ethylene can be produced from the dehydration of bio-ethanol.<sup>19, 20</sup> We have demonstrated that 90% selectivity to *p*-xylene can be achieved by conducting the tandem Diels–Alder/dehydration reactions over Brønsted acid zeolite catalysts (i.e. Al-BEA zeolite, Si/Al=12.5) in *n*-heptane solvent.<sup>7</sup> Toluene and benzene can also be produced with similar chemistry by starting with 2-methylfuran and furan, respectively.<sup>21</sup> Computational studies including density functional theory (DFT) and quantum mechanics/molecular mechanics (QM/MM) revealed that the formation of oxanorbornene cycloadduct intermediate by the addition of ethylene to DMF is likely not catalyzed by Brønsted acid sites within zeolite catalysts.<sup>8, 22, 23</sup> However, Brønsted acids can effectively catalyze the dehydration of the cycloadduct intermediate and decrease the activation energy from 58–60 kcal/mol to 14–19 kcal/mol, leading to a significantly increased overall reaction rate.<sup>8, 15, 22</sup>

Although Brønsted acid zeolite catalysts exhibit promising performance, the overall reaction rate is limited due to the uncatalyzed Diels–Alder reaction. There are thus persistent needs for improving the overall reaction rate by developing catalysts which can promote the Diels–Alder reaction and more selectively dehydrate to reduce side product formation. Previous studies have suggested that Lewis acids can coordinate with dienes to catalyze the Diels–Alder reaction.<sup>10, 24–27</sup> DFT studies of the production of *p*-xylene from DMF have also suggested that Lewis acids can coordinate with ethylene to catalyze the Diels–Alder reaction to form the cycloadduct intermediate, oxanorbornene.<sup>15, 28</sup> In addition, experimental and theoretical studies have shown that solid Lewis acid catalysts are capable of catalyzing the dehydration of cycloadduct intermediate and other alcohols.<sup>15, 28–30</sup> Using Fe<sup>3+</sup>-exchanged montmorillonite K10 clay as a Lewis acid catalyst for the aromatization of oxabicyclic derivatives has also been reported.<sup>27, 31</sup> Lewis acid zeolite catalysts, in particular Sn-BEA and Zr-BEA, have also shown catalytic activity for the synthesis of terephthalic acid via Diels–Alder reactions with oxidized variants of 5-hydroxymethylfurfural.<sup>3</sup>

Motivated by the existing experimental and theoretical studies, Lewis acid catalysts were employed in this work for producing *p*-xylene from DMF and ethylene through the tandem Diels–Alder/dehydration reaction pathway. We demonstrate that Lewis acid zeolite catalysts are active for producing *p*-xylene. Zr-BEA catalyst, in particular, exhibited a high selectivity of 90% to *p*-xylene and slower deactivation due to the low hydrolysis rate for by-product, 2,5-hexanedione. It was also evidenced that Zr-BEA can moderately enhance the formation of cycloadduct from DMF and ethylene, resulting in the highest measured *p*-xylene production rate.

## EXPERIMENTAL

### Preparation of catalysts

Solid Lewis acid zeolite catalysts employed in this study were prepared according to literature and our previous report based on a seeded growth method developed for Sn-BEA.<sup>32–34</sup> The detailed procedure for the preparation of seed suspension is available in our previous study.<sup>33</sup>

**Preparation of Zr-BEA** Typically, 23.72 g of tetraethylorthosilicate (TEOS, 99%, Alfa Aesar) was added to 27.39 g of tetraethylammonium hydroxide solution (TEAOH, 35 wt.%, SACHEM) and magnetically stirred in a plastic beaker. After a homogeneous solution was obtained (about one hour), 0.3 g of zirconium (IV) oxychloride octahydrate (ZrOCl<sub>2</sub>•8H<sub>2</sub>O, Sigma-Aldrich) was dissolved in 1.92 g water and added dropwise into the silicate solution. The mixture was kept stirring in a fumed hood until the desired amount of water and ethanol (generated from hydrolysis of TEOS) were evaporated. To this solution, 1.712 mL of dealuminated zeolite BEA seed suspension (0.163 g of seed crystal per mL; corresponding to 4.0 wt.% seed with respect to silica) was added and mixed with a plastic spatula. Lastly, 2.36 mL of hydrofluoric acid (49%, Alfa Aesar) was added and mixed with a plastic spatula, and a hard gel was formed. The final composition of the gel was SiO<sub>2</sub>: 0.008 ZrO<sub>2</sub>: 0.56 TEAOH: 0.56 HF: 7.5 H<sub>2</sub>O. The hard gel was transferred to a Teflon lined stainless steel autoclave and heated in a preheated convection oven at 140 °C for four days with 2.0 rpm rotation. The solids were washed with 1.0 L of deionized water by filtration and dried in an 80 °C oven overnight. The organic template was removed by calcining the as-made catalyst at 550 °C with a ramping rate of 1.0 °C/min for 12 h under flowing dry air (Grade 0.1, Middlesex Gases & Technologies, Inc.).

**Preparation of Sn-BEA** Typically, 20.94 g of TEOS was added to 23.02 g of TEAOH solution and magnetically stirred in a plastic beaker. After a homogeneous solution was obtained (about one hour), 0.3 g of tin (IV) chloride hydrate (SnCl<sub>4</sub>•xH<sub>2</sub>O, 34.4 wt. % of tin) was dissolved in 1.96 g water and added dropwise into the silicate solution. The mixture was kept stirring in a fumed hood until the desired amount of water and ethanol were evaporated. To this solution, 1.541 mL of dealuminated zeolite BEA seed suspension (corresponding to 4.0 wt.% seed with respect to silica) was added and mixed with a plastic spatula. Lastly, 1.941 mL of hydrofluoric acid (49%, Alfa Aesar) was added and mixed with a plastic spatula, and a hard gel was formed. The final composition of the gel was SiO<sub>2</sub>: 0.008 SnO<sub>2</sub>: 0.54 TEAOH: 0.54 HF: 7.5 H<sub>2</sub>O. The hard gel was transferred to a Teflon lined stainless steel autoclave and heated in a preheated convection oven at 140 °C for four days with 2.0 rpm rotation. The solids were washed with 1.0 L of deionized water by filtration and dried in an 80 °C oven overnight. The organic template was removed by calcining the as-made catalyst at 550 °C with a ramping rate of 1.0 °C/min for 12 h under flowing dry air.

**Preparation of Ti-BEA** Typically, 24.66 g of TEOS was added to a mixture of 26.76 g of TEOH solution and 4.24 g of hydrogen peroxide solution (H<sub>2</sub>O<sub>2</sub>, 30 %, Fisher) and magnetically stirred in a plastic beaker. After a homogeneous solution was obtained (about one hour), 0.45 g of titanium (IV) ethoxide (Aldrich) was added dropwise into the silicate solution. The mixture was kept stirring in a fumed hood until the desired amount of water and ethanol were evaporated. To this yellow clear solution, 1.708 mL of dealuminated zeolite BEA seed suspension (corresponding to 4.0 wt.% seed with respect to silica) was added and mixed with a plastic spatula. Lastly, 2.306 mL of hydrofluoric acid (49 %, Alfa Aesar) was added and mixed with a plastic spatula, and a hard gel formed. The final composition of the gel was SiO<sub>2</sub>: 0.008 TiO<sub>2</sub>: 0.54 TEOH: 0.54 HF: 7.5 H<sub>2</sub>O. The hard gel was transferred to a Teflon lined stainless steel autoclave and heated in a preheated convection oven at 140 °C for eight days with 2.0 rpm rotation. The solids were washed with 1.0 L of deionized water by filtration and dried in an 80 °C oven overnight. The organic template was removed by calcining the as-made catalyst at 550 °C with a ramping rate of 1.0 °C/min for 12 h under flowing dry air.

**Preparation of Al-BEA** Aluminosilicate zeolite BEA (CP814E, Si/Al=12.5) was obtained from Zeolyst. The catalyst was calcined at 550 °C with a ramping rate of 1.0 °C/min for 12 h under flowing dry air prior to the reaction.

#### Characterizations of the catalysts

The crystalline phase of the Lewis acid catalysts were examined by powder X-ray diffraction (PXRD) on a diffractometer (X'Pert Pro, PANalytic) operated at a voltage of 40 kV and a current of 45 mA with an X'cellerator detector scanning from 4° to 40°. The quantity of Lewis acid sites within the zeolites was determined by diethylether temperature programmed desorption coupled with thermogravimetric analysis (TPD-TGA), with the exception of Ti-BEA. Ti-BEA interacted weakly with the probe molecules, and did not provide characterization of Lewis acid sites. Temperature Programmed Desorption (TPD) and Thermogravimetric Analysis (TGA) experiments were carried out using a CAHN 2000 microbalance mounted within a vacuum chamber that could be evacuated with a diffusion pump.<sup>35</sup> Prior to exposing them to a few hundred Pa of the diethyl ether, the samples were heated in vacuum to 500 °C then cooled to room temperature in vacuo. During TPD-TGA measurements, the sample weights were recorded continuously using the microbalance and the desorbing species were monitored using an SRI quadrupole mass spectrometer (RGA100) at a ramping rate of 10 °C/min. Elemental analyses were carried out in Analytical Geochemistry Lab, Department of Earth Sciences in University of Minnesota using ICP-OES (iCAP 6500 duo view, Thermo Scientific).

#### Reaction experiments

The reactor system schematic is available in our previous work.<sup>8</sup> In typical reactions with DMF (Alfa Aesar), 100 mL of 1.35 M of DMF in n-heptane (Alfa Aesar) with 0.08 M n-

tridecane (Alfa Aesar) was enclosed in a 160 mL bench-top reactor (Parr), and the reaction vessel was purged by nitrogen. The catalyst acid concentration present in the system was defined as the total number of acid sites of the catalyst divided by the reactant volume. The mixture was then stirred at 1000 rpm with a gas entrainment impeller to ensure facile mass transfer. The system was heated to 250 °C and controlled with a 4848 control unit (Parr). The reactor was then pressurized with 38 bar (partial pressure) of ethylene gas (Airgas), and the total pressure of the system was maintained at 62 bar over the reaction period. Liquid was withdrawn by a double block sampling system at designated reaction times. The composition of the sample was then analyzed with an Agilent 6890A gas chromatograph with a Rtx-VMS (Restek) column equipped with a flame ionization detector. The products (DMF, *p*-xylene, 2,5-hexanedione) were identified by comparing the retention times with standard chemicals. Based on the reaction scheme,<sup>16</sup> the concentration of alkylated products was estimated by using the response factor (RF) for 1-methyl-4-propylbenzene, and the concentration of the oligomers was estimated using the additive RF of *p*-xylene and DMF. The oxanorbornene cycloadduct of DMF and ethylene was identified with a GC-MS system (5890 GC/5972 series mass selective detector, HP) and by comparing the electron ionization spectrum to literature.<sup>16</sup> The concentration of the cycloadduct was estimated using the RF for *p*-xylene. The conversion of DMF and selectivity to products were defined as follows

$$X_{\text{DMF}}(\%) = 100 \times \frac{C_{\text{DMF},t_0} - C_{\text{DMF},t}}{C_{\text{DMF},t_0}} \quad (1)$$

$$\text{Selectivity}_i(\%) = 100 \times \frac{C_i - C_{i,t_0}}{\sum_i (C_i - C_{i,t_0})} \quad (2)$$

$$\text{Yield}_i(\%) = 100 \times \frac{C_i}{C_{\text{DMF},t_0}} \quad (3)$$

where *t* is the duration of time after ethylene was added to the reactor, and *C<sub>i</sub>* is concentration of the reactant and products, *i*. For a reaction carried out with 2,5-hexanedione, 0.2 M of 2,5-hexanedione (Alfa Aesar) was added with 1.35 M DMF solution in n-heptane. The reactor was purged with N<sub>2</sub>, heated to 250 °C and held at 250 °C for one hour prior to addition of ethylene (62 bar).

## RESULTS AND DISCUSSION

To demonstrate the catalytic activity of solid Lewis acid catalysts for the Diels–Alder dehydration reaction, siliceous zeolite BEA with substituted metal atoms (Zr-, Sn-, and Ti-BEA) at framework positions were prepared according to the methods reported in literature and applied in the reaction of DMF and ethylene. Other conventional metal oxide catalysts including ZrO<sub>2</sub>, SnO<sub>2</sub>, TiO<sub>2</sub> were also tested in the reaction for comparison. The corresponding XRD patterns for the Lewis acid zeolites used in this study are shown in Figure S1. Typical diffraction peaks for zeolite BEA were observed for all samples, and no impurity phase (i.e., metal oxides) was detected,

indicating that high-quality crystals were obtained. Acid site concentrations of the Lewis acid zeolites were determined by the Si/M ratio obtained from elemental analysis measurement (ICP-OES), and further confirmed by diethylether TPD-TGA measurement (Table 1). It has been shown that diethylether forms 1:1 complex pair with Lewis acid sites (Sn center) in Sn-BEA catalyst, and it desorbs from the Sn site at the temperatures from 350K to 450K. Measuring the weight change between the temperatures can provide the quantity of Lewis acid sites in the sample.<sup>29</sup> Diethylether TPD-TGA results obtained from Sn-BEA, Zr-BEA and Ti-BEA catalysts are shown in Figure S2. As listed in Table 1, the TPD-TGA measurements for Sn- and Zr-BEA indicate good agreement with the elemental analysis, while the measurement for Ti-BEA shows a lower acid site density than the Ti concentration in the sample determined by the elemental analysis (40  $\mu\text{mol/g}$  vs. 129  $\mu\text{mol/g}$ ). This may be due to the weak interaction between diethylether and the Ti site in the Ti-BEA sample, resulting in desorption of the probe molecule from the sample in vacuo prior to heating. For Al-BEA, isopropylamine TPD-TGA was utilized to obtain the Brønsted acid site concentration.<sup>21</sup> The quantity of Brønsted acid sites in Al-BEA (620  $\mu\text{mol/g}$ ) was lower than the Al concentration (1230  $\mu\text{mol/g}$ ), indicating the presence of extra framework Al in the sample. Contribution from extra framework Al species was neglected due to low activity from  $\text{Al}_2\text{O}_3$  according to our previous report.<sup>7</sup> For the reaction rate calculations, the acid site concentrations determined by TPD-TGA analysis were used. Due to weak adsorption of diethylether on Ti-BEA, the Ti concentration determined by elemental analysis was used in the reaction rate calculations.

Figure 1 depicts the temporal profiles of yield and selectivity in the reaction to *p*-xylene with respect to DMF conversion over different catalysts at the same acid site concentration (1.0 mM) in the reaction system (1.35 M DMF in *n*-heptane and 62 bar of ethylene) at 250 °C. Surprisingly, all considered Lewis acid zeolites are capable of catalyzing the reaction to produce *p*-xylene. This activity was attributed to the Lewis acidity from the isolated metal atoms located in the zeolite frameworks, as metal oxides ( $\text{ZrO}_2$ ,  $\text{SnO}_2$ , and  $\text{TiO}_2$ ) and pure siliceous BEA did not show significant catalytic activity


**Table 1.** Acid site density of the zeolites

Catalyst	Acid site density ( $\mu\text{mol/g}$ )		
	Si/T ICP	ICP	Chemical TPD <sup>b</sup>
Zr-BEA	168	98	95
Sn-BEA	126	130	120
Ti-BEA	128	129	40
Al-BEA	12.5 <sup>a</sup>	1230	620 <sup>c</sup>

<sup>a</sup>Zeolyst

<sup>b</sup>Diethylether TPD except for otherwise noted

<sup>c</sup>isopropylamine TPD for Brønsted acid sites

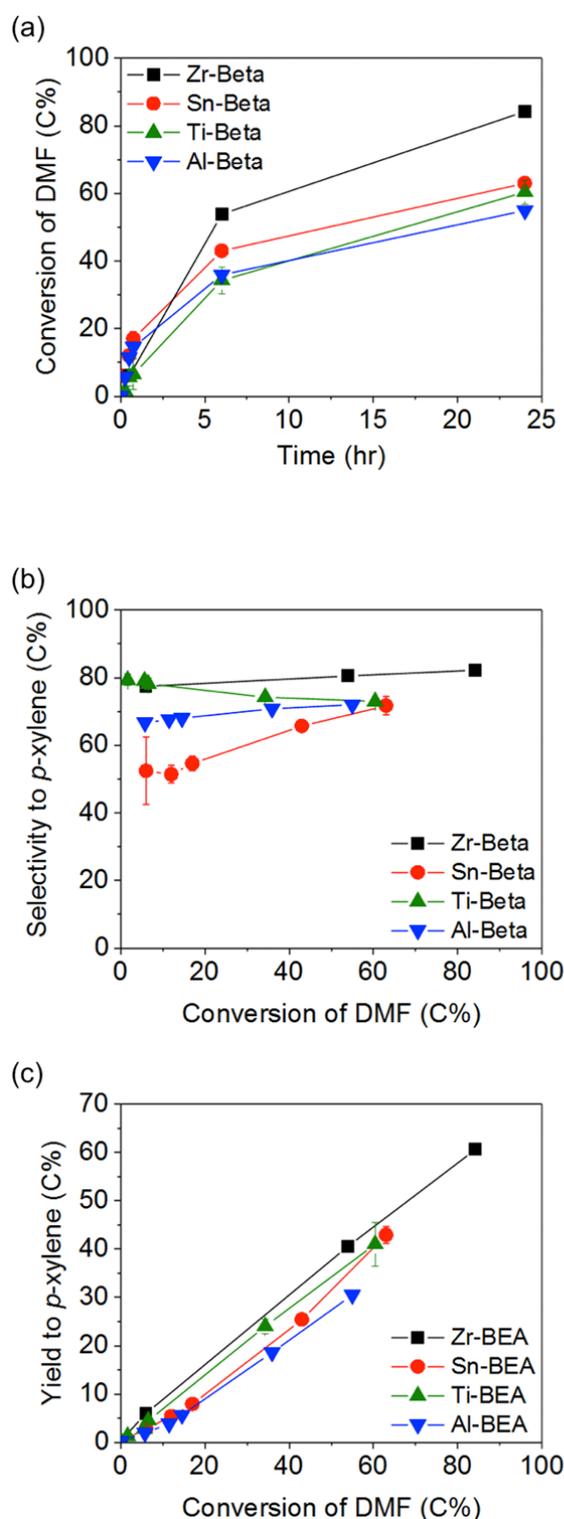

**Figure 1.** (a) Kinetics of DMF conversion at 250 °C. (b) Selectivity and (c) yield to *p*-xylene as a function of DMF conversion for the reaction of DMF and ethylene at 1.0 mM acid loading of Sn-BEA, Zr-BEA, Ti-BEA, and Al-BEA.


**Table 2.** Summary of reaction results for the catalysts<sup>a</sup>

Catalyst	Rate of <i>p</i> -Xylene Production (mM/hr)	DMF Conversion after 24 hr	<i>p</i> -Xylene Yield after 24 hr
Al-BEA	122 ± 11.0	55 ± 3.7	30 ± 0.5
Sn-BEA	113 ± 6.8	63 ± 0.1	43 ± 1.8
Zr-BEA	121 ± 4.9	83 ± 1.6	61 ± 1.5
Ti-BEA	65 ± 11.2	60 ± 3.5	41 ± 4.5
Sn-MFI	8	27	17
SnO <sub>2</sub>	0.6	2	0.3
ZrO <sub>2</sub>	0.7	2	0.5
TiO <sub>2</sub>	1.1	3	1.4

<sup>a</sup>Reaction conditions: 1.0 mM acid (0.8 g for metal oxides), 1.35 M DMF in *n*-heptane, 62 bar ethylene, at 250 °C

(Figure S3).<sup>8</sup> Among the tested catalysts, Zr-BEA exhibited superior performance with 80% selectivity to *p*-xylene at 80% conversion of DMF (Figure 1b) in 24 hr. Sn-, Ti-, and Al-BEA, however, deactivated noticeably faster, and only achieved about 60% DMF conversion after 24 hours of reaction with lower selectivity to *p*-xylene. Furthermore, Zr-BEA yielded ~33% more *p*-xylene than Al-BEA at 60% conversion (Figure 1c). It is worth noting that the activity of Sn-MFI was considerably lower (8 mM/hr; Table 2) at identical conditions, as it converted less than 20% of DMF after 24 hr of reaction, which highlights the uniqueness of zeolite BEA structure for this reaction. The result is consistent with our previous report which suggested the small micropore structure of ZSM-5, an aluminum analog of Sn-MFI, is not favorable for the reaction.<sup>7</sup> This implies either the Diels–Alder reaction could not be catalyzed within the framework or the formed cycloadduct intermediate could not easily diffuse within the micropore structure of MFI zeolite.

To further understand the high selectivity to *p*-xylene over Zr-BEA, the byproduct distributions for the reaction of DMF and ethylene over Lewis acid zeolite catalysts and Al-BEA were measured and shown in Figure 2. Sn-BEA preferentially catalyzes the side reactions and produces more hydrolysis product, 2,5-hexanedione, and oligomers at lower conversion, which explains the low selectivity to *p*-xylene for Sn-BEA. Zr-BEA, however, is able to minimize the hydrolysis of DMF, with low 2,5-hexanedione yield at all extents of conversion (Figure 2a). Zr-BEA also minimizes the formation of oligomers (Figure 2b) but promotes the reaction between cycloadduct and ethylene, giving the highest yield of alkylated products (Figure 2c). Al-BEA, on the other hand, produces only small amounts of oligomeric products and more 2,5-hexanedione and alkylated products. At low conversion of DMF, strong Brønsted acidity of Al-BEA can effectively catalyze the hydrolysis reaction of DMF, which explains the even lower *p*-xylene selectivity at high catalyst loading shown later (Figure 3). All results suggest that using Zr-BEA is moderately beneficial for the production of *p*-xylene compared with Al-BEA due to its low activity for catalyzing side reaction of the hydrolysis of DMF. The reaction results reveal that the characteristics of the acid type can manipulate the product distributions by affecting

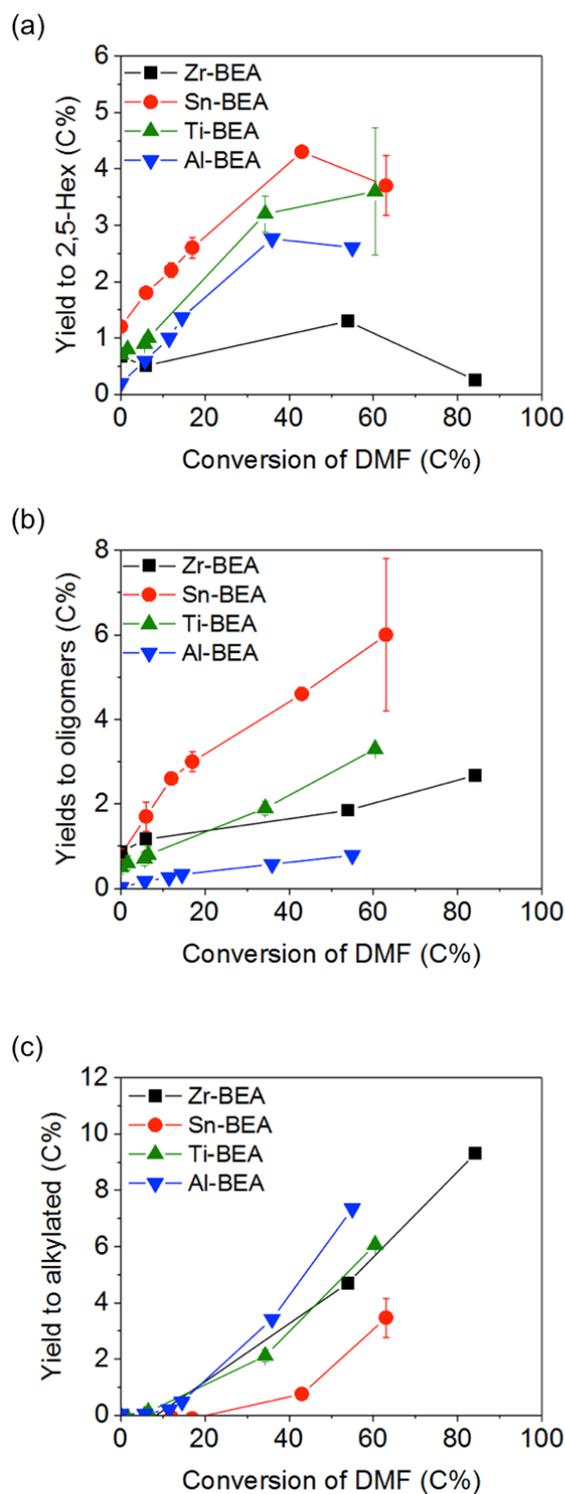


**Figure 2.** Yield of (a) 2,5-hexanedione, (b) oligomers and (c) alkylated side products as a function of DMF conversion for the reaction of DMF in heptane with ethylene (62 bar) at 250 °C with Sn-BEA, Zr-BEA, and Ti-BEA as well as Al-BEA catalysts at 1.0 mM acid concentration.

the reaction rates between the competing reaction pathways, while the selectivity towards *p*-xylene for all catalysts are not significantly different at high conversion of DMF.


To understand the effect of active site concentration, Zr-BEA and Al-BEA catalysts were compared at high catalyst loading (acid site concentration of 3.5 and 3.1 mM, respectively). As shown in Figure 3, it was found that the kinetics of DMF conversion and overall *p*-xylene yield were similar between Zr-BEA and Al-BEA, but the selectivity to *p*-xylene for Zr-BEA was significantly higher at low conversion (80% vs. 60%). Differences in selectivity to *p*-xylene were larger when compared at low acid site loading (acid site concentration of 1.0 mM), which appears due to the low activity of Zr-BEA for catalyzing the hydrolysis reaction of DMF. Zr-BEA exhibited the highest selectivity to *p*-xylene (~90 %) at full conversion of DMF at the acid site concentration of 3.5 mM, which was similar to the previously reported selectivity to *p*-xylene achieved with Al-BEA.<sup>7</sup>

Figure 4 shows the rate of production of *p*-xylene versus acid site concentration for different catalysts. Reaction rates were deliberately presented on a volumetric basis of mM/hr (rather than TOF), due to previous work which indicated the overall reaction was limited by either Diels–Alder cycloaddition or dehydration depending on the active site concentration.<sup>7, 8, 22</sup> At low acid site concentration, it was found that the rate of *p*-xylene production is proportional to the acid concentration and reaches a maximum when the acid site concentration is higher than ~2.5 mM for both Brønsted acid, Al-BEA, and Lewis acid zeolites, Sn-BEA and Zr-BEA. This is consistent with our recent report on the kinetic study for the same system using Brønsted acid zeolite, zeolite Y.<sup>22</sup> The kinetic behavior and rate dependence on acid site concentration can be interpreted as a transition in the rate controlling reaction. The overall reaction from DMF and ethylene to *p*-xylene is a sequence of Diels–Alder cycloaddition of ethylene and DMF followed by subsequent dehydration of the cycloadduct. Similar to the Brønsted acid zeolite catalysts, at low Lewis acid site concentration, the overall rate might be controlled by dehydration reaction due to insufficient quantity of catalytic sites; at high Lewis acid site loadings, the reaction could be limited by the cycloaddition reaction, which results in the plateau (i.e. a maximum reaction rate) of *p*-xylene production.

The activity of the catalysts was compared using the turnover frequencies (TOF) calculated within the dehydration-limited region (linear dependent region, <2.5 mM acid sites in Figure 4) using the production rate of *p*-xylene normalized to the amount of acid sites of the catalysts (only Brønsted acid sites were considered for Al-BEA). Interestingly, Zr-BEA exhibited higher TOF ( $121 \pm 4.9 \text{ hr}^{-1}$ ) than Sn-BEA ( $113 \pm 6.8 \text{ hr}^{-1}$ ) and Ti-BEA ( $65 \pm 11 \text{ hr}^{-1}$ ), and was similar to Al-BEA ( $122 \pm 11 \text{ hr}^{-1}$ ) as shown in Table 2. The results suggest that Zr-BEA is an efficient catalyst for the sequential reaction to produce *p*-xylene. The result was unexpected since it has been known that Lewis acid zeolites are not efficient dehydration catalysts for several alcohols compared with Brønsted acid zeolites.<sup>35</sup>

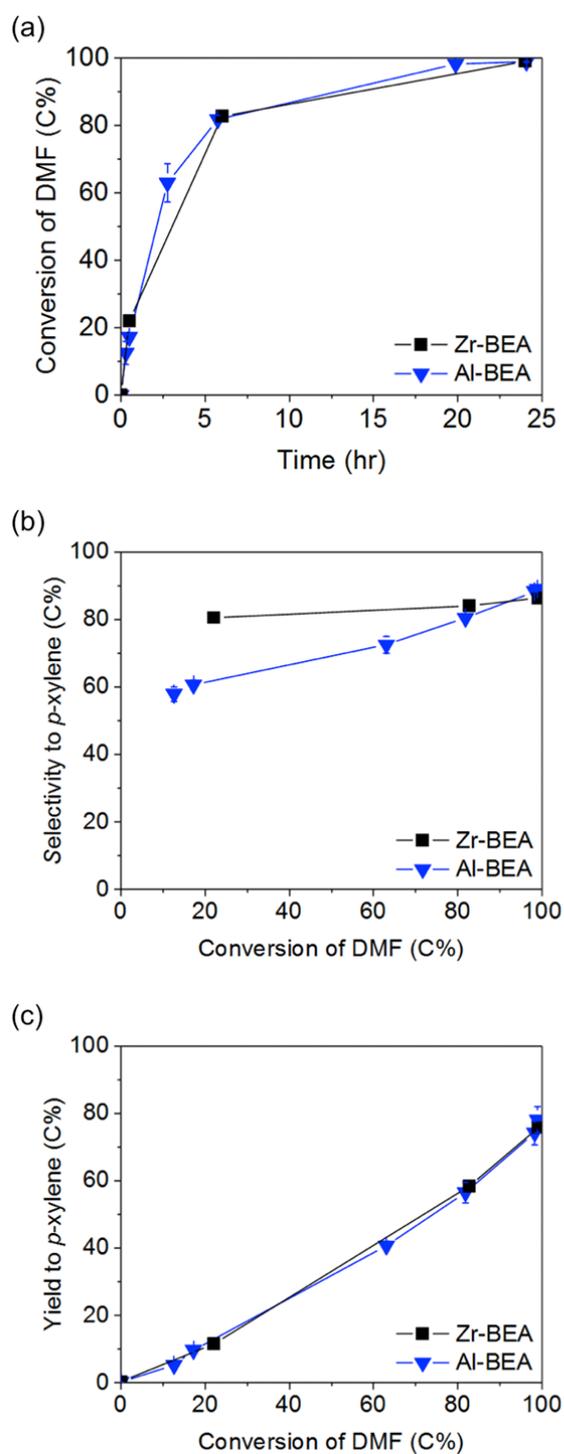

**Figure 3** (a) Kinetics of conversion of DMF, (b) selectivity, and (c) yield to *p*-xylene as a function of DMF conversion for the reaction of 1.35 M DMF in heptane and 62 bar of ethylene at 250 °C with high acid loading of Zr-BEA (3.5 mM) and Al-BEA (3.1 mM).

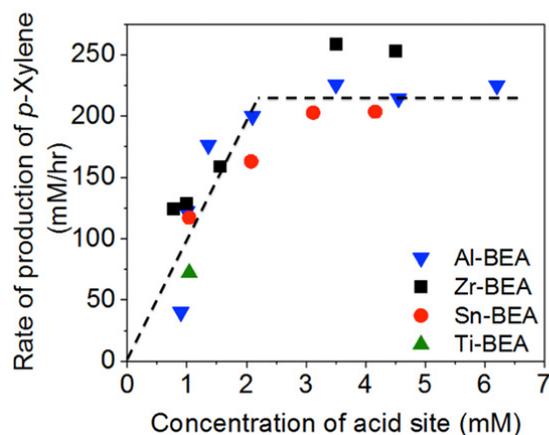


**Figure 4.** *p*-Xylene production rate versus the active site concentration in *n*-heptane for Zr-BEA, Sn-BEA, Ti-BEA and Al-BEA for the reaction of DMF with ethylene (62 bar) at 250 °C. Initial catalytic rates were calculated at < 20% conversion of DMF. The dashed line is provided as a guide to the eyes.

Our control experiment for dehydration of cyclohexanol to cyclohexene using Al-BEA and Zr-BEA also indicates that Al-BEA is generally superior for dehydration reactions (Figure S4). Further study on the catalytic activity of Zr-BEA for the dehydration of cycloadduct to *p*-xylene is necessary in order to further improve the catalytic system.

Despite significant catalytic differences under dehydration-controlling reaction conditions, only subtle differences were observed between Lewis acid catalysts and Brønsted acid zeolites within the “plateau region” (catalyst independent region, >2.5 mM acid sites in Figure 4) where the Diels–Alder reaction controls the overall rate. Comparing the formation rates of *p*-xylene, Zr-BEA exhibited about 10–20% higher production rate than Sn-BEA and Al-BEA, which might indicate a slight enhancement in catalysis of the Diels–Alder reaction. However, the enhancement of the overall reaction with Lewis acids is minor; variation of the Lewis acid site concentration for either Sn-BEA or Zr-BEA (3.5–5.0 mM acid sites in Figure 3) did not result in measurable differences in overall rate.


To confirm the limited catalytic activity of Zr-BEA for the Diels–Alder reaction, the concentration of cycloadduct produced from the Diels–Alder reaction during the reaction was monitored at low catalyst loadings. The formation of the DMF/ethylene cycloadduct was confirmed by GC/MS (Figure S5). As shown in Figure 5, the Lewis acid zeolites are moderately more active to catalyze the Diels–Alder reaction compared to Al-BEA, and they produce slightly higher cycloadduct intermediate concentration during the tandem reaction than Al-BEA. In particular, Zr-BEA produced the most cycloadduct intermediate throughout the reaction while exhibiting the same initial production rate of *p*-xylene as Al-BEA (Figure 3). The results suggest that the Zr center is moderately effective for the cycloaddition reaction and less efficient for dehydration reaction compared to Al-BEA.

In addition to the moderately improved production rate of *p*-xylene, Zr-BEA also exhibited slower deactivation compared

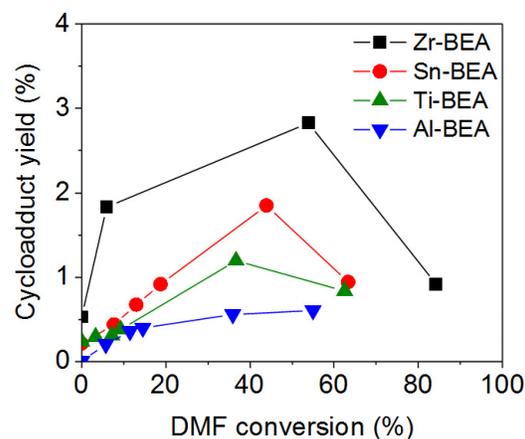

**Figure 5.** Yield of cycloadduct versus DMF conversion (1.35 M DMF in heptane, 250 °C, 62 bar ethylene). The concentration of cycloadduct was estimated by using the response factor of *p*-xylene. The acid concentration is 1.0 mM for all.

to other Lewis acid zeolites and Al-BEA as shown in Figure 1a. In the plot of selectivity to *p*-xylene (Figure 1b), it was observed that both Lewis and Brønsted acid zeolite catalysts exhibit counter-intuitive behavior of increasing selectivity to *p*-xylene with DMF conversion. With the Zr-BEA catalyst, the selectivity to *p*-xylene at the DMF conversion of 20% is slightly lower than 80%, while it increases to 80% at higher conversion. This phenomenon has been observed with the Brønsted acid zeolite, Al-BEA, and was attributed to the equilibrium-driven formation of DMF from its hydrolysis byproduct, 2,5-hexanedione, followed by the formation of the thermodynamically stable final product, *p*-xylene.<sup>7</sup> It has been suggested by Do et al. that 2,5-hexanedione formed from the hydrolysis of DMF can cause catalyst deactivation by forming insoluble surface condensates via acid catalyzed aldol-type reactions.<sup>16</sup> In order to further understand the effects of 2,5-hexanedione on the deactivation of zeolite catalysts in the reaction, 2,5-hexanedione (0.2 M) was intentionally added in the reaction mixture as a reactant with Zr-BEA and Al-BEA catalysts (at 1.0 mM acid site concentration). The reaction mixture was well mixed and heated at 250 °C under nitrogen for one hour prior to the addition of ethylene. The changes in the concentration of 2,5-hexanedione and *p*-xylene with reaction time are shown in Figure 6. It was found that with increasing the temperature, the concentration of 2,5-hexanedione quickly decreased over both Zr-BEA and Al-BEA catalysts. After one hour at 250 °C, the concentration of 2,5-hexanedione was 0.05 M for Al-BEA catalyst and 0.1 M for Zr-BEA catalyst, indicating a faster reaction rate of 2,5-hexanedione over the Brønsted acid zeolite catalyst. After the introduction of ethylene one hour into the experiment, *p*-xylene was produced by both catalysts with Zr-BEA exhibiting a significantly higher *p*-xylene formation rate than Al-BEA (56 mM/hr vs. 35 mM/hr). However, the production rates of *p*-xylene were significantly lower than the rate achieved without

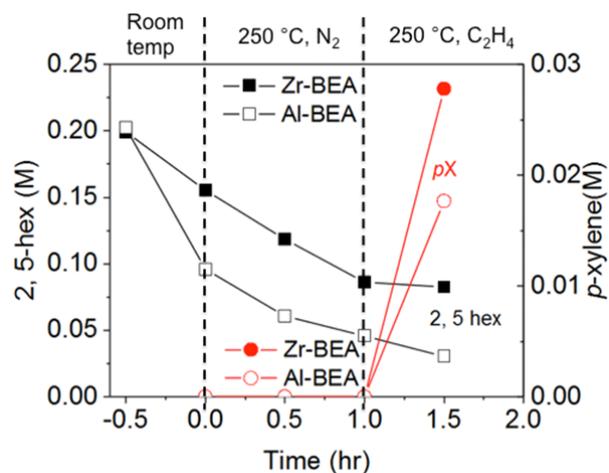


**Figure 6.** The concentration evolution of 2,5 hexanedione (2,5-hex) and *p*-xylene with time for the deactivation-simulated reaction with 2,5 hexanedione added with DMF as reactant for Al-BEA and Zr-BEA. The reaction mixture was heated at 250 °C under N<sub>2</sub> for 1 h before ethylene (62 bar of total pressure) was introduced into the reactor. Acid concentration is 1 mM in the system.

adding 2,5-hexanedione at the beginning of the reaction (120 mM/hr). In addition, it was observed that during the reaction the concentration of DMF does not increase with the decrease of 2,5-hexanedione, which indicates that 2,5-hexanedione did not undergo dehydration to form DMF under the reaction conditions (Figure S6a).

The results clearly suggest that the addition of 2,5-hexanedione did indeed cause catalyst deactivation, in particular for the Brønsted acid zeolite catalyst, Al-BEA. Zr-BEA, however, deactivated slower under the same conditions, which could be due to weaker acid sites on Zr-BEA compared to Al-BEA that are not efficient at catalyzing the condensation reactions of 2,5-hexanedione. The longer catalyst life (slower deactivation) of Zr-BEA may therefore be attributed to: (1) a slower production rate of 2,5-hexanedione (Figure 2a), and (2) weaker acid sites that are not efficient for catalyzing condensation reactions of 2,5-hexanedione (Figure 6).

The cycloaddition/dehydrative aromatization chemistry can be extended to 2-methylfuran (MF) and furan to produce toluene and benzene.<sup>7, 17, 21</sup> Due to the lack of protecting methyl groups on the furan  $\alpha$ -carbon, the yields of toluene and benzene were generally lower than the reaction for producing *p*-xylene from DMF. As shown in Figure 7, the conversion of MF and yield of toluene achieved over Zr-BEA catalyst were slightly higher than Al-BEA after a 24 hour reaction. However, the selectivity to toluene was similar, which indicates that Zr-BEA can prevent fast catalyst deactivation but does not significantly enhance the production rate of toluene (70 vs. 68 mM/hr toluene production rate for Zr-BEA and Al-BEA, respectively). In the reaction with furan, Zr-BEA only produced ~5% of benzene after 24 hr reaction (~70 % conversion), revealing that Lewis acid zeolite (Zr-BEA) is not effective in improving the yield of benzene. Overall, the performance of Zr-BEA was slightly better in furan and MF reactions in terms

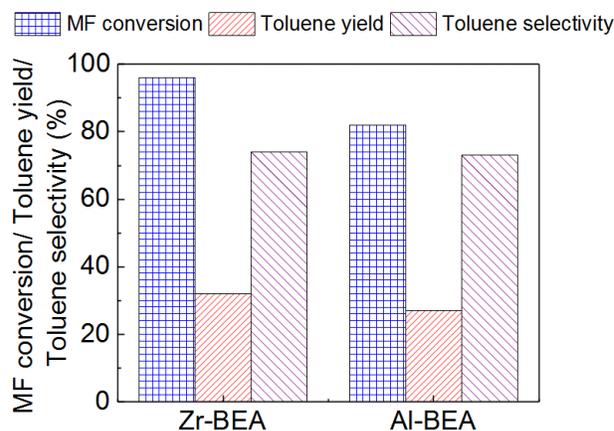

**Figure 7.** MF conversion, toluene yield, and toluene selectivity for the reaction of MF and ethylene with Zr-BEA and Al-BEA after 24 hr reaction. The reaction involves 1.35 M of MF in *n*-heptane with 62 bar of ethylene at 250 °C. The acid concentration for both catalysts is 0.8 mM.

of catalyst life, but they exhibited no significant difference with regard to selectivity to benzene and toluene when compared with Al-BEA.

## Conclusions


Solid Lewis acid zeolites including Zr-, Sn-, and Ti-BEA were evaluated in *p*-xylene production from DMF and ethylene. Lewis acid zeolites were shown to catalyze the Diels–Alder addition/dehydration reactions. It was also found that Lewis acid zeolites exhibit longer lifetime than Al-BEA, in particular Zr-BEA shows the best performance with higher turnover frequency and slower deactivation, which could be attributed to its low selectivity to hydrolysis product, 2,5-hexanedione, and weak acid site nature which prevents the polymerization of 2,5-hexanedione. It was also demonstrated that the production rate of *p*-xylene was dependent of the total amount of Lewis acid catalyst at low loading and independent at high loading due to the nature of the tandem reaction, which was similar to the behavior of Brønsted acid zeolite catalysts. Finally, it was revealed that Zr-BEA moderately promoted the Diels–Alder cycloaddition reaction by producing more oxanorbornene while being a less efficient dehydration catalyst; this resulted in a mild enhancement of *p*-xylene production by ~10–20% compared to Al-BEA. Current findings can serve as a guide to design efficient and long-lasting catalysts for the tandem Diels–Alder cycloaddition/dehydration reactions.

## Acknowledgements

The authors acknowledge financial support from Center for Catalysis and Energy Innovation, an Energy Frontier Research Center funded by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences under award number DE-SC0001004.

## References

1. R. A. F. Tomás, J. C. M. Bordado and J. F. P. Gomes, *Chem. Rev.*, 2013, 113, 7421-7469.
2. Y. Tachibana, S. Kimura and K.-i. Kasuya, *Sci. Rep.*, 2015, 5, 8249.
3. J. J. Pacheco and M. E. Davis, *Proc. Nat. Acad. Sci.*, 2014, 111, 8363-8367.
4. P. Wantanachaisaeng and K. O'Neil, Capturing opportunities for para-xylene production, UOP LLC, 2007.
5. M. N. Masuno, P. B. Smith, D. A. Hucul, K. Brune, R. L. Smith, J. Bissell, D. A. Hirsch-Weil and E. J. Stark, Methods of producing *p*-xylene from 2,5-hexanedione and ethylene in the presence of catalysts and solvents, US Patent 8889938B2, 2014.
6. B. Saha and M. M. Abu-Omar, *ChemSusChem*, 2015, 8, 1133-1142.
7. C.-C. Chang, S. K. Green, C. L. Williams, P. J. Dauenhauer and W. Fan, *Green Chem.*, 2014, 16, 585-588.
8. C. L. Williams, C.-C. Chang, P. Do, N. Nikbin, S. Caratzoulas, D. G. Vlachos, R. F. Lobo, W. Fan and P. J. Dauenhauer, *ACS Catal.*, 2012, 2, 935-939.
9. Y.-T. Cheng, Z. Wang, C. J. Gilbert, W. Fan and G. W. Huber, *Angew. Chem., Int. Ed.*, 2012, 51, 11097-11100.
10. M. Shiramizu and F. D. Toste, *Chem. Eur. J.*, 2011, 17, 12452-12457.
11. D. Wang, C. M. Osmundsen, E. Taarning and J. A. Dumesic, *ChemCatChem*, 2013, 5, 1-8.
12. T. W. Lyons, D. Guironnet, M. Findlater and M. Brookhart, *J. Am. Chem. Soc.*, 2012, 134, 15708-15711.
13. M. W. Peters, J. D. Taylor, M. Jenni, L. E. Manzer and D. E. Henton, Integrated process to selectively convert renewable isobutanol to *p*-xylene, US Patent 20110087000, 2011.
14. T. A. Brandvold, Carbohydrate route to para-xylene and terephthalic acid, US Patent 20100331568, 2010.
15. N. Nikbin, P. T. Do, S. Caratzoulas, R. F. Lobo, P. J. Dauenhauer and D. G. Vlachos, *J. Catal.*, 2013, 297, 35-43.
16. P. T. M. Do, J. R. McAtee, D. A. Watson and R. F. Lobo, *ACS Catal.*, 2013, 3, 41-46.
17. D. Wang, C. M. Osmundsen, E. Taarning and J. A. Dumesic, *ChemCatChem*, 2013, 5, 2044-2050.
18. R. A. Sheldon, *Green Chem.*, 2014, 16, 950-963.
19. A. Morschbacker, *Polym. Rev.*, 2009, 49, 79-84.
20. A. P. Kagyrmánova, V. A. Chumachenko, V. N. Korotkikh, V. N. Kashkin and A. S. Noskov, *Chem. Eng. J.*, 2011, 176-177, 188-194.
21. S. K. Green, R. E. Patet, N. Nikbin, C. L. Williams, C.-C. Chang, J. Yu, R. J. Gorte, S. Caratzoulas, W. Fan, D. G. Vlachos and P. J. Dauenhauer, *Appl. Catal. B.*, 2016, 180, 487-496.
22. R. E. Patet, N. Nikbin, C. L. Williams, S. K. Green, C.-C. Chang, W. Fan, S. Caratzoulas, P. J. Dauenhauer and D. G. Vlachos, *ACS Catal.*, 2015, 5, 2367-2375.
23. Y.-P. Li, M. Head-Gordon and A. T. Bell, *J. Phys. Chem. C*, 2014, 118, 22090-22095.
24. M. V. Gómez, Á. Cantín, A. Corma and A. de la Hoz, *J. Mol. Catal. A: Chem.*, 2005, 240, 16-21.
25. Y. Hayashi, M. Nakamura, S. Nakao, T. Inoue and M. Shoji, *Angew. Chem., Int. Ed.*, 2002, 41, 4079-4082.
26. R. M. Dessau, *J. Chem. Soc., Chem. Commun.*, 1986, 1167-1168.
27. P. Vogel, J. Cossy, J. n. Plumet and O. n. Arjona, *Tetrahedron*, 1999, 55, 13521-13642.
28. N. Nikbin, S. Feng, S. Caratzoulas and D. G. Vlachos, *J. Phys. Chem. C*, 2014, 118, 24415-24424.
29. S. Roy, K. Bakhmutsky, E. Mahmoud, R. F. Lobo and R. J. Gorte, *ACS Catal.*, 2013, 3, 573-580.
30. S. Roy, G. Mpourmpakis, D.-Y. Hong, D. G. Vlachos, A. Bhan and R. J. Gorte, *ACS Catal.*, 2012, 2, 1846-1853.
31. D. D. Claeys, C. V. Stevens, B. I. Roman, P. Van De Caveye, M. Waroquier and V. Van Speybroeck, *Org. Biomol. Chem.*, 2010, 8, 3644-3654.
32. Y. Zhu, G. Chuah and S. Jaenicke, *Chem. Commun.*, 2003, 2734-2735.
33. C.-C. Chang, Z. Wang, P. Dornath, H. J. Cho and W. Fan, *RSC Adv.*, 2012, 2, 10475-10477.
34. T. Blasco, M. A. Cambor, A. Corma, P. Esteve, A. Martinez, C. Prieto and S. Valencia, *Chem. Commun.*, 1996, 2367-2368.
35. J. Luo, J. Yu, R. J. Gorte, E. Mahmoud, D. G. Vlachos and M. A. Smith, *Catal. Sci. Tech.*, 2014, 4, 3074-3081.

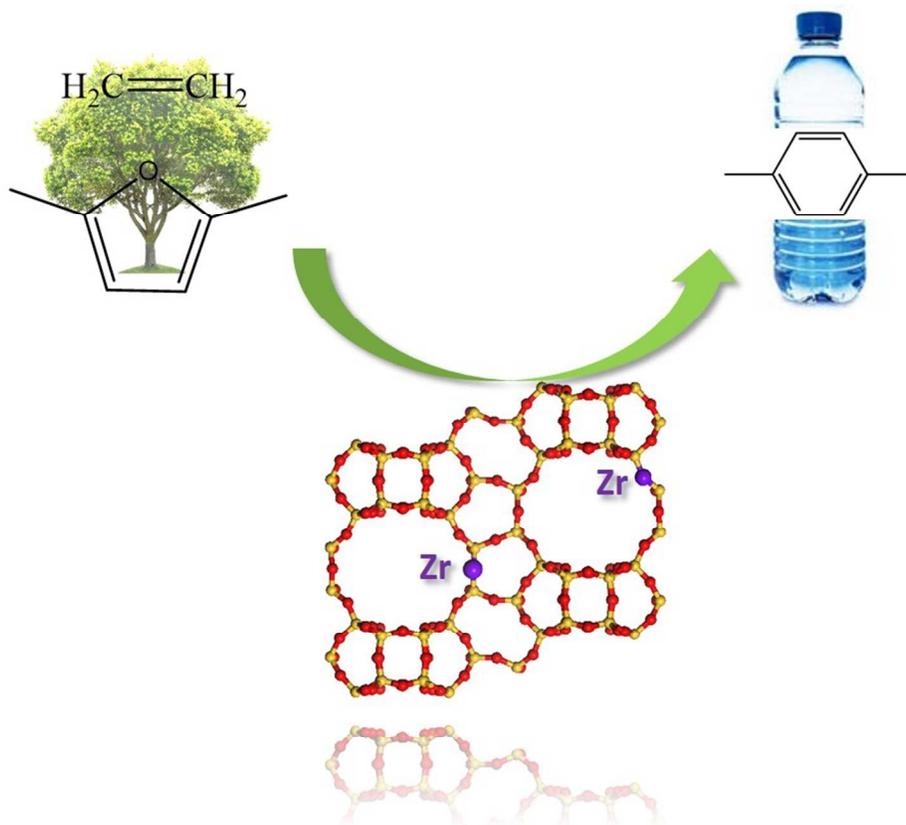

p-Xylene, the precursor for PET bottles, was synthesized by [4+2] cycloaddition of biomass-derivable ethylene and dimethylfuran followed by subsequent dehydration reaction over Lewis acid zeolite catalyst, Zr-BEA, with 90% selectivity in products.  
165x173mm (150 x 150 DPI)