

Lab on a Chip

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Doping of Inorganic Materials in Microreactors - Preparation of Zn doped Fe₃O₄ Nanoparticles

M. D. Simmons,^{a,b} N. Jones,^a D. J. Evans,^a C. Wiles,^{a,c} P. Watts,^d S. Salamon,^e M. Escobar Castillo,^f H. Wende,^e D. C. Lupascu^f and M. G. Francesconi^{a*}

^a Department of Chemistry, University of Hull, Cottingham Road, Hull HU6 7RX, UK.

^b Molecular Vision, Abingdon Health Ltd., Sand Hutton, York, YO41 1LZ, UK.

^c Chemtrix BV, Chemelot Campus, Urmonderbaan 22, 6167 RD, Geleen, The Netherlands.

^d InnoVenton: NMMU Institute for Chemical Technology, Nelson Mandela Metropolitan University, PO Box 77 000, Port Elizabeth, 6031, South Africa.

^e Faculty of Physics and Center for Nanointegration Duisburg-Essen (CENIDE), University of Duisburg-Essen, 45141, Duisburg, Germany

^f Institute for Materials Science and Center for Nanointegration Duisburg-Essen (CENIDE), University of Duisburg-Essen, 45141, Essen Germany

Abstract

Microreactor systems are now used more and more for the continuous production of metal nanoparticles and metal oxide nanoparticles owing to the controllability of the particle size, an important property in many applications. Here, for the first time, we used microreactors to prepare metal oxide nanoparticles with controlled and varying metal stoichiometry. We prepared and characterised Zn-substituted Fe₃O₄ nanoparticles with linear increase of Zn content (Zn_xFe_{3-x}O₄ with $0 \leq x \leq 0.48$), which causes linear increases in properties such as the saturation magnetization, relative to pure Fe₃O₄. The methodology is simple and low cost and has great potential to be adapted to the targeted doping of a vast array of other inorganic materials, allowing greater control on the chemical stoichiometry for nanoparticles prepared in microreactors.

Introduction

Microreactors are used as a common tool for the study and optimization of a wide variety of synthetic organic reactions, but also increasingly in the synthesis of organic and inorganic nanoparticles. When compared to conventional batch reactions, microreactors offer many practical advantages, such as continuous processing and highly controlled reaction conditions e.g. low and precisely controllable mass transfer times.¹⁻³ This has culminated in “black box”

techniques, which seek to automate these synthetic processes completely, on the basis of specific product properties, affording quality by design.⁴

Greater control of reaction conditions has led to vastly greater yields and stereoselectivity in the preparation of organic compounds, and to smaller particle sizes and increased monodispersity in the preparation of nanoparticles.^{3,4} Microreactor systems are now able to produce a diverse array of metal nanoparticles, including Au,⁵ Ag,⁶ and Au-Ag nanoalloys,⁷ metal oxide nanoparticles including TiO₂⁸ and SiO₂⁹ and non-oxide compounds such as CdSe.¹⁰ Recently, such devices have been used for the synthesis of iron oxide nanoparticles.¹¹⁻¹³ Iron oxide nanoparticles (IONs) have multiple uses in technology, but recent research has focussed mainly on their use in biomedicine as magnetic resonance imaging (MRI) contrast agents and hyperthermia treatments for arteriosclerosis and cancer.¹⁴ Magnetic hyperthermia treatments use magnetic nanoparticles to induce death of cancer cells by heating the tissue; as magnetic nanoparticles can be engineered to target specific cells, consequently invasive surgery can be avoided. Furthermore, magnetic nanoparticles are favoured for hyperthermia treatments compared to gold nanoparticles as they are activated by external application of a magnetic field and do not require potentially harmful laser light.¹⁵

Fe₃O₄, magnetite, exhibits the inverse spinel structure (space group $Fd\bar{3}m$).¹⁶ The oxide anions form a face centred cubic sublattice, with half of the Fe³⁺ cations occupying the tetrahedral holes and the other half occupying the octahedral holes together with the Fe²⁺ cations. The cubic unit cell has a lattice parameter of 8.3985(5) Å and contains eight Fe₃O₄ formula units, so that a more representative formula can be written as [(Fe³⁺)₈]_{TET}[(Fe³⁺Fe²⁺)₈]_{OCT}O₃₂.¹⁷

Substitution of various transition metals into the spinel structure can have varying effects upon both the structural and magnetic properties of the material. Partial substitution of iron with zinc leads to the Zn_xFe_{3-x}O₄ series (0 ≤ x ≤ 1), within which the compound with x ≈ 0.3 was reported to show a maximum in the value of the saturation magnetisation.¹⁸

Zinc ferrites exhibit the normal spinel structure ($Fd\bar{3}m$ $a = 8.4432(3)$ Å) in which most Zn²⁺ cations occupy the tetrahedral sites and the Fe³⁺ cations the octahedral sites (Supplementary Figure 1).¹⁹

The magnetic properties of Fe₃O₄ are due to superexchange interactions between the Fe cations and mediated by the oxide anions. These interactions can be intra-site, when they occur between Fe cations on the tetrahedral sites, (Fe³⁺)_{TET}-O-(Fe³⁺)_{TET}, or between iron cations on the octahedral sites, (Fe³⁺)_{OCT}-O-(Fe³⁺)_{OCT}/(Fe³⁺)_{OCT}-O-(Fe²⁺)_{OCT}, and, inter-

sites, when occurring between cations on the octahedral and tetrahedral sites, $(\text{Fe}^{3+})_{\text{TET}}\text{O}-(\text{Fe}^{3+}/\text{Fe}^{2+})_{\text{OCT}}$. Inter-site superexchange interactions are much stronger and will contribute the most to the magnetic properties. In the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ series ($0 \leq x \leq 1$) Zn^{2+} occupies the tetrahedral sites, hence substituting for Fe^{3+} into the structure of Fe_3O_4 . According to Wen, for $x < 0.37$ the effect of the substitution of the diamagnetic Zn^{2+} for Fe^{3+} lowers the magnetisation of the tetrahedral site, increasing the magnetisation of the whole compound. However, for $x > 0.37$ the magnetisation of the A site becomes much weaker, to the point that $(\text{Fe}^{3+})_{\text{OCT}}\text{O}-(\text{Fe}^{3+})_{\text{OCT}}/(\text{Fe}^{3+})_{\text{OCT}}\text{O}-(\text{Fe}^{2+})_{\text{OCT}}$ become the main super-exchange interactions and the total magnetisation decreases.²⁰

Similarly to IONS, $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ nanoparticles are being studied as both MRI contrast agents and for hyperthermia treatments of cancer cells, complementary to IONS, due to the increased magnetisation obtained for $x < 0.37$ and larger T_2 relaxivity.^{20,21}

$\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ nanoparticles are mostly prepared via co-precipitation methods and solvothermal methods.^{19,20,22–26} Here, we report a simple one-step synthetic method to prepare $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ samples with controlled and varied Zn content ($0 \leq x \leq 0.5$) using microreactors. This technique allows for the continuous production of zinc doped iron oxide nanoparticles with controlled magnetic and physical properties, which would be difficult to achieve in a reliable manner through the use of current batch techniques.

A method based on two interconnected microreactors and comprising a heating step, has been recently used by Abou-Hassan et al. to prepare CoFe_2O_4 .²⁷ However, to the best of our knowledge, no microreactor based methods have been reported for the preparation of Zn-containing ferrites and, more importantly, for solid solutions with variable metal content.

Experimental


Synthesis

The synthetic procedure is based on the methodology reported for the preparation of undoped iron oxide in microreactors, reported recently by Simmons et al.¹² A schematic diagram of the microreactor used is shown in Figure 1. The microreactor comprised of one etched layer and one cover plate, which, upon bonding, afforded isotropic channels of a depth of 60 μm and width of 300 μm (volume 10 μl).

To prepare pure iron oxide nanoparticles, an iron salts precursor solution (ISPS) was prepared by mixing stoichiometric volumes of $\text{FeCl}_2 \cdot 4\text{H}_2\text{O}$ (0.01 mol dm^{-3}) in HCl (1.10 mol dm^{-3})

and FeCl_3 (0.02 mol dm^{-3}) in HCl (1.10 mol dm^{-3}), and a base solution, NaOH (1.00 mol dm^{-3}) was also prepared. The solutions were pumped into the microreactor simultaneously.

The synthesis of $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ was achieved via a modified version of the above procedure (Figure 2b), according to the general equation, where $x = 0 - 0.5$:



A solution of iron and zinc salts was prepared by mixing stoichiometric volumes of $\text{FeCl}_2 \cdot 4\text{H}_2\text{O}$ (0.01 mol dm^{-3}) in HCl (1.10 mol dm^{-3}), FeCl_3 (0.02 mol dm^{-3}) in HCl (1.10 mol dm^{-3}), and ZnCl_2 (0.01 mol dm^{-3}) in HCl (1.10 mol dm^{-3}) (Figure 1).

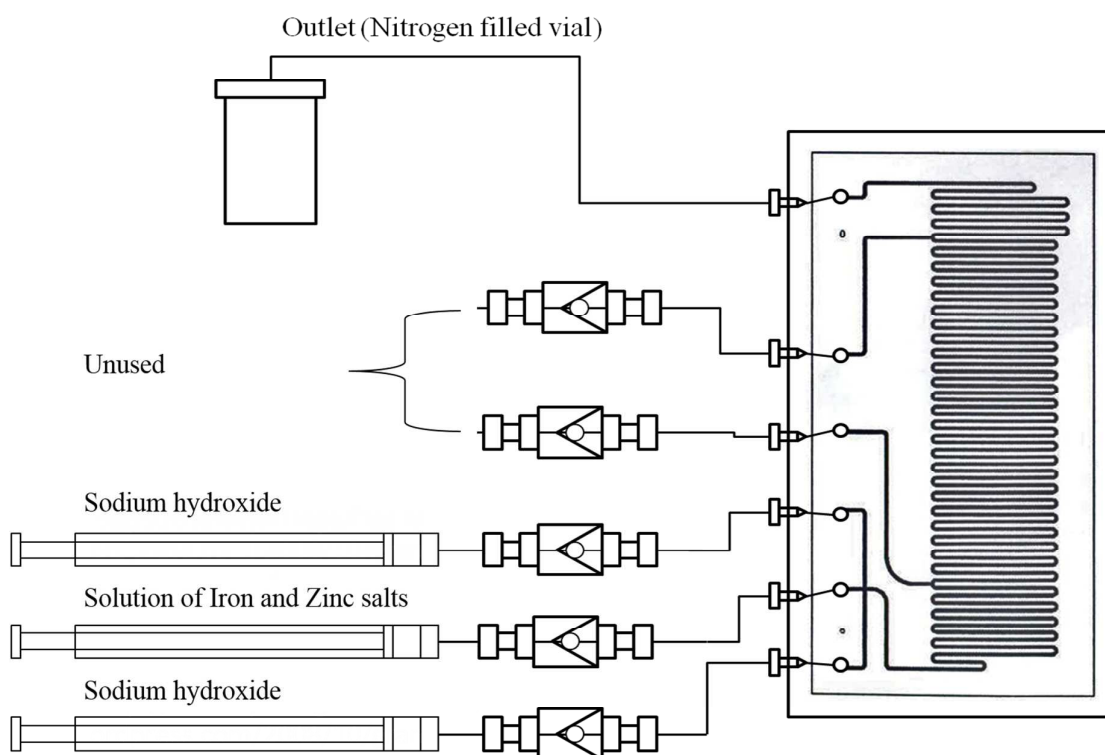


Figure 1. Schematic diagram for the microreactor set up used in the syntheses of $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ nanoparticles.

The volumes of solutions of the reagents used in this work are listed in Table 1.

Volume of ZnCl_2 (0.01 M) (ml)	Volume of FeCl_2 (0.01 M) (ml)	Volume of FeCl_3 (0.02 M) (ml)
1.25	11.25	12.5

2.50	10.00	
3.75	8.75	

Table 1. Volume of reagents used for the preparation of the $Zn_xFe_{3-x}O_4$ series in microreactors.

The Labtrix[®] Start system was used for these experiments, with glass microreactor design 3025, further details can be found in the paper by Simmons et al.¹²

The solutions were pumped into the reactor along with a solution of NaOH (1.00 mol dm⁻³). Oxidation of Fe²⁺ was prevented by de-oxygenating all solutions for 1 hour by bubbling nitrogen through them prior to use.¹¹ As the precipitation of iron oxide nanoparticles is pH controlled and occurs mainly at basic pH, acidifying the ISPS favours the formation of the nanoparticles in the central microchannel upon addition of NaOH.

The precursor solution was pumped into the central microchannel (mod-ISPS), while the base was pumped through the two lateral micro channels. By “focusing” the precursor solution between the two flows of base, the area upon which nanoparticles can adhere to the microreactor walls was minimised, thus greatly reducing the amount of precipitating nanoparticles upon the microreactor walls and preventing blocking of the channel. Flow rates of 2000 µl hr⁻¹ per feed line (6000 µl hr⁻¹ total flow rate) were used, flow rates < 1500 µl hr⁻¹ led to clogging of the microreactor, while flow rates > 6000 µl hr⁻¹ led to an undesired elevated pressure drop. Under these conditions, we calculate residence times ranging from 6 to 24 sec and Re numbers of 10.3 to 3 respectively which confirm the work is performed under a laminar flow regime. No back pressure regulator was fitted to the outlet of the microreactor. Photos of the equipment are shown in the Supplementary Information section (Supplementary Figure 2).

$Zn_xFe_{3-x}O_4$ nanoparticles formed and precipitated within the channels and were carried through to the outlet tube where they were collected in a N₂ filled vial.

Magnetic nanoparticles were removed from the liquid phase via magnetic decantation and further washed with deionised water and ethanol to remove any sodium chloride by-product. No thermal steps were included in the procedure, except an overnight drying stage under argon at 100 °C.

Characterisation

Powder X-Ray Diffraction (PXRD) patterns were collected using a Bruker D5000 diffractometer with Cu K α radiation over the range $20 \leq 2\theta \leq 80$, with a step size of 0.02° and a time step of 28 seconds per step.

For ICP-AES analyses, the samples (approximately 0.03 g) were dissolved in 3 ml of conc. HCl, while heated on a hotplate. The dissolved samples were then diluted and the Fe and Zn content was measured in weight percentage of a 10 ml aliquot. Analysis was carried out using a Perkin Elmer Optima 5300DV instrument, Fe in radial view, Zn in axial view against calibration at 0 and 10 ppm Fe (238.204 nm) and Zn (206.200 nm).

Mössbauer spectra for the three $Zn_xFe_{3-x}O_4$ ($x = 0.3, 0.4, 0.5$) were recorded at $T = 80$ K, on an ES-Technology MS-105 Mössbauer spectrometer. Spectra were referenced against $25 \mu\text{m}$ iron foil at 298 K and spectrum parameters were obtained by fitting with Lorentzian curves. Mössbauer spectra for the three $Zn_xFe_{3-x}O_4$ ($x = 0.3, 0.4, 0.5$) and for Fe_3O_4 were also recorded at 4.2 K in transmission geometry using a constant acceleration spectrometer with a ^{57}Co source (Rh-matrix) and a liquid helium bath cryostat. The setup was calibrated using α -Fe foil as reference at room temperature.

Magnetometry measurements were carried out using a Quantum Design MPMS-5S SQUID magnetometer. The saturation magnetisation was measured at 5K and a maximum applied magnetic field of 5T, while field-cooled (FC) and zero-field-cooled (ZFC) curves were recorded at an applied field of 0.1T between 5K and room temperature. Additionally, temperature dependent AC susceptibility measurements have been carried out to characterise the superparamagnetic blocking temperatures of each sample, using alternating magnetic fields with amplitude of 0.4mT at 11Hz. Magnetometry measurements and Mössbauer spectroscopy were carried out on the powders collected from the microreactor after washing and drying without further treatment.

The morphology of the powders was studied using a scanning electron microscope (ESEM Quanta 400 FEG) and a high-resolution transmission electron microscope (HR-TEM Tecnai F20) with a high-angle annular dark field detector. For the TEM analyses the synthesized powders were ground in a ball mill with zirconia oxide spheres in ethanol (consistent ratio powder/spheres 1g/10g) for 240 hours at 10 rpm and then sonicated for 10 min with an ultrasonic sonotrode (Bandelin Sonopuls HD 70).

Results and Discussion

Recently we developed a simple synthetic method for the preparation of iron oxide nanoparticles (IONs) in commercially available micro-reactors.¹² The synthesis is based on a laminar flow technique that grants careful control of precipitation while avoiding channel blockage. Furthermore, no fouling was observed for up to 40 hours of continuous operation. The IONs obtained were of comparable size and polydispersity to those previously prepared in ad-hoc built continuous flow reactors, which constituted the first seminal works, but were somehow limited in the fact that upscaling would be complex with homemade reactors.^{11,13,28,29}

Considering the high degree of controllability achieved via our method, we have exploited it to achieve controlled doping in IONs. In particular, we focussed on $Zn_xFe_{3-x}O_4$, with the view to varying the value of x , i.e. the Zn^{2+} content. The reactor design allowed three single reagent streams to come together, so that one solution of metal salts and two of a base solution could be reacted while pumped along the channel of the microreactor and produce a precipitate of nanoparticles, which are moved along by the flow and collected at the channels outlet. Under the laminar flow conditions employed, mixing occurs exclusively by molecular diffusion, and it needs to be emphasized that the speed of mixing is directly related to the thickness of the resulting lamella, with the proportion of mixing determined by the channel length. Consequently, the speed of precipitation is highly controlled and repeatable. Furthermore, under these flow conditions ($6000 \mu l hr^{-1}$ total, $2000 \mu l hr^{-1}$ each feed line), the particles flow freely from the reactor avoiding blockage; no backpressure regulator (BPR) was employed.

The same technique was used for the preparation of $Zn_xFe_{3-x}O_4$ nanoparticles by simply replacing a portion of the iron chlorides with zinc chloride in the initial solution. The amount of solutions of starting reagents are shown in Table 1.

ICP-AES analyses were carried out to determine the chemical formulae of the $Zn_xFe_{3-x}O_4$ nanoparticles. The raw data obtained from ICP are expressed in weight percentages and shown in Table 2.

Weight percentage of Fe from ICP*	Weight percentage of Zn from ICP*	Formula of $Zn_xFe_{3-x}O_4$ Compound
2.721 ± 0.018	0.291 ± 0.005	$Zn_{0.27}Fe_{2.73}O_4$
2.298 ± 0.006	0.332 ± 0.008	$Zn_{0.37}Fe_{2.63}O_4$
2.294 ± 0.019	0.433 ± 0.002	$Zn_{0.48}Fe_{2.52}O_4$

Table 2. Predicted and actual formulas for the $Zn_xFe_{3-x}O_4$ series, calculated from ICP-AES data. *The Standard Deviations were calculated from three replicates.

There is a linear increase of Zn content (value of x in the $Zn_xFe_{3-x}O_4$ series) with increasing $ZnCl_2$ in the initial mixture (and decreasing $FeCl_2$), indicating that our simple route allows controllability of doping up to $x = 0.5$.

PXRD patterns of the $Zn_xFe_{3-x}O_4$ series (Figure 2) suffer badly from peak broadening. This is likely to be due to the very small size of the nanoparticles, and the presence of a small percentage of impurities cannot be ruled out completely. All three patterns of the $Zn_xFe_{3-x}O_4$ compounds are compared and show little difference. The average two theta positions of the broad peaks can be related to the position of the diffraction peaks for Fe_3O_4 , calculated using the cubic model reported by Fleet ($Fd\bar{3}m$, $a = 8.3941 \text{ \AA}$), suggesting that the spinel structure is maintained throughout the Zn/Fe substitution carried out in this work.³⁰ An additional heating step would probably have increased the crystallinity of the compounds, however it bears the risk of increasing the particle size.

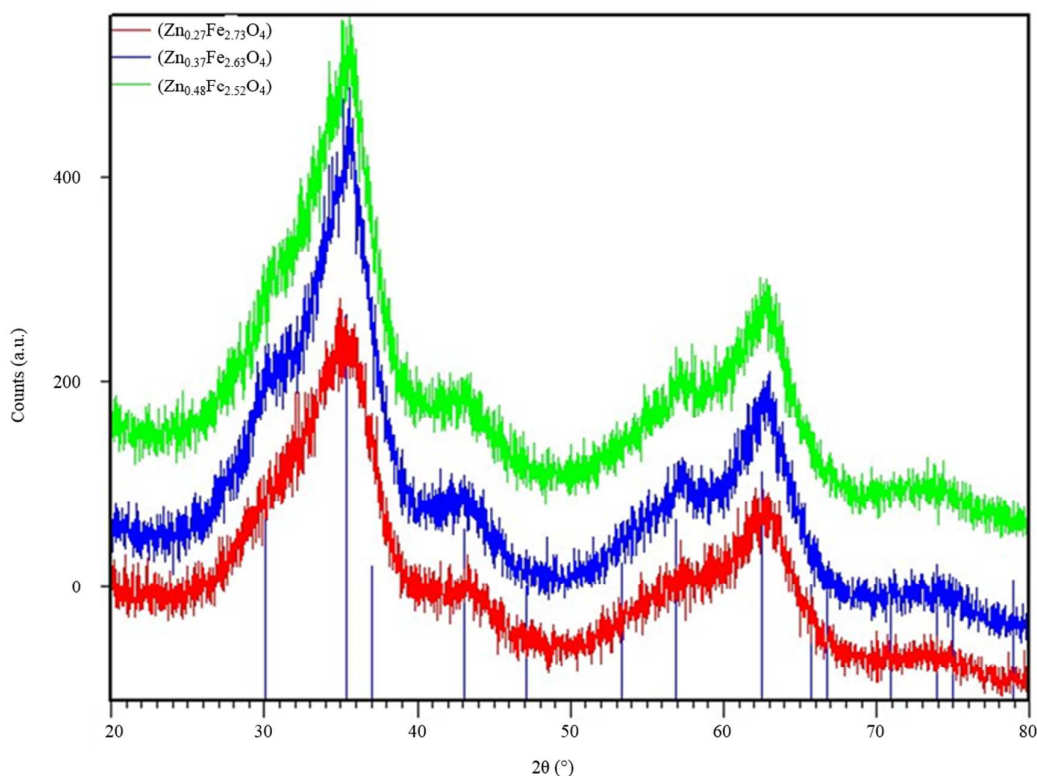


Figure 2. PXRD patterns of $Zn_xFe_{3-x}O_4$ series synthesised using microreactors. The lines represent the PXRD pattern for magnetite, calculated from the model reported by Fleet.³⁰

PXRD data were used as an additional tool to estimate the particle size, after fitting the profile of all peaks, via the Williamson-Hall plot.³¹ The PXRD patterns of all samples were used with the exception of the sample with the lowest Zn content, $Zn_{0.27}Fe_{2.73}O_4$, as the profile fit of the peak was not satisfactory. The average size of the nanoparticles was found to be 1.6 nm for $Zn_{0.37}Fe_{2.63}O_4$ and 1.3 nm for $Zn_{0.48}Fe_{2.52}O_4$, in good agreement with the results from size analysis of the particles, using TEM data (Figure 3).

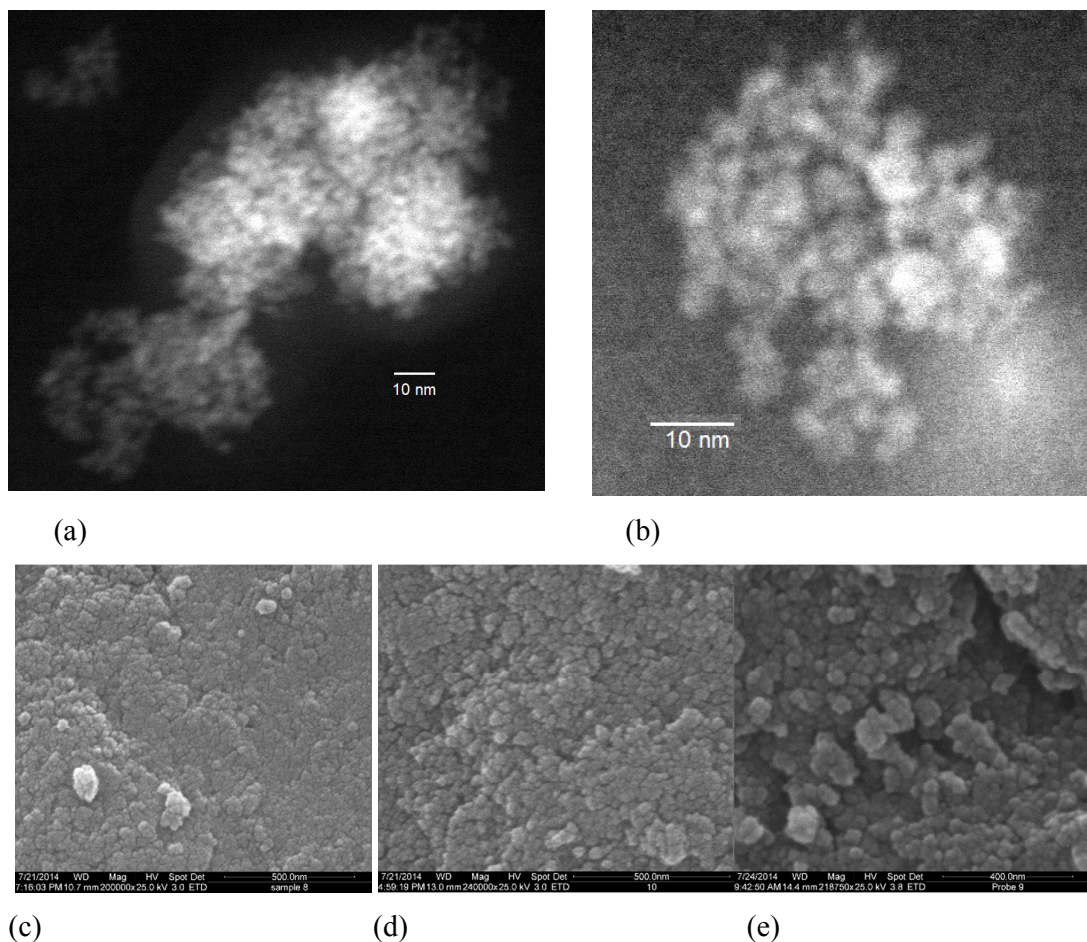


Figure 3. (a) and (b) TEM images of the sample $Zn_{0.27}Fe_{2.73}O_4$; (c) – (e) SEM images of the nanoparticles of (c) $Zn_{0.27}Fe_{2.73}O_4$; (d) $Zn_{0.37}Fe_{2.63}O_4$; (e) $Zn_{0.48}Fe_{2.52}O_4$.

Figures 3a and 3b show the TEM micrographs of $Zn_{0.27}Fe_{2.73}O_4$ nanoparticles, after partial de-agglomeration. The TEM pattern confirms that the particles are spherical with a uniform

grain size distribution. The measured particle size is visually estimated to be less than 5 nm, supporting the size analysis performed using the Scherrer formula and the Williamson-Hall plot.

It is interesting to point out that the average size of $Zn_xFe_{3-x}O_4$ nanoparticles prepared via coprecipitation or sol-gel methods is generally above 10 nm, without the use of capping agents. Figure 3 (c) – (e) shows SEM pictures of the nanoparticles for all the samples within the $Zn_xFe_{3-x}O_4$ series, taken after drying. The particles appear approximately spherical, homogeneous in shape and size and highly agglomerated. This high degree of agglomeration is due to the fact that the particles were not coated after synthesis, and to their small size and magnetic properties.

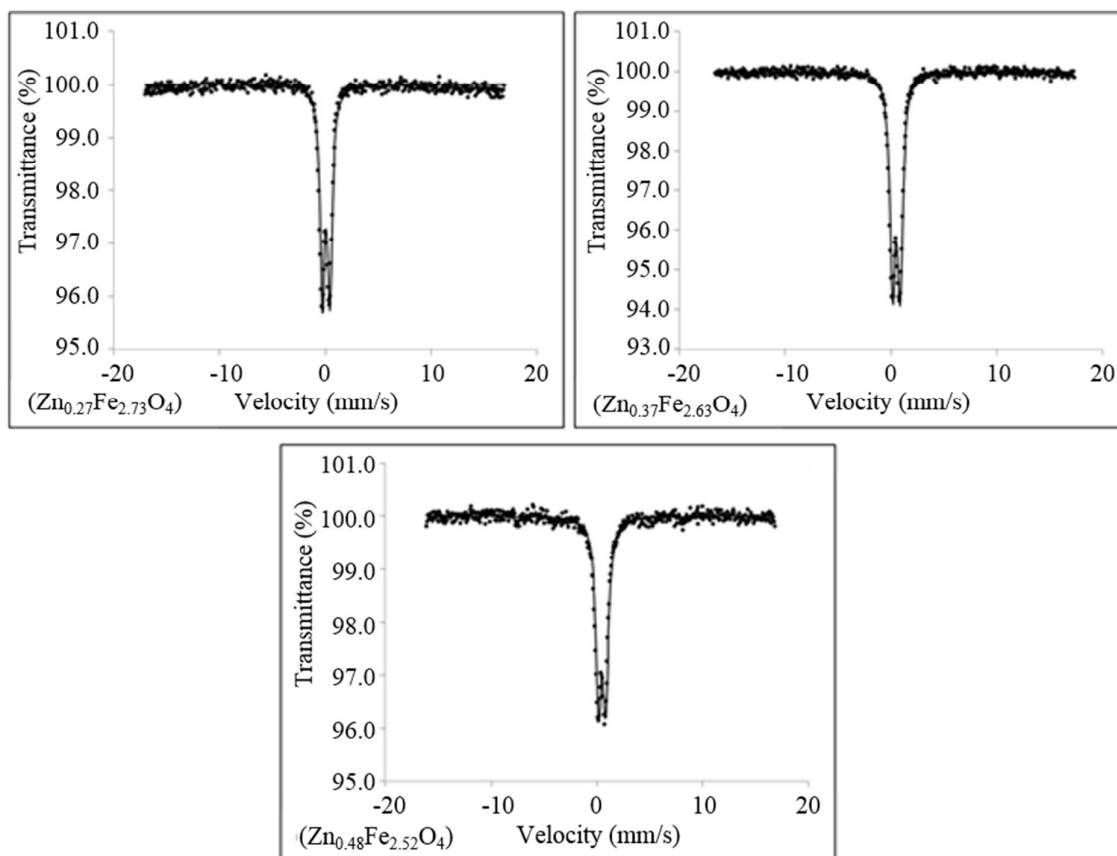


Figure 4. Mössbauer spectra recorded at $T = 80$ K for the $Zn_xFe_{3-x}O_4$ ($x = 0.27, 0.37, 0.48$) series.

No impurities were detected in the Mössbauer spectra for the three $Zn_xFe_{3-x}O_4$ ($x = 0.27, 0.37, 0.48$) samples collected at 80 K (Figure 4), although close inspection of the baseline of

the spectrum of the sample $\text{Zn}_{0.27}\text{Fe}_{2.73}\text{O}_4$ shows some deviation, which may be due to a very small amount of another iron oxide (Fe_3O_4 or $\gamma\text{-Fe}_2\text{O}_3$) or a very broad six-line hyperfine component of the spectra. The spectrum of Fe_3O_4 was also collected for direct comparison (Supplementary Figure 3) and no substantial differences could be noticed.

Sample	Isomer shift (mm/s)	Quadrupole Splitting (mm/s)	Half Width at Half Maximum (mm/s)
$\text{Zn}_{0.27}\text{Fe}_{2.73}\text{O}_4$	0.43 ± 0.02	0.71 ± 0.02	0.27 ± 0.02
$\text{Zn}_{0.37}\text{Fe}_{2.63}\text{O}_4$	0.45 ± 0.02	0.71 ± 0.02	0.31 ± 0.02
$\text{Zn}_{0.48}\text{Fe}_{2.52}\text{O}_4$	0.43 ± 0.02	0.70 ± 0.02	0.33 ± 0.02
Fe_3O_4	0.34 ± 0.001	0.69 ± 0.002	0.31 ± 0.003
ZnFe_2O_4 ³¹	0.39	0.59	N/A

Table 3. Mössbauer parameters from spectra recorded at $T = 80$ K for $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ ($x = 0.3, 0.4, 0.5$), Fe_3O_4 and parameters for ZnFe_2O_4 taken from the literature for comparison. The Mössbauer spectra in reference 31 were collected at $T = 85$ K. No errors were provided for Isomer shift and quadrupole splitting and the value of half width at half maximum was not given.

The Mössbauer isomer shift and quadrupole splitting were seen to be of the same order as those seen in the literature (Table 3). The well-defined doublet seen in all spectra is common for nanosized zinc ferrite systems displaying superparamagnetic behaviour. The isomer shift and quadrupole splitting for each sample was higher than those seen for ZnFe_2O_4 nanoparticles at 85 K and Fe_3O_4 at 80 K, indicating different behaviour of the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ series, compared to both the end members of the solid solution.³¹ The half-width at half-maximum peak for the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ series increases slightly for x values from $x=0.3$ to $x=0.5$, hence supporting increasing substitution of Zn^{2+} in Fe_3O_4 . The deviation from the baseline in the spectrum of $\text{Zn}_{0.27}\text{Fe}_{2.73}\text{O}_4$, may be due to the sample being close to the blocking temperature at which point the expected sextet would emerge from the baseline.

Further spectra of the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ ($x = 0.3, 0.4, 0.5$) samples were collected at 4.2 K and are shown in Figure 3 SI. The hyperfine field distribution fit was applied and the parameters obtained from the fitting procedure are summarized in Table 1 SI, including the mean hyperfine field B_{hf} , isomer shift, quadrupole shift and line width. Except for a slightly increased line width for the sample with the lowest amount of Zn doping, no noticeable changes could be detected throughout the doping series. The spectrum of Fe_3O_4 was also collected for direct comparison (Supplementary Figure 4) and no substantial differences

could be noticed, indicating that magnetic properties below T_B are unchanged compared to pure Fe_3O_4 .

Figure 5 shows the saturation magnetisation as a function of Zn content for each of the observed samples. Each data point consists of four individual measurements of the magnetic moment at 5K and $\pm 5\text{T}$, with error bars being calculated from the standard deviation of the magnetic measurements and the uncertainty of the scale used to determine each sample's weight. Standard error propagation was used for the final error. The data display an increase of the magnetisation with Zn content by 35% from un-doped Fe_3O_4 up to the sample with the highest Zn doping. This is a clear indicator of a change in magnetic properties due to a change in Zn content. It should be noted however, that small fluctuations of the mean particle diameter can also be responsible for changes of the magnetisation values. Plotting magnetisation against mean particle diameter did not yield any recognizable pattern, leading us to conclude that the increased saturation magnetisation is caused mainly by Zn doping.


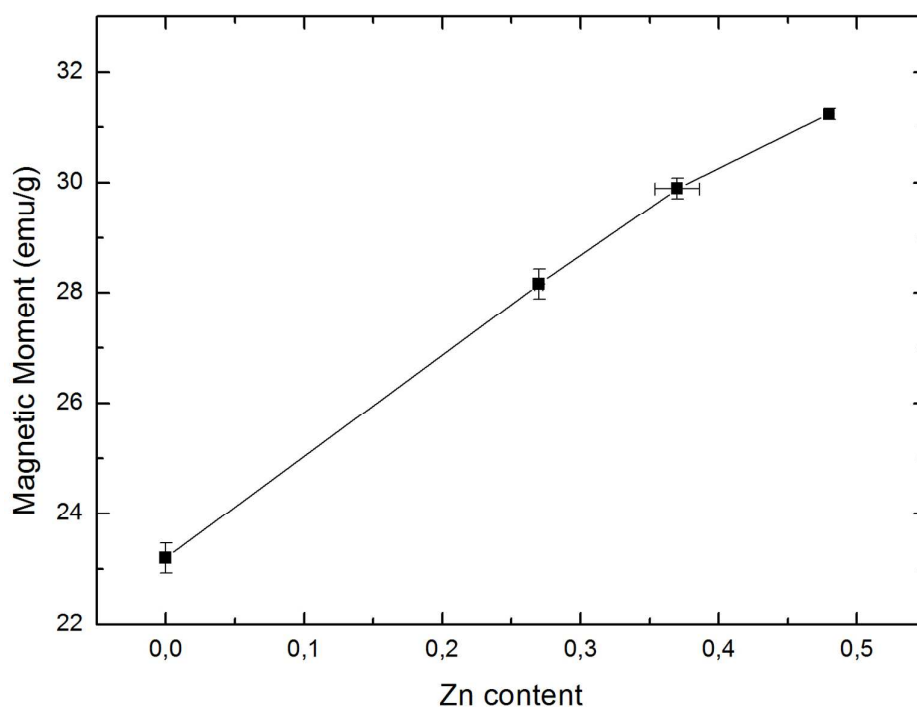



Figure 5. Saturation magnetic moments as function of increasing Zn content in $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$, at 5 K and 5 T.

Figure 6a shows the ZFC-FC curves of the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ samples, with the ZFC peaks being shown in the inset. The samples were cooled to 5K at zero applied field, after which the field was ramped to 0.1T, with the samples' magnetic moment being measured while warming up to room temperature, then cooling back down to 5K. For better comparability, the curves


were scaled so that the ZFC peaks have equal amplitude. No error bars are shown due to the constant change of temperature only allowing for one scan per measurement. The peaks obtained from ZFC measurements are indicative of the mean blocking temperature, T_B , for superparamagnetic particles.

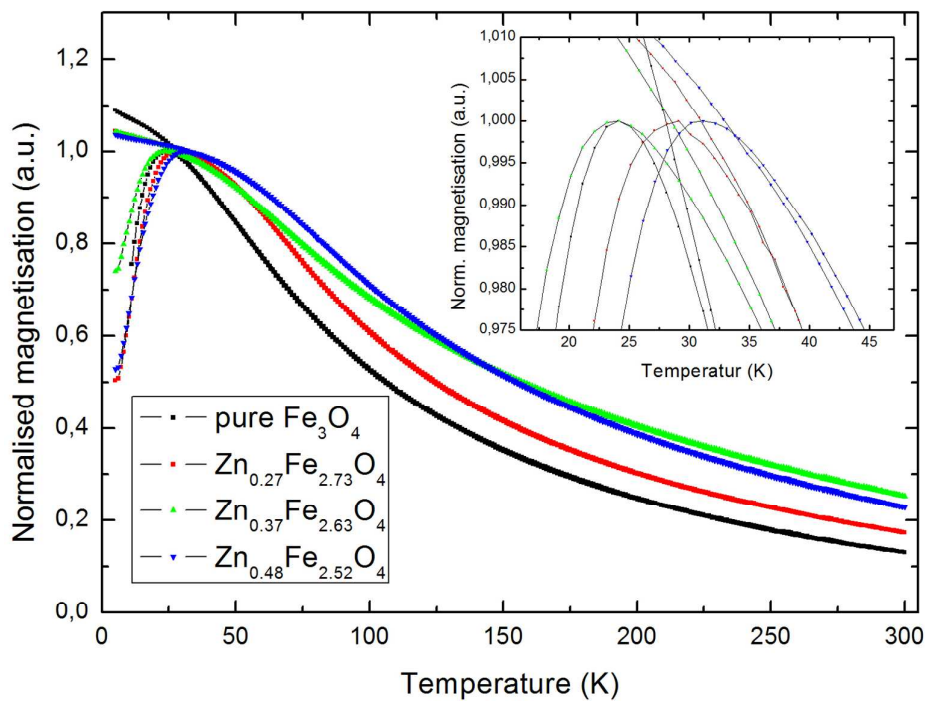


(a)

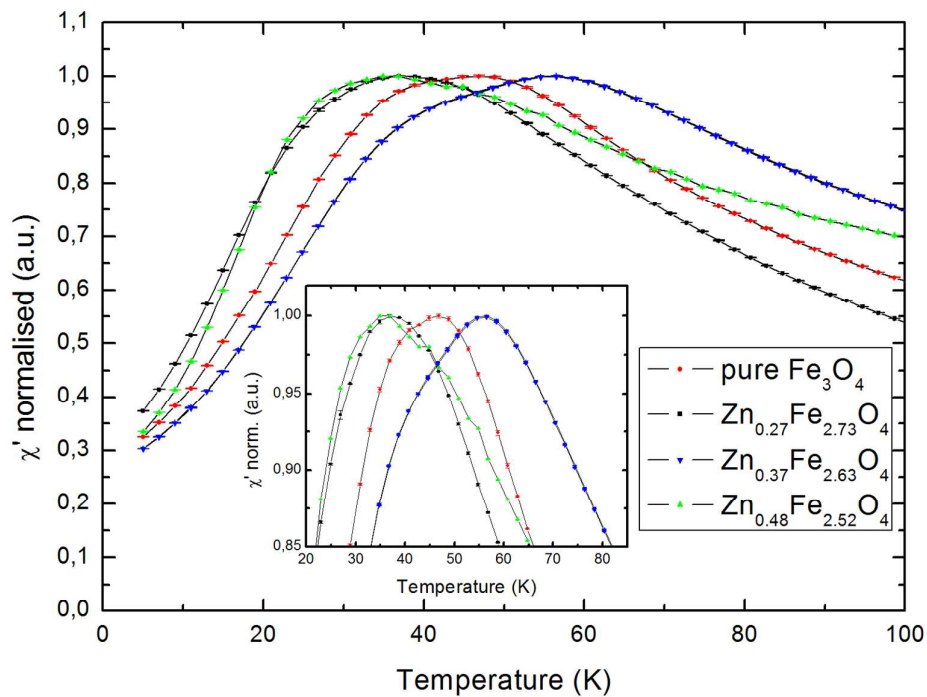

(b)

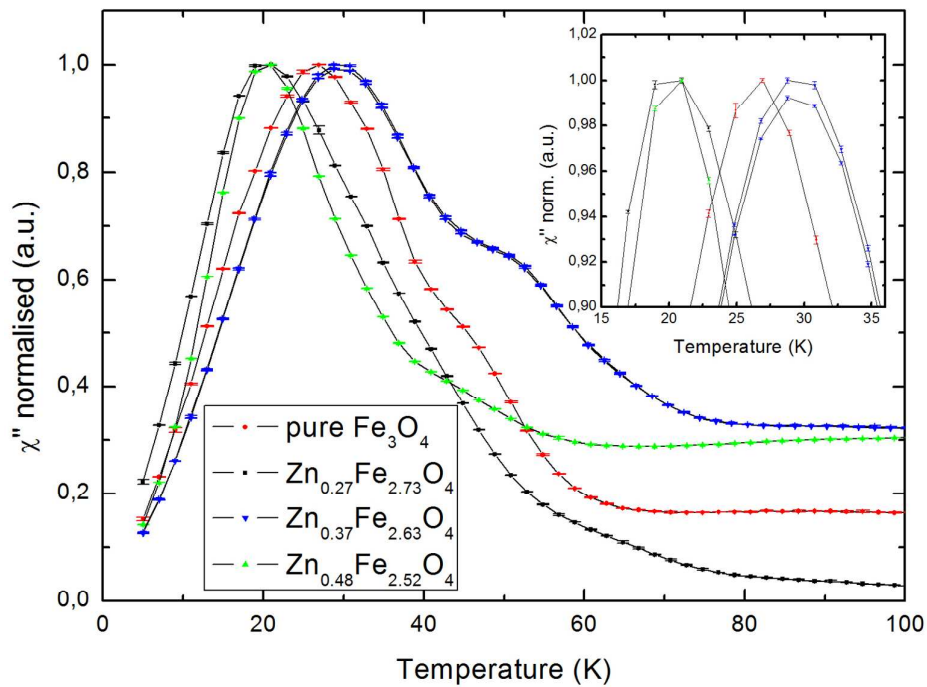

(c)

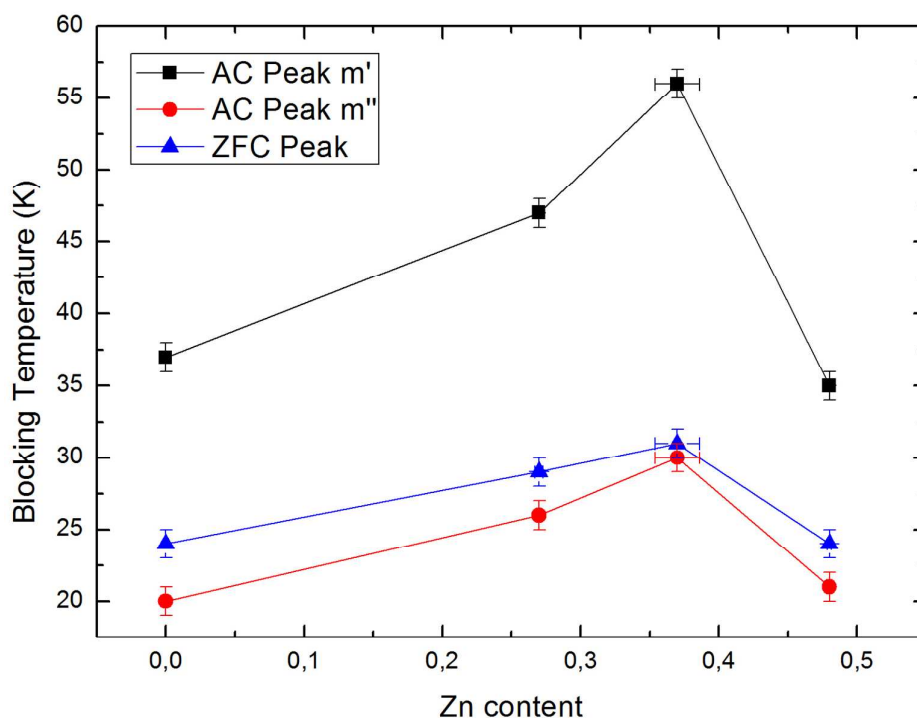

(d)

Figure 6. (a) ZFC-FC curves for the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ series; (b) Real component χ' of the AC signal for the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ series; (c) Imaginary component χ'' of the AC signal for the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ series; (d) Blocking temperatures from AC and ZFC peaks for the $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ series.

In addition to the ZFC-FC curves, data from AC susceptibility measurements was used to substantiate the determined blocking temperatures, and to examine the samples' superparamagnetic behaviour in greater detail. This specialized measurement option uses alternating magnetic fields to probe a sample's dynamic response, with two sets of data being produced: the magnitude of the susceptibility, χ , and the phase shift between applied and measured signal, ϕ , which can also be displayed as an in-phase (real) component χ' and an out-of-phase (imaginary) component χ'' . The latter indicates dissipative processes in the sample, with peaks in the χ'' versus T curve being a good indicator for blocking temperatures. Both sets of curves are displayed in Figures 6b and 6c, with only the temperature region of interest around the peaks being shown (normalised). Samples were cooled to 5 K at zero applied field and the susceptibility was measured while heating to room temperature. To make sure that no thermal hysteresis effects are present, the measurement was run in both directions for one of the samples, $\text{Zn}_{0.37}\text{Fe}_{2.63}\text{O}_4$. As seen in the diagrams, the

two curves are perfectly identical. Generally speaking, all samples showed a distinct peak at low temperatures, clearly showing superparamagnetic behaviour. While the main peak of each sample is clearly visible, especially on the χ'' curves, there are also secondary peaks or shoulders, best visible for $\text{Zn}_{0.37}\text{Fe}_{2.63}\text{O}_4$. As superparamagnetic behaviour is strongly size-dependent, this indicates a particle size distribution that has two peaks, one main peak containing the majority of particles in the sample and a smaller peak. Due to this secondary peak being visible towards higher temperatures in the measurements, it can be assumed that the size distribution also has a small secondary peak at larger particle sizes. However, with particle sizes in the range of 1.3-1.6 nm, these fluctuations are assumed to be very small. Generally speaking, a good agreement can be seen between the peaks determined from the ZFC-FC curves and the ones determined from AC measurements, showing reproducible results by both static and dynamic magnetometry. As shown in Figure 6d, our results indicate that a change in Zn content leads to a change of T_B compared to the un-doped pure Fe_3O_4 sample, with $\text{Zn}_{0.37}\text{Fe}_{2.63}\text{O}_4$ having the highest blocking temperature of all samples measured. Plotting the mean particle diameter against T_B does not yield any clear pattern, with T_B for $\text{Zn}_{0.37}\text{Fe}_{2.63}\text{O}_4$ and $\text{Zn}_{0.48}\text{Fe}_{2.52}\text{O}_4$ being 19K apart while mean particle diameters for both samples were determined to be 1.3 nm. This proves that changes in T_B are caused by the Zn doping rather than fluctuations in particle size.

Conclusions

Microreactors have been used for the synthesis of inorganic compounds, but this is the first report of chemical doping achieved via this technique. The synthesis of the series of zinc-doped Fe_3O_4 , $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ ($0 \leq x \leq 0.48$), nanoparticles was carried out using a reversed engineered microfluidic technique. The partial substitution of zinc for iron in magnetite, Fe_3O_4 , shows a linear increase in Zn content with increase of ZnCl_2 in the initial mixture of reagents. The $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ ($0 \leq x \leq 0.48$) nanoparticles show average size below 5 nm, smaller than those obtained via more traditional methods such as co-precipitation or sol-gel. PXRD show that all samples show the spinel structure and Mössbauer spectra showed the nanoparticles to be superparamagnetic, at 80 K, with the width of the spectrum peak increasing linearly with the zinc content. Magnetic measurements showed a linear increase of the saturation magnetisation with increasing Zn content, further supporting the observed linear substitution while also showing that Zn substitution actively alters the compound's magnetic properties. Superparamagnetic behaviour was clearly visible in both ZFC and AC

curves, with results indicating that shifts of the mean blocking temperature TB were not caused by fluctuations in particle diameter but mostly by changes in Zn content. In conclusion, the use of microreactors has been shown here to be successful for the preparation of doped Fe₃O₄ nanoparticles below 5 nm and with progressively increasing Zn content. This relatively simple and low-cost synthetic route has great potential to be exploited for the synthesis and doping of a wide range of inorganic nanoparticles. With the chance of tailoring the chemical formulas, hence properties, as well as the particle size and distribution of inorganic nanoparticles, microfluidic technology is set to grow in importance as synthetic tool.

Acknowledgements

The authors would like to thank the Department of Chemistry, University of Hull for a PhD studentship for M. D. Simmons and Mr Bob Knight for ICP measurements. The authors would like to thank Dr V. V. Shvartsman for his helpful instructions in the magnetic measurements. This work was supported by Stiftung Mercator (MERCUR). D. C. Lupascu acknowledges partial support through DFG Forschergruppe 1509.

1. T. W. Phillips, I. G. Lignos, R. M. Maceiczky, A. J. deMello and J. C. deMello, *Lab Chip*, 2014, **14**, 3172–3180.
2. C. Wiles and P. Watts, *Chem. Commun.*, 2011, **47**, 6512–35.
3. M. Pumera, *Chem. Commun.*, 2011, **47**, 5671–80.
4. S. Krishnadasan, R. J. C. Brown, A. J. deMello, and J. C. deMello, *Lab Chip*, 2007, **7**, 1434–41.
5. J. Wagner and J. M. Ko, *Nano Lett.*, 2005, **5** (4), 685–691.
6. X. Z. Lin, A. D. Terepka, and H. Yang, *Nano Lett.*, 2004, **4**, 2227–2232.
7. L. Sun, W. Luan, Y. Shan, and S. Tu, *Chem. Eng. J.*, 2012, **189-190**, 451–455.
8. T. N. G. and C. O. K. Mostafa Baghbanzadeh, *J. Flow Chem.*, 2013, **3**, 109–113.
9. S. A. Khan, A. Guenther, M. A. Schmidt, and K. F. Jensen, *Langmuir*, 2004, **20**, 8604–8611.

10. S. Krishnadasan, J. Tovilla, R. Vilar, A. J. deMello, and J. C. deMello, *J. Mater. Chem.*, 2004, **14**, 2655–2660.
11. A. Abou Hassan, O. Sandre, V. Cabuil, and P. Tabeling, *Chem. Commun.*, 2008, 1783–1785.
12. M. Simmons, C. Wiles, V. Rocher, M. G. Francesconi, and P. Watts, *J. Flow Chem.*, 2013, **3**, 7–10.
13. L. Frenz, A. El Harrak, M. Pauly, S. Begin-Colin, A. D. Griffiths, and J.-C. Baret, *Angew. Chemie, Int. Ed.*, 2008, **47**, 6817–6820.
14. E. Kim, K. Lee, Y.-M. Huh, and S. Haam, *J. Mater. Chem. B Mater. Biol. Med.*, 2013, **1**, 729–739.
15. S. Laurent, S. Dutz, U. O. Häfeli, and M. Mahmoudi, *Adv. Colloid Interface Sci.*, 2011, **166**, 8–23.
16. M. E. Fleet, *J. Solid State Chem.*, 1986, **62**, 75–82.
17. R. M. Cornell and U. Schwertmann, *The Iron Oxides: Structure, Properties, Reactions, Occurrences and Uses*, Wiley-VCH Verlag GmbH & Co. KGaA, 2nd edn., 2003.
18. M. Wen, Q. Li, and Y. Li, *J. Electron Spectros. Relat. Phenomena*, 2006, **153**, 65–70.
19. S. S. Pati and J. Philip, *J. Appl. Phys.*, 2013, **113**, 044314.
20. B. Behdadfar, A. Kermanpur, Hojjat Sadeghi-Aliabadi, M. D. P. Morales, and M. Mozaffari, *J. Magn. Magn. Mater.*, 2012, **324**, 2211–2217.
21. C. Bárcena, A. K. Sra, G. S. Chaubey, C. Khemtong, J. P. Liu, and J. Gao, *Chem. Commun.*, 2008, 2224–6.
22. J. C. Apesteguy, S. E. Jacobo, L. Lezama, G. V Kurllyandskaya, and N. N. Schegoleva, *Molecules*, 2014, **19**, 8387–401.
23. J. Liu, Y. Bin, and M. Matsuo, *J. Phys. Chem. C*, 2012, **116**, 134–143.
24. Z. R. Marand, M. H. R. Farimani, and N. Shahtahmasebi, *Nanomedicine J.*, 2014, **1**, 238–247, 10 pp.
25. Y. Li, Q. Li, M. Wen, Y. Zhang, Y. Zhai, Z. Xie, F. Xu, and S. Wei, *J. Electron Spectros. Relat. Phenomena*, 2007, **160**, 1–6.
26. Y. H. Li, S. Y. An, and C. S. Kim, *IEEE Trans. Magn.*, 2013, **49**, 4287–4290.
27. A. Abou-Hassan, S. Neveu, V. Dupuis, and V. Cabuil, *RSC Adv.*, 2012, **2**, 11263.
28. S. F. Chin, K. S. Iyer, C. L. Raston, and M. Saunders, *Adv. Funct. Mater.*, 2008, **18**, 922–927.

29. K. Kumar, A. M. Nightingale, S. H. Krishnadasan, N. Kamaly, M. Wylenzinska-Arridge, K. Zeissler, W. R. Branford, E. Ware, A. J. de Mello, and J. C. de Mello, *J. Mater. Chem.*, 2012, **22**, 4704–4708.
30. M. E. Fleet, *Acta Crystallogr. Sect. B Struct. Crystallogr. Cryst. Chem.*, 1982, **38**, 1718–1723.
31. Y. Ahn, E. J. Choi, S. Kim, D. H. An, K. U. Kang, B. G. Lee, K. S. Baek and H. N. Oak, *J. Korean Phys. Soc.*, 2002, **41**, 123-128.