

**NJC****One-Pot Preparation of Cationic Charged Pt Nanoparticles Through an Autocatalytic Hydrolysis of Acetylthiocholine**

Journal:	<i>New Journal of Chemistry</i>
Manuscript ID:	NJ-LET-02-2015-000420.R1
Article Type:	Letter
Date Submitted by the Author:	15-Mar-2015
Complete List of Authors:	Ishida, Yohei; Hokkaido University, Division of Materials Science and Engineering Jirasupangkul, Thatchanont; Hokkaido University, Division of Materials Science and Engineering; Chulalongkorn University, International School of Engineering, Faculty of Engineering Yonezawa, Tetsu; Hokkaido University, Division of Materials Science and Engineering, Faculty of Engineering

SCHOLARONE™
Manuscripts

One-Pot Preparation of Cationic Charged Pt Nanoparticles By the Autocatalytic Hydrolysis of Acetylthiocholine

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Yohei Ishida,^a Thatchanont Jirasupangkul^{a†} and Tetsu Yonezawa^{a*}

We propose a novel synthetic approach for cationic charged platinum nanoparticles by the autocatalytic hydrolysis of acetylthiocholine. This method can be extended to platinum group of metals.


In recent years, significant advances have been made toward the development of metallic nanoparticles (NPs)¹ having a controlled size, shape, and composition for applications in photonics,^{2,3} electronics,⁴ medicine,⁵ and catalysis.^{6,7} For these applications, it is imperative to control the size of the metal NPs, and several molecules such as amines, mercaptans, and polymers have been used as stabilizers caused by their good coordination properties.¹

Recently, the self-organization of monodisperse metal NPs has been extensively investigated to considerably broaden the spectrum of their applications.⁸ Several methods have been reported for assembling NPs into superstructures, including the interaction between NPs^{9,10} as well as that between NPs and other host materials such as inorganic nanosheets,^{11,12} cavitands,¹³ and DNA.^{14,15} Such organization between NPs and/or hosts can be achieved through van der Waals, dipole–dipole, and electrostatic interactions as well as other interactions. Moreover, self-assembly can also be achieved by the effect of external electrical¹⁶ field, irradiation,¹⁷ and magnetic¹⁸ field. The regular superstructures of NPs thus obtained can offer unique possibilities such as the control of the coupling between excitons and plasmons¹⁹ and the transfer of excitation energies.²⁰

A major approach for the formation of NP assemblies is by exploiting electrostatic interactions,^{9,10,21} where the charged NPs attach to oppositely charged NPs or hosts via electrostatic interactions and forms superstructures. This self-assembly requires the use of charged NPs; however, reports of the synthesis of cationic charged metal NPs²² are quite limited as compared with those of the synthesis of anionic charged NPs, such as those stabilized by mercaptoundecanoic acid,²³ mercaptopropionic acid,²⁴ or glutathione.²⁵ The scarcity of the reports on cationic charged NPs possibly originates from the low availability and selectability of cationic charged organic stabilizers containing mercapto groups. Meanwhile, cationic charged ligands such as cetyltrimethylammonium bromide have been used as the stabilizing reagent for metal NPs. The mechanism for stabilization involves the

formation of a micelle; hence, as compared to thiol-stabilized systems, the resultant structure is not as stable.²⁶ Moreover, if an easy and facile approach can be developed for the synthesis of thiol-stabilized cationic NPs, the chemistry of supramolecular NP assembly will accelerate, and the synthetic strategies for such structures will considerably broaden.

Herein, we report the synthesis of cationic charged Pt NPs by a novel approach based on organic chemistry. Typically, the synthesis of metal NPs only utilizes metal ions as the metal source, while in our new approach, the Pt ion is used as the metal source and the Pt NPs formed initially act as autocatalysts for the hydrolysis of the mercaptan precursor, namely, acetylthiocholine. By employing this strategy, we can eliminate the chemical synthesis of mercaptan; furthermore, this approach can be widely applicable to a wide variety of metals in the platinum group. To the best of our knowledge, this is the first report of the synthesis of metal NPs by the autocatalytic reaction of a ligand precursor by the formed NPs.



Scheme Hydrolysis from acetylthiocholine to thiocholine.

Cationic charged platinum NPs (Pt NPs) were obtained by the chemical reduction of H₂PtCl₆ with acetylthiocholine (ATC) and NaBH₄. The one-pot synthesis of cationic Pt NPs was performed as follows. First, 5 mL of an H₂PtCl₆ solution (10 mM in methanol) was added into 5 mL of an ATC aqueous solution (10, 20, or 30 mM). Next, the solution mixture immediately turned colloidal, and it was stirred for 30 min. To evaluate transparency, absorption spectra of the solutions were recorded without dilution by using a 1 mm quartz cell (Fig. 1). By the addition of ATC, the absorption of platinum ions at 456 nm (black line) almost disappeared, and large scattering was observed in the whole wavelength region (blue line), which is attributed to the colloidal species formed by the ion complex of PtCl₄²⁻ and ATC⁺. To the colloidal suspension, 1.7 mL of a freshly prepared NaBH₄ aqueous solution (0.4 M) was slowly

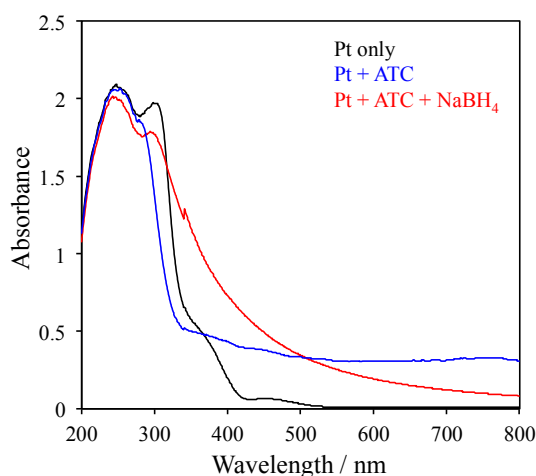


Fig. 1 Absorption spectra of (a) H_2PtCl_4 solution in methanol, (b) after the addition of an acetylthiocholine (ATC) aqueous solution to a, (c) after addition of the NaBH_4 aqueous solution to b. All measurements were performed using a 1 mm quartz cell without dilution.

rate of 1 drop per minute, and the stirring of the mixture was continued for another 3 h. With the addition of several drops, the colour of the suspension started to turn black (red line; Fig. 1), indicating the reduction of Pt ions and the formation of Pt NPs. Notably, NaBH_4 does not catalyze the hydrolysis of ATC. Typically, as catalytic hydrolysis by Pt proceeds under alkaline conditions, the slow addition of NaBH_4 would simultaneously suppress the rapid formation of NPs and enhance the catalytic hydrolysis of ATC to thiocholine (TC).

For transmission electron microscopy (TEM) analysis, the obtained suspension of the Pt NPs was purified by ultracentrifugation. By centrifugation at 150,000 rpm for 3 h, the impurities remained in the supernatant and Pt NPs precipitated out. Furthermore, after repeated ultracentrifugation (3 times) by the addition of pure water to each cycle, purified Pt NPs were obtained. The Pt NPs were then redispersed into water and methanol, and the TEM sample was prepared by dropping an aqueous dispersion of Pt NPs onto a carbon-coated Cu grid. Fig. 2 shows the TEM images and the size distribution of the obtained Pt NPs at a 1:3 mol ratio of Pt:ATC. Highly monodisperse spherical NPs were observed, and the distribution histogram was well described by the Gaussian distribution. The average diameter of the obtained NPs was 2.3 nm. Moreover, at a lower ATC concentration (Pt:ATC = 1:1 and 1:2), slightly larger NPs were obtained (both 2.4 nm). In this study, the change of diameter with ligand concentrations was not significant, and it was within error. This small change is attributed to the synthetic mechanism, where the ATC ligands attached to Pt ions (as an ion complex) can only act as a stabilizer immediately after the addition of NaBH_4 , suggesting that the actual concentration of ATC near Pt ions is the same under different ATC concentrations. Thus, the ATC–Pt ion complex is the actual precursor for the synthesis of Pt NPs in this system, and the obtained size of Pt NPs is thus almost constant under different ATC concentrations.

To clarify whether the catalytic hydrolysis of ATC to TC proceeded as we expected, $^1\text{H-NMR}$ (400 MHz) measurements were performed. All spectra were recorded in D_2O . Fig. 3a shows the $^1\text{H-NMR}$ spectrum of ATC. A sharp singlet peak was observed at 2.4 ppm, corresponding to the methyl group of ACT. Under several relaxation time conditions, no peaks were observed for the purified Pt NPs, caused by the attachment of organic ligands onto the NP surfaces. Typically, treatment by I_2 is employed to extract

mercaptans from metal NPs via the formation of disulfides.²⁷ Hence, Pt NPs were treated with I_2 . The treatment involved the addition of 1

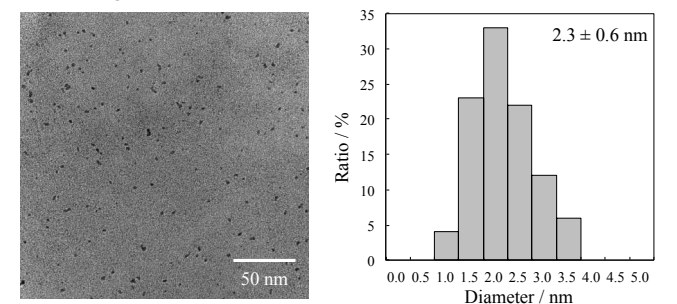


Fig. 2 TEM images and size distribution histogram of Pt nanoparticles prepared at a 1:3 mol ratio of Pt:acetylthiocholine (ATC).

powder into 5 mL of an aqueous suspension containing 1 mg of Pt NPs. A black precipitate formed instantly. The supernatant was dried under vacuum, and the powder obtained was then dissolved in D_2O for $^1\text{H-NMR}$ measurement (Fig. 3b). The characteristic singlet of ATC disappeared, indicating the hydrolysis of ATC to TC. Moreover, we chemically synthesized TC by the hydrolysis of ATC in the presence of HBr according to a previous paper.²⁸ The synthetic TC thus exhibited an NMR spectrum (Fig. 3c) similar to that of the extracted TC by I_2 treatment (3b). Thus, we can conclude that the synthesis of cationic Pt NPs was successfully achieved by the hydrolysis of ATC. FT–IR spectra of ATC, synthetic TC and Pt NPs also support the discussion (see Figure S1 in supporting information). A characteristic C=O stretching vibration of ATC observed at 1680 cm^{-1} disappeared in Pt NPs.

A question that still remains is whether Pt ions or the Pt NPs that are formed initially catalyze the hydrolysis of ATC. To answer this question, a solution mixture containing H_2PtCl_6 and ATC was stirred with NaOH instead of NaBH_4 . This experiment aims to clarify whether Pt ions can act as a catalyst for the hydrolysis of ATC to TC, as NaOH does not reduce Pt ions but only increases the solution pH, similar to that observed for NaBH_4 systems. After stirring for 3 h, the solution mixture containing H_2PtCl_6 , ATC, and NaOH was dried, and the residue was dissolved in $\text{DMSO-}d_6$ for $^1\text{H-NMR}$ measurement. All peaks for ATC were observed in the $^1\text{H-NMR}$ spectrum (Figure S2). Hence, the results from this experiment clearly indicate that the Pt NPs formed initially, not Pt ions, catalyze the hydrolysis of ATC.

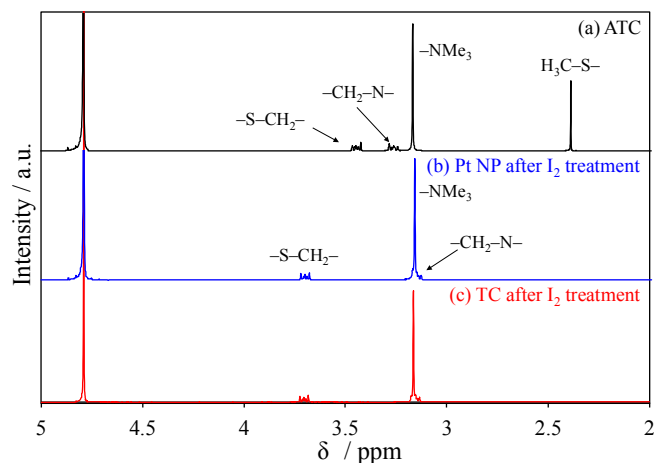


Fig. 3 $^1\text{H-NMR}$ (400 MHz) spectra of (a) acetylthiocholine (ATC), (b) ligand of Pt NPs that was extracted by I_2 treatment, (c) synthesized thiocholine (TC) treated with I_2 . All measurements were performed in D_2O .

As this synthesis depends on the catalytic ability of Pt, it can be extended to other metals in the platinum group, such as Pd. On the other hand, this synthetic route cannot be applied to metals that do not catalyze hydrolysis reactions. To examine the generality of this method for other metals, we examined the synthesis of Pd and Au NPs by using H_2PdCl_4 and HAuCl_4 , respectively, as the metal sources in the presence of ATC. Figs. 4a–4c show TEM images and size distribution histograms of the Pd and Au NPs thus prepared at a 1:3 mol ratio of metal:ATC. The Pd NPs thus obtained had a small size, with the average NP size being $2.0 \text{ nm} \pm 0.6 \text{ nm}$. On the other hand, Au NPs exhibited large aggregates in sizes ranging from 30 to 200 nm. These results clearly indicate that Pd, not Au, can catalyze the hydrolysis of ATC, indicating that only metals in the platinum group can be used for the autocatalysis of thioacetyl compounds. Our previous study on the synthesis of Au NPs having a diameter of 2.7 nm by using TC as a stabilizer also supports this conclusion.²⁸

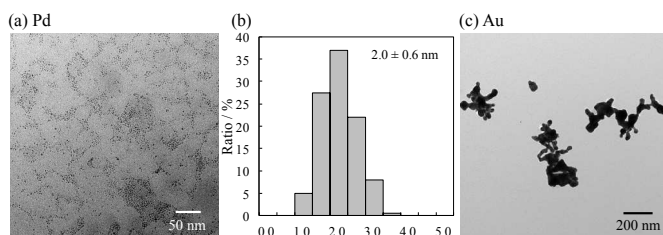


Fig. 4 (a) TEM image of Pd NPs, (b) size distribution histogram of Pd NPs, and (c) TEM image of Au NPs. Pd and Au NPs were prepared at a 1:3 mol ratio of metal:acetylthiocholine (ATC).

In conclusion, we described a novel approach for preparing cationic charged Pt NPs by the autocatalytic hydrolysis of acetylthiocholine. Typically, the synthesis of metal NPs uses only a metal ion as the metal source, while in our proposed approach, the Pt ion is used as the metal source and the Pt NPs formed initially serve as autocatalysts for the hydrolysis of the mercaptan precursor. This strategy eliminates the chemical synthesis of mercaptan; furthermore, it can be applied to a wide variety of metals in the platinum group. Charged, especially cationic charged NPs, thiol-stabilized metal NPs are fascinating as building blocks for supramolecular NP assemblies. Regular NP superstructures can offer unique possibilities, such as exciton–plasmon coupling, magnetic enhancement, as well as the utilization of excitation energy; hence, this study can serve as a novel, simple synthetic approach for broadening the scope of NPs.

Experimental Section

The details of the synthesis of platinum nanoparticles (Pt NPs) are provided in the results and discussion section. H_2PtCl_6 , PdCl_2 , and HAuCl_4 were purchased from Kojima Chemicals (Japan), and acetylthiocholine iodide was purchased from Aldrich. NaBH_4 was obtained from Kanto Chemical. The counter ion of acetylthiocholine iodide was converted to the corresponding chloride by using an ion-exchange column (Organo Amberlite IRA400JCL) before the use.

Acknowledgement

This work is partially supported from Grant-in-Aid for Scientific Research (A) (to TY, 24241041) and from Hokkaido University (to YI and TY). Authors acknowledge Mr. Hideo Genda and Prof. Kunihito Koumoto (Nagoya Univ.) for fruitful discussions. A part of this work is supported by Hokkaido University, microstructural characterization platform as a program of Nanotechnology Platform of the Ministry of Education, Culture, Sports, Science and Technology (MEXT), Japan.

Notes and references

^a Division of Material Science and Engineering, Faculty of Engineering, Hokkaido University, Kita 13, Nishi 8, Kita-ku, Sapporo, Hokkaido 060-8628, Japan.

E-mail address: tetsu@eng.hokudai.ac.jp

† Present address: Undergraduate Student, International School of Engineering, Chulalongkorn University, 254 Phayathai Road, Patumwan, Bangkok 10330, Thailand.

Electronic Supplementary Information (ESI) available: Detailed experimental conditions, FT-IR spectra, additional $^1\text{H-NMR}$ spectra, and magnified TEM images.

- D. V. Talapin, J.-S. Lee, M. V. Kovalenko, and E. V. Shevchenko, *Chem. Rev.*, 2010, **110**, 389.
- Z. Wu and R. Jin, *Nano Lett.*, 2010, **10**, 2568.
- X. Yuan, Z. Luo, Q. Zhang, X. Zhang, Y. Zheng, J. Y. Lee, and J. Xie, *ACS Nano*, 2011, **5**, 8800.
- H. C. Choi, S. Kundaria, D. Wang, A. Javey, Q. Wang, M. Rolandi, and H. Dai, *Nano Lett.*, 2003, **3**, 157.
- E. C. Dreaden, A. M. Alkilany, X. Huang, C. J. Murphy, and M. A. El-Sayed, *Chem. Soc. Rev.*, 2012, **41**, 2740.
- A. Taketoshi, and M. Haruta, *Chem. Lett.*, 2014, **43**, 380.
- N. Toshima and T. Yonezawa, *New J. Chem.* 1988, 1179.
- L. Xu, W. Ma, L. Wang, C. Xu, H. Kuang, and N. A. Kotov, *Chem. Soc. Rev.* 2013, **42**, 3114.
- R. Klajn, K. J. M. Bishop and B. A. Grzybowski, *Proc. Natl. Acad. Sci. USA* 2007, **104**, 10305.
- Q. Yao, Z. Luo, X. Yuan, Y. Yu, C. Zhang, J. Xie, and J. Y. Lee, *Sci. Rep.* 2014, **4**, 3848.
- L. Zhu, S. Letaief, Y. Liu, F. Gervais, and C. Detellier, *Applied Clay Science* 2009, **43**, 439.
- P. Podsiadlo, M. Michel, K. Critchley, S. Srivastava, M. Qin, J. W. Lee, E. Verploegen, A. J. Hart, Y. Qi, and N. A. Kotov, *Angew. Chem. Int. Ed.* 2009, **48**, 7073.
- B. Mondal, N. Kamatham, S. R. Samanta, P. Jagadesan, J. He, and V. Ramamurthy, *Langmuir*, 2013, **29**, 12703.
- T. Yonezawa, S. Onoue, and T. Kunitake, *Kobunshi Ronbunshu*, 1999, **56**, 855.
- M. B. Dickerson, K. H. Sandhage, and R. R. Naik, *Chem. Rev.*, 2008, **108**, 4935.
- S. Acharya, I. Patla, J. Kost, S. Efrima, and Y. Golan, *J. Am. Chem. Soc.*, 2006, **128**, 9294.
- S. Srivastava, A. Santos, K. Critchley, K. S. Kim, P. Podsiadlo, K. Sun, J. Lee, C. Xu, G. D. Lilly, S. C. Glotzer, and N. A. Kotov, *Science*, 2010, **327**, 1355.
- A. Ahniyaz, Y. Sakamoto, and L. Bergström, *Proc. Natl. Acad. Sci. U.S.A.*, 2007, **104**, 17570.
- P. Lodahl, A. Floris Van Driel, I. S. Nikolaev, A. Irman, K. Overgaag, D. Vanmaekelbergh, and W. L. Vos, *Nature* 2004, **430**, 654.
- E. V. Shevchenko, M. Ringler, A. Schwemer, D. V. Talapin, T. A. Klar, A. L. Rogach, J. Feldmann, and A. P. Alivisatos, *J. Am. Chem. Soc.*, 2008, **130**, 3274.
- F. Aldeek, M. A. H. Muhammed, G. Palui, N. Zhan, and H. Mattoussi, *ACS Nano*, 2013, **7**, 2509.
- A. M. Kalsin, B. Kowalczyk, S. K. Smoukov, R. Klajn, and B. A. Grzybowski, *J. Am. Chem. Soc.*, 2006, **128**, 15046.
- Z. Zhang, L. Xu, H. Li, and J. Kong, *RSC Adv.*, 2012, **3**, 59.
- M. Kondon, J. Kim, N. Udawatte, and D. Lee, *J. Phys. Chem. C*, 2008, **112**, 6695.
- S. Link, A. Beeby, S. FitzGerald, M. A. El-Sayed, T. G. Schaaff, and R. L. Whetten, *J. Phys. Chem. B*, 2002, **106**, 3410.
- L. Vigderman, P. Manna, and E. R. Zubarev, *Angew. Chem. Int. Ed.* 2011, **51**, 636–641.

27. A. C. Templeton, M. J. Hostetler, E. K. Warmoth, S. Chen, C. M. Hartshorn, V. M. Krishnamurthy, M. D. Forbes, and R. W. Murray, *J. Am. Chem. Soc.*, 1998, **120**, 4845.
28. T. Yonezawa, S. Onoue, and N. Kimizuka, *Chem. Lett.*, 2002, 1172.