

NJC

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/njc

Correspondence to: Professor Peter C. Junk
College of Science, Technology & Engineering,
James Cook University,
Townsville, Qld 4811, Australia
Email: peter.junk@jcu.edu.au

Rare Earth 3-(4'-Hydroxyphenyl)propionate Complexes – A System Highly Responsive to the Lanthanoid Contraction and Potential Corrosion Inhibitors

Glen B. Deacon,^A Peter C. Junk,^B Winnie W. Lee,^{A,B} Maria Forsyth^C and Jun Wang^{A,B}

^A School of Chemistry, Monash University, Clayton, Vic. 3800, Australia

^B College of Science, Technology & Engineering, James Cook University, Townsville, Qld 4811, Australia

^C ARC Centre of Excellence for Electromaterials Science, Institute for Frontier Materials, Deakin University, Burwood Campus, Australia

Received:

Rare Earth 3-(4'-Hydroxyphenyl)propionate Complexes – A System Highly Responsive to the Lanthanoid Contraction and Potential Corrosion Inhibitors

Glen B. Deacon,^A Peter C. Junk,^B Winnie W. Lee,^{A,B} Maria Forsyth^C and Jun Wang^{A,B}

^A School of Chemistry, Monash University, Clayton, Vic. 3800, Australia

^B College of Science, Technology & Engineering, James Cook University, Townsville, Qld 4811, Australia

^C ARC Centre of Excellence for Electromaterials Science, Institute for Frontier Materials, Deakin University, Burwood Campus, Australia

Abstract

Reaction of lanthanoid chlorides or nitrates with sodium 3-(4'-hydroxyphenyl)propionate (Na4hpp) in methanol or water has yielded the complexes [La₄(4hpp)₁₂(H₂O)₆].4H₂O.MeOH (**1**), [Ce₂(4hpp)₆(H₂O)₃].(H₂O).2.5(EtOH) (**2a**) (after crystallization from ethanol), [Ho(4hpp)₃(H₂O)₂] (**5**), [Er(4hpp)₃(H₂O)₂].1.5(H₂O) (**6**), [Lu(4hpp)₃].H₂O (**7**), as well as the heterobimetallics [NaCe₂(4hpp)₇(H₂O)₂].2(H₂O) (**2b**), [NaPr₂(4hpp)₇(H₂O)₂].2(H₂O) (**3**), and [NaNd₂(4hpp)₇(H₂O)(MeOH)].(H₂O).3(MeOH) (**4**). The structures of the homometallic complexes **1**, **2a**, **6**, **7** reveal one-dimensional coordination polymers and vividly illustrate the effect of the lanthanoid contraction with a decline in coordination numbers in the series from 9-11 (**1**), 9,10 (**2a**), 8 (**6**) to 7 (**7**) through variations in carboxylate coordination and ligation of water. The bimetallic complexes **2a** and **4** each exhibit *five* different carboxylate binding modes as well as coordination of the 4-OH substituent of 4hpp to sodium thereby linking 1-D polymer chains into a 2-D network with both 9 and 10 coordinate Ln atoms and 6 coordinate sodium. Bulk products after drying lose solvent of crystallization in some cases (**2a**, **6**), or exchange MeOH for water (**4**). X-ray powder diffraction indicates bulk **2b** and **3** are isotypic, as are bulk **5** and **6**. In contrast with the excellent corrosion protection of lanthanum 4-hydroxycinnamate, compound **1** is ineffective in preventing corrosion of mild steel, thereby establishing the importance of the –CH=CH– structural unit of the former in its

anti-corrosion properties. However the flexible -CH₂-CH₂- chain of the 4hpp ligand enables crystal engineering of its lanthanoid complexes in a wide variety of structures as well as effective crystallization for structure determination, whereas the analogous 4-hydroxycinnamates have so far evaded structural characterization except for Ln = La, Ce owing to crystallization problems.

Keywords: Lanthanoids; Rare Earths; Carboxylates; Crystal Structures; Lanthanoid Contraction

Introduction


Although the 20% decline in ionic radii¹ from La^{3+} to Lu^{3+} might be expected to lead to a reduction in coordination numbers for a series of analogous complexes, the actual situation is complicated.² Thus in the case of cyclopentadienyllanthanoids, the coordination numbers of the $[\text{LnCp}_3]$ complexes decrease from 11 to 8 from $[\text{LaCp}_3]$ to $[\text{LuCp}_3]$ with intermediate 10 and 9 coordinate derivatives,^{3,4} whereas the $[\text{LnCp}_3(\text{thf})]$ (thf = tetrahydrofuran) complexes are all ten coordinate.^{3,4} Accordingly, it remains a challenge to harness the ionic radius reduction to engineer predetermined structural outcomes. However, use of multidentate ligands to cage or wrap the metal ions is a useful approach to block coordination number change.⁵

In conjunction with our studies of the anti-corrosion properties of rare earth cinnamates ($[\text{Ln}(\text{cinn})_3]$) and 4-substituted cinnamates ($[\text{Ln}(4\text{-Xcinn})_3(\text{solv})_n]$ ($\text{X} = \text{OH}, \text{NO}_2, \text{Cl}, \text{MeO}$; $\text{solv} = \text{H}_2\text{O}/\text{MeOH}$)^{6,7} (as potential replacements for the toxic⁸ commonly used⁹ metal chromates) where lanthanum 4-hydroxycinnamate proved to be the optimum compound,^{6,7} we have determined the structures of a range of rare earth cinnamates¹⁰ adding to earlier studies.¹¹ This revealed just two structural series, La-Dy (nine coordinate, 1-D polymer) and Dy-Lu, Y (seven coordinate, 1-D polymer), with Dy able to crystallise in both forms.¹⁰ In the case of $[\text{Ln}(4\text{-Xcinn})_3(\text{solv})_n]$ complexes, the better protection agents, considerable difficulty was encountered in obtaining single crystals, and only $[\text{Ce}(4\text{-OHcinn})_3(\text{MeOH})_2(\text{H}_2\text{O})].\text{H}_2\text{O}$ was structurally characterised,¹² as well as an earlier isomorphous La complex.¹³ Although X-ray powder diffraction suggested more than one structural class for each group with the same X substituent, crystallization difficulties frustrated establishing defined structural changes induced by the lanthanoid contraction. This has led us to investigate complexation by the reduced 4-hydroxycinnamate, namely 3-(4'-hydroxyphenyl)propionate ions, in the expectation that replacing the rigid $-\text{CH}=\text{CH}-$ linker of cinnamate by a more flexible $-\text{CH}_2-\text{CH}_2-$ unit would facilitate crystallization and enable engineering of a progressive structural change as the Ln^{3+} radius declines. Accordingly, we now report the preparations and structures of rare earth 3-(4'-hydroxyphenyl)propionates, $[\text{Ln}(4\text{hpp})_3(\text{solv})_n]$ and the bimetallics $[\text{NaLn}(4\text{hpp})_4(\text{H}_2\text{O})_2]$, where the lanthanoid contraction has been utilised to give several structural classes. In addition, $[\text{La}_4(4\text{hpp})_{12}(\text{H}_2\text{O})_6]$ was found to be ineffective as a corrosion inhibitor thereby showing the importance of the $-\text{CH}=\text{CH}-$ unit in the effective inhibitor properties of lanthanum 4-hydroxycinnamate.

Results & Discussions

Syntheses and Characterisation

Metathesis reactions of rare earth metal salts with 3-(4'-hydroxyphenyl)propionic acid (H(4hpp)) deprotonated *in situ* with aqueous NaOH, or the preformed sodium salt (mole ratio 1:3) yield rare earth complexes $[\text{Ln}(\text{4hpp})_3(\text{solv})_n]$ (Scheme 1 Ln = La (**1**), Ce (**2a**), Ho (**5**), Er (**6**), Lu (**7**)).

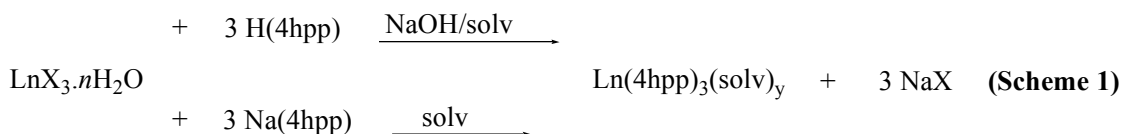

Whilst use of CeCl_3 provided $[\text{Ce}_2(\text{4hpp})_6(\text{H}_2\text{O})_3] \cdot \text{H}_2\text{O} \cdot 2.5\text{EtOH}$ (**2a**) in low yield, use of $\text{Ce}(\text{NO}_3)_3$ gave the bimetallic complex $[\text{NaCe}_2(\text{3hpp})_7(\text{H}_2\text{O})_2] \cdot 3\text{H}_2\text{O}$ (**2b**). For Pr and Nd, bimetallic complexes $[\text{NaLu}_2(\text{4hpp})_7(\text{solv})_n]$ (Ln = Pr (**3**), Nd (**4**)) were obtained regardless of the use of chloride or nitrate reactant. In several cases, the bulk product was obtained as a precipitate and single crystals were obtained by slow evaporation of the filtrate (**3**, **6**, **7**). Single crystals of **2a** were derived from recrystallization of the bulk product from ethanol, crystals of **2b** were mixed with bulk product, whilst **1** and **4** were initially isolated as crystals. Precipitated **5** was microcrystalline but single crystals could not be obtained.

The characterisation of the bulk samples of compounds **1-7** was carried out after drying over silica gel to constant weight. This resulted in the loss of solvent of crystallisation for some of the complexes from the compositions derived by X-ray crystallography for single crystals. Thus, compounds **2a** and **6** lost lattice solvent from the single crystal composition whilst both lattice and coordinated methanol of single crystals of **4** were replaced by water. However, bulk **1** and **2b** had the same bulk and crystal composition. On the other hand, microanalysis and TGA of bulk **7** were indicative of one more water of crystallisation than in the single crystals, suggesting the powdered bulk material was hygroscopic.

The X-ray powder pattern of bulk **2b** was in agreement with that simulated from single crystal data and was also in agreement with that of **3** indicating **2b** and **3** are isotypic (*d*-spacings Experimental Section, Fig S1). It was different from that generated from crystal data for **4**, which has coordinated methanol and methanol of crystallisation. Powder data of bulk **5** and **6** are in agreement but differ from that simulated from the crystal structure of **6**, which has additional water of crystallisation (Fig S2). Consistent with the observation that bulk **7** has more water of crystallisation than the single

crystals, the powder pattern of the former differs from that simulated from single crystal data (d -spacings, Experimental Section).

Broad infrared bands at 3600-3200 cm^{-1} (Table 1) are attributable to overlap of $\nu(\text{OH})$ of water (both coordinated and lattice) and of the 4-hydroxy group of the 4hpp ligand. Antisymmetric carboxylate stretching gave rise to at least two intense bands at 1580-1515 cm^{-1} , whereas the symmetric mode gave only a single band at 1420-1404 cm^{-1} . The separation between $\nu_{\text{as}}(\text{CO}_2)_{\text{ave}}$ and $\nu_{\text{s}}(\text{CO}_2)$ (145-104 cm^{-1}) (Table 1) are close to that (120 cm^{-1}) of the sodium salt consistent¹⁴ with the predominantly bridging nature of the carboxylate coordination (below). However, given the complexity of the carboxylate bonding (Table 2), it is fruitless to seek further structure/IR correlation. This is well illustrated by the similarity of the $\nu_{\text{as}}(\text{CO}_2)$ frequencies of **4**, **6**, **7**, which have entirely different carboxylate coordination. The range of different bridging and chelating modes is observed in the structures of this series of complexes are shown in Figure 1.

Table 1: Selected IR bands of Ln^{III} 3-(4'-hydroxyphenyl)propionate complexes.

Compounds	Main bands (cm^{-1})			
	$\nu(\text{OH})_{\text{water}}$	$\nu_{\text{as}}(\text{CO}_2^-)$	$\nu_{\text{s}}(\text{CO}_2^-)$	$\Delta\nu = (\nu_{\text{as}} - \nu_{\text{s}})_{\text{avg}}$
Na(4hpp)	3404 m br, 3350 m br	1556 s, 1517 s	1417 s	120
$[\text{La}_4(4\text{hpp})_{12}(\text{H}_2\text{O})_6] \cdot 4(\text{H}_2\text{O}) \cdot (\text{MeOH})$ 1	3368 m br, 3286 m br, 3172 br m	1529 s, 1516 s	1419 s	104
$[\text{Ce}_2(4\text{hpp})_6(\text{H}_2\text{O})_3] \cdot (\text{H}_2\text{O}) \cdot 2.5(\text{EtOH})$ 2a	3350 m br, 3205 m br	1536 s, 1515 s	1419 s	107
$[\text{NaCe}_2(4\text{hpp})_7(\text{H}_2\text{O})_2] \cdot 3(\text{H}_2\text{O})$ 2b	3606 w, 3369 m br	1578 m, 1527 s, 1516 s	1418 s	122
$[\text{NaPr}_2(4\text{hpp})_7(\text{H}_2\text{O})_2] \cdot 3(\text{H}_2\text{O})$ 3	3623 w, 3271 s br	1580 s, 1516 s	1417 s	131
$[\text{NaNd}_2(4\text{hpp})_7(\text{H}_2\text{O})(\text{MeOH})] \cdot (\text{H}_2\text{O}) \cdot 3(\text{MeOH})$ 4	3530 m, 3256 s br	1579 m, 1536 s, 1516 s	1407 s	137
$[\text{Ho}(4\text{hpp})_3(\text{H}_2\text{O})_2]$ 5	3566 w, 3432 m br, 3220 m br	1577 m, 1543 s, 1515s	1417 m	128
$[\text{Er}(4\text{hpp})_3(\text{H}_2\text{O})_2] \cdot 1.5(\text{H}_2\text{O})$ 6	3567 w, 3436 m br, 3221 m br	1578 m, 1543 s, 1515 m	1419 m	126

[Lu(4hpp) ₃].(H ₂ O) 7	3568 m, 3256 s br, 3197 s br	1581 s, 1550 s, 1515 s	1404 s	145
--	------------------------------------	------------------------------	--------	-----

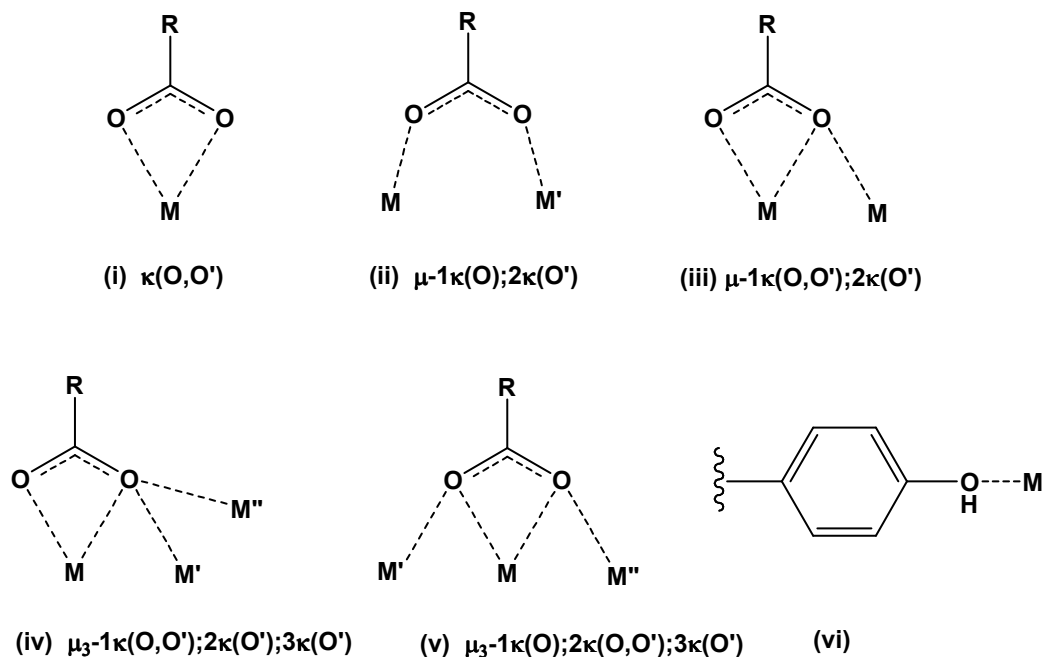


Figure 1: Different coordination modes observed by the 3-(4'-hydroxyphenyl)propionate ion.

X-ray crystal structures

Monometallic 1D polymeric chains of [La₄(4hpp)₁₂(H₂O)₆].4(H₂O).(MeOH) (**1**), [Ce₂(4hpp)₆(H₂O)₃].(H₂O).2.5(EtOH) (**2a**), [Er(4hpp)₃(H₂O)₂].1.5(H₂O) (**6**) and [Lu(4hpp)₃].(H₂O) (**7**)

The structures of the monometallic complexes [La₄(4hpp)₁₂(H₂O)₆].4(H₂O) (**1**), [Ce₂(4hpp)₆(H₂O)₃].(H₂O).2.5(EtOH) (**2a**), [Er(4hpp)₃(H₂O)₂].1.5(H₂O) (**6**) and [Lu(4hpp)₃].(H₂O) (**7**) show considerable changes with the lanthanoid contraction. The most obvious is the decrease in the coordination number of the metal atoms as well as the decrease of the average Ln-O bond distances (Table 2). Details of bond distances and angles are in Supplementary Data. The asymmetric units also show a decrease of unique metal centres with complex **1** having four unique metal atoms, **2a** having two unique metal centres whilst **6** and **7** have only one unique metal atom. The coordination modes of the carboxylate ligands (Fig. 1) vary both across the unique metal centres within the compound and more strikingly across the four different compounds (Table 2). The two compounds of the larger

metal ions, **1** and **2a**, both show the same three different coordination modes (μ -1 κ (O,O');2 κ (O')), (κ (O,O')) and (μ -1 κ (O);2 κ (O')) but in different combinations (Table 2). On the other hand, the complexes of the two smaller ions each show quite different coordination patterns. Compound **6** has (κ (O,O')) and (μ -1 κ (O);2 κ (O')) coordination modes whilst compound **7** has (μ -1 κ (O,O');2 κ (O')) and (μ -1 κ (O);2 κ (O')) ligation, (Table 2), quite a profound change for a small change in ionic radius. Furthermore, **7** is the only complex without a chelating ligand (binding mode (i)) and the sole homoleptic complex without a water coligand even though it has water of crystallisation.

Table 2. Coordination numbers, carboxylate ligation and average Ln-O bond distances for **1-7**.

Compound	Ln atom	Coordination Number	Ligation	Ave Ln-O (\AA)
1	Ln(1)	11	4 x (iii) ^a ; 1 x (iii) ^b ; 2 x H ₂ O	2.67
	Ln(2)	9	1 x (i); 1 x (iii) ^a ; 4 x (iii) ^b ; H ₂ O	2.54
	Ln(3)	9	1 x (i); 1 x (ii); 1 x (iii) ^a ; 3 x (iii) ^b ; H ₂ O	2.54
	Ln(4)	10	1 x (ii); 3 x (iii) ^a ; 1 x (iii) ^b ; 2 x H ₂ O	2.63
2a	Ce(1)	9	1 x (i); 1 x (ii); 1 x (iii) ^a ; 3 x (iii) ^b ; H ₂ O	2.53
	Ce(2)	10	1 x (ii); 3 x (iii) ^a ; 1 x (iii) ^b ; 2 x H ₂ O	2.57
2b*	Ce(1)	10	1 x (ii); 1 x (iii) ^a ; 1 x (iv) ^a ; 1 x (iv) ^b ; 2 x (v) ^a	
	Ce(2)	9	1 x (i); 1 x (ii); 1 x (iii) ^a ; 1 x (iii) ^b ; 2 x (v) ^b ; H ₂ O	
	Na(1)	6	1 x (iii) ^b ; 1 x (iv) ^b ; 2 x (v) ^b ; 1 x (vi); H ₂ O	
4	Nd(1)	10	1 x (ii); 1 x (iii) ^a ; 1 x (iv) ^a ; 1 x (iv) ^b ; 2 x (v) ^a	2.55
	Nd(2)	9	1 x (i); 1 x (ii); 1 x (iii) ^a ; 1 x (iii) ^b ; 2 x (v) ^b ; H ₂ O	2.50
	Na(1)	6	1 x (iii) ^b ; 1 x (iv) ^b ; 2 x (v) ^b ; 1 x (vi); MeOH	
6	Er(1)	8	2 x (i); 2 x (ii); 2 x H ₂ O	2.36
7	Lu(1)	7	4 x (ii); 1 x (iii) ^a ; 1 x (iii) ^b	2.27

^a chelating; ^b unidentate, * provided for connectivity purposes only

Even though coordination of the metal centres La(3) and La(4) in complex **1** correspond to those of Ce(1) and Ce(2) in complex **2a**, the eleven coordinate La(1) and nine-coordinate La(2) have no counterparts in **2a**. As a result, the 1D polymeric chain in complex **2a** propagates in the mirroring of the asymmetric unit in the sequence of Ce(1)#...Ce(1)...Ce(2)...Ce(2)# whilst complex **1** propagates in the sequence La(4)#...La(1)...La(2)...La(3)...La(4)...La(1)# (Figure 2). In the asymmetric unit of complex **1**, the two nine coordinate metal atoms, La(2) and La(3), have two pairs of chelating carboxylate oxygen atoms (La(2)-O(13,14;16,17) and La(3)-O(19,20;22,23)) with O(17) and O(20)

bridging the two metal centres (μ -1 κ (O,O'):2 κ (O')). The other coordination sites are occupied by three other bridging carboxylate oxygen atoms (La(2)-O(5,8,11) and La(3)-O(25,29,32)) and one water molecule each. La(1) is eleven coordinate with four chelating carboxylate ligands, O(1,2;4,5;7,8;10,11), all also bridging μ -1 κ (O,O');2 κ (O'), two water molecules O(1Z, 2Z), and an oxygen atom O(35)# bridging to La(4)# in an adjacent asymmetric unit. La(4) differs from La(1) in that there are only three chelating carboxylate ligands O(28,29;31,32;34,35). An oxygen atom O(26) from a (μ -1 κ (O);2 κ (O')) ligand (the only one in the asymmetric unit) and two water molecules make up the coordination sphere. The O(25,26) carboxylate ligand is regarded as μ -1 κ (O);2 κ (O') rather than μ -1 κ (O,O');2 κ (O') as La(4)···O(25) is 3.191(5) Å and is 0.23 Å longer than the next longest La-O distance (La(1)-O(5) 2.960(5) Å).¹⁵ A similar (μ -1 κ (O);2 κ (O')) carboxylate(O(7,8)) is seen in complex **2a** where the Ce(1)...O(8) and Ce(2)...O(7) values of 3.59 Å and 4.09 Å are far too long to be part of chelating interactions.¹ In **1**, the three longest La-O bond lengths (La(1)-O(5)); La(1)-O(8); La(4)-O(32), all >0.2 Å longer than the next longest), all involve the bridging oxygen of a chelating oxygen pair of a 1 κ (O,O'):2 κ (O') ligand (Table S1/Fig. 2). The range of La-O bonds falls from 0.43 Å for La(1) to 0.24 Å (La(3)) and 0.17 Å (La(2)) with decrease in coordination number from 11 to nine. The La-O bond length range for **1** (Table S2) is similar to that (2.443-3.06(2) Å) of [La₃(O₂CPh)₉(dmf)₃] which has nine and 11-coordinate La atoms.¹⁶ In ten coordinate [La₂(ad)₃(H₂O)₄] (adH₂ = adipic acid), the range of La-O bond lengths and the average La-O length¹⁷ are similar to those of La(4) of **1**. With **2a**, the average Ce-O bond length of nine-coordinate Ce(1) and ten coordinate Ce(2) relate to corresponding values of nine coordinate Ce in cerium phenylene-1,2-dioxyacetate¹⁸ and ten coordinate Ce in cerium pimelinate respectively.¹⁹

The asymmetric unit of complex **1** is almost linear with angles of 170.1° and 170.6° between La(1)–La(2)–La(3) and La(2)–La(3)–La(4) respectively. However, the angles formed between adjacent asymmetric units are smaller (150.5° and 150.4° between La(4)#–La(1)–La(2) and La(3)–La(4)–La(1)# respectively). This results in a slight wave with nodes between the repeating asymmetric units in the 1D polymeric chain (Fig. 2). Most of the chelating carboxylates have varying degrees of asymmetry with the exception of ligands O(13,14) and O(16,17) which show symmetrical chelation. A similar trend is observed in complex **2a** where most of the chelating carboxylate ligands are asymmetric except for ligand O(16,17). Although the asymmetric units of complexes **1** and **2a** contain a (μ -1 κ (O');2 κ (O')) carboxylate bridge, the La(3)–O(25)–C(73)–O(26)–La(4) bridge is asymmetric due to a twist of the carboxylate group whilst the Ce(1)–O(7)–C(19)–O(8)–Ce(2) bridge is more symmetrical.

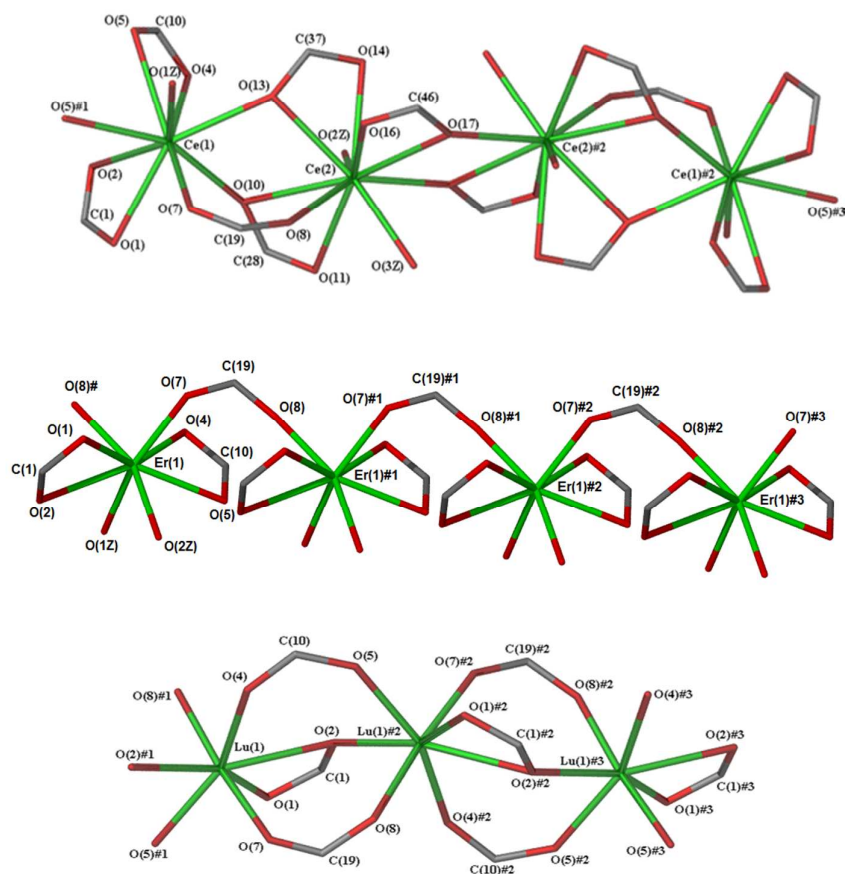


Figure 2: The propagation of the 1D polymeric chains of $[\text{La}_4(4\text{hpp})_{12}(\text{H}_2\text{O})_6] \cdot 4(\text{H}_2\text{O})$ (**1**) and $[\text{Ce}_2(4\text{hpp})_6(\text{H}_2\text{O})_3] \cdot 2.5(\text{EtOH}) \cdot (\text{H}_2\text{O})$ (**2a**), $[\text{Er}(4\text{hpp})_3(\text{H}_2\text{O})_2] \cdot 1.5(\text{H}_2\text{O})$ (**6**) and $[\text{Lu}(4\text{hpp})_3] \cdot (\text{H}_2\text{O})$ (**7**). Symmetry equivalents used: complex **1** (#1 $x, y-1, z$; #2 $x, 1+y, z$), complex **2a** (#1 $1-x, -y, 1-z$; #2 $1-x, 1-y, 1-z$; #3 $x, 1+y, z$), complex **6** (# $x, 1+x, z$; #1 $x-1/2, 1/2-y, z$; #2 $1/2-x, 1/2+y, z-1/2$), and complex **7** (#1 $1-x, 1/2+y, 3/2-z$; #2 $1-x, y-1/2, 3/2-z$; #3 $x, y-1, z$).

*Bimetallic 2D polymeric networks of $[\text{NaCe}_2(4\text{hpp})_7(\text{H}_2\text{O})_2] \cdot 3(\text{H}_2\text{O})$ (**2b**) & $[\text{NaNd}_2(4\text{hpp})_7(\text{H}_2\text{O})(\text{MeOH})] \cdot (\text{H}_2\text{O}) \cdot 3(\text{MeOH})$ (**4**)*

Crystal structures of $[\text{NaCe}_2(4\text{hpp})_7(\text{H}_2\text{O})_2] \cdot 3(\text{H}_2\text{O})$ (**2b**) and $[\text{NaNd}_2(4\text{hpp})_7(\text{H}_2\text{O})(\text{MeOH})] \cdot (\text{H}_2\text{O}) \cdot 3(\text{MeOH})$ (**4**) were obtained, but the former only provided the connectivity owing to the low precision of the data. Comparison of X-ray powder patterns of the bulk samples of complex **2b** and $[\text{NaPr}_2(4\text{hpp})_7(\text{H}_2\text{O})_2] \cdot 3(\text{H}_2\text{O})$ (**3**) showed them to be isotypic. However, attempts to obtain suitable crystals of complex **3** for a structure determination were unsuccessful, repeatedly yielding microcrystalline needles. Although the ligand binding modes of both complexes **2b** and **4** are very similar, they are anisotypic as their unit cells are different with inequivalent β -

angles and the ligation of a methanol instead of water molecule at the sodium centre of complex **4**. The solvent of crystallisation is also different as complex **2b** contains three lattice water molecules whilst complex **4** contains three methanol molecules and one water molecule.

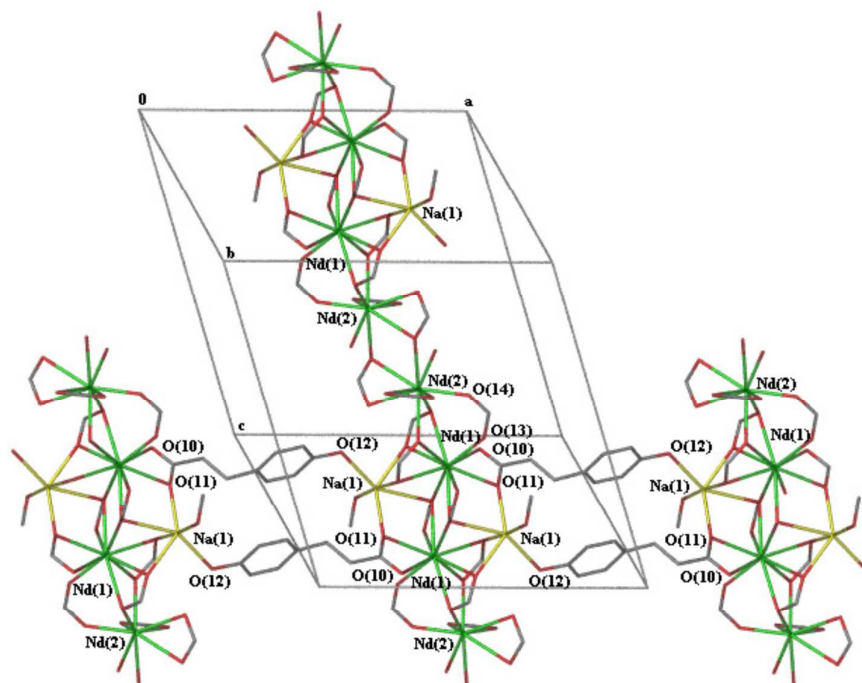


Figure 3: The propagation of the 2D polymeric network of $[\text{NaND}_2(4\text{hpp})_7(\text{H}_2\text{O})(\text{MeOH})] \cdot (\text{H}_2\text{O}) \cdot 3(\text{MeOH})$ (**4**) showing the bridging of the phenolic oxygen atom to the sodium metal centre from a neighbouring chain. Non-metal atoms except those immediately surrounding the metal centres are omitted for clarity.

Both complexes **2b** and **4** form a bimetallic two dimensional network with very similar ligand binding modes to the metal centres. The same five unique carboxylate binding modes are observed in both complexes. There are two $\mu_3\text{-}1\kappa(\text{O}); 2\kappa(\text{O}, \text{O}'); 3\kappa(\text{O}')$, two $\mu\text{-}1\kappa(\text{O}, \text{O}'); 2\kappa(\text{O}')$ and one each of $\mu_3\text{-}1\kappa(\text{O}, \text{O}'); 2\kappa(\text{O}'); 3\kappa(\text{O}')$, $\mu\text{-}1\kappa(\text{O}); 2\kappa(\text{O}')$ and $\kappa(\text{O}, \text{O}')$. Adjacent one dimensional polymeric chains of repeating asymmetric units (through bridged $\text{Ln}(2) \dots \text{Ln}(1) \dots \text{Ln}(1) \# \dots \text{Ln}(2) \#$ chains) of these complexes are bridged by the phenolic oxygen atom of one the ($\mu\text{-}1\kappa(\text{O}, \text{O}'); 2\kappa(\text{O}')$) ligands (O(7,8)) to a sodium metal centre of a neighbouring chain (Fig. 3). The metal–metal distances between Nd(1) ... Nd(2) and Nd(1) ... Na(1) in complex **4** are 4.167 Å and 3.608 Å respectively. There are two unique Ln metal centres with one being ten coordinate and the second being nine coordinate whilst the sodium metal centre is six coordinate in **2b** and **4** (Table 2). Comparison of the Nd-O bond

lengths for ten coordinate Nd(1) (Table S6) and nine coordinate Nd(2) with those of ten coordinate Nd in the adipate complex¹⁷ and nine coordinate Nd in the anthranilate complex²⁰ respectively, shows the values are similar.

Given the facile loss of solvent of crystallisation for **2a** and **6** as indicated by microanalysis and TGA and the facile replacement of coordinated and lattice MeOH by water in **4**, it is probable that bulk **2a**, **4** and **6** retain the structures determined for single crystals.

Corrosion inhibition

Because of our discovery that lanthanum 4-hydroxycinnamate provides the optimum corrosion protection for mild steel from examination of a wide range of lanthanoid carboxylates including many cinnamates and substituted cinnamates,^{6,7} examination of the anti-corrosion properties of lanthanum 3-(4'-hydroxyphenyl)propionate **1** was of considerable interest. Both **1** and sodium 3-(4'-hydroxy)propionate were examined for their protective properties (200 ppm concentration) for a mild steel coupon in 0.01M aqueous sodium chloride. Visual inspection of both coupons and examination under an optical microscope showed extensive corrosion (Fig. S3), hence neither showed useful inhibitor properties at a concentration at which lanthanum 4-hydroxycinnamate is particularly effective. The sodium salt was also ineffective at 2000 ppm. Because of the poor qualitative performance, electrochemical evaluation by linear polarisation resistance or potentiodynamic polarisation was not carried out. These negative results *are highly significant*, as they show that the –CH=CH– structural unit of the cinnamate/4-hydroxycinnamate ion is an essential structural feature for effective inhibitor performance.

Dissolution of **1** requires breakup of the coordination polymer, and the subsequent poor inhibitor performance of **1** may be related to low stability of La/4hpp complexes in solution. The mass spectrum shows *no* La³⁺ containing complexes in the +ve ESMS, and *no* La(4hpp) species in the –ve ESMS even though the complex was examined in the poor donor solvent methanol. Thus carboxylate coordination is completely dissociated in solution. By contrast, the effective inhibitors lanthanum 4-hydroxycinnamate,²² praseodymium 4-hydroxycinnamate²³ and lanthanum 3-hydroxycinnamate²³ examined in the highly coordination competitive environment of 0.01M aqueous sodium chloride show the existence of [LnL₂Cl₂][–], [LnL₃Cl][–] and [LnL₄][–], complexes which evidently account for the good protective properties.

Although Ln³⁺ ions have some inhibitor properties,^{24,25} La³⁺ is less effective than the optimum Ce³⁺,²⁴ and 4hpp[–] ions have poor inhibitor properties as indicated by the sodium salt (Fig. S3). The lack of stable La/4hpp complexes in solution obviates synergic lanthanoid carboxylate corrosion inhibition observed for lanthanum 4-hydroxycinnamates.^{6,7,25}

Conclusions

From reactions between lanthanoid salts and sodium 3-(4'-hydroxy)propionate both homometallic $[\text{Ln}(4\text{hpp})_3(\text{H}_2\text{O})_n]$ and bimetallic $[\text{NaLn}_2(4\text{hpp})_7]$ complexes have been obtained and representative structures determined. The former are one dimensional polymers for which there is a decrease in coordination number progressively from Ln = La (9-11), Ce (9, 10), Er (8), Lu (7), the last having no coordinated water. By contrast, the bimetallics are 2D networks with a much wider range of carboxylate binding modes and cross chain coordination of the 4-hydroxy substituent to sodium. The La complex is a poor inhibitor of corrosion of mild steel in contrast to the corresponding 4-hydroxycinnamates, thereby establishing that the $-\text{CH}=\text{CH}-$ functionality of the latter is vital to the excellent anti-corrosion behaviour of lanthanum 4-hydroxycinnamate.

Experimental

General details

All commercially available solvents and chemicals were obtained from Sigma-Aldrich, BDH or Ajax and used without further purification. IR spectra were collected on a Perkin-Elmer 1600 Fourier Transform Infra-red Spectrometer (FTIR) as Nujol mulls on NaCl plates. CH analyses were performed by the Campbell Microanalytical Laboratory, University of Otago, New Zealand. Metal analyses were effected by complexometric titrations with EDTA using Xylenol Orange indicator. Thermogravimetric analysis (TGA) was conducted with a Perkin-Elmer Pyris TGA instrument. X-ray powder diffraction (XRD) patterns were obtained on a Philips 1140 powder diffractometer with a Cu K α source and the X-ray diffraction screen processing software, Traces Ver. 6.6.1 was used as a graphical interface. X-ray powder simulations were undertaken with LAZY PULVERIX²⁶ powder generation software from data obtained from low temperature single crystal X-ray measurements.

X-ray crystallography

Single crystals were mounted on fine glass fibres using viscous hydrocarbon oil and collections were carried out at 123 K using an open-flow N₂ Oxford Cryosystems cryostream. Single crystal X-ray crystallographic data were collected using either a Bruker X8 Apex II diffractometer or an Enraf-Nonius Kappa-CCD diffractometer, both utilising graphite monochromated Mo-K α radiation ($\lambda = 0.71013 \text{ \AA}$). Collection and refinement parameters are shown in Table 3. Data were initially processed with the program SAINT²⁷ or DENZO program²⁸ for the respective instruments. Structures were solved using SHELXS-97²⁹ and refined using conventional alternating least-squares methods with SHELXL-97²⁹ or SHELXL-2014. The program X-Seed³⁰ or Olex2 was used as a graphical interface. Anisotropic thermal parameters were refined for non-hydrogen atoms except some atoms of the disordered fragments (complex **2a**) and lattice solvent molecules (complex **4**). Most hydrogen atoms were calculated and refined with a riding model, but those of lattice water molecules were located from the difference Fourier maps. High mobility of lattice solvent molecules in compounds **2a** and **6** results to destabilisation of the refinement, thus they were treated with Platon/Squeeze program. Bond distances and angles are in Supplementary Data. For compound **2b**, data were very poor and it is included only for connectivity purposes.

Crystallographic data (excluding structure factors) for the structures reported in this paper and associated ESI have been deposited with the Cambridge Crystallographic Data Centre as supplementary numbers CCDC 1055961 for compound **2a**, 1055962 for compound **6**, 1055963 for compound **1**, 1055964 for compound **7**, 1055965 for compound **2b**, 1055966 for compound **4**.

Copies of the data can be obtained free of charge on application to CCDC, 12 Union Road, Cambridge, CB2 1EZ, UK (fax: +44 (0) 1223 336033; e-mail: deposit@ccdc.cam.ac.uk).

Syntheses

Treatment of 3-(4'-hydroxyphenyl)propionic acid, H(4hpp), deprotonated *in situ* with aqueous sodium hydroxide or of the preformed sodium salt (**1,6**), with hydrated lanthanoid chloride (**1, 2a, 7**) or nitrate (**2b, 3-6**), (mole ratio 3:1) in methanol (**1-5**) or water (**6-7**) at pH 6 gave lanthanoid 3-(4'-hydroxyphenyl)propionate complexes. The reaction mixtures were stirred at room temperature for a minimum of 3 hours. Where precipitates (**2b, 3, 5-7**) formed, they were filtered off and dried over silica. **1** and **4** deposited as crystals whilst crystals of **2b** were mixed with the bulk precipitate. Crystals (**3, 6, 7**) were obtained upon the slow evaporation of the mother liquor but the reaction with holmium nitrate (**5**), only gave a microcrystalline precipitate. Data reported are for the bulk precipitated samples except for complexes **1, 2a** and **4** which were crystalline samples. Bulk samples were dried to constant weight in a desiccator over silica gel.

[Na(4hpp)]

H(4hpp) was neutralised with aqueous NaOH (0.25 M) in EtOH resulting in a clear colourless solution. It was dried *in vacuo* and the resultant white solid was rinsed with diethyl ether, filtered and dried over silica gel. The isolated Na(4hpp) salt was used for the preparation of the lanthanoid complexes **1, 6**.

(Yield: 100%).

IR (v/cm^{-1}): 3404 br m, 3350 br m, 1883 vw, 1658 w, 1614 w, 1601 w, 1556 s, 1517 s, 1444 s, 1417 s, 1296 w, 1256 m, 1235 m, 1177 w, 1160 w, 1105 m, 1015 w, 934 w, 826 s, 779 m, 689 m.

^1H NMR (d_6 -DMSO): δ = 6.98 (d, 2 H, $^3J_{\text{H-H}} = 8$ Hz, Ar-H3',5'), 6.66 (d, 2 H, $^3J_{\text{H-H}} = 8$ Hz, Ar-H2',6'), 2.68 (t, 2 H, $^3J_{\text{H-H}} = 8$ Hz, H2), 2.16 (t, 2 H, $^3J_{\text{H-H}} = 8$ Hz, H3). The OH proton was not observed.

[La₄(4hpp)₁₂(H₂O)₆].4(H₂O).(MeOH) (**1**)

Colourless crystals (Yield: 57%) C₁₀₉H₁₃₂La₄O₄₇ (2749.81) calculated: C 47.61, H 4.84, La 20.20%; found: C 47.89, H 4.35, La 20.86%.

IR (v/cm^{-1}): 3368 m br, 3286 m br, 3172 m br, 1612 m, 1591 m, 1529 s, 1516 s, 1419 s, 1340 m, 1314 w, 1259 m, 1238 m, 1209 w, 1172 w, 1103 w, 1071 w, 1045 w, 1017 w, 963 w, 829 m, 695 w.

TGA weight loss: 1.33% (25-65 °C, 1 step, 1 MeOH, calculated 1.16%), 2.40% (65-163 °C, 1 step, 4H₂O, calculated 2.62%), 3.66% (163-335 °C, 1 step, 6H₂O, calculated 3.93%).

ESI-MS [M/z (I/I°)]: (-ve) 92.8 (10) [HOC₆H₄]⁻, 148.9 (100) [C₆H₅(CH₂)₂CO₂]⁻, 165.0 (70) [(4hpp)]⁻, 223.0 (15), 233.0 (5) [La(OH)₂CO₃]⁻, 353.3 (4) [La(OC₆H₄Et)(OMe)₃]⁻. Powder XRD (*d*-spacings Å (I/I°)): 13.64 (32), 12.99 (63), 12.54 (100), 11.19 (22), 10.71 (64), 7.99 (23), 6.68 (69), 6.57 (57), 6.45 (26), 6.30 (33), 6.15 (19), 6.05 (18), 5.38 (21), 5.14 (39), 5.03 (28), 4.91 (27), 4.65 (21), 4.17 (19), 4.10 (21), 3.87 (20), 3.74 (26), 3.72 (29), 3.65 (18), 3.58 (23), 3.36 (27), 2.89 (37), 2.86 (17), 2.78 (20), 2.71 (20), 2.50 (23), 2.46 (33), 2.32 (18). *d*-Spacings simulated from X-ray structure: 13.34 (31), 13.10 (100), 12.54 (72), 10.92 (54), 7.91 (14), 6.73 (16), 6.55 (11), 6.50 (10), 6.27 (6), 6.01 (4), 5.46 (5), 5.07 (9), 5.01 (3), 4.87 (5), 4.63 (6), 4.43 (4), 4.41 (4), 4.03 (5), 3.75 (5), 3.70 (2), 3.65 (2), 3.64 (3), 3.52 (3), 3.42 (2), 2.52 (2), 2.18 (2).

[Ce₂(4hpp)₆(H₂O)₃].(H₂O).2.5(EtOH) (2a)

The product from preparation in methanol was recrystallised from ethanol giving colourless single crystals. [Ce₂(4hpp)₆(H₂O)₄] (ethanol of crystallisation lost) (Yield: 7%) C₅₄H₆₂Ce₂O₂₂ (1343.29) calculated: C 48.28, H 4.65%; found: C 47.95, H 4.50%.

IR (ν/cm⁻¹): 3307 br m, 1612 w, 1595 w, 1531 s, 1515 s, 1417 s, 1312 w, 1236 m, 1171 w, 1102 w, 1043 w, 1021 w, 960 w, 830 m.

[NaCe₂(4hpp)₇(H₂O)₂].3(H₂O) (2b)

White precipitate with colourless single crystals. (Yield: 75%) C₆₃H₇₃Ce₂NaO₂₆ (1549.46) calculated: C 48.83, H 4.75, Ce 18.09%; found: C 48.26, H 4.38, Ce 17.48%.

IR (ν/cm⁻¹): 3606 w, 3369 m br, 1885 w, 1614 m, 1598 m, 1578 m, 1527 s, 1516 s, 1418 s, 1338 w, 1312 w, 1237 s, 1174 w, 1158 w, 1103 w, 1016 w, 949 w, 829 m, 788 w.

TGA weight loss: 3.99% (25-70 °C, 1 step, 3H₂O, calculated 3.48%), 2.22% (70-100 °C, 1 step, 2H₂O, calculated 2.32%).

Powder XRD [*d*-spacings Å (I/I°)]: 14.49 (84), 13.94 (100), 10.97 (44), 9.54 (33), 7.36 (29), 7.08 (39), 6.95 (35), 6.77 (26), 6.18 (22), 6.07 (26), 5.52 (20), 4.72 (20), 3.94 (20). *d*-Spacings simulated from X-ray structure: 14.70 (100), 14.16 (96), 11.14 (24), 9.46 (10), 7.35 (9), 7.08 (6), 7.00 (13), 6.83 (6), 6.13 (4), 6.01 (4), 5.60 (5), 5.57 (5), 5.31 (3), 3.92 (8).

ESI-MS [M/z (I/I°)]: (+ve) 282.3 (34) [Ce(OH)₂(H₂O)₆]⁺, 304.2 (100) [Ce(OC₆H₄(CH₂)₂CO₂)₂]⁺, 321.9 (32) [Ce(4hpp)(OH)]⁺, 338.3 (25), 360.3 (80), 410.0 (15), 428.0 (10) [Ce(4hpp)(OH)₃(H₂O)₄]⁺, 442.0 (14), 469.9 (20), 529.9 (12), 589.8 (12) [NaCe(4hpp)₂(HCO₃)(H₂O)₂]⁺; (-ve) 164.9 (81)

$[4\text{hpp}]^-$, 353.0 (100), 375.2 (15), 540.9 (15), 559.9 (11) $[\text{Ce}(4\text{hpp})_2(\text{OEt})_2]^-$, 679.9 (18)
 $[\text{Ce}(4\text{hpp})_3(\text{OEt})]^-$, 701.8 (15) $[\text{Ce}(4\text{hpp})_3(\text{OH})(\text{H}_2\text{O})(\text{MeOH})]^-$.

$[\text{NaPr}_2(4\text{hpp})_7(\text{H}_2\text{O})_2] \cdot 3(\text{H}_2\text{O})$ (3)

Green solid and green single crystals. (Yield: (precipitate) 74%; (crystals) 23%) $\text{C}_{63}\text{H}_{73}\text{NaO}_{26}\text{Pr}_2$ (1551.04) calculated: C 48.78, H 4.74, Pr 18.17%; found: C 48.32, H 4.56, Pr 17.96%.

IR (v/cm^{-1}): 3623 w, 3271 s br, 1888 w, 1615 m, 1600 m, 1580 s, 1516 s, 1417 s, 1336 m, 1311 m, 1237 s, 1172 m, 1159 m, 1103 m, 1047 w, 1010 w, 949 w, 830 m, 784 w, 697 w.

TGA weight loss: 4.06% (25-70 °C, 1 step, $3\text{H}_2\text{O}$, calculated 3.48%), 2.25% (70-150 °C, 1 step, $2\text{H}_2\text{O}$, calculated 2.32%).

Powder XRD [d -spacings ($1/I^\circ$): 14.56 (100), 14.07 (37), 10.96 (27), 9.53 (21), 7.37 (39), 6.95 (35), 6.20 (17), 5.52 (14), 4.87 (17), 4.73 (12), 4.46 (12), 3.94 (12), 3.670 (13).

$[\text{NaNd}_2(4\text{hpp})_7(\text{H}_2\text{O})(\text{MeOH})] \cdot (\text{H}_2\text{O}) \cdot 3(\text{MeOH})$ (4)

Blue crystals, $\text{NaNd}_2(4\text{hpp})_7(\text{H}_2\text{O})_6$ from exchange of coordinated MeOH and MeOH of crystallisation with atmospheric water. (Yield: 71%) $\text{C}_{63}\text{H}_{75}\text{NaNd}_2\text{O}_{27}$ (1575.72) calculated: C 48.02, H 4.80, Nd 18.31%; found: C 47.93, H 4.51, Nd 18.66%.

IR (v/cm^{-1}): 3530 m, 3256 br s, 1880 w, 1617 m, 1600 m, 1579 m, 1536 s, 1516 s, 1407 s, 1332 m, 1300 w, 1237 s, 1172 m, 1155 w, 1102 w, 1073 w, 1042 w, 1015 w, 950 w, 828 m, 672 m.

TGA weight loss: 2.46% (25-115 °C, 1 step, $2\text{H}_2\text{O}$, calculated 2.39%).

Generated powder XRD [d -spacings Å ($1/I^\circ$): 15.15 (93), 14.46 (100), 10.48 (28), 10.44 (24), 7.57 (17), 7.23 (11), 6.72 (12), 6.51 (5), 6.23 (4), 5.55 (5), 5.31 (3), 5.24 (6), 4.64 (4), 4.51 (5), 4.33 (4), 3.99 (3), 3.84 (6), 3.79 (3), 3.69 (3), 3.67 (5), 3.50 (5).

$[\text{Ho}(4\text{hpp})_3(\text{H}_2\text{O})_2]$ (5)

Pink solid. (Yield: 67%) $\text{C}_{27}\text{H}_{31}\text{HoO}_{11}$ (696.46) calculated: C 46.56, H 4.49, Ho 23.68%; found: C 46.75, H 4.43, Ho 22.90%.

IR (v/cm^{-1}): 3562 w, 3432 m br, 3224 m br, 1612 w, 1597 w, 1577 m, 1543 s, 1515 m, 1419 m, 1340 w, 1318 w, 1302 w, 1257 m, 1230 m, 1158 w, 1104 w, 1050 w, 957 w, 828 m, 707 w, 675 m.

Powder XRD [d -spacings Å ($1/I^\circ$): 14.50 (32), 13.44 (81), 10.50 (70), 9.69 (69), 8.17 (12), 7.59 (11), 6.56 (100), 5.81 (29), 5.62 (10), 4.84 (12), 4.68 (13), 4.50 (10), 4.22 (41), 4.16 (11), 4.01 (15), 3.89 (12), 3.40 (74), 3.75 (28), 3.63 (12), 3.20 (22), 2.97 (11), 2.86 (14), 2.80 (14), 2.66 (14), 2.63 (12), 2.53 (15), 2.45 (16), 2.39 (11), 2.35 (10), 2.26 (17), 2.08 (13).

[Er(4hpp)₃(H₂O)₂].1.5(H₂O) (6)

Pink solid. (Yield: (precipitate) 0.198 g, 57%; (crystals) 17%) [Er(4hpp)₃(H₂O)₂] precipitate (no water of crystallisation. C₂₇H₃₁ErO₁₁ (698.79) calculated: C 46.41, H 4.47, Er 23.94%; found: C 45.60, H 4.31, Er 23.66%.

IR (v/cm⁻¹): 3567 w, 3436 m br, 3221 m br, 1612 w, 1600 w, 1578 m, 1543 s, 1515 m, 1419 m, 1340 w, 1301 w, 1257 m, 1231 m, 1174 w, 1158 w, 1105 w, 1051 w, 1015 w, 956 w, 878 w, 855 w, 828 w, 707 w, 675 w.

TGA weight loss: 5.16% (20-150 °C, 1 step, 2H₂O, calculated 5.15%).

Powder XRD [*d*-spacings Å (I/I°)]: 14.42 (35), 13.48 (83), 10.50 (88), 9.68 (64), 8.16 (16), 7.58 (16), 6.56 (100), 5.81 (29), 4.86 (14), 4.66 (19), 4.22 (43), 4.00 (19), 3.80 (62), 3.74 (34), 3.64 (16), 3.20 (26), 2.85 (20), 2.80 (19), 2.66 (17), 2.53 (21), 2.45 (21), 2.39 (16), 2.26 (18).

[Lu(4hpp)₃].2(H₂O) (7)

[Lu(4hpp)₃].2H₂O (Yield: (precipitate) 49%; (crystals) 32%) C₂₇H₃₁LuO₁₁ (706.50) calculated: C 45.90, H 4.42, Lu 24.76%; found: C 46.08, H 4.21, Lu 24.73%.

IR (v/cm⁻¹): 3568 m, 3256 s br, 3197 s br, 1613 m, 1581 s, 1550 s, 1515 s, 1404 s, 1339 m, 1318 w, 1297 w, 1255 s, 1234 s, 1174 m, 1158 m, 1105 m, 1048 w, 956 w, 824 m, 708 m.

TGA weight loss: 5.33% (20-150 °C, 1 step, 2H₂O, 5.10%).

Powder XRD [*d*-spacings (I/I°)]: 13.71 (100), 10.47 (71), 9.34 (72), 7.88 (26), 7.57 (16), 7.00 (15), 6.42 (60), 5.62 (21), 5.18 (15), 4.99 (23), 4.61 (43), 4.50 (31), 4.24 (19), 4.09 (29), 3.95 (46), 3.89 (19), 3.73 (32), 3.55 (19), 3.25 (23), 3.21 (19), 3.13 (18), 2.92 (18).

d-spacings simulated from X-ray structure:: 13.26 (100), 12.20 (82), 9.53 (52), 8.51 (41), 7.64 (2), 6.63 (44), 6.12 (22), 6.10 (23), 5.79 (22), 5.57 (4), 5.32 (9), 5.10 (3), 4.76 (2), 4.58 (25), 4.44 (11), 4.26 (9), 3.97 (10), 3.61 (17), 3.53 (16), 3.24 (12), 3.10 (11), 2.98 (4), 2.93 (5), 2.89 (5), 2.63 (6), 2.63 (6).

Corrosion testing

Corrosion immersion tests were conducted according to ASTM G31-72.³¹ The appropriate weights of sample compounds were dissolved in water to give concentrations of 200 ppm (for Na(4hpp) and [La₄(4hpp)₁₂(H₂O)₆].4(H₂O) (1)) and 2000 ppm (for Na(4hpp)) in 0.01 M sodium chloride solution.

The pH of the resultant test solutions were maintained within the range of 5-7. Mild steel alloy AS1020 coupons (cut to approx. 25 x 25 x 1 mm) used in the immersion tests were progressively polished with silica-carbide polishing papers of 240, 400, 800, 1200 and 4000 grits. The coupons were rinsed thoroughly with water and dried under flowing N₂ gas and used immediately after polishing and washing to ensure optimum surface conditions.

The sample and reference coupons were immersed in a standard beaker (500 mL) containing the test solutions. Two sample coupons were suspended by Teflon- string and fully immersed at mid-depth in each beaker filled with 500 mL of test solution. The immersion coupon was left standing for seven days and the level of test solution was checked intermittently during the duration of the test and was readjusted as required to replenish water loss due to evaporation. The mouth of the beakers was covered with filter paper to prevent contaminants (dusts, insects, etc.) whilst still allowing free air flow. As the corrosion of the sample coupon progresses, it is important to avoid oxygen depletion in the test solution which affects the uniformity of the environment within the solution during the test duration. The post immersion cleaning procedure involved the rinsing of the coupons first with water and then with mild sonication in clean water for approx. one minute to remove rusts clinging to the test coupons' surface. They were then dried by N₂ gas.

Both normal photography and an optical microscope (with up to 20x magnification) were used for the visual inspection of the tested coupons. The general uniformity of the metal surface on the coupons was compared amongst the tested coupons with the blank coupons.

Table 3: Crystal data for complexes 1-7.

	1	2a	4	6	7
Formula	C ₁₀₉ H ₁₃₂ La ₄ O ₄₇	C ₅₄ H ₆₀ Ce ₂ O ₂₁	C ₆₇ H ₈₃ NaN ₂ O ₂₇	C ₂₇ H ₃₁ ErO ₁₁	C ₂₇ H ₂₉ LuO ₁₀
<i>M</i>	2749.78	1325.26	1631.80	698.78	688.47
Crystal system	triclinic	triclinic	triclinic	orthorhombic	monoclinic
Space group	<i>P</i> -1	<i>P</i> -1	<i>P</i> -1	<i>Pna</i> 2 ₁	<i>P</i> 2 ₁ / <i>c</i>
<i>a</i> /Å	15.2502(9)	14.2020(11)	15.328(3)	24.425(5)	13.345(3)
<i>b</i> /Å	16.6406(10)	15.9564(14)	15.480(3)	5.351(1)	8.0505(16)
<i>c</i> /Å	25.6709(14)	16.1020(11)	16.300(3)	22.945(5)	24.550(5)
α /°	89.014(2)	116.872(5)	78.16(3)	90	90
β /°	78.289(2)	93.433(5)	70.63(3)	90	96.45(3)
γ /°	64.668(3)	92.854(5)	86.33(3)	90	90
<i>V</i> /Å ³	5747.7(6)	3236.9(4)	3571.0(14)	2999.0(11)	2621.0(9)
<i>Z</i>	2	2	2	4	4
μ /mm ⁻¹	1.547	1.455	1.524	2.853	3.824
No. total reflections	80774	20909	31950	26496	25249
No. unique	25932	11352	12470	6590	6018
No. observed [<i>I</i> ≥ 2σ _{<i>I</i>}]	20184	7369	7672	4452	4263
Parameters	1500	707	822	314	354
R _{int}	0.0552	0.0627	0.1163	0.1058	0.1513

wR ₂ (all data)	0.1419	0.1755	0.1616	0.1225	0.1632
R [I ≥ 2σI]	0.0814	0.0676	0.0687	0.0627	0.0714

References:

1. R. D. Shannon. *Acta Crystallogr.*, 1976, **A32**, 751.
2. (a) S.A. Cotton, *Scandium, Yttrium and the Lanthanides*, in *Comprehensive Coordination Chemistry II*, Editors-in-Chief, J. A. McCleverty and T. J. Meyer, Elsevier Science, 2003, **Vol. 3**, 93–188; (b) S.A. Cotton, *Lanthanide and Actinide Chemistry*, John Wiley & Sons, Chichester, 2006.
3. F.T. Edelman, *Scandium, Yttrium and the Lanthanide and Actinide Elements, Excluding their Zero Oxidation State Complexes*, in *Comprehensive Organometallic Chemistry II*, Editors-in-Chief: E.W. Abel, F. G.A. Stone and G. Wilkinson, Elsevier Science, 1995, **Vol. 4**, 11-212.
4. G.B. Deacon, P. MacKinnon, R.S. Dickson, G.N. Pain and B.O. West, *Appl. Organomet. Chem.*, 1990, **4**, 439.
5. (a) M. Kanesato and Y. Yokoyama, *Chem. Lett.*, 1999, **28**, 137; (b) M. Kanesato and Y. Yokoyama, *Anal. Sci.*, 2000, **16**, 335; (c) P.V. Bernhardt, B.M. Flanagan and M.J. Riley, *Aust. J. Chem.*, 2000, **53**, 229; (d) P.V. Bernhardt, B.M. Flanagan and M.J. Riley, *Aust. J. Chem.*, 2001, **54**, 229; (e) M. Seitz, A.G. Oliver and K.N. Raymond, *J. Am. Chem. Soc.*, 2007, **129**, 11153.
6. F. Blin, S.G. Leary, K. Wilson, G.B. Deacon, P.C. Junk and M. Forsyth, *J. Appl. Electrochem.*, 2004, **34**, 591.
7. F. Blin, S.G. Leary, G.B. Deacon, P.C. Junk and M. Forsyth, *Corrosion Sci.*, 2006, **48**, 404.
8. a) R. P. Farrell, P. A. Lay, *Comm. Inorg. Chem.* 1992, **13**, 133; b) R. Codd, C. T. Dillon, A. Levina, P. A. Lay, *Coord. Chem. Rev.* 2001, **216-217**, 537; c) A. Levina, R. Codd, C. T. Dillon, P. A. Lay, *Prog. Inorg. Chem.* 2003, **51**, 145.
9. a) E. McCafferty, *J. Electrochem. Soc.* 1979, **126**, 385; b) G. P. Bierwagen, D. E. Tallman, *Prog. Org. Coatings* 2001, **41**, 201; c) J. Sinko, *Prog. Org. Coatings* 2001, **42**, 267.
10. G.B. Deacon, C.M. Forsyth, P.C. Junk, M. Hilder, S.G. Leary, C. Bromant, I.Pantenburg, G.Meyer, B.W. Skelton and A.H. White, *Z. Anorg. Allg. Chem.*, 2008, **634**, 91.
11. (a) W. Lu, Li Xiaoyang, C. Weigno, P. Wei, D. Nan, L. Keti, H. Youging and H. Shengzhi, *J. Hangzhao U. (Nat. Sci.)*, 1997, **24**, 55; (b) W. Lu, W.-G. Chen, X.-Y. Luo, N. Dong, K.-L. Liang, Y.-Q. Huang and S.-Z. Hu, *Chem. J. Chin. Univ.*, 1997, **18**, 337.
12. G.B. Deacon, M. Forsyth, P.C. Junk, S.G. Leary and W.W. Lee, *Z. Anorg. Allg. Chem.*, 2009, **635**, 833.
13. H. Li and C.W. Hu, *J. Solid State Chem*, 2004, **177**, 4501.
14. G.B. Deacon and R.J. Phillips, *Coord. Chem. Rev.*, 1980, **33**, 227.
15. Only one out of 14,117 La-O distances in the CCDC (3.224 Å) exceeds this value with the next longest 3.133 Å significantly shorter than La(4)...(O5).

16. H. Busskamp, G.B. Deacon, M. Hilder, P.C. Junk, U.H. Kynast, W.W. Lee and D.R. Turner, *CrystEngComm.*, 2007, **9**, 394.
17. C. Bromant, H. Flemig, W. Nika, I. Pantenburg and G. Meyer, *Z. Anorg. Allg. Chem.*, 2006, **632**, 851.
18. T. Behrsing, G.B. Deacon, P.C. Junk, B.W. Skelton, A.N. Sobolev and A.H. White, *Z. Anorg. Allg. Chem.*, 2013, **639**, 41.
19. H. Flemig, I. Pantenburg and G. Meyer, *Z. Anorg. Allg. Chem.*, 2006, **632**, 2205.
20. G.B. Deacon, M. Forsyth, P.C. Junk, S.G. Leary and G.J. Moxey, *Polyhedron*, 2006, **25**, 579.
21. G.B. Deacon, C.M. Forsyth, P.C. Junk, M. Hilder, S.G. Leary, I. Pantenburg, G. Meyer, B.W. Skelton and A.H. White, *Z. Anorg. Allg. Chem.*, 2008, **634**, 91.
22. M. Seter, B. Hinton and M. Forsyth, *J. Electrochem. Soc.*, 2012, **159**, c181.
23. M. Seter, G. Girard, W.W. Lee, G. Deacon, P. Junk, B. Hinton and M. Forsyth, *AIMS Materials Science*, 2015, **2**, 1.
24. J. de Damborenea, A. Conde and M.A. Arenas, *Corrosion Inhibition with Rare Earth Metal Compounds in Aqueous Solution*, in *Rare Earth-based Corrosion Inhibitors*, ed. M. Forsyth and B. Hinton, Woodhead Publishing, Cambridge 2014, Ch. 3.
25. M. Forsyth, M. Seter, B. Hinton, G. Deacon and P. Junk, *Aust. J. Chem.*, 2011, **64**, 812.
26. K. Yvon, W. Jeitschko and E. Parthe. *J. Appl. Crystallogr.*, 1977, **10**, 73.
27. Apex II Version 2.1, Bruker AXS Ltd., Madison, Wisconsin, 2005.
28. Z. Otwinowski and W. Minor. In *Macromolecular Crystallography*, Pt A, ed. C. W. Carter Jr. and R. M. Sweet; 1997, **Vol.276**, p 307.
29. G. M. Sheldrick. *Acta Crystallogr., Found. Crystallogr.*, 2008, **A64**, 112.
30. L. J. Barbour. *J. Supramol. Chem.*, 2001, **1**, 189.
31. American-Standard-Test-Methods in ASTM G31-72, Philadelphia, USA, 2004.

GRAPHICAL ABSTRACT:**Rare Earth 3-(4'-Hydroxyphenyl)propionate Complexes – A System Highly Responsive to the Lanthanoid Contraction and Potential Corrosion Inhibitors**

Glen B. Deacon, Peter C. Junk, Winnie W. Lee, Maria Forsyth and Jun Wang

Structural variation of the lanthanoid 3-(4'-hydroxyphenyl)propionates and an investigation of the anti-corrosion properties of lanthanum 3-(4'-hydroxyphenyl)propionate are presented, highlighting the lanthanoid contraction and the importance of the –CH=CH– structural unit of 4-hydroxycinnamates in corrosion mitigation.

