

# Nanoscale

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

**ARTICLE TYPE**

# Understanding the Origin of Phase Segregation of Nano-Crystalline in $\text{Be}_x\text{Zn}_{1-x}\text{O}$ Random Alloy: A Novel Phase of $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$

Dingyu Yong,<sup>a</sup> Haiyan He,<sup>a</sup> Longxing Su,<sup>d</sup> Yuan Zhu,<sup>d</sup> Zikang Tang,<sup>c,d</sup> Xiao Cheng Zeng,<sup>\*b,e</sup> Bicao Pan<sup>\*a,b</sup><sup>5</sup> Received (in XXX, XXX) XthXXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXXXX 20XX

DOI: 10.1039/b000000x

The usage of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy in ultraviolet (UV)-region optoelectronic devices is largely hindered by its intricate phase segregation of crystallites at different sizes. To understand the physical origin of this phase segregation phenomenon on the atomistic scale, we undertake an extensive study of the structural evolution of the segregation phases in  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy at finite temperatures by using the first-principles calculations combined with the cluster expansion approach. We find that a random alloy of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  tends to segregate into a mix-ordered phase below a critical temperature, through the growth of prototype and nano-sized structures. The segregated phases in  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  entail not only ZnO or BeO crystallites, but also hitherto unreported two phases with beryllium concentration of 1/3 and 2/3. Both new phases of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  are direct wide-gap semiconductors with band gap values of 4.88 eV and 6.78 eV respectively. We envision that the novel  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  crystal is highly promising for solar-blind device applications.

## INTRODUCTION

Zinc oxide (ZnO) is a semiconductor with direct band gap of 3.37 eV and high exciton binding energy (60 meV) at room temperature<sup>1</sup>. These desirable electronic and optical properties render it a promising material for applications in ultraviolet (UV) optoelectronic devices<sup>2</sup>, such as light emitting diodes (LEDs) and UV detectors<sup>3,4</sup>. The latter are typically operated in the solar-blind region from 4.4eV (280nm) to 5.6 eV (220nm). Clearly, the band gap of pristine ZnO does not match this region, and thus it is necessary to tune the band gap of ZnO to the desired UV region. For this purpose, alloying ZnO with other II–VI oxide semiconductors such as MgO, BeO, etc. has been explored. Among these ZnO-based alloys, the  $\text{Mg}_x\text{Zn}_{1-x}\text{O}$  alloy has been widely investigated<sup>5–13</sup>, since its band gap can be tuned from 3.37eV (for wurtzite ZnO) to 7.8eV (for rocksalt MgO). However, due to unmatched crystal structures between ZnO and MgO, the  $\text{Mg}_x\text{Zn}_{1-x}\text{O}$  alloy transforms from the wurtzite phase to the rocksalt phase when the Mg content  $x > 0.36$ . This structure transition limits the band gap of the wurtzite  $\text{Mg}_x\text{Zn}_{1-x}\text{O}$  alloy being less than 3.99eV, which falls short of the solar-blind region<sup>5</sup>.

More recently, recognizing the wurtzite hexagonal structure of BeO that has a wide bandgap (10.8eV),  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  was proposed by Ryu et al. as a candidate for the solar-blind devices<sup>14</sup>. However, due to the large difference in ionic radii between  $\text{Be}^{2+}$  (0.27 Å) and  $\text{Zn}^{2+}$  (0.60 Å), the quality of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  crystal grown using various methods<sup>15–18</sup> was found to deteriorate with increasing Be content. This is probably due to the phase

separation and compositional fluctuation of Be in the  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy<sup>19</sup>. Particularly, annealing the system at high temperatures, Be content in the synthesized  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  with intermediate  $x$  values is not distributed uniformly but segregated into regions with either low or high Be contents<sup>20–22</sup>. More recently, the recrystallization of the  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy under thermal treatment has been found to significantly influence the electronic and optical properties of the BeZnO based devices<sup>23,24</sup>. To understand this unevenly distribution of Be content in  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy, a few theoretical studies have been reported over the past few years<sup>25–27</sup>. Based on a search of the atomistic configurations with a supercell containing 32 atoms, Fan et al. found that the  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy favoured local phase segregation, where three kinds of crystallites with Be concentration values of  $x = 1/4, 1/2$  and  $3/4$  arise<sup>25</sup>. Dong et al. also noticed that  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloys might possess a novel crystalline structure different from the end components ZnO and BeO<sup>27</sup>. In the previous studies, however, sizes of supercells were quite small such that the  $x$  values are limited to the multiples of 1/16 and 1/8, respectively. In other words, these previous theoretical searches of the compound structures were only taken within a narrow configuration space, and thus, the lowest-energy structure of the compound is still unknown. More importantly, how the phase segregation couples with the annealing temperature and with the Be content in the  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy remains open questions. Hence, it is of both fundamental and technological importance to understand physical origin of the phase segregation in  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy and identify structures of the segregated phases, thereby providing insightful guidance to experimental fabrication of high-quality  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy.

Here, by combining first-principles calculations with the

cluster expansion (CE) approach, we have systematically studied structural evolution of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy at different temperatures. We find that the phase segregation occurs in  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  when the annealing temperature is below a critical value. Moreover, the critical temperature (CT) is tightly correlated with the Be content in the system. The segregated crystallites include not only the common end components ZnO and BeO, but also two novel  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  phases with Be concentration  $x = 1/3$  and  $2/3$  respectively. Both new  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  crystal phases are predicted to be semiconductors with direct band gaps of 4.88 eV and 6.78 eV respectively.


## COMPUTATIONAL DETAILS

To study the structural evolution of the segregation phase in  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy at finite temperatures, a huge supercell containing tens of thousands of atoms is needed for theoretical treatment. Thus far, the first-principles calculation cannot handle such a large size system. We therefore employ the well-established state-of-the-art CE approach to study the structural and thermodynamic properties of the alloy<sup>28-32</sup>. In the CE approach, the alloy Hamiltonian is mapped onto a generalized Ising Hamiltonian, and thus a function  $E(\sigma)$  with configuration  $\sigma$  can be represented by selecting effective cluster interactions  $J_\alpha$  for the alloy considered<sup>33</sup>.

Specifically, we treat the  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  solid solution as a pseudobinary alloy with beryllium and zinc atoms substituting the cation lattice sites. The total energies of the  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloys are represented with CE. The Alloy-Theoretic Automated Toolkit (ATAT) package is used to carry out the cluster expansion constructions<sup>33-38</sup>. The parameters in CE are determined by fitting  $E(\sigma)$  to the total energies of many typical small-sized configurations, which are computed using density functional theory (DFT) methods as implemented in the Vienna ab-initio simulation package (VASP)<sup>39</sup>, where the interaction between ions and valence electrons is described with the projector augmented wave (PAW) potentials, and the exchange–correlation between electrons is treated through using the generalized gradient approximation (GGA) in the Perdew–Burke–Ernzerhof (PBE) form<sup>40</sup>. We expand the one-electron wave functions in a plane-wave basis with an energy cutoff of 600 eV. In addition, the Gamma centered Monkhorst–Pack mesh is used to sample the Brillouin zone for all the structures, ensuring approximately the same k-point density among different-sized supercells. All the small-sized structures are fully relaxed until the force on each atom is less than 0.02 eV/Å.

Combining the CE approach with the Monte Carlo (MC) method<sup>41-43</sup>, the evolution of the structure in each concerned  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy is simulated. In our simulations, the supercell contains 23 040 cation-anion pairs. For each case with a given content of Be, the initial distribution of Be in the alloy is random. Such a system is annealed from 2000 K to 0 K, with temperature step of 100 K. At a given temperature, it takes 30 000 000 exchange attempts to equilibrate this system. We obtain the averaged energy of the system from additional 30 000 000 MC steps for each temperature.

## RESULTS AND DISCUSSIONS

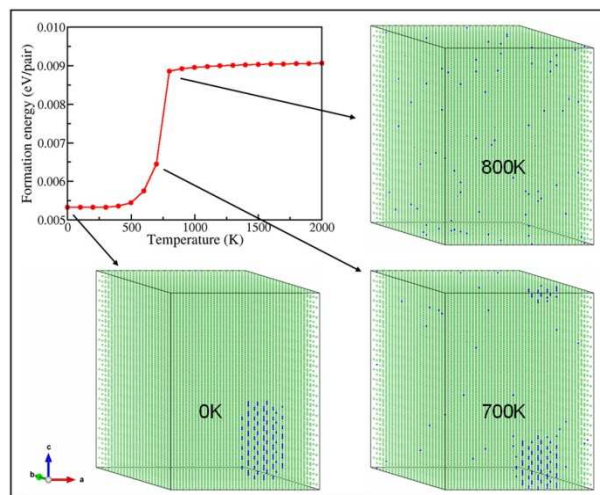


**Fig. 1** Snapshots of  $\text{Be}_{0.01}\text{Zn}_{0.99}\text{O}$  atomic structure varying with temperature during annealing. To depict the atomic distribution more clearly, only Be atoms and Zn atoms are shown. The blue and green spheres represent the Be and the Zn atoms, respectively. The inset plots the formation energy (per cation-anion pair) versus temperature.

First, we study cation distribution behavior in a representative pseudobinary  $\text{Be}_{0.01}\text{Zn}_{0.99}\text{O}$  alloy which has a very low beryllium concentration. Our MC simulations provide the averaged energy  $E(\text{Be}_x\text{Zn}_{1-x}\text{O}, T)$  for the  $\text{Be}_{0.01}\text{Zn}_{0.99}\text{O}$  alloy at different temperatures, ranging from 2000 K to 0 K. From this energy and the energies of bulk BeO and bulk ZnO,  $E(\text{BeO})$  and  $E(\text{ZnO})$ , the formation energy of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  ( $x = 0.01$ ) at a given temperature is evaluated by using the definition

$$E_f(\text{Be}_x\text{Zn}_{1-x}\text{O}, T) = E(\text{Be}_x\text{Zn}_{1-x}\text{O}, T) - xE(\text{BeO}) - (1-x)E(\text{ZnO}) \quad (1)$$

Fig. 1 plots the formation energy as a function of the temperature. It shows that the formation energy of the system decreases slightly from 2000 K to 800 K, and then abruptly drops from 800 K to 500 K. Below 500 K, again the formation energy decreases smoothly with the temperature. Notably, there is an inflection point at  $T = 700$  K in the energy curve. Normally, a sharp change in energy near an inflection point correlates with a change in structure of the system. Closer examination of the structure of the system at each temperature indicates that the Be ions distribute uniformly in the system for  $T \geq 800$  K (see Fig. 1). However, at 700 K, most Be ions accumulate to form an “ordered structure” (see below). As the temperature is further lowered, more and more Be ions converge into the nano-sized “ordered structure”, and eventually all Be ions gather together in the form of the “ordered structure” at 0 K. So, from 700 K to 0 K, both the “ordered structure” of Be and ZnO coexist in the system. Thus the phase segregation occurs below 700 K. Relating this phenomenon below 700 K with the inflection point at 700 K in the formation energy curve indicates their close correlation. Further MC simulations show that the phase segregation shown in Fig. 1 occurs in many other configurations of  $\text{Be}_{0.01}\text{Zn}_{0.99}\text{O}$  alloy with different initial Be distributions. Hence, the phase segregation in  $\text{Be}_{0.01}\text{Zn}_{0.99}\text{O}$  alloy is a generic phenomenon at low temperature.

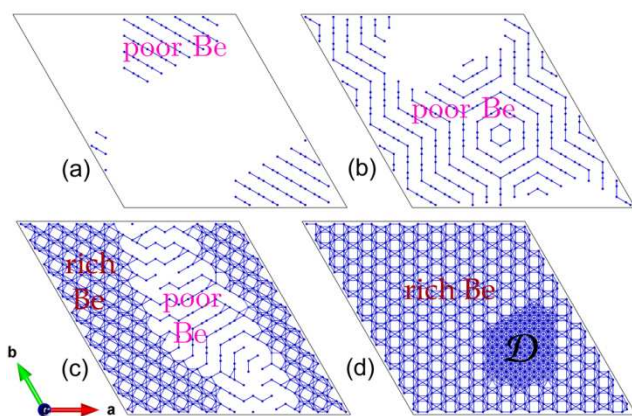


**Fig. 2** The top view of the structures of  $\text{Be}_{0.05}\text{Zn}_{0.95}\text{O}$ (a),  $\text{Be}_{0.25}\text{Zn}_{0.75}\text{O}$ (b),  $\text{Be}_{0.5}\text{Zn}_{0.5}\text{O}$ (c) and  $\text{Be}_{0.7}\text{Zn}_{0.3}\text{O}$ (d) at 0 K after annealing. Zn and O atoms are not shown here, and only Be atoms (blue) are shown. The bonds between Be atoms that are the first or the second neighbors, are shown.


Next, we extend our MC simulations to systems with different beryllium contents, e.g.,  $\text{Be}_{0.05}\text{Zn}_{0.95}\text{O}$ ,  $\text{Be}_{0.25}\text{Zn}_{0.75}\text{O}$ ,  $\text{Be}_{0.5}\text{Zn}_{0.5}\text{O}$  and  $\text{Be}_{0.7}\text{Zn}_{0.3}\text{O}$ . In each system, the phase segregation is observed during the MC simulations. Fig. 2 shows the segregated “ordered phases” for these systems at low temperatures. As depicted in Fig. 2(a), when  $x = 0.05$ , the segregated phase relevant to Be exhibits parallel stripes in local structure, as in  $\text{Be}_{0.01}\text{Zn}_{0.99}\text{O}$ . For  $x = 0.25$ , the Be stripes in the segregated phase form hexagonal rings (Fig. 2(b)). These hexagonal rings are seemingly assembled from the stripes oriented in different directions, and thus there exist grain boundaries between the segregated phases. A common feature in Fig. 2(a) and (b) is that the entire system is composed of the Be-stripe region and the Be free region. For  $x = 0.5$ , Be distributes over the entire system. However, the segregated structure of  $\text{Be}_{0.5}\text{Zn}_{0.5}\text{O}$  at low temperature can still be seen. It displays Be-rich region and Be-poor region, as shown in Fig. 2(c). Here, the structural pattern in the Be-poor region is also stripe-like, as in  $\text{Be}_{0.01}\text{Zn}_{0.99}\text{O}$ ,  $\text{Be}_{0.05}\text{Zn}_{0.95}\text{O}$  and  $\text{Be}_{0.25}\text{Zn}_{0.75}\text{O}$ . As  $x$  value further increases, the stripe-like regions gradually shrink and eventually disappear while the Be-rich regions expand. When the beryllium ions are over dosed, like  $\text{Be}_{0.7}\text{Zn}_{0.3}\text{O}$ , the whole system consists of both the Be-rich region and the BeO domains marked with D (Fig. 2(d)) at low temperatures.

To describe the detailed segregation behavior of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  solid solution, we investigate numerous cases with different  $x$  values (step sets as 0.01 for  $0.0 < x < 0.1$  range and  $0.9 < x < 1.0$  range, 0.05 for the other ranges). The whole phase diagram of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  versus Be content  $x$  and temperature is shown in Fig. 3. As shown in Fig. 3, the CT for the phase separation is strongly dependent on the  $x$  value. Typically, for  $x < 0.33$ , the CT increases with increasing  $x$ . However, when  $x > 0.66$ , the CT decreases with increasing  $x$ . More interestingly, for  $x < 0.33$ ,  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy favours the mixed ZnO and Be-poor phase. For  $0.33 < x < 0.66$ , the alloys are composed of both the Be-poor and the Be-rich phases. And for  $x > 0.66$ , the alloys favour the phase

separation of BeO and Be-rich phases. For  $0.25 < x < 0.85$ , the low-energy alloy configurations obtained from CE convert to the segregation phases as shown in Fig. 3, even annealing at 2000 K. Overall, regardless of the  $x$  value, phase segregation occurs below a critical temperature. This leads to that random alloy of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  is unstable after annealing, consistent with the observation that random BeZnO alloy is rarely seen in experiments<sup>20-22</sup>.

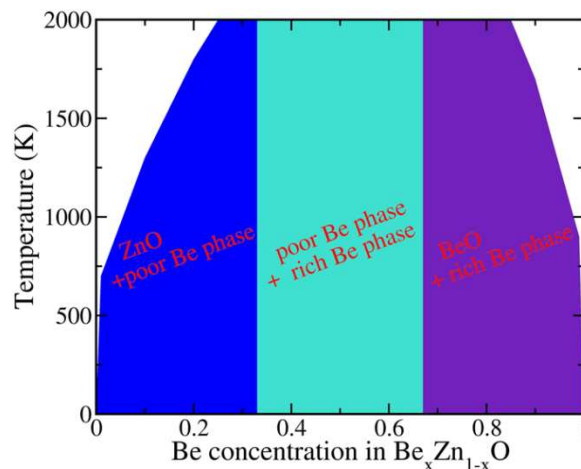

**Fig. 3** The calculated segregation behavior of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  solid solution versus Be concentration. The regions correspond to different kinds of phase separation are highlighted with different colors, and the white regions stand for the  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy obtained from CE.

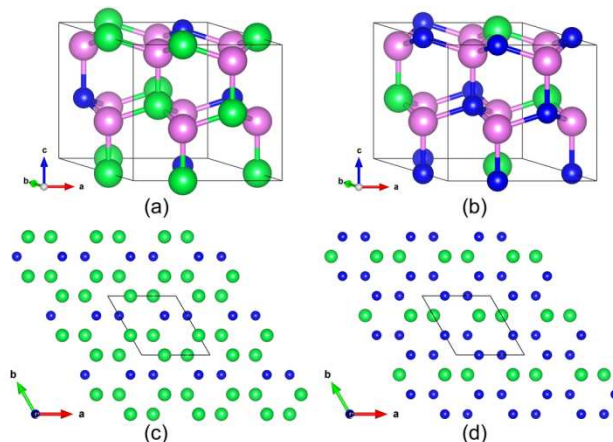

**Fig. 4** The atomic structures of the two segregation phases: (a) The poor-Be phase  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and (b) the rich-Be phase  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ . The blue, green and the pink balls represent the Be, Zn and the O atoms, respectively. For clearer view of the distribution of cations, the O atoms are not shown in the top view of (c)  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and (d)  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ .

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

## ARTICLE TYPE


**Table 1** Structural information of both  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ .

Phase		$\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$			$\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$			
Space group		Cmc21 (No. 36)			Cmc21 (No. 36)			
Cell parameters		$a(\text{\AA})$	$b(\text{\AA})$	$c(\text{\AA})$	$a(\text{\AA})$	$b(\text{\AA})$	$c(\text{\AA})$	
		9.304	5.364	4.929	8.730	5.019	4.639	
		$\alpha(\text{deg})$	$\beta(\text{deg})$	$\gamma(\text{deg})$	$\alpha(\text{deg})$	$\beta(\text{deg})$	$\gamma(\text{deg})$	
		90.0	90.0	90.0	90.0	90.0	90.0	
Atomic coordinates								
Atom	Label <sup>a</sup>	$x$	$y$	$z$	Label <sup>a</sup>	$x$	$y$	$z$
Be	4a	0.000	0.655	0.000	8b	0.674	0.160	0.002
O	4a	0.000	0.621	0.341	8b	0.693	0.144	0.362
O	8b	0.146	0.188	0.406	4a	0.000	0.217	0.428
Zn	8b	0.160	0.175	-0.002	4a	0.000	0.180	-0.007

<sup>a</sup> The letters in each Label column are Wyckoff labels and the number before each letter is the corresponding multiplicity.


Our simulations suggest that the segregated crystallites not only include the common end components ZnO and BeO but also contain two novel  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  phases. Their appearance indicates two novel  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  phases with stable ordered structures. Closer examinations reveal that the Be content of the poor-Be phase and the rich-Be phase are 1/3 and 2/3, respectively. For convenience, the structure of the poor-Be phase is named as  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and the rich Be phase as  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ . Both two new phases have the same space group of Cmc21, and their primitive cells are shown in Fig. 4 (a), and Fig. 4(b). In both new phases, the beryllium atoms fully occupy the cation sites in (010) atomic layers. The detailed structural information of the conventional cells for both  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  is listed in Table 1. And it is worth noting that, with the same space group of Cmc21, the segregated phases are not hexagonal, but orthorhombic structures. Now we examine the stability of both new crystals. The formation

energies of  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  are predicted to be 54 meV/pair and 55 meV/pair, respectively, slightly higher than those of bulk BeO and bulk ZnO. This implies that the stabilities of both new crystals are less than either bulk BeO or bulk ZnO. Furthermore, their phonon dispersion<sup>44,45</sup> and their vibrational density of states are computed. As shown in Fig. 5, no imaginary mode is found in the phonon dispersion, indicating that both  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  are dynamically stable. We have also examined thermal stability of both crystals at an elevated temperature. To this end, the first-principles molecular dynamics (FP-MD) simulations in canonical ensembles are performed using the  $2 \times 2 \times 2$  supercells. The temperature of the concerned systems is controlled at 1000 K. For each system, our FP-MD simulations run over 10 ps. It is found that the structure of both crystals remains intact, except for small displacement of atoms away from their lattice-site positions.

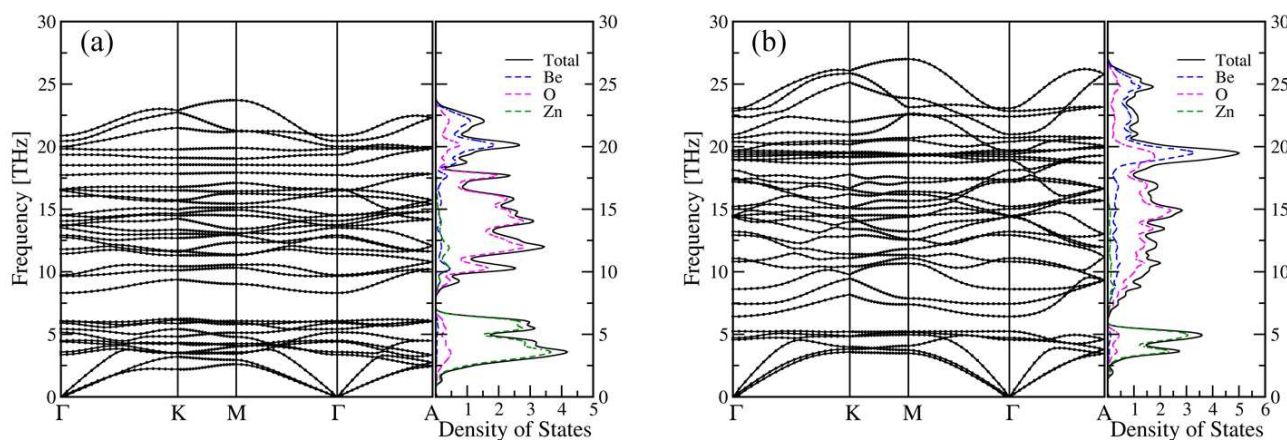**Fig. 5** Computed phonon dispersion and the density of states of (a)  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and (b)  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ .


Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

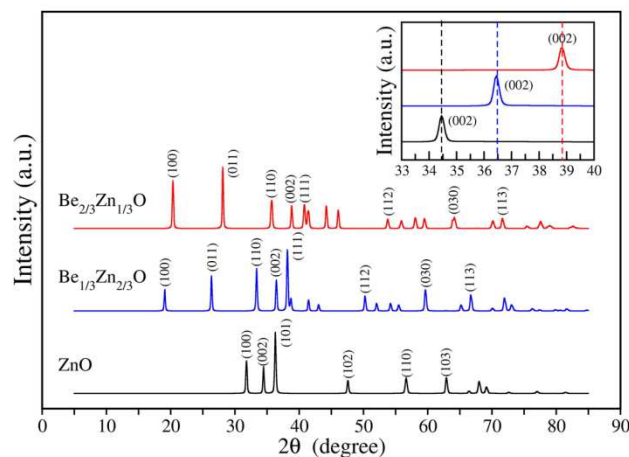**ARTICLE TYPE**

**Fig. 6** Computed X-ray diffraction (XRD) spectra of ZnO,  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ .

To gain more knowledge on both crystalline structures, we compute the x-ray diffraction (XRD) spectra for both  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ . As plotted in Fig. 6, compared to the bulk ZnO, more peaks arise in the XRD spectra of both new crystals. Notably, as displayed in the inset of Fig. 6, the (002) peaks at  $2\theta = 34.5, 36.5$  and  $38.9$  belong to ZnO,  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ , respectively. This feature can be used to identify the new phases from the BeZnO mixed phases in experiment in the future.

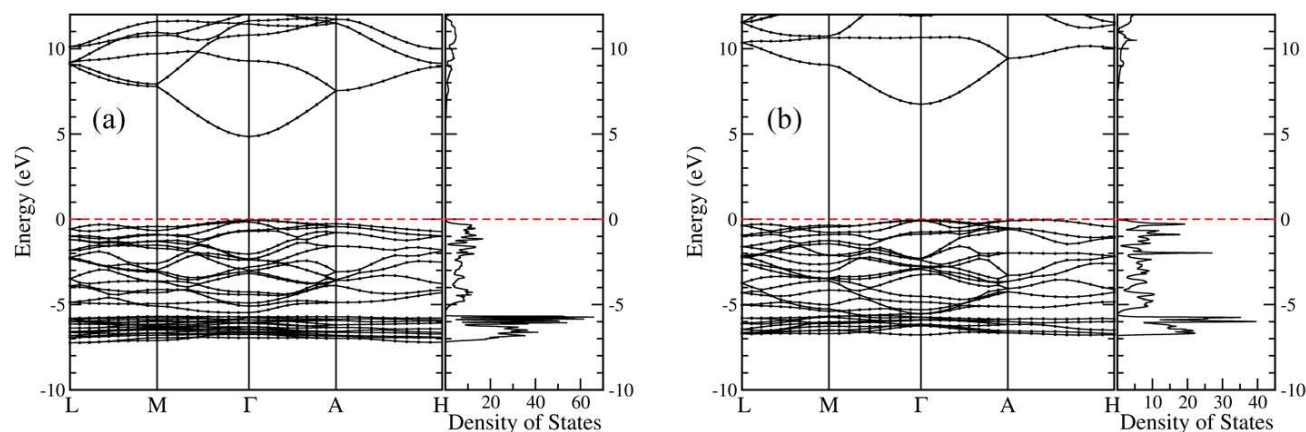

**Fig. 7** Computed electronic band structures and density of states of (a)  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and (b)  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ . Femi levels are at 0.0 eV, which are marked with red dashed lines.


Electronic structures of both new crystals are computed at the level of the hybrid functional (HSE06), where the portion of the exact exchange is 0.375<sup>46</sup>. As shown in Fig. 7, both  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  are predicted to be direct wide-gap semiconductors, with band gap values of 4.88 eV and 6.78 eV respectively. The computed band gaps are just between computed band gap 3.40 eV for BeO and 10.69 eV for ZnO. Importantly, the band gap (4.88 eV) of  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  just falls in the solar-blind spectrum range (4.4 - 5.6 eV). Hence, the  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  crystal can be a promising candidate for solar-blind detectors.

As mentioned above, Fan et al<sup>25</sup> predicted that  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloys favour local decomposition into three different compounds with  $x = 1/4, 2/4$  and  $3/4$ , respectively. In their calculations, a small-sized supercell with 32 atoms was used. As such, the  $x$  value in the considered structures was restricted as multiples of 1/16 only, thereby representing a limited search over possible configurations of compounds. Here, our calculations indicate that the formation energies of the three compounds of  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  ( $x = 1/4, 2/4$  and  $3/4$ ) are about 79 meV/pair, 132 meV/pair and 157

meV/pair, respectively, slightly higher than those of  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ . Hence, the crystals of  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  are expected to be more stable than those reported previously.

Because the formation energies of  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  are positive, from the energetic view,  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  would favour phase segregation into BeO and ZnO rather than into  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$ . This view would be inconsistent with our simulation in which either  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  or  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  crystallite is observed. This apparent inconsistency is due to the fact that the relative stabilities between ZnO, BeO,  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  are entirely based on the energies of their bulk states. In our simulation, the observed  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  are all domains with finite sizes, and their stabilities can be quite different from those of the bulk crystals. To examine relative stabilities of the crystallites of both  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  with different sizes, we compute the size-dependent formation energies. As shown in Fig. 8, the formation energies of BeO grains embedded in the matrix of ZnO and the  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  grains

embedded in the matrix of ZnO increase with increasing the size of either BeO or  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  grain. Interestingly, when the number of Be atoms in the system is less than about 1100 (corresponding to the sizes of 54 Å for a  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  grain or 38 Å for a BeO grain), the embedded BeO grain is less stable than the embedded  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  grain. Otherwise, their relative stabilities reverse. This clearly demonstrates that the formation of nano-sized  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  grains is energetically more favorable than the formation of nano-sized BeO grain, in the ZnO matrix.

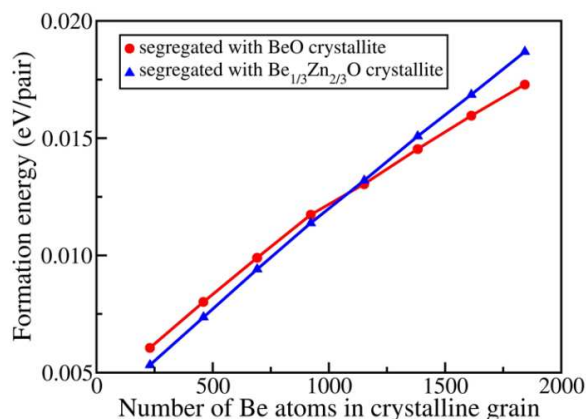

**Fig. 8** Calculated formation energies (per cation-anion pair) of systems, segregated with BeO (red line) or  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  (blue line) nanocrystalline grains in the ZnO matrix, as a function of number of Be atoms in crystalline grains.

Lastly, we stress that since the relative stabilities between BeO and BeZnO at finite size are comparable, as shown in Fig. 8, a typical BeZnO sample may be a heavy mixture of several ordered phases, including the two new structures and BeO, among others. Therefore, it would be very difficult to determine properties (e.g. the XRD spectra) of the pure ordered BeZnO structures from the mixed phases in experiment. We hope that these new structures can be detected in future experiments, and that every pure ordered structure can be synthesized.

## Conclusions

In conclusion, we show simulation evidence that the phase segregation exists universally in  $\text{Be}_x\text{Zn}_{1-x}\text{O}$  alloy below a certain temperature. In the mixed phases, two new crystals of  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  are predicted to form favourably. We also demonstrate that the formation of nano-sized  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  grains is energetically more favorable than the formation of nano-sized BeO grains in the ZnO matrix. These nano-sized  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  grains can serve as nucleation center for bigger crystallites. Hence, during the realistic phase segregation, there is little chance for the growth of BeO grains in BeZnO alloy during the annealing process. Indeed, there exists no BeO grain in our systems except for the system with over dosed Be content. We thus expect that both new BeZnO crystals can be experimentally synthesized via annealing random alloy. Finally, we predict that both  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  and  $\text{Be}_{2/3}\text{Zn}_{1/3}\text{O}$  crystals are direct wide-gap semiconductors with band gap values of 4.88 eV and 6.78 eV, respectively. The band gap (4.88 eV) of  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  is within the solar-blind spectrum range (4.4 - 5.6 eV). Hence, the  $\text{Be}_{1/3}\text{Zn}_{2/3}\text{O}$  crystal may find application in solar-blind UV devices.

## Acknowledgments

This work is financially supported by the National Natural Science Foundation of China (No. 51232009).XCZ is supported by a grant from USTC for Qianren-B (1000 Talents Plan B) summer research. The computational center of USTC is acknowledged for computational support.

## Notes and references

<sup>a</sup>Key Laboratory of Strongly-Coupled Quantum Matter Physics, Department of Physics, University of Science and Technology of China, Hefei 230026, Anhui, P.R. China. E-mail: bcp@ustc.edu.cn

<sup>b</sup>Hefei National Laboratory for Physical Sciences at Microscale, University of Science and Technology of China, Hefei 230026, Anhui, P.R. China

<sup>c</sup>Department of Physics, Hong Kong University of Science and Technology, Hong Kong, China

<sup>d</sup>State Key Laboratory of Optoelectronic Materials and Technologies, School of Physics and Engineering, Sun Yat-sen University, Guangzhou 510275, China

<sup>e</sup>Department of Chemistry and Nebraska Center for Materials and Nanoscience, University of Nebraska, Lincoln, Nebraska 68588, USA

- Özgür, Ü.; Alivov, Y. I.; Liu, C.; Teke, A.; Reshchikov, M. A.; Doğan, S.; Avrutin, V.; Cho, S.-J.; Morkoç, H. *J. Appl. Phys.* 2005, **98**, 044301.
- Service, R. F. *Science* 1997, **276**, 5314.
- Bagnall, D. M.; Chen, Y. F.; Zhu, Z.; Yao, T.; Koyama, S.; Shen, M. Y.; Goto, T. *Appl. Phys. Lett.* 1997, **70**, 2230-2232.
- Tang, Z. K.; Wong, G. K. L.; Yu, P.; Kawasaki, M.; Ohtomo, A.; Koinuma, H.; Segawa, Y. *Appl. Phys. Lett.* 1998, **72**, 3270.
- Ohtomo, A.; Kawasaki, M.; Koida, T.; Masubuchi, K.; Koinuma, H.; Sakurai, Y.; Yoshida, Y.; Yasuda, T.; Segawa, Y. *Appl. Phys. Lett.* 1998, **72**, 2466.
- Sanati, M.; Hart, G. L.; Zunger, A. *Phys. Rev. B* 2003, **68**, 155210.
- Seko, A.; Oba, F.; Kuwabara, A.; Tanaka, I. *Phys. Rev. B* 2005, **72**, 024107.
- Fan, X. F.; Sun, H. D.; Shen, Z. X.; Kuo, J. L.; Lu, Y. M. *J. Phys.: Condens. Matter* 2008, **20**, 235221.
- Shi, H. L.; Duan, Y. *Eur. Phys. J. B* 2008, **66**, 439-444.
- Maznichenko, I. V.; Ernst, A.; Bouhassoune, M.; Henk, J.; Däne, M.; Lüders, M.; Bruno, P.; Hergert, W.; Mertig, I.; Szotek, Z.; Temmerman, W. M. *Phys. Rev. B* 2009, **80**, 144101.
- Zhang, Y. G.; He, H. Y.; Pan, B. C. *Eur. Phys. J. B* 2011, **80**, 395-400.
- Zhang, Y. G.; He, H. Y.; Pan, B. C. *J. Appl. Phys.* 2011, **110**, 124315.
- Su, L. X.; Zhu, Y.; Zhang, Q. L.; Chen, M. M.; Ji, X.; Wu, T. Z.; Gui, X. C.; Pan, B. C.; Xiang, R.; Tang, Z. K. *J. Phys. D-Appl. Phys.* 2013, **46**, 245103.
- Ryu, Y. R.; Lee, T. S.; Lubguban, J. A.; Corman, A. B.; White, H. W.; Leem, J. H.; Han, M. S.; Park, Y. S.; Youn, C. J.; Kim, W. *J. Appl. Phys. Lett.* 2006, **88**, 052103.
- Kim, W. J.; Leem, J. H.; Han, M. S.; Park, I.-W.; Ryu, Y. R.; Lee, T. S. *J. Appl. Phys.* 2006, **99**, (9), 096104.
- Khoshman, J. M.; Ingram, D. C.; Kordes, M. E. *Appl. Phys. Lett.* 2008, **92**, (9), 091902.
- Yang, C.; Li, X. M.; Gu, Y. F.; Yu, W. D.; Gao, X. D.; Zhang, Y. W. *Appl. Phys. Lett.* 2008, **93**, (11), 112114.
- Han, M. S.; Kim, J. H.; Jeong, T. S.; Park, J. M.; Youn, C. J.; Leem, J. H.; Ryu, Y. R. *J. Cryst. Growth* 2007, **303**, (2), 506-509.
- Park, D.-S.; Mudd, J. J.; Walker, M.; Krupski, A.; Seghier, D.; Saniee, N. F.; Choi, C.-J.; Youn, C.-J.; McMitchell, S. R. C.; McConville, C. F. *CrystEngComm* 2014, **16**, (11), 2136-2143.
- Chen, M.; Zhu, Y.; Su, L.; Zhang, Q.; Chen, A.; Ji, X.; Xiang, R.; Gui, X.; Wu, T.; Pan, B.; Tang, Z. *Appl. Phys. Lett.* 2013, **102**, 202103.

- 21 Su, L.; Zhu, Y.; Chen, M.; Zhang, Q.; Su, Y.; Ji, X.; Wu, T.; Gui, X.; Xiang, R.; Tang, Z. *Appl. Phys. Lett.* 2013,**103**, 072104.
- 22 Park, D.-S.; Krupski, A.; Sanchez, A. M.; Choi, C.-J.; Yi, M.-S.; Lee, H.-H.; McMitchell, S. R. C.; McConville, C. F. *Appl. Phys. Lett.* 2014,**104**, 141902.
- 23 Park, D.-S.; Vashghani Farahani, S. K.; Walker, M.; Mudd, J. J.; Wang, H.; Krupski, A.; Thorsteinsson, E. B.; Seghier, D.; Choi, C.-J.; Youn, C.-J.; McConville, C. F. *ACS Applied Materials & Interfaces* **2014**, 6, (21), 18758-18768.
- 24 Zhu, Y.; Chen, M.; Su, L.; Su, Y.; Ji, X.; Gui, X.; Tang, Z. *J. Alloys Compd.* **2014**, 616, (0), 505-509.
- 25 Fan, X. F.; Zhu, Z.; Ong, Y.-S.; Lu, Y. M.; Shen, Z. X.; Kuo, J.-L. *Appl. Phys. Lett.* 2007,**91**, 121121.
- 26 Gan, C. K.; Fan, X. F.; Kuo, J.-L. *Comput. Mater. Sci.* 2010,**49**, S29-S31.
- 27 Dong, L.; Alpay, S. P. *Phys. Rev. B* 2011,**84**, 035315.
- 28 Sanchez, J. M.; Ducastelle, F.; Gratias, D. *Physica A* 1984,**128**, 334-350.
- 29 Asta, M.; Wolverton, C.; de Fontaine, D.; Dreyssé, H. *Phys. Rev. B* 1991,**44**, 4907-4913.
- 30 Wolverton, C.; Asta, M.; Dreyssé, H.; de Fontaine, D. *Phys. Rev. B* 1991,**44**, 4914-4924.
- 31 Sanchez, J. *Phys. Rev. B* 1993,**48**, 14013-14015.
- 32 Sanchez, J. M. *Phys. Rev. B* 2010,**81**, 224202.
- 33 van de Walle, A.; Ceder, G. *Journal of Phase Equilibria* 2002,**23**, 348-359.
- 34 van de Walle, A.; Asta, M. *Modell. Simul. Mater. Sci. Eng.* 2002,**10**, 521-538.
- 35 van de Walle, A.; Asta, M.; Ceder, G. *CALPHADJournal* 2002,**26**, 539-553.
- 36 van de Walle, A. *CALPHADJournal* 2009,**33**, 266-278.
- 37 Hart, G.; Forcade, R. *Phys. Rev. B* 2008,**77**, 224115.
- 38 van de Walle, A. The Alloy Theoretic Automated Toolkit (ATAT) 2001, <http://alum.mit.edu/www/avdw/atat/>
- 39 Kresse, G.; Furthmuller, J. *Phys. Rev. B* 1996,**54**, 11169-11186.
- 40 Perdew, J. P.; Burke, K.; Ernzerhof, M. *Phys. Rev. Lett.* 1996,**77**, 3865-3868.
- 41 Lavrentiev, M. Y.; Drautz, R.; Nguyen-Manh, D.; Klaver, T. P. C.; Dudarev, S. L. *Phys. Rev. B* 2007,**75**, 014208.
- 42 Kawasaki, K.; Domb, C. d.; Green, M. Phase Transitions and Critical Phenomena. Academic, New York: 1972.
- 43 Binder, K.; Heermann, D. *Monte Carlo simulation in statistical physics: an introduction*. Springer: 2010.
- 44 Togo, A.; Oba, F.; Tanaka, I. *Phys. Rev. B* 2008,**78**, 134106.
- 45 Togo, A. phonopy, <http://sourceforge.net/projects/phonopy>.
- 46 Oba, F.; Togo, A.; Tanaka, I. *Phys. Rev. B* 2008,**77**, 245202.