

Polymer Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Polyvinylpyridinium-type gradient porous membranes: synthesis, actuation and intrinsic cell growth inhibition

Cite this: DOI: 10.1039/x0xx00000x

Karoline Täuber,^a Bernd Lepenies,^{b,c} and Jiayin Yuan^{a*}Received 00th January 2015,
Accepted 00th January 2015

DOI: 10.1039/x0xx00000x

www.rsc.org/


Gradient porous membranes were prepared from a poly(4-vinylpyridinium)-based poly(ionic liquid) together with carboxylic multi-acid compounds via electrostatic complexation. Their unique tuneable actuation kinetics in humid environment as well as their intrinsic cell toxicity were studied.

Polymer actuators are capable of transforming changes occurring on a molecular level inside the material to responses detectable on a macro-scale, *i.e.* bending, swelling/deswelling, solubility changes, alteration of surface characteristics, to name a few.¹⁻⁵ These changes may be induced by a variety of material-specific stimuli, which include pH, temperature, ionic strength, or electric and magnetic field.⁶ In this regard, polyelectrolyte membrane actuators have especially attracted much attention due to their high charge density and their potential applications in fields such as energy conversion, catalysis and electro-active sensors.^{2-3, 7-13} Stable polyelectrolyte membranes are usually prepared by the layer-by-layer (LbL) technique.¹⁴⁻²⁰ To fabricate high performance polyelectrolyte membrane actuators with fast kinetics and high sensitivity, a possible design is to make these films highly porous to accelerate the mass diffusion and to amplify the interfacial interaction.²¹ Synthetically this task is addressable *via* LbL on porous templates, which yet delivers products of very limited amount.

Our group has previously reported the synthesis of a hierarchically structured porous poly(ionic liquid) (PIL) membrane by electrostatic complexation of a hydrophobic imidazolium based PIL with poly(acrylic acid) (PAA).²² Here PILs, the polymerization products of ionic liquids,²³⁻²⁸ were employed as innovative polyelectrolytes that facilitate the pore generation on account of their ionic, but at the same time water-insoluble features.^{5, 24, 29-33} The role of PAA was to neutralize the polycation and to electrostatically cross-link the PIL porous network under basic conditions. Expanding this work, our group has created an ultra-fast porous polymer membrane actuator responding to solvent vapour with unprecedented bending speed and stability.²¹ The membrane actuation stems from a gradient in the

degree of electrostatic complexation (DEC) of the PIL with a multivalent acid along the membrane cross-section. Applying the same principle of gradient complexation, we have been able to tune the pore size of these membranes from nm to μm range when using a series of benzoic acids of different multivalency.³⁴ From a chemical structure standpoint, these porous membranes and actuators are so far only polyvinylimidazolium based. It is therefore of scientific curiosity to explore alternative polymers as building blocks to expand the synthetic scope of porous PIL membrane actuators.

In this communication, we applied the membrane fabrication principle to a poly(4-vinyl pyridine) (P4VP) derived PIL, which together with various types of multivalent organic acids builds up porous gradient polyelectrolyte membranes. Scheme 1 illustrates the chemical structure of the multi-acid derivatives used in this work. These membranes feature tuneable bending speed upon change from wet to dry environment, and are of intrinsic cell toxicity, making them potentially applicable as actuators with antimicrobial or antifouling properties.

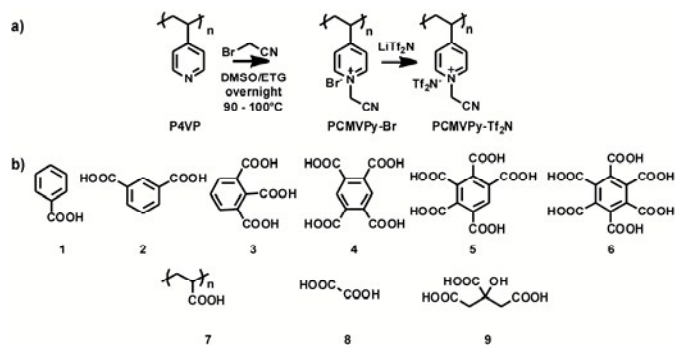

Scheme 1: a) Synthesis of polyvinylpyridinium-type PIL, PCMVPy-Tf₂N by post-modification from poly(4-vinyl pyridine) (P4VP). b) Structures of the acids used for electrostatic complexation. ETG denotes ethylene glycol.

The PIL, poly[1-cyanomethyl-4-vinylpyridinium bis(trifluoromethane sulfonyl)imide] (PCMVPy-Tf₂N) was synthesized by post-modification of commercially available P4VP ($M_w \sim 60$ kDa) rather than by the traditional route of polymerizing an ionic liquid monomer. In detail, P4VP was reacted with excessive bromoacetonitrile, followed by anion exchange to replace Br⁻ by bis(trifluoromethane sulfonyl)imide (Tf₂N⁻) (Scheme 1a).³⁵ A quantitative quaternization was confirmed by proton nuclear magnetic resonance. Following our previous reports,^{21-22, 34} the polymer membrane was synthesized by ionic complexation of the cationic PIL with *in-situ* deprotonated organic multi-acid derivatives (Scheme S1). In a typical run, the PIL and the acid were dissolved at a molecular level in dimethylsulfoxide (DMSO), cast onto a glass plate and dried at 80 °C in air for 2 h. This non-porous dry polymer film was then immersed into aqueous NH₃ (0.2 wt%) in order to induce pore formation and simultaneous PIL-acid complexation. As NH₃ is gradually penetrating into the polymer film from the top (side facing NH₃ solution) to the bottom (side facing the glass slide), the resulting product shows a gradient in its DEC, being highest on the top and lowest at the bottom. The sulfur content along the membrane cross-section was taken as a quantitative measure of the DEC, as the Tf₂N⁻ counteranions of the PILs, the only source of sulfur, are replaced by carboxylates in the step of electrostatic complexation. Monitoring therefore the sulfur content in the cross-sections of the membranes by energy dispersive X-ray diffraction (EDX) analysis, the gradient in the DEC was confirmed. The amount of sulfur is lowest in the membrane top, where the crosslinking density is the highest and increases gradually towards the bottom. Moreover, similar to previously reported polyvinylimidazolium counterparts, the membranes from PCMVPy-Tf₂N and the multivalent organic acids show a gradient in their pore size with smallest pores in the denser upper part and larger pores in the less cross-linked bottom (Figure 1b-c).³⁴

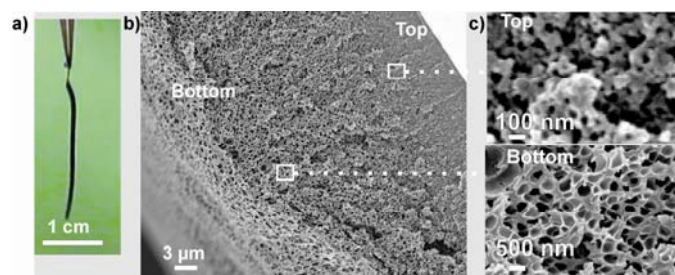


Figure 1: a) Photograph of a stripe-shaped membrane. b) Cross-section view of a porous PIL membrane prepared from PCMVPy-Tf₂N with acid 3. c) An enlarged view of the same membrane on the top and at the bottom.

In order to show that PCMVPy-Tf₂N may be generally complexed by multivalent acids, polymeric and low molecular weight organic acids (**2-9**) were employed as cross-linkers, yielding membranes with average pore sizes ranging from 460 down to 70 nm. The average pore sizes of the membranes followed the same trend as reported for polyvinylimidazolium membranes with benzoic acid derivatives³⁴, *i.e.* acids of higher multivalency yield membranes with smaller pore sizes (Figure S5, Table 1 and Table S1). The higher

multivalency results in overall higher cross-linking density, which is important to stabilize smaller nanosized pores.

Table 1: Average pore sizes of the membrane cross-section of PCMVPy-Tf₂N with different acids employed as cross-linker.

Acid	1	2	3	4	5	6	7	8	9
Pore size / nm	-	460	270	155	174	100	300	216	70

With these porous membranes in hand, we started to investigate their actuation properties. Generally speaking, membranes of PCMVPy-Tf₂N and acids **2-9** are all responsive to water. Placed into a wet environment, the membranes have a stretched shape, whereas upon drying they bend into loops with the upper part of the membrane inward. Depending on the type of acid used for network formation, the bending degree and speed differ significantly. In a systematic study, benzoic acid derivatives **2-6** were employed as a model system, where only the multivalency of the benzoic acids varies. The humidity sensing properties of these membranes were studied by taking membrane stripes with dimensions of 30 mm x 2 mm from a water-filled petri dish, blotting the bulk water from the stripe surface by filter paper, and recording immediately the time-dependent bending angle (unit in rad) by a digital camera. In order to obtain representative and comparable results, the bending angle was multiplied by the thickness of the membranes, which varied depending on the acid (Figure 2a) and is known to have a major influence on the bending behavior of materials. .

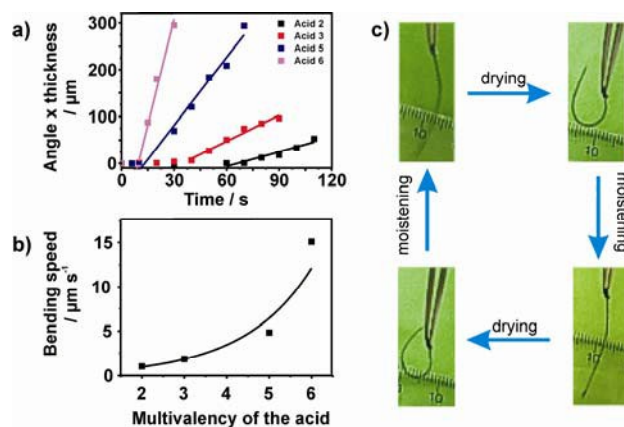


Figure 2: a) Plot of bending angle x membrane thickness vs. time for membrane actuators prepared from different acids. b) Bending speed derived from the slopes of b) vs. multivalency of the acid. c) On-off experiment, where a membrane from acid 6 was repeatedly dried and wetted.

The maximal bending angle and the bending speed increase with the multivalency of the benzoic acid (Figure 2a-b). The bending speed is lowest for membranes prepared from PCMVPy-Tf₂N and acid **2**, reaching a maximal angle within 110 s (see ESI for angle calculations). This membrane fails to recover its original shape after being placed back in water, that is, the humidity sensing property is irreversible. For membranes with acids of higher multivalency, the bending and unbending speed in the dry and wet state increase significantly and the actuation becomes reversible (Figure 2c). Membranes of acid **6** show the fastest kinetics, curving within 30 s to its maximal bending angle.

The water responsiveness of these membranes is traced back to the gradient in the DEC from the top to the bottom of the membranes. The dehydration of the charged polymer chains results in a strong decrease of the dielectric constant of the polymer chain's environment. Since the coulombic attraction is indirectly proportional to the dielectric constant of the surrounding medium, the attraction between the polymer and the acid carboxylates increases as water, possessing a relatively large dielectric constant compared to air, is evaporating from the membrane. On account of the gradient in the cross-linking structure of the material, this contraction leads to a membrane bending movement. This explanation was further confirmed by temperature variation. As the dielectric constant of water in its liquid state decreases with increasing temperatures,³⁶ the membranes in water also take a bending conformation when water temperature jumps from 20 to 60 °C.

The difference in the bending speed of the membranes prepared from different acids is related to multiple factors, such as pore size, pore size distribution, pore volume, DEC, DEC distribution, crosslinking density, *etc.* For example, the porous structure compared with the non-porous one is believed to speed up the bending as it facilitates the fast mass-transport of water in and out of the material.²¹ This is however only true when the mechanical property of the membrane remains constant or is a secondary effect. The aforementioned factors are often intercorrelated with each other and intrinsically connected to the choice of the acids. Therefore, at present it is difficult to dissect the role of each structure factor and to discriminate it from potential subtle changes in others. In spite of this limitation, our data indicate that the choice of acid for the fabrication process is a convenient means to modulate the actuation degree and kinetics.

After analysis of the responsiveness of these membranes in wet and dry environment, their chemical stability in aqueous environment was of intrinsic importance to be examined. The membranes' leaching properties were therefore investigated by taking Fourier-transformed infrared (FTIR)-spectra of the aqueous solution, in which they were stored for months. It was found that neither polymer nor acid compounds were blooming out of the membrane (Figure S2), showing their chemical stability in aqueous environment though shrinkage of the average pore size was observed by SEM characterization of the membrane during the stability test.

A common issue of practical applications of humidity induced actuators is the alteration of their properties by growth of algae, bacteria or fungi. The growth of such organisms may degrade the membrane function and should be desirably inhibited. There are studies about the toxicity of ionic liquids³⁷⁻⁴¹, however little-to-no is reported about their polymeric derivatives, though many synthetic ionic polymers are considered toxic.⁴²⁻⁴⁴ Correspondingly, we performed cytotoxicity tests by MTS assays on two different cell lines, L929 mouse fibroblast cells and CHO hamster ovary cells (Figure 3a-b). The MTS assay is a standard colorimetric method to determine cell viability by UV-detection of formazan, which is formed from added colorless tetrazolium derivatives by cell enzymes.⁴⁵ It was found that the porous membranes strongly inhibited growth of both cell lines. For these studies, we have tested

a benzoic acid (3), a polymeric acid (7), and a natural acid (9). From the results, we conclude that the cytotoxicity of these membranes was regardless of the type of acids, as even membranes from natural acids strongly inhibited cell growth. The cationic polymer seems to be the major reason for the membrane cytotoxicity, since it may inhibit cell growth by electrostatic complexation with negatively charged biomolecules, such as proteins or phospholipids.³⁹⁻⁴¹ The results of the MTS assay show that the tested membranes markedly inhibit the growth of the selected eukaryotic cell lines.

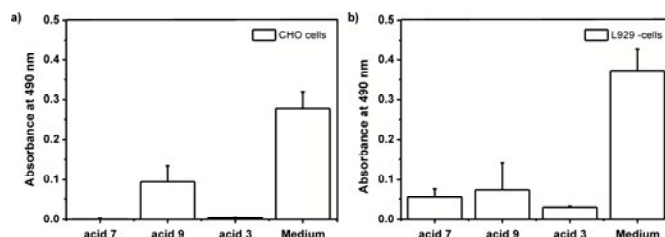


Figure 3: Results of the MTS cell toxicity tests. a) CHO-cell line. b) L929 cell line. The absorbance of the cell medium containing *in-vivo* generated formazan dye is plotted for membranes from PCMVPy-Tf₂N and different organic acids.

In summary, we have fabricated porous polyelectrolyte membranes by electrostatic cross-linking of a polyvinylpyridinium-based poly(ionic liquid) with multivalent organic acids. The actuation speed and degree when drying the membrane was tuneable in terms of the multivalency of the benzoic acid derivative utilized for electrostatic complexation. Furthermore, we have shown that this material, on account of its charged character, strongly inhibits cell growth and may therefore be used as a potential antifouling coating and material. This work in general points out that porous gradient PIL membranes do not need to be necessarily polyvinylimidazolium-based, but are also achievable *via* other PILs, which opens a new dimension to functionalize membranes by structure variation.

Notes and references

- ^a Max Planck Institute of Colloids and Interfaces, Dep. of Colloid Chemistry, Am Mühlenberg 1, 14476 Potsdam, Germany
^b Max Planck Institute of Colloids and Interfaces, Dep. of Biomolecular Systems, Arnimallee 22, 14195 Berlin, Germany
^c Free University Berlin, Dep. of Biology, Chemistry, and Pharmacy, Arnimallee 22, 14195 Berlin, Germany


Acknowledgements

This research is supported by the ERC (European Research Council) Starting Grant with project number 639720 – NAPOLI, and the Max Planck Society. B.L. thanks the German Federal Ministry of Education and Research (BMBF) for financial support. We thank Marie Urbicht and Uwe Vogel for help with the cell toxicity assays.

- Kumar, A.; Srivastava, A.; Galaev, I. Y.; Mattiasson, B., *Prog. Polym. Sci.* **2007**, *32* (10), 1205-1237.
- Mirfakhrai, T.; Madden, J. D. W.; Baughman, R. H., *Materials Today* **2007**, *10* (4), 30-38.

- 3 O'Halloran, A.; O'Malley, F.; McHugh, P., *J. Appl. Phys.* **2008**, *104* (7), -.
- 4 Pang, C.; Lee, C.; Suh, K.-Y., *J. Appl. Polym. Sci.* **2013**, *130* (3), 1429-1441.
- 5 England, D.; Tambe, N.; Texter, J., *ACS Macro Lett.* **2012**, *1* (2), 310-314.
- 6 Stuart, M. A. C.; Huck, W. T. S.; Genzer, J.; Muller, M.; Ober, C.; Stamm, M.; Sukhorukov, G. B.; Szleifer, I.; Tsukruk, V. V.; Urban, M.; Winnik, F.; Zauscher, S.; Luzinov, I.; Minko, S., *Nat. Mater.* **2010**, *9* (2), 101-113.
- 7 Nakano, T.; Takeoka, Y.; Rikukawa, M.; Sanui, K., *Synth. Met.* **2005**, *153* (1-3), 121-124.
- 8 Jangu, C.; Wang, J.-H. H.; Wang, D.; Sharick, S.; Heflin, J. R.; Winey, K. I.; Colby, R. H.; Long, T. E., *Macromol. Chem. Phys.* **2014**, *215* (13), 1319-1331.
- 9 Asaka, K.; Mukai, K.; Sugino, T.; Kiyohara, K., *Polym. Int.* **2013**, *62* (9), 1263-1270.
- 10 Tokarev, I.; Orlov, M.; Minko, S., *Adv. Mater.* **2006**, *18* (18), 2458-2460.
- 11 Baker, C. O.; Shedd, B.; Innis, P. C.; Whitten, P. G.; Spinks, G. M.; Wallace, G. G.; Kaner, R. B., *Adv. Mater.* **2008**, *20* (1), 155-158.
- 12 DeLuca, N. W.; Elabd, Y. A., *J. Polym. Sci., Part B: Polym. Phys.* **2006**, *44* (16), 2201-2225.
- 13 Nguyen, P. T.; Wiesenauer, E. F.; Gin, D. L.; Noble, R. D., *J. Membr. Sci.* **2013**, *430* (0), 312-320.
- 14 Decher, G.; Hong, J.-D., *Makromol. Chem., Macromol. Symp.* **1991**, *46* (1), 321-327.
- 15 Decher, G.; Hong, J. D.; Schmitt, J., *Thin Solid Films* **1992**, *210-211*, Part 2 (0), 831-835.
- 16 Lvov, Y.; Decher, G.; Moehwald, H., *Langmuir* **1993**, *9* (2), 481-486.
- 17 Mallwitz, F.; Laschewsky, A., *Adv. Mater.* **2005**, *17* (10), 1296-1299.
- 18 Hiller, J. A.; Mendelsohn, J. D.; Rubner, M. F., *Nat. Mater.* **2002**, *1* (1), 59-63.
- 19 Li, Q.; Quinn, J. F.; Caruso, F., *Adv. Mater.* **2005**, *17* (17), 2058-2062.
- 20 Lutkenhaus, J. L.; McEennis, K.; Hammond, P. T., *Macromolecules* **2008**, *41* (16), 6047-6054.
- 21 Zhao, Q.; Dunlop, J. W. C.; Qiu, X.; Huang, F.; Zhang, Z.; Heyda, J.; Dzubilla, J.; Antonietti, M.; Yuan, J., *Nat. Commun.* **2014**, *5*.
- 22 Zhao, Q.; Yin, M.; Zhang, A. P.; Prescher, S.; Antonietti, M.; Yuan, J., *J. Am. Chem. Soc.* **2013**, *135* (15), 5549-5552.
- 23 Mecerreyes, D., *Prog. Polym. Sci.* **2011**, *36* (12), 1629-1648.
- 24 Green, O.; Grubjesic, S.; Lee, S.; Firestone, M. A., *Polym. Rev.* **2009**, *49* (4), 339-360.
- 25 Lu, J.; Yan, F.; Texter, J., *Prog. Polym. Sci.* **2009**, *34* (5), 431-448.
- 26 Coupillaud, P.; Fèvre, M.; Wirocius, A.-L.; Aissou, K.; Fleury, G.; Debuigne, A.; Detrembleur, C.; Mecerreyes, D.; Vignolle, J.; Taton, D., *Macromol. Rapid Commun.* **2014**, *35* (4), 422-430.
- 27 Cordella, D.; Kermagoret, A.; Debuigne, A.; Riva, R.; German, I.; Isik, M.; Jérôme, C.; Mecerreyes, D.; Taton, D.; Detrembleur, C., *ACS Macro Lett.* **2014**, *3* (12), 1276-1280.
- 28 Nykaza, J. R.; Ye, Y.; Elabd, Y. A., *Polymer* **2014**, *55* (16), 3360-3369.
- 29 Marcilla, R.; Alberto Blazquez, J.; Rodriguez, J.; Pomposo, J. A.; Mecerreyes, D., *J. Polym. Sci., Part A: Polym. Chem.* **2004**, *42* (1), 208-212.
- 30 Klahn, M.; Stüber, C.; Seduraman, A.; Wu, P., *J. Phys. Chem. B* **2010**, *114* (8), 2856-2868.
- 31 Yan, F.; Texter, J., *Angew. Chem., Int. Ed.* **2007**, *46* (14), 2440-2443.
- 32 England, D.; Yan, F.; Texter, J., *Langmuir* **2013**, *29* (38), 12013-12024.
- 33 Wiesenauer, E. F.; Nguyen, P. T.; Newell, B. S.; Bailey, T. S.; Noble, R. D.; Gin, D. L., *Soft Matt.* **2013**, *9* (33), 7923-7927.
- 34 Täuber, K.; Zhao, Q.; Antonietti, M.; Yuan, J., *ACS Macro Lett.* **2015**, *4*, 39-42.
- 35 Yuan, J.; Marquez, A. G.; Reinacher, J.; Giordano, C.; Janek, J.; Antonietti, M., *Polym. Chem.* **2011**, *2* (8), 1654-1657.
- 36 Owen, B. B.; Miller, R. C.; Milner, C. E.; Cogan, H. L., *J. Phys. Chem.* **1961**, *65* (11), 2065-2070.
- 37 e Silva, F. A.; Siopa, F.; Figueiredo, B. F. H. T.; Gonçalves, A. M. M.; Pereira, J. L.; Gonçalves, F.; Coutinho, J. A. P.; Afonso, C. A. M.; Ventura, S. P. M., *Ecotoxicol. Environ. Saf.* **2014**, *108* (0), 302-310.
- 38 Choi, S. Y.; Rodriguez, H.; Gunaratne, H. Q. N.; Puga, A. V.; Gilpin, D.; McGrath, S.; Vyle, J. S.; Tunney, M. M.; Rogers, R. D.; McNally, T., *RSC Adv.* **2014**, *4* (17), 8567-8581.
- 39 Choi, S. Y.; Rodriguez, H.; Mirjafari, A.; Gilpin, D. F.; McGrath, S.; Malcolm, K. R.; Tunney, M. M.; Rogers, R. D.; McNally, T., *Green Chem.* **2011**, *13* (6), 1527-1535.
- 40 Latala, A.; Nedzi, M.; Stepnowski, P., *Green Chem.* **2009**, *11* (9), 1371-1376.
- 41 Latala, A.; Nedzi, M.; Stepnowski, P., *Green Chem.* **2009**, *11* (4), 580-588.
- 42 Biesinger, K. E.; Lemke, A. E.; Smith, W. E.; Tyo, R. M., *Journal (Water Pollution Control Federation)* **1976**, *48* (1), 183-187.
- 43 Bolto, B.; Gregory, J., *Water Res.* **2007**, *41* (11), 2301-2324.
- 44 Biesinger, K. E.; Stokes, G. N., *Journal (Water Pollution Control Federation)* **1986**, *58* (3), 207-213.
- 45 Mosmann, T., *J. Immunol. Methods* **1983**, *65* (1-2), 55-63.

TOC

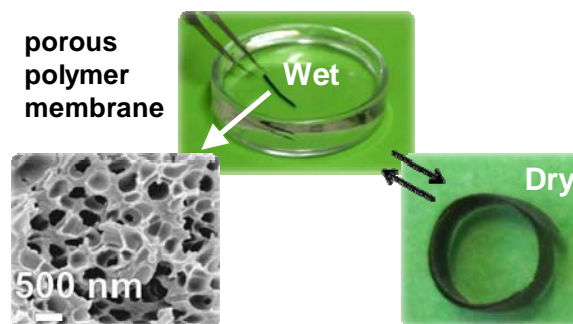

Gradient porous membranes were prepared from a poly(4-vinylpyridinium) polymer together with carboxylic multi-acid compounds via electrostatic complexation.