

Polymer Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

A Dinuclear Gold(I) Complex as a Novel Photoredox Catalyst for Light-Induced Atom Transfer Radical Polymerization

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/Frida Nzulu,^a Sofia Telitel,^b François Stoffelbach,^a Bernadette Graff,^b Fabrice Morlet-Savary,^b Jacques Lalevée,^{*b} Louis Fensterbank,^{*a} Jean-Philippe Goddard,^{*c} Cyril Ollivier^{*a}

Controlled/living atom transfer radical polymerization of methacrylates and acrylates initiated by ethyl α -bromophenylacetate (EBPA) as initiator in the presence of low loadings (1.25 mol% vs. initiator) of a dinuclear gold(I) complex based photocatalyst $[\text{Au}_2(\mu\text{-dppm})_2]\text{Cl}_2$ has been accomplished in solution and in laminate under UVA and visible-light photoreductive conditions. In solution, the linear increase of molecular weights with methyl methacrylate (MMA) conversion and the low dispersity are consistent with a controlled/living process. In film, trimethylolpropane triacrylate (TMPTA) was polymerized and the ethyl α -bromophenylacetate (EBPA)/ $[\text{Au}_2(\mu\text{-dppm})_2]\text{Cl}_2$ system resulted in faster rate of polymerization compared to EBPA/Ir(ppy)₃. Chain extensions of polymers were successfully conducted leading to block copolymers, which also confirms the living character of this new system. Photophysical experiments support a conventional photoredox-catalyzed ATRP mechanism. Finally, this approach utilizes a gold catalyst featuring better solubility and lower cost than the well-known Ir(ppy)₃ complex.


Introduction

Controlled/Living radical polymerization (CRP) is among the most rapidly developing areas of chemistry and polymer science. Over the last decades, many novel previously inaccessible materials have been prepared using CRP. This process has provided access to nearly all types of macromolecular species exhibiting predetermined molecular weights, low dispersities, and precisely controlled composition and architectures (block copolymers, star-like, comb-like, dendritic...).¹ The CRP techniques that have been implemented so far consist mainly in reversible addition-fragmentation chain transfer polymerization (RAFT),² organometallic radical polymerization,³ nitroxide-mediated polymerization (NMP)⁴ and atom transfer radical polymerization (ATRP).⁵ In all these CRP methods, control is achieved by the equilibrium maintained between an active and a dormant chain *via* a reversible deactivation mechanism (RDRP). Currently, these systems are initiated by free-radical initiators and/or metal catalysts and by external stimuli including chemical reducing agents, microwave, heat, electrical current and light.⁶

The use of photochemical stimuli had a tremendous impact not only in organic chemistry,⁷ molecular biology and electronics but also in polymer chemistry since the pioneer work of Otsu.⁸ Accordingly

some controlled radical photopolymerization (CRP2) methodologies have been recently proposed. The most substantial advantage is that photo-induced processes are extremely fast, give access to spatially controlled reactions for photografting, photoinduced modification or (micro)patterning of surfaces. They also represent an environment friendly alternative to thermal processes allowing reactions to proceed under mild conditions and to use functional groups and materials that decompose at high temperatures. Several CRP2 systems including transition metal-mediated CRP,⁹ RAFT,¹⁰ NMP,^{4,11} ITP¹² and ATRP have been applied. Of all the CRPs, ATRP¹³ has been the focus of intense research in the polymer community owing to its versatility for the synthesis of well-defined polymers. Quite recently, Matyjaszewski's,¹⁴ Yagci's,¹⁵ and Hawker's¹⁶ groups have successfully devised reactive systems exploiting the redox properties of copper and iridium catalysts respectively in the presence of light. In this field, the development of very efficient photosensitive systems for UVA/visible light remains a huge challenge. Indeed, these radiations are safer than the more-energetic UVB and UVC light for the operator, more chemoselective causing less side reactions with reactants, and also eco-friendly (low energy consumption, no release of ozone or harmful UV rays and very little heat emission). Among the few examples of gold catalyzed polymerization,¹⁷ the use of a gold photocatalyst to

promote photo-ATRP upon UVA/visible light has not been reported so far.

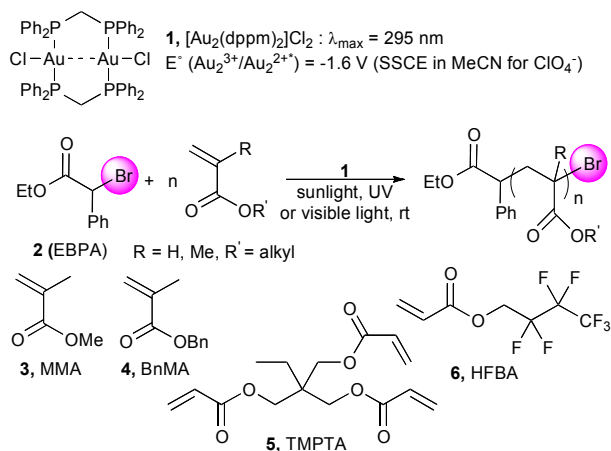

Scheme 1 Atom Transfer Radical Polymerization of various (meth)acrylates catalyzed by digold bis(diphenylphosphino)methane dichloride $[\text{Au}_2(\mu\text{-dppm})_2]\text{Cl}_2$ **1** as a photoredox catalyst.

In this context, we showed that photoactivated digold bis(diphenylphosphino)methane dichloride $[\text{Au}_2(\mu\text{-dppm})_2]\text{Cl}_2$ **1** first reported by Schmidbauer,¹⁸ was able to catalyze ATRP processes (Scheme 1). Photoredox properties of the corresponding photoactivated cationic complex $[\text{Au}_2(\mu\text{-dppm})_2][\text{ClO}_4]$ were studied by Che who highlighted its ability to generate carbon-centered radicals by single electron transfer (SET) from alkyl halides.¹⁹ In 2013, Barriault nicely demonstrated the synthetic potential of **1** in combination with Hünig's base as a sacrificial electron donor for the photoreduction of unactivated aryl and alkyl bromides.²⁰ Inspired by these seminal works, we anticipated that the unique properties of **1** would permit SET reduction of activated alkyl bromides, initiate and control ATRP processes. Therefore, we investigated the catalytic properties of **1** in different solvents at rt under light activation to generate a carbon-centered radical from ethyl α -bromophenylacetate (EBPA, **2**) and trigger polymerization of rather hydrophilic monomers such as methyl methacrylate (MMA, **3**) in solution and trimethylolpropane triacrylate (TMPTA, **5**) in laminate. Chain extension experiments with benzyl methacrylate (BnMA, **4**) and hydrophobic 2,2,3,3,4,4,4-heptafluorobutyl acrylate (HFBA, **6**) were also studied (Scheme 1).

Results and discussions

UV-visible and luminescence spectroscopies were used to determine the photophysical properties of **1** and understand its role as a photoredox catalyst (see Supporting information, S-8). The UV-visible absorption spectrum of **1** exhibits two bands at 258 nm ($\epsilon_{\text{max}} 42\,343 \text{ L}\cdot\text{mol}^{-1}\cdot\text{cm}^{-1}$) and 320 nm ($\epsilon_{\text{max}} 11\,343 \text{ L}\cdot\text{mol}^{-1}\cdot\text{cm}^{-1}$). A weak and broad absorption band at 320 nm was visualized while under excitation at the same wavelength, the luminescence spectroscopy of **1** showed a strong emission-band at 390 nm. Thus, the energy of the excited state has been determined as $^*E(\text{Au}_2^{\text{II}}) \approx 3.5 \text{ eV}$ ($^*E(\text{Au}_2^{\text{II}}) \approx 1240/((390+320)/2) \approx 3.5 \text{ eV}$). The frontier molecular orbitals

obtained for the optimized geometry of **1** are given in supporting information (Figure 12) and suggest a metal to ligand charge transfer transition MLCT for this lowest energy band the HOMO and the LUMO being located on the metal and ligand moieties, respectively.

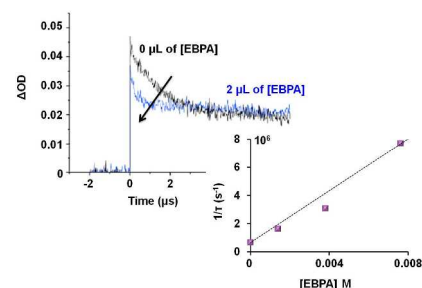


Figure 1 Laser flash photolysis. Decay of the $[\text{1}]^{\text{II}*}$ signal at 390 nm in dichloromethane with increasing concentrations of **2**. The arrow shows that the $\text{Au}_2^{\text{II}*}$ lifetime decreases as the concentration of **2** increases (from 0 to $7.6 \cdot 10^{-3} \text{ M}$). ΔOD is the change in optical density associated with the light excitation ($\lambda = 355 \text{ nm}$).

We used laser flash photolysis (LFP) experiments in order to know if the initiator **2** was able to interact with the excited state of complex **1** ($\text{Au}_2^{\text{II}*}$). The transient absorption spectrum was recorded after laser flash excitation at 355 nm.²¹ The excited state of **1** is characterized by a transient absorption at about 390 nm in accordance with Che's results.²² Then, LFP allowed to determine the rate constant of the $\text{Au}_2^{\text{II}*}$ quenching by **2** (Figure 1).²³ Increasing amount of **2** was added to a solution of **1** under irradiation and a decay of $\text{Au}_2^{\text{II}*}$ absorption at 390 nm in DCM was observed. When **2** was omitted, lifetime of **1** was 1.56 μs under nitrogen atmosphere. This value significantly decreased to 110 ns in the presence of 4 μL of **2** ($7.6 \cdot 10^{-3} \text{ M}$) (Figure 1). From a Stern-Volmer analysis, we have found that **2** is an excellent oxidative quencher of $\text{Au}_2^{\text{II}*}$ with a rate constant photolysis of $9.2 \cdot 10^8 \text{ M}^{-1} \text{ s}^{-1}$. In addition, the cyclic voltammogram (CV) of **1** revealed three oxidation waves that appeared at +0.6 V, +1.2 V and +2.0 V in MeCN vs SCE. The first wave at +0.6 V is assigned to Au^{I} metal-centered oxidation process while the CV of **2** also gave a reduction potential at -1.3 V (in MeCN vs SCE). Thus, the oxidation of $\text{Au}_2^{\text{II}*}$ by **2** would presumably occur as supported by the favorable free energy change ΔG , derived from the Rehm-Weller equation ($\Delta G^\circ = -1.6 \text{ eV}$) (see Supporting information, S-10). These initial findings suggest that the rate of photoreaction is primarily governed by the homolysis of the C-Br bond of EBPA. These also support that the system **1/2** could be used to initiate radical polymerization with no need of an additional sacrificial donor of electron, as required for the photoreduction of unactivated aryl and alkyl bromides.²⁰

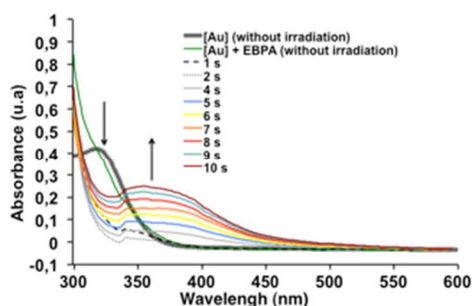


Figure 2 Steady state photolysis of **1** and **2** in dichloromethane upon exposure to the Xe-Hg under air at different irradiation times (from $t = 0$ to 10 s). **1/2**: 1/0.045. UV-vis spectra clearly demonstrate that one species disappears rapidly at very early stage and one appears.

To support this mechanism, we monitored the steady state photolysis of [**1**] in the presence of **2**. We observed a strong decrease of the absorption band at 320 nm upon diode laser exposure concomitantly with the apparition of a band at 420 nm over 10 s of irradiation (Figure 2). This result confirmed the quenching of the excited state of **1** by the initiator **2** leading to the formation of ethyl phenylacetyl radical, that could initiate the radical polymerization, and an oxidized gold complex $\{[\text{Au}_2(\mu\text{-dppm})_2\text{Cl}_2]^+, \text{Br}^-\}$ with an absorption UV signal suspected at 420 nm.

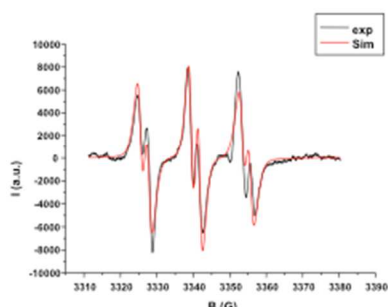


Figure 3. ESR spin trapping (PBN) spectrum. $[\text{PBN}] = 7.90 \cdot 10^{-4}$ M, $[\mathbf{1}] = 1.57 \cdot 10^{-4}$ M, $[\mathbf{2}] = 1.91 \cdot 10^{-3}$ M in 1.5 mL of DCM/*tert*-butylbenzene 1:2.


From this system, the generation of carbon-centered radical intermediate derived from **2** was also confirmed by ESR spin-trapping experiments (Figure 3).²⁴ A dichloromethane solution of **2/1** and *N-tert*-butyl- α -phenylnitron (PBN) was irradiated (Xe-Hg lamp) during 20 s and monitored by ESR. A characteristic signal of a nitroxide adduct which originates from the addition of the phenylacetate radical to PBN ($a_N = 14.3$ G, $a_H = 2.5$ G) was observed. Similarly, 6 minutes of sunlight exposition to the same solution resulted in an identical ESR signal. This set of experiments confirmed that gold catalyst **1** allows a very responsive photo radical process and **2** is an excellent oxidative quencher. Given the perfect adequacy in terms of photochemical properties and reactivity between catalyst **1** and initiator **2**, polymerization of MMA **3** in solution was then carried out.

Influence of the irradiation wavelength and the solvent were first examined. Typical conditions involved a controlled concentration of MMA (2.08 M) with an initiator/monomer/catalyst (**2/3/1**) ratio fixed at 1/500/0.0125

(mol/mol). Conversion of **3**, molecular weight and dispersity of the so-formed PMMA were measured by gravimetry and GPC analysis and reported in Table 1.

Experiments were performed in *N,N'*-dimethylformamide (DMF) or dichloromethane (DCM) under UV to visible-light activation at 25 °C. At 300 nm in DMF, 84% of conversion was reached in 24 h (Table 1, entry 1). PMMA with lower number-average molar mass than the theoretical value was obtained with a dispersity of 1.81. Under these reaction conditions, effective initiation proceeded but the physical datas of the PMMA can be diagnostic of side reactions. Lower conversions were observed at 380 and 419 nm (54 and 63% respectively) and the resulting polymers have higher molar mass, revealing a failure of the initiation system (Table 1, entries 3-4). A good control of the polymerization was achieved when the irradiation was done at 350 nm (Table 1, entry 2). The conversion of MMA was 75%, the molar mass distribution (\mathcal{D}) of PMMA decreased to 1.67 with a number-average molar mass closer than the theoretical value. Well controlled polymerization was also obtained in DCM under irradiation at 350 nm (Table 1, entry 5). Molar mass fitted with the theoretical value and the dispersity was 1.62. These last results indicated that the initiation process was efficient and side reactions giving birth to dead chains were very limited. In order to argue in the favor of a controlled radical polymerization, the same mixture of **2/3/1** was placed in the dark and no polymer was formed (Table 1, entry 6). If gold catalyst was omitted, polymerization occurred but cannot be controlled (Table 1, entry 7).

Table 1 Polymerization of MMA **3** catalyzed by $[\text{Au}_2(\mu\text{-dppm})_2\text{Cl}_2]$ under light activation.^a

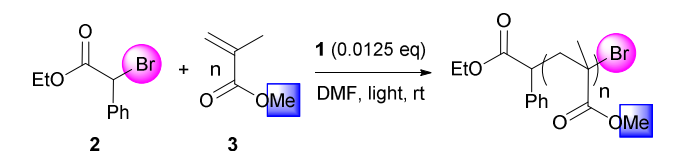


Entry	Light (nm)	2 Conv. ^b (%)	$M_{n,theo}$ (kg mol ⁻¹)	$M_{n,exp}$ (kg mol ⁻¹)	\mathcal{D} ^c
1	300	84	42.3	34.0	1.81
2	350	75	37.5	34.0	1.67
3	380	54	27.4	42.0	1.77
4	419	63	31.7	48.4	1.85
5	350 ^d	55	27.8	24.7	1.62
6	dark	-	-	-	-
7	350 ^e	100	50.0	25.0	2.1

^a Polymerizations were performed with $[\text{MMA}] = 2.08$ M (vol MMA + vol solvent) at rt with **2/3/1** = 1/500/0.0125 mol/mol. All reactions were degassed before setting the reaction. ^b Conversion measured by gravimetric analysis. ^c Determined after one precipitation in MeOH. ^d Reaction performed in DCM. ^e Reaction in a mixture **2/3** (1/500) in DMF without gold catalyst.

To evaluate the living character of this polymerization process, chain extension experiments were conducted using MMA or BnMA as second monomer (Scheme 2). An original sample of PMMA obtained by the present protocol and purified by precipitation in methanol ($M_n = 18.0$ kg mol⁻¹, $\mathcal{D} = 1.32$), was consider as

macroinitiator and placed in DMF with MMA **3** and the gold photocatalyst **1** in a 1/500/0.0125 proportion respectively (Scheme 2, Figure A). After 24 h of irradiation at 350 nm, PMMA homopolymer was isolated showing an important increase of M_n up to 30.9 kg mol⁻¹. From a different PMMA sample ($M_{n,exp} = 14.2$ kg mol⁻¹, $D = 1.50$), a block copolymer was obtained with BnMA **4** (PMMA/4/1 1/500/0.0125 mol/mol) (Scheme 2, Figure B). Similarly, a considerable $M_{n,exp}$ increase was observed and has been determined to 43.8 kg mol⁻¹. The corresponding SEC traces of both experiments showed the evolution of the polymer populations. This clearly demonstrated the possibility to reactivate the bromide terminus of the polymer. Thus, it appears reasonable to postulate a photoATRP pathway for this novel new gold-catalyzed polymerization.

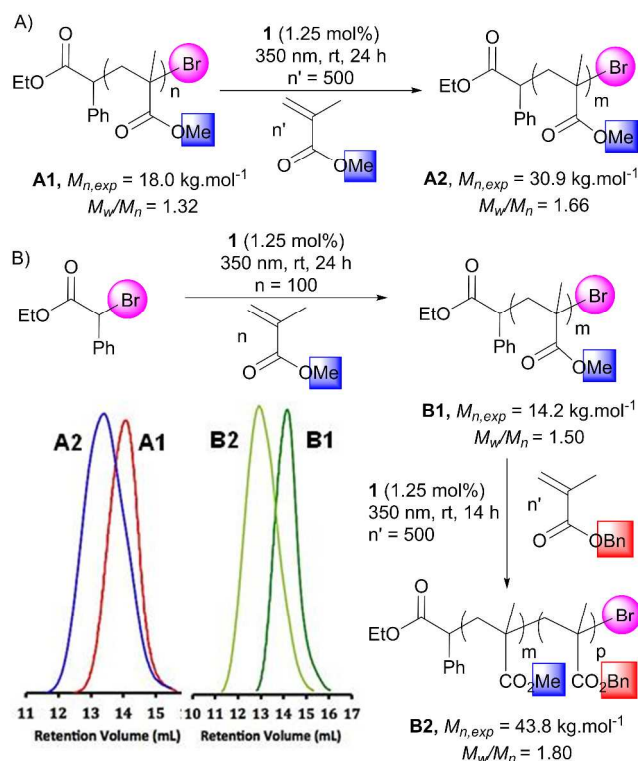

Scheme 2 A) Chain extension of poly(methyl methacrylate) with MMA and SEC chromatogram with the red and blue traces corresponding respectively to A1 and A2. B) Synthesis of poly(methyl methacrylate)-*b*-poly(benzyl methacrylate) well defined diblock copolymer and SEC chromatograms with the dark green and light green corresponding respectively to B1 and B2.

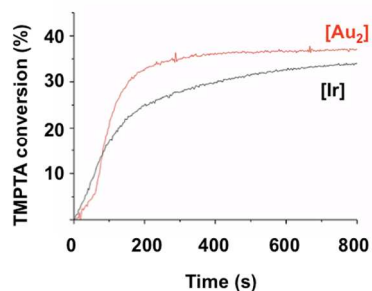


Figure 4 Compared polymerization profiles for TMPTA in laminate system for different catalysts upon a blue LED bulb irradiation (405 nm). Red curve: **2/5/1** (1/100/0.0125 mol/mol); black curve: **2/5/fac-Ir(ppy)₃** (1/100/0.0125 mol/mol).

As initial experiments revealed that **1** efficiently catalyzes the polymerization of methacrylates **3** and **4** in solution, comparative kinetic experiments were carried out. Laminate system, was chosen to compare the present system (**2/1**) with the known **2/fac-Ir(ppy)₃** (Figure 4). To address this question, the polymerization of TMPTA **5** in laminate with both systems was monitored by RT-FTIR spectroscopy at 405 nm. The disappearance of a characteristic absorption band of **5** (1600-1650 cm⁻¹) served to measure the conversion of this monomer.²⁵ The **2/fac-Ir(ppy)₃** polymerization profile (black curve) showed a rapid initial rate to reach 33% conversion in 800 s. After an activation period of 50 s, the **2/1** system gave a faster polymerization rate than with iridium to reach 38% conversion in 400 s. The iridium catalyst was already known to be very efficient but to our delight, this new gold photocatalyst **1** proved to be even more active for the polymerization of acrylates in bulk.

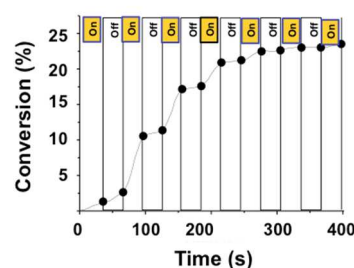


Figure 5 TMPTA conversion as a function of time for intermittent blue LED bulb irradiation. Polymerization was performed from **2/5/1** (1/100/0.0125 mol/mol) mixture.

The dependence of this polymerization process to light was further studied by employing a periodic “on/off” light event during the TMPTA polymerization in laminate **2/5/1** (1/100/0.0125 mol/mol) (Figure 5). The film was irradiated with LED bulbs (405 nm) with alternating irradiation periods (30 s) and blackout (30 s). The conversion of **5** was monitored by RT-FTIR spectroscopy and reported in Figure 5 according to the sequential irradiation. The polymerization rates were dramatically impacted and turning off the light resulted in significantly low rate. Thus, a clear acceleration of the polymerization was observed under irradiation. This experiment also showed the living character of the polymerization and turning off the light did not induce the interruption of the growing chains.


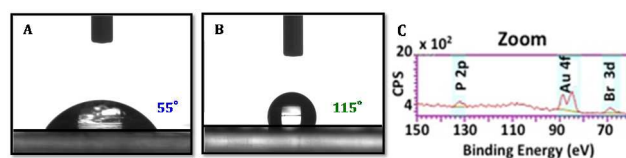


Figure 6 Contact angle experiments: Picture A) First layer: TPMTA/[Au₂]/EBPA: 1/0.0125/100 mol/mol after 3 minutes upon a blue LED bulb irradiation (405 nm). Picture B) Second layer after re-initiation with a fluoromonomer (HFBA **6**) after 10 minutes upon a Xe-Hg lamp. Picture C) represents high resolution XPS spectra after re-initiation and formation of the fluorinated polymer.

Investigation of the living character was extended to surface functionalization. Photo-ATRP of TMPTA **5** in laminate with

the 2/1 system (2/5/1 1/100/0.0125 mol/mol) allowed to obtain a well defined film after Xe-Hg lamp irradiation for 3 min (Figure 6A). Residual monomer was removed by washing with acetone and the surface was analyzed by XPS (See Supporting Information for full spectrum). This analysis evidenced the presence of gold and bromine atoms at the surface of the film. A drop of water on the layer lied with a 55° contact angle in agreement with the wettability character of PMMA. Then, HFBA **6** was deposited on the surface of the first layer and irradiated under the same conditions during 10 minutes (Figure 6B). The contact angle dramatically changed from 55° to 115°, illustrating the surface modification to a more hydrophobic property due to the presence of perfluoroalkyl chains. This change proved the reactivation of the first layer for the synthesis of block copolymer. Moreover, XPS of the second layer still showed the presence of gold and bromine atoms and open the possibility of a third reactivation process (Figure 5C). TEM (Transmission Electron Microscopy) analysis allowed to visualize the layer surfaces and so to exclude the presence of gold nanoparticles which could have been the active catalyst.

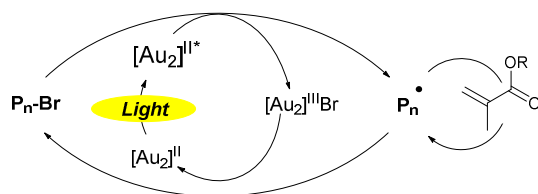

Scheme 3 Proposed mechanism for photo-ATRP of (meth)acrylates using $[\text{Au}_2(\mu\text{-dppm})_2]\text{Cl}_2$ as a photocatalyst.

All these experiments completed by further mass spectrometry analysis by MALDI-TOF/ESI-TOF and ATRA studies (See Supporting Information, S17 and S18) drove us to the following mechanism proposal for this new photoATRP process (Scheme 3). The polymerization relies on the in situ photogeneration of excited state $[\mathbf{1}]^*$ and its subsequent reaction with alkyl halide ($\text{P}_n\text{-X}$) resulting in the formation of the active radical ($\text{P}_n\cdot$) and $[\text{Au}_2]^{\text{III}}\text{X}$. Then, the radical adds onto a monomer and the resulting radical would be rapidly deactivated by $[\text{Au}_2]^{\text{III}}\text{X}$ to form a dormant species and regenerate **1**.

Conclusions

In summary, we report here the first gold-catalyzed photoATRP process of methacrylates and acrylates. The novel photocatalyst $[\text{Au}_2(\mu\text{-dppm})_2]\text{Cl}_2$ in combination with ethyl α -bromophenylacetate (EBPA) as initiator allows the development of a highly responsive controlled living radical polymerization under UVA, sunlight and visible-light irradiation conditions as evidenced by fluorescence and absorbance measurements, steady-state photolysis, laser flash photolysis (LFP), electron spin resonance (ESR) experiments, Fourier transform infrared (FTIR) spectroscopy and “on-off” switchable experiments. In solution, the linear increase of molecular weights with methyl methacrylate (MMA) conversion and the low dispersity are consistent with a

controlled/living process. In film, trimethylolpropane triacrylate (TMPTA) was polymerized and the ethyl α -bromophenylacetate (EBPA)/ $[\text{Au}_2(\mu\text{-dppm})_2]\text{Cl}_2$ system resulted in faster rate of polymerization compared to EBPA/Ir(ppy)₃. Chain extensions of polymers were successfully conducted leading to block copolymers, which confirmed the living character of this system. Importantly, this approach utilizes a gold catalyst with lower cost and more soluble than conventional iridium complexes. The use of dichloromethane as solvent without loss of reactivity will open new perspectives in the combination of this photoATRP process with other polymerization modes. Moreover, the reported system is highly sensitive to sunlight and application of photopolymerization using this source of energy will be envisaged.

Acknowledgements

This work was supported by the CNRS, UPMC and, IUF, which we gratefully acknowledge. This work was supported by the LabEx MiChem part of French state funds managed by the ANR within the Investissements d’Avenir programme under reference ANR-11-IDEX-0004-02. JPG thanks UHA, Fondation pour l’ENSCMu and Actelion for support (Actelion Chair in Innovative Organic Chemistry). The authors acknowledge ANR (NHX ANR-11-BS07-008) to stimulate fruitful collaborations.

Notes and references

- ^a UMR CNRS 8232, Institut Parisien de Chimie Moléculaire, Sorbonne Université UPMC Univ Paris 06, 4 place Jussieu, CC 229, F-75252 Paris Cedex 05, France louis.fensterbank@upmc.fr, cyril.ollivier@upmc.fr
^b Institut de Science des Matériaux de Mulhouse IS2M, UMR 7361 CNRS, Université de Haute Alsace, 15 Rue Jean Starcky, 68057 Mulhouse Cedex, France jacques.lalvee@uha.fr
^c Laboratoire de Chimie Organique et Bioorganique EA 4566, Université de Haute-Alsace, Ecole Nationale Supérieure de Chimie de Mulhouse 3 bis rue Alfred Werner, 68093 Mulhouse Cedex, France jean-philippe.goddard@uha.fr

Electronic Supplementary Information (ESI) available: Characterization data of catalyst, organic compounds and polymers are provided. Photochemical and photophysical properties of the catalytic system are available. See DOI: 10.1039/c000000x/

- a) W. A. Braunecker, K. Matyjaszewski, *Progr. Polym. Sci.*, 2007, **32**, 93. b) A. Goto, T. Fukuda, *Progr. Polym. Sci.*, 2004, **29**, 329.
- a) C. Boyer, V. Bulmus, T. P. Davis, V. Ladmiral, J. Liu, S. Perrier, *Chem. Rev.*, 2009, **109**, 5402. b) J. Chiefari, Y. K. Chong, F. Ercole, J. Krstina, J. Jeffery, T. P. T. Le, R. T. A. Mayadunne, G. F. Meijs, C. L. Moad, G. Moad, E. Rizzardo, S. H. Thang, *Macromolecules*, 1998, **31**, 5559.
- a) I. Allaoua, B. E. Goi, M. M. Obadia, A. Debuigne, C. Detrembleur, E. Drockenmuller, *Polym. Chem.*, 2014, **5**, 2973. b) L. E. N. Allan, M. R. Perry, M. P. Shaver, *Progr. Polym. Sci.*, 2012, **37**, 127. c) S. Yamago, *Chem. Rev.*, 2009, **109**, 5051.
- a) J. Nicolas, Y. Guillauneuf, C. Lefay, D. Bertin, D. Gigmes, B. Charleux, *Progr. Polym. Sci.*, 2013, **38**, 63. b) C. J. Hawker, A. W. Bosman, E. Harth, *Chem. Rev.*, 2001, **101**, 3661.
- a) J. S. Wang, K. Matyjaszewski, *J. Am. Chem. Soc.*, 1995, **117**, 5614. b) M. Kato, M. Kamigaito, M. Sawamoto, T. Higashimura,

- Macromolecules*, 1995, **28**, 1721. c) T. E. Patten, J. Xia, T. Abernathy, K. Matyjaszewski, *Science*, 1996, **272**, 866. d) K. Matyjaszewski, J. Xia, *Chem. Rev.*, 2001, **101**, 2921. d) K. Matyjaszewski, N. V. Tsarevsky, *J. Am. Chem. Soc.*, 2014, **136**, 6513.
- 6 a) F. A. Leibfarth, K. M. Mattson, B. P. Fors, H. A. Collins, C. J. Hawker, *Angew. Chem. Int. Ed.*, 2013, **52**, 199; b) Y. Yagci, S. Jockusch, N. J. Turro, *Macromolecules*, 2010, **43**, 6245. c) N. J. Treat, H. Sprafke, J. W. Kramer, P. G. Clark, B. E. Barton, J. R. de Alaniz, B. P. Fors, C. J. Hawker, *J. Am. Chem. Soc.*, 2014, **136**, 16096.
- 7 For reviews on photoredox catalysis in organic synthesis, see : a) C. K. Prier, D. A. Rankic, D. W. C. MacMillan, *Chem. Rev.*, 2013, **113**, 5322. b) J. M. R. Narayanam, C. R. J. Stephenson, *Chem. Soc. Rev.*, 2010, **40**, 102; c) T. P. Yoon, M. A. Ischay, J. Du, *Nature Chemistry*, 2010, **2**, 527. For our contributions to this field, see : d) M. H. Larrauffe, R. Pellet, L. Fensterbank, J.-P. Goddard, E. Lacôte, M. Malacria, C. Ollivier, *Angew. Chem. Int. Ed.*, 2011, **50**, 4463; e) S. Donck, A. Baroudi, L. Fensterbank, J.-P. Goddard, C. Ollivier, *Adv. Synth. Catal.*, 2013, **355**, 1477. f) A. Baralle, L. Fensterbank, J.-P. Goddard, C. Ollivier, *Chem. Eur. J.*, 2013, **19**, 10809. g) M. Daniel, L. Fensterbank, J.-P. Goddard, C. Ollivier, *Org. Chem. Front.*, 2014, **1**, 551. h) L. Cheneberg, A. Baralle, M. Daniel, L. Fensterbank, J.-P. Goddard, C. Ollivier, *Adv. Synth. Catal.*, 2014, **356**, 2756.
- 8 T. Otsu, A. Kuriyama, *Polym J.*, 1985, **17**, 97.
- 9 a) S. Yamago, Y. Ukai, A. Matsumoto, Y. Nakamura, *J. Am. Chem. Soc.*, 2009, **131**, 2100. b) A. Nomura, A. Goto, K. Ohno, E. Kayahara, S. Yamago, Y. Tsujii, *J. Polym. Sci. A Polym. Chem.*, 2011, **49**, 5284. c) C. Detrembleur, D.-L. Versace, Y. Piette, M. Hurtgen, C. Jérôme, J. Lalevée, A. Debuigne, *Polym. Chem.*, 2012, **3**, 1856. d) Y. Nakamura, T. Arima, S. Tomita, S. Yamago, *J. Am. Chem. Soc.*, 2012, **134**, 5536. e) Y. Nakamura, S. Yamago, *Beilstein J. Org. Chem.*, 2013, **9**, 1607.
- 10 a) J. F. Quinn, L. Barner, C. Barner-Kowollik, E. Rizzardo, T. P. Davis, *Macromolecules*, 2002, **35**, 7620. b) S. Muthukrishnan, E. H. Pan, M. H. Stenzel, C. Barner-Kowollik, T. P. Davis, D. Lewis, L. Barner, *Macromolecules*, 2007, **40**, 2978. c) M. A. Tasdelen, Y. Y. Durmaz, B. Karagoz, N. Bicak, Y. Yagci, *J. Polym. Sci. A Polym. Chem.*, 2008, **46**, 3387. d) C. Zhang, Y. Yang, J. He, *Macromolecules*, 2013, **46**, 3985. e) J. Xu, K. Jung, A. Atme, S. Shanmugam, C. Boyer, *J. Am. Chem. Soc.*, 2014, **136**, 5508.
- 11 a) S. Hu, J. H. Malpert, X. Yang, D. C. Neckers, *Polymer*, 2000, **41**, 445. b) Y. Guillaneuf, D.-L. Versace, D. Bertin, J. Lalevée, D. Gigmes, J. P. Fouassier, *Macromol. Rapid Commun.*, 2010, **31**, 1909. c) D.-L. Versace, J. Lalevée, J. P. Fouassier, D. Gigmes, Y. Guillaneuf, D. Bertin, *J. Polym. Sci. A Polym. Chem.*, 2010, **48**, 2910. d) D.-L. Versace, J. Lalevée, J. P. Fouassier, Y. Guillaneuf, D. Bertin, D. Gigmes, *Macromol. Rapid Commun.*, 2010, **31**, 1383. e) Y. Guillaneuf, D. Bertin, D. Gigmes, D.-L. Versace, J. Lalevée, J. P. Fouassier, *Macromolecules*, 2010, **43**, 2204.
- 12 A. Wolpers, P. Vana, *Macromolecules*, 2014, **47**, 954.
- 13 a) Z. Guan, B. Smart, *Macromolecules*, 2000, **33**, 6904. b) J. Mosnáček, M. Ilčíková, *Macromolecules*, 2012, **45**, 5859. c) N. V. Alfredo, N. E. Jalapa, S. L. Morales, A. D. Ryabov, R. Le Lagadec, L. Alexandrova, *Macromolecules*, 2012, **45**, 8135.
- 14 a) Y. Kwak, K. Matyjaszewski, *Macromolecules* **2010**, **43**, 5180–5183. b) D. Konkolewicz, K. Schröder, J. Buback, S. Bernhard, K. Matyjaszewski, *ACS Macro Lett.*, 2012, **1**, 1219.
- 15 a) M. A. Tasdelen, M. Uygun, Y. Yagci, *Macromol. Rapid Commun.*, 2011, **32**, 58. b) M. A. Tasdelen, M. Ciftci, Y. Yagci, *Macromol. Chem. Phys.*, 2012, **213**, 1391.
- 16 a) B. P. Fors, C. J. Hawker, *Angew. Chem. Int. Ed.*, 2012, **51**, 8850; b) N. J. Treat, B. P. Fors, J. W. Kramer, M. Christianson, C.-Y. Chiu, J. R. de Alaniz, C. J. Hawker, *ACS Macro Lett.*, 2014, **3**, 580.
- 17 a) L. Ray, V. Katiyar, M. J. Raihan, H. Nanavati, M. M. Shaikh, P. Ghosh, *Eur. J. Inorg. Chem.*, 2006, 3724. b) L. Ray, V. Katiyar, S. Barman, M. J. Raihan, H. Nanavati, M. M. Shaikh, P. Ghosh, *J. Organomet. Chem.*, 2007, **692**, 4259. c) J. Urbano, A. J. Hormigo, P. de Frémont, S. P. Nolan, M. M. Díaz-Requejo, P. J. Pérez, *Chem. Commun.*, 2008, 759. d) E. Brulé, S. Gaillard, M.-N. Rager, T. Roisnel, V. Guérineau, S. P. Nolan, C. M. Thomas, *Organometallics*, 2011, **30**, 2650. e) R. A. Sanguramath, S. K. Patra, M. Green, C. A. Russell, *Chem. Commun.*, 2012, **48**, 1060. f) F. Nzulu, A. Bontemps, J. Robert, M. Barbazanges, L. Fensterbank, J.-P. Goddard, M. Malacria, C. Ollivier, M. Petit, J. Rieger, F. Stoffelbach, *Macromolecules*, 2014, **47**, 6652.
- 18 H. Schmidbaur, A. Wohlleben, F. Wagner, O. Orama, G. Huttner, *Eur. J. Inorg. Chem.*, 1977, **110**, 1748.
- 19 a) D. Li, C.-M. Che, H.-L. Kwong, V. W.-W. Yam, *J. Chem. Soc., Dalton Trans.*, 1992, 3325. b) C.-M. Che, H.-K. Yip, V. W.-W. Yam, P.-Y. Cheung, T.-F. Lai, S.-J. Shieh, S.-M. Peng, *J. Chem. Soc., Dalton Trans.*, 1992, 427.
- 20 a) G. Revol, T. McCallum, M. Morin, F. Gagosz, L. Barriault, *Angew. Chem. Int. Ed.*, 2013, **52**, 13342; b) T. McCallum, E. Slavko, M. Morin, L. Barriault, *Eur. J. Org. Chem.*, 2015, 81.
- 21 The wavelength 355 nm corresponds to the third Nd:YAG harmonic.
- 22 C.-M. Che, H.-L. Kwong, C.-K. Poon hieh, *J. Chem. Soc., Dalton Trans.*, 1990, 3215.
- 23 a) J. Lalevée, N. Blanchard, C. Fries, M.-A. Tehfe, F. Morlet-Savary, J.P. Fouassier, *Polym. Chem.*, 2011, **2**, 1077; b) S. Telitel, J. Lalevée, N. Blanchard, T. Kavalli, M.-A. Tehfe, F. Morlet-Savary, B. Graff, J.P. Fouassier, *Macromolecules*, 2012, **45**, 6864.
- 24 a) N. M. Atherton, M. J. Davies, B. C. Gilbert, P. Tordo. Spin-Trapping: Recent Developments and Applications. In *Electron Paramagnetic Resonance: Volume 16*, B. C. Gilbert, N. M. Atherton, M. J. Davies eds., The Royal Society of Chemistry Cambridge, U.K., 1998, **16**, pp. 116; b) J. Lalevée, F. Dumur, C. R. Mayer, D. Gigmes, G. Nasr, M. A. Tehfe, S. Telitel, F. Morlet-Savary, B. Graff, J. P. Fouassier, *Macromolecules*, 2012, **45**, 4134.
- 25 S. Telitel, F. Dumur, S. Telitel, O. Soppera, M. Lepeltier, Y. Guillaneuf, J. Poly, F. Morlet-Savary, P. Fioux, J. P. Fouassier, D. Gigmes, J. Lalevée, *Polym. Chem.*, 2015, **6**, 613.