

Polymer Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Enhancement of Crosslink Density, Glass Transition Temperature, and Strength of Epoxy Resin by Using Functionalized Graphene Oxide Co-curing Agents†

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/polymers

Jin Won Yu,^{a,b,‡} Jin Jung,^{a,‡} Yong-Mun Choi,^a Jae Hun Choi,^a Jaesang Yu,^a Jae-Kwan Lee,^b Nam-Ho You,^a Munju Goh,^{a,*}

We synthesized diamine-functionalized graphene oxide—DDS-GO and HMDA-GO—by introducing 4,4'-diaminodiphenyl sulfone (DDS) or hexamethylenediamine (HMDA) into the carboxylic acid groups on graphene oxide (GO) *via* amide bonds. The introduction of diamines was confirmed by analytical methods such as FT-IR, TG-DTA, XPS, AFM, and optical microscopy. Then, we applied DDS-GO and HMDA-GO as co-curing agents for epoxy (EP) nanocomposites that were prepared by mixing bisphenol-A type EP and DDS curing agent (*ca.* 21 wt%). Interestingly, when 1.0 wt% of DDS-GO was added to the EP/DDS mixture, crosslink density (CD) increased from 0.028 to 0.069 mol/cm³. Due to the higher CD, both glass transition temperature and tensile strength of the EP/DDS/DDS-GO nanocomposite effectively improved from 160.7 °C for EP to 183.4 °C and from 87.4 MPa for EP to 110.3 MPa, respectively.

Introduction

Epoxy resin (EP), the most common thermosetting resin, forms a three-dimensional cross-linked network structure when subjected to exothermic curing. Epoxy resin has been used in various industrial applications because of its good adhesion, chemical resistance, thermal resistance, and mechanical properties. However, despite its good properties, there has been a persistent demand for more functional EP that can be used in potential applications such as in automotive, aerospace, construction, and electronic industries. For example, various structure-modified EPs such as novolac¹, phenoxy², crystalline³, and rubber-modified EPs⁴ have been developed. Another attempt to improve the properties of cured EP has been to change curing agents and/or co-curing agents, which dramatically affect the thermal and mechanical properties of cured EP.

The use of carbon nanomaterials like carbon black⁵, carbon nanotube^{6–7}, carbon nanofiber⁸, and graphene^{9–12} as fillers to prepare EP nanocomposites has been attracting attention owing to their unique properties. In addition to these nanomaterials, graphene oxide (GO) has been considered a promising nanomaterial for the improvement of the mechanical and

thermal properties of polymer nanocomposites such as poly(methyl methacrylate), polystyrene, polyurethane, and poly(vinylidene fluoride) nanocomposites^{13–14}. Various neat and functionalized GOs have also been adapted for enhancing the glass transition temperature (T_g) and/or mechanical strength of EP nanocomposites^{15–20}. The crosslink density (CD) is generally recognized as a critical factor influencing the thermal^{21–22} and mechanical^{23–24} properties of EP nanocomposites. If the interfacial strength between the GO and EP is low, the CD of nanocomposites will be low, and because of the low CD value, improvements in the thermal and mechanical properties of EP nanocomposites can be not sufficient and, in some cases, these properties can worsen. In order to improve the interfacial strength between GO and EP, some studies focused on the preparation of functionalized GOs with epoxide terminal groups^{15–17} and with amine terminal groups^{18–20}. In these studies, slight improvements in the T_g and tensile strength of cured EP nanocomposites compared to those of neat cured EPs were realized. Further, it has been mentioned that incorporation of nanomaterials into EP could slightly increase the CD of EP nanocomposites^{25–30}, but there have been few studies that calculated the CD of EP nanocomposites, made an effort to increase the CD of EP nanocomposite, and discussed an effect of the nanomaterials on the CD of EP nanocomposite.

In this work, we report a novel technique to improve the CD of GO-incorporated EP nanocomposites. We synthesized two diamine-functionalized GO—DDS-GO, HMDA-GO—by introducing 4,4'-diaminodiphenyl sulfone (DDS) or hexamethylenediamine (HMDA) into the carboxylic acid groups on GO *via* amide bonds. We prepared two kinds of mixtures, EP/DDS/DDS-GO and EP/DDS/HMDA-GO, by

^a Carbon Composite Materials Research Center, Institute of Advanced Composites Materials, Korea Institute of Science and Technology (KIST), Chudong-ro 92, Bondong-eup, Wanju-gun, Jeollabuk-do, 565-905, Korea. E-mail: goh@kist.re.kr; Tel: +82 63 2198141

^b Department of Carbon Materials, Chosun University, Gwangju, 561-756, Korea.

† Electronic Supplementary Information (ESI) available: Results of FT-IR spectra, TD-TGA curves, XPS spectra, DSC curves, DMA analysis, and UTM analysis of EP nanocomposites were provided. See DOI: 10.1039/x0xx00000x

‡ These authors contributed equally.

adding each diamine-functionalized GO as the co-curing agent into the mixture of diglycidyl ether of bisphenol-A (DGEBA)-type EP and 4,4'-diaminodiphenyl sulfone (DDS) curing agent (ca. 21 wt%). By increasing the amounts of DDS-GO from 0 to 1 wt%, the CD of EP/DDS/DDS-GO nanocomposite increased, and thus, we could effectively increase the T_g and tensile strength of EP nanocomposite.

Experimental

Materials

Graphite powder (average particle size < 30 μm), potassium permanganate (KMnO_4), hexamethylenediamine (HMDA), and N,N' -dicyclohexylcarbodiimide (DCC) were purchased from Sigma-Aldrich Co. (USA). Sulfuric acid (H_2SO_4 ; 98%), hydrogen peroxide (H_2O_2 ; 30% in water), hydrochloric acid (HCl ; 35% in water), and dichloromethane (DCM; 99.5%) were purchased by Daejung Chemical Co. (Korea). 4,4'-diaminodiphenyl sulfone (DDS) and 4-dimethylaminopyridine (DMAP) were obtained from TCI Co. (Japan). Diglycidyl ether of bisphenol-A (DGEBA)-type EP resin (YD-128) was purchased from Kukdo Chemical Co. (Korea).

General procedure for synthesis of graphene oxide (GO)

GO was synthesized using the modified Hummer's method³¹. A round-bottom flask containing 98% H_2SO_4 (80 mL) was chilled to 0 $^\circ\text{C}$. Graphite powder (2 g) was added into the flask and stirred until mixed. KMnO_4 (10 g) was slowly added to the chilled graphite solution, and the resulting mixture was kept at 0 $^\circ\text{C}$. The mixture was then taken from the ice bath and stirred at 35 $^\circ\text{C}$ for 6 h. Deionized water (DI-water, 0.5 L) was slowly added, and the mixture was further stirred for 2 h. Subsequently, additional DI-water (1.5 L) was added followed by dropwise addition of 30% H_2O_2 (30 mL). The mixture was left undisturbed for 3 days for the precipitation to complete. The clear supernatant was decanted. The precipitate was repeatedly washed with DI-water followed by centrifugation with 20 ml of HCl solution (1 N), at least five times to remove residual metal oxides. The resulting GO dispersion was subjected to ultrasonication for 30 min, with occasional agitation at

regular intervals of 10 min) for monolayer exfoliation. Dialysis was performed with a sealed membrane tube (Spectra/Por 1 Dialysis Tubing, MWCO 6-8,000) in DI-water with constant stirring for 7 days. The DI-water was continuously exchanged every 3 h. After dialysis, the clear supernatant was removed by centrifugation at 10000 rpm for 30 min. After freeze-drying, deep-brown GO powder was obtained.

General procedure for synthesis of diamine-functionalized GO (diamine-GO)

A schematic representation of this process is shown in Fig. 1. All experiments were performed in an argon atmosphere. DCM was distilled prior to use. GO (0.1 g) and the diamine derivative (0.1 g) was added to DCM (200 mL) in a 500 mL flask, followed by ultrasonication for 60 min. After that, DCC and DMAP were added into the flask and ultrasonication was performed for 60 min. The number of moles of DCC and DMAP were the same as that of the diamine derivative. The reaction mixture was taken from the ultrasonicator and stirred at room temperature for 24 h. After the reaction, the mixture was washed with DCM, DI-water, and acetone, and filtered to remove excess diamine. The product was finally dried at 60 $^\circ\text{C}$ in vacuum for 24 h.

General procedure for fabrication of epoxy nanocomposite

We calculated the approximately stoichiometric quantities of curing agent required for realizing optimum properties. The EP resin used in this study (DGEBA-type) has an epoxide equivalent weight (EEW) of about 185 g/eq. The viscosity is about 12,000 cP at 25 $^\circ\text{C}$. The curing agent used in this study, DDS, has an amine hydrogen equivalent weight (AHEW) of 62 g/eq. Stoichiometric amounts of the EP resin (E) and curing agent (C) were calculated according to the following formula because one N-H group reacts with one epoxide group.

$$E = \frac{AHEW \times C}{EEW} \quad (1)$$

For example, the stoichiometric amount of DDS for 100 g of YD-

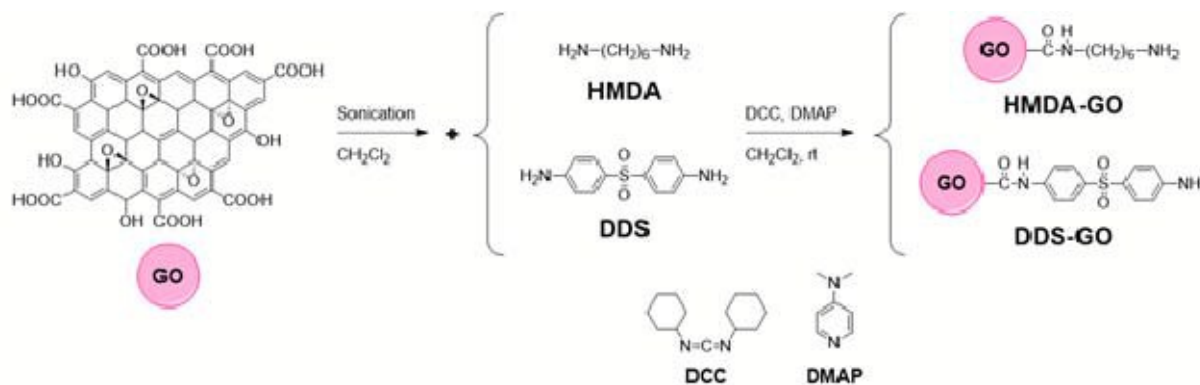


Fig. 1 Synthetic routes for diamine-GO derivatives

128 was calculated to be 33 g. When diamine-GO was added in the nanocomposite, the mixing amount of curing agent reduced to 80% of the stoichiometric amount of DDS, because the amine groups on DDS-GO could also react with epoxide groups as a curing agent. The content of diamine-GO was calculated based on the entire amount of the EP resin and curing agent. EP/DDS/diamine-GO nanocomposites were prepared with different weight fractions of the diamine-GO (0.1 wt%, 0.5 wt%, and 1 wt%). More details on the mixing ratios for obtaining EP nanocomposites are shown in Supplementary Information (Table S1). The fabrication procedure for EP nanocomposites is as follows. Stoichiometric amounts of diamine-GO and EP resin were mixed using a planetary mixer with mixing speed of 2000 rpm for 10 min. After adding stoichiometric amount of DDS to the mixture of EP/amine-GO, the mixture was further mixed by stirring at 155 °C for 20 min. Then, the mixture was placed in vacuum to remove trapped air bubbles and poured into a mold, followed by pre-curing it in an oven at 170 °C for 4 h and curing at 230 °C for 2 h.

Material characterization

The structural divergence of the GO and diamine-GO were confirmed by Fourier-transformation infrared spectroscopy (FT-IR; Nicolet iS 10, Thermo Scientific, USA). Thermogravimetric differential thermal analysis (TG-DTA) of the GO and diamine-GO were carried out with TA Q50 (TA Instrument, USA) under nitrogen gas flow at a heating rate of 10 °C per minute. X-ray photoelectron microscopy (XPS; AXIS-NOVA, Kratos Inc., USA) was employed to discern chemical changes on the surface of GO and diamine-GO. Al K α (1485.6 eV) was used as the X-ray source at 14.9 keV anode voltage. 4.6 A and 20 mA were applied as the filament current and mission current, respectively. Atomic force microscopy (AFM; Veeco-Digital Instruments, USA) images of the GO and diamine-GO were recorded to study morphologies. Optical microscopy (OM; Eclipse Ni, Nikon Inc, Japan) images of the GO and diamine-GO were used to evaluate the dispersion stability of DDS-GO in the EP

nanocomposites. To investigate the thermal properties of EP nanocomposites, a differential scanning calorimeter (DSC; Q20, TA Instrument, USA) and a dynamic mechanical analyzer (DMA; Q800, TA Instrument, USA) were used. The DSC scanning temperature range was from 25 to 350 °C under nitrogen gas flow with a heating rate of 10 °C per minute. The DMA scanning temperature range was from 30 to 260 °C with a scanning rate of 3 °C/min. The mechanical properties of nanocomposites were measured by using a universal testing machine (UTM; Instron, USA). The samples for UTM measurement were prepared with 1.5 mm thickness, 0.5 cm width, and 2.5 cm length, and the tensile strength test was performed at a testing speed of 5 mm/min.

Result and discussion

The carboxylic acid groups on GO and the amine groups were connected *via* amide covalent groups formed by the Steglich reaction.³² Steglich esterification is the most common reaction for condensation of carboxylic acid and alcohol groups to form an ester group, and it is also very powerful to form an amide group from a carboxylic acid group and an amine group, which is more nucleophilic than the alcohol group. Successful condensation was confirmed by the appearance of amide groups determined *via* several analyses, as presented in Fig. 2.

FT-IR analysis is an important technique to study the structural change in diamine-GO. Representative FT-IR spectra of DDS-GO are presented in Fig. 2a to provide the proof of the successful synthesis of DDS-GO. FT-IR spectra of HMDA-GO are in Supplementary Information (Fig. S1). There are three characteristic absorption bands in the FT-IR spectra of DDS-GO. First, an absorption band at 3450 cm⁻¹ attributed to the O-H stretching vibration derived from O-H groups on GO.³³ This absorption band was quite broad, because the absorption band at about 3350 cm⁻¹ assigned to N-H vibration of the amine group on DDS³⁴ combined with the O-H stretching vibration

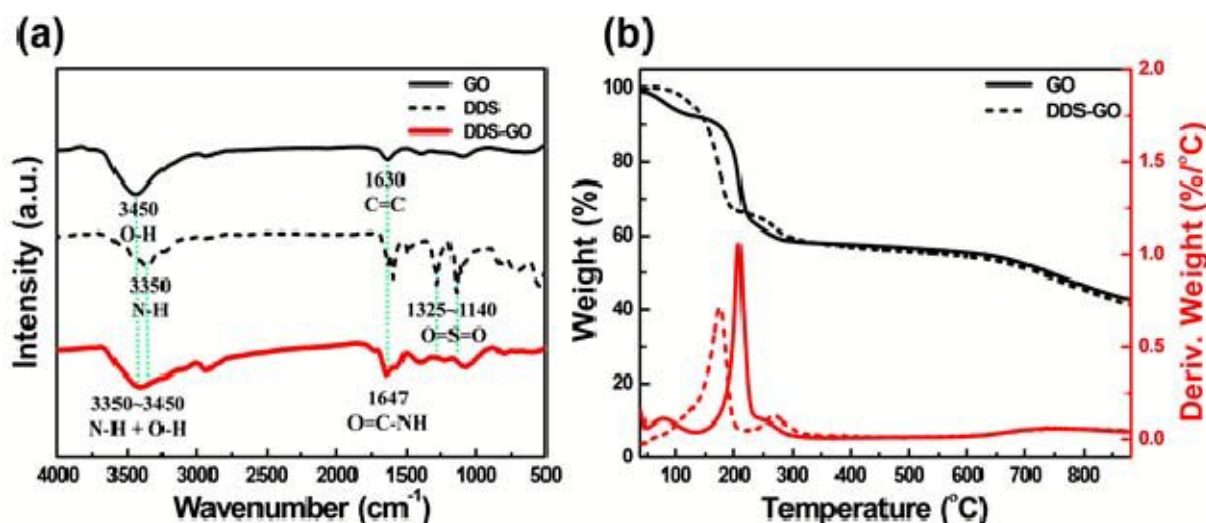


Fig. 2 (a) FT-IR spectra of GO, DDS, and DDS-GO. (b) TG-DTA curves of GO and DDS-GO during heating up to 900 °C in a N₂ atmosphere.

band of GO. Absorption bands corresponding to C=C skeletal vibration at 1630 cm^{-1} and C=O stretching vibration in the spectra of GO³³ and absorption bands of sulfone O=S=O stretching vibration at $1140\text{--}1325\text{ cm}^{-1}$ in the spectrum of DDS³⁴ also appeared in the FT-IR spectrum of DDS-GO. Meanwhile, a strong absorption band newly appeared at 1647 cm^{-1} in the spectrum of DDS-GO. We assigned it to the stretching vibration of the amide group created by condensation of the carboxylic acid group at the GO edge with the amine group of DDS.¹⁹ These FT-IR analysis results are strong evidences of GO functionalization with the diamine derivatives.

Fig. 2b shows the TG-DTA curves of GO and DDS-GO under a N_2 atmosphere (for the curves of HMDA-GO, see Fig. S2 in the Supplementary Information). In the TG-DTA curve of GO, the small weight loss peak at $80\text{ }^\circ\text{C}$ was due to the loss of residual water in GO, and the main weight loss peak that appeared around $210\text{ }^\circ\text{C}$ is assigned to the pyrolysis of the labile oxygen functional groups, yielding CO, CO_2 , and steam^{35–36}. On the other hand, we could observe two different major loss peaks from the TG-DTA curve of DDS-GO. The peak near $160\text{ }^\circ\text{C}$ could be ascribed to the loss of the remaining oxygen functional groups on GO, which slightly shifted to a temperature lower than that of non-functionalized GO. The peak around $270\text{ }^\circ\text{C}$ corresponds to the decomposition of DDS.³⁴ From the decomposed weight, we calculated the substituted amount of DDS in DDS-GO as 7 wt%. With this method, the substituted amount of HMDA in HMDA-GO was also evaluated as 7 wt%. These results of TG-DTA analysis also indicate that diamine derivatives were successfully introduced to GOs.

Further investigation by XPS analysis was performed to characterize diamine-GOs, and the resulting deconvoluted XPS C1s spectra of GO and DDS-GO are shown in Fig. 3 (for the spectra of HMDA-GO, see Fig. S3 in the Supplementary Information). In Fig. 3a, five characteristic peaks were

observed at 284.4, 285.2, 286.3, 287.0, and 290.7 eV, which correspond to C-C, C-OH, C-O-C, C=O, and C(=O)-O, respectively. Further, an additional peak at 288.4 eV was observed in Fig. 3b, and it could be assigned to O=C-NH moieties.³⁷ Integrated areas of the peaks corresponding to each chemical bond are listed in Table S2. From the existences of the O=C-NH peak in the XPS results, we found that amide groups were newly formed in the functionalized GO.

Thus, the results of FT-IR, TG-DTA, and XPS analyses confirmed that diamine derivatives were successfully introduced to GOs *via* amide chemical bonds.

AFM analysis was employed to study morphologies of GO and diamine-GOs, and their images are in Fig. 4. From these images, the presence of the nanolayer-type GO is clearly observed. The width and thickness of GO and diamine-GO were determined by the analysis results. The image of GO showed 2.0 nm of average thickness and 300–1100 nm width range. Further, images of DDS-GO and HMDA-GO revealed an average thickness of 1.0 nm and a width ranging from 100–500 nm. It is considered that the additional ultrasonication process in the case of the functionalized GO would shatter the GO into smaller pieces.

Good dispersion of nanomaterials greatly influences and improves the properties of the EP nanocomposites. Therefore, in order to investigate the dispersion state, EP/DDS/DDS-GO nanocomposites were observed by optical microscopy. The results are shown in the Fig. 5, and they indicated that the DDS-GO dispersion in the EP nanocomposites was very homogeneous when the concentration was increased to 1.0 wt%. The presence of many polar moieties such as carboxylic acid, amide, and amine groups was thought to facilitate the dispersion of DDS-GO in the EP nanocomposite because they actively interact with EP *via* hydrogen or covalent bonding.

Addition of nanomaterials into the EP had a significant effect on the resulting thermal properties. As described in the

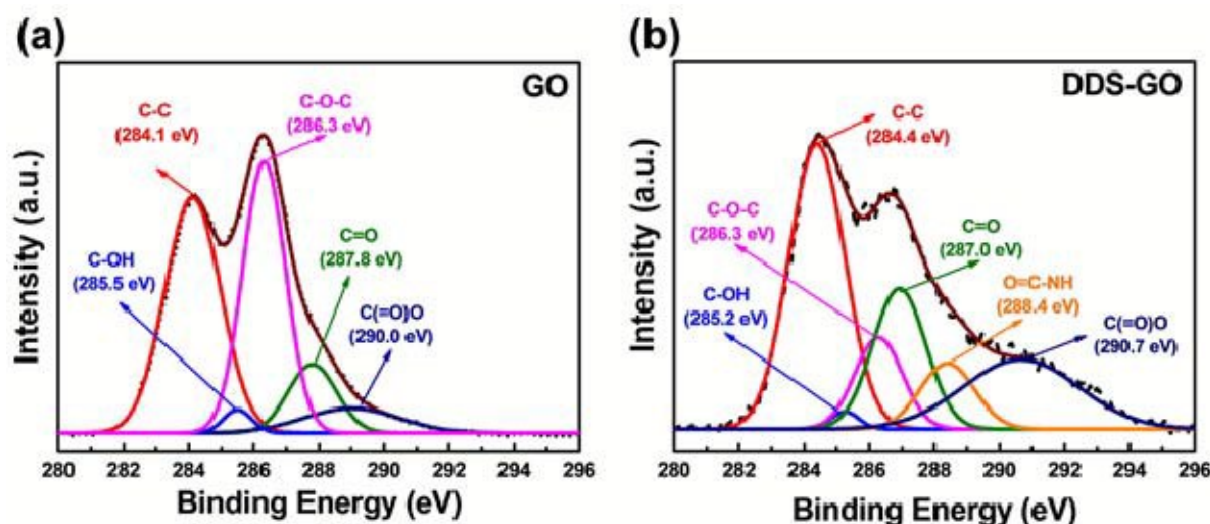


Fig. 3 XPS C1s spectra of (a) GO and (b) DDS-GO. Deconvoluted curves represent the theoretical XPS spectra for different chemical bonds.

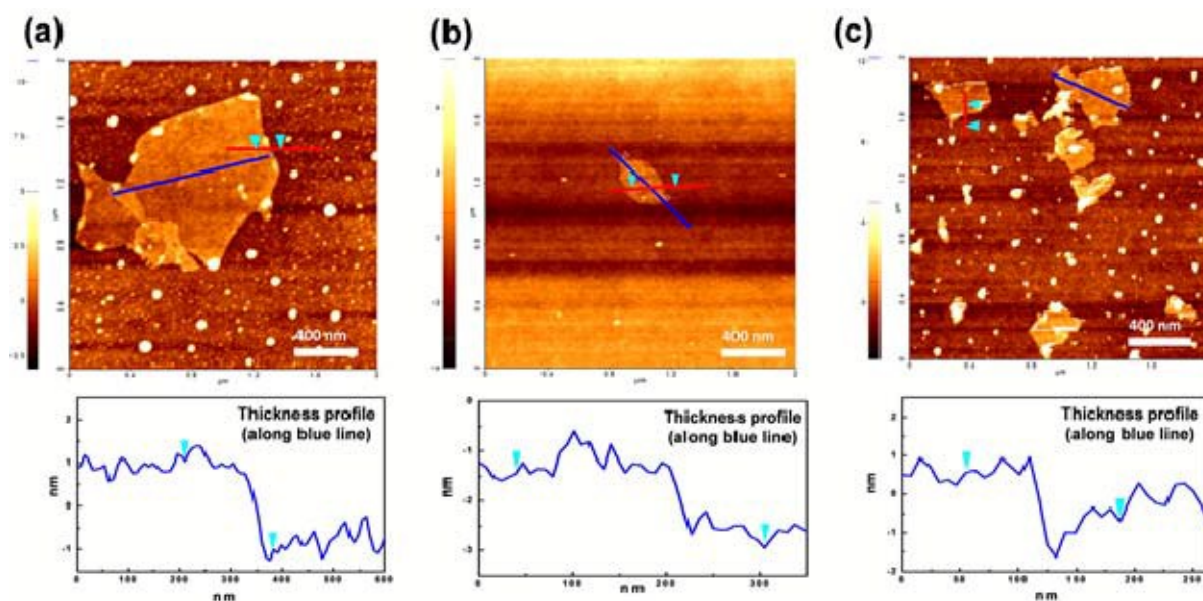


Fig. 4 AFM images of (a) GO, (b) DDS-GO, and (c) HMDA-GO.

Experimental section, diamine-GOs were used as co-curing agents of EP nanocomposites and their amount was controlled from 0.0 to 1.5 wt%. Curing temperatures were estimated from the temperatures of exothermic peaks in the first heating DSC curves of the EP/DDS/GO and EP/DDS/diamine-GO mixtures (for the DSC curves, see Fig. S4-6 in the Supplementary Information), and are presented in Table S3. T_g of the cured EP/DDS/GO and EP/DDS/diamine-GO nanocomposites were determined based on endothermic peaks of their second heating DSC curves (Fig. 6, Table S4) (for the DSC curves, see Fig. S7-9 in the Supplementary Information). When the GO was added to 1.0 wt% to the EP/DDS, the T_g of the EP/DDS/DDS-GO nanocomposite decreased from 160.7 to 136.8 °C. It has been reported that the non-functionalized GOs decrease T_g of EP nanocomposites because of the tendency of GO to agglomerate in the polymer matrix and disturb polymer heat flow, but this tendency has not been investigated sufficiently.³⁸ In contrast, when 1.0 wt% of HMDA-GO or DDS-GO was added to the mixture of EP/DDS, the T_g of EP/DDS/diamine-GO nanocomposites remarkably increased to

170.5 or 183.4 °C, respectively; these high values of obtained by adding HMDA-GO or DDS-GO are 125 and 135% of those for EP/DDS/GO nanocomposite, respectively. This is because the amine moieties functionalized on GO could improve the interfacial affinity by reacting with the epoxide groups of the EP resin. Subsequently, the disturbance of the interface between GO and EP could be reduced. If terminal amine groups on GO react with the epoxide groups of EP, diamine-GO could participate in the formation of a polymer crosslink network like curing agent, and EP/DDS/diamine-GO nanocomposites would show higher CD than the EP/DDS/GO nanocomposite. Further, it is known that the CD of EP nanocomposites is closely related to their thermal properties.²¹⁻²²

DMA measurements of EP/DDS/GO nanocomposites and EP/DDS/DDS-GO nanocomposites were performed to estimate the CD of EP nanocomposites. Storage modulus and $\tan\delta$ of EP/DDS/DDS-GO nanocomposites are shown in Fig. 7a-b (for the DMA results of the EP/DDS/GO nanocomposite, see Fig. S10 in the Supplementary Information). Based on the storage modulus and $\tan\delta$ in the rubber region, CD of EP

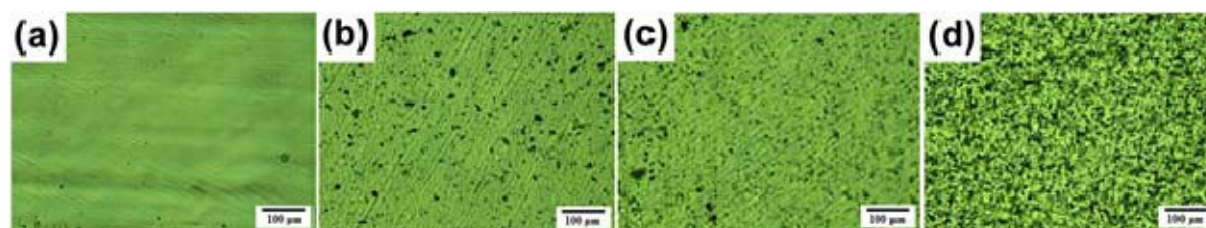


Fig. 5 Optical microscope photographs of EP/DDS/DDS-GO nanocomposites as a function of weight percentage of DDS-GO. (a), (b), (c), and (d) correspond to 0, 0.1, 0.5, and 1.0 wt% of DDS-GO into the mixture of EP/DDS, respectively.

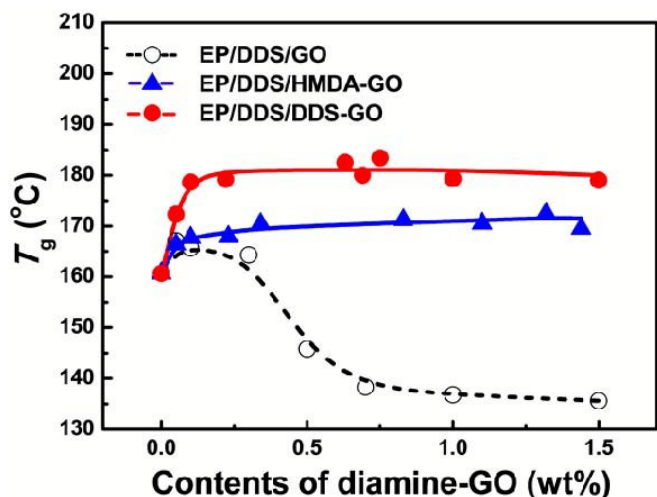


Fig. 6 Glass transition temperatures (T_g) of EP/DDS/diamine-GO nanocomposites. T_g was estimated from the second heating DSC results of EP/DDS/diamine-GO mixture..

nanocomposites were calculated according to the following formula:³⁰

$$(2)$$

where ρ is the CD in mol/cm^3 , G' is the shear modulus calculated from the storage modulus measured in the rubbery region of EP nanocomposites, R is a universal gas constant ($8.314472 \text{ J}/\text{K}\cdot\text{mol}$), and T is the absolute temperature at which G' was determined. The results of calculated crosslink densities are shown in Fig. 7c and Table S5. The CD of EP/DDS/GO and EP/DDS/HMDA-GO nanocomposites did not change much from that of neat EP. However, the CD of EP/DDS/DDS-GO nanocomposite showed significant enhancement as the contents of DDS-GO increased. In particular, when 1.0 wt% of DDS-GO was incorporated, the CD of EP/DDS/DDS-GO nanocomposites was $0.069 \text{ mol}/\text{cm}^3$, and this is 240% of the CD of cured EP ($0.028 \text{ mol}/\text{cm}^3$). Amine terminal groups

attached to the DDS-GO could react with the epoxide groups of the EP and construct the crosslink network through covalent bonds on the interface between GO and EP. Therefore, the CD of EP/DDS/DDS-GO nanocomposite became higher than that of the EP/DDS/GO nanocomposite, and the former showed superior thermal properties.

It has been also known that CD is not only related to the thermal properties of EP nanocomposite, but also related to the mechanical properties.^{23–24} In order to investigate the effect of CD on the mechanical properties of EP nanocomposite, the tensile strength of EP/DDS/diamine-GO nanocomposites was evaluated by UTM analysis; an analysis result is shown in Fig. 8 (for all results of UTM analysis, see Figures S11–13 in the Supplementary Information). Similar to the T_g , the tensile strength of EP/DDS/DDS-GO nanocomposite was higher (110.3 MPa) than those of neat EP (87.4 MPa) and the EP/DDS/GO nanocomposite (74.3 MPa) when 0.1 wt% of DDS-GO or GO was added. When 0.1 wt% of HMDA-GO was added, the EP/DDS/HMDA-GO nanocomposite also showed the higher tensile strength (90.4 MPa) compared to those of neat EP and the EP/DDS/GO nanocomposite, but the tensile strength is relatively smaller than that of EP/DDS/DDS-GO nanocomposite (110.3 MPa) with 0.1 wt% of DDS-GO. In the EP/DDS/diamine-GO nanocomposites, diamine-GOs could have strong interactions with EP through covalent bonds between diamine-GOs and EP, and this is considered to be the reason for the improvement in the tensile strength of the EP/DDS/diamine-GO nanocomposite.

Meanwhile, both EP/DDS/HMDA-GO and EP/DDS/DDS-GO nanocomposites showed higher T_g and tensile strength values than the EP/DDS/GO nanocomposite, but the EP/DDS/DDS-GO nanocomposite exhibited superior properties to the EP/DDS/HMDA-GO nanocomposite. We thought that this result was due to the structural difference between HMDA, which has a flexible aliphatic structure, and DDS, which has a rigid aromatic sulfone structure. In the case of HMDA-GO, terminal amine groups are connected with GO through a flexible alkyl chains, and these may affect the lower T_g and tensile strength of EP/DDS/HMDA-GO nanocomposite than

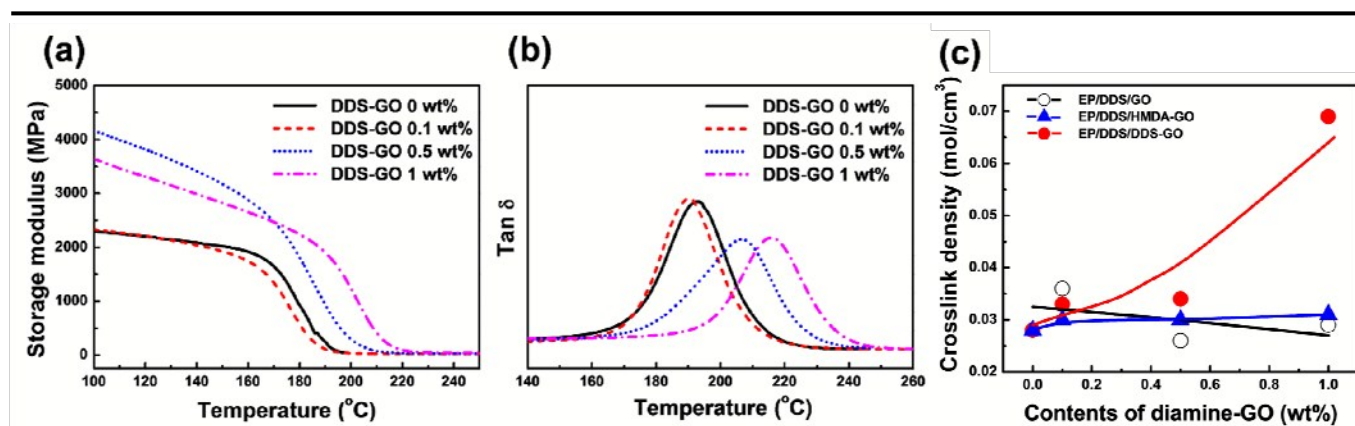


Fig. 7 DMA results of EP/DDS/diamine-GO nanocomposites. (a) Storage modulus, (b) $\tan\delta$, and (c) crosslink density of the EP/DDS/diamine-GO nanocomposites. Samples were tested in a temperature range of 30 to 260 °C at a scanning rate of 3 °C/min. The crosslink density was calculated using storage modulus and $\tan\delta$ in the rubbery region of EP/DDS/diamine-GO nanocomposites.

Fig. 8 Tensile strengths of EP/DDS/diamine-GO nanocomposites. It was estimated by using a universal testing machine. Samples for measurement were prepared with 1.5 mm × 50 mm × 250 mm size, and tests were performed with a testing speed of 5 mm/min.

those of EP/DDS/DDS-GO nanocomposite. In addition, terminal amine groups with different nucleophilicity exist. These terminal amine groups act as curing sites and are considered to be major factors that affect the thermal and mechanical properties of EP nanocomposites. HMDA has electron-rich aliphatic amine groups which can make the curing temperature of HMDA-GO lower than that of the main curing agent DDS. Consequently, a spatially heterogeneous curing reaction will take place in the nanocomposite, and this could negatively affect the thermal properties of EP/DDS/HMDA-GO. In contrast, DDS-GO starts to participate in curing at a similar temperature as DDS. Therefore, the curing reaction would occur more homogeneously in the EP/DDS/DDS-GO nanocomposite, and the thermal properties would be better. This hypothesis about the difference between HMDA-GO and DDS-GO was supported by the CD of EP/DDS/HMDA-GO, which was much lower than that of EP/DDS/DDS-GO. Moreover, the EP/DDS/DDS-GO nanocomposite showed increasing CD when the more DDS-GO was added, while the CD of EP/DDS/HMDA-GO nanocomposite did not change much despite the high contents of HMDA-GO.

Conclusions

We successfully prepared diamine-functionalized graphene oxides (diamine-GOs), by introducing diamine derivatives at GO edge. The formation of amide groups was confirmed by several analyses such as FT-IR, TG-DTA, and XPS. EP nanocomposites obtained using diamine-GOs as co-curing agents of commercially available EP showed significantly improved thermal and mechanical properties compared to those of neat EP. In particular, 4,4'-diaminodiphenyl sulfone-functionalized GO (DDS-GO) was the most effective additive: 0.1 wt% content of DDS-GO enhanced the T_g of EP/DDS/DDS-

GO nanocomposite from 160.7 °C for EP to 183.4 °C and the tensile strength from 87.4 MPa for EP to 110.3 MPa. The improvement in properties was considered to be due to the good dispersion of DDS-GO in the EP/DDS/DDS-GO nanocomposite and the increase in the crosslink density (CD) of the EP/DDS/DDS-GO nanocomposite. Thus, we can improve the CD value of EP/DDS from 0.028 to 0.069 mol/cm³ by adding 1.0 wt% of DDS-GO. Higher CD value was achieved for EP/DDS/DDS-GO because DDS-GO has terminal amine groups that tend to participate in the formation of crosslink network *via* direct covalent bonding with epoxide groups of EP. It is expected that the high-performance EP nanocomposite could be prepared by improving the CD of EP nanocomposites, and the method in this study could provide great potential to future industrial applications.

Acknowledgements


This work was supported by a grant from the Korea Institute of Science and Technology (KIST) Institutional program (2Z04480). This work was also supported by the Ministry of Trade, Industry and Energy (MOTIE) and Korea Institute for Advancement of Technology (KIAT) through the Research and Development for Regional Industry (R0004423).

References

- 1 A. M. Atta, N. O. Shaker, N. E. Nasser, *J. Appl. Polym. Sci.*, **2008**, *107*, 347.
- 2 V. Dixit, A. K. Nagpal, R. Singhal, *Int. J. Plast. Technol.*, **2010**, *14*, 38.
- 3 T. Song, Z. Li, J. Liu, S. Yang, *Polym. Sci. Ser. B*, **2013**, *55*, 147.
- 4 B. J. P. Jansen, K. Y. Tamminga, H. E. H. Meijer, P. J. Lemstra, *Polymer*, **1999**, *40*, 5601.
- 5 T. V. Kosmidou, A. S. Vatalis, C. G. Delides, E. Logakis, P. Pissis, G. C. Papanicolaou, *EXPRESS Polym. Lett.*, **2008**, *2*, 364.
- 6 M. Abdalla, D. Dean, M. Theodore, J. Fielding, E. Nyairo, G. Price, *Polymer*, **2010**, *51*, 1614.
- 7 M. M. Rahman, S. Zainuddin, M. V. Hosur, C. J. Robertson, A. Kumar, J. Trovillion, S. Jeelani, *Compos. Struct.*, **2013**, *95*, 213.
- 8 J. Zhu, S. Wei, J. Ryu, M. Budhathoki, G. Liang, Z. Guo, *J. Mater. Chem.*, **2010**, *20*, 4937.
- 9 L. Tang, Y. Wan, D. Yan, Y. Pei, L. Zhao, Y. Li, L. Wu, J. Jiang, G. Lai, *Carbon*, **2013**, *60*, 16.
- 10 J. A. King, D. R. Klimek, I. Miskioglu, G. M. Odegard, *J. Appl. Polym. Sci.*, **2013**, *128*, 4217.
- 11 A. S. Wajid, H. S. T. Ahmed, S. Das, F. Irin, A. F. Jankowski, M. J. Green, *Macromol. Mater. Eng.*, **2013**, *298*, 339.
- 12 Q. Li, Y. Guo, W. Li, S. Qiu, C. Zhu, X. Wei, M. Chen, C. Liu, S. Liao, Y. Gong, A. K. Mishra, L. Liu, *Chem. Mater.*, **2014**, *26*, 4459.
- 13 T. Ramanathan, A. A. Abdala, S. Stankovich, D. A. Dikin, M. Herrera-Alonso, R. D. Piner, D. H. Adamson, H. C. Schniepp,

- X. Chen, R. S. Ruoff, S. T. Nguyen, I. A. Aksay, R. K. Prud'homme, L. C. Brinson, *Nat. Nanotechnol.*, **2008**, *3*, 327.
- 14 T. Kuilla, S. Bhadra, D. Yao, N. H. Kim, S. Bose, J. H. Lee, *Prog. Polym. Sci.*, **2010**, *35*, 1350-1375.
- 15 C. Bao, Y. Guo, L. Song, Y. Kan, X. Qian, Y. Hu, *J. Mater. Chem.*, **2011**, *21*, 13290.
- 16 B. Qi, S. R. Lu, X. E. Xiao, L. L. Pan, F. Z. Tan, J. H. Yu, *eXPRESS Polym. Lett.*, **2014**, *8*, 467.
- 17 B. Qi, Z. Yuan, S. Lu, K. Liu, S. Li, L. Yang, J. Yu, *Fiber. Polym.*, **2014**, *15*, 326.
- 18 M. M. Gudarzi, F. Sharif, *eXPRESS Polym. Lett.*, **2012**, *6*, 1017.
- 19 T. Liu, Z. Zhao, W. W. Tjiu, J. Lv, C. Wei, *J. Appl. Polym. Sci.*, **2014**, *131*, 40236.
- 20 L. Guan, Y. Wan, L. Gong, D. Yan, L. Tang, L. Wu, J. Jiang, G. Lai, *J. Mater. Chem. A*, **2014**, *2*, 15058.
- 21 T. Iijima, N. Yoshioka, M. Tomoi, *Eur. Polym. J.*, **1992**, *28*, 573.
- 22 K. W. Putz, M. J. Palmeri, R. B. Cohn, R. Andrews, L. C. Brinson, *Macromolecules*, **2008**, *41*, 6752.
- 23 K. Kim, I. Jeon, S. Ahn, Y. Kwon, J. Baek, *J. Mater. Chem.*, **2011**, *21*, 7337.
- 24 K. Wei, G. Zhu, Y. Tang, T. Liu, J. Xie, *J. Mater. Res.*, **2013**, *28*, 2903.
- 25 V. Patil, R. V. Dennis, T. K. Rout, S. Banerjee, G. D. Yadav, *RSC Adv.*, **2014**, *4*, 49264.
- 26 G. Z. Li, L. Wang, H. Toghiani, T. L. Daulton, K. Koyama, C. U. Pittman, *Macromolecules*, **2001**, *34*, 8686.
- 27 J. Park, S. C. Jana, *Macromolecules*, **2003**, *36*, 8391.
- 28 W. Naous, X. Yu, Q. Zhang, K. Naito, Y. Kagawa, *J. Polym. Sci. Polym. Phys.*, **2006**, *44*, 1466.
- 29 M. S. Lakshmi, B. Narmadha, B. S. R. Reddy, *Polym. Degrad. Stab.*, **2008**, *93*, 201.
- 30 C. Lee, J. Park, *Trans. Electr. Electron. Mater.*, **2010**, *11*, 69.
- 31 W. S. Hummers, R. E. Offeman, *J. Am. Chem. Soc.*, **1958**, *80*, 1339.
- 32 B. Neises, W. Steglich, *Angew. Chem. Int. Ed. Eng.*, **1978**, *17*, 522.
- 33 L. Shahriary, A. A. Athawale, *Int. J. Renew. Energy Environ. Eng.*, **2014**, *2*, 58.
- 34 L. Jiang, Y. Huang, Q. Zhang, H. He, Y. Xu, X. Mei, *Cryst. Growth Des.*, **2014**, *14*, 4562.
- 35 S. Stankovich, D. A. Dikin, R. D. Piner, K. A. Kohlhaas, A. Kleinhammes, Y. Jia, Y. Wu, S. T. Nguyen, R. S. Ruoff, *Carbon*, **2007**, *45*, 1558.
- 36 X. Du, Z. Yu, A. Dasari, J. Ma, M. Mo, Y. Meng, Y. Mai, *Chem. Mater.*, **2008**, *20*, 2066.
- 37 Y. Chen, X. Zhang, P. Yu, Y. Ma, *Chem. Commun.*, **2009**, 4527.
- 38 N. Norhakim, S. H. Ahmad, C. H. Chia, N. M. Huang, *Sains Malays.*, **2014**, *43*, 603.

Table of Contents Graphic

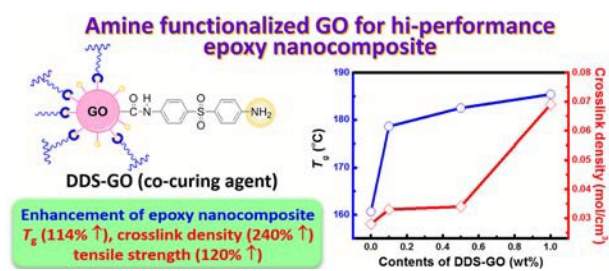

Epoxy nanocomposite are fabricated by using diamine-functionalized GO and exhibit high T_g , tensile strength, and crosslink density.