

Polymer Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Thiophene-fused isoindigo based conjugated polymers for ambipolar organic field-effect transistors

Na Zhao,^{a,c} Na Ai,^b MianCai,^{a,c} Xiao Wang,^a Jian Pei,^b Xiaobo Wan*^a

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/


A series of donor-acceptor (D-A) type of conjugated polymers based on novel thiophene-fused isoindigo (TII) were designed and synthesized via palladium catalyzed Stille copolymerization. We found that the redesign of the synthesis of brominated TII was necessary, and the α -bromination had to be completed at the very beginning, or β -brominated TII was obtained, which only led to cross conjugated polymers. Once the bromination was introduced at the correct position, fully conjugated D-A type polymer could be obtained. A series of fully conjugated polymers were obtained by Stille coupling polymerization of α -brominated TII with different donors, and among them, copolymers with thiophene (T) and (E)-1,2-bis(3-octylthiophen-2-yl)ethene(TVT-8) showed acceptable solubility and were suitable to fabricate solution-processable organic field-effect transistors(OFETs). Top-gate/bottom-contact (TG/BC) devices were constructed for the polymers to test their OFET performances. Both fully conjugated polymers exhibit two-orders higher charge carrier mobilities than the cross conjugated ones, and **PTII-T** shows balanced electron and hole mobility and **PTII-TVT-8** is a *p*-type dominated semiconductor. These observations indicated that the developed TII unit that has improved coplanarity can be a promising building block for the construction of highly efficient conjugated polymers for OFET applications.

Introduction

Organic semiconducting materials have received increasing attentions in recent years because of their promising applications in various areas such as organic field-effect transistors (OFETs), organic light-emitting diodes (OLEDs), organic solar cells (OSCs), and sensors.¹⁻⁵ In the past few years, the need for better performing materials in the organic electronics field has inspired a resurgence of natural dyes and pigments, such as diketopyrrolopyrrole (DPP), naphthalene diimide (NDI) and indigo. Isoindigo is a well-known structural motif for the design of such OFET materials. Its electron-deficient core as well as its off axis dipole moment promotes intermolecular interactions and ambient stability is imparted through the generally low-lying HOMO levels.⁶⁻¹²

The modification of isoindigo core plays an important role in the manipulation of the properties of the resulting materials, since it could alter the HOMO/LUMO energy levels, change the strength of π - π interaction and even decrease the steric hindrance in some cases. The modification of isoindigo core was firstly reported by Ashraf and coworkers, in which the benzene ring in isoindigo was replaced by a thiophene ring. The resultant compound, namely thienoisoindigo (Scheme 1a), was used as a novel building blocks for

polymeric OFETs, and a balanced hole and electron mobilities up to $0.1 \text{ cm}^2 \text{V}^{-1} \text{s}^{-1}$ was reported.¹³ Inspired by this report, we synthesized thiophene-fused isoindigo (as shown in Scheme 1b) and disclosed its photophysical and electrochemical properties, showing that the intramolecular charge transfer was enhanced due to the extension of the π -conjugated system.¹⁴ Further extension of the π -conjugated system (benzothiophene-fused isoindigo and benzofuran-fused isoindigo, Scheme 1c and 1d) led to small molecular OFETs with electron mobility up to $0.074 \text{ cm}^2 \text{V}^{-1} \text{s}^{-1}$ in ambient conditions.¹⁵ More recently, similar modifications on isoindigo core were also reported, (Scheme 1, e ~ g), including thieno[3,2-*b*]thiophene isoindigo¹⁶, benzothienoisoindigo¹⁷, and thieno[3,2-*b*][1]benzothiopheneisoindigo¹⁸. OFET devices fabricated with small molecules and polymers based on these structures all showed promising performances.¹⁶⁻¹⁸ All these progress indicate the great potential of isoindigo core modification in improving OFET properties, which deserves further exploration.

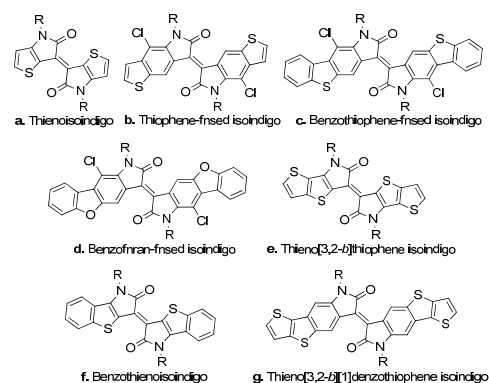

Scheme 1. The reported manipulation on the isoindigo core.

^a CAS Key Laboratory of Bio-based Materials, Qingdao Institute of Bioenergy & Bioprocess Technology, Chinese Academy of Sciences, 189 Songling Road, Qingdao 266101, People's Republic of China. E-mail: wanxb@qibebt.ac.cn

^b College of Chemistry and Molecular Engineering, Peking University, Beijing 100871, People's Republic of China.

^c University of Chinese Academy of Sciences, Beijing 100049, People's Republic of China.

Electronic Supplementary Information (ESI) available. See DOI: 10.1039/x0xx00000x

As our continuous efforts in the design of small molecules and macromolecules based on modified isoindigo core, we herein wish to report the synthesis towards polymers based on thiophene-fused isoindigo building blocks and the investigation of their performance as OFET materials.


Results and discussion

Polymer Synthesis and properties.


Recently, we reported a new way to synthesize TII with linear alkyl chain on nitrogen atom.¹⁴ It is known from the single crystal X-ray diffraction study that in 1,1'-dimethyl-isoindigo, the dihedral angle between the two oxindole rings is around 22.3(2)°,¹⁹ which is destructive for long range conjugation. While for TII, the dihedral angle is close to 0° (see Supplementary Information, Figure S1), which we believe is beneficial to form good intermolecular π - π stacking. Furthermore, we anticipate that when TII is copolymerized with other co-monomers, the steric hindrance between the two building blocks will be further decreased due to the less-hindered terminal thiophene rings on TII. Thus, the corresponding copolymers of TII will show better planarity than that of isoindigo, and lead to better OFET performance.

Bromination of TII was necessary to get the corresponding monomer for Stille coupling polymerization. However, the direct bromination on TII turned out to be rather difficult (Scheme 2): no reaction was observed in THF and chloroform from 0 °C to reflux using *N*-bromosuccinimide (NBS) as the bromination reagent, even when acetic acid was added to promote the reaction. Bromination using liquid bromine under various conditions also failed, yielding inseparable multi-brominated mixtures, presumably due to the similar reaction activities of α - and β - position of the outer thiophene ring, caused by electron delocalization in the whole conjugated structure. We have to change our itinerary to introduce the bromine at the earlier stage.

Thus, the synthetic route was revised, as shown in Scheme 3. 4-Chloro-5*H*-thieno[2,3-*f*]indole-6,7-dione (**1**) was alkylated with 9-(bromomethyl)nonadecane using K₂CO₃, and the reaction proceeded smoothly at 50 °C to give **2** in 71% yield. Due to the electron deficiency of the dione, bromination of **2** only works with liquid bromine in the presence of sodium acetate, giving a mono-brominated compound **3** as a pure single regio-isomer in 70% yield. The dibrominated TII (**4**) was synthesized in 90% yield according to the method reported by Bogdanov.²⁰

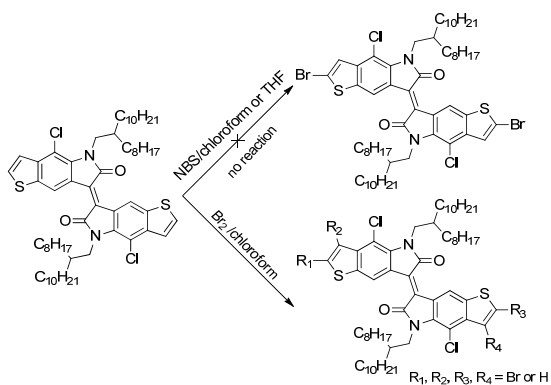

Scheme 2. Attempts for direct bromination on TII.

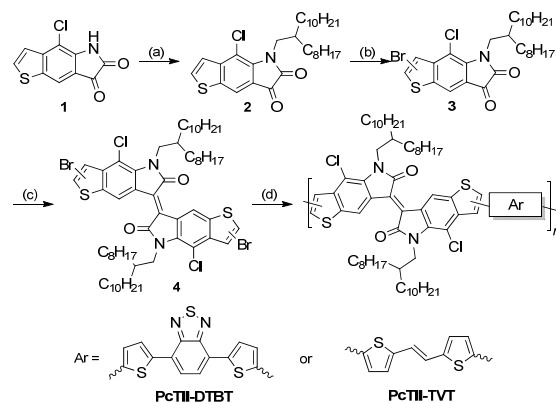


Scheme 3. Original synthetic route of two TII based polymers.^a

^aReagents and conditions: (a) 9-(bromomethyl)nonadecane, K₂CO₃, DMF, 50 °C, 71%; (b) Br₂, AcONa, AcOH, reflux, 2h, 70%; (c) P(NEt₃)₃, CH₂Cl₂, -60 °C, 90%; (d) 4,7-bis(5-(trimethylstannyl)thiophen-2-yl)benzo[*c*][1,2,5]thiadiazole or (*E*)-1,2-bis(5-(trimethylstannyl)thiophen-2-yl)ethane, Pd(PPh₃)₄, toluene, 110 °C, 48h; for PcTII-DTBT, 85%; for PcTII-TVT, 92%.

With the dibrominated TII in hand, Stille-coupling polymerization between **4** and two different monomers, 4,7-bis(5-(trimethylstannyl)thiophen-2-yl)benzo[*c*][1,2,5]thiadiazole (DTBT) or (*E*)-1,2-bis(5-(trimethylstannyl)thiophen-2-yl)ethane (TVT) was tested, giving PcTII-DTBT and PcTII-TVT respectively, in high yields. Both polymers were obtained as dark red metallic solids after careful purification and showed excellent solubility in common organic solvents such as chloroform.

UV-vis absorption spectra of the polymers both in chloroform solution were measured (Figure 1a). To our surprise, compared with TII monomer, the polymers do not show any obvious bathochromic-shifted absorption, which was not in accordance with the literatures about the conjugated polymers of isoindigo.^{7, 13, 21, 22} Reynolds and coworkers have reported two low-energy gap oligothiophenes connected with isoindigo, both of which showed greater red shift in the UV spectra.⁶ To rule out the possible problems that might be involved in Stille coupling, a model compound *c*TII-2T, with two thiophene ring capped at either end of TII, was synthesized in the same way and well characterized (see Experimental for the details). The same result was obtained: *c*TII-2T only has a red-shift of 10 nm to TII, which aroused more questions on the regioselectivity of the dibrominated TII (**4**). Very possibly, the dibromination occurred at β -position of the benzothiophene core, which led to cross conjugation rather than full conjugation.²³ To confirm the position of bromine atom on the thiophene ring, the single crystal of an analogue of compound **3** (alkylated with dodecane chain) was prepared, since the longer branched alkyl chain was detrimental for single crystal growth.

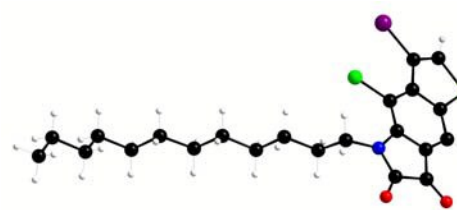


Scheme 4. Single crystal structure of dodecane substituted compound **3**.

The single structure depicted in Scheme 4 clearly showed that the bromine atom was at the β -position of the thiophene ring, validating our presumption of cross conjugation. By examining the literatures in detail, we found out that for benzofused heterocycles such as benzofurans, benzothiophenes, and indoles, treatment of the unsubstituted parent substrate with an electrophilic halogen source typically provides access to β -halogenated substrates.²⁴⁻²⁸ So, to achieve full conjugation, the bromine atom has to be introduced at the α -position at the very beginning, before the formation of benzothiophene core. Thus, the synthetic route was further modified and was shown in Scheme 5. The starting material 2-bromo-5-nitrobenzo[*b*]thiophene (**5**) was synthesized according to the literature.^{29, 30} Following the similar procedure to previously reported ones,¹⁴ α, α' -dibrominated TII (**11**) was synthesized. Polymers based on α -brominated TII were synthesized via Stille-coupling polymerization, with five different co-monomers, denoted as Ar in Scheme 5. The solubility of the resulting polymer is greatly influenced by the structure of the co-monomers: when TII was copolymerized with 2,5-bis(trimethylstannyl)thiophene, a copolymer with excellent solubility in chloroform was obtained (Scheme 5, **PTII-T**); when switched to (*E*)-1,2-bis(3-octyl-5-(trimethylstannyl)thiophen-2-yl)ethene, the solubility of the copolymer **PTII-TVT-8** was acceptable in heated chlorobenzene and *o*-dichlorobenzene; while for 5,5'-bis(trimethylstannyl)-2,2'-bithiophene, 4,7-bis(5-(trimethylstannyl)thiophen-2-yl)benzo[*c*][1,2,5]thiadiazole, and (*E*)-1,2-bis(5-(trimethylstannyl)thiophen-2-yl)ethane, the solubility of the resulting copolymers became very poor in all aromatic solvents, even in heated 1,2,4-trichlorobenzene. Thus, we were unable to fully characterize the properties of **PTII-2T**, **PTII-DTBT**, and **PTII-TVT**. Meanwhile, compared with the cross conjugated polymers we prepared before, these polymers exhibit decreased solubility, which could be explained by the improved rigidity and linearity of the polymer backbone. All the polymers were obtained as dark blue metallic solids after careful purification, presenting a completely different color from cross conjugated polymers due to the longer effective conjugation length and donor-acceptor interactions. Molecular weights of **PTII-T** and **PTII-TVT-8** were evaluated by high-temperature gel permeation chromatography (GPC) with 1,2,4-trichlorobenzene (TCB) as eluent at 150 °C. Both polymers show comparable M_n (**PTII-T**, 26.6kDa; **PTII-TVT-8**, 31.0kDa). Nonetheless, the PDI of **PTII-TVT-8** (3.46) is larger than that of **PTII-T** (2.41). Large PDI might be the result of strong aggregation of the polymers. We also measured their thermal properties. Both polymers showed decomposition temperatures above 350 °C under nitrogen atmosphere, and no phase transition was observed before decomposition.

Optical properties

Since **PTII-T** and **PTII-TVT-8** exhibit acceptable solubility, their electronic properties and OFET performance were examined in detail. UV-vis absorption spectra of the two polymers both in solution and in thin film were measured (Figure 1b). Compared with their cross conjugated counterparts, greater red-shift was observed in the UV-vis spectra for both polymers, clearly indicating that they are fully conjugated. This again testified that full conjugation is needed to form strong donor-acceptor (D-A) intramolecular charge transfer

complex, facilitating electron delocalization over the conjugated main chain.³¹

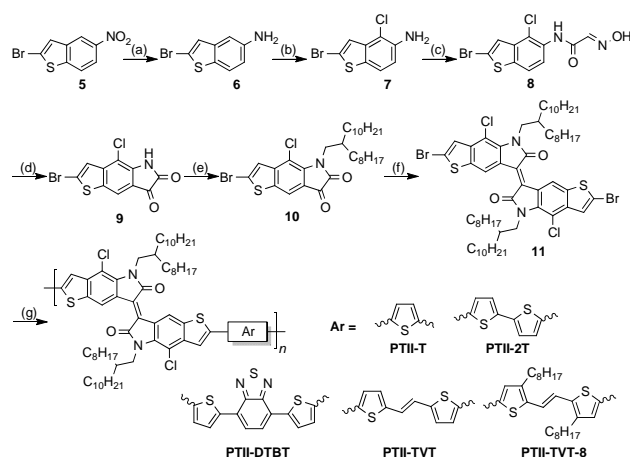

Scheme 5. Modified synthetic route of polymers based on α -brominated TII. ^a

^aReagents and conditions: (a) $\text{SnCl}_2 \cdot \text{H}_2\text{O}$, HCl, MeOH, reflux 4h, 90%; (b) N-Chlorosuccinimide, THF, reflux 2h, 88%; (c) $\text{Cl}_3\text{CCH}(\text{OH})_2$, $\text{NH}_2\text{OH} \cdot \text{HCl}$, Na_2SO_4 , HCl, $\text{H}_2\text{O}/\text{EtOH}$ (v/v = 4:1), 80 °C, 2h, 91%; (d) H_2SO_4 , 80 °C, 30 min; (e) 9-(bromomethyl)nonadecane, K_2CO_3 , DMF, 50 °C, 12h, 2 steps, 35%; (f) $\text{P}(\text{NEt}_2)_3$, CH_2Cl_2 , -78 °C to room temperature, 92%; (g) 2,5-bis(trimethylstannyl)thiophene, 5,5'-bis(trimethylstannyl)-2,2'-bithiophene, 4,7-bis(5-(trimethylstannyl)thiophen-2-yl)benzo[*c*][1,2,5]thiadiazole, (*E*)-1,2-bis(5-(trimethylstannyl)thiophen-2-yl)ethane, (*E*)-1,2-bis(3-octyl-5-(trimethylstannyl)thiophen-2-yl)ethene, $\text{Pd}(\text{PPh}_3)_4$, toluene, 110 °C, 48h; for **PTII-2T**, **PTII-DTBT**, and **PTII-TVT**, ca. 20%; for **PTII-T**, 92%; for **PTII-TVT-8**, 71%.

The UV-vis spectrum of each polymer in solution displays two absorption bands characteristic of D-A systems from 350 to 1000 nm: a high-energy band attributed to the localized π - π^* transition, and a low-energy band assigned to excited states with a prevalent highest occupied molecular orbital (HOMO)-lowest unoccupied molecular orbital (LUMO) contribution. Through the increase of the effective conjugation length after the introduction of TVT unit, a red-shifted absorption band for **PTII-TVT-8** relative to **PTII-T** is predicted; however, note that the absorption maximum of **PTII-TVT-8** is blue-shifted vs. that of **PTII-T** by 16 nm in the film and 8 nm in solution. This may be due to the destabilization of the LUMO with successive expansion of the π -system of the thiophene moieties, which could be supported by the data from CV. While both polymers show similar maximum absorption around 710 nm in solution, the onset of the absorption of **PTII-TVT-8** is remarkably red-shifted compared with that of **PTII-T** (900 nm vs. 800 nm), indicating that the bandgap of **PTII-TVT-8** is smaller than that of **PTII-T**. Optical bandgaps (E_g^{opt}) deduced from the absorption edges of the film spectra are in the same order: **PTII-T** (1.56 eV) > **PTII-TVT-8** (1.35 eV). In film state, the UV spectrum of **PTII-T** exhibits little difference from that in solution state, indicating that the aggregation state of **PTII-T** in film is very similar to that in solution. On the other hand, the UV-vis spectrum of **PTII-TVT-8** in film state is quite different from that in solution state: the localized π - π^* transition at 462 nm in the solution state disappears, and a strong and broad absorption ranging from 400 nm to 900 nm appears (with

maximum absorption peak at 704 nm). Furthermore, a red-shifted shoulder at 766 nm was observed, indicating that stronger π - π stacking exists in the film of **PTII-TVT-8**.

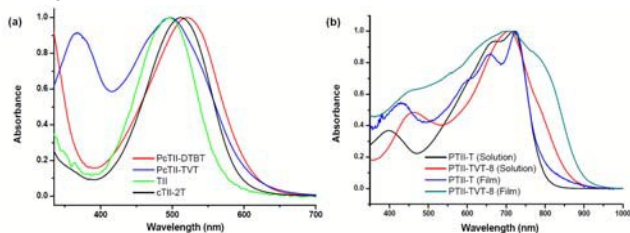


Figure 1. (a) Normalized UV-vis absorption spectra of TII, cTII-2T, and two TII based polymers in CHCl_3 solution (1×10^{-5} M); (b) normalized UV-vis absorption spectra of two TII based polymers both in chlorobenzene solution (1×10^{-5} M) and in film.

Electrochemical properties

In order to experimentally determine the energy levels of the polymers, we investigated the electrochemical properties of **PTII-T** and **PTII-TVT-8** via cyclic voltammetry (CV). Thin films of both polymers were drop-casted onto a glassy carbon electrode respectively, and their CV diagram were recorded in an acetonitrile solution containing 0.1 M *n*-Bu₄NPF₆ under an inert atmosphere versus the Ag/AgCl redox couple. The data are summarized in detail in Table 1. The HOMO energy level was calculated using the equation $E_{\text{HOMO}} = -(E_{\text{onset}}^{\text{ox}} - \text{ferrocene}) - 4.8$ eV, where $E_{\text{onset}}^{\text{ox}}$ was the onsets of the oxidation potential. The LUMO energy level was deduced from the equation $E_{\text{LUMO}} = E_{\text{HOMO}} + E_g^{\text{opt}}$.³² The HOMO/LUMO levels of **PTII-T** are -5.73 and -4.17 eV, and that of **PTII-TVT-8** are -5.35/-4.00 eV. Compared with **PTII-T**, **PTII-TVT-8** exhibits high-lying HOMO level, due to the stronger electron-donating ability of TVT than thiophene ring. Both polymers belong to low band-gap conducting polymer, and one would like to predict that both will exhibit ambipolar charge transfer properties. Especially, LUMO level of **PTII-T** is even lower, which implies that electron-transfer process in **PTII-T** will be more facile than that in **PTII-TVT-8**.

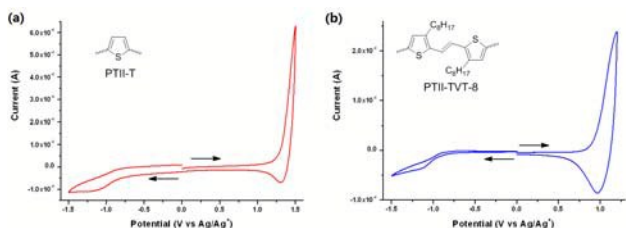


Figure 2. Cyclic voltammogram of (a) **PTII-T** and (b) **PTII-TVT-8** in thin film drop-casting on a glassy carbon electrode and tested in *n*-Bu₄NPF₆/CH₃CN solution (scan rate: 0.1 V/s).

OFET properties

To test their OFET performance, top-gate/bottom-contact (TG/BC) devices were constructed for both polymers to fabricate polymer FETs. This device configuration is preferred for ambient-stable ambipolar or *n*-type organic materials, because of its better injection

characteristics and the encapsulation effect of the top dielectric layer.⁹ The semiconducting layer was deposited by spin-coating the corresponding polymer solutions (3 mg/mL in TCE) on untreated Au (Source-Drain)/SiO₂/Si substrate. After thermal annealing the film at 180 °C for 5 min, a CYTOP solution was spin-coated on top of the polymer film as the dielectric layer, and an aluminum layer was thermally evaporated as the gate electrode. All devices were tested in ambient on a probe station and exhibited ambipolar properties. As shown in table 2, both fully conjugated polymers exhibit electron and hole mobilities in the 10⁻² order of magnitude, much higher than crossconjugated polymers (which show mobilities in 10⁻⁴ range or lower, see Supplementary Information). **PTII-T** shows balanced electron and hole mobility of 0.029 and 0.018 cm²V⁻¹s⁻¹, respectively. On the other hand, **PTII-TVT-8** exhibits better hole mobility (0.037 cm²V⁻¹s⁻¹), almost one-order larger than its electron mobility (0.004 cm²V⁻¹s⁻¹). These results indicate that both polymers are good *p*-type semiconductors, but for electron transport, **PTII-TVT-8** was not as good as **PTII-T**. At the first glance, **PTII-TVT-8** should also exhibit balanced hole and electron mobility by judging from its HOMO/LUMO level. However, it is also generally accepted that in D-A type polymers, *p*-type charge transfer becomes predominant with the size increase of the donor. Thus, **PTII-TVT-8** mainly exhibits hole transfer ability since TVT is a larger and bigger electron donor than thiophene ring. **PTII-TVT-8** shows better hole mobility and smaller threshold voltage than **PTII-T**, presumably due to incorporation of the highly π -extended TVT unit with better electron donating ability than thiophene unit. Compared with other reported isoindigobased polymers, the OFET performances of TII based polymers are lower, presumably due to the molecular weights of **PTII-T** and **PTII-TVT-8** are relatively low. The sufficiently high molecular weight that enables polymer chains to form well-interconnected crystalline grains to establish efficient pathways for intergranular charge transport.³³ It was reported that mobility increase upon annealing was observed in other isoindigo based polymers,^{7, 34, 35} and we also tried to improve the OFET performance by annealing the film at higher temperature for longer time. However, no substantial improvements were observed in comparison with as-spun films, implying that a subtle change in the structure of polymer backbones can greatly affect the thermodynamic behaviour of the resulting solid-state thin film.

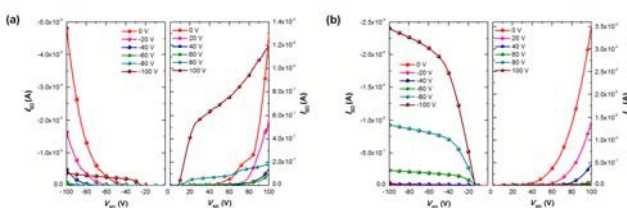


Figure 3. Output characteristics of (a) **PTII-T** and (b) **PTII-TVT-8** OFET devices. All OFET devices (*W/L* = 20) were fabricated with CYTOP in ambient conditions.

Table 1. Molecular weight, optical (UV-vis) properties and electrochemical data.

polymers	M _n (kDa)	PDI	λ_{max} (nm) solution	λ_{max} (nm) film	E _g ^{opt} (eV)	LUMO (eV)	HOMO (eV)
PTII-T	26.6	2.41	715	720	1.56	-4.17	-5.73

Polymer Chemistry Accepted Manuscript

PTII-TVT-8	31.0	3.46	707	704	1.37	-4.00	-5.35
-------------------	------	------	-----	-----	------	-------	-------

Table 2. OFET performance of **PTII-T** and **PTII-TVT-8** thin films under ambient.

polymers	μ_e (cm ² /Vs)	V_T (V)	I_{on}/I_{off}	μ_h (cm ² /Vs)	V_T (V)	I_{on}/I_{off}
PTII-T	0.029	72	538	0.018	-81	10 ³
PTII-TVT-8	0.004	83	4x10 ³	0.037	-53	10 ³

Morphology

The thin film crystallinity and morphologies of both polymers were investigated by X-ray diffraction (XRD) and tapping-mode atomic force microscopy (AFM) to better understand the relationships between the morphology and device performance. The crystallinity and molecular orientations of thin films were investigated by XRD analysis. The out of plane XRD patterns of the thin film of **PTII-T** and **PTII-TVT-8** are shown in Fig. 4a. The d -spacing of both molecules were calculated from the out-of-plane XRD patterns and Bragg equation. **PTII-T** and **PTII-TVT-8** films exhibited similar primary diffraction peaks at 2θ of 3.75°, corresponding to d (100)-spacing of 23.55 Å, indicating good layer-by-layer packed lamellar structure.

Besides crystallinity, the semiconductor film morphology is another decisive factor that affects charge transport properties. For OFETs to achieve high charge mobility, it is favorable for thin films to have large interconnected domains in order to minimize crystallite grain boundaries.³² As illustrated in Figure 4, the AFM image of **PTII-TVT-8** film showed almost smooth and spherical morphology, while the **PTII-T** film shows relatively fine, highly interconnected fibrillar domains with an obvious reduction of the surface roughness (RMS = 0.707 nm) when compared to **PTII-TVT-8** (RMS = 1.48 nm). Crystalline zones of **PTII-T** film are formed presumably due to strong intermolecular π - π interactions. We speculate that the more efficient ambipolar charge transport in the **PTII-T** film is related to more densely interconnected compact domains of bundled nanofibers.

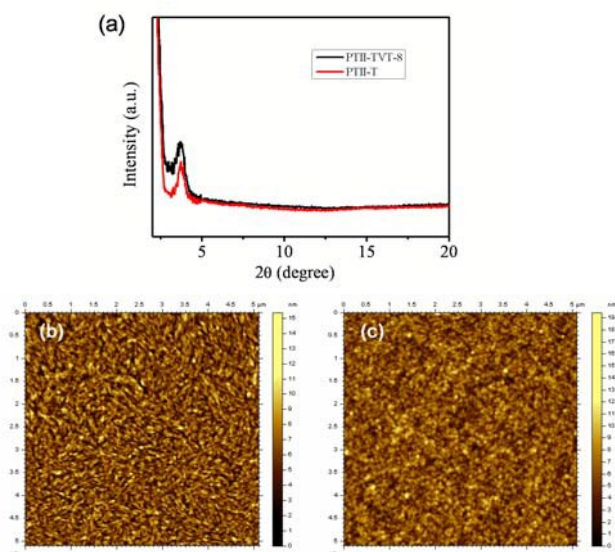


Figure 4. (a) Out-of-plane XRD patterns of **PTII-T** and **PTII-TVT-8**; tapping-mode AFM height images of (b) **PTII-T** and (c) **PTII-TVT-8** films. Films were spin-coated from the TCE solutions of the polymers (3 mg/mL).

Conclusions

In conclusion, we have presented the synthesis of both cross conjugated and fully conjugated polymers based on thiophene-fused isoindigo. Solution-processed OFETs based on two fully conjugated polymers exhibited stable performance in ambient conditions due to their low-lying LUMO level. Both fullyconjugated polymers exhibit better performance than crossconjugated polymers. **PTII-T** shows balanced electron and hole mobility of (0.029 and 0.018 cm²V⁻¹s⁻¹ respectively), and **PTII-TVT-8** exhibits better hole mobility (0.037 cm²V⁻¹s⁻¹). Further improvement in OFET performance can be expected by optimizing the electron rich units and improving the molecular weight for TII-based polymers with both good solubility and OFET properties.

Experimental

General Procedures and Experimental Details.

All glassware was completely dried before use. Chemicals and solvents were purchased from commercial suppliers or purified by standard techniques. TLC plates were observed by exposure to UV light and/or immersion in a phosphomolybdic acid staining solution followed by drying. Column chromatography was carried out using silica gel 200–300 mesh. ¹H NMR and ¹³C NMR spectra were collected on a Bruker AVANCE-III 600 MHz with tetramethylsilane (TMS) as an internal standard at 298K and CDCl₃ was used as the solvent. The coupling constants J are given in Hz. The IR spectra were observed with Nicolet 6700 FTIR Spectrometer. Cyclic voltammetry (CV) curves were performed on an electrochemistry workstation (CHI660D, Chenhua Shanghai) in an anhydrous argon-saturated chloroform solution (10⁻³ mol/L) of 0.1 M tetrabutylammoniumhexafluorophosphate (*n*-Bu₄NPF₆) at room temperature by three-electrode system, which utilize glassy carbon electrode as the working electrode, Pt as the counter electrode and a Ag/AgCl as the reference electrode at a potential scan rate of 0.1 V/s. The potential of reference electrode in chloroform was identified by using ferrocene as internal standard. The UV-*vis* spectra were recorded with a Hitachi U-4100 UV-*vis* spectrophotometer in an anhydrous chloroform solution (10⁻⁵ mol/L). HRMS were investigated on a Bruke Maxis UHR TOF. Gel permeation chromatography (GPC) was performed on Waters 1151 pump and UV-*vis* monitor (700 nm) using 1,2,4-trichlorobenzene (TCB) as eluent (150 °C). XRD patterns were investigated with Rigaku D/MAX-2500 X-ray diffractometer. AFM patterns were collected with Digital Instrument NanoScopeIIIa. TGA patterns were collected with TGA Q50 V20.13 Build 39. DSC patterns were collected with DSC Q20 V24.11 Build 124.

Device Fabrication and Characterization.

Top-gate/bottom-contact FET devices were fabricated using n^{++} -Si/SiO₂ (300 nm) substrates. The gold source and drain bottom electrodes (with Ti as the adhesion layer) were patterned by photolithography on the SiO₂ surface. The substrates were treated by using ultrasonication in acetone, cleaning agent, deionized water (twice), and isopropanol. The treated substrates were dried under vacuum at 80 °C. The substrates were used by transferring into a glove box. The thin films of the small molecules were deposited on the substrates by spin-coating using TCE solutions (3 mg/mL) at 1500 rpm for 60 s. After OFET thin films were deposited, a CYTOP solution (CTL809M:CT-solv180 = 3:1) was spin-coated onto the semiconducting layer at 2000 rpm for 60 s resulting in a dielectric layer of 500 nm thick. The CYTOP layer was then cross-linked at 100 °C for 1 h. A layer of Al (50 nm) were then evaporated onto the dielectric layer by thermal evaporation as gate electrodes. The OFET devices had a channel ratio of width to length ($W/L = 20$). The performance of the OFETs were investigated on a probe stage using a Keithley 4200 parameter analyzer in atmosphere (humidity 50-60%). The carrier mobility, μ , was calculated from the data in the saturated regime according to the equation $I_{SD} = (W/2L)C_i\mu(V_G - V_T)^2$, where I_{SD} is the drain current in the saturated regime. W and L are the semiconductor channel width and length, respectively. C_i ($C_i = 3.5$ nF) is the capacitance per unit area of the gate dielectric layer. V_G and V_T are the gate voltage and threshold voltage, respectively. $V_G - V_T$ of the devices were determined from the relationship between the square root of I_{SD} and V_G at the saturated regime.

Synthetic procedures

4-Chloro-5*H*-thieno[2,3-*f*]indole-6,7-dione (**1**) and 2-Bromo-5-nitrobenzo[*b*]thiophene (**5**) were synthesized according to the literature.^{14, 29, 30}

4-Chloro-5-(2-octyldecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione (2). To a solution of 4-chloro-5*H*-thieno[2,3-*f*]indole-6,7-dione (238 mg, 1.0 mmol, 1.0 equiv.), potassium carbonate (207 mg, 1.5 mmol, 1.5 equiv.) in dimethylformamide (DMF) (10 mL), 1-bromo-2-octyldecane (434 mg, 1.2 mmol, 1.2 equiv.) was added under argon. The mixture was stirred for 24 h at 50 °C and then the solvent was removed under reduced pressure. The residues were purified by silica gel chromatography with eluting (PE : EA = 10 : 1) to give 4-chloro-5-(2-octyldecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione as a red solid (337 mg, 65 %). ¹H NMR (CDCl₃, 600 MHz, ppm) δ : 8.06 (s, 1H), 7.85 (d, $J = 5.5$ Hz, 1H), 7.58 (d, $J = 5.5$ Hz, 1H), 4.09 (d, $J = 7.6$ Hz, 2H), 2.06 (m, 1H), 1.39-1.25 (m, 32H), 0.91-0.86 (m, 6H). ¹³C NMR (CDCl₃, 150 MHz, ppm) δ : 182.64, 159.67, 145.98, 141.19, 135.10, 135.00, 123.71, 119.83, 118.53, 110.69, 46.32, 37.59, 37.57, 31.91, 31.87, 31.79, 30.86, 30.84, 30.04, 29.73, 29.63, 29.62, 29.58, 29.53, 29.34, 29.29, 26.14, 26.10, 22.70, 22.67, 22.64, 14.13, 14.12, 14.08. ESI-HRMS: Calcd. for $[M+H]^+$: 518.2860. Found: 518.2850.

3-Bromo-4-chloro-5-(2-octyldecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione (3). A mixture of 4-chloro-5-(2-octyldecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione (518 mg, 1.0 mmol, 1.0 equiv.), sodium acetate (164 mg, 2.0 mmol, 2.0 equiv.), bromine (206 μ L, 4.0 mmol, 4.0 equiv.), and acetic acid (2.0 mL) was heated under reflux for 2 h, then poured into crushed ice (20 mL). The mixture was extracted

with dichloromethane, and then the solvent was removed under reduced pressure. The residues were purified by silica gel chromatography with eluting (PE : EA = 10 : 1) to give 3-bromo-4-chloro-5-(2-octyldecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione as a red solid (418 mg, 70 %). ¹H NMR (CDCl₃, 600 MHz, ppm) δ : 8.03 (s, 1H), 7.84 (s, 1H), 4.16 (d, $J = 7.6$ Hz, 2H), 2.06 (m, 1H), 1.39-1.26 (m, 32H), 0.91-0.87 (m, 6H). ¹³C NMR (CDCl₃, 150 MHz, ppm) δ : 182.58, 159.57, 142.65, 138.81, 135.70, 134.20, 119.75, 118.91, 112.24, 107.16, 46.96, 37.66, 37.64, 31.92, 31.88, 31.79, 30.85, 30.83, 30.06, 29.75, 29.65, 29.62, 29.57, 29.52, 29.35, 29.30, 26.12, 26.08, 22.70, 22.68, 22.65, 14.14, 14.12, 14.08. ESI-HRMS: Calcd. for $[M+H]^+$: 596.1965. Found: 596.1949.

β -Dibromothiophen fused isoindigo (4, β -Br-TII). Tris(diethylamino)phosphine (274 μ L, 1.0 mmol, 1.0 equiv.) was added dropwise to a solution of 3-bromo-4-chloro-5-(2-octyldecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione (597 mg, 1.0 mmol, 1.0 equiv.) in dichloromethane (10 mL) at -78 °C under an argon atmosphere. Thereafter, the temperature was gradually increased to room temperature and stirred for another 30 min. The solvent was removed under reduced pressure, and the residue was then purified by column chromatography using petroleum ether as eluent to give β -Br-TII as a dark-red solid (511 mg, 88%). ¹H-NMR (CDCl₃, 600 MHz) δ : 9.65 (s, 2H), 7.62 (s, 2H), 4.14 (d, $J = 7.6$ Hz, 4H), 2.03 (m, 2H), 1.36-1.25 (m, 64H), 0.90-0.84 (m, 12H). ¹³C-NMR (CDCl₃, 150 MHz) δ : 168.32, 138.34, 134.80, 134.52, 132.16, 131.03, 123.40, 123.11, 109.42, 106.27, 46.65, 37.71, 31.93, 31.88, 31.81, 30.90, 30.14, 29.79, 29.72, 29.68, 29.64, 29.62, 29.57, 29.38, 29.33, 26.14, 26.11, 22.71, 22.68, 22.64, 14.15, 14.12, 14.08. APCI-HRMS: Calcd. for $[M+H]^+$: 1161.3932. Found: 1161.3932.

***c*TII-2T.** β -Br-TII (116 mg, 0.1 mmol, 1.0 equiv.), tributyl(thiophen-2-yl)stannane (78 mg, 0.21 mmol, 2.1 equiv.), Pd(PPh₃)₄ (2.3 mg, 2 mol%), and 2 mL of THF were added to a Schlenk tube. The tube was charge with argon through a freeze-pump-thaw cycle for three times. The mixture was stirred for 24 h at 80 °C. The solvent was removed under reduced pressure, and the residue was then purified by column chromatography using petroleum ether as eluent to give *c*TII-2T as a dark-red solid (103 mg, 89%). ¹H-NMR (CDCl₃, 600 MHz) δ : 9.72 (d, 2H, $J = 1.86$ Hz), 7.63 (s, 2H), 7.43 (dd, 2H, $J_1 = 5.10$ Hz, $J_2 = 1.08$ Hz), 7.10 (m, 4H), 4.11 (d, $J = 7.6$ Hz, 4H), 2.01 (m, 2H), 1.29-1.21 (m, 64H), 0.90-0.83 (m, 12H). ¹³C-NMR (CDCl₃, 150 MHz) δ : 168.60, 138.24, 137.61, 137.49, 135.66, 133.58, 132.25, 131.10, 128.91, 126.43, 125.88, 123.43, 122.85, 109.85, 46.55, 37.44, 31.93, 31.88, 31.80, 30.81, 30.08, 29.73, 29.68, 29.64, 29.60, 29.54, 29.37, 29.33, 26.05, 26.02, 22.71, 22.68, 22.66, 14.15, 14.13, 14.09. APCI-HRMS: Calcd. for $[M+H]^+$: 1167.5497. Found: 1167.5487.

2-Bromobenzo[*b*]thiophen-5-amine (6). To a suspension of 2-bromo-5-nitrobenzo[*b*]thiophene (1.29 g, 5.0 mmol, 1.0 equiv.) in methanol (15 mL) was added Stannous chloride hydrate (6.77 g, 30.0 mmol, 6.0 equiv.) and catalytic amount of hydrochloric acid. Then the mixture was heated to reflux and stirred until TLC indicated consumption of starting material (up to 4 hours). Then reaction was then cooled to 0 °C in an ice bath, and 2M aqueous solution of NaOH was added to adjust the pH value of the system to 8 ~ 9. The product was extracted with ethyl acetate for 5 times and the combined organic phase was dried with anhydrous MgSO₄. The solvent was removed under reduced pressure, and the residue was

then purified by column chromatography using petroleum ether/ethyl acetate (4:1) as eluent to give 2-bromobenzo[*b*]thiophen-5-amine as a white solid (1.02 g, 90%). ¹H-NMR (CDCl₃, 600 MHz) δ: 7.49 (d, 1H, *J* = 8.54 Hz), 7.16 (s, 1H), 6.99 (d, *J* = 2.22 Hz, 1H), 6.76 (dd, *J*₁ = 8.54 Hz, *J*₂ = 2.22 Hz, 1H), 3.73 (br, 2H). ¹³C-NMR (CDCl₃, 150 MHz) δ: 144.00, 140.66, 131.41, 125.92, 122.15, 115.88, 114.64, 107.50. APCI-HRMS: Calcd. for [M+H]⁺: 227.9483, found: 227.9482.

2-Bromo-4-chlorobenzo[*b*]thiophen-5-amine (7). To the solution of 2-bromobenzo[*b*]thiophen-5-amine (2.28 g, 10.0 mmol, 1.0 equiv.) in anhydrous THF (50 mL) was added N-chlorosuccinimide (1.47 g, 10.0 mmol, 1.0 equiv.) in one portion. The mixture was heated to reflux and stirred for 2 hour. The reaction was quenched by water and extracted with dichloromethane for 3 times. The combined organic phases were dried with sodium sulfate. The solvent was removed under reduced pressure and the crude product was purified by column chromatography (silica gel; eluent: PE:EA = 10:1) to afford 2-bromo-4-chlorobenzo[*b*]thiophen-5-amine as a white solid (2.32 g, 88 %). ¹H-NMR (CDCl₃, 600 MHz) δ: 7.38 (m, 2H), 6.81 (d, *J* = 8.40 Hz, 1H), 4.10 (br, 2H). ¹³C-NMR (CDCl₃, 150 MHz) δ: 140.18, 138.57, 131.43, 124.58, 120.32, 116.81, 114.78, 111.16. APCI-HRMS: Calcd. for [M+H]⁺: 261.9093, found: 261.9090.

(*E*)-N-(2-bromo-4-chlorobenzo[*b*]thiophen-5-yl)-2-(hydroxyimino)acetamide (8). Solution A: To a 6.0 mL ethanol solution of 2-bromo-4-chlorobenzo[*b*]thiophen-5-amine (1.45 g, 5.5 mmol, 1.0 equiv.), was added ethanol (35 mL), conc. HCl (2.5 mL), water (130 mL) and anhydrous Na₂SO₄ (6.25 g, 44.0 mmol, 8.0 equiv.). To aid dissolution, the mixture was heated to approximately 40°C and stirred vigorously. Solution B: Chloral hydrate (1.36 g, 8.25 mmol, 1.5 equiv.) and hydroxylamine hydrochloride (1.34 g, 19.25 mmol, 3.5 equiv.) was dissolved in 25 mL of water and stirred for 10 min. Solution A was then added in one portion to solution B. The resulting mixture was heated to 80°C, and stirred for 2 hours. Then the mixture was cooled to room temperature. The precipitate was collected by filtration and washed with water. After drying in vacuum oven overnight, 1.68 g (91 %) of product was obtained. The crude product can be used in the next step without further purification. APCI-HRMS: Calcd. for [M+H]⁺: 332.9100, found: 332.9093.

2-Bromo-4-chloro-5*H*-thieno[2,3-*f*]indole-6,7-dione (9). A 25-mL flask was charged with 5.0 mL of conc. sulfuric acid. After heating to 50 °C in an oil bath, (*E*)-N-(2-bromo-4-chlorobenzo[*b*]thiophen-5-yl)-2-(hydroxyimino) acetamide (1.00 g, 3.0 mmol) was added over a period of 10 min. The resulting deep red solution was heated to 80 °C for 30 min and then cooled to room temperature. The mixture was then added rapidly to a vigorously stirred mixture of 30 mL of crashed ice and stood for an hour. The precipitate was removed by filtration and washed with water. The crude product was dried at low pressure, whereupon 0.91 g (95 %) of red powder was obtained. The crude product can be used in the next step without further purification. APCI-HRMS: Calcd. for [M+H]⁺: 315.8835, found: 315.8829.

2-Bromo-4-chloro-5-(2-octyldodecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione (10). To a solution of 2-bromo-4-chloro-5*H*-thieno[2,3-*f*]indole-6,7-dione (0.91 g, 2.9 mmol, 1.0 equiv.), potassium carbonate (0.80 mg, 5.8 mmol, 2.0 equiv.) in dimethylformamide (DMF) (30 mL), 1-bromo-2-octyldodecane (2.10 g, 5.8 mmol, 2.0

equiv.) was added under argon. The mixture was stirred for 24 h at 50 °C and then the solvent was removed under reduced pressure. The residues were purified by silica gel chromatography with eluting (PE : EA = 10 : 1) to give 2-bromo-4-chloro-5-(2-octyldodecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione as a red solid (0.63 g, 35 % for 2 steps). ¹H NMR (CDCl₃, 600 MHz, ppm) δ: 7.89 (s, 1H), 7.56 (s, 1H), 4.06 (d, *J* = 7.6 Hz, 2H), 2.01 (m, 1H), 1.38-1.24 (m, 32H), 0.90-0.87 (m, 6H). ¹³C NMR (CDCl₃, 150 MHz, ppm): δ 182.19, 159.39, 145.85, 141.90, 135.80, 126.53, 124.51, 118.49, 118.11, 109.61, 46.32, 37.59, 31.92, 31.88, 30.81, 30.03, 29.64, 29.62, 29.57, 29.53, 29.35, 29.30, 26.11, 22.70, 22.68, 14.14, 14.12. APCI-HRMS: Calcd. for [M+H]⁺: 596.1965, found: 596.1963.

α-Dibromothiophen fused isoindigo (11, α-Br-TII). Tris(diethylamino)phosphine (466 μL, 1.7 mmol, 1.0 equiv.) was added dropwise to a solution of 2-bromo-4-chloro-5-(2-octyldodecyl)-5*H*-thieno[2,3-*f*]indole-6,7-dione (1.01 g, 1.7 mmol, 1.0 equiv.) in dichloromethane (35 mL) at -78 °C under an argon atmosphere. Thereafter, the temperature was gradually increased to room temperature and stirred for another 30 min. The solvent was removed under reduced pressure, and the residue was then purified by column chromatography using petroleum ether as eluent to give α-Br-TII as a dark-red solid (0.91 g, 92%). ¹H-NMR (CDCl₃, 600 MHz) δ: 9.54 (s, 2H), 7.48 (s, 2H), 4.11 (d, *J* = 7.6 Hz, 4H), 2.02 (m, 2H), 1.32-1.23 (m, 64H), 0.91-0.86 (m, 12H). ¹³C-NMR (CDCl₃, 150 MHz) δ: 168.31, 141.55, 137.27, 135.13, 132.22, 126.02, 122.47, 121.73, 120.89, 107.35, 46.10, 37.69, 31.93, 31.89, 30.94, 30.10, 29.68, 29.64, 29.62, 29.57, 29.38, 29.33, 26.20, 26.19, 22.71, 22.68, 14.15, 14.11. APCI-HRMS: Calcd. for [M+H]⁺: 1161.3932, found: 1161.3950.

Procedures for Stille Polymerization and Polymer Purification.

PTII-T.α-Br-TII (116 mg, 0.1 mmol, 1.0 equiv.), 2,5-bis(trimethylstannyl)thiophene (41 mg, 0.1 mmol, 1.0 equiv.), Pd(PPh₃)₄ (2.3 mg, 2 mol%), and 2.5 mL of toluene were added to a Schlenk tube. The tube was charge with argon through a freeze-pump-thaw cycle for three times. The mixture was stirred for 48 h at 110 °C. And then the mixture was precipitated into methanol (50 mL). The precipitate was filtered and purified via Soxhlet extraction for 8 h with methanol, 12 h with hexane, and finally was collected with chloroform. The chloroform solution was then concentrated and precipitated into methanol (50 mL) to give a dark blue solid (100 mg, 92%). GPC: M_n = 26.6 kDa; PDI = 2.41.

PTII-TV.8.α-Br-TII (116 mg, 0.1 mmol, 1.0 equiv.), (*E*)-1,2-bis(3-octyl-5-(trimethylstannyl)thiophen-2-yl)ethene (74 mg, 0.1 mmol, 1.0 equiv.), Pd(PPh₃)₄ (2.3 mg, 2 mol%), and 2.5 mL of toluene were added to a Schlenk tube. The tube was charge with argon through a freeze-pump-thaw cycle for three times. The mixture was stirred for 48 h at 110 °C. And then the mixture was precipitated into methanol (50 mL). The precipitate was filtered and purified via Soxhlet extraction for 8 h with methanol, 12 h with chloroform, and finally was collected with chlorobenzene. The chlorobenzene solution was then concentrated and precipitated into methanol (50 mL) to give a dark blue solid (101 mg, 71%). GPC: M_n = 31.0 kDa; PDI = 3.46.

Acknowledgements

This work is supported by “100 Talents” Program from Chinese Academy of Sciences and National Science Foundation of China (NSFC No. 21174157, 51573204).

Notes and references

1. S. Kola, J. Sinha and H. E. Katz, *J. Polym. Sci., Part B: Polym. Phys.*, 2012, **50**, 1090-1120.
2. A. Mishra and P. Bauerle, *Angew. Chem. Int. Ed.*, 2012, **51**, 2020-2067.
3. J. Mei, Y. Diao, A. L. Appleton, L. Fang and Z. Bao, *J. Am. Chem. Soc.*, 2013, **135**, 6724-6746.
4. Y. Zhao, Y. Guo and Y. Liu, *Adv. Mater.*, 2013, **25**, 5372-5391.
5. S. Holliday, J. E. Donaghey and I. McCulloch, *Chem. Mater.*, 2014, **26**, 647-663.
6. J. Mei, K. R. Graham, R. Stalder and J. R. Reynolds, *Org. Lett.*, 2010, **12**, 660-663.
7. T. Lei, Y. Cao, Y. Fan, C.-J. Liu, S.-C. Yuan and J. Pei, *J. Am. Chem. Soc.*, 2011, **133**, 6099-6101.
8. T. Lei, Y. Cao, X. Zhou, Y. Peng, J. Bian and J. Pei, *Chem. Mater.*, 2012, **24**, 1762-1770.
9. T. Lei, J.-H. Dou, Z.-J. Ma, C.-H. Yao, C.-J. Liu, J.-Y. Wang and J. Pei, *J. Am. Chem. Soc.*, 2012, **134**, 20025-20028.
10. P. Deng and Q. Zhang, *Polym. Chem.*, 2014, **5**, 3298-3305.
11. T. Lei, J.-Y. Wang and J. Pei, *Acc. Chem. Res.*, 2014, **47**, 1117-1126.
12. R. Stalder, J. Mei, K. R. Graham, L. A. Estrada and J. R. Reynolds, *Chem. Mater.*, 2014, **26**, 664-678.
13. R. S. Ashraf, A. J. Kronemeijer, D. I. James, H. Sirringhaus and I. McCulloch, *Chem. Commun.*, 2012, **48**, 3939-3941.
14. N. Zhao, L. Qiu, X. Wang, Z. An and X. Wan, *Tetrahedron Lett.*, 2014, **55**, 1040-1044.
15. S. Xu, N. Ai, J. Zheng, N. Zhao, Z. Lan, L. Wen, X. Wang, J. Pei and X. Wan, *RSC Adv.*, 2014, **5**, 8340-8344.
16. I. Meager, M. Nikolka, B. C. Schroeder, C. B. Nielsen, M. Planells, H. Bronstein, J. W. Rumer, D. I. James, R. S. Ashraf, A. Sadhanala, P. Hayoz, J.-C. Flores, H. Sirringhaus and I. McCulloch, *Adv. Funct. Mater.*, 2014, **24**, 7109-7115.
17. T. Hasegawa, M. Ashizawa and H. Matsumoto, *RSC Adv.*, 2015, **5**, 61035-61043.
18. W. Yue, R. S. Ashraf, C. B. Nielsen, E. Collado-Fregoso, M. R. Niazi, S. A. Yousaf, M. Kirkus, H. Y. Chen, A. Amassian, J. R. Durrant and I. McCulloch, *Adv. Mater.*, 2015, **27**, 4702-4707.
19. Y. K. Voronina, D. B. Krivolapov, A. V. Bogdanov, V. F. Mironov and I. A. Litvinov, *J. Struct. Chem.*, 2012, **53**, 413-416.
20. A. V. Bogdanov, V. F. Mironov, L. I. Musin, B. I. Buzykin and A. I. Konovalov, *Russ. J. Gen. Chem.*, 2008, **78**, 1977-1979.
21. T. Lei, J.-H. Dou, Z.-J. Ma, C.-J. Liu, J.-Y. Wang and J. Pei, *Chem. Sci.*, 2013, **4**, 2447-2452.
22. I. Meager, M. Nikolka, B. C. Schroeder, C. B. Nielsen, M. Planells and I. McCulloch, *Adv. Funct. Mater.*, 2014, **24**, 7109-7115.
23. N. F. Phelan and M. Orchin, *J. Chem. Educ.*, 1968, **45**, 633-637.
24. R. P. Dickinson and B. Iddon, *J. Chem. Soc. C*, 1968, 2733-2737.
25. E. Baciocchi, R. Ruzziconi and G. V. Sebastiani, *J. Am. Chem. Soc.*, 1983, **105**, 6114-6120.
26. T. Yamamoto, S. Ogawa and R. Sato, *Tetrahedron Lett.*, 2004, **45**, 7943-7946.
27. T. Kobayashi, M. Nakashima, T. Hakogi, K. Tanaka and S. Katsumura, *Org. Lett.*, 2006, **8**, 3809-3812.
28. T. Qi, Y. Guo, Y. Liu, H. Xi, H. Zhang, X. Gao, Y. Liu, K. Lu, C. Du, G. Yu and D. Zhu, *Chem. Commun.*, 2008, **46**, 6227-6229.
29. S. G. Newman, V. Aureggi, C. S. Bryan and M. Lautens, *Chem. Commun.*, 2009, **35**, 5236-5238.
30. T. T. B. Nguyen, T. Lomberget, N. C. Tran and R. Barret, *Tetrahedron*, 2013, **69**, 2336-2347.
31. Y. J. Cheng, S. H. Yang and C. S. Hsu, *Chem. Rev.*, 2009, **109**, 5868-5923.
32. J.-L. Bredas, *Mater. Horiz.*, 2014, **1**, 17-19.
33. H. N. Tsao and K. Mullen, *Chem. Soc. Rev.*, 2010, **39**, 2372-2386.
34. J. Mei, D. H. Kim, A. L. Ayzner, M. F. Toney and Z. Bao, *J. Am. Chem. Soc.*, 2011, **133**, 20130-20133.
35. G. Kim, A. R. Han, H. R. Lee, J. Lee, J. H. Oh and C. Yang, *Chem. Commun.*, 2014, **50**, 2180-2183.

RSC Author Templates - ChemDraw (CDX) - Graphical Abstracts

All text and images must be placed within the frame.

A series of donor-acceptor type of polymers based on thiophene-fused isoindigo were synthesized, among which the fully conjugated PTII-T showed well balanced ambipolar OFET performance.

