



# INORGANIC CHEMISTRY

FRONTIERS

Accepted Manuscript

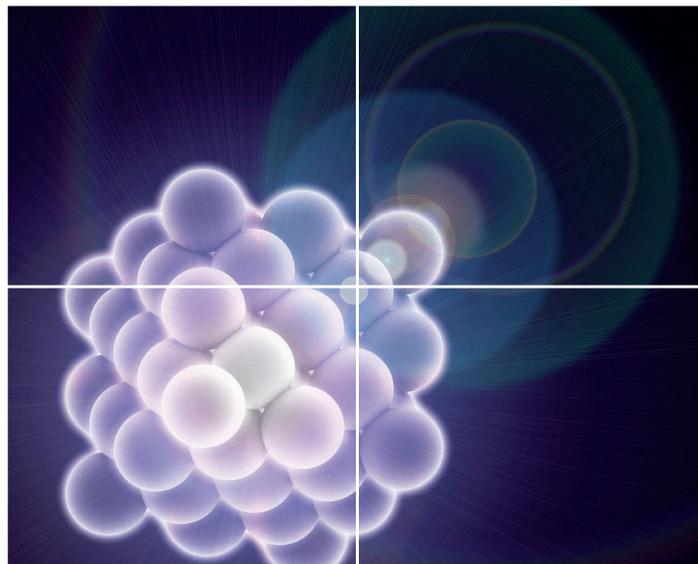

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

# Ultra-rapid microwave synthesis of $\text{Li}_{3-x-y}\text{M}_x\text{N}$ ( $M = \text{Co}, \text{Ni}$ and $\text{Cu}$ ) nitridometallates.

Nuria Tapia-Ruiz,<sup>a</sup> Josefa Vidal Laveda,<sup>a</sup> Ronald I. Smith,<sup>b</sup> Serena A. Corr<sup>a</sup> and Duncan H. Gregory<sup>a\*</sup>

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x

Single phase nitridometallates  $\text{Li}_{3-x-y}\text{M}_x\text{N}$  ( $0.05 \leq x \leq 0.27$ ;  $M = \text{Co}, \text{Ni}$  and  $\text{Cu}$ ) with potential use as negative electrodes in lithium ( $\text{Li}^+$ ) ion batteries have been synthesised in < 10 minutes *via* solid state reactions in a single mode cavity microwave reactor without an external susceptor. Reaction times are reduced by up to four orders of magnitude over previous synthetic methods. A combination of powder X-ray and neutron diffraction has provided detailed crystal structures of the vacancy-disordered nitrides. The electrochemical performance of these materials is comparable to that observed in conventionally-heated analogues.

## Introduction


Lithium nitridometallates,  $\text{Li}_{3-x-y}\text{M}_x\text{N}$  ( $M = \text{Co}, \text{Ni}, \text{Cu}$ ) have shown great promise as anodes in  $\text{Li}^+$  ion batteries, with competitive capacity and cycleability which is not hampered by significant volume changes on (de)lithiation. For example,  $\text{Li}_{2.6}\text{Co}_{0.4}\text{N}$  exhibits a capacity more than twice that of lithiated graphite, at *ca.* 900 mAh  $\text{g}^{-1}$ .<sup>1</sup> These  $\text{Li}_{3-x-y}\text{M}_x\text{N}$  materials have an  $\alpha$ - $\text{Li}_3\text{N}$ -type structure, where the transition metal is incorporated at the interplanar positions (Li(1) sites) and cationic  $\text{Li}^+$  vacancies are created in the  $[\text{Li}_2\text{N}]$  planes (Li(2) sites) (Fig. 1).<sup>2</sup> The vacancies provide a mechanism for the exceptionally high ionic conductivity observed in these materials and can be controlled by the transition metal substitution level and the synthesis conditions. Typically, high temperatures and long reaction times are required to make single phase materials (*e.g.*  $\text{Li}_{3-x-y}\text{Ni}_x\text{N}$  crystals require heating  $\text{Li}_3\text{N}$  and  $\text{Ni}$  powders at 853-983 K for 7 days).<sup>3</sup> Ideally sustainable energy materials, such as those employed as electrodes in batteries, should themselves be produced sustainably and energy-efficiently. Reducing processing times and temperatures is an important part of this process and microwave (MW) heating might therefore offer an energy-efficient alternative. MW synthesis of ternary and higher nitrides has so far been limited to five compounds; the anti-fluorites  $\text{Li}_3\text{FeN}_2$ ,  $\text{Li}_5\text{TiN}_3$  and  $\text{Li}_3\text{AlN}_2$ <sup>4</sup> and the nitridosilicates  $\text{Li}_2\text{SiN}_2$  and  $\text{LiSi}_2\text{N}_3$ .<sup>5</sup> The phase purity of the products in these cases was challenging to achieve. Here, we demonstrate that phase-pure  $\alpha$ - $\text{Li}_3\text{N}$ -type ternary nitrides with appreciable vacancy concentrations can be synthesised in minutes using a commercial benchtop MW reactor at 300 W.

Furthermore, we compare the electrochemical performance of the materials with their conventionally heated counterparts.

## Experimental

### Synthesis of $\text{Li}_{3-x-y}\text{M}_x\text{N}$ materials

All manipulations were performed in an  $\text{N}_2$ -filled glovebox (5 ppm  $\text{O}_2$ ; 10 ppm  $\text{H}_2\text{O}$ ). Transition metal powders ( $\text{Co}, \text{Ni}, \text{Cu}$ ; Laboratory BDH Reagent, 99 %) were reduced prior to reaction to remove surface metal oxides (under a flow of  $\text{H}_2/\text{N}_2$  (95:5 %) gas at 600 °C for 12 h). Molar ratios of  $\text{Li}_3\text{N}$  powder (Alfa Aesar, 300 mesh, 99.95 %; *ca.* 0.1 g) and  $\text{Co}, \text{Ni}$  or  $\text{Cu}$  metal powder were ground, pressed into pellets (13 mm diameter, 1-2 mm thickness) and placed in a nitrogen-filled silica tube (250 x 8 x 2 mm) sealed with a septum (Fig. 1a). Reactions were conducted in a single mode cavity (SMC) microwave reactor (CEM Discover®, CEM corporation, 300 W max. output, 2.45 GHz) at 300 W to yield black powders (Fig. 1b). Table 1 shows representative experiments performed (1-7) and the reaction conditions used for each.

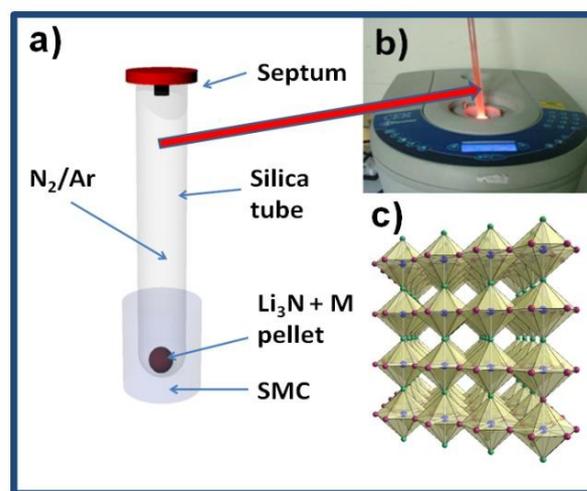

**Fig. 1** (a) Schematic experimental configuration for the SMC MW synthesis of lithium nitridometallates; (b) Image of reaction in progress; and (c) Polyhedral representation of  $\text{Li}_{3-x-y}\text{M}_x\text{N}$ , where  $M = \text{Co-Cu}$ . N (blue spheres); Li(2) (pink spheres); and Li(1) (green spheres).

**Table 1 Summary of reactions (1-7), including the experimental parameters and products identified by PXD.**

Sample	M	Li <sub>3</sub> N:M Molar ratio	Time (seconds)	Atm.	Products
1	Ni	1:0.10	210	N <sub>2</sub>	Li <sub>3-x-y</sub> Ni <sub>x</sub> N
2	Ni	1:0.22	180	N <sub>2</sub>	Li <sub>3-x-y</sub> Ni <sub>x</sub> N
3	Ni	1:0.29	260	N <sub>2</sub>	Li <sub>3-x-y</sub> Ni <sub>x</sub> N
4	Co	1:0.09	60	N <sub>2</sub>	Li <sub>3-x-y</sub> Co <sub>x</sub> N
5	Co	1:0.21	120	N <sub>2</sub>	Li <sub>3-x-y</sub> Co <sub>x</sub> N, Li <sub>2</sub> O
6	Co	1:0.30	420 + 420	Ar	Li <sub>3-x-y</sub> Co <sub>x</sub> N, Li <sub>2</sub> O
7	Cu	1:0.11	240	N <sub>2</sub>	Li <sub>3-x-y</sub> Cu <sub>x</sub> N, Li <sub>3</sub> N

### Characterisation

Powder X-ray diffraction (PXD) data from samples 1-7 were collected at room temperature with a PANalytical XPERT Pro MPD diffractometer using a Cu K $\alpha$  source. The diffraction data were collected in the range  $5 \leq 2\theta \leq 85^\circ$  with a  $0.0168^\circ 2\theta$  step size for 1-12 h, depending on sample quantity and quality. The air sensitive samples were ground into fine powders, which were placed in 0.5 mm diameter sealed glass capillaries for data collection. Experimental diffraction data were compared to powder patterns generated from data in the Inorganic Crystal Structure Database (ICSD)<sup>6</sup> using PowderCell 2.4.<sup>7</sup> X-ray data were indexed and unit cell parameters refined by least squares fitting using the CELREF software package.<sup>8</sup> Crystal structure refinements of compounds 1-7 were performed using time of flight (ToF) powder neutron diffraction (PND) data collected on the POLARIS diffractometer at the UK pulsed spallation neutron source ISIS (Rutherford Appleton Laboratory). For each sample, ~ 0.1 g of powder were loaded into a thin-walled cylindrical vanadium can and sealed with indium wire in an N<sub>2</sub>-filled glovebox. Normalised diffraction patterns from the detector banks centred at  $2\theta = 90^\circ$  and  $2\theta = 145^\circ$  were used to refine a structural model based on  $\alpha$ -Li<sub>3</sub>N (in hexagonal space group  $P6/mmm$ )<sup>2</sup> using the GSAS and EXPGUI software packages.<sup>9,10</sup> Starting lattice parameters were obtained from the PXD data and the initial transition metal occupancy of the interplanar Li(1) site was determined from the reaction stoichiometry.

Galvanostatic measurements at room temperature of samples were conducted over the voltage range of 0-1.4 V at a C/30 rate in a Swagelok-type cell using a BioLogic VSP potentiostat. The working electrode consisted of the active material, Li<sub>3-x-y</sub>M<sub>x</sub>N mixed with carbon black in a weight ratio of 8.5:1.5. In each case, the nitride-carbon mixture was mechanically mixed for 15 min using a Retsch MM 200 ball mill in an air-tight, stainless steel sealed container, packed under argon. 0.765 mg active material (3) and 1.190 mg active material (5) were used in the respective cells. A thin plate of lithium metal (Sigma Aldrich, 99.9% trace metal basis) was


used as a counter electrode. The electrolyte solution used was 1 M LiPF<sub>6</sub> dissolved in ethylene carbonate:diethyl carbonate (EC:DEC) in 1:1 molar ratio and a Whatman glass filter was used as the separator. Electrode preparation and (dis)assembly of the electrochemical cells were conducted in an Ar-filled glovebox (< 0.5 ppm O<sub>2</sub>; < 0.5 ppm H<sub>2</sub>O). Post-cycled electrodes were washed with THF and dried under vacuum for 1 h prior to XRD analysis.

### PND structure refinement

In each case, the background was fitted using the reciprocal interpolation function (number 8 within GSAS) employing 10-18 coefficients. The unit cell parameters, peak profile parameters, occupancies of the shared sites (Li(1) and M) and temperature factors were all then refined, followed by the application of an absorption correction. Peak shapes were modelled in each case using ToF profile function 3 (convolution of back-to-back exponentials with a pseudo-Voigt function). At this point, any extra phases such as V from the sample canister (samples 1-7; see Figure 3), Li<sub>2</sub>O (5 and 6) or Li<sub>3</sub>N (7) were introduced in the refinement. Lastly, anisotropic temperature factors were refined and the occupancy of the Li(2) site was allowed to vary freely to investigate the possibility of vacancies at this site. Constraints were applied to the fractional occupancies and thermal parameters of the disordered Li(1)/M site such that the total occupancy was unity and the thermal parameters were equal. The refinements were considered complete when convergence was achieved, all the variables were stable and the R-values minimised.

### Results and Discussion


Fig. 2 shows a typical X-ray diffraction pattern of the as-formed products after MW irradiation (for sample 2). Powder X-ray diffraction data from samples 1-7 revealed phases that were isostructural with  $\alpha$ -Li<sub>3</sub>N, with reflections shifted in  $2\theta$  when compared to the calculated pattern of Li<sub>3</sub>N ( $P6/mmm$ ,  $a = 3.648(1) \text{ \AA}$  and  $c = 3.875(1) \text{ \AA}$ ).<sup>6</sup>

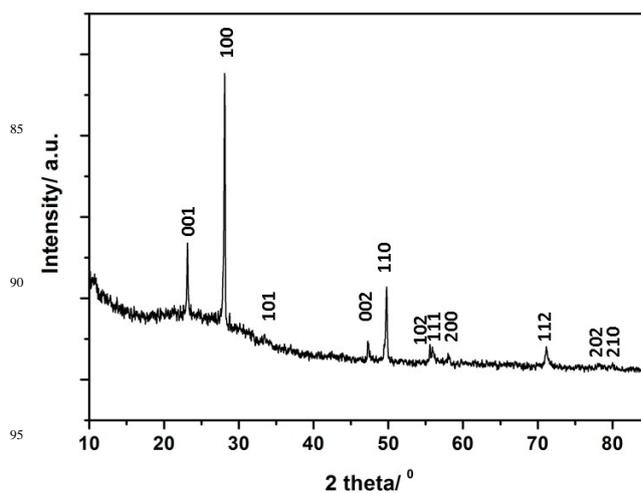

**Fig. 2 Typical XRD pattern of a Li<sub>3-x-y</sub>M<sub>x</sub>N sample (M= Co-Cu) synthesised by MW methods (sample 2 is shown). Indices for the expected reflections are indicated.**

The absence of transition metal reagents in the final PXD patterns of **1-7** indicate full conversion of the initial mixtures to final products (Table 1). The oxidation products of  $\text{Li}_3\text{N}$  or  $\text{Li}$  ( $\text{Li}_2\text{O}$ ) found in samples **5** and **6** might originate either from the starting materials and/or air exposure during handling. Lattice parameters of samples (**1-7**) were indexed in the hexagonal space group  $P6/mmm$  (ESI; Table S1). Samples **1-6** showed similar trends in cell parameters vs. transition metal content to those previously reported by Juza *et al.*<sup>11</sup> a slight increase in the  $a$  parameter and a steeper linear decrease in the  $c$  parameter respectively with increasing metal substitution,  $x$ . Several authors have observed a similar dependence of the lattice parameters on  $x$ .<sup>12,13</sup>

Selected room temperature crystallographic information from the MW-synthesised lithium ternary nitrides containing Ni (**1-3**), Co (**4-6**) and Cu (**7**) following Rietveld refinement is shown in Table 2 (with additional information in the ESI). An example fit to the data is shown in Fig. 3. Despite the small sample volumes used, good fits were obtained and the lattice parameters determined from PND data were in good agreement with those obtained from PXD (ESI; Table S1). Fig. 4 plots the lattice parameters against the transition metal stoichiometry,  $x$ , obtained from the refinements against PND data and compares these with those from the literature.<sup>11</sup> For nitridonickelates, our data often reveal larger  $c$  parameters than those reported previously from PXD data, whereas for nitridocobaltates the sets of data are in very close agreement.<sup>11</sup> The  $a$  parameter vs.  $x$  relationship closely follows the previously reported trend.

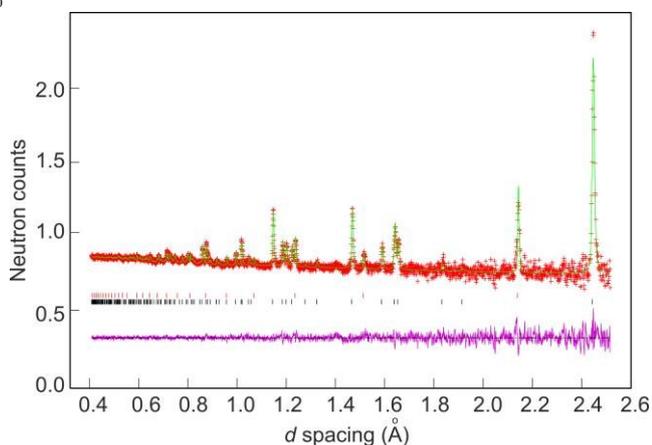

**Fig. 3** Rietveld fit against PND data collected at room temperature from sample **4** in the  $2\theta = 145^\circ$  (backscattering) detector bank. Observed data points are shown in red, calculated profile in green and the difference (obs-calc) profile in pink. Black and red vertical tick marks indicate reflections from the  $\text{Li}_{3-x-y}\text{Co}_x\text{N}$  phase and the vanadium sample can respectively.

The variations in the  $a$  and  $c$  parameters with  $x$  are directly related to the Li(2)-N and Li(1)/M)-N distances respectively (Table 2). The reduction in Li(1)/M)-N bond lengths

compared to the equivalent distance in  $\text{Li}_3\text{N}$  ( $1.9368(1) \text{ \AA}$ )<sup>2</sup> is attributed to an increase in the covalency of the Li(1)/M)-N bond due to the presence of the transition metal, which increases the  $\pi$  character of the bond.<sup>14,15</sup>

Moreover, a slight increase in the interplanar Li(2)-N bond length as the level of dopant increases was also observed. The  $a$  parameter (and Li(2)-N distance) has been directly related to the existence of  $\text{Li}^+$  vacancies in these compounds. The introduction of  $\text{Li}^+$  vacancies has been related to an increase in aliovalent metal substitution level and also correlates to reaction temperature and time.<sup>3</sup> Importantly, Rietveld refinement against PND data was able to confirm the presence of Li(2) vacancies ( $y$ ) in the majority of samples prepared using microwaves (Table 2). Negligible Li(2) vacancies were detected however in the nitridonickelate with the lowest metal content,  $x \sim 0.07$  (**1**); refining the Li(2) occupancy caused the refinement to diverge. This was also the case for the copper-containing sample  $\text{Li}_{2.95}\text{Cu}_{0.05}\text{N}$  (**7**). As  $x$  increased, however, an increase in  $y$  values was observed. Hence, for example, for  $\text{Li}_{3-x-y}\text{Ni}_x\text{N}$ , where  $x \sim 0.22$  (**2**) and  $x \sim 0.27$  (**3**),  $y$  values of 0.24(4) and 0.36(4) were obtained, leading to compounds of stoichiometry  $\text{Li}_{2.54}\text{Ni}_{0.22}\text{N}$  and  $\text{Li}_{2.36}\text{Ni}_{0.27}\text{N}$ , respectively. Although the level of vacancies found in **2** and **3** (*ca.* 10 %) was considerably lower than that observed in some other  $\text{Li}_3\text{N}$ -type nitridonickelates (typically  $\geq 30\%$  for  $x \sim 0.8$ ),<sup>2</sup> the  $y$  values are commensurate with the lower transition metal content in **1-3**.

Similarly, for the lithium cobalt nitrides (**4-6**) a dependence of  $y$  on  $x$  was evident; the (unconstrained) refined Li(2) occupancy decreased as the Co occupancy at the Li(1) site increased. For example, for  $x = 0.1$ , there are approximately 3 % vacancies at the Li(2) site, which then increases to 20 % when the amount of metal substituted increases to  $x = 0.21$ . Accordingly, the PND data indicate stoichiometries of  $\text{Li}_{2.84}\text{Co}_{0.10}\text{N}$  (**4**),  $\text{Li}_{2.45}\text{Co}_{0.17}\text{N}$  (**5**) and  $\text{Li}_{2.41}\text{Co}_{0.21}\text{N}$  (**6**) for our lithium cobalt nitride compounds. Although the cobalt contents are lower here, the vacancy levels of **5** and **6** are in line with those reported by Takeda *et al.* from electrochemical Li extraction of  $\text{Li}_{2.6}\text{Co}_{0.4}\text{N}$  (*ca.* 15 %)<sup>16</sup> and also by Gordon *et al.*, who identified Li(2) vacancy levels above 20 % for  $\text{Li}_{3-x-y}\text{Co}_x\text{N}$  with  $0.53 \leq x \leq 0.6$ .<sup>17</sup>

Assuming oxidation states of +1 and -3 for Li and N respectively, nominal transition metal oxidation states of +1 (**1**), +2.1 (**2**), and +2.4 (**3**); and +1.6 (**4**), +3.2 (**5**), +2.8 (**6**) and +1 (**7**) could be assigned. Given the elevated levels of vacancies in samples of higher  $x$  (such as **5** and **6**) and previously reported correlations between  $y$  and reaction temperature, one might deduce that the temperatures achieved in these relatively low power MW reactions are in excess of 873 K. Hence as a result and as for similar nitrides prepared by conventional heating,<sup>2,15</sup> in most cases transition metal substitution is essentially aliovalent. The presence of higher oxidation states for the metals in **5** and **6** might be rationalised in terms of the redox chemistry of Co.


Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

## ARTICLE TYPE

**Table 2.** Selected data for samples 1-7 obtained from refinements against ToF PND data from  $2\theta = 90^\circ$  and  $2\theta = 145^\circ$  banks.

Sample	1	2	3	4	5	6	7
Stoichiometry	$\text{Li}_{2.93}\text{Ni}_{0.07}\text{N}$	$\text{Li}_{2.54}\text{Ni}_{0.22}\text{N}$	$\text{Li}_{2.36}\text{Ni}_{0.27}\text{N}$	$\text{Li}_{2.84}\text{Co}_{0.10}\text{N}$	$\text{Li}_{2.45}\text{Co}_{0.17}\text{N}$	$\text{Li}_{2.41}\text{Co}_{0.21}\text{N}$	$\text{Li}_{2.95}\text{Cu}_{0.05}\text{N}$
Crystal system	Hexagonal						
Space group	$P6/mmm$						
Z	1						
Density, $\rho/\text{g cm}^{-3}$	1.426	1.673	1.732	1.513	1.559	1.588	1.882
$a/\text{\AA}$	3.6675(2)	3.6860(2)	3.6950(2)	3.6679(1)	3.6800(2)	3.6977(2)	3.6675(2)
$c/\text{\AA}$	3.8383(4)	3.7700(4)	3.7390(4)	3.8305(2)	3.7931(3)	3.7576(3)	3.7983(2)
$V/\text{\AA}^3$	44.712(6)	44.360(6)	44.210(6)	44.629(4)	44.486(5)	44.496(4)	44.245(4)
M occupancy (x)	0.069(9)	0.221(2)	0.267(3)	0.102(1)	0.171(2)	0.210(3)	0.051(2)
Li(2) occupancy	1	0.88(4)	0.82(4)	0.97(3)	0.811(4)	0.81(2)	1
(Li(1)/M) – N / $\text{\AA}$	1.9190(2)	1.8850(2)	1.8697(2)	1.9152(1)	1.8965(2)	1.8788(1)	1.9053(2)
Li(2) – N / $\text{\AA}$	2.1176(1)	2.1282(1)	2.13360(9)	2.11776(8)	2.1244(1)	2.13499(9)	2.11532(9)
Observations	7261	7364	7428	7728	7326	6949	7670
Parameters	57	49	61	56	59	46	56
$R_{\text{wp}}$	0.0136	0.0181	0.0175	0.0147	0.0126	0.0186	0.0136
$R_p$	0.0245	0.0313	0.0302	0.0323	0.0192	0.328	0.0293

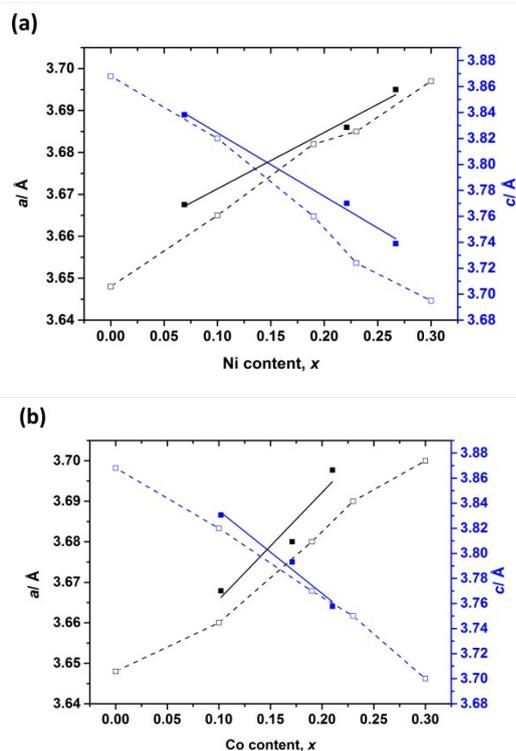

**Fig. 4** Variations of unit cell parameters with varying (a) Ni (1-3) and (b) Co (4-6) substitution levels ( $x$ ). Filled squares show refined values from our PND data. Empty squares show data from reference 11. Trend lines serve as a guide to the eye.

10

Indeed, during electrochemical lithium extraction of  $\text{Li}_{2.6}\text{Co}_{0.4}\text{N}$ , the nominal Co oxidation reaches a maximum value of *ca.* +5, assuming that only cobalt oxidation charge compensates for the loss of 1.6 Li ions. In fact, given the unrealistic oxidation state for cobalt in the delithiated compounds, a mechanism for charge balance involving also nitrogen oxidation has been proposed previously. Such a hypothesis is supported experimentally by electron energy-loss spectroscopy (EELS) in  $\text{Li}_{2.6}\text{Co}_{0.4}\text{N}$ ; both cobalt and nitrogen are apparently oxidised when vacancies form during Li extraction.<sup>18</sup>

An alternative charge compensating mechanism might invoke the presence of hydrogen (as  $\text{H}^{\delta+}$ ) bonded to nitrogen (creating partial imide substitution), although there is no experimental evidence to corroborate this for **1-6**, (*e.g.* typical N-H bands from the  $\text{NH}^{2-}$  group were not observed in either the Raman or IR spectra of the as-formed materials). Imide substitution (N-H bond formation) has been previously suggested as one means by which the necessary defect structure is created to enable fast lithium ion conductivity in  $\text{Li}_3\text{N}$  itself. The presence of naturally abundant hydrogen at implied concentrations approaching 20 % could not be detected in our PND measurements either from negative peaks in difference Fourier maps (given its scattering length of  $b = -3.75$  fm) or from an increased background (arising from its large incoherent scattering cross section).<sup>19</sup>

The MW syntheses described in this work are possible due to the ability of the starting materials ( $\text{Li}_3\text{N}$  and metal powders) to absorb microwave energy and convert this to heat. As electrical conductors, the finely divided metal powder starting materials provide heat (*i.e.* via Ohmic

heating) to the reaction mixture<sup>20,21,22</sup> and the inherent ionic conductivity<sup>23</sup> and semiconducting behaviour<sup>24</sup> of Li<sub>3</sub>N would be expected to produce heat *via* mixed conduction mechanisms in a microwave field.<sup>25</sup> In fact, it is well established that microwaves couple directly to charge carriers, accelerating the reactions in which good ionic conductors and semiconductors are employed.<sup>26</sup> The ability of other semiconductors such as SiC to generate heat due to matter-radiation interaction has been exploited for example, in use as microwave susceptors (*e.g.* PHEs (passive heating elements)).<sup>27</sup> Furthermore, the outstanding microwave susceptibility of ionic liquids, for example, is attributed to their high ionic conductivity (and polarizability).<sup>28,29</sup> The properties of the metal and nitride starting materials are thus important in being able to design a microwave reaction *without an external susceptor* (such as carbon, typically) and thus minimise possible contamination of products.

Following a few seconds of irradiation, a purple plasma was observed near the reagents (Fig. 2b). Characteristic purple nitrogen plasmas induced by arc discharge were also observed at 10<sup>-2</sup> Pa by Aoki *et al.* and other coloured plasmas are common during microwave processing under gaseous environments (*e.g.* sulfur produces a blue plasma).<sup>30,31</sup> We attribute the onset of this plasma formation to an increase in temperature and a variation in the N<sub>2</sub> partial pressure inside the nitrogen-filled reaction vessel caused by the decomposition of Li<sub>3</sub>N, which occurs at ~ 800 °C (ΔH = -171.3 kJ mol<sup>-1</sup>) (Equation 1).<sup>32,33</sup>



In our experiments N<sub>2</sub> plasmas were more prevalent (and of longer duration) when reactions were performed in a gaseous nitrogen atmosphere. In fact, it was observed that when the reactions were conducted in an argon atmosphere, longer reaction times were required (6). This suggests that plasma formation (and Li<sub>3</sub>N decomposition) probably play a key role in the reaction proceeding. The purple N<sub>2</sub> plasma was followed on most occasions by yellow/orange flashes (ESI; Fig. S1) that were related to Li evaporation, which occurs at *ca.* 1300 °C.<sup>34</sup> Similar observations were made in the previous work by Houmes and zur Loye<sup>4</sup> and in the case of reactions to form Li<sub>3-x-y</sub>MN from Li<sub>3</sub>N and M, Li is an expected byproduct. The ability to maintain homogeneity and phase purity of products in our reactions depends upon the use of the well-defined electric field distribution from the single mode cavity reactor and the ability to limit reaction temperature (and gradients) through a lower applied power than is typical with a multimode cavity (MMC) domestic microwave oven.

Under the specific conditions employed in our synthesis experiments, the maximum metal loading of the MW-ternary compounds was found to be lower ( $x = 0.27$  (3),  $x = 0.21$  (6) and  $x < 0.1$  (7), for M = Ni, Co and Cu respectively) than some of those in the Li<sub>3-x-y</sub>M<sub>x</sub>N compounds previously reported in the literature.<sup>3,15,17</sup> Difficulties in achieving higher transition metal doped samples might be rationalised in terms of the high electric conductivity of the metals. Within the electric field of the MW, the finely divided metal powders are

anticipated to generate significant heat (Co powders can achieve 700 °C after 3 minutes of MW exposure using a MMC at 1 kW).<sup>35</sup> Li<sub>3</sub>N and transition metal substituted derivatives typically decompose at *ca.* 750 °C and so increasing the metal content in the reactant mixtures might be expected to yield reaction temperatures in excess of this decomposition limit, leading to further evaporation of lithium. Accordingly, this might contribute to the lower substitution limits obtained in these MW reactions when using copper, which has an electrical conductivity *ca.* four times higher than Ni or Co [ $5.96 \times 10^7 \text{ S m}^{-1}$  (20 °C)].<sup>36</sup> Higher substitution levels might be achieved by adding additional Li<sub>3</sub>N to initial products, regrinding and reheating, but a more satisfactory alternative would be to modify the design of the cavity and/or utilise alternative reactants that do not couple as strongly to the microwave field.

The electrochemical behaviour of these as-synthesised nitridometallate samples was studied *via* galvanostatic measurements (See ESI; Figs. S2-S5). The nickel-nitride sample with the highest level of Li vacancies determined by PND (3) reached a discharge capacity of 458 mAh g<sup>-1</sup>. This capacity however, was reduced to 175 mAh g<sup>-1</sup> by the 5<sup>th</sup> cycle (Fig. S3). Similarly, the cobalt-nitride sample (5) showed a capacity of 642 mAh g<sup>-1</sup> that faded to 95 mAh g<sup>-1</sup> after the 5<sup>th</sup> cycle (Fig S5). This capacity fade was irreversible and noted up to 50 cycles for both compounds. The insertion of Li<sup>+</sup> in both materials is most likely made possible by the presence of cation vacancies in the Li<sub>3-x</sub>M<sub>x</sub>N structure and confirms our results obtained from neutron data and the previous reports in the literature.<sup>2</sup> The charging curves during the first cycle for samples 3 and 5 show two well defined segments as previously observed in the literature;<sup>16,18,37,38</sup> first, the voltage gradually increases until *ca.* 1.2 V ( $x \sim 0.3$  Li deintercalated) (3) and 1.1 V ( $x \sim 0.3$  Li deintercalated) (5) and then plateaux at the above mentioned potentials followed. These data show that this process clearly affects the following charge-discharge cycles, which in turn, correspond to single-phase mechanisms. Nevertheless, the formation of these plateaux during the first charging process accounts for the initial high capacity in these materials. These features are quite representative of these type of materials and hence agree with previous reports in the literature.<sup>16,18,37,38</sup> Further electrochemical tests to optimise the processing of the electrode are underway.

## Conclusions

Li<sub>3-x-y</sub>M<sub>x</sub>N (M = Co, Ni and Cu) materials, which find potential applications in lithium ion batteries, have been synthesised in a single mode cavity MW reactor on unprecedented timescales, orders of magnitude faster than previously documented. PXD and ToF PND data demonstrated that these syntheses can yield single phase materials without the need for a microwave susceptor. Diffraction data also confirmed that the nitridometallates resemble those prepared by conventional heating in terms of their stoichiometry and defect structure. Li<sup>+</sup> ion vacancies are

created *via* the aliovalent substitution of  $M^{n+}$  ( $n > 1$ ) for  $Li^+$ . These experiments demonstrate both that complex nitrides and lithium-containing electrode materials can be synthesised as phase-pure compounds by energy-efficient methods; appropriate reactor and experiment design are key factors. Furthermore, we have corroborated by means of electrochemical insertion that  $Li^+$  vacancies were present and that these materials can (de)intercalate lithium in the voltage range 0-1.4 V at C/30 rate with initial discharge capacities of 458 mAh  $g^{-1}$  and 642 mAh  $g^{-1}$  for the samples with higher metal doping levels (and Li-vacancies); *i.e.*  $Li_{2.36}Ni_{0.27}N$  and  $Li_{2.41}Co_{0.21}N$ . It should thus be possible to extend the methodology to the sustainable synthesis and processing of a wide range of other important battery materials.

## Acknowledgements

DHG thanks ScotCHEM for a SPIRIT PhD studentship for NTR and STFC for provision of neutron beam time at ISIS. SAC gratefully acknowledges funding support from the EPSRC (EP/K029290/1) and the allocation of a PhD scholarship from the University of Glasgow.

## Notes and references

<sup>25</sup> <sup>a</sup> WestCHEM, School of Chemistry, University of Glasgow, Glasgow G82 5EZ, UK, . Fax: +44(0)1413304888; Tel:+44(0)1413306438; E-mail: [Duncan.Gregory@Glasgow.ac.uk](mailto:Duncan.Gregory@Glasgow.ac.uk).

<sup>b</sup> ISIS Facility, Rutherford Appleton Laboratory, Harwell Oxford, Didcot OX11 0QX, UK.

<sup>30</sup> † Electronic Supplementary Information (ESI) available: Refinement procedures, lattice parameters from XRD, thermal displacement parameters, structure plot, refinement profile plots, schematic and photographs of the synthesis set-up.

- 1 (a) T. Shodai, S. Okada, S. Tobishima and J. Yamaki, *J. Power Sources*, 1997, **68**, 515; (b) Y. Takeda, M. Nishijima, M. Yamahata, K. Takeda, N. Imanishi and O. Yamamoto, *Solid State Ionics*, 2000, **130**, 61
- 2 D. H. Gregory, P. M. O' Meara, A. G. Gordon, J. P. Hodges, S. Short and J. D. Jorgensen, *Chem. Mater.*, 2002, **14**, 2063.
- 3 Z. Stoeva, R. I. Smith and D. H. Gregory, *Chem. Mater.*, 2006, **18**, 313.
- 4 J. D. Houmes and H.-C. zur Loye, *J. Solid State Chem.*, 1997, **130**, 266.
- 5 A. J. Anderson, R. G. Blair, S. M. Hick and R. B. Kaner, *J. Mater. Chem.*, 2006, **16**, 1318.
- 6 A. Rabenau and H. Schulz, *J. Less-Comm. Met.*, 1976, **50**, 155.
- 7 G. Nolze and W. Kraus, *Powder Diffraction*, 1998, **13**, 256.
- 8 J. Laugier and B. Bochu, Laboratoire des Matériaux et du Génie Physique de L' Ecole Supérieure de Physique de Grenoble; <http://www.inpg.fr/LMGP>, accessed on 28/04/13.
- 9 A. C. Larson and R. B. Von Dreele, "The General Structure Analysis System", Los Alamos National Laboratories, Los Alamos, NM, 2000.
- 10 B. H. Toby, *J. Appl. Crystallogr.*, 2001, **34**, 210.
- 11 W. Sachsze and R. Juza, *Z. Anorg. Chem.*, 1949, **259**, 278.
- 12 R. Niewa, Z.-L. Huang, W. Schnelle, Z. Hu and R. Kniep, *Z. Anorg. Allg. Chem.*, 2003, **629**, 1778.
- 13 Z. Stoeva, R. Gomez, D. H. Gregory, G. B. Hix and J. J. Titman, *Dalton Trans.*, 2004, **3093**.
- 14 A. G. Gordon, D. H. Gregory, A. J. Blake, D. P. Weston and M. O. Jones, *Int. J. Inorg. Mater.*, 2001, **3**, 973.
- 15 M. G. Barker, A. J. Blake, D. H. Gregory, D. J. Siddons, S. E. Smith, P. P. Edwards and T. A. Hamor, *Chem. Comm.*, 1999, 1187.

- 16 Y. Takeda, M. Nishijima, M. Yamahata, K. Takeda, N. Imanishi and O. Yamamoto, *Solid State Ionics*, 1996, **86**, 785.
- 17 A. G. Gordon, R. I. Smith, C. Wilson, Z. Stoeva and D. H. Gregory, *Chem. Comm.*, 2004, 2812.
- 18 S. Suzuki, T. Shodai and J. Yamaki, *J. Phys. Chem. Solid.*, 1998, **59**, 331.
- 19 V. F. Sears, *Neutron News*, 1992, **3**, 26.
- 20 A. G. Whittaker and D. M. Mingos, *J. Chem. Soc. Dalton Trans.*, 1995, 2073.
- 21 R. Roy, D. Agrawal, J. Cheng and S. Gedevarishvili, *Nature*, 1999, **399**, 668
- 22 H. J. Kitchen, S. R. Vallance, J. L. Kennedy, N. Tapia-Ruiz, L. Carassiti, A. Harrison, A. G. Whittaker, T. D. Drysdale, S. W. Kingman and D. H. Gregory, *Chem. Rev.* 2014, **114**, 1170.
- 23 B. A. Boukamp and R. A. Huggins, *Mater. Res. Bull.*, 1978, **13**, 23.
- 24 D. H. Gregory, *J. Mater. Chem.*, 2008, **18**, 2321.
- 25 N. Tapia-Ruiz, N. Sorbie, N. Vaché, T. K. A. Hoang and D. H. Gregory, *Materials*, 2013, **6**, 5410.
- 26 A. Harrison, R. Ibberson, G. Robb, G. Whittaker, C. Wilson and D. Youngson, *Faraday Discuss.*, 2002, **122**, 363.
- 27 J. M. Kresner and C. O. Kappe, *J. Org. Chem.*, 2006, **71**, 4651.
- 28 S. Mallakpour and A. Zadehnazari, *Adv. Polym. Tech.*, 2013, **32**, 21333.
- 29 T. E. Ashton, J. Vidal Laveda, D. A. MacLaren, P. J. Baker, A. Porch, M. O. Jones and S. A. Corr, *J. Mater. Chem. A*, 2014, **2**, 6238.
- 30 R. Kniep, *Angew. Chem. Int. Ed.*, 1993, **32**, 1411.
- 31 H. Aoki, K. Takahashi, K. Takaki, Member, IEEE and T. Fujiwara, *IEEE T. Plasma Sci.*, 2011, **39**, 2912.
- 32 P. F. Adams, P. Hubberstey and R. J. Pulham, *J. Less-Comm. Met.*, 1975, **42**, 1.
- 33 H. Kimura, M. Asano and K. Kubo, *J. Nucl. Mater.*, 1980, **91**, 200.
- 34 R. C. Weast and M. J. Astle, *Handbook of Chemistry and Physics*, 61<sup>st</sup> Ed., 1980, CRC Press, Inc.
- 35 K. J. Rao, B. Vaidhyanathan, M. Ganguli and P. A. Ramakrishnan, *Chem. Mater.*, 1999, **11**, 882.
- 36 D. Griffiths, *Introduction to Electrostatics* (3<sup>rd</sup> Edition) Upper Saddle River, New Jersey, Prentice Hall, p. 286, ISBN 0-13-805326.
- 37 M. Nishijima, T. Kagohashi, Y. Takeda, M. Imanishi and O. Yamamoto, *J. Power Sources*, 1997, **68**, 510.
- 38 T. Y. Kim, M. G. Kim, J. M. Lee, T. Kang and H.-J. Sohn, *Electrochem. and Solid-State Lett.*, 2002, **5**, A103.