

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Novel Photolabile Crosslinkers Based on *O*-Acyloxime Moiety

Kanji Suyama^{1*} and Hideki Tachi²

¹Faculty of Liberal Arts and Sciences, Osaka Prefecture University, 1-1, Gakuen-Cho, Naka-Ku, Sakai, Osaka 599-8531, Japan, and ²Textile & Polymer Section, Technology Research Institute of Osaka Prefecture, 7-1 Ayumino-2, Izumi, Osaka 594-1157, Japan,

Abstract:

Controlled decrosslinking is an attractive technique in the fields of functional materials and polymer recycling. Especially, photo-triggered decrosslinking is advantageous for easy remote activation and spatiotemporal control. However, only a few photolabile units have been used for the cleavage in crosslinkers. Herein, 1,4-diacetylbenzene 1,4-bis(*O*-methacryloyl)dioxime and 1,3,5-triacetylbenzene 1,3,5-tris(*O*-methacryloyl)trioxime are proposed as novel crosslinkers. They have a benzene ring bearing two or three arms in which *O*-acyloxime moiety is introduced as a novel type of photolabile unit. These crosslinkers were prepared from aromatic ketones in two steps. Photopolymerization of methyl acrylate and the crosslinkers was performed using diphenyl(2,4,6-trimethylbenzoyl)phosphine oxide as a photoinitiator and UV light above 310 nm. Obtained polymer films were crosslinked and insoluble in tetrahydrofuran (THF). These films were further irradiated at 254 nm of light. The photolysis of *O*-acyloxime units in these crosslinkers were confirmed by UV and IR spectral measurements. The precedence of decrosslinking on 254 nm irradiation was evidenced by the decrease in thickness of the films after soaking in THF. Soluble fraction of the decrosslinked polymers were subjected to size exclusion chromatography, and their molecular weights were found to be similar to that obtained by photopolymerized film in the absence of the crosslinker. These results demonstrated that the proposed compounds are potential candidates for novel photolabile crosslinkers.

Keywords: crosslinking, degradation, photochemistry, networks, recycling

Introduction

Crosslinked polymers show excellent mechanical strength as well as thermal and chemical stability compared to linear polymers. Therefore, decrosslinking can give rise to drastic changes in many properties of the crosslinked polymers. In this regard, the incorporation of the units that leads to the decrosslinking on demand is an attractive design

for functional materials. Furthermore, decrosslinking technology provides an important process in the field of polymer recycling.¹

Several stimuli such as heat,²⁻⁶ pressure,⁷ electrical voltage,⁸ ultrasonic,⁹ the addition of acids,¹⁰⁻¹² bases,^{3,12-14} and other reagents,^{15,16} and light^{3,7,17-34} have been applied to trigger the decrosslinking. Among them, photochemical process is appealing because of its easy remote activation and spatiotemporal control. These features have been applied in the fields of nanoimprint lithography,^{17,18} drug delivery,¹⁹ and self-healing materials.²⁰

Photo-triggered decrosslinking can be accomplished by incorporating photolabile units into main-chain or linker units. Although indirect methods which utilize photo-triggered release of catalysts such as strong acids have been proposed recently,^{17,18,21-25} the most versatile approach is to design crosslinkers bearing both polymerizing and photolabile units and to polymerize them. However, in most cases, the photolabile units used in the crosslinkers were limited to *o*-nitrobenzyl-²⁶⁻³² and coumarine-based^{33,34} families. Especially, crosslinkers bearing three or higher polymerizing groups are rare.^{33,34}

Recently, we have proposed 1,4-diacetylbenzene 1,4-bis(*O*-methacryloyl)dioxime (DBzM) and 1,3,5-triacetylbenzene 1,3,5-tris(*O*-methacryloyl)trioxime (TBzM) as novel photolabile crosslinkers.³⁵ The chemical structures of these crosslinkers have *O*-acyloxime and methacryl units as photolabile and polymerizing units, respectively, as shown in Fig. 1.


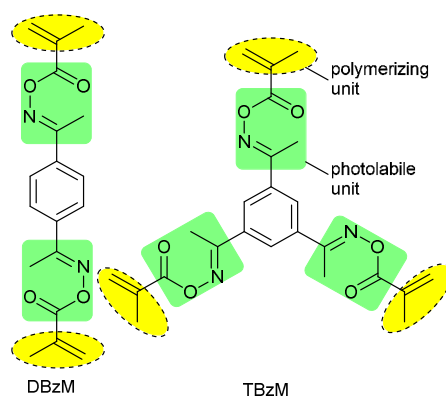


Fig. 1. *O*-Acyloxime-based crosslinkers.

These crosslinkers could be derived from starting ketones in two steps. The short synthetic route is advantageous to easy preparation of multifunctional monomers. Also, *O*-acyloxime moieties show good photo-reactivity and thermal stability. For example, quantum yield of photolysis at 254 nm and onset thermal decomposition temperature of 1,3,5-triacetylbenzene 1,3,5-tris(phenylacetyl)trioxime were 0.41 and 208 °C, respectively.³⁶

As polymerizing units, we used methacrylates in this study. It has already found that

methacrylates can serve six-membered transition state due to the presence of β -hydrogen, and finally turned into vinylidene double bond on main-chains and an imine as shown in Scheme 1(i).^{37,38} In case of acrylates, the coupling of C radical and imino radical is a major reaction to form a ketimine which is hydrolyzed into an amine and a ketone as Scheme 1(ii). We have been studied the photochemical changes of various *O*-acyloximes in polymer matrixes and found that the hydrolysis of ketimine proceeded immediately in polymer films with 0.3 – 0.4 μm thickness.^{36,39,40} Because we used thicker films in this study, we avoided acrylates that require the hydrolysis process for complete cleavage.

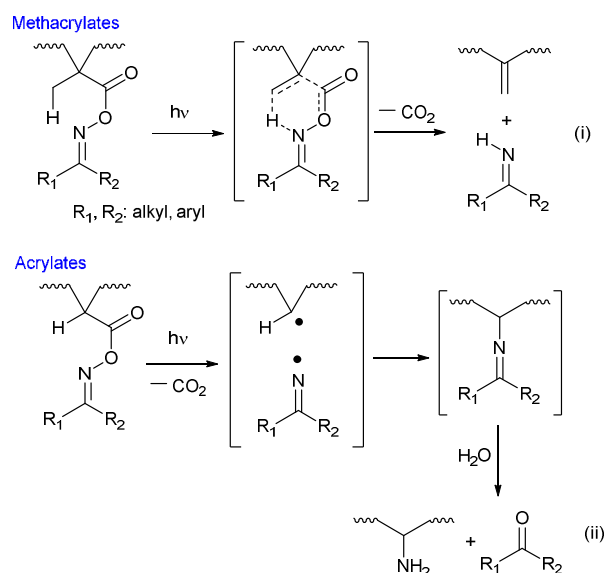

Scheme 1. Photoreactions of pendant *O*-acyloxime moieties.

In this article, we report the photochemical behaviors of DBzM and TBzM in detail, especially comparing with that of polymers without the crosslinkers. We also analyzed the photodegradation process with spectroscopic and molecular weight measurements.

Experimental

Instruments

Simultaneous thermogravimetry / differential thermal analysis (TG/DTA) measurements were carried out using a Seiko Instruments TG/DTA320 with a heating rate of 10 K / min under N_2 . Mass spectra were taken with a Thermo Scientific Q Exactive by using positive electrospray ionization (ESI).

NMR, IR, and UV spectra were recorded by Jeol JNM-ECX400, Jasco FT-IR4200, and

Jasco V530 spectrometers, respectively. Elemental analyses were carried out by a Perkin Elmer 2400 Elemental Analyzer.

Number (Mn) and weight (Mw) average molecular weights of polymers were obtained by size exclusion chromatography (SEC) using a system composed of Tosoh two sequential TSKgel H_{XL} columns, a Tosoh DP8020 pump, and a Viscotek TriSEC 302W detector with THF eluent at 40 °C. In this experiment, the molecular weights were estimated using refractometer detector calibrated with polystyrene standards. Sample solutions were filtered with 0.2 µm pore sized PTFE disposable filters.

The formulations for photopolymerization were treated with a Shibata glass digit dispenser (Tokyo, Japan). Thickness of films on substrates was measured by a Mitsutoyo SJ210 contact profilometer (Kawasaki, Japan) using a 5 µm^ϕ tip stylus with 4 mN measuring force.

Heating was performed on a Koike Precision Instruments KPI HP-19U300 hot plate (Itami, Hyogo, Japan).

Light sources for photopolymerization and photodegradation were performed with a Hayashi Watch-Works LA410 Xe-Hg lamp (Tokyo, Japan) and an Ushio ULO-6DQ low pressure lamp, respectively. Their light intensities were measured by an Orc UV-M03 illuminometer (Tokyo, Japan).

Materials

Methyl acrylate (MA) was purchased from Nacalai Tesque (Kyoto, Japan) and filtered with activated neutral alumina (Aldrich) to remove polymerization inhibitors. Diphenyl(2,4,6-trimethylbenzoyl)phosphine oxide (TPO) (Tokyo Chemical Industry) was recrystallized from hexane. Tetrahydrofuran (THF) was distilled before use. 1,3,5-Triacetylbenzene trioxime was prepared as described in literature.⁴¹

Poly(ethylene terephthalate) (PET) films for covering the formulation was Toyobo Lumilar whose thickness was 50 µm. The transmittance at 313 and 365 nm were 7 and 79 %, respectively. Polyethylene (PE) films with 80 µm thick were used for the measurement of IR changes.

1,4-Diacetylbenzene dioxime

In a flask, 16.2 g (10.0 mmol) of 1,4-diacetylbenzene, 16.4 g (236 mmol) of hydroxylamine hydrochloride, 70 mL of methanol, and 10 mL of water were refluxed for 1 h. After cooling, the mixture was filtered to afford 17.6 g of ivory fine powder. From the

filtrate, 2.33 g of powder was recovered when concentrated to ca. 30 mL. IR spectra of both powders showed a small C=O stretching band at 1680 cm^{-1} . Thus, both powders were put together in a flask with 70 mL of methanol and 3.0 mL of hydroxylamine solution (Wako, 50 %) and refluxed for 30 min. After cooling and filtration, recovered powder was refluxed for 1 h with 60 mL of ethanol and 3.0 mL of the hydroxylamine solution. Finally, 17.6 g (91.5 mmol) of colorless fine powder was obtained. Yield: 91.5 % ^1H NMR (DMSO-d_6): 2.14 (6H, s, CH_3), 7.62 (4H, s, aromatic), 11.24 (2H, s, OH). ^{13}C NMR (DMSO-d_6): 11.93, 126.02, 137.53, 153.15. IR (KBr): 2600-3500 cm^{-1} (OH).

DBzM

In a 200 mL of two-necked flask, 5.77 g (30.0 mmol) of 1,4-diacetylbenzene dioxime and 15.5 mL (112 mmol) of triethylamine were dissolved in 150 mL of dry dichloromethane, and a thermometer and a dropping funnel containing 10.0 mL (10.8 g, 103 mmol) of methacryloyl chloride were equipped. The flask was cooled in a bath at $-20\text{ }^\circ\text{C}$, and methacryloyl chloride was added dropwise over 8 min with stirring. The internal temperature was below $-15\text{ }^\circ\text{C}$. Then the cooling bath was removed, and the mixture was stirred for 24 h at ambient temperature. The mixture was washed with 1.2 N HCl and sat. NaHCO_3 , and dried over MgSO_4 for 2 h. After removing the solvent from the solution, 10.96 g of yellowish solid was obtained. The solid was recrystallized twice (from toluene / hexane and from methanol) to afford 6.34 g (19.3 mmol) of target monomer as ivory powder. Yield: 64.3 % mp: $156\text{ }^\circ\text{C}$ (DTA on set). ^1H NMR (CDCl_3): 2.07 (6H, s, $\text{CH}_3\text{-C=NO-}$), 2.44 (6H, s, methacryl CH_3), 5.70 (2H, s, CH=), 6.25 (2H, s, CH=), 7.84 (4H, s, aromatic). ^{13}C NMR (CDCl_3): 14.39, 18.40, 126.45, 127.23, 135.22, 136.78, 162.46, 164.32. IR (KBr): 1738(C=O), 1634, 1606, 1317, 1122 (C-O-C) cm^{-1} . UV: λ_{max} (CH_3CN) 275 nm (ϵ 27 600 $\text{dm}^3\text{ mol}^{-1}\text{ cm}^{-1}$). ϵ at 254 nm was 16 300 $\text{dm}^3\text{ mol}^{-1}\text{ cm}^{-1}$. Elemental Analysis, found: C, 65.55; H, 6.16; N, 8.76. Calc. for $\text{C}_{18}\text{H}_{20}\text{N}_2\text{O}_4$: C, 65.84; H, 6.14; N, 8.53%. MS/MS (ESI): m/z $[\text{M}+\text{Na}]^+$ 351.

TBzM

In a 200 mL of two-necked flask, 4.43 g (17.8 mmol) of 1,3,5-triacetylbenzene trioxime and 24 mL (172 mmol) of triethylamine were dissolved in 150 mL of dry dichloromethane, and a thermometer, and a dropping funnel containing 15.0 mL (16.2 g, 155 mmol) of methacryloyl chloride were equipped. After the flask was cooled in a bath at $-30\text{ }^\circ\text{C}$, methacryloyl chloride was added dropwise over 10 min with stirring. The internal

temperature was below $-10\text{ }^{\circ}\text{C}$. Then the cooling bath was removed, and the mixture was stirred for 24 h at ambient temperature. The solution was quenched with methanol with cooling in an ice bath. Then, the mixture was washed with 1.2 N HCl and sat. NaHCO_3 , and dried over Na_2SO_4 overnight. After the drying, the solution contained gelatinous materials which were removed by filtering. Resulting solution was rotavapped to afford 19.6 g of amber tar. The tar was washed with hexane 3 times, and recrystallized from methanol. Finally, obtained solid was column chromatographed with dichloromethane : ethyl acetate = 5 : 1 (v/v) to afford 2.25 g (4.96 mmol) of target monomer as colorless powder. Yield: 27.9 % mp: $178\text{ }^{\circ}\text{C}$ (DTA on set). ^1H NMR (CDCl_3): 2.09 (9H, s, $\text{CH}_3\text{-C=NO-}$), 2.50 (9H, s, methacryl CH_3), 5.73 (3H, s, CH=), 6.27 (3H, s, CH=), 8.27 (3H, s, aromatic). ^{13}C NMR (CDCl_3): 14.73, 18.46, 126.66, 127.72, 135.19, 135.96, 162.44, 164.35. IR (KBr): 1747 (C=O), 1635, 1621, 1373, 1317, 1289, 1279, 1139 (C-O-C), 1119 (C-O-C) cm^{-1} . UV : λ_{max} (CH_3CN) 245 nm (ϵ 49 200 $\text{dm}^3\text{ mol}^{-1}\text{ cm}^{-1}$). ϵ at 254 nm was 42 100 $\text{dm}^3\text{ mol}^{-1}\text{ cm}^{-1}$. Elemental analysis, found: C, 63.44; H, 5.87; N, 9.39. Calc. for $\text{C}_{24}\text{H}_{27}\text{N}_3\text{O}_6$: C, 63.56; H, 6.00; N, 9.27%. MS/MS (ESI): m/z $[\text{M}+\text{Na}]^+$ 476.

Photopolymerization

Formulations composed of DBzM : TPO : MA and TBzM : TPO : MA = 1.5 : 1 : 1,000 and 1 : 1 : 1,000 (mol/mol), respectively, were prepared for photopolymerization. After bubbling with nitrogen gas, 20 μL of the formulation was put on a quartz disc (20 mm^{ϕ}) with the dispenser, covered with a PET film (20 mm^{ϕ}), and irradiated with the Hg-Xe lamp for 60 s. The light intensity at 365 nm was 250 mW/cm^2 .

For the measurement of IR changes, CaF_2 discs (20 mm^{ϕ} , 2 mm thick) were used as substrates. In this case, we covered the formulation with PE and PET films, and irradiated for 120 s with the Hg-Xe lamp, because polymerized films often remained on PET films rather than CaF_2 discs. All irradiated films were baked at $80\text{ }^{\circ}\text{C}$ for 2 min on a hot plate after removing the covering films.

The insoluble fraction of photopolymerized films was calculated by measuring the weight of 4 sample films before and after soaking in THF for 3 min followed by baking at $80\text{ }^{\circ}\text{C}$ for 2 min.

Photodegradation

Photodegradation of crosslinked polymers was carried out on irradiation at 254 nm with intensity of 1.8 mW/cm^2 . Irradiated films were soaked in THF for 3 min at room

temperature followed by baking at 80 °C for 2 min. The films were scratched with a needle, and resulting cross-sections were measured with the surface roughness tester before the soaking. After soaking, the thickness was measured again. Normalized film thickness was calculated from the ratio of thickness before and after the soaking.

For SEC measurement, decrosslinked polymers were recovered by rotavap of the THF solutions.

Results and discussion

Synthesis and properties of crosslinkers

Starting from corresponding aromatic ketones, DBzM and TBzM were obtained in two steps. The yields of the latter was relatively low because of the proceeding of polymerization during working up. Solubility of crosslinkers in organic solvents was not so high. For example, the solubility of DBzM and TBzM in MA was ca. 0.57 and 0.55 wt% at room temperature.

TG/DTA profiles of DBzM and TBzM indicate small endoenergetic peaks around 160 and 180 °C, respectively, which were followed by exothermic peaks (supporting information Fig. S5). No DTA peak was observed below their melting points, suggesting that the thermal decomposition did not occur below these temperatures. The observed thermal stability fulfills the demand often required for imaging systems.⁴²

The copolymerization of monofunctional *O*-methacryloyl oximes with common monomers such as styrene³⁸ and methyl methacrylate⁴³ was already published. Thus DBzM and TBzM can be expected to copolymerize with a variety of vinyl monomers.⁴⁴

In UV spectra in acetonitrile, absorption maximum due to π - π^* transition of DBzM appears at 275 nm, although that in TBzM is at 245 nm as shown in Fig. 2. Similar bathochromic shift of para-disubstituted benzenes compared to 1,3,5-trisubstituted ones is also found in starting ketones as well as other substituents such as cyano⁴⁵ and alkyl groups,⁴⁶ probably due to the participation of imino moieties in the resonance with benzene rings.⁴⁶

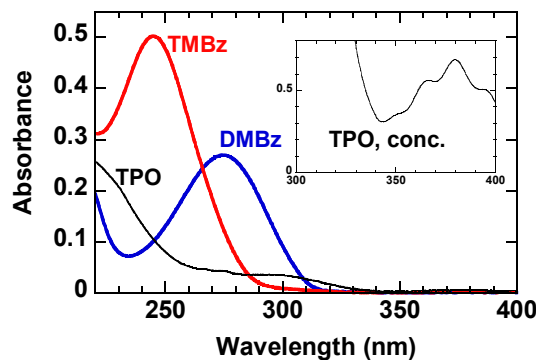


Fig. 2. UV spectra of 1.0×10^{-5} M acetonitrile solutions of DBzM, TBzM, and TPO. Inset shows UV spectra of 1.2×10^{-3} M acetonitrile solution of TPO.

Figure 3a shows IR spectra of DBzM in KBr, where peaks due to C=O and C-O stretching bands in *O*-acyloxime moiety appeared at 1738 and 1122 cm^{-1} , respectively. When the KBr pellet was irradiated at 254 nm, these peaks decreased and a new peak appeared at 1684 cm^{-1} . These characteristic peaks and their photochemical changes were also observed for TBzM as shown in Fig. 3b, where peaks due to C=O and C-O stretching bands in *O*-acyloxime moiety at 1747, 1139, and 1119 cm^{-1} decreased on irradiation at 254 nm, and new peak appeared at 1688 cm^{-1} . These IR spectral changes suggested the proceeding of photolysis of *O*-acyloxime moieties in Scheme 1(i). In aromatic imines, C=N stretching bands appear in the region of 1620-1635 cm^{-1} with medium intensity.⁴⁷ Therefore, the new peaks for DBzM and TBzM at 1684 and 1688 cm^{-1} , respectively, are assigned to aromatic ketones rather than imines. Considering the moisture in KBr pellet, generated imine units would be hydrolyzed immediately.

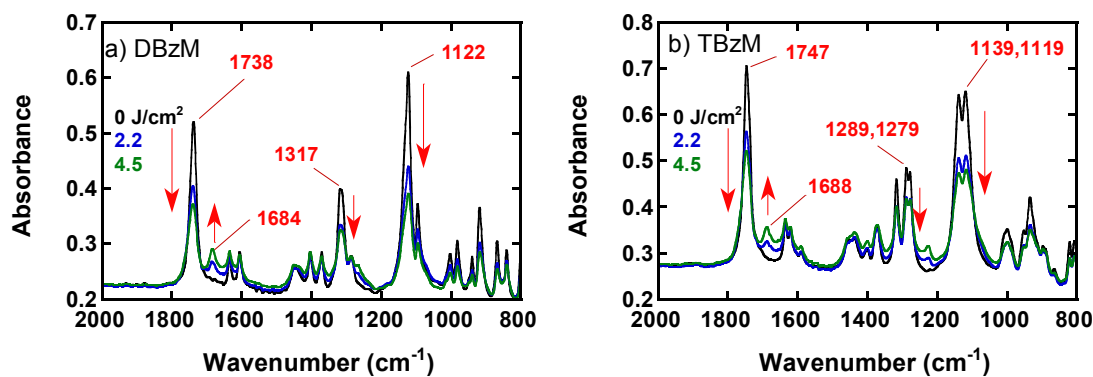


Fig. 3. IR spectral changes of a) DBzM and b) TBzM in KBr on irradiation at 254 nm. Numbers in the figure show irradiation energy and wavenumbers of peak tops.

Photopolymerization

Photopolymerization of MA in the absence and presence of crosslinkers was performed with TPO as a photoinitiator and a light above 310 nm. In the absence of crosslinker, resulting homopolymer (pMA) was not hard film but viscous tar.⁴⁸ However, SEC profile revealed that Mn and Mw of pMA were 57,600 and 324,000, respectively. Both the greater value of polydispersity and a shoulder at higher molecular weight region in SEC profile (Fig. S6) suggest that inhomogeneous proceeding of polymerization occurred in bulk polymerization.

When 0.15 mol% of DBzM against MA were involved in the formulation, obtained copolymer (DBzM-MA) gave films. Similarly, MA containing 0.10 mol% of TBzM turned into a copolymer (TBzM-MA) films. These films were hard and smooth-surfaced with 5 μm thickness. In addition, the insoluble fractions of DBzM-MA and TBzM-MA after soaking in THF were 52 and 79 wt%, respectively. These results show the formation of networked structure containing photolabile crosslinkers.

During the photopolymerization, the proceeding of simultaneous photodegradation could be considered. The photolysis of *O*-acyloxime moiety by using Hg-Xe lamp is possible in two ways: one is direct photolysis with 313 nm light, and the other is sensitized one by TPO with 365 nm light, because TPO involves benzoyl moiety which are known to sensitize the photoreaction of *O*-acyloximes as triplet sensitizers.^{49,50} However, judging from the insolubility of the polymers in THF, the degradation of *O*-acyloxime units was negligible. It is suggested that the direct photolysis was reduced by the low transmittance of the PET film at 313 nm (7%) and lower molar absorption coefficients of crosslinkers at 313 nm compared to those at 254 nm (DBzM: 7.5 %, TBzM: 0.9 %), and the sensitized photolysis did not occur due to low concentration of TPO and crosslinkers in solid films.

Photodegradation

The polymer films were further irradiated at 254 nm. Figure 4 shows the UV spectral changes of these films. In the absence of crosslinkers, pMA film had a small absorbance at 254 nm, and there was little change in their spectra as shown in Fig. 4a. In the presence of crosslinkers, a peak at 274 nm in DBzM-MA (Fig. 4b) and a shoulder around 250 nm in TBzM-MA films (Fig. 4c), both are assigned to the π - π^* transition of benzene units bearing *O*-acyloximes, decreased on irradiation at 254 nm. Although simple first-ordered decay was not observed in case of DBzM-MA as shown in Fig. 4d, the decrease for both polymers

suggests that the photoreaction of *O*-acyloximes proceeded on irradiation at 254 nm.

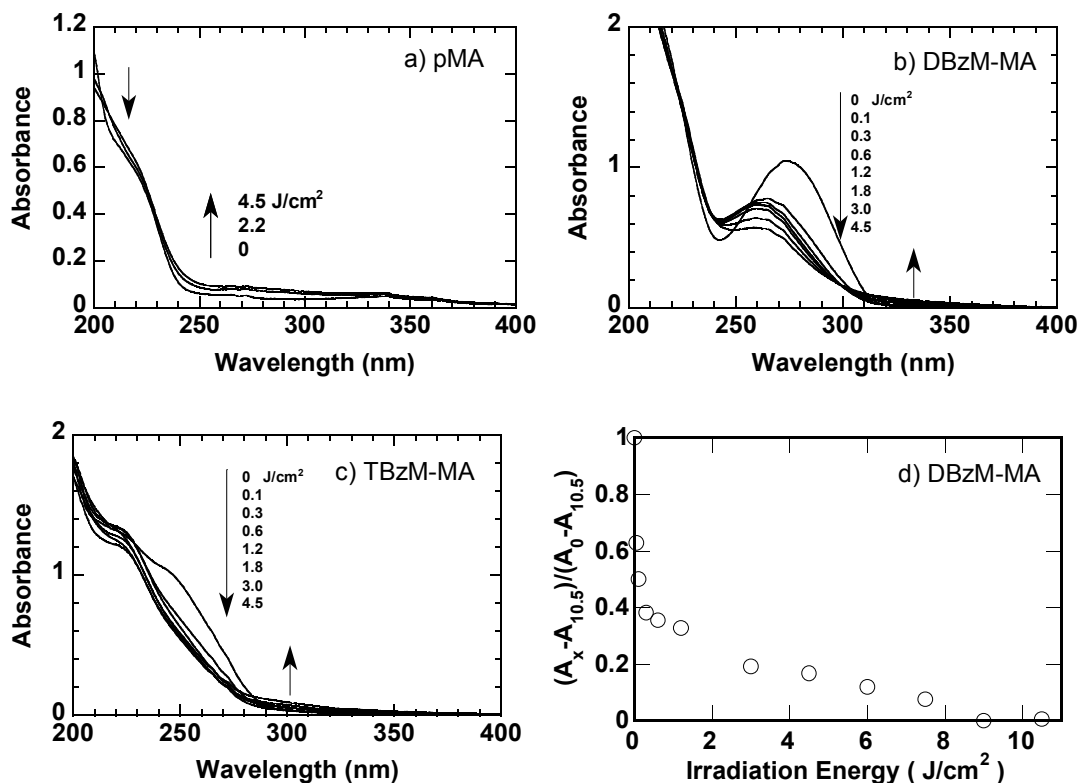


Fig. 4. UV spectral changes of a) pMA, b) DBzM-MA, and c) TBzM-MA films on irradiation at 254 nm. Numbers in the figures show irradiation energy. Film thickness: 5 μm . d) Changes of normalized absorbance of DBzM-MA film as a function of irradiated energy at 254 nm. A_x indicates the absorbance at 274 nm with irradiation energy of $x \text{ J/cm}^2$.

The changes of IR spectra of polymerized films were also measured. Although the molar feed of the crosslinkers was low, the changes of peaks due to the crosslinkers could be detected in difference spectra between non-irradiated and irradiated films as shown in Fig. 5.

In Fig. 5a, the decrease at 1736 and 1161 cm^{-1} and increase at 1712 cm^{-1} were observed in pMA films. The reason of these changes are unclear, although it might be assigned to the slight shift of strong ester peaks in MA on irradiation at 254 nm. Figure 5b showed the changes of difference spectra for DBzM-MA films. Unfortunately, the changes were similar to those with pMA, because the characteristic peaks due to C=O and C-O stretching bands in *O*-acyloxime unit overlapped with those in MA. However, DBzM-MA film showed a small increase in the region of 1620-1712 cm^{-1} . This increase suggested that imine units were produced as shown in Scheme 1(i), and a part of the imine units were hydrolyzed to ketone

units. In case of TBzM-MA, the decrease at 1764 cm^{-1} due to C=O stretching band in *O*-acyloxime unit was clearly observed in Fig. 5c, and the decrease was monotonous as plotted in Fig. 5d. In addition, the appearance of peaks at 1688 and 1645 cm^{-1} were observed, which are assignable to C=O stretching band in aromatic ketones and C=N stretching band in aromatic imines, respectively. From the above spectral changes, the plausible photochemical reactions of crosslinkers in polymers are summarized in Scheme 2.


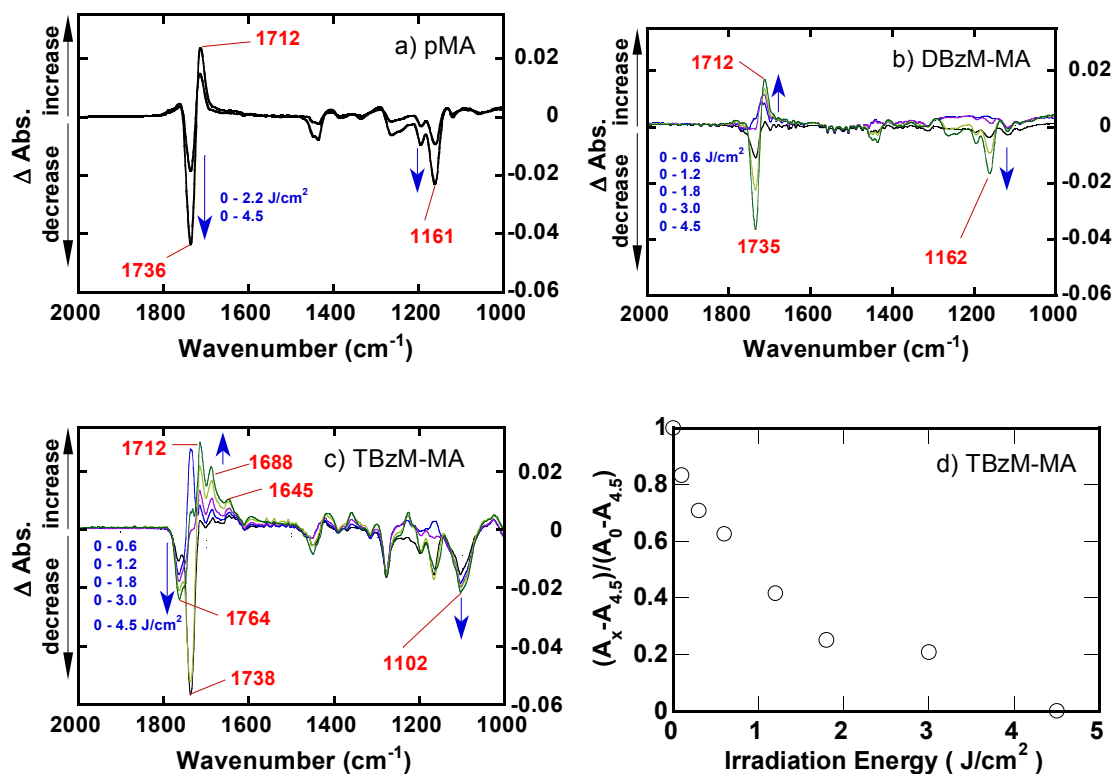


Fig. 5. Changes of difference IR spectra between non-irradiated and 254-nm irradiated films of a) pMA, b) DBzM-MA, and c) TBzM-MA. Numbers in the figure show irradiation energy at 254 nm and wavenumbers of peak tops. d) Changes of normalized absorbance of TBzM-MA film as a function of irradiated energy at 254 nm. A_x indicates the absorbance at 1764 cm^{-1} with irradiation energy of $x\text{ J/cm}^2$.

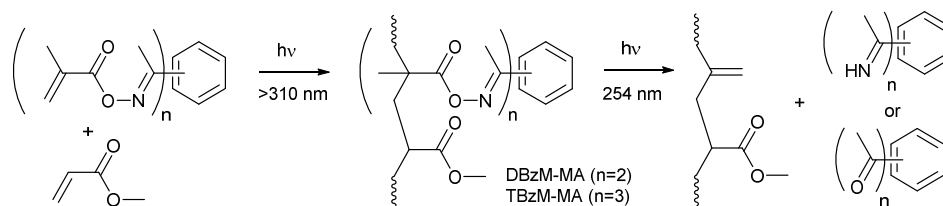

Scheme 2. Plausible photoreaction of *O*-acyloxime-based crosslinkers.

Photopolymerized films with different irradiation energies were soaked in THF. Although both DBzM-MA and TBzM-MA films were almost insoluble without irradiation at 254 nm, film thickness decreased along with an increase in irradiation energy at 254 nm irradiation as shown in Fig. 6. These results clearly indicate the proceeding of decrosslinking to form linear polymer chains as shown in Scheme 2. The remaining thickness for TBzM-MA films was slightly higher than those of DBzM-MA films. This may be due to the higher functionality of the crosslinker to maintain networked structure.

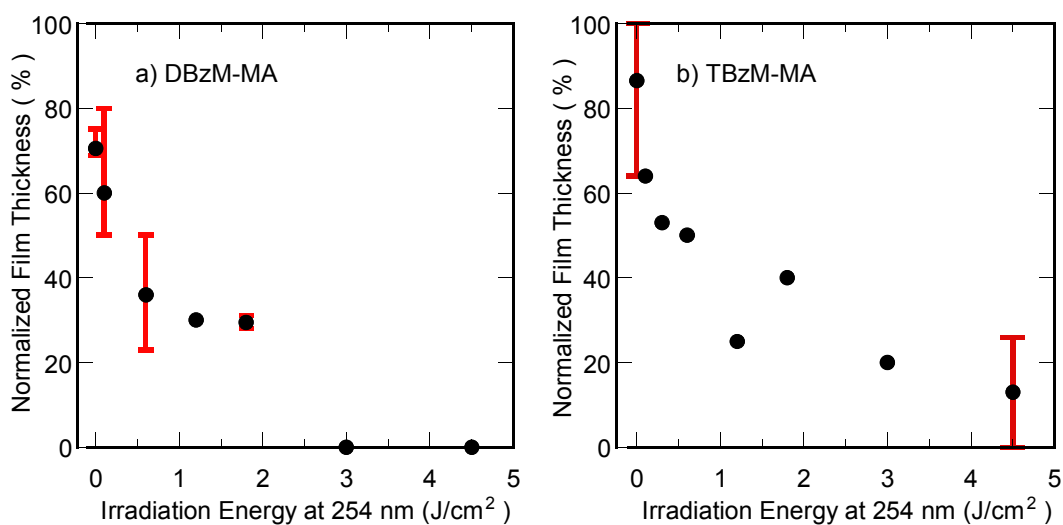


Fig. 6. Thickness changes of a) DBzM-MA and b) TBzM-MA films after soaking in THF as a function of irradiation energy at 254 nm. Film thickness before soaking: 5 μm .

Soluble fractions in THF were collected, filtered, and their molecular weights were measured by SEC. Table 1 summarizes the molecular weights, where M_n of TBzM-MA was slightly smaller than that of DBzM-MA. This tendency is consistent with the discussion on the relationship between molecular weight and crosslinker functionality,^{51,52} where trifunctional crosslinkers tended to form more rigid networks and thus to give lower

molecular weight between crosslinking points compared to difunctional ones. However, the SEC profiles of pMA, DBzM-MA, and TBzM-MA were almost identical as observed in Fig. S6. In order to discuss the effect of the functionality, other experimental condition such as higher concentration of the crosslinkers might be needed. The small decrease in molecular weights for pMA on irradiation at 4.5 J/cm² would be due to proceeding of main-chain scission and volatile products formation, which has often been found on irradiation in the presence of oxygen.⁵³

Table 1. Molecular weights of soluble fractions of polymers in THF.

Polymer	Irradiation at 254 nm (J/cm ²)	Mn ^a	Mw ^a	Mw/Mn
pMA	0	57,600	324,000	5.63
pMA	4.5	34,100	206,900	6.07
DBzM-MA	4.5	58,900	297,100	5.04
TBzM-MA	4.5	44,400	194,300	4.38

a) From SEC.

Conclusion

Novel photolabile crosslinkers, DBzM and TBzM were prepared and characterized. Both crosslinkers were successfully photopolymerized with MA on irradiation at > 310 nm in the presence of TPO. The photolysis of *O*-acyloxime units in the resulting polymers at 254 nm was confirmed by UV and IR difference spectral changes, which lead to the degradation of the networked structure. SEC analysis revealed that the molecular weights of linear pMA were similar to those of DBzM-MA and TBzM-MA after irradiation at 254 nm. These results demonstrated that DBzM and TBzM are potential candidates for novel photolabile crosslinkers.

Acknowledgement

The authors thank to Dr. Hirokazu Hayashi for measuring MS spectra of crosslinkers. This work was supported by JSPS KAKENHI Grant Number 25340095.

References and notes

1. H. Nishida, *Polym. J.*, 2011, **43**, 435.
2. K. Ogino, J. -S. Chen and C. K. Ober, *Chem. Mater.*, 1998, **10**, 3833.
3. S. Taketani and A. Matsumoto, *Macromol. Chem. Phys.*, 2004, **205**, 2451.
4. Z. Chen, L. Zhao and Z. Wang, *Polymer*, 2013, **54**, 5182.
5. H. Otsuka, *Polym. J.*, 2013, **45**, 879.
6. A. Gandini, *Prog. Polym. Sci.*, 2013, **38**, 1.
7. T. Iwamura and S. Nakamura, *Polymer*, 2013, **54**, 4161.
8. T.-W. Chuo, T.-C. Wei and Y.-L. Liu, *J. Polym. Sci. Part A: Polym. Chem.*, 2013, **51**, 3395.
9. K. Huang, A. I. Isayev and J. Zhong, *J. Appl. Polym. Sci.*, 2014, **131**, 40680.
10. R. R. De Clercq and E. J. Goethals, *Macromolecules*, 1992, **25**, 1109.
11. T. Hashimoto, H. Meiji, M. Urushisaki, T. Sakaguchi, K. Kawabe, C. Tsuchida and K. Kondo, *J. Polym. Sci. A: Polym. Chem.*, 2012, **50**, 3674.
12. Y. Kohsaka, K. Nakazono, Y. Koyama, S. Asai and T. Takata, *Angew. Chem. Int. Ed.*, 2011, **50**, 4872.
13. G. K. Paul and S. Ramakrishnan, *Macromol. Chem. Phys.*, 2001, **202**, 2872.
14. J. J. Gallagher, M. A. Hillmyer and T. M. Reineke, *Macromolecules*, 2014, **47**, 498.
15. X. Hu, H. Li, S. Luo, T. Liu, Y. Jiang and S. Liu, *Polym. Chem.*, 2013, **4**, 695.
16. M. Yonekawa, Y. Furusho, T. Takata and T. Endo, *J. Polym. Sci. Part A: Polym. Chem.*, 2014, **52**, 921.
17. M. Shirai, *Prog. Org. Coat.*, 2007, **58**, 158.
18. M. Shirai, *Polym. J.*, 2014, **46**, 859.
19. S. Mura, J. Nicolas and P. Couvreur, *Nature Mater.*, 2013, **12**, 991.
20. Y. Yang and M. W. Urban, *Chem. Soc. Rev.*, 2013, **42**, 7446.
21. H. Okamura and M. Shirai, *Polymer*, 2010, **51**, 5087.
22. G. Huh, K.-O. Kwon, S.- H. Cha, S. -W. Yoon, M. Y. Lee and J. -C. Lee, *J. Appl. Polym. Sci.*, 2009, **114**, 2093.
23. D. Matsukawa, H. Okamura and M. Shirai, *J. Mater. Chem.*, 2011, **21**, 10407.
24. M. Adachi, H. Okamura and M. Shirai, *Chem. Lett.*, 2013, **42**, 1056.
25. E. M. White, J. E. Seppala, P. M. Rushworth, B. W. Ritchie, S. Sharma and J. Locklin, *Macromolecules*, 2013, **46**, 8882.
26. A. M. Kloxin, A. M. Kasko, C. N. Salinas and K. S. Anseth, *Science*, 2009, **324**, 59.
27. D. Klinger and K. Landfester, *Soft Matter.*, 2011, **7**, 1426.

28. D. Klinger and K. Landfester, *Macromolecules*, 2011, **44**, 9758.
29. F. Ercole, H. Thissen, K. Tsang, R. A. Evans, and J. S. Forsythe, *Macromolecules*, 2012, **45**, 8387.
30. C. S. Ki, H. Shih and C. -C Lin, *Polymer*, 2013, **54**, 2115.
31. M. W. Tibbitt, A. M. Kloxin, L. A. Sawicki and K. S. Anseth, *Macromolecules*, 2013, **46**, 2785.
32. S. Bian, J. Zheng and W. Yang, *J. Polym. Sci. Part A: Polym. Chem.*, 2014, **52**, 1676.
33. Q. Huang, C. Bao, W. Ji, Q. Wang and L. Zhu, *J. Mater. Chem.*, 2012, **22**, 18275.
34. M. A. Azagarsamy, D. D. McKinnon, D. L. Alge and K. S. Anseth, *ACS Macro Lett.*, 2014, **3**, 515.
35. K. Suyama and H. Tachi, *J. Photopolym. Sci. Technol.*, 2014, **27**, 231.
36. K. Suyama, T. Inoue and M. Shirai, *J. Photopolym. Sci. Technol.*, 2010, **23**, 439.
37. K. -H. Song, M. Tsunooka and M. Tanaka, *Makromol. Chem. Rapid Commun.*, 1988, **9**, 519.
38. K. Suyama and M. Tsunooka, *Polym. Degrad. Stab.*, 1994, **45**, 409.
39. K. Suyama and M. Shirai, *Prog. Polym. Sci.*, 2009, **34**, 194.
40. K. Suyama, S. Ozaki and M. Shirai, *React. Funct. Polym.*, 2013, **73**, 518.
41. M. Leeman, G. Brasile, E. Gelens, T. Vries, B. Kaptein and R. Kellogg, *Angew. Chem. Int. Ed.*, 2008, **47**, 1287.
42. J. F. Cameron and J. M. J. Fréchet, *J. Am. Chem. Soc.*, 1991, **113**, 4303.
43. M. Tsunooka, S. Imono, K. Nakayama, H. Kuwabara, and M. Tanaka, *J. Polym. Sci. Polym. Chem. Ed.*, 1986, **24**, 317.
44. We have confirmed the copolymerization of DBzM and TBzM with butyl acrylate or poly(ethylene glycol) monomethacrylate.
45. H. B. Lueck, T. C. Swinney, B. S. Hudson and D. M. Freidrich, *Chem. Phys. Lett.*, 1996, **258**, 80.
46. R. M. Silverstein, G. Clayton and T. C. Morrill, in *Spectrometric Identification of Organic Compounds*, 4th edn., John Wiley & Sons, New York, 1981, p 321.
47. G. Socrates, in *Infrared and Raman Characteristic Group Frequencies*, 3rd edn., John Wiley & Sons, New York, 2001, p78.
48. In our experimental condition, the lower conversion of the photopolymerization is suggested. In fact, for one sample film of TBzM-MA, the weight of formulation on the substrate changed from 19 mg to 10 mg on irradiation followed by removing the PET film. The weight of the film was still 10 mg after soft baking at 80 °C for 2 min, indicating that

- the conversion for TBzM-MA was ca. 50 %.
49. J. Lalevée, X. Allonas, J. P. Fouassier, H. Tachi, A. Izumitani, M. Shirai and M. Tsunooka, *J. Photochem. Photobiol. A: Chem.*, 2002, **151**, 27.
 50. T. Ohba, K. Suyama and M. Shirai, *React. Funct. Polym.*, 2006, **66**, 1189.
 51. J. S. Young, A. R. Kannurpatti and C. N. Bowman, *Macromol. Chem. Phys.*, 1998, **199**, 1043.
 52. J. E. Elliott and C. N. Bowman, *Macromolecules*, 2001, **34**, 4642.
 53. R. B. Fox, L. G. Isaacs, S. Stokes, and R. E. Kagarise, *J. Polym. Sci.: Part A*, 1964, **2**, 2085.