

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Poly (ether-amide)s vs poly(ether-imide)s copolymers for post-combustion membrane separation processes

Alberto Tena^a, Sergey Shishasky^a, Volkan Filiz^a

^aHelmholtz-Zentrum Geesthacht, Institute of Polymer Research Max-Planck-Str.1, 21502 Geesthacht, Germany. E-mail: alberto.tena@hzg.de; Fax: +49 4152 872499; Tel: +49 4152 872448

This work is focused on the comparison between the commercial polyamide PEBAX[®] MH 1657 and a new set of synthesized polyimides with different polyethylene glycol length. The samples were synthesized with the same poly(ethylene oxide) (PEO) content (57 wt%) in order to compare with the commercial polymers. All polymers have been characterized by several techniques revealing a direct relationship between crystallinity, PEO length and permeability properties. Results at temperatures lower than the T_m of the polyether blocks confirms that the lower PEO crystallinity showed higher permeability. At temperatures higher than the T_m of the PEO block, not significant differences were found between the commercial polyamides and the synthesized polyimides. This confirms that the aliphatic phase controls the separation while the hard block provides mechanical strength. Remarkable are the results for the CO₂/N₂ separation. It introduces these new copolyimides in promising materials for post-combustion processes.

Introduction

The augment of carbon dioxide concentration in the atmosphere due to the use of fossil fuels is believed to be a reason for a global climate change which, because of its potentially dangerous effects, requires energetic actions. 60 % of total CO₂ emission is produced by power generation facilities and industrial factories. Of course, an important amount of research should focus on the development of clean energy sources and on more efficient use of energy. However, it's also necessary to reduce CO₂ emission levels from existing industrial sources, so carbon capture and storage (CCS) must be considered as an urgent issue. CO₂ can be captured by a variety of methods, which can be classified as post-combustion, pre-combustion and oxy-combustion ones. Among these methods, post-combustion appears as one of the most attractive and ready for use alternatives. This process can be applied to different sources: power, steel, cement or petrochemical plants. In this process, the CO₂ of the flue gas must be concentrated, purified and compressed (liquefied) to meet the transport and storage specifications. The amount of CO₂ in the flue gas ranges from low (4%) to high (30 %) concentrations and therefore the technology under development should consider these differences. Other gaseous compounds in the flue gas are H₂O, O₂, H₂, CO, NO_x or SO_x, although the most frequent is N₂. One of the most interesting options for post-combustion CCS are widespread coal fired power plants, where CO₂ concentrations are typically around 15 vol.%.

Nowadays, the role of polymeric membranes applied to gas separation is more and more important. Although a number of them have already an application in industrial separations¹, research is still necessary to discover new materials and/or to improve the properties of existing polymers to assure them an actual applicability at an industrial level. In order to guarantee a real application of new polymeric materials in gas separation, an adequate balance of high permeability and good selectivity must be achieved^{2,3}. Moreover, in addition to the criteria of permeability and selectivity, polymers to be used in new gas separation membranes, must

have good mechanical properties and thermal resistance to ensure stability of approximately 100 nm thick defect free selective layer at required operating conditions.

In order to be useful in such gas separation applications, a polymer film should show a preferential affinity for condensable gases such as CO₂ or CH₄ as compared with a mostly inert gas such as N₂. The polar ether oxygen of poly(ethylene oxide) PEO presents this kind of preferential interaction with carbon dioxide while the interaction with nitrogen molecules is weaker. It was determined that the greater amount of this groups increase the performance of the polymers for membranes of post-combustion separation processes⁴. In this sense, (PEO) compounds give excellent results for the CO₂ separation from other light gases due to the existence of this favorable electronic interaction with the ether moiety⁵⁻⁷.

Commercially available multiblock copolymers like PEBAX, consisting of an alternating sequence of flexible polyether and rigid polyamide blocks, is one of the most popular strategies to face CO₂/N₂ separation. The commercial polymers of PEBAX[®] family showed the most promising results for this application. PEBAX[®] properties can be tailored by varying the chemical structures and the contents of the polyamide (PA) and polyether⁸. The properties could be improved by the incorporation of different fillers or blending with another oligomer or polymer⁹⁻¹¹. As a function of the composition, there are several kinds of commercially available PEBAX[®], but from the literature, the best results for the separation of carbon dioxide and nitrogen were found for the called PEBAX[®] MH 1657¹²⁻¹⁴. The composition of this polymer is 40% semicrystalline amide domains and 60% soft amorphous segments.

On the other hand, copoly(ether-imide)s, containing microphase-separated PEO and imide domains, are of the most interest as membrane's selective layer compounds for post-combustion applications. Polyimides are well known for their excellent thermal, oxidative stability, good organic solvent resistance and exceptional mechanical properties, along with an extraordinary ability to separate complex mixtures of gases in diverse applications². Typically these materials present a high selectivity but seldom with sufficiently high permeability^{15,16}. Therefore, it would be convenient to increase permeability without losing selectivity utilizing ability of copoly(ether-imides) to transport gas molecules through both amorphous domains in contrast to copoly(ether-amide)s where one domain is often barrier for gas transport due to its semicrystallinity. One of the most common approaches to meet these requirements is the use of aromatic-aliphatic block-copolymers including aliphatic chains showing a certain affinity for condensable gases such as CO₂, or CH₄. In consequence, block-copolyimides combining aromatic blocks and PEO appear to be a successful route^{17,18}.

Then, in both cases, copoly(ether-amide)s and copoly(ether-imide)s, the hard block can be formed by a polymer with well-packed and more or less rigid structures; and the soft block, which consists in a polymer with more flexible chains, which can form rubbery segments within the polymer chain normally with high free volume and mobility. When aromatic-aliphatic block-copolymers are phase-separated, the glassy segments in the polymer would usually provide mechanical support. The rubbery segments, due to the nature of the flexible chain structure, allow an efficient transport of gas, giving a good permselectivity to the copolymer for the CO₂/N₂ gas pair¹⁹⁻²¹ and the amount of these soft segments in the copolymers has a strong influence on the mechanical and gas transport properties²². This is attributed mainly to the high solubility-selectivity²³, which is due to the commented strong interactions of CO₂ with the oxyethylene group in PEO. The interaction between CO₂ and PEO has been discussed and used previously for the development of CO₂ selective membranes²⁴⁻²⁶.

For these reasons it is necessary to carry on studies for a better understanding of this type of PEO copolymers, in order to reach optimal structures for specific applications. In particular, here we were focused on the influence of the kind of copolymer, length

of the polyether and effect of the crystallinity in the properties for different copolymers with the same amount of poly(ethylene oxide).

Experimental

Chemicals

The dianhydride 3,3',4,4'- biphenyl tetracarboxylic dianhydride (BPDA) and 3,3',4,4'- and the diamines 4,4'-oxydianiline (ODA), poly (ethylene glycol) 6000 and 10000 g/mol were purchased from Aldrich. BPDA and ODA were purified by sublimation at high vacuum just before use. Poly(oxyethylene) bis(amine) (Jeffamine ED-2003, $n = 41$) with nominal molecular weight of 2000 g/mol, was kindly donated by Huntsman[®] (Holland). Polyethers were dried at 70°C in vacuum for 5 hours and stored in a desiccator at vacuum until use. PEBAX[®] MH 1657 was purchased from ARKEMA. Anhydrous N-methyl pyrrolidinone (NMP) and methanol were purchased from Sigma-Aldrich Co. All gases used for gas transport properties tests were purchased from Linde AG and Air Liquide and had purity at least 4.5.

Synthesis of copoly(ether-imide)s and preparation of the dense films

The samples were synthesized by combination of the aromatic diamine (ODA) with the aromatic dianhydride (BPDA), and polyethers of different length (PEO2000, PEO6000 and PEO10000). The corresponding copoly(ether-imide) was nominated by the name of the poly ethylene glycol and the length, because the amount of polyether in the copolymer was always the same (57 % w/w) with the exception of PEO2000 with around 55 % w/w content. Thus, PEO2000 refers to the sample BPDA-PEO2000-ODA with a weight ratio of the aliphatic diamine and the aromatic diamine of 3,5:1 (w /w) into the copolymer. For the commercial polymer PEBAX[®] MH 1657, the weight content of PEO is 57 %²⁵, and in this way we can compare in the same conditions with the synthesized copolymers.



Polyether poly(oxyethylene oxide) (PEO x 000) (x mmol), and 4,4'-oxydianiline (ODA) (y mmol) in the corresponding weight ratios (3,5:1) were dissolved in anhydrous NMP (5 mmol ($x+y$)/10 mL) in a 100 mL three-necked flask blanketed with argon. Then, the reaction mixture was cooled down to 0 °C, and under mechanical stirring, a stoichiometric amount of the dianhydride (BPDA) ($x+y$ mmol) was added and the mixture was stirred overnight at room temperature. During this time the dianhydride completely dissolved and the solution reached high viscosity. Figure 1 shows the chemical structure of the polymers from a general point of view. In the case of the copoly (ether-imide)s, n is 41 (for PEO2000), 134 (for PEO6000), or 225 (for PEO10000). Table 1 records the proportions of PEO and the acronym for each of the polymers synthesized and used in this work.

The resultant viscous polyamic acid solution was diluted with NMP to the appropriate viscosity for casting, filtered through a nominal #1 fritted glass funnel, degassed, and cast onto a leveled glass plate. The resulting film was covered with a conical funnel to avoid fast evaporation of the solvent, dried at 80 °C overnight, and finally treated at 200 °C for 6 hours in a vacuum oven, in order to the complete solvent evaporation and to get a complete imidization.

For the commercial polymer PEBAX[®] MH 1657 (from now on, for simplicity, we will call just PEBAX[®]) the solution was prepared in NMP. After the complete dissolution, it was followed the same procedure as for other copolymers. After that, thermal treatments under inert atmosphere were carried out at 200 °C. For the preparation of the second PEBAX[®] membrane the polymer was dissolved at a concentration of 10 wt.% in a mixture of ethanol/water (70/30 wt/wt), with heating at 80–85 °C and magnetic stirring for 24 h. After, the solution was filtering and cast at 60 °C for 48 hours. Films of the copolymers of 50-70 μm in thickness were obtained. All films showed excellent mechanical properties.

Table 1. Overview about the characterized copolymers.

COPOLYMER	%PEO theoretical	DSC characterization		
		Polyether Tg / °C	Polyether Tm / °C	Crystallinity / %
PEBAX Ethanol/water	57	-50.9	15.3	19.4
PEBAX [®] Nmp	57	-56.9	14.4	14.3
PEO2000	53.9	-55.8	29.7	0.25
PEO6000	57.0	-58.6	32.9	27.2
PEO10000	57.6	-56.2	44.6	36.8

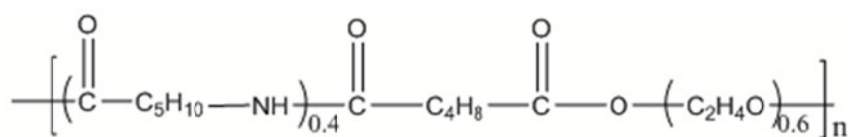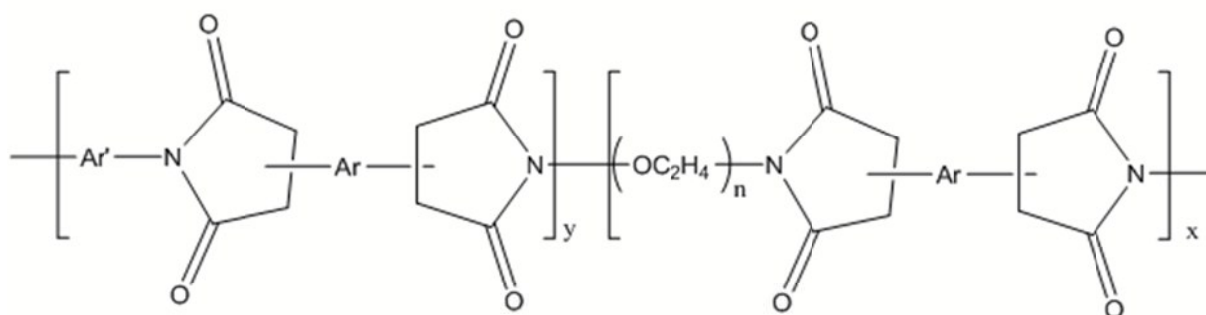Copoly(ether-amide) PEBAX[®] MH 1657

Aromatic-aliphatic copoly(ether-imide)

Figure 1. General structures for the copolymers used at this work.

Characterization Methods

Attenuated total internal reflectance-Fourier transform infrared analyses (ATR-FTIR) were performed at room temperature using a Bruker ALPHA FT-IR spectrometer in a spectral range of 400–4000 cm^{-1} with a resolution of 2 cm^{-1} and average of 32 scans. Perkin Elmer Spectrum One infrared spectrometer was equipped with an ATR accessory.

A thermal analysis NETZSCH TG209 F1 Iris instrument was used for thermogravimetric study (TGA) of the copolymers and PEBAX[®]. Disc samples, cut from films, with weights between 5 and 15 mg were tested. It was done with an initial heating rate of 5 K/min under a flux of 20 mL/min of argon, in a dynamic scans.

Differential scanning calorimetry (DSC) analyses were carried out in a Mettler Toledo (DSC 1 star system) calorimeter equipped with a liquid nitrogen accessory. Disc samples cut from films weighting 5–15 mg were sealed in aluminum pans. Samples were heated at 10 °C/min to a target temperature (a “cleaning step” was made before in order to remove the adsorbed water or solvent traces and the thermal history of the samples).

The permeability, P , was determined by using a permeator with constant volume which uses the *time-lag* operation method. The measurements were carried out at 700 mbar feed pressure and thirteen different temperatures from 10 to 70 °C with steps of 5 °C. Despite we will be focus in CO₂ and N₂, the permeability was also determined for H₂, He, O₂ and CH₄. A sketch of the device and the analyzed method used has been described in previous studies²⁷.

Results and discussion

Copoly(ether-imide)s imidization

After the films were dried overnight, they were annealed in a vacuum oven at 200 °C for 6 hours to almost complete removal of the solvent. Infrared spectra were recorded to check for the progress of imidization of the copolymers and to compare with the spectra for the PEBAX® samples.

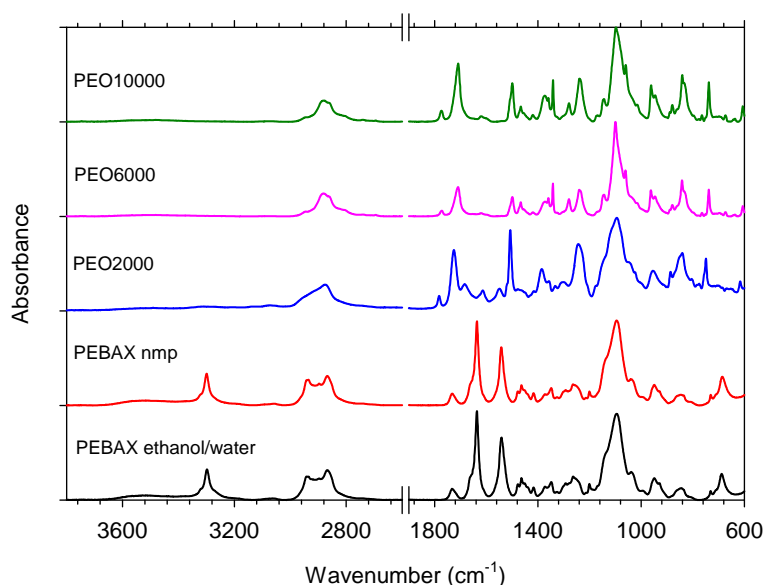


Figure 2. FTIR spectra for the synthesized copolymers and PEBAX® treated at 200 °C.

Under the commented protocol, the copolymer films were found completely imidized according to their FTIR spectra at 200 °C. For the synthesized copolymers, common bands appeared in the spectra: 2895 cm⁻¹ (aliphatic C-H stretching), 1790 cm⁻¹ (symmetric stretching of C=O imide groups), 1730 cm⁻¹ (asymmetric stretching of C=O imide groups), 1370 cm⁻¹ (C-N stretching of imide groups), 1244 cm⁻¹ (twisting CH₂), 1105 cm⁻¹ (C-O stretching), 845 cm⁻¹ (rocking CH₂) and 740 cm⁻¹ (imide ring deformation).

In the case of PEBAX®, the characteristic peaks at 1638 cm⁻¹ and 1742 cm⁻¹ represent the presence of a O=C=O and N-C=O bonds. For this commercial copolyamide, common bands appeared in the spectra: 1105 cm⁻¹ (stretching vibrations C-O), 1641 and 1657 cm⁻¹ (stretching of C=O imide groups), 3300 cm⁻¹ (vibrations N-H), at 2880 cm⁻¹ and 2948 cm⁻¹ (aliphatic C-H stretching). No differences in spectra were observed between the poly (ether-amide)s dissolved in different solvents.

Thermal Stability

Thermogravimetric analysis was performed to evaluate the thermal stability of the polymers. In the case of the copolyimides (annealed at 200 °C for 6 hours), it showed a weight loss pattern consisting of three consecutive steps (see Figure 3): an initial loss from ambient temperature to 300 °C; a second loss from 300 °C to 460-480 °C; and a third loss from 460-480 °C to 800 °C.

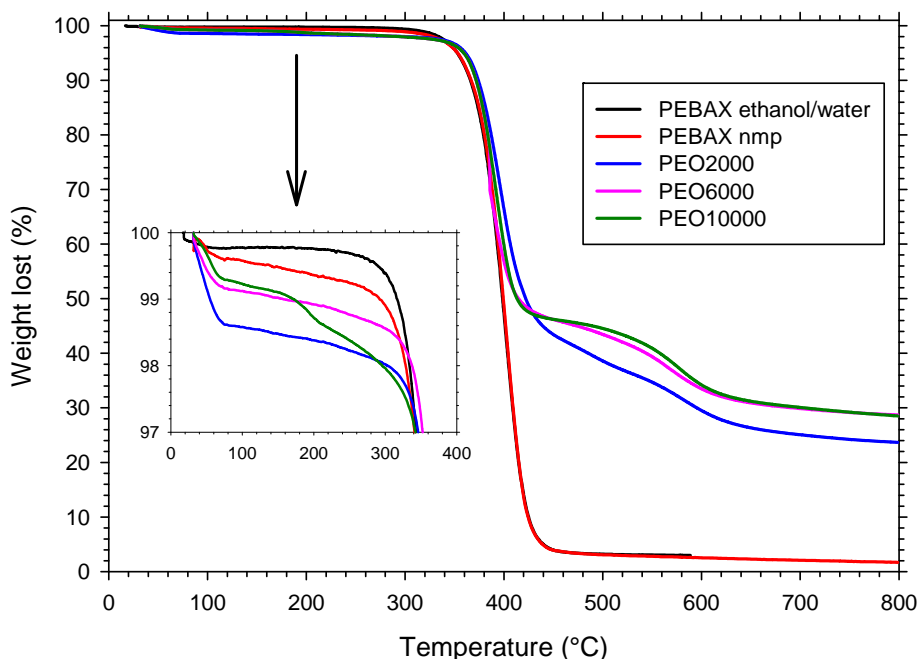


Figure 3.-TGA curves in dynamic conditions of copolymers having different poly-ethers length and PEBAX® annealed at 200 °C for 6 h.

The first loss can be attributed to the absorbed water plus the residual solvent trapped in the film. The weight change for this step was in the order of 2 %. The second loss stage, after correcting for the first one, agreed with the theoretical contribution of PEO entering the copolymer composition²⁸, and it was therefore assigned to the loss of polyether block sequences. The third and final stage of weight loss was due to the thermal decomposition of the remaining aromatic polyimide segments. TGA analysis confirmed that the polyether chains are much less thermally stable than the aromatic segments, as already found for another copoly(ether-imide)s based on PEO²³ and therefore a selective degradation of the polyether moiety can be performed in these copolymers. The temperature of maximum weight loss rate took place between 360-380 °C for all copolymers.

In the case of the PEBAX® films, despite the structure is also made-up by hard and soft blocks, like in the synthesized copolymers, the weight loss pattern consisting of two consecutive steps (see Figure 3): an initial loss from ambient temperature to 100 °C; and a second loss from 300 °C to 460-480 °C. The first loss can be attributed mainly to the absorbed water. The weight change for this step was lower than 1%. The second loss stage was therefore assigned to the thermal decomposition of the polymer. Consequently, for this copoly(ether amide) the degradation is in one step, showing the same stability for the hard and soft blocks. Not differences were observed between the polymers dissolved in ethanol/water or *N*-methyl pyrrolidinone.

Calorimetric Studies

The synthesized copoly(ether-imide)s showed only the T_g , and in some cases the melting temperature, T_m , for the poly(ethylene oxide) segments, and no transition for the aromatic polyimide segments could be detected, but for similar polymers, the aromatic T_g was determined at temperatures around 200 °C²².

Small changes in the polyether T_g were observed as a function of the PEO length. The melting enthalpy of PEO was taken from literature as 8.67 kJ/mol²³, and in this way we could calculate the crystallinity of the aliphatic polyether. A clear tendency was observed in the case of the aliphatic T_m and crystallinity. In the case of the polyimide PEO2000 the crystallinity found was almost negligible (0,25 %), whereas for the sample PEO6000, crystallinity was around 27 %, and for the longer polyether, PEO10000, the crystallinity was close to 37 % (all the value could be found in Table 1). From these data it is clear that longer PEO chains develop higher crystallinities. In the same way, the melting temperature for the polyethers was higher for longer chains length.

$$T_m \text{ PEO10000 (44,6)} > T_m \text{ PEO6000 (32,9)} > T_m \text{ PEO2000 (29,7)} > \text{PEBAX (15,3/14,4)}$$

For PEBAX[®] samples, the T_m was comparable (15,3 and 14,4 °C) with independence of the solvent. The crystallinity showed some differences between the samples prepared from ethanol/water or N-methyl pyrrolidinone as a solvent. For ethanol/water the crystallinity was 19,4 %, whereas for the samples dissolved in N-methyl pyrrolidinone, the crystallinity was 14,3 %. This could be related with a better segregation in the samples dissolved in the mixture ethanol/water.

It is well known that gases do not easily pass through the crystal structures²⁹, and for this reason it is important to know the actual crystallinity of our samples as a function of the temperature of permeation measurement. It is necessary to bethink about the process. In this case, the post-combustion membrane separation process is carried out at pressures close to one bar, and the temperatures generally are situated between 50-60 °C. Thus, from these results, it can be affirmed that for all the polymers studied in this work, at a temperature of the process, the polyether segments will be totally amorphous and above their corresponding T_g .

Gas transport properties

The gas transport properties of the polymers are strongly influenced by the quantity of amorphous or crystalline PEO in the sample. Therefore it's very important to check the permeation performance as a function of the measurement temperature because high temperatures would lower the presence of crystalline phase in the segregated domains that could act as barriers hampering the passage of gases through the film. For this reason, gas transport processes were determined by a two stage procedure used for all the samples under study. The first one is the heating stage, when the separation properties were determined from low (10 °C) to a temperature high enough for polyether switch from crystalline to an amorphous state (70 °C) with a steps of 5 °C between each temperature of permeability coefficients measurement, in order to obtain really precise results of the evolution of the samples during the melting process. The second stage is the stepwise cooling with steps of 5 °C, from 70°C to 10 °C in order to study the crystallization process.

From the results of the DSC experiments it was determined that sample that contain the higher percentage of crystalline PEO was the sample with the longer one, PEO10000 in this work. The evolution of the CO₂ permeability and CO₂/N₂ selectivity as a function of the measurement temperature for the sample PEO10000 is represented in Figure 4.

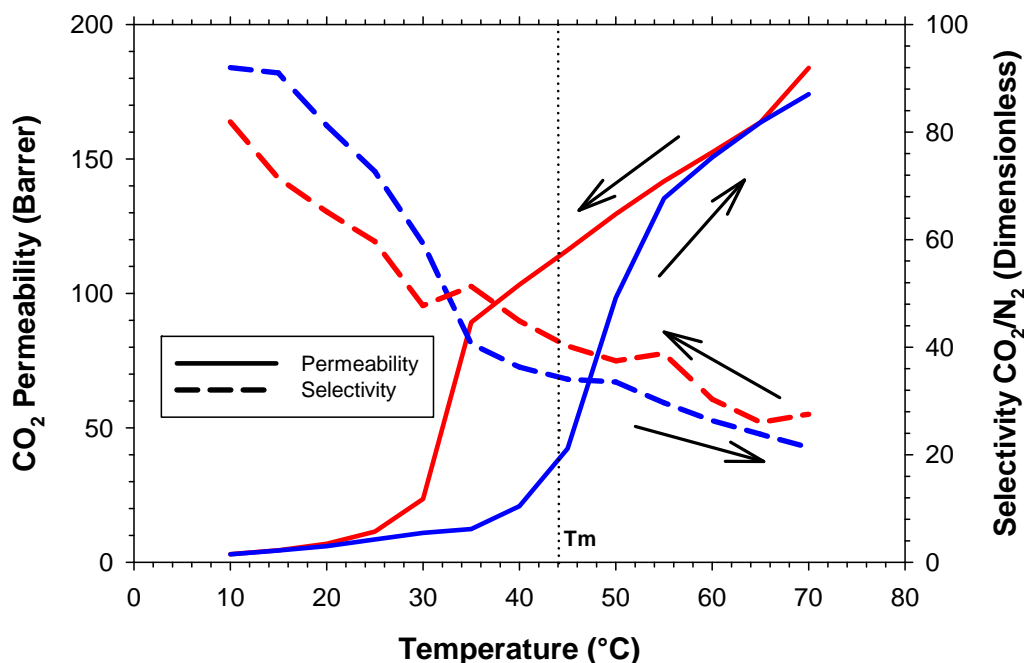


Figure 4.- CO₂ permeability and CO₂/N₂ selectivity for the sample PEO10000 as a function of the measurement temperature.

Due to the high percentage of crystallinity in the sample (44.6 %), one can observe a strong effect of the crystalline phase melting when the sample is heated above the T_m . It is interesting to observe that permeability rise starts at a temperature lower than T_m , indicating that close to T_m an amorphous phase of the PEO starts to act as a plasticizer for macromolecular chains, taking part in the crystallite formation. It should be mentioned that the process of the temperature change of the experimental setup is a slow process; the stabilization of the temperature when the tempered part of the setup is heated up or cooled down takes from 1 to 2 hours, and results of permeability measurement at each temperature can be considered as static from the point of view of temperature influence on the sample, in contrast to e.g. DSC or DSC measurements where the sample response to the temperature change is a function of the speed of heat transfer to the sample. It means that at a given temperature of permeability measurement, the sample can be considered to be in an equilibrium state where all parts of the crystalline phase are able to melt at this temperature. In this sense, during the heating process, it was possible to observe a snappish increase in permeability at temperatures close to the melting point. Before 35 °C and after 55 °C, the evolution of the permeability coefficient was gradual, as it should be expected for the parameters of the thermally activated process. In the range of temperatures 35-55 °C, the melting process occurred. During the cooling process, similar behavior was observed, but in this case, the range for the crystallization process was between 35 °C to 25 °C. It is a sign that after a membrane “conditioning” by crystallite melting, the behavior of the polymer could be different. With respect to selectivity, it was not affected significantly by temperature. Small deviations were observed, but the behavior followed the expected path. This observation leads us to the conclusion that the PEO crystalline phase is not taking part in the gas molecule transport through the bulk of a PEO-containing polymer, and permeability coefficients are increasing and decreasing in accordance with the content of the amorphous phase available for gas transport.

Similar behavior was observed for the sample PEO6000, but the effect of crystallinity is lower. During the heating and cooling processes, the effect of melting and crystallization was perceived in the range of 25 to 30 °C. For the rest of the copolymers,

PEO2000 and the PEBAX[®] membranes (dissolved in methanol/water and dissolved in NMP), not significant melting and crystallization effects were detected. As in the previous case, there wasn't observed significant changes in the selectivity discarding of course the effect due to the measurement temperature.

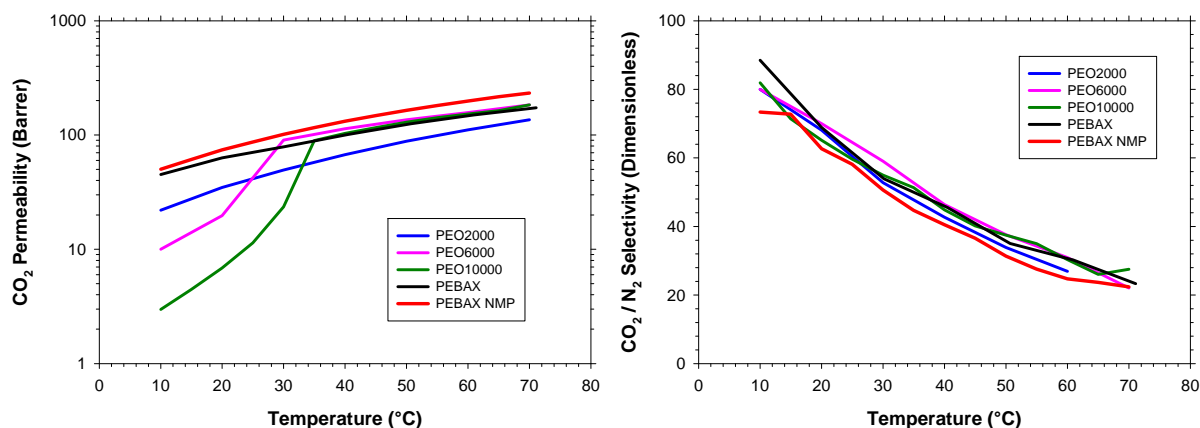


Figure 5.- a) CO₂ permeability and b) CO₂/N₂ selectivity; as a function of the measurement temperature during the heating process for all the copolymers studied in this work.

In Figure 5 is shown the evolution of the CO₂ permeability and CO₂/N₂ selectivity for all the copolymers during the heating process. It is clear to observe for lower temperatures the effect of the crystallinity for the PEO6000 and PEO10000 copolymers. Above the melting temperature the permeability of all the copolymers was comparable. PEO2000 showed a lower permeability than the rest of copolymers probably due to a slightly lower amount of poly (ethylene glycol) in the copolymer, or because not all the PEO chains, despite being at similar content, is effective for the interaction with CO₂, and this is especially remarkable for PEO with short chain length. For the sample of PEBAX[®] prepared from the solution in NMP the permeability was slightly higher compared to the sample prepared from the ethanol/water solution. The effect could rise from the different solvent quality in respect to the PEBAX[®] which results in differences of polymer gelation, phase separation etc. during the sample preparation and differences in the sample microstructure related to the polyamide phase will remain after the thermal treatment procedure used in the work which doesn't affect the polyamide phase. PEO phase in the vicinity of two different hard polyamide phases will behave differently and will result in slight difference of the e.g. CO₂ permeability coefficient but not in the selectivity as it can be seen from the Figure 5. This effect will be studied in upcoming work. For the rest of the copolymer the results were completely the same.

Figure 6 shows typical Robeson's plot for the polymers studied. It is possible to observe the evolution of the properties with the measurement temperature, although it should be remembered that the upper bound were described for an experimental temperature of 35 °C³⁰. Of course this upper bound is influenced by the temperature as Rowe et al. confirmed³¹. After overpass the melting point of the polyether, all the samples showed similar behavior. The evolution of the properties, with the measurement temperature, suggests that studied materials could overpass the Rowe's upper bound at higher temperatures.

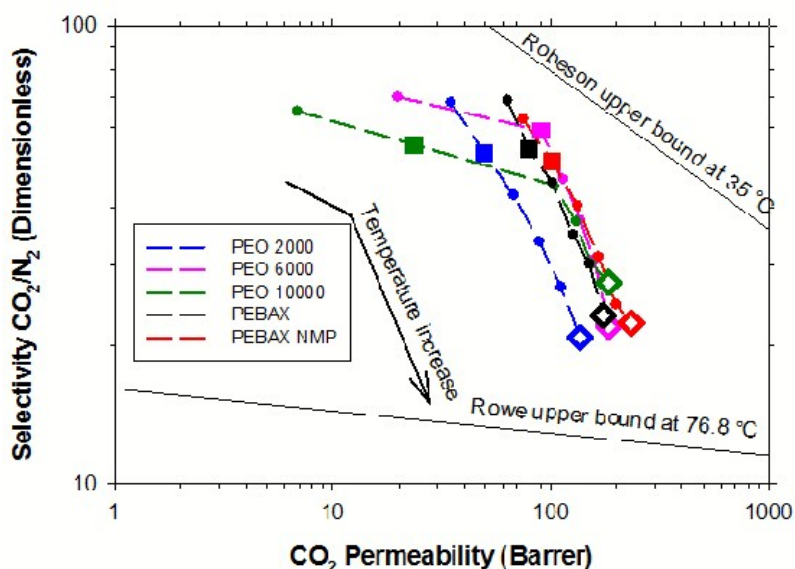


Figure 6. Robeson's plot for the separation CO₂/N₂ for the polymers studied at temperatures from 20 to 70 °C (symbols connected with dash lines). Big solid symbols represent experimental points at 30°C; big open symbols – at 70°C.

Attending the composition of the samples, if we compare poly(ether-amide)s and poly(ether-imide)s the main differences are the amide and imide groups. With respect to the composition of this copolymers, PEBAX has a linear hard block whereas the copoly(ether-amide)s more rigid hard block due to crystalline phase presence. It seems that the effect of the hard block only has a relation with the phase segregation in this kind of copolymers³², while the separation properties are affected only for the soft segment, poly(ethylene glycol) in both cases. The selectivity is almost the same in all the cases, which is a clear proof that the most important is gas transport through the soft block while hard block even being amorphous as in the case of poly(ether-imides) cannot influence significantly overall gas transport properties due to significantly lower permeability coefficients. After overpass the melting point, the permeability for all the copolymers became comparable, and again this should be due to the effect of the nearly same content of the soft block in copolymers under study. This is really important because it is possible tuning materials for post-combustion processes by the simple design of poly(ethylene glycol) copolymers with the most convenient hard block. In this sense, it will be possible to look for an improvement in solvent and thermal resistance and the most adequate solubility of the polymer as long as the copolymers are capable of undergoing phase segregation.

Table 2. Gas permeation properties for the homo- and co-polymers.

Comparing the permeation properties of the segments^{22, 25, 33, 34} with the properties of the materials used in this work, it's simple to observe that the main separation abilities are provided by the rubbery segments. In Table 2 are shown the gas transport parameters for the blocks and for the copolymers. For the copolymer used in this work, two temperatures were described. The first temperature (35 °C) was used to compare with the literature data. The second one (60 °C) was selected for two reasons: it

Polymer	Temperature / °C	Permeability (Barrer)		Selectivity (Dimensionless)		Reference
		P(H ₂)	P(CO ₂)	α CO ₂ /N ₂	α CO ₂ /H ₂	
Nylon 6	30	0.58	0.00049	9.6	0.00084	³⁵
BPDA-ODA	30	3.68	0.90	38.0	0.24	^{22, 34}
PEO semi-crystalline	35	1.8	12.0	48.0	6.7	²⁵
PEO amorphous	35	21.0	143.0	47.7	6.8	²⁵
PEBAX [®] 1657 Ethanol/water	35	6.67	90.1	47.3	13.5	This work
	60	23.6	149.7	28.6	6.3	
PEBAX [®] 1657 Nmp	35	13.2	116.2	44.7	8.8	This work
	60	32.2	198.4	24.7	6.2	
PEO2000	35	7.6	54.8	47.7	7.2	This work
	60	19.8	111.2	26.9	5.6	
PEO6000	35*	10.4/11.3	95.8/101.8	49.0/51.1	9.2/9.0	This work
	60	22.9	153.0	30.4	6.7	
PEO10000	35*	2.7/8.9	12.36/89.31	40.6/51.3	4.6/10.0	This work
	60	24.7	151.5	30.1	6.1	

was enough elevated to have all the poly (ethylene glycol) in amorphous state; and it's within the application temperature range of the (post-combustion processes). Values of permeability coefficient determined at 35°C are shown for both heating and cooling stages to demonstrate the effect of the PEO recrystallization in copoly(ether-imide)s.

As it was expected, the permeabilities for the homopolymers or hard blocks (nylon 6 and BPDA-ODA) are low compared to those of PEO, as well the selectivities for this glassy polymers were considerable different from each other and from PEO. Considering the crystallites as an impermeable barrier, the amorphous PEO has a one order of magnitude higher permeability than the semicrystalline PEO. Despite this, the selectivity is similar, indicating that the permeation process occurs through the remaining amorphous phase. A more extent discussion on gas transport mechanisms in the PEBAX[®] membranes with different polyethylene glycol length were carried out by Rahman et al.³⁵. Then, if we analyze the results for the copolymers, we should expect three different possibilities for the evolution of the permeation properties: permeability similar to the hard block, similar to the soft block, or a combination of properties between both segments. The results showed properties closer to the behavior of the soft blocks. This is a clear indication that the gas transport is fully controlled by the properties of amorphous poly(ethylene glycol) phase. Then, if the process occurs through the PEO, and all the copolymers have the same amount, it's expected similar properties for all of them. This was right but not for all the cases and temperatures.

For PEBAX[®] samples prepared from different solvents significant differences in properties were found. The copolymer dissolved in NMP showed higher permeabilities and lower selectivities than the copolymer dissolved in ethanol/water. Once verified by TGA that there wasn't remained solvent in the copolymers, the explanation should be in a relation with the interaction between the chains. The elimination of some of the typical hydrogen bonds formed in polyamides, could produce and increase on the mobility chains, and then an increase on the permeability and most probably with some effect on the selectivity. These effects will be studied with more detail in future works. In the case of the copolyimide, at 35 °C, the crystallinity has a really important

role. Higher crystallinity, like in the case of PEO10000, produced low permeabilities. Comparing the heating and the cooling cycle for PEO10000, it was observed great differences in the selectivities (CO_2/N_2 and CO_2/H_2). While the selectivity in the heating cycle was low, during the cooling cycle the selectivity was similar to the others copolyimides, and higher than selectivity for the copolyamide PEBAX[®].

Comparing the synthesized copolymers, the permeability for the sample PEO2000 was lower than for the rest of copolymers. Shorter chains produced lower mobility and then lower permeability. Interesting is stuck out the permeability at 60 °C. The permeability values were almost the same for the samples PEBAX (ethanol/water), PEO6000 and PEO10000, and the selectivity were higher for the copoly(ether imides). Therefore, although it's true that the permeation properties are regulated, especially the permeability, by the soft block, there could be an influence of the hard block on the selectivity factor. The CO_2 permeability for the copolymers is not comparable to the permeability of pure amorphous PEO, but of course the content of the copolymers is around 57 % while the pure PEO is 100%. The permeability could be increased in an effective way by for example the addition of inorganic nanoparticles^{36,37}. Nevertheless, as it was effectively predicted³⁸, the evolution in the permeability shouldn't be a really big growth on the permeability. On the other hand, it's necessary a certain level environmental resistance and mechanical properties, which is not simple when the PEO content is very high due mainly to the high solubility in solvents like water, and very poor mechanical properties.

Table 3. Activation energies for CO_2 permeability (E_p) and the differences in the activation energies for CO_2 and N_2 .

	PEBAX [®] EtOH/H ₂ O	PEBAX [®] Nmp	PEO2000	PEO6000	PEO10000
$E_p / \text{KJ} \cdot \text{mol}^{-1}$	13.3	16.1	20.8	14.4	16.2
$E_{p\text{CO}_2} - E_{p\text{N}_2} / \text{KJ} \cdot \text{mol}^{-1}$	-17.1	-18.2	-21.2	-17.8	-18.3

The dependence of gas diffusion on temperature can be expressed in terms of an Arrhenius type relationship that considers the movement of the gas molecules through a membrane as a thermally activated process³⁹. Therefore, by an Arrhenius' representation was possible to obtain the activation energies for the carbon dioxide and nitrogen permeability (E_p) (display in Table 3).

The character positive or negative of the energies has a direct relationship with the evolution of the behavior with the temperature. In this sense, the CO_2 permeability will increase with the temperature, and the bigger increase should be produce to the sample PEO2000. In the case of the selectivity is the opposite behavior as it was tested previously. With the exception of PEO2000, the rest of the samples showed very close values, so it could be expected a similar evolution of separation properties of the samples with the temperature.

Conclusions

A set of new copoly(ether-imide)s were prepared by the reaction between an aromatic dianhydride (BPDA), an aromatic diamine (ODA), and poly(ethylene oxide) diamine (PEO) with different length (2000, 6000 and 10000) and the same content, in order to compare with the commercial copoly(ether-amide) PEBAX[®] MH 1657 (obtaining one from methanol/water and other from N-methyl pyrrolidinone). All the copolymer are able to experimented phase segregation, where the aromatic phase contributed to the mechanical and thermal stability of the polymer, the aliphatic phase contributed to high CO_2 permeability.

For copolyimides, the thermal stability in inert atmosphere was above 350 °C, showing two-step decomposition, being the PEO segments the less thermally stable units. For copolyamides, the thermal analysis showed one-step decomposition at similar temperatures.

By calorimetric techniques were determine the T_g , T_m and crystallinity of the copolymers. PEO T_g values between -50 and -57 °C were found for all the samples. For PEBAX samples small differences were found for the T_m and crystallinity, showing in both cases higher values the sample obtaining from the mixture methanol/water. Copolyimides showed an evolution with the molecular weight of the PEO. Then at higher PEO length was founded higher T_m and higher crystallinity.

Different heating and cooling cycles were carried out in order to determine the influence and evolution of the crystallinity with the permeability measurement temperature. It could not observed differences on the permeability properties of the samples at temperatures where the amount of crystalline PEO was zero or negligible (> 50 °C). With the exception of the shorter polyethylene glycol (2000 g mol⁻¹), the copolyimides showed similar results than the commercial copolyamide PEBAX®. Then, it's possible to tuning the structure of the polymers keeping the same properties.

These results show that it is possible to obtain PEO copolymers with controlled structures and really promising results for the application in *post-combustion* processes. Thus, the properties can be tuned to some extent by simply varying the aromatic composition in the copolymer. Besides, it is possible to control several parameters: cost, processability, solubility and other factors in order to adapt these copolymers for other specific applications and processes.

Acknowledgements

The authors would like to thank Silvio Neuman and Judith Grünauer for technical support. This work was financially supported by Helmholtz Association of German Research Centers through the Helmholtz Portfolio MEM-BRAIN.

Notes and references

1. R. W. Baker, *Industrial & Engineering Chemistry Research*, 2002, **41**, 1393-1411.
2. M. T. Bessonov, M. M. Koton, V. V. Kudryavtsev and L. A. Laius, eds., *Polyimides: Thermally Stable Polymers*, Consultants Bureau, New York, 1987.
3. E. Favre, *Journal of Membrane Science*, 2007, **294**, 50-59.
4. A. Tena, A. Marcos-Fernández, L. Palacio, P. Cuadrado, P. Prádanos, J. de Abajo, A. E. Lozano and A. Hernández, *Industrial & Engineering Chemistry Research*, 2012, **51**, 3766-3775.
5. H. Z. Chen, Y. C. Xiao and T.-S. Chung, *Journal of Membrane Science*, 2011, **381**, 211-220.
6. Y. Hirayama, Y. Kase, N. Tanihara, Y. Sumiyama, Y. Kusuki and K. Haraya, *Journal of Membrane Science*, 1999, **160**, 87-99.
7. M. Minelli, M. Giacinti Baschetti, D. T. Hallinan Jr and N. P. Balsara, *Journal of Membrane Science*, 2013, **432**, 83-89.
8. S. L. Liu, L. Shao, M. L. Chua, C. H. Lau, H. Wang and S. Quan, *Progress in Polymer Science*, 2013, **38**, 1089-1120.
9. J. Lillepär, P. Georgopoulos and S. Shishatskiy, *Journal of Membrane Science*, 2014, **467**, 269-278.
10. M. M. Rahman, V. Filiz, S. Shishatskiy, C. Abetz, S. Neumann, S. Bolmer, M. M. Khan and V. Abetz, *Journal of Membrane Science*, 2013, **437**, 286-297.
11. A. Car, C. Stropnik, W. Yave and K.-V. Peinemann, *Journal of Membrane Science*, 2008, **307**, 88-95.

12. V. Bondar, B. Freeman and I. Pinnau, *Journal of Polymer Science Part B: Polymer Physics*, 2000, **38**, 2051-2062.
13. B. Wilks and M. E. Rezac, *Journal of applied polymer science*, 2002, **85**, 2436-2444.
14. J. H. Kim, S. Y. Ha and Y. M. Lee, *Journal of Membrane Science*, 2001, **190**, 179-193.
15. D. Ayala, A. E. Lozano, J. de Abajo, C. García-Perez, J. G. de la Campa, K. V. Peinemann, B. D. Freeman and R. Prabhakar, *Journal of Membrane Science*, 2003, **215**, 61-73.
16. K. Tanaka, H. Kita, K. Okamoto, A. Nakamura and Y. Kusuki, *Journal of Membrane Science*, 1989, **47**, 203-215.
17. K.-i. Okamoto, M. Fujii, S. Okamoto, H. Suzuki, K. Tanaka and H. Kita, *Macromolecules*, 1995, **28**, 6950-6956.
18. H. Suzuki, K. Tanaka, H. Kita, K. Okamoto, H. Hoshino, T. Yoshinaga and Y. Kusuki, *Journal of Membrane Science*, 1998, **146**, 31-37.
19. T. A. Barbari, W. J. Koros and D. R. Paul, *Journal of Membrane Science*, 1989, **42**, 69-86.
20. A. Tena, A. E. Lozano, L. Palacio, A. Marcos-Fernández, P. Prádanos, J. de Abajo and A. Hernández, *International Journal of Greenhouse Gas Control*, 2013, **12**, 146-154.
21. D. Husken, T. Visser, M. Wessling and R. J. Gaymans, *Journal of Membrane Science*, 2010, **346**, 194-201.
22. A. Tena, A. Marcos-Fernández, L. Palacio, P. Prádanos, A. E. Lozano, J. de Abajo and A. Hernández, *Journal of Membrane Science*, 2013, **434**, 26-34.
23. A. Tena, A. Marcos-Fernández, A. E. Lozano, J. G. de la Campa, J. de Abajo, L. Palacio, P. Prádanos and A. Hernández, *Journal of Membrane Science*, 2012, **387-388**, 54-65.
24. A. Car, C. Stropnik, W. Yave and K. V. Peinemann, *Separation and Purification Technology*, 2008, **62**, 110-117.
25. H. Lin and B. D. Freeman, *Journal of Membrane Science*, 2004, **239**, 105-117.
26. S. R. Reijerkerk, M. H. Knoef, K. Nijmeijer and M. Wessling, *Journal of Membrane Science*, 2010, **352**, 126-135.
27. A. M. Shishatskii, Y. P. Yampol'skii and K. V. Peinemann, *Journal of Membrane Science*, 1996, **112**, 275-285.
28. A. Marcos-Fernández, A. Tena, A. E. Lozano, J. G. De La Campa, J. De Abajo, L. Palacio, P. Prádanos and A. Hernández, *European Polymer Journal*, 2010, **46**, 2352-2364.
29. C. Casado-Coterillo, J. Soto, M. T Jimaré, S. Valencia, A. Corma, C. Téllez and J. Coronas, *Chemical Engineering Science*, 2012, **73**, 116-122.
30. L. M. Robeson, *Journal of Membrane Science*, 2008, **320**, 390-400.
31. B. W. Rowe, L. M. Robeson, B. D. Freeman and D. R. Paul, *Journal of Membrane Science*, 2010, **360**, 58-69.
32. A. Tena, A. Marcos-Fernández, A. E. Lozano, J. G. de la Campa, J. de Abajo, L. Palacio, P. Prádanos and A. Hernández, *Journal of Membrane Science*, 2012, **387-388**, 54-65.
33. E. Picard, A. Vermogen, J. F. Gérard and E. Espuche, *Journal of Membrane Science*, 2007, **292**, 133-144.
34. J. Y. Park and D. R. Paul, *Journal of Membrane Science*, 1997, **125**, 23-39.
35. M. M. Rahman, V. Filiz, S. Shishatskiy, C. Abetz, P. Georgopoulos, M. M. Khan, S. Neumann and V. Abetz, *ACS Applied Materials & Interfaces*, 2014.
36. V. Nafisi and M.-B. Hägg, *Journal of Membrane Science*, 2014, **459**, 244-255.
37. V. Nafisi and M.-B. Hägg, *ACS Applied Materials & Interfaces*, 2014, **6**, 15643-15652.
38. A. Tena, M. de la Viuda, L. Palacio, P. Prádanos, Á. Marcos-Fernández, Á. E. Lozano and A. Hernández, *Journal of Membrane Science*, 2014, **453**, 27-35.
39. R. E. F. Kesting, John Wiley & Sons, New York, Editon edn., 1993.

