

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Surface-modified spherical activated carbon materials for
pre-combustion carbon dioxide capture

Nannan Sun^{1,3,*}, Chenggong Sun¹, Hao Liu¹, Jingjing Liu¹, Colin E. Snape¹,

Kaixi Li², Wei Wei³, Yuhan Sun³

¹ Energy and Sustainability Research Division, Faculty of Engineering, University of Nottingham, University Park, Nottingham NG7 2RD, UK

² Key Laboratory of Carbon Materials, Institute of Coal Chemistry, Chinese Academy of Sciences, Taiyuan 030001, PR China

³ CAS Key Lab of Low-Carbon Conversion Science and Engineering, Shanghai Advanced Research Institute, Chinese Academy of Sciences, Shanghai 201203, PR China

Abstract

Surface modification of activated carbon beads via HNO₃ oxidation and subsequent amination at elevated temperatures was investigated as a means to improve their performance for CO₂ capture, and the effects of the resultant changes in porosity and surface chemistry on adsorption characteristics of the samples was studied. Characterisations conducted with elemental analysis, physical adsorption, x-ray photoelectron spectroscopy and scanning electron microscope demonstrate that both the porosity and surface chemistry of the carbon beads were tuned by the modification without any alteration of the integrity of the desirable spherical morphology. Adsorption evaluation with both thermogravimetric analysis and high pressure volumetric analysis under various conditions indicate that one of the modified samples had a high CO₂ adsorption capacity (8.64 mmol/g at 20 bar and 30 °C) with fast adsorption/desorption kinetics, superior durability and good selectivity over N₂ and H₂. Both the unique spherical form (diameter=1.2±0.2 mm) and the superior adsorption performance render the modified carbon beads a promising candidate for CO₂ capture especially in pre-combustion capture using pressure swing adsorption.

* Corresponding author. E-mail: sunnn@sari.ac.cn (Nannan Sun)

Key Words: Carbon, Adsorption, CO₂, Carbon Capture.

1. Introduction

Various world energy outlooks suggest that in spite of the great efforts and heavy investments that have been made to improve energy efficiency and increase the share of renewable energy in primary energy supply, fossil fuels will continue to dominate the world primary energy supply for the coming decades [1-4]. Consequently, significant contributions from carbon capture and storage (CCS) will be required to combat with climate change to increase the opportunity for the continual use of fossil fuels [5-7]. However, the current state-of-the-art aqueous amine scrubbing technology for CO₂ capture is prohibitive for wide deployment due to its high operational costs and high energy penalty associated with absorbent regeneration [8,9]. On the other hand, solid adsorbents looping technology (SALT) offers a viable alternative that has many advantages over solution-based technologies, including substantially reduced energy consumption, greatly minimised health, safety and environmental hazards and greater structural variability of the adsorbents that can be selected.

Over recent years, a wide array of solid adsorbents have been used for CO₂ capture, those including zeolites, carbon materials, inorganic oxides, amine modified silicates and more recently, the more niche metal-organic frameworks (MOFs) and covalent organic frameworks (COFs) materials [10-12]. In previous investigations, a high adsorption capacity is the most pursued parameter among many others [10, 11]. In practical carbon capture applications however, the so-called “working capacity” should be more important as it concerns both material and engineering issues. Other challenges facing real carbon capture applications, such as the large volume of flue gas at high flow rate, complicated chemical compositions of the flue gas and fast capture rate that is required, should also be emphasized [13]. Therefore, one needs to consider process costs, process efficiencies and engineering feasibilities for a real carbon capture process, and these criteria impose further requirements for applicable CO₂ adsorbents as illustrated in Figure 1. For example, the factor of adsorption/desorption kinetics

(Factor 6 in Figure 1) is located on the left-bottom of the triangle in Figure 1 because adsorbents with fast kinetics can increase the efficiencies of a capturing process and lowering related costs by accelerating the adsorption-desorption cycles for a given carbon capture facility. Meanwhile, faster cycling requires a better designed and integrated adsorption/desorption subunit, giving rise to further challenges in process engineering and limitations in adsorbents selection. The comprehensive requirements for CO₂ adsorbents are also discussed in a recent review by Sayari et al. [14].

A screening of the possible adsorbents for CO₂ capture indicates that carbon based adsorbents represent a good option to balance all the factors in Figure 1 due to its promising properties such as low cost for preparation, chemical inertness, easy-to-regeneration, etc. [10, 11, 14, 15]. As a result, the development of effective carbon-based adsorbent materials for CO₂ capture has received significant attentions over recent years [15], related works including: i) preparation of carbons by templating methods [16, 17] or direct carbonization of coal [18], polymers [19, 20] and biomass residuals [21-25]; ii) chemical activation of carbon by KOH [21] and K₂CO₃ [22, 26]; and iii) modification of carbon by N doping [17, 20, 27], S doping [28] and amine loading [29, 30]. More recently, some carbon materials with exceptionally high CO₂ uptake were reported. For example, Srinivas et al. [31] prepared MOF-derived porous carbons with CO₂ adsorption capacities as high as 27.0 mmol/g at 27 °C and 30 bar. By carbonation and activation of selected coal tar pitches, a CO₂ uptake of 20.5 mmol/g was obtained by Shao et al. at 25 °C and 18 bar [22]. In addition to these results, Sjoström et al. [32] has reached the conclusion that carbon can be the viable adsorbents for practical CO₂ capture especially if their CO₂ uptake can be improved, which emphasized again that carbon-based materials have great potential in CO₂ capture, particularly for pre-combustion capture where the CO₂ partial pressure in the gas stream is much higher than in post-combustion flue gases.

Although many carbon-based adsorbents currently under development have

superior adsorption capacity, they are produced predominantly in low-density powder form which is unsuitable for practical applications and therefore needs to be further fabricated via pelletisation or granulation process with the aid of binders or additives, which can often lead to significant loss of their adsorption performance [33-38]. To address this issue, some researchers tried to prepare carbon monolith/honeycomb adsorbents using purpose-designed molding processes [20, 39, 40], however these methodologies often involves the use of complicated processes, and the fabricated materials, mostly in their cylindrical and/or rod shapes, are not particularly suitable for use in SALT processes (e.g. circulating fluidized bed) due to serious attrition problems that may arise from the undesirable material morphology.

In our previous work, a cost-effective and easy-to-scale-up hydrothermal technique has successfully been developed to produce spherical active carbon materials from a variety of polymeric precursors. The prepared porous carbon beads possess the most favourable properties for applications in continuous CO₂ capture using circulating fluidised bed, such as their tuned porosity, high mechanical strength and desirable spherical forms with uniform diameters [41]. In this paper, different post-treatments, including HNO₃ oxidation and amination were investigated as an effective means to further improve the CO₂ adsorption performance of the carbon beads, the adsorption behaviour of the samples was rationalized based on extensive characterization tests, and their application potential in CO₂ capture was evaluated based on the analysis of adsorption capacity, selectivity, kinetics and reusability.

2. Experimental

2.1 Preparation of the original carbon beads

The parent carbon beads were prepared from phenolic resins using a novel hydrothermal process. Typically, novolac-type phenolic resins were first dissolved in a formulated solvent to form a solution which was later mixed with

aqueous polyvinyl alcohol (PVA) and sealed in an autoclave. The mixture was then heated to 130 °C at a rate of 5 °C/min and held at this temperature for 1 h with rigorous stirring (400 RPM). The autoclave reactor was then cooled down to ambient temperature to allow the formed resin beads to be recovered. The resin beads were first washed adequately with distilled water and dried at 110 °C for 24 h before it was carbonised in N₂ at 800 °C for 1 h to yield the carbon beads (Sample *AC*, hereafter) for further treatments.

2.2 Surface modification of sample *AC*

The *AC* sample was further submitted to HNO₃ oxidation by mixing 10 g of *AC* and 250 ml of concentrated HNO₃ in a beaker at room temperature (25 °C) for 1 h (Sample *oxAC*), after washing and drying, the obtained *oxAC* was aminated in a tube furnace under NH₃ at 300, 600 and 800 °C to afford sample *oxAC-300NH3*, *oxAC-600NH3* and *oxAC-800NH3*, respectively. For comparison, a sample thermally treated at 800 °C in N₂ after HNO₃ oxidation was also prepared (*oxAC-800N2*).

2.3 Characterization

Textural properties of the samples were measured by N₂ physisorption on an Micromeritics ASAP 2420 instrument at -196 °C and CO₂ at 0 °C. Prior to any measurements, all samples were first degased at 120 °C overnight. The apparent surface area (S_{BET}) was calculated according to the method suggested by Parra et al. [42]. The cumulative pore volumes (V_{total}) were calculated from the amount of nitrogen adsorbed at P/P_0 of ca. 0.99, and the average pore diameter (D_{avg}) was calculated by $4V_{\text{total}}/S_{\text{BET}}$. The micropore volume (V_{micro}) and surface area (S_{micro}) were determined by the *t-plot* method. Narrow micropore volumes (W_0) of the samples were calculated by the Dubinin-Radushkevich (DR) method [43] from CO₂ isotherms obtained at 0 °C. In theory, the DR method allows the calculation of average width of the narrow micropores (L_0) based on the empirical relationship between L_0 and the characteristic adsorption potential (E_0)

in the DR equation [44]. However, it was reported that this relationship is influenced by the surface chemistry of samples [45]. Therefore, L_0 was not calculated here due to the significant differences in the surface properties of the samples.

X-ray photoelectron spectroscopy (XPS) was carried out using a Kratos AXIS ULTRA instrument with an Al K α source (energy 1486.6 eV). The high resolution scans were charge corrected to the main C1s peak (284.8 eV). Morphology of the samples was examined with a QUANTA 600 scanning electron microscope (SEM) instrument. An elemental analyser (Thermo EA1112 series) was used to determine the carbon, hydrogen, and nitrogen contents of the samples.

2.4 Evaluation of the CO₂ adsorption performance

The CO₂ capture behaviors of the samples were measured by a TA Q500 thermal gravimetric analyser (TGA) under ambient pressure. In brief, 20-30 mg of the samples were loaded in a platinum pan, heated to 115 °C and held at this temperature in flowing N₂ (100 mL/min) for 10 min to remove any physisorbed moisture and/or CO₂, and the temperature was then decreased (10 °C/min) to and equilibrated at 30 °C. To start the adsorption tests, the gas flow was switched to 100 mL/min of pure CO₂ or 15 vol.% CO₂ in N₂ to perform CO₂ adsorption tests and the temperature was held at 30 °C for 30 min in order for the adsorption to reach equilibrium. The samples were then heated to 115 °C at a ramp rate of 0.5 °C/min. The use of such a slow ramp allows the adsorption to change with temperature in a quasi-equilibrium state and the mass change recorded can be used to assess the influence of temperature on CO₂ adsorption capacity. Reversibility of CO₂ adsorption/desorption was previously checked to make sure the as-obtained data is valid.

High pressure CO₂ adsorption tests were carried out with a High Pressure Volumetric Analyser (Particulate Systems HPVA-100). Prior to any tests, the sample was first degassed in vacuum at 120 °C overnight to remove any

physisorbed moisture and/or CO₂.

3. Results and Discussion

3.1 Characterization

3.1.1 Elemental Analysis

Table 1 presents the results from elemental analysis (EA) of the samples. The parent *AC* showed a high carbon content of 93.6 wt. %. This result is expectable as the sample was derived from phenolic resin precursors containing little mineral substances. After HNO₃ treatment (sample *oxAC*), the contents of oxygen and nitrogen increased by an order of magnitude due to the introduction of surface nitrogen and oxygen-bearing functionalities, such as hydroxyl, carboxyl and quinone groups [46]. Significant proportions of these functionalities were eliminated during the subsequent thermal treatment in N₂ as indicated by the decreased oxygen and nitrogen contents in the sample *oxAC-800N2*. Similarly, both the nitrogen and oxygen contents diminished when *oxAC* was treated by NH₃ at 300 and 600 °C, which is a typical behaviour for the pyrolysis of carbon precursors [26]. Interestingly, although the *oxAC* sample showed the highest bulk nitrogen content, the highest surface nitrogen content was observed for the sample *oxAC-300NH3* as measured by XPS. This result confirms the occurrence of surface reactions between NH₃ and oxygenated groups to introduce nitrogen functionalities onto the surface of *oxAC-300NH3*. Despite the decrease in surface nitrogen concentration observed for *oxAC-600NH3*, further increase of the amination temperature to 800 °C led to the increase of nitrogen content in the resulted *oxAC-800NH3*, indicating a different mechanism of nitrogen incorporation process at different temperatures that might lead to the formation of different nitrogen-bearing functionalities. It is believed that at high temperatures such as 800 °C, most of the oxygenated groups have decomposed, and therefore the surface amination was mainly dominated by the anchoring of free radicals such as NH₂ and NH from the decomposition of NH₃, and the formed nitrogen functionalities had a

higher opportunity to further cleavage the N-H bond, leading to the formation of pyridine-like structures. This assumption is also in line with decreased H/N mass ratio with the increasing of amination temperature (Table 1).

3.1.2 Textural properties

Figure 2 and Table 2 summarise the textural properties of the samples measured by the physical adsorption of N₂ at -196 °C and CO₂ at 0 °C. According to the IUPAC classification, all but the *oxAC* sample exhibited a type-I isotherm, suggesting the materials are mainly microporous [47]. The isotherm of *oxAC* is characterized by an opening knee and a considerable increase of N₂ uptake at higher partial pressure region, indicating its higher fraction of mesopores.

As shown in Table 2, the parent carbon beads (sample *AC*) have a moderate surface area (S_{BET}) of 972 m²/g with a total pore volume (V_{total}) of 0.45 cm³/g. After HNO₃ oxidation, the S_{BET} and V_{total} of *oxAC* decreased with slightly increased average pore diameter (D_{avg}). Upon removal of the generated oxygen-containing groups by thermal treatment in N₂, a significant improvement in porosity can be observed for *oxAC-800N2*, which has a surface area comparable to that of the parent sample *AC*. It has been frequently reported that HNO₃ oxidation can reduce the porosity of carbon materials [47], due to either the blockage of micropores by the formed oxygen-containing functionalities or partial destruction of the carbon framework by damaging the basal planes [49]. Although pore blockage cannot be ruled out based on the present data, the high microporosity of the *oxAC-800N2* convinced us that extra micropores, which could be recovered by the removal of oxygen-containing functionalities during thermal treatment, were formed via the penetration of the carbon framework by the oxidant. As shown in Table 2, both *oxAC* and *oxAC-800N2* exhibit W_0 values similar to that of the parent sample *AC* of ca. 0.24 cm³/g, suggesting that the influence of HNO₃ treatment on the narrow micropores is small. This can be expected, given the difficulty for the oxidant to enter these narrow micropores as a result of the high surface tension of the aqueous solution and the hydrophobic nature of the carbon surface.

A substantial increase in microporosity was observed for the 300 °C aminated sample (*oxAC-300NH3*). It is interesting to note that while the total micropore volume of the *oxAC300NH3* increased by over 20% as compared with *oxAC* (from 0.28 to 0.35 cm³/g), the total pore volume of this sample remained relatively unchanged (0.41 versus 0.39 cm³/g). This implies that the mesopores in the sample *oxAC* diminished due to pore narrowing during the amination, which might be triggered by the reactions of NH₃ with the oxygenate groups [50-52]. Similar assumption can be applied to explain the increase of W_0 for this sample because carbon activation by NH₃ becomes less effective under temperatures as low as 300 °C. With increasing the amination temperature from 300 to 800 °C, further activation/surface modification of the carbon beads can be achieved, which imposed a range of changes on the porosity of the samples such as formation of new narrow-micropores, widening/blocking of the existing wide- and narrow-micropores, etc. [18, 27]. These synergetic effects led to a gradual increase in $S_{\text{micro}}/V_{\text{micro}}$ and a decrease in W_0 . Consequently, both the SA_{BET} and V_{total} increased for the *oxAC-600NH3* and *oxAC-800NH3* samples. It seems that the increase was most likely induced by the enhancement of wide-microporosity as indicated by the similar increasing of V_{total} and V_{micro} . Similar results, namely the increased wide-microporosity during enhanced activation, were also observed by An et al. during their attempts to carbonise activated carbon fibre-phenolic resin composites [39].

3.1.3 Morphology

Morphology of the samples observed by SEM are presented in Figure 3. In general, surface modification imposed little influence on the morphological integrity of the desired spherical form, and all the samples showed similar morphology (details not shown). It has been reported this kind of spherical materials possess great potential and engineering flexibilities in large scale process as their shape and texture exhibit the ability to minimize material attrition in circulating fluidized bed reactors [53]. Interconnected 3D porous network structures are also evident inside the carbon beads with irregular openings and cracks in μm -scale on both the external and internal

surfaces of the samples (Figure 3a, 3b). These features serve as channels for fluids to pass through and thus facilitate the more effective diffusion of CO₂ molecules within the interior porous networks present in the carbon beads, which is of vital importance for the adsorption efficiency and kinetics of the materials [22]. A closer check of the carbon beads revealed a relatively smooth outer surface (Figure 3c), indicating a better capability for these samples to resist attrition. In contrast, as showed in Figure 3d, the surface of cavities inside the carbon beads are sponge-like frameworks comprising of relatively uniform micro-spheres with a diameter of ca. 100 nm.

3.1.4 Surface chemistry

It has been recognized that the CO₂ affinity of N functionalities incorporated into graphene structures were governed by the mobility and delocalization of the lone pair electrons on the N atoms, which is determined by adjacent chemical environment [54]. Therefore, XPS was carried out over the oxidized and aminated samples to investigate their surface chemistries. The quantified surface compositions are listed in Table 1. For clearer comparison with the EA results, the initially obtained atomic compositions were converted to weight-percentage concentrations. As can be seen, increases in nitrogen and oxygen contents were evident as a result of HNO₃ oxidation, being consistent with the EA results. Substantially higher surface N/C mass ratios measured by XPS were found for all aminated samples, while the values obtained for *oxAC* from EA and XPS were similar. On the other hand, it is interesting to note that all the O/C mass ratios measured by XPS were considerably lower than those measured by EA, being in contrast to the trend observed for the N/C mass ratios. This clearly indicates again that the oxidation by liquid phase HNO₃ was so aggressive that not only the surface, but also the carbon framework was altered by involving nitrogen and oxygen atoms. The hypothesis can be evidenced by the considerably higher O/C mass ratios measured by EA than that by XPS, which is indicative of the preferential occurrence of oxygenated functionalities within the carbon framework in addition to the outmost surface. As mentioned in Section 3.1.2, due to the hydrophobic nature of the *AC* surface, it is reasonable to assume that during oxidation, the distribution of aqueous HNO₃ over the carbon surface is unlikely to be uniform but preferably in the

form of micro droplets. This might lead to the localised penetration of the corrosive HNO_3 into the the carbon framework, creating interior “channels” with abundance of oxygenate groups. By comparing the textural parameters of *oxAC* and *oxAC-800N2* (Table 2), it can be concluded that these “channels” can be regarded as blocked micropores where oxygen present in various functionalities that can hardly be detected by XPS. In contrast, there is little limitation on the accessibility of the NH_3 molecule to enter the micropores, and thus amination occurs more evenly and preferably on the surface, leading to pore widening and surface enrichment of nitrogen as revealed by the higher N/C ratio measure by XPS than that of EA.

Figure 4 presents the N1s spectra and the peak fitting results of the N-containing samples, for the sample *oxAC*, peaks at 399.4, 401.0, and 406.0 eV can be attributed to pyridinic, quaternary and nitro-nitrogen according to the NIST XPS Database. After amination, a new peak was detected at 400.0 eV, which is attributable to pyrrolic and/or pyridone nitrogen. Although these two functionalities cannot be effectively differentiated by XPS, it was reported that pyridone nitrogen is more stable than pyrrolic nitrogen at elevated temperatures [55], therefore pyridone has a higher opportunity to survive on the aminated samples. Among the identified groups, pyridinic nitrogen has lone pair of electrons, which may enhance the alkaline character of the surface, and thus would facilitate the adsorption of acidic CO_2 . As for the pyridone nitrogen, Fan et al. has reported that the $p-\pi$ conjugation between the -OH and the aromatic rings endows the ortho-N with a higher electron density, which can lead to higher affinity for CO_2 adsorption [26]. It is noteworthy that the delocalization and conjugation effects from electrons of nitrogen, aromatic rings and other atoms have a significant impact on the basicity of nitrogen-containing groups, therefore it is arbitrary to allege the relative importance of these groups in terms of their affinity to acid gases such as CO_2 [56, 57]. For the quaternary and nitro- nitrogen on the other hand, they are partially positive charged due to the adjacent oxygen and aromatic rings, therefore it is reasonable to assume a limited contribution for these functionalities to the adsorption of CO_2 .

The relative fractions of the identified nitrogen functionalities are tabulated in

Table 3. It can be observed that with the increase of amination temperature, the fraction of nitro-nitrogen decreased notably due to the removal and/or reduction of these functionalities, while the relative abundance of pyridone and quaternary nitrogen were less affected due to their higher thermal stability as compared with nitro-nitrogens. A higher fraction of pyridinic nitrogen can be seen for the samples aminated at higher temperatures, which is indicative of the enhanced surface amination by the formed N- radicals and further cleavage of the N-H bonds at higher temperatures as has been discussed in Section 3.1.1.

3.2 CO₂ adsorption behaviour

3.2.1 Adsorption capacity

The spherical carbon adsorbents, including both the parent and surface-modified carbon beads, were subjected to different test regimes to determine their performance for CO₂ capture. Table 4 presents the CO₂ uptakes of the samples measured in TGA at different CO₂ partial pressures, and significant improvements in CO₂ adsorption capacity was obtained for the surface-modified carbon beads particularly at low CO₂ partial pressures. At 30 °C and a CO₂ partial pressure of 0.15 bar, the *oxAC* sample, which has the lowest textural properties (Table 2), shows the highest CO₂ uptake (0.91 mmol/g, 25% increase as compared with *AC*). This can be ascribed to the strong affinity of the abundant heteroatom functionalities, oxygenate functional groups in particular, with the quadrupole moment of the CO₂ molecule. Similar effects have also been reported for carbons, MOFs and task-specific ionic liquids (TSILs) [28, 58, 59]. When comparing adsorption capacity at 15vol.% CO₂ of the three aminated samples, it can be observed that *oxAC-300NH3* possessed the highest CO₂ uptake at both 30 and 45 °C, which can be explained by the higher amount of N-H functionalities (Table 1 and 3) because the binding between CO₂ and C-N-H groups is stronger than that of C=N-C. At a CO₂ partial pressure of 1 bar, the CO₂ uptake of all the aminated samples were higher than that of *oxAC*, suggesting the greater importance of textural properties on adsorption capacity. The sample *oxAC-300NH3* showed the highest

uptake (2.57 mmol/g), most probably due to its highest narrow micropore volume (W_0). It has been reported that at atmospheric pressure, only pores with diameters lower than 5 times of the molecular size of the adsorbate are effective for gas adsorption [18]. As for CO₂, the dynamic molecular diameter is 0.209 nm, it is therefore expected that the narrow micropores are the major locations that accommodate CO₂ at 1 bar [39]. The combinative effect of surface chemistry and textural properties on CO₂ adsorption of surface-modified carbon materials has been well-demonstrated in open literatures [41, 54], and it is believed that the surface chemistry, rather than the textural properties, governs the CO₂ capture performance at lower (partial) pressures, while the textural properties becomes more important at higher CO₂ pressures as the adsorption process becomes controlled by the micropore filling mechanism.

In fact, activated carbons in general are well known for their capability to achieve higher adsorption capacities at pressures higher than atmospheric, and this together with their moderate adsorption strength makes them the ideal adsorbents for CO₂ capture at high pressures (such as pre-combustion capture) [21, 23, 31]. In this study, the high pressure CO₂ adsorption performance of the samples was measured using a high pressure volumetric method, and the obtained isotherms are presented in Figure 5. Note that all the reported high pressure adsorption capacities are absolute loadings, calculated from the experimentally obtained excess loadings and V_{total} by using Peng-Robinson equation of state as suggested by Myers and Wang [60, 61]. For all the samples, CO₂ uptake increased with the increasing of pressure, and the highest uptakes of 8.64 and 7.93 mmol/g were achieved over sample *oxAC-800NH3* at 30 and 45 °C, respectively. These high uptakes together with the unique spherical form and good mechanical strength make the current carbon beads a promising option for CO₂ capture applications. Figure 6 illustrates the adsorption capacities at a pressure of 20.2 bar as a function of the BET surface areas of the samples, and the obtained good linear relationship highlighted the vital importance of the above mentioned pore filling mechanism where textural properties are expected to be the key driver of CO₂ uptake at elevated pressures.

Table 5 presented a comparison of the CO₂ adsorption capacity of the carbon beads with those phenolic resin-derived carbons reported in the literature. It can be seen that the adsorption capacity of samples reported here is only slightly lower than those non-KOH activated carbon adsorbents in a powder form. Together with the uniform spherical form, we thus believe these carbon beads may represent a potential option for practical CO₂ capture. We are currently working on the effect of KOH activation on the adsorption performance as well as the morphological integrity of the carbon beads.

To examine the effectiveness of the carbon beads as an adsorbent for pre-combustion CO₂ capture by pressure swing adsorption, the working capacity of the carbon adsorbents, which is defined as the difference in equilibrium capacities at given adsorption and desorption pressures (in the present case, 20 and 2 bar for adsorption and desorption, respectively), were obtained as shown in Table 6. Of all the samples examined, the sample *oxAC-800NH3* showed the highest working capacity of 4.94 mmol/g, which is nearly 20% higher than that of the parent *AC*. It is also interesting to highlight that the working capacities of all the carbon beads at 45 °C are slightly higher than those achieved at 30 °C, this is a phenomenon that has rarely been reported in previous studies on activated carbons, but is fairly meaningful because carbon-based materials are normally regarded as a highly temperature-sensitive adsorbents that rapidly lost their capacities with increasing temperatures, and thus the current observations are persuasive to demonstrate the feasibility of using the current carbon-based materials for pre-combustion CO₂ capture by pressure swing adsorption.

3.2.2 Adsorption selectivity

To assess the selectivity of the carbon adsorbents for CO₂ over N₂ and H₂, the N₂ and H₂ adsorption isotherms were measured and compared with those of CO₂ for some of the modified samples, namely *oxAC* and *oxAC-300NH3*. It can be seen from Figure 7 that within the adsorption pressure range examined, the adsorption capacities of the samples for CO₂ are remarkably higher than those for both N₂ and, in particular,

H₂. Here, the ratio of adsorption capacity of different gases under 5.0 bar was used as an indicator for the adsorption selectivity, the CO₂/N₂ selectivities thus obtained were 4.61 and 4.81 for oxAC and oxAC-300NH₃, respectively. These values are remarkably higher for CO₂/H₂ (30.50 and 38.36). Although investigations are ongoing, it is expected that the selectivity for CO₂ can be even higher in a competitive adsorption process, given the higher surface affinity of the adsorbents to CO₂ than to N₂ and H₂.

3.2.3 Adsorption kinetics

Using the CO₂ adsorption data obtained from the high pressure volumetric adsorption analyser, the adsorption kinetics could be estimated by plotting the ratio of the CO₂ uptake at time t to the equilibrium uptake, $(\text{uptake})/(\text{uptake})_{eq}$, as a function of contact time t . The results are shown in Figure 8. It is encouraging that regardless of the operation temperature, 90% of the equilibrium capacity could be achieved within less than 1 min and only approximately 2 min is needed to reach the full equilibrium capacity for all the samples, highlighting the desirable adsorption kinetics of the carbon beads for CO₂ capture.

3.2.4 Cyclic Adsorption performance

The reusability of *oxAC-300NH3* was evaluated by TGA as presented in Figure 8. Within 20 cycles of adsorption and desorption, there are negligible changes on the CO₂ uptake (Figure 9a), an inspection of the weight change curve (Figure 9b) indicates that the fast adsorption/desorption kinetics is stable as well, which is important to enhance the cyclic working capacity of the samples at reduced circulating times. The superior cyclic adsorption performance together with other adsorption characteristics as mentioned above endows the novel spherical carbon adsorbents with great promise in practical pre-combustion capture applications using pressure swing adsorption.

4. Conclusion

The effectiveness of using surface amination treatments as a means to improve the CO₂ capture performance of carbon beads produced from a novel cost-effective hydrothermal process has been investigated. It was found that the surface modifications hardly compromised the desirable spherical morphology and mechanical strength of the activated carbon beads while their adsorption performance for CO₂ was enhanced. In specific, HNO₃ oxidation and low temperature amination with NH₃ appear to be significantly more effective in improving the low pressure CO₂ adsorption performance of the carbon beads, while the modification with NH₃ at high temperatures was found instead to be more effective to boost their capture capacity at high pressures. Comprehensive characterisations demonstrate that the CO₂ uptake capacity of the carbons at low CO₂ partial pressures was more related to their surface chemistry and narrow micropores, while the high pressure adsorption capacity was found to have a linear relationship with the BET surface areas, indicating a pore-filling dominated adsorption mechanism. The highest working capacity of ca. 4.9 mmol/g was achieved for the sample *oxAC-800NH3* and little variation was observed with the adsorption temperatures examined in this investigation. The results demonstrate the great potential of the spherical carbon beads as CO₂ adsorbents particularly suitable for pre-combustion capture by pressure swing adsorption systems.

Acknowledgments

The authors wish to acknowledge the financial support of the UK EPSRC Grants (EP/I010955/1, EP/G063176/1), and the National Natural Science Foundation of China (51061130536, 51172251).

References

- [1] IEA. World energy outlook 2012, OECD/IEA, France, 2012.
- [2] IEA. World energy outlook 2013, OECD/IEA, France, 2013.
- [3] ExxonMobil. The outlook for energy: A view to 2040, USA, 2013.
- [4] BP. BP energy outlook 2013, UK, 2013.
- [5] Climate change. The scientific basis. Contribution of working group I to the third assessment report of the intergovernmental panel on climate change. Cambridge (United Kingdom) and New York (NY, USA): Cambridge University Press; 2001
- [6] L. Christian L, *Science*, 2010, 330, 595-596.
- [7] M. O. Franklin, *Energy Environ. Sci.*, 2009, 2, 449-458.
- [8] T. R. Gary, *Science*, 2009, 325, 1652-1654.
- [9] M. E. Boot-Handford, J. C. Abanades, E. J. Anthony, M. J. Blunt, S. Brandani, N. Mac Dowell, J. R. Fernandez, M. C. Ferrari, R. Gross, J. P. Hallett, R. S. Haszeldine, P. Heptonstall, A. Lyngfelt, Z. Makuch, E. Mangano, R. T. J. Porter, M. Pourkashanian, G. T. Rochelle, N. Shah, J. G. Yao, and P. S. Fennell, *Energy Environ. Sci.*, 2014, 7, 130-189.
- [10] S. Choi, J. H. Drese, and C. W. Jones, *ChemSusChem*, 2009, 2, 796-854.
- [11] Q. Wang, J. Luo, Z. Zhong, and A. Borgna, *Energy Environ. Sci.*, 2011, 4, 42-55.
- [12] S. Wang, S. Yan, X. Ma, and J. Gong, *Energy Environ. Sci.*, 2011, 4, 3805-3819.
- [13] P. Markewitz, W. Kuckshinrichs, W. Leitner, J. Linssen, P. Zapp, R. Bongartz, A. Schreiber, and T. E. Mueller, *Energy Environ. Sci.*, 2012, 5, 7281-7305.
- [14] A. Sayari, Y. Belmabkhout, and R. Serna-Guerrero, *Chem. Eng. J.*, 2011, 171, 760-774.
- [15] S. S. Mohammad, W. M. A. W. Daud, A. Houshmand, and A. Shamiri, *J. Anal. Appl. Pyrol.*, 2010, 89, 143-151.
- [16] S.-Y. Lee, D. Jang, S.-T. Bae, and S.-J. Park, *Int. J. Hydrogen Energy*, 2014, 39, 12347-12352.
- [17] Y. Xia, R. Mokaya, G. S. Walker, and Y. Zhu, *Adv. Energy Mater.*, 2011, 1, 678-783.
- [18] M. M. Maroto-Valer, Z. Tang, and Y. Zhang, *Fuel Process. Technol.*, 2005, 86, 1487-1502.

- [19] J. Ludwinowicz, and M. Jaroniec, *Carbon*, 2015, 82, 297-303.
- [20] G. P. Hao, C. W. Li, W. C. Li, D. Qian, D., and A. H. Lu, *Adv. Mater.*, 2010, 22, 853-857.
- [21] L. K. C. De Souza, N. P. Wickramaratne, A. S. Ello, M. J. F. Costa, M. J. F. Costa, C. E. F. Da Costa, and M. Jaroniec, *Carbon*, 2013, 65, 334-340.
- [22] T. C. Drage, A. Arenillas, K. M. Smith, C. Pevida, S. Piippo, and C. E. Snape, *Fuel*, 2007, 86, 22-31.
- [23] X. Shao, Z. Feng, R. Xue, C. Ma, W. Wang, X. Peng, and D. P. Cao, *AIChE J.*, 2011, 57, 3042-3051.
- [24] G. K. Parshetti, S. Chowdhury, and R. Balasubramanian, *Fuel*, 2015, 148, 246-254.
- [25] X. Zhang, S. Zhang, H. Yang, Y. Feng, Y. Chen, X. Wang, and H. Chen, *Chem. Eng. J.*, 2014, 257, 20-27.
- [26] X. Fan, L. Zhang, G. Zhang, Z. Shu, and J. Shi, *Carbon*, 2013, 61, 423-430.
- [27] S. M. Mahurin, J. Górká, K. M. Nelson, R. T. Mayes, and S. Dai, *Carbon*, 2014, 67, 457-464.
- [28] H. Seema, K. C. Kemp, N. H. Le, S. W. Park, V. Chandra, J. W. Lee, and K. S. Kim, *Carbon*, 2014, 66, 320-326.
- [29] L. Zhao, Z. Bacsik, N. Hedin, W. Wei, Y. H. Sun, M. Antonietti, and M. M. Titirici, *ChemSusChem*, 2010, 3, 840-845.
- [30] M. L. Gray, Y. Soong, K. J. Champagne, J. Baltrus, R. W. Stevens, P. Toochinda, and S. S. C. Chuang, *Sep. Purif. Technol.*, 35, 2004, 31-36.
- [31] G. Srinivas, V. Krungleviciute, Z. Guo, and T. Yildirim, *Energy Environ. Sci.*, 2014, 7, 335-342.
- [32] S. Sjostrom, and H. Krutka, *Fuel*, 2010, 89, 1298-1306.
- [33] M. E. Davis, *Nature*, 2002, 417, 813-821.
- [34] G. P. Hao, W. C. Li, D. Qian, G. H. Wang, W. P. Zhang, T. Zhang, A. Q. Wang, F. Schuth, H. J. Bongard, and A. H. Lu, *J. Am. Chem. Soc.*, 2011, 133, 11378-11388.
- [35] M. R. Lohe, M. Rose, and S. Kaskel, *Chem. Commun.*, 2009, 40, 6056-6058.
- [36] A. E. Kadib, R. Chimenton, A. Sachse, F. Fajula, A. Galarneau, and B. Coq,

- Angew. Chem. Int. Ed., 2009, 48, 4969-4972.
- [37] J. L. Williams, *Catal. Today*, 2001, 69, 3-9.
- [38] J. J. Wen, F. N. Gu, F. Wei, Y. Zhou, W. G. Lin, J. Yang, J. Y. Yang, Y. Wang, Z. G. Zou, and J. H. Zhu, *J. Mater. Chem.*, 2010, 20, 2840-2846.
- [39] H. An, B. Feng, and S. Su, *Carbon*, 2009, 47, 2396-2405.
- [40] Y. Jin, S. C. Hawkins, C. P. Huynh, and S. Su, *Energy Environ. Sci.*, 2013, 6, 2591-2596.
- [41] N. N. Sun, C. G. Sun, H. Liu, J. J. Liu, L. Stevens, T. Drage, C. E. Snape, K. X. Li, W. Wei, and Y. H. Sun, *Fuel*, 2013, 113, 854-862.
- [42] J. B. Parra, J. C. Sousa, R. C. Bansal, J. J. Pis, and J. A. Pajares, *Adsorpt. Sci. Technol.*, 1995, 12, 51-66.
- [43] M. M. Dubinin, *Chemistry and physics of carbon*. Marcel Dekker Inc. USA, 1966.
- [44] F. Stoeckli, and L. Ballerini, *Fuel*, 1991, 70, 557-559.
- [45] R. Ghosal, and D. M. Smith, *J. Porous Mater.*, 1996, 3, 247-255.
- [46] J. W. Shim, S. J. Park, and S. K. Ryu, *Carbon*, 2001, 39, 1635-1642.
- [47] K. S. W. Sing, D. H. Everett, R. A. W. Haul, L. Moscou, R. A. Pierotti, J. Rouquerol, and T. Siemieniewska, *Pure & Appl. Chem.*, 1985, 57, 603-619.
- [48] P. Chingombe, B. Saha, and R. J. Wakeman, *Carbon*, 2005, 42, 3132-3143.
- [49] P. Vinke, M. Van Der Eijk, M. Verbree, A. F. Voskamp, and H. Van Bekkum, *Carbon*, 1994, 32, 675-686.
- [50] C. Pevida, M. G. Plaza, B. Arias, J. Feroso, F. Rubiera, and J. J. Pis, *Appl. Surf. Sci.*, 2008, 254, 7165-7172.
- [51] B. Stöhr, and H. P. Boehm, *Carbon*, 1991, 29, 707-720.
- [52] H. P. Boehm, G. Mair, T. Stoehr, A. R. De Rincon, and B. Tereczki B, *Fuel*, 1984, 63, 1061-1063.
- [53] S. Araki, H. Doi, Y. Sano, S. Tanaka, and Y. Miyake, *J. Colloid Interface Sci.*, 2009, 339, 382-389.
- [54] A. Arenillas, T. C. Drage, K. Smith, and C. E. Snape, *J. Anal. Appl. Pyrolysis*, 2005, 74, 298-306.

- [55] A. W. Marek, J. R. Pels, and J. A. Moulijn, *Fuel*, 1995, 74, 507-516.
- [56] G. Sethia, and A. Sayari, *Energy Fuels*, 2014, 28, 2727-2731.
- [57] A. Zukal, I. Dominguez, J. Mayerová, and J. Čejka, *Langmuir*, 2009, 25, 10314-10321.
- [58] Z. Xiang, S. Leng, and D. Cao, *J. Phys. Chem. C*, 2012, 116, 10573-10579.
- [59] F. Karadas, M. Atilhan, and S. Aparicio, *Energy Fuels*, 2010, 24, 5817-5828.
- [60] A. L. Myers, and P. A. Monson, *Langmuir*, 2002, 18, 10261-10273.
- [61] J. Wang, A. Heerwig, M. R. Lohe, M. Oschatz, L. Borchardt, and S. Kaskel, *J. Mater. Chem.*, 2012, 22, 13911-13913.
- [62] C. F. Martin, M. G. Plaza, S. Garcia, J. J. Pis, F. Rubiera, and C. Pevida, *Fuel*, 2011, 90, 2064-2072.
- [63] L. Liu, Q. F. Deng, T. Y. Ma, X. Z. Lin, X. X. Hou, Y. P. Liu, and Z. Y. Yuan, *J. Mater. Chem.*, 2011, 21, 16001-16009.
- [64] J. Choma, K. Jedynak, W. Fahrenholz, J. Ludwinowicz, and M. Jaroniec, *Appl. Surf. Sci.*, 2014, 289, 592-600.
- [65] M.G. Plaza, K.J. Thurecht, C. Pevida, F. Rubiera, J.J. Pis, C.E. Snape, and T.C. Drage, *Fuel Process. Technol.* 2013, 110, 53-60.
- [66] J. Wei, D. Zhou, Z. Sun, Y. Deng, Y. Xia, and D. Zhao, *Adv. Funct. Mater.*, 2013, 23, 2322-2328.
- [67] N. P. Wickramaratne, and M. Jaroniec, *J. Mater. Chem. A.*, 2013, 1, 112-116.

Captions of the illustration

- Table 1 Weight based composition measured by EA and XPS (Dry Base)
- Table 2 Textural properties of the samples
- Table 3 Assignment and fraction of surface N functionalities
- Table 4 CO₂ adsorption capacities of the samples at different partial pressures under atmospheric conditions
- Table 5 A comparison on the CO₂ adsorption capacity of the current study and reported values
- Table 6 Working capacities of the samples
- Figure 1 Features of solid CO₂ adsorbents for industrial applications
- Figure 2 N₂ Isotherms of the samples
- Figure 3 SEM images of the samples
(a-A whole bead of oxAC, b-cracks and pores inside a oxAC bead
c-Smooth outer surface of AC, d-Initial particles and pores inside a AC bead)
- Figure 4 XPS spectra of the oxidized and aminated samples
(a-oxAC, b-oxAC-300NH₃, c-oxAC-600NH₃, d-oxAC-800NH₃)
- Figure 5 High pressure CO₂ adsorption isotherms of the samples
(a-30 °C, b-45 °C)
- Figure 6 Adsorption capacity at 20.2 bar as a function of BET surface area
- Figure 7 Comparison of adsorption isotherms for CO₂, N₂ and H₂
(a-oxAC, b-oxAC-300NH₃)
- Figure 8 Kinetics of high pressure (10 bar) CO₂ adsorption
(a-30°C, b-45 °C)
- Figure 9 Reusability of oxAC-300NH₃
(a-CO₂ uptake, b-Weight change curve)

Table 1 Weight based composition measured by EA and XPS (Dry Base)

	Elemental Analysis							XPS				
	C ^a	H ^a	N ^a	O ^a	H/N ^b	N/C ^b	O/C ^b	C ^a	N ^a	O ^a	N/C ^b	O/C ^b
<i>AC</i>	93.6	0.52	0.00	5.84	0.006	0.000	0.062	-	-	-	-	-
<i>oxAC</i>	68.6	1.91	1.85	27.7	0.028	0.027	0.404	87.0	1.74	11.3	0.023	0.173
<i>oxAC-300NH3</i>	74.7	2.11	1.44	21.8	0.028	0.019	0.291	90.0	2.03	8.34	0.026	0.124
<i>oxAC-600NH3</i>	82.5	1.34	1.13	15.0	0.016	0.014	0.181	91.8	1.64	6.53	0.021	0.095
<i>oxAC-800NH3</i>	83.0	0.87	1.37	14.7	0.010	0.017	0.178	91.3	1.98	6.75	0.025	0.099
<i>oxAC-800N2</i>	88.8	0.90	0.42	9.90	0.010	0.005	0.112	-	-	-	-	-

^a weight percentage in wt. %^b mass ratio, a.u.

Table 2 Textural properties of the samples

	S _{BET} (m ² /g)	V _{total} (cm ³ /g)	D _{avg} (nm)	Microporosity		
				S _{A_{micro}} ^a (m ² /g)	V _{micro} ^a (cm ³ /g)	W ₀ ^b (cm ³ /g)
<i>AC</i>	972	0.45	1.84	907	0.36	0.238
<i>oxAC</i>	788	0.39	1.99	707	0.28	0.245
<i>oxAC-300NH3</i>	936	0.41	1.77	891	0.35	0.277
<i>oxAC-600NH3</i>	1020	0.45	1.75	974	0.38	0.262
<i>oxAC-800NH3</i>	1106	0.49	1.76	1052	0.41	0.237
<i>oxAC-800N2</i>	1058	0.47	1.76	1009	0.40	0.247

^a Calculated by *t*-plot method

^b Calculated from CO₂ adsorption at 0 °C by applying DR method

Table 3 Assignment and fraction of surface N functionalities

samples	Fractions (%)			
	Pyridine	Pyridone	Quaternary	-NO ₂
<i>oxAC</i>	16.4	-	20.4	63.2
<i>oxAC-300NH3</i>	20.8	37.0	27.1	15.1
<i>oxAC-600NH3</i>	33.8	31.0	22.4	12.9
<i>oxAC-800NH3</i>	42.5	32.4	25.1	-

Table 4 CO₂ adsorption capacities of the samples at different partial pressures under atmospheric conditions

Sample	atmospheric conditions			
	15vol.% CO ₂ (mmol/g)		100vol.% CO ₂ (mmol/g)	
	30 °C	45 °C	30 °C	45 °C
<i>AC</i>	0.73	0.48	2.36	1.71
<i>oxAC</i>	0.91	0.59	2.34	1.72
<i>oxAC-300NH3</i>	0.85	0.56	2.57	1.90
<i>oxAC-600NH3</i>	0.76	0.50	2.44	1.78
<i>oxAC-800NH3</i>	0.74	0.49	2.42	1.75
<i>oxAC-800N2</i>	0.73	0.48	2.39	1.74

Table 5 A comparison on the CO₂ adsorption capacity of the current study and reported values

Ref.	KOH Activation	Adsorption Temperature (°C)	Adsorption Capacity (wt.%)
62	No	25	2.45
41	No	30	2.34
39	No	20	2.27
63	No	25	3.30
20	No	25	3.20
64	No	25	2.75
65	No	25	2.90
66	No	25	2.75
67	Yes	23	4.59
21	Yes	25	4.41
This Work	No	30	2.57

Table 6 working capacities of the samples

Sample	Working Capacities (mmol/g) ^a	
	30 °C	45 °C
<i>AC</i>	4.01	4.21
<i>oxAC</i>	3.15	3.18
<i>oxAC-300NH3</i>	3.67	3.77
<i>oxAC-600NH3</i>	4.29	4.33
<i>oxAC-800NH3</i>	4.81	4.94
<i>oxAC-800N2</i>	4.46	4.54

^a defined as the difference of equilibrium adsorption capacity at 20 and 2 bar

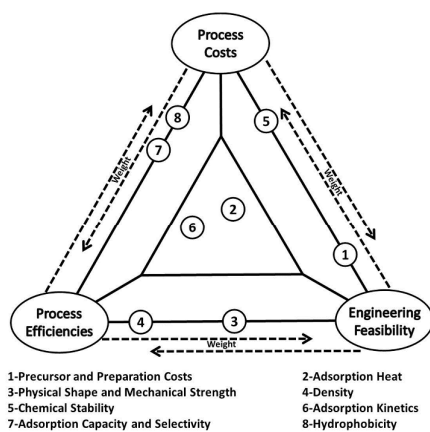


Figure 1 Features of solid CO₂ adsorbents for industrial applications

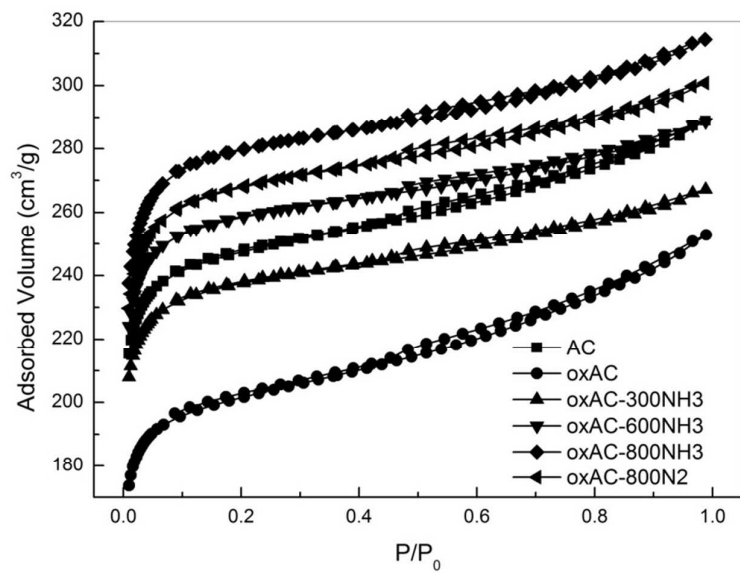


Figure 2 N_2 Isotherms of the samples

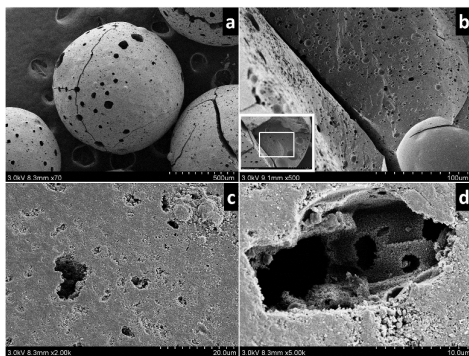


Figure 3 SEM images of the samples

(a-An *oxAC* bead, b-cracks and pores inside an *oxAC* bead

c-Smooth outer surface of *AC*, d-Initial particles and pores inside an *AC* bead)

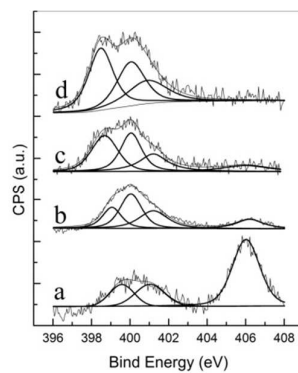


Figure 4 XPS spectra of the oxidized and aminated samples
(a-oxAC, b-oxAC-300NH₃, c-oxAC-600NH₃, d-oxAC-800NH₃)

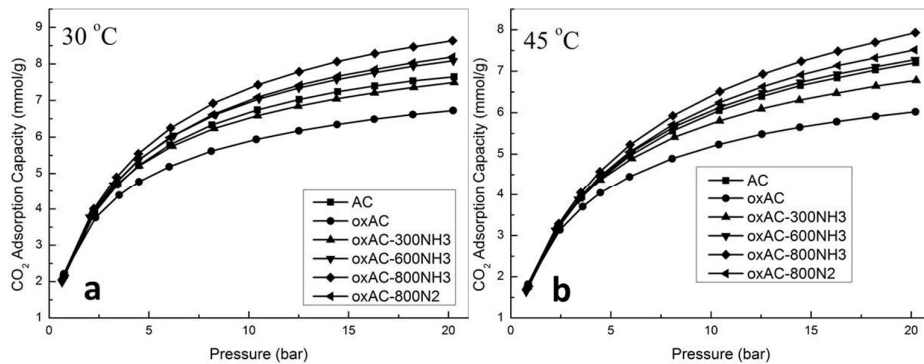


Figure 5 High pressure CO₂ adsorption isotherms of the samples (a-30 °C, b-45 °C)

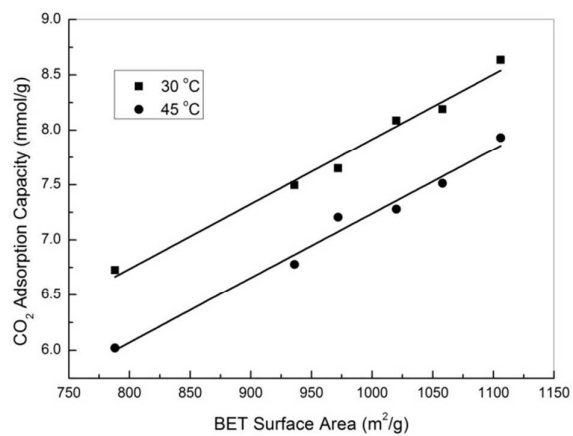


Figure 6 Adsorption capacity at 20.2 bar as a function of BET surface area

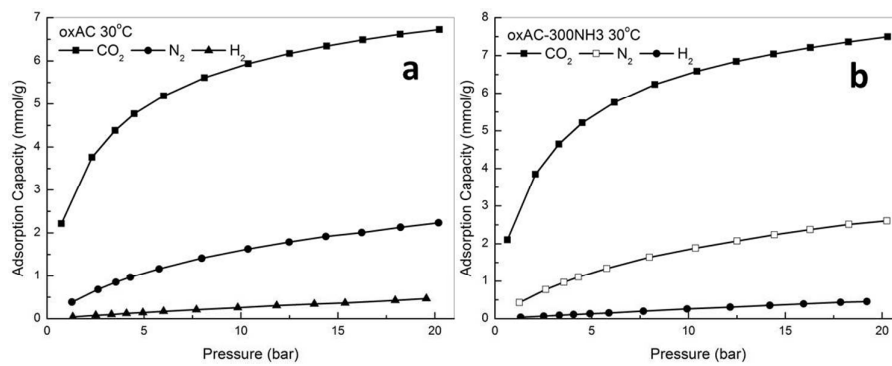


Figure 7 Comparison of adsorption isotherms for CO₂, N₂ and H₂ (a-oxAC, b-oxAC-300NH3)

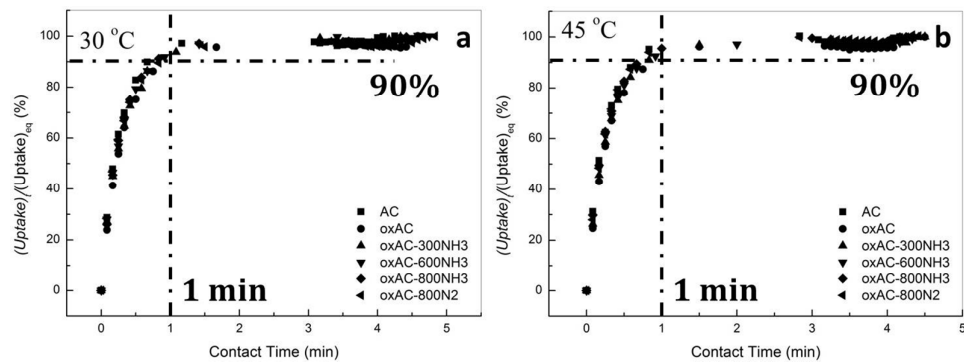


Figure 8 Kinetics of high pressure (10 bar) CO₂ adsorption (a-30 °C, b-45 °C)

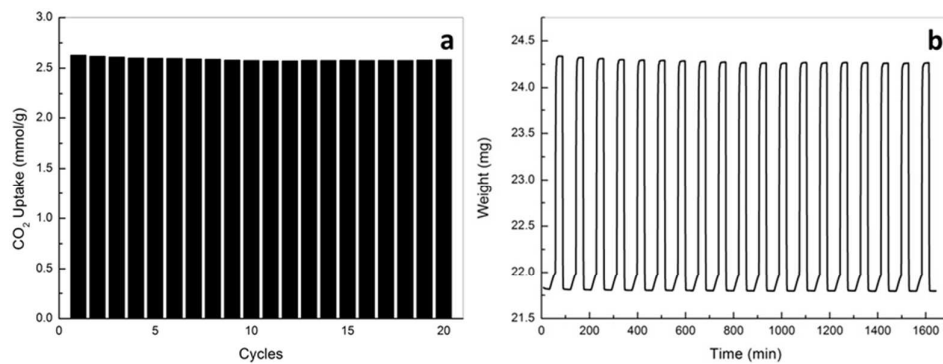


Figure 9 Reusability of *oxAC-300NH3*
(a- CO_2 uptake, b-Weight change curve)