

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Constrained formation of 2-(1-(arylimino)ethyl)-7-arylimino-6,6-dimethylcyclopentapyridines and their cobalt(II) chloride complexes: synthesis, characterization and ethylene polymerization

Junjun Ba,^{†,‡} Shizhen Du,[‡] Erlin Yue,[‡] Xinquan Hu,[†] Zygmunt Flisak,^{‡,§} Wen-Hua Sun^{*,‡}

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX


DOI: 10.1039/b000000x

A series of 2-(1-(arylimino)ethyl)-7-arylimino-6,6-dimethylcyclopentapyridine derivatives (**L1-L5**) was synthesized, and individually reacted with cobalt(II) chloride to form the corresponding cobalt chloride complexes (**C1-C4**). These compounds were characterized, and the single crystal X-ray diffraction for two representative cobalt complexes was carried out. The molecular structures indicate that 2,7-bis(arylimino)cyclopentapyridines act as tridentate ligands; however, one of the Co-N coordinative bonds is weak due to the spatial separation of nitrogen atoms. Upon activation with either MAO or MMAO, all cobalt complexes exhibit catalytic activities toward ethylene. Polymerization takes place in presence of MAO with the activities of approximately 10⁴ g of PE (mol of Co)⁻¹ h⁻¹, but oligomerization occurs in presence of MMAO with the activities higher by one order of magnitude. The resultant products, either polyethylenes or oligomers, display high linearity. Relatively low activities observed for cobalt complexes discussed reflects the importance of the proper spatial arrangement of the three donor nitrogen atoms.

Introduction

Late-transition-metal complex pre-catalysts have attracted much attention^{1,2} since the results of the pioneering research on α -diiminometal (Ni²⁺ or Pd²⁺)³ and bis(imino)pyridylmetal (Fe²⁺ or Co²⁺) halide complexes in ethylene activation were reported.⁴ Regarding the iron or cobalt pre-catalysts, the common characteristics of the polymerization or oligomerization products is their high linearity.¹ The modification of existing pre-catalysts by introduction of various substituents improves the catalytic performance of the corresponding metal complexes.^{1,2} For example, the modifications of 2-imino-1,10-phenanthrolines,⁵ were extensively investigated⁶ and successfully implemented in a pilot process with the scale of 500 tons annually. Moreover, the newly developed ligand models with finely tuned framework backbones, distinctively improved the catalytic performance of their metal complexes. For the derivatives of 2,6-bis(imino)pyridines (**A**, Scheme 1), the innovations resulted in 2-imino-1,10-phenanthrolines,^{5,6} 2-*N*-heterocyclic-6-iminopyridines,⁷ 2,8-bis(imino)quinolines,⁸ 2-methyl-2,4-bis(6-iminopyridin-2-yl)-1,5-benzo-diazepines,⁹ and 1,8-diimino-2,3,4,5,6,7-hexahydroacridines (**B**, Scheme 1),¹⁰ however, most of these complex pre-catalysts were active in ethylene oligomerization, while some of them polymerized ethylene to polyethylenes with low molecular weights. The idea of iminopyridine derivatives with fused rings materialized in the design of 2-imino-1,10-phenanthrolines,^{5,6} and 1,8-diimino-2,3,4,5,6,7-hexahydroacridines.¹⁰ Moreover, new promising catalytic systems toward ethylene polymerization have been recently developed through the application of new 2-(1-(arylimino)ethyl)-8-arylimino-5,6,7-trihydroquinolines (**C**, Scheme 1)¹¹ and 2-(1-(arylimino)ethyl)-9-arylimino-5,6,7,8-tetrahydrocycloheptapyridines (**D**, Scheme 1).¹² The success of **C** and **D** models inspired us to attempt the synthesis of 2-(1-(arylimino)ethyl)-7-aryliminocyclopentapyridine derivatives (**E**, Scheme 1). However, neither the desired organic compounds were observed in the condensation reaction of 2-acetylcyclopentapyridin-7-one with anilines, nor the corresponding

metal complexes were formed in the one-pot reaction with metal halides. We suspect that one of the possible reactions leading to the decomposition of model **E** (or preventing its formation) might be the imine-enamine or keto-enol tautomerization.

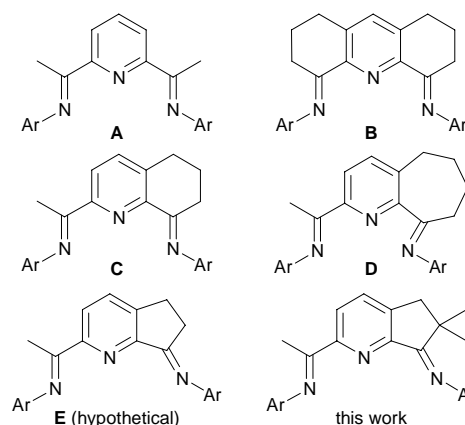

Scheme 1. Ligands derived from bis(imino)pyridines

The molecule of 7-aryliminocyclopentapyridine is not reported in the literature; besides the tautomerization, another contributing factor for its instability might be the ring tension. To overcome the first problem, two methyl substituents are added at the C-6 position within cyclopentapyridine. 2-Acetyl-6,6-dimethylcyclopentapyridin-7-one is prepared and used to form the title compound (Scheme 1). The series of 2-(1-(arylimino)ethyl)-7-arylimino-6,6-dimethylcyclopentapyridine derivatives and the corresponding cobalt complexes is synthesized and characterized. The molecular structures of representative cobalt complexes show relatively long distance between the cobalt and the nitrogen attached to the fused cyclopentyl ring, indicating the tension due to the size of this ring. Moreover, upon activation with either MAO or MMAO, all cobalt complexes exhibited catalytic activities toward ethylene, but lower activities are achieved

comparing with the analogue complex pre-catalysts.^{11,12} Herein the synthesis and characterization of the title compounds and the catalytic performance of the cobalt complexes are reported and discussed in detail.

Results and discussion

Metal-ligand interactions

To understand certain aspects of metal-ligand interactions in the complexes discussed within this work, we decided to compare the **Co1** complex with its analogue containing the six-membered cycloalkane ring fused with the pyridine moiety – see the structure of the corresponding **Co1** complex in Ref. 11 (a). In order to facilitate our calculations on the latter, we assumed that $R^1 = H$; herein this model will be referred to as **Co0**. The energies of two spin states of **Co0**, namely the doublet and the quartet, were compared and it turned out that the quartet is the ground state with the relatively large separation energy of 10.4 kcal/mol with respect to the doublet. Therefore the same spin state was adopted for the simplified model of the **Co1** complex taken from the current work (herein referred to as **Co1'**), in which two methyl groups corresponding to the R1 substituent were also replaced by the hydrogen atoms.


X-ray analysis performed on selected complexes (**Co1** and **Co2**) indicates three Co–N coordinative bonds of unequal length, where the imine nitrogen atom attached to the cycloaliphatic ring is only weakly bound to the transition metal atom due to spatial constraints caused by the five-membered ring (vide infra). Our DFT calculations for the **Co1'** model confirm this finding, since the Co1–N2 bond is the longest of all three Co–N bonds. For the comparison of the Co–N bond lengths in **Co1** and its model **Co1'** see Table 1.

Table 1. Co–N bond lengths* in **Co1** and **Co1'**, Å

	Co1 , experimental	Co1' , theoretical
Co(1)–N(1)	2.018(3)	2.08
Co(1)–N(2)	2.69	2.59
Co(1)–N(3)	2.188(3)	2.27

*Atom numbering corresponds to the X-ray structure below

To estimate the degree of weakening of the Co–N bond in **Co1'** comparing with **Co0**, we calculated the formation energies of both species from cobalt(II) chloride (where the quartet is the ground state) and the corresponding ligand L (in the conformation identical to this occurring in the complex) according to the following equation:




Our results indicate that the formation energies for **Co0** and **Co1'** are equal -62.2 and -58.1 kcal/mol, respectively. This suggests weaker interactions between the ligand and the CoCl_2 moiety in **Co1'** comparing with **Co0**, which confirms our hypothesis that the geometry of the five-membered ring in **Co1'** (and also **Co1**) places one of the imine nitrogen atoms farther away from the metal atom, which weakens the corresponding Co–N bond.

2-(1-Aryliminoethyl)-7-arylimino-6,6-dimethylcyclopentapyridine derivatives and their cobalt chloride complexes

2-Chloro-cyclopentapyridin-7-one¹³ was prepared using our procedure. It was reacted with the excessive amount of methyl iodide in the tetrahydrofuran solution containing sodium hydride according to the literature procedure¹⁴ to form 2-chloro-6,6-

dimethyl-cyclopentapyridin-7-one. In the next step, 2-acetyl-6,6-dimethylcyclopentapyridin-7-one was obtained in the Stille reaction (Scheme 2).¹⁵ The condensation reaction of 2-acetyl-6,6-dimethylcyclopentapyridin-7-one with 2,6-dimethylaniline was performed using a catalytic amount of *p*-toluenesulfonic acid in either ethanol or toluene; however, the corresponding compound, 2-(1-(2,6-dimethylphenylimino)ethyl)-7-(2,6-dimethylphenylimino)-6,6-dimethylcyclopentapyridine (**L1**) was obtained in the yield less than 10%. Using *n*-butanol as the solvent,¹⁶ the condensation reaction was enhanced to form the product (**L1**) in the isolated yield of 62.9%. Therefore the 2-(1-(arylimino)ethyl)-7-arylimino-6,6-dimethylcyclopentapyridine derivatives (**L2** – **L5**, Scheme 2) were individually synthesized in *n*-butanol with reasonable yields.

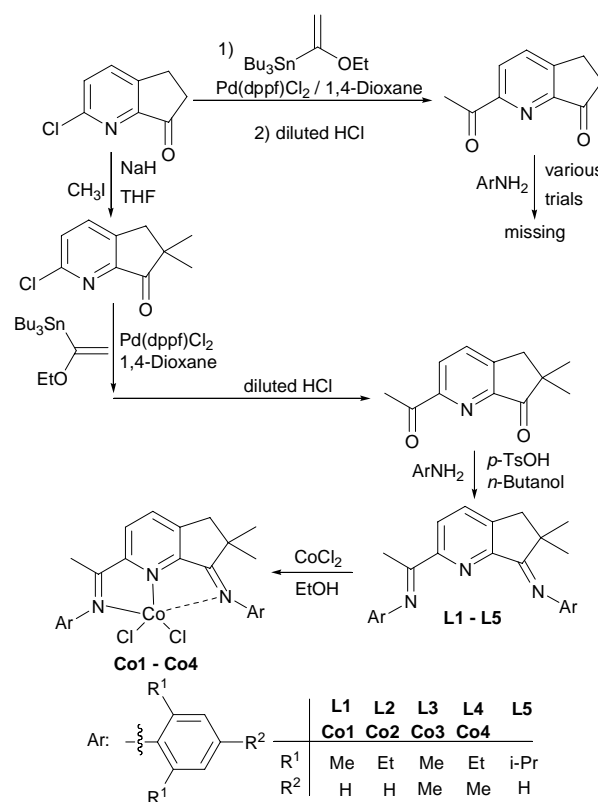

Scheme 2. Synthetic procedure for **L1** - **L5** and **Co1** - **Co4**

The 2-(1-(arylimino)ethyl)-7-arylimino-6,6-dimethylcyclopentapyridine derivatives (**L1**–**L5**) reacted with CoCl_2 in anhydrous ethanol, and the corresponding cobalt complexes (**Co1**–**Co4**) were obtained. For the reaction of 2-(1-(2,6-diisopropylphenylimino)ethyl)-7-(2,6-diisopropylphenylimino)-6,6-dimethylcyclopentapyridine with CoCl_2 , the oily brown product was obtained and its composition could not be confirmed by reliable data from elemental analysis. Elemental analyses for the other cobalt complexes (**Co1**–**Co4**) were consistent with their formula LCoCl_2 . Moreover, the single crystals of complexes **Co1** and **Co2** were also obtained, and their molecular structures were further confirmed by the single crystal X-ray diffraction.

X-ray Crystallographic Studies

Single crystals of complex **Co1** were obtained by slow diffusion of diethyl ether into its DMF solution at ambient temperature, whilst single crystals of complex **Co2** were obtained by slow diffusion of diethyl ether into its methanol solution at room temperature. According to the molecular structures of the

complexes **Co1** (Figure 1) and **Co2** (Figure 2), the 2-(1-aryliminoethyl)-7-arylimino-6,6-dimethylcyclopentapyridines act as tridentate ligands, coordinating to the cobalt atom to form the distorted trigonal-bipyramidal geometry. This result is consistent with the structural data obtained for the majority of bis(imino)pyridylmetal (iron or cobalt) dihalides.¹ However, large variations in the Co–N bond lengths were observed because of the weak bonding between cobalt and the imino-nitrogen linked to the pyridyl-fused cyclopentane.

Shown in Figure 1, there are three Co–N bonds of significantly different lengths. Two of them, Co(1)–N(1) and Co(1)–N(3), are comparable with the corresponding bond lengths in the cobalt complexes bearing unsymmetrical bis(imino)pyridines¹⁷ and 2-(1-arylimino-ethyl)-9-arylimino-5,6,7,8-tetrahydrocycloheptapyridines;¹² however, the distance of 2.690 Å between Co(1) and N(2) is larger than the sum of the corresponding ionic radii, which is equal 2.43 Å; such weak bond is caused by the N(1)–C(7)–C(6) angle of 122.3(3)° in cyclopentapyridine being much wider than N(1)–C(1)–C(11) of 112.9(3)°.

The existence of the bond between Co(1) and N(2) (imino-nitrogen linked to the cyclopentane ring) within the complex **Co1** may be disputed (Figure 1), however, the direct evidence could be found from the analysis of the molecular structure of complex **Co2**, which provides further information on different Co–N bonds. There are three independent molecules in the solid state. One of them (Fig. 2A) indicates the distance of 2.314(2) Å between Co(1) and N(3), which is slightly shorter than the sum of ionic radii (2.43 Å), confirming the existence of the Co–N bond; however, the distance between the cobalt and the nitrogen of the other imino group is elongated. Meanwhile, the remaining two molecules have weak bonds between the cobalt and the nitrogen of the imino group linked to the cyclopentyl moiety, with the longest one equal 2.785 Å for Co(2)–N(6) (shown in Fig. 2B). Again, the weak bond between the cobalt and the nitrogen of the imino group linked to the cyclopentyl moiety is ascribed to the ring stress caused by the dimethyl-substituted fused-cyclopentapyridine frame and ethyl-substituted phenyl group. For the **L5** ligand containing the bulkiest substituents, the elemental analysis indicates that the cobalt complex was not formed.

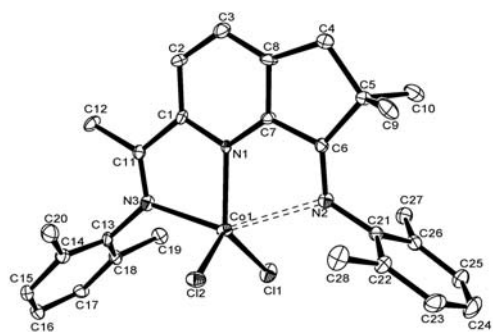


Figure 1. Molecular structure of complex **Co1** with thermal ellipsoids at 30% probability. Hydrogen atoms have been omitted for clarity. Selected bond lengths (Å) and angles (°): Co(1)–N(1) = 2.018(3), Co(1)–N(2) = 2.690, Co(1)–N(3) = 2.188(3), Co(1)–Cl(1) = 2.2365(12), Co(1)–Cl(2) = 2.2454(12); N(1)–Co(1)–N(3) = 76.53(13), N(1)–Co(1)–Cl(1) = 125.03(11), N(3)–Co(1)–Cl(1) = 107.43(9), N(1)–Co(1)–Cl(2) = 112.89(11), N(3)–Co(1)–Cl(2) = 102.17(10), Cl(1)–Co(1)–Cl(2) = 119.14(5).

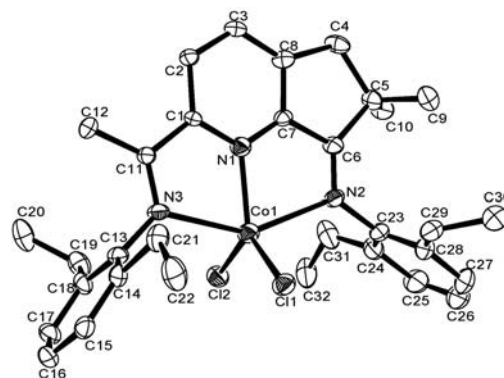


Figure 2A. Molecular structure of complex **Co2** with thermal ellipsoids at 30% probability. Hydrogen atoms have been omitted for clarity. Selected bond lengths (Å) and angles (°): Co(1)–N(1) = 2.014(2), Co(1)–N(2) = 2.423(2), Co(1)–N(3) = 2.314(2), Co(1)–Cl(1) = 2.2450(10), Co(1)–Cl(2) = 2.2307(9); N(1)–Co(1)–N(3) = 73.54(8), N(1)–Co(1)–Cl(1) = 123.11(7), N(3)–Co(1)–Cl(1) = 95.11(6), N(1)–Co(1)–Cl(2) = 115.93(7), N(3)–Co(1)–Cl(2) = 98.26(6), Cl(1)–Co(1)–Cl(2) = 120.88(3).

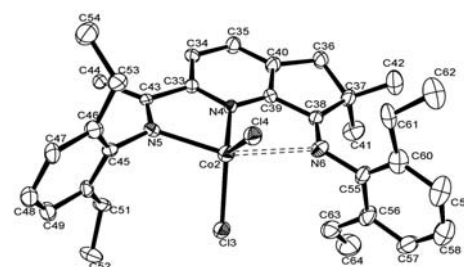


Figure 2B. Molecular structure of complex **Co2** with thermal ellipsoids at 30% probability. Hydrogen atoms have been omitted for clarity. Selected bond lengths (Å) and angles (°): Co(2)–N(4) = 2.042(2), Co(2)–N(5) = 2.145(2), Co(2)–N(6) = 2.785, Co(2)–Cl(3) = 2.2360(8), Co(2)–Cl(4) = 2.2513(8); N(4)–Co(2)–N(5) = 76.69(7), N(4)–Co(2)–Cl(3) = 119.84(6), N(5)–Co(2)–Cl(3) = 103.61(6), N(4)–Co(2)–Cl(4) = 121.69(6), N(5)–Co(2)–Cl(4) = 107.72(6), Cl(3)–Co(2)–Cl(4) = 115.31(3).

The existence of one weak coordinative bond between the cobalt atom and the nitrogen of the imino group in the **Co1**–**Co4** cobalt complexes can affect their catalytic performance. Studying the activity would be helpful to understand the correlation between the ligand framework and the catalytic properties of the complexes.

Ethylene polymerization

The co-catalysts of methylaluminumoxane (MAO) and modified methylaluminumoxane (MMAO) were routinely used to screen the catalytic performance of the cobalt complexes toward ethylene polymerization. The moderate activities in ethylene polymerization were observed in the presence of MAO; meanwhile the catalytic systems with MMAO showed good activities towards ethylene oligomerization.

Ethylene polymerization by the Co1-Co4/MAO

All the cobalt pre-catalysts were investigated by using MAO as the co-catalyst and the results are listed in Table 2. The **Co3** complex was examined to find the optimum reaction conditions. Firstly, the influence of reaction temperature was investigated by elevating the temperature from 30°C to 70°C (entries 1-5 in Table 2). The highest activity was achieved at 50°C, and with the further increase of temperature beyond that point, the activity decreased substantially, which could be caused by the partial decomposition of the active centres and lower concentration of ethylene in toluene at higher temperature¹⁸. Usually, polyethylenes with low

molecular weights are obtained under elevated reaction temperature, which is due to increased rate of chain transfers at higher temperature. But in this catalytic system, there is no such tendency in the molecular weights of the resultant polyethylenes (entries 1-5 in Table 2). The polyethylenes obtained exhibit higher M_w (246000 to 681900) as well as higher PDI comparing with the analogue cobalt-based catalytic systems¹¹. As indicated by the GPC curves of the resultant polyethylenes (Figure 3), all the cobalt pre-catalysts investigated display the multiple-site nature of the active species.

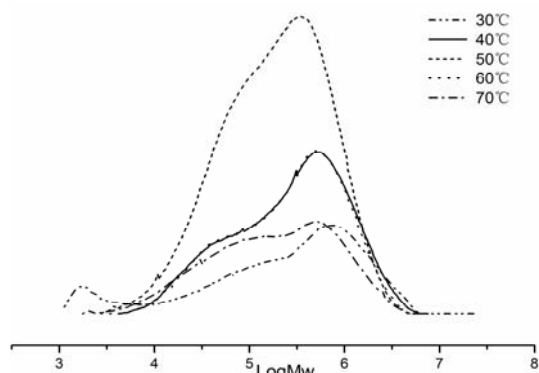


Figure 3. GPC traces of PEs produced at different reaction temperatures (entries 1-5, Table 1).

The Al/Co molar ratio also affected the catalytic behavior of the pre-catalysts (entries 3, 6-8 in Table 2). On increasing it from 2500 to 4000 at 50 °C, the best activity was obtained for the value of 3000 (entry 3 in Table 2). With the Al/Co ratio increased, the polyethylenes of low molecular weights were obtained (entries 6-8 in Table 2), which is attributed to higher probability of chain transfer from cobalt to aluminum for higher concentration of the co-catalyst in the system. From the view of GPC curves (Figure 4), it was found that only single-site active centres exist at the Al/Co

ratio of 3500 and 4000, but multiple-site active centres appear at the Al/Co ratio of 2500 and 3000.

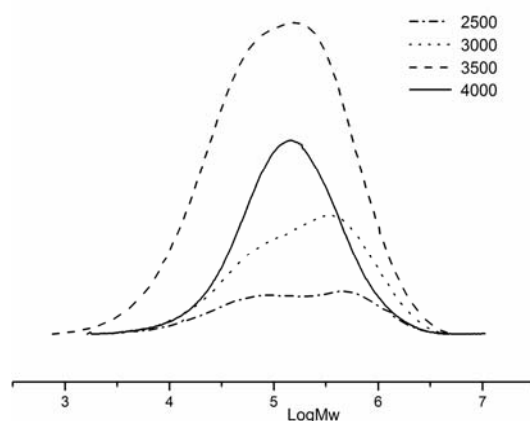


Figure 4. GPC traces of PEs produced with different Al/Co ratios (entries 3, 9-11, Table 1).

Employing the optimum reaction conditions (Al/Co equal 3000, temperature of 50°C and polymerization time of 30 min), all cobalt pre-catalysts were evaluated for their ethylene polymerization activity (entries 3, 10-12 in Table 2). Though these complexes just show low catalytic activity for ethylene polymerization, some trends still could be found. For example, better activities are obtained when using less bulky substituents within the ligand, which is illustrated by the following order of activities: 2,4,6-tri(Me)>2,6-di(Me)>2,6-di(Et)-4-Me>2,6-di(Et); this finding is consistent with observations reported in the literature,¹¹ stating that less bulky substituents in the *ortho* position and the methyl substituent in the *para* position within the ligand are beneficial to the catalytic activity of pre-catalysts toward ethylene polymerization.

Table 2. Polymerization results for Co1-Co4/MAO at 10 atm ethylene pressure^a

entry	precat.	T(°C)	Al/Co	polymer(mg)	activity ^b	T _m ^c (°C)	M _w /kg.mol ^{-1d}	M _w /M _n ^d
1	Co3	30	3000	23.4	0.47	128.2	681.9	34.4
2	Co3	40	3000	28.6	0.57	137.8	561.3	5.9
3	Co3	50	3000	144.5	2.89	138.4	372.7	4.9
4	Co3	60	3000	21.3	0.43	137.0	510.7	5.5
5	Co3	70	3000	11.2	0.22	133.6	430.5	7.5
6	Co3	50	2500	84.1	1.68	138.0	360.7	6.1
7	Co3	50	3500	97.4	1.95	138.6	257.0	6.4
8	Co3	50	4000	73.6	1.47	138.5	246.0	3.3
9	Co1	50	3000	98.0	1.96	139.9	397.4	4.2
10	Co2	50	3000	54.9	1.10	139.1	267.6	4.6
11	Co4	50	3000	86.6	1.73	137.0	325.2	5.2

^aConditions: 10μmol Co, 30min, 100mL of toluene. ^b10⁴gPE·mol⁻¹(Co)·h⁻¹. ^cDetermined by DSC. ^dDetermined by GPC.

Ethylene polymerization by Co1-Co4/MMAO systems

The polymerization results for the Co1-Co4/MMAO systems are collected in Table 3 with the optimum conditions selected earlier for complex Co2. When changing the Al/Co molar ratio from 1000 to 3000 (entries 1-5 in Table 3), the highest activity was reached for the value of 2000, and further increase in MMAO concentration led to the evident decrease in activity, which is caused by the increased amount of isobutyl groups from MMAO.⁷

With the Al/Co molar ratio fixed at 2000, the influence of the reaction temperature was also investigated (entries 3, 6-8 in Table 3). With elevating the temperature from 20°C to 50°C, the

activity reached the maximum at 30°C, and an obvious deactivation was observed as a result of the unstable active species at 50 °C.

All cobalt pre-catalysts Co1-Co4 were evaluated for ethylene oligomerization under the optimum reaction conditions of Al/Co equal 2000 at the temperature of 30 °C (entries 3, 9-11 in Table 3). As shown in Table 2, the Co3 and Co4 precatalysts, bearing methyl groups at the *para* position of the aromatic ring, exhibited slightly higher activities than the Co1 and Co2 precatalysts, indicating the positive effect of an additional methyl group within the ligand for the activity; the same applies to the MAO cocatalyst. Unlike the Co1-Co4/MAO system, the pre-

catalysts **Co2** and **Co4**, with ethyl groups at the *ortho* position of the aromatic ring, show higher activity than **Co1** and **Co3**, respectively.

As shown in Table 3, the oligomerization process shows high

selectivity toward α -olefins and the oligomers obtained fulfill the Schulz-Flory rule characterized by K , where K is determined by the molar ratio of C_{14} and C_{12} fractions.¹⁹

Table 3. Oligomerization results for **Co1-Co4**/MMAO at 10 atm ethylene pressure^a

entry	precat.	T(°C)	Al/Co	Oligomer distribution/% ^b						
				Activity ^b	α -O ^c	$C_4/\sum C$	$C_6/\sum C$	$C_8/\sum C$	$C_{10-22}/\sum C$	K
1	Co2	30	1000	1.48	89.2	36.9	13.6	15.3	34.2	0.67
2	Co2	30	1500	2.08	87.6	57.2	13.2	13.2	16.4	0.51
3	Co2	30	2000	3.20	89.0	56.8	13.4	11.7	18.1	0.55
4	Co2	30	2500	2.91	85.4	46.5	15.6	14.6	23.3	0.53
5	Co2	30	3000	2.75	86.2	69.3	8.8	9.2	12.7	0.57
6	Co2	20	2000	2.89	84.6	37.9	19.3	16.9	25.9	0.51
7	Co2	40	2000	1.32	89.7	62.2	10.8	14.6	12.4	0.60
8	Co2	50	2000	trace	38.2	100	-	-	-	-
9	Co1	30	2000	2.49	82.2	63.8	14.5	11.6	10.1	0.44
10	Co3	30	2000	3.27	81.6	60.1	15.4	11.8	12.7	0.48
11	Co4	30	2000	3.68	75.1	59.8	12.0	12.8	15.4	0.53

^aConditions: 4 μ mol Co, 30 min, 100 mL toluene. ^b10⁵ g mol⁻¹(Co)·h⁻¹, determined by GC; $\sum C$ signifies the total amount of oligomers. ^c α -olefin percentage content determined by GC.

Conclusions

A series of 2-(1-(arylimino)ethyl)-7-arylimino-6,6-dimethylcyclopentapyridylcobalt dichloride complexes was synthesized and characterized. Due to the nature of the ligands, namely the spatial separation of the aryl-substituted imino-group attached to the five-membered ring fused to the pyridine ring, all the Co(II) complexes obtained in this work did not show equally high activity toward ethylene polymerization as the analogous systems^{11,12}. Though the cobalt complexes developed within this study are not useful for ethylene polymerization, this work sheds some light on the differences between the 2-(1-aryliminoethyl)-7-arylimino-6,6-dimethylcyclopentapyridines and analogous (2-(1-(arylimino)ethyl)-8-arylimino-5,6,7-trihydroquinoline¹¹ and 2-(1-aryliminoethyl)-9-arylimino-5,6,7,8-tetrahydrocyclohepta pyridine¹², and provides new concepts for further research.

Experimental section

General procedures

All works involving air- and/or moisture-sensitive compounds were performed in an atmosphere of nitrogen using standard Schlenk techniques. Before being used, toluene was refluxed over sodium-benzophenone and distilled under nitrogen. Methylaluminoxane (MAO, 1.46M solution in toluene) and modified methylaluminoxane (MMAO, 1.93M in n-heptane 3A) were purchased from Akzo Nobel Corp. High-purity ethylene was purchased from Beijing Yanshan Petrochemical Co. and used as received. Other reagents were purchased from Aldrich, Acros, or local suppliers. NMR spectra were recorded on a Bruker DMX 400/500 MHz instrument at ambient temperature using TMS as an internal standard. IR spectra were recorded on a Perkin-Elmer System 2000 FT-IR spectrometer. Elemental analysis was carried out using a Flash EA 1112 microanalyzer.

Synthesis and characterization of substrates

Synthesis of 2-chloro-cyclopentapyridin-7-one

A 1000 ml four-necked flask was charged with 350 mL of CH₂Cl₂, 42.4 g 2-chloro-cyclopentapyridin-7-ol, 63.0 g NaHCO₃, 2.98 g KBr and 0.39 g TEMPO. Then 400 ml water solution of NaClO (5%) was added slowly under 0°C water bath.

The start of the reaction was detected by GC; after the substrate was totally consumed, the reaction was quenched. The reaction mixture was extracted with CH₂Cl₂ (75 mL×2), and the afforded organic layer was washed with water, dried over MgSO₄, and filtered. The filtrate was evaporated in vacuo to afford 38.8 g brown solid, which was purified by column chromatography on silica gel to give 37.6 g 2-chloro-cyclopentapyridin-7-one as yellow solid. FT-IR (KBr, cm⁻¹): 3110.2, 3041.8, 2957.6, 2930.7, 1714.3, 1582.9, 1427.4, 1305.4, 1243.7, 1207.3, 1173.3, 1123.3, 1082.8, 974.0, 864.4, 841.0, 749.8, 716.4, 670.1. Anal. Calcd for C₈H₆ClNO: C, 57.33, H, 3.61, N, 8.36. Found: C, 56.92, H, 3.27, N, 8.12. ¹H NMR (CDCl₃, 500 MHz, TMS): δ 7.86 (d, J = 8.5 Hz, 1H), 7.49 (d, J = 8.0 Hz, 1H), 3.16 (t, J = 5.0 Hz, 2H), 2.80 (t, J = 5.0 Hz, 2H). ¹³C NMR (CDCl₃, 125MHz, TMS): δ 201.2, 153.7, 146.2, 139.1, 135.4, 124.9, 34.3, 25.6.

Synthesis of 2-acetyl-cyclopentapyridin-7-one

2-Chloro-cyclopentapyridin-7-one (16.7 g, 0.10 mol), tributyl (1-ethoxyvinyl)tin (39.8 g, 0.11 mol), Pd(dppf)Cl₂ (2.2 g, 3.0 mmol), and 250 mL of 1,4-dioxane were added to a 500 mL three-necked jacketed flask. The mixture was refluxed for 12h under N₂, and cooled to room temperature. The mixture was treated with aqueous HCl (1.2 M, 150 mL). Then the resulting mixture was neutralized by NaOH solution and extracted with CH₂Cl₂. The organic layer was dried over anhydrous Na₂SO₄ and concentrated in vacuo to afford the crude product. The residue was purified by silica gel chromatography to afford 10.3 g 2-acetyl-cyclopentapyridin-7-one of as yellow solid. FT-IR (KBr, cm⁻¹): 3045.0, 2927.9, 1700.9, 1584.4, 1457.6, 1397.0, 1361.0, 1292.6, 1270.8, 1161.5, 1110.1, 1025.2, 981.3, 956.7, 875.2, 857.2, 764.0. Anal. Calcd for C₁₀H₉NO₂: C, 68.56, H, 5.18, N, 8.00. Found: C, 68.84, H, 5.41, N, 7.86. ¹H NMR (CDCl₃, 500 MHz, TMS): δ 8.22(d, J =8.5, 1H), 8.02(d, J =8.0, 1H), 3.25(t, J =5.8, 2H), 2.86(t, J =5.8, 2H), 2.82(s, 3H). ¹³C NMR (CDCl₃, 125MHz, TMS): δ 204.8, 199.9, 154.7, 153.8, 153.0, 136.4, 125.5, 35.5, 26.0, 23.9.

Synthesis of 2-chloro-6,6-dimethylcyclopentapyridin-7-one

2-Chloro-cyclopentapyridin-7-one (37.6 g, 0.224 mol) was added to the suspension of NaH (27.0 g, 60%, 0.675 mol) in 500 mL of dry THF at 0°C under N₂. After being stirred for one hour, methyl iodide (37.0 mL, 0.561 mol) was slowly added by a syringe; then the mixture was stirred at ambient temperature for ten hours. The reaction mixture was cooled to 0 °C, quenched

with water slowly, and extracted with ethyl acetate. The organic layer was washed with brine, water, dried over MgSO_4 , and filtered. The filtrate was evaporated in vacuo to afford a crude product, which was purified by column chromatography on silica gel to give 2-chloro-6,6-dimethylcyclopentapyridin-7-one of 11.6 g as white solid. FT-IR (KBr, cm^{-1}): 3082.5, 3047.0, 2972.8, 2932.2, 2866.7, 1719.8, 1578.9, 1465.6, 1430.4, 1375.6, 1310.5, 1176.3, 1126.0, 1085.1, 1025.2, 1000.5, 915.1, 872.5, 846.7, 820.4, 730.2, 657.4. Anal. Calcd for $\text{C}_{10}\text{H}_{10}\text{ClNO}$: C, 61.39, H, 5.15, N, 7.16. Found: C, 61.02, H, 5.29, N, 6.82. ^1H NMR (CDCl_3 , 500 MHz, TMS): δ 7.81 (d, $J = 8.5$ Hz, 1H), 7.51 (d, $J = 8.0$ Hz, 1H), 2.98 (s, 2H), 1.30 (s, 6H). ^{13}C NMR (CDCl_3 , 125MHz, TMS): δ 201.3, 154.7, 143.6, 140.5, 135.1, 126.7, 42.6, 41.2, 25.3.

Synthesis of 2-acetyl-6,6-dimethylcyclopentapyridin-7-one

2-Chloro-6,6-dimethylcyclopentapyridin-7-one (9.50 g, 0.049 mol), tributyl (1-ethoxyvinyl)tin (19.3 g, 0.053 mol), $\text{Pd}(\text{dppf})\text{Cl}_2$ (1.07 g, 1.47 mmol), and 100 mL of 1,4-dioxane were added to a 250 mL three-necked jacketed flask. The mixture was refluxed for 12h under N_2 , and cooled to room temperature. Then the mixture was washed with KF solution (0.3 M, 50 mL \times 3) and treated with aqueous HCl (1.2 M, 100 mL). The resulting mixture was neutralized by NaOH solution and extracted with CH_2Cl_2 . The organic layer was dried over anhydrous Na_2SO_4 and concentrated in vacuo to afford the crude product. The residue was purified by silica gel chromatography to afford 8.1 g 2-acetyl-6,6-dimethylcyclopentapyridin-7-one of as pale yellow solid. FT-IR (KBr, cm^{-1}): 2968.8, 2870.3, 1724.3, 1692.4, 1580.2, 1458.8, 1424.3, 1383.6, 1362.7, 1296.6, 1272.3, 1158.5, 1106.7, 1025.0, 1004.3, 955.3, 905.7, 879.4, 854.5, 822.5 743.7 678.0. Anal. Calcd for $\text{C}_{12}\text{H}_{13}\text{NO}_2$: C, 70.92, H, 6.45, N, 6.89. Found: C, 70.58, H, 6.13, N, 6.72. ^1H NMR (CDCl_3 , 500 MHz, TMS): δ 8.24 (d, $J = 8.0$ Hz, 1H), 7.98 (d, $J = 8.0$ Hz, 1H), 3.08 (s, 2H), 2.83 (s, 3H), 1.33 (s, 6H). ^{13}C NMR (CDCl_3 , 125MHz, TMS): δ 201.7, 198.2, 153.4, 151.5, 138.1, 137.6, 123.2, 42.7, 41.5, 27.3, 25.2.

Synthesis and characterization of organic compounds (L1–L5)

2-(1-(2,6-Dimethylphenylimino)ethyl)-7-(2,6-dimethylphenylimino)-6,6-dimethylcyclopentapyridine (L1)

2,6-dimethylaniline (0.31 g, 2.5 mmol) was added to a solution of 2-acetyl-6,6-dimethylcyclopentapyridin-7-one (0.20 g, 1.0 mmol) with a catalytic amount of p-toluenesulfonic acid (20.0 mg, 0.1 mmol) in 30 mL of n-butanol. The mixture was stirred for 8h at refluxing temperature. Under reduced pressure, the solvent was evaporated and the residue was subsequently purified by silica gel chromatography to afford 0.28 g (yield: 62.9%) of yellow oil. FT-IR (KBr, cm^{-1}): 2919.6, 2854.7, 1669.7, 1645.5, 1591.6, 1462.5, 1434.3, 1363.0, 1295.9, 1259.2, 1207.2, 1185.5, 1159.1, 1110.7, 1085.8, 1040.8, 918.8, 888.6, 845.5, 817.1, 748.1, 732.1, 685.4. Anal. Calcd for $\text{C}_{28}\text{H}_{31}\text{N}_3$: C, 82.11; H, 7.63; N, 10.26. Found: C, 81.92; H, 7.94; N, 10.16. ^1H NMR (CDCl_3 , 400 MHz, TMS): δ 8.30 (d, $J = 8.0$ Hz, 1H), 7.76 (d, $J = 8.0$ Hz, 1H), 7.00 (d, $J = 7.6$ Hz, 2H), 6.94-6.86 (m, 3H), 6.73 (t, $J = 7.6$ Hz, 1H), 3.04 (s, 2H), 2.00 (s, 6H), 1.92 (s, 6H), 1.52 (s, 6H), 1.41 (s, 3H). ^{13}C NMR (CDCl_3 , 100MHz, TMS): δ 175.0, 167.8, 156.3, 151.5, 149.7, 148.8, 143.6, 134.7, 127.9, 127.4, 125.5, 125.0, 123.0, 122.6, 122.0, 43.1, 42.5, 29.9, 28.0, 18.1, 18.0, 15.9.

2-(1-(2,6-Diethylphenylimino)ethyl)-7-(2,6-diethylphenylimino)-6,6-dimethylcyclopentapyridine (L2)

Using the same procedure as for the synthesis of L1, L2 was obtained as yellow oil (0.25 g, 49.9%). FT-IR (KBr, cm^{-1}):

2962.1, 2927.8, 2867.7, 1666.5, 1644.7, 1454.2, 1365.5, 1261.1, 1161.6, 1110.1, 1041.6, 844.5, 772.6, 737.2, 701.9. Anal. Calcd for $\text{C}_{32}\text{H}_{39}\text{N}_3$: C, 82.53; H, 8.44; N, 9.02. Found: C, 82.24; H, 8.63; N, 9.15. ^1H NMR (CDCl_3 , 400 MHz, TMS): δ 8.25 (d, $J = 8.0$ Hz, 1H), 7.76 (d, $J = 8.0$ Hz, 1H), 7.06 (d, $J = 7.2$ Hz, 2H), 7.00-6.97 (m, 3H), 6.84 (t, $J = 7.6$ Hz, 1H), 3.06 (s, 2H), 2.50-2.41 (m, 2H), 2.38-2.18 (m, 6H), 1.54 (s, 6H), 1.42 (s, 3H), 1.09-1.05 (m, 12H). ^{13}C NMR (CDCl_3 , 100MHz, TMS): δ 174.7, 167.7, 156.2, 151.4, 148.8, 147.8, 143.5, 134.6, 131.2, 130.6, 125.9, 125.5, 123.2, 122.3, 122.2, 42.9, 42.3, 27.7, 24.7, 24.5, 16.2, 13.9, 13.7.

2-(1-(2,4,6-Trimethylphenylimino)ethyl)-7-(2,4,6-trimethylphenylimino)-6,6-dimethylcyclopentapyridine (L3)

Using the same procedure as for the synthesis of L1, L3 was obtained as yellow oil (0.23 g, 48.6%). FT-IR (KBr, cm^{-1}): 2917.3, 2857.3, 1666.9, 1642.6, 1474.7, 1455.8, 1365.9, 1267.0, 1214.1, 1165.2, 1146.4, 1112.1, 1042.0, 1011.3, 849.7, 743.2, 706.0. Anal. Calcd for $\text{C}_{30}\text{H}_{35}\text{N}_3$: C, 82.34; H, 8.06; N, 9.60. Found: C, 82.13; H, 8.25; N, 9.30. ^1H NMR (CDCl_3 , 400 MHz, TMS): δ 8.28 (d, $J = 8.0$ Hz, 1H), 7.73 (d, $J = 8.0$ Hz, 1H), 6.84 (s, 2H), 6.74 (s, 2H), 3.02 (s, 2H), 2.27 (s, 3H), 2.15 (s, 3H), 1.95 (s, 6H), 1.89 (s, 6H), 1.95 (s, 6H), 1.51 (s, 6H), 1.43 (s, 3H). ^{13}C NMR (CDCl_3 , 100MHz, TMS): δ 175.2, 167.9, 156.1, 151.4, 147.0, 146.2, 143.3, 134.4, 132.1, 130.8, 128.4, 127.9, 125.2, 124.7, 122.4, 42.9, 42.3, 27.8, 20.7, 20.6, 17.9, 17.8, 15.4.

2-(1-(2,6-Diethyl-4-methylphenylimino)ethyl)-7-(2,6-diethyl-4-methylphenylimino)-6,6-dimethylcyclopentapyridine (L4)

Using the same procedure as for the synthesis of L1, L4 was obtained as yellow oil (0.22 g, 42.0%). FT-IR (KBr, cm^{-1}): 2962.3, 2927.5, 2866.6, 1665.5, 1644.1, 1458.1, 1365.8, 1263.0, 1211.9, 1165.3, 1112.1, 1041.6, 856.2, 805.5, 736.8, 702.0. Anal. Calcd for $\text{C}_{34}\text{H}_{43}\text{N}_3$: C, 82.71; H, 8.78; N, 8.51. Found: C, 82.36; H, 8.64; N, 8.32. ^1H NMR (CDCl_3 , 400 MHz, TMS): δ 8.21 (d, $J = 8.0$ Hz, 1H), 7.74 (d, $J = 8.0$ Hz, 1H), 6.89 (s, 2H), 6.78 (s, 2H), 3.03 (s, 2H), 2.44-2.35 (m, 4H), 2.32 (s, 3H), 2.31-2.17 (m, 4H), 2.15 (s, 3H), 1.52 (s, 6H), 1.43 (s, 3H), 1.07 (t, $J = 6.4$ Hz, 6H), 1.05(t, $J = 6.4$ Hz, 6H). ^{13}C NMR (CDCl_3 , 100MHz, TMS): δ 175.0, 167.9, 156.1, 151.4, 146.3, 145.2, 143.3, 134.5, 132.3, 131.1, 131.0, 130.5, 126.7, 126.1, 122.2, 42.9, 42.3, 27.7, 24.6, 24.5, 21.0, 20.9, 15.9, 14.0, 13.8.

2-(1-(2,6-Diisopropylphenylimino)ethyl)-7-(2,6-diisopropylphenylimino)-6,6-dimethylcyclopentapyridine (L5)

Using the same procedure as for the synthesis of L1, L5 was obtained as yellow oil (0.28g, 50.3%). FT-IR (KBr, cm^{-1}): 2961.1, 2927.5, 2866.6, 1666.2, 1638.5, 1586.3, 1457.2, 1433.5, 1378.4, 1375.5, 1361.5, 1302.8, 1108.9, 1043.4, 843.1, 801.5, 773.3, 739.4. Anal. Calcd for $\text{C}_{36}\text{H}_{47}\text{N}_3$: C, 82.87; H, 9.08; N, 8.05. Found: C, 82.49; H, 9.32; N, 8.21. ^1H NMR (CDCl_3 , 400 MHz, TMS): δ 8.16 (d, $J = 8.0$ Hz, 1H), 7.76 (d, $J = 8.0$ Hz, 1H), 7.10 (d, $J = 6.8$ Hz, 2H), 7.04 (t, $J = 7.6$ Hz, 3H), 6.88 (t, $J = 7.6$ Hz, 1H), 3.06 (s, 2H), 2.87-2.80 (m, 2H), 2.61-2.54 (m, 2H), 1.53 (s, 6H), 1.39 (s, 3H), 1.18 (d, $J = 6.8$ Hz, 6H), 1.08(d, $J = 6.8$ Hz, 6H), 1.05 (d, $J = 6.8$ Hz, 6H), 0.85 (d, $J = 6.8$ Hz, 6H). ^{13}C NMR (CDCl_3 , 100MHz, TMS): δ 174.8, 168.0, 156.2, 151.3, 147.7, 146.4, 143.5, 135.8, 134.9, 134.7, 123.5, 122.9, 122.4, 122.3, 122.2, 42.8, 42.3, 28.1, 28.0, 27.7, 23.2, 23.1, 22.9, 16.7.

Syntheses and characterization of complexes

2-(1-(2,6-Dimethylphenylimino)ethyl)-7-(2,6-dimethylphenylimino)-6,6-dimethylcyclopentapyridylcobalt dichloride (CoI)

The ligand L1 (0.16 g, 0.40 mmol) and CoCl_2 (0.047 g, 0.36 mmol) were added to a Schlenk tube, 5 mL of anhydrous ethanol was injected into this tube, and the mixture was rapidly stirred at room temperature overnight. The Et_2O was added to

the reaction to precipitate the complex Co1. After filtering, the precipitate was washed with Et₂O and dried under vacuum to give the product as deep green powder (0.15 g, 77.1%). FT-IR (KBr, cm⁻¹): 2984.9, 2964.1, 2921.5, 2874.9, 1651.9, 1608.6, 1575.3, 1465.5, 1425.8, 1368.8, 1303.1, 1225.5, 1193.3, 1092.8, 1044.7, 983.7, 896.5, 841.6, 774.7. Anal. Calcd for C₂₈H₃₁Cl₂CoN₃: C, 62.35; H, 5.79; N, 7.79. Found: C, 62.17; H, 5.68; N, 7.52.

2-(1-(2,6-Diethylphenylimino)ethyl)-7-(2,6-diethylphenylimino)-6,6-dimethylcyclopentapyridylcobalt dichloride (Co2)

By the above procedure, Co2 was isolated as deep green powder in 63.9% yield. FT-IR (KBr, cm⁻¹): 2964.0, 2932.1, 2873.1, 1649.1, 1607.5, 1580.1, 1445.6, 1368.3, 1331.9, 1289.8, 1239.7, 1220.3, 1186.2, 1134.5, 1106.6, 1046.9, 899.2, 862.4, 847.1, 809.8, 777.3. Anal. Calcd for C₃₂H₃₉Cl₂CoN₃: C, 64.54; H, 6.60; N, 7.06. Found: C, 64.21; H, 6.34; N, 6.62.

2-(1-(2,4,6-Trimethylphenylimino)ethyl)-7-(2,4,6-trimethylphenylimino)-6,6-dimethylcyclopentapyridylcobalt dichloride (Co3)

By the above procedure, Co4 was isolated as light green powder in 37.5% yield. FT-IR (KBr, cm⁻¹): 2965.4, 2921.2, 2865.1, 2361.5, 2336.2, 1653.4, 1631.5, 1609.4, 1574.8, 1478.4, 1427.6, 1378.3, 1302.6, 1232.0, 1194.1, 1143.4, 1116.8, 1045.0, 898.8, 849.5, 819.5, 715.5. Anal. Calcd for C₃₀H₃₅Cl₂CoN₃: C, 63.50; H, 6.22; N, 7.40. Found: C, 63.37; H, 6.11; N, 7.26.

2-(1-(2,6-Diethyl-4-methylphenylimino)ethyl)-7-(2,6-diethyl-4-methylphenylimino)-6,6-dimethylcyclopentapyridylcobalt dichloride (Co4)

By the above procedure, Co4 was isolated as deep green powder in 73.9% yield. FT-IR (KBr, cm⁻¹): 2965.6, 2930.9, 2913.6, 2873.4, 1653.0, 1609.9, 1575.5, 1456.4, 1425.2, 1369.9, 1337.5, 1302.5, 1280.8, 1228.6, 1192.3, 1136.6, 1041.4, 986.7, 892.4, 856.0. Anal. Calcd for C₃₄H₄₃Cl₂CoN₃: C, 65.49; H, 6.95; N, 6.74. Found: C, 65.37; H, 6.90; N, 6.63.

X-ray crystallographic studies

Single crystals of complexes Co1 and Co2 suitable for X-ray diffraction were grown by slow diffusion of diethyl ether into the solutions of Co1 in DMF and Co2 in methanol at room temperature, respectively. X-ray studies were carried out on a Rigaku Saturn724 + CCD with graphite-monochromatic Mo K α radiation ($\lambda = 0.71073$ Å) at 173(2) K; cell parameters were obtained by global refinement of the positions of all collected reflections. Intensities were corrected for Lorentz and polarization effects and empirical absorption. The structures were solved by direct methods and refined by full-matrix least squares on F². All hydrogen atoms were placed in calculated positions. Structure solution and refinement were performed by using the SHELXL-97 package.²⁰ During structure refinement of Co1 and Co2, there were free solvent molecules which had no influence on the geometry of the main compounds. Therefore, the SQUEEZE option of the crystallographic program PLATON²¹ was used to remove these free solvents from the structure. Details of the X-ray structure determinations and refinements are provided in Table 4.

Computational details

The calculations were carried out at the DFT level of theory, using the B3LYP hybrid density functional.²² The 6-31G(d,p) basis set²³ was applied for the H, C, N and the Cl atoms, whereas the LANL2DZ basis set²⁴ was used for the Co atom. The calculations were carried out by means of the Gaussian 09

software²⁵ at the default SCF and geometry convergence criteria. The identities of all optimized structures as the true minima were confirmed by the lack of imaginary frequencies.

Table 4. Crystal data and structure refinement for complexes Co1 and Co2

	Co1	Co2
CCDC	1054234	1054235
Empirical formula	C ₂₈ H ₃₁ Cl ₂ CoN ₃	C ₃₂ H ₃₉ Cl ₂ CoN ₃
Formula weight	539.39	595.49
Temperature (K)	173(2)	173(2)
Wavelength (Å)	0.71073	0.71073
Crystal system	Orthorhombic	Triclinic
space group	P2(1)2(1)2(1)	P-1
a (Å)	11.693(2)	15.556(4)
b (Å)	14.583(3)	16.925(4)
c (Å)	17.761(4)	20.273(6)
α (°)	90	99.470(3)
β (°)	90	110.249(2)
γ (°)	90	98.841(3)
V (Å ³)	3028.8(10)	4810(2)
Z	4	6
D _{calc} (g cm ⁻³)	1.183	1.233
μ (mm ⁻¹)	0.762	0.726
F(000)	1124	1878
Crystal size (mm)	0.38×0.26×0.13	0.37×0.36×0.15
θ Range (°)	1.81–27.47	1.10–27.49
Limiting indices	-14 ≤ h ≤ 15 -18 ≤ k ≤ 18 -23 ≤ l ≤ 22	-18 ≤ h ≤ 20 -21 ≤ k ≤ 21 -26 ≤ l ≤ 26
No. rflns collected	19692	43098
No. unique rflns [R(int)]	6890 (0.0252)	21832 (0.0141)
Completeness to θ (%)	99.7 %	99.0 %
Data / restraints / parameters	6890 / 1 / 314	21832 / 0 / 1027
Goodness of fit on F ²	1.105	1.041
Final R indices [I > 2 σ (I)]	R1 = 0.0682 wR2 = 0.1863	R1 = 0.0593 wR2 = 0.1502
R indices (all data)	R1 = 0.0710 wR2 = 0.1890	R1 = 0.0686 wR2 = 0.1537
Largest diff peak and hole(e Å ⁻³)	1.044 and -0.557	0.566 and -0.495

ACKNOWLEDGMENT

This work is supported by National Natural Science Foundation of China (NSFC Nos. 21374123 and U1362204). ZF thanks the Chinese Academy of Sciences for the Visiting Scientist Fellowship. The computational study was supported in part by the PL-Grid Infrastructure at the Academic Computer Centre CYFRONET AGH and the Wrocław Supercomputing and Networking Centre.

Notes and references

[†] College of Chemical Engineering, Zhejiang University of Technology, Hangzhou 310014, China;

[‡] Key laboratory of Engineering Plastics and Beijing National Laboratory for Molecular Science, Institute of Chemistry, Chinese Academy of Sciences, Beijing 100190, China;

[§] Faculty of Chemistry, Opole University, Oleska 48, 45-052 Opole, Poland.

- (a) J. Ma, C. Feng, S. Wang, K.-Q. Zhao, W.-H. Sun, C. Redshaw and G. A. Solan, *Inorg. Chem. Front.*, 2014, **1**, 4–34; (b) A. Boudier, P.-A. R. Breuil, L. Magna, H. Olivier-Bourbigou and P. Braunstein, *Chem. Commun.*, 2014, **50**, 1398–1407; (c) W. Zhang, W.-H. Sun and C. Redshaw, *Dalton Trans.*, 2013, **42**, 8988–8997; (d) T. Xiao, W. Zhang, J. Lai and W.-H. Sun, *C. R. Chim.*, 2011, **14**, 851–855; (e) C. Bianchini, G. Giambastiani, L. Luconi and A. Meli, *Coord.*


- Chem. Rev.*, 2010, **254**, 431–455; (f) W.-H. Sun, *Adv. Polym. Sci.*, 2013, **258**, 163–178.
- 2 (a) R. Gao, W.-H. Sun and C. Redshaw, *Catal. Sci. Technol.*, 2013, **3**, 1172–1179; (b) S. Wang, W.-H. Sun and C. Redshaw, *J. Organomet. Chem.*, 2014, **751**, 717–741.
- 3 (a) L. K. Johnson, C. M. Killian and M. Brookhart, *J. Am. Chem. Soc.*, 1995, **117**, 6414–6415; (b) C. M. Killian, D. J. Tempel, L. K. Johnson and M. Brookhart, *J. Am. Chem. Soc.*, 1996, **118**, 11664–11665.
- 4 (a) B. L. Small, M. Brookhart and A. M. A. Bennett, *J. Am. Chem. Soc.*, 1998, **120**, 4049–4050; (b) G. J. P. Britovsek, V. C. Gibson, B. S. Kimberley, P. J. Maddox, S. J. McTavish, G. A. Solan, A. J. P. White and D. J. Williams, *Chem. Commun.*, 1998, 849–850.
- 5 (a) W.-H. Sun, S. Jie, S. Zhang, W. Zhang, Y. Song and H. Ma, *Organometallics*, 2006, **25**, 666–677; (b) S. Jie, S. Zhang, W.-H. Sun, X. Kuang, T. Liu and J. Guo, *J. Mol. Catal. A: Chem.*, 2007, **269**, 85–96; (c) S. Jie, S. Zhang, K. Wedeking, W. Zhang, H. Ma, X. Lu, Y. Deng and W.-H. Sun, *C. R. Chim.*, 2006, **9**, 1500–1509; (d) S. Jie, S. Zhang and W.-H. Sun, *Eur. J. Inorg. Chem.*, 2007, **35**, 5584–5598; (e) L. Wang, W.-H. Sun, L. Han, H. Yang, Y. Hu and X. Jin, *J. Organomet. Chem.*, 2002, **658**, 62–70.
- 6 (a) M. Zhang, P. Hao, W. Zuo, S. Jie and W.-H. Sun, *J. Organomet. Chem.*, 2008, **693**, 483–491; (b) A. Boudier, P.-A. R. Breuil, L. Magna, C. Rangheard, J. Ponthus, H. Olivier-Bourbigou and P. Braunstein, *Organometallics*, 2011, **30**, 2640–2642.
- 7 (a) G. J. P. Britovsek, S. P. D. Baugh, O. Hoarau, V. C. Gibson, D. F. Wass, A. J. P. White and D. J. Williams, *Inorg. Chim. Acta*, 2003, **345**, 279–291; (b) W.-H. Sun, P. Hao, S. Zhang, Q. Shi, W. Zuo, X. Tang and X. Lu, *Organometallics*, 2007, **26**, 2720–2734; (c) Y. Chen, P. Hao, W. Zuo, K. Gao and W.-H. Sun, *J. Organomet. Chem.* 2008, **693**, 1829–1840; (d) L. Xiao, R. Gao, M. Zhang, Y. Li, X. Cao and W.-H. Sun, *Organometallics*, 2009, **28**, 2225–2233; (e) R. Gao, K. Wang, Y. Li, F. Wang, W.-H. Sun, C. Redshaw and M. Bochmann, *J. Mol. Catal. A: Chem.*, 2009, **309**, 166–171; (f) R. Gao, Y. Li, F. Wang, W.-H. Sun and M. Bochmann, *Eur. J. Inorg. Chem.*, 2009, **27**, 4149–4156; (g) W.-H. Sun, P. Hao, G. Li, S. Zhang, W. Wang, J. Yi, M. Asma and N. Tang, *J. Organomet. Chem.*, 2007, **692**, 4506–4518; (h) S. Song, R. Gao, M. Zhang, Y. Li, F. Wang and W.-H. Sun, *Inorg. Chim. Acta*, 2011, **376**, 373–380; (i) T. Xiao, S. Zhang, B. Li, X. Hao, C. Redshaw, Y.-S. Li and W.-H. Sun, *Polymer*, 2011, **52**, 5803–5810.
- 8 S. Zhang, W.-H. Sun, T. Xiao and X. Hao, *Organometallics*, 2010, **29**, 1168–1173.
- 9 (a) S. Zhang, I. Vystorop, Z. Tang and W.-H. Sun, *Organometallics*, 2007, **26**, 2456–2460; (b) S. Zhang, W.-H. Sun, X. Kuang, I. Vystorop and J. Yi, *J. Organomet. Chem.* 2007, **692**, 5307–5316.
- 10 V. K. Appukkuttan, Y. Liu, B. C. Son, C.-S. Ha, H. Suh, and I. Kim, *Organometallics*, 2011, **30**, 2285–2294.
- 11 (a) W. Zhang, W. Chai, W.-H. Sun, X. Hu, C. Redshaw and X. Hao, *Organometallics* 2012, **31**, 5039–5048; (b) W.-H. Sun, S. Kong, W. Chai, T. Shiono, C. Redshaw, X. Hu, C. Guo and X. Hao, *Appl. Catal. A: Gen.* 2012, **447–448**, 67–73.
- 12 F. Huang, Q. Xing, T. Liang, Z. Flisak, B. Ye, X. Hu, W. Yang and W.-H. Sun, *Dalton Trans.* 2014, **43**, 16818–16829.
- 13 Y. Xie, H. Huang, W. Mo, X. Fan, Z. Shen, N. Sun, B. Hu and X. Hu, *Tetrahedron: Asymmetry*, 2009, **20**, 1425–1432.
- 14 (a) N. Yoshimitsu, T. Satoru, U. Akiharu, K. Masunori, G. Satoru, O. Takashi, S. Shigeki and S. Motoo, *Organic Letters* 2004, **6**, 2133–2136; (b) J. Yu, Y. Zeng, W. Huang, X. Hao and W.-H. Sun, *Dalton Trans.* 2011, **40**, 8436–8443.
- 15 D. Milstein and J. K. Stille, *J. Am. Chem. Soc.* 1978, **100**, 3636–338.
- 16 G. J. P. Britovsek, V. C. Gibson, B. S. Kimberley, P. J. Maddox, S. J. McTavish, G. A. Solan, A. J. P. White and D. J. Williams, *Chem. Commun.*, 1998, 849–850.
- 17 (a) J. Yu, W. Huang, L. Wang, C. Redshaw, W.-H. Sun, *Dalton Trans.*, 2011, **40**, 10209–10214; (b) J. Lai, W. Zhao, W. Yang, C. Redshaw, T. Liang, W.-H. Sun, *Polym. Chem.*, 2012, **3**, 787–793; (c) S. Wang, B. Li, T. Liang, C. Redshaw, Y. Li, W.-H. Sun, *Dalton Trans.*, 2013, 9188–9197; (d) Q. Xing, T. Zhao, S. Du, W. Yang, T. Liang, C. Redshaw, W.-H. Sun, *Organometallics*, 2014, **33**, 1382–1388; (e) W. Zhang, S. Wang, S. Du, C.-Y. Guo, X. Hao, W.-H. Sun, *Macromol. Chem. Phys.*, 2014, **215**, 1797–1809; (f) W.-H. Sun, Q. Xing, J. Yu, E. Novikova, W. Zhao, X. Tang, T. Liang, C. Redshaw, *Organometallics*, 2013, **32(8)**, 2309–2318; (g) S. Wang, W. Zhao, X. Hao, B. Li, C. Redshaw, Y. Li, W.-H. Sun, *J. Organomet. Chem.*, 2013, **731**, 78–84; (h) F. He, W. Zhao, X.-P. Cao, T. Liang, C. Redshaw, W.-H. Sun, *J. Organomet. Chem.*, 2012, **713**, 209–216.
- 18 W. Krauss and W. Gestrich, *Chem.-Tech.*, 1977, **6**, 513–516.
- 19 (a) G. V. Z. Schulz, *Phys. Chem. Abt. B*, 1935, **30**, 379–398; (b) G. V. Z. Schulz, *Phys. Chem. Abt. B*, 1939, **43**, 25–46; (c) P. J. J. Flory, *Am. Chem. Soc.*, 1940, **62**, 1561–1565.
- 20 G. M. Sheldrick, SHELXTL-97, Program for the Refinement of Crystal Structures, University of Göttingen, Germany, 1997.
- 21 L. Spek, *Acta Crystallogr., Sect. D: Biol. Crystallogr.*, 2009, **65**, 148–155.
- 22 (a) A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 5648–5652; (b) C. Lee, W. Yang and R. G. Parr, *Phys. Rev. B*, 1988, **37**, 785–789.
- 23 (a) R. Ditchfield, W. J. Hehre and J. A. Pople, *J. Chem. Phys.*, 1971, **54**, 724–728; (b) W. J. Hehre, R. Ditchfield and J. A. Pople, *J. Chem. Phys.*, 1972, **56**, 2257–2261; (c) M. M. Francl, W. J. Pietro, W. J. Hehre, J. S. Binkley, D. J. DeFrees, J. A. Pople and M. S. Gordon, *J. Chem. Phys.*, 1982, **77**, 3654–3665; (d) V. A. Rassolov, M. A. Ratner, J. A. Pople, P. C. Redfern and L. A. Curtiss, *J. Comput. Chem.*, 2001, **22**, 976–984.
- 24 (a) T. H. Dunning, Jr. and P. J. Hay, in *Modern Theoretical Chemistry*, Ed. Schaefer, H., F., III, Vol. 3 (Plenum, New York, 1977) 1–28; (b) P. J. Hay and W. R. Wadt, *J. Chem. Phys.*, 1985, **82**, 270–283; (c) W. R. Wadt and P. J. Hay, *J. Chem. Phys.*, 1985, **82**, 284–298; (d) P. J. Hay and W. R. Wadt, *J. Chem. Phys.*, 1985, **82**, 299–310.
- 25 Gaussian 09, Revision D.01, M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, B. Mennucci, G. A. Petersson, H. Nakatsuji, M. Caricato, X. Li, H. P. Hratchian, A. F. Izmaylov, J. Bloino, G. Zheng, J. L. Sonnenberg, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, J. A., Jr. Montgomery, J. E. Peralta, F. Ogliaro, M. Bearpark, J. J. Heyd, E. Brothers, K. N. Kudin, V. N. Staroverov, R. Kobayashi, J. Normand, K. Raghavachari, A. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, N. Rega, M. J. Millam, M. Klene, J. E. Knox, J. B. Cross, V. Bakken, C. Adamo, J. Jaramillo, R. Gomperts, R. E. Stratmann, O. Yazyev, A. J. Austin, R. Cammi, C. Pomelli, J. W. Ochterski, R. L. Martin, K. Morokuma, V. G. Zakrzewski, G. A. Voth, P. Salvador, J. J. Dannenberg, S. Dapprich, A. D. Daniels, Ö. Farkas, J. B. Foresman, J. V. Ortiz, J. Cioslowski and D. J. Fox, Gaussian, Inc., Wallingford CT, 2009

Graphical Abstract

for

Constrained formation of 2-(1-(arylimino)ethyl)-7-arylimino-6,6-dimethylcyclopentapyridines and their cobalt(II) chloride complexes: synthesis, characterization and ethylene polymerization

Junjun Ba, Shizhen Du, Erlin Yue, Xinquan Hu, Zygmunt Flisak, Wen-Hua Sun

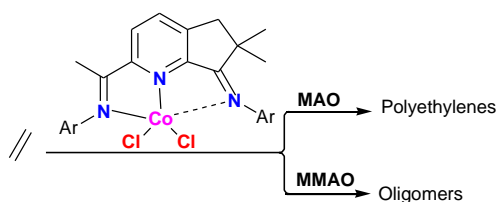

The 2-(1-(arylimino)ethyl)-7-arylimino-6,6-dimethylcyclopentapyridylcobalt complexes were constrainedly prepared, performing polymerization with MAO but oligomerization with MMAO.