

# RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



## Synthesis of bulk and supported nickel phosphide using microwave radiation for hydrodeoxygenation of methyl palmitate

Yinan Xue,<sup>1,2</sup> Qingxin Guan,<sup>1,2\*</sup> Wei Li<sup>1,2</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

In this paper, we proposed a novel method for preparing bulk and supported Ni<sub>2</sub>P catalysts under mild conditions. Ni<sub>2</sub>P and Ni<sub>2</sub>P/SiO<sub>2</sub> were synthesized from nickel hypophosphite precursors at 230 °C for 5 min using a CEM Discover microwave reactor, and the initial reaction temperature is about 202 °C. The catalysts were characterized using XRD, TEM, SEM, XPS, BET, carbon monoxide chemisorption, and catalytic performance was tested for hydrodeoxygenation (HDO) of methyl palmitate in a fixed-bed reactor. Interestingly, microwave irradiation does not result in sintering of Ni<sub>2</sub>P particles. The principal products of the HDO reaction for both catalysts are pentadecane and hexadecane. Isomerization products were not detected, and other by-products content is very low (<1%). The HDO results demonstrate that the catalyst prepared using microwave having better activity than that prepared using calcination.

### 1. Introduction


In recent years, synthesis of renewable fuel from biomass has attracted considerable attention. HDO reaction is an important reaction for the preparation of renewable fuel. However, conventional hydrogenation catalyst (such as CoMo/Al<sub>2</sub>O<sub>3</sub> and NiMo/Al<sub>2</sub>O<sub>3</sub>) does not possess sufficient stability under HDO reaction conditions, because sulfur content will be gradually decreased during the reaction.<sup>1</sup> Therefore, more and more studies focused on seeking for noble metal catalyst and other novel catalytic materials to promote HDO efficiently.

Metal phosphides, a class of interstitial compounds, have attracted considerable attention for their unexpected properties in catalysis, magnetic applications, and applications in telecommunications, optoelectronic devices, lithium batteries, and solar cells.<sup>2, 3</sup> In particular, Ni<sub>2</sub>P used as hydrodesulfurization catalyst shows excellent activity and resistance to sulfur poisoning performance.<sup>2</sup> In recent studies, Ni<sub>2</sub>P as a highly effective HDO catalyst shows good activity and stability in converting biomass to renewable oil.<sup>4-10</sup> J. Moon and coworkers studied the active sites of Ni<sub>2</sub>P/SiO<sub>2</sub> catalyst for HDO of guaiacol by using XAFS and DFT study. They revealed that the active site of Ni<sub>2</sub>P is composed of a threefold hollow Ni and P sites which lead to adsorption of H or OH groups.<sup>7</sup> A. lino and coworkers studied the reaction mechanism of Ni<sub>2</sub>P/SiO<sub>2</sub> catalyst for HDO of 2-methyltetrahydrofuran at a medium pressure of 0.5 MPa. They concluded that Ni<sub>2</sub>P/SiO<sub>2</sub> showed 100% conversion and 85% selectivity to n-pentane, with higher oxygen removal activity and less C—C bond cracking activity than commercial noble metal Ru/C and

Pd/Al<sub>2</sub>O<sub>3</sub> catalysts based on the same amount of active sites.<sup>8</sup>

As a class of new catalytic materials, the synthesis and applications of metal phosphides underwent tremendous development in the recent decades. A variety of methods for synthesizing metal phosphides have been reported.<sup>11-26</sup> Generally, the synthesis of metal phosphide has become highly convenient, which has broken through the limitations of high temperature and heating rate.<sup>19, 20</sup> In this paper, we proposed an alternative path to the synthesis of nickel phosphide. Ni<sub>2</sub>P and Ni<sub>2</sub>P/SiO<sub>2</sub> were synthesized from nickel hypophosphite precursor at 230 °C for 5 min using a CEM DISCOVER microwave reactor. Interestingly, microwave radiation does not result in sintering of Ni<sub>2</sub>P particles. The HDO results show that the catalyst prepared using microwave having better activity than that prepared using calcination.

Microwave is an electromagnetic wave with a frequency of 2.45 GHz and commonly used in materials synthesis.<sup>27-29</sup> It is mainly through the polarization of electromagnetic waves on the polar molecules to achieve a uniform temperature inside the sample. In our previous studies, bulk and supported Ni<sub>2</sub>P could be synthesized from the decomposition of nickel hypophosphite precursor in a static protecting gas atmosphere at 250 °C.<sup>20</sup> Herein, we use microwave radiation instead of traditional tube furnace to synthesize bulk and supported Ni<sub>2</sub>P. The reaction may occur at a high temperature is expressed in ionic formula as follows:



### 2. Experimental methods

SiO<sub>2</sub> was purchased from Tianjin Chemist Scientific Ltd., China. It has a specific surface area of 279 m<sup>2</sup> g<sup>-1</sup>, a pore volume of 0.8 cm<sup>3</sup> g<sup>-1</sup>. Other reagents were analytical pure grade and purchased from Alfa Aesar.

<sup>1</sup>College of Chemistry, Key Laboratory of Advanced Energy Materials Chemistry (Ministry of Education), <sup>2</sup>Collaborative Innovation Center of Chemical Science and Engineering (Tianjin), Nankai University, Tianjin, 300071, China. E-mail: qingxinguan@nankai.edu.cn, Fax: +86-22-23504436; Tel: +86-22-23504436.

## 2.1. Synthesis of bulk and supported nickel phosphides

**2.1.1. Calcination method.** The preparation of bulk Ni<sub>2</sub>P is illustrated as follows. Nickel chloride (NiCl<sub>2</sub>·H<sub>2</sub>O) and sodium hypophosphite (NaH<sub>2</sub>PO<sub>2</sub>·H<sub>2</sub>O) were dissolved in deionized water under stirring with a mole ratio of P/Ni = 1.5/1. After stirring for 1 h, the solution was evaporated slowly to dehydrate, and was dried at 80 °C for 8 h to obtain the precursor. At the beginning of the thermal decomposition, the air in the reactor was removed by flowing Ar, after which the precursor was treated at 250 °C for 30 min in a static Ar atmosphere (heating rate: 5–20 °C min<sup>-1</sup>). The product was cooled to ambient temperature under Ar and was washed several times with deionized water to remove ion impurities, after which the wet material was dried at 120 °C for 3 h.

The preparation of Ni<sub>2</sub>P/SiO<sub>2</sub> is illustrated as follows. NiCl<sub>2</sub>·H<sub>2</sub>O and NaH<sub>2</sub>PO<sub>2</sub>·H<sub>2</sub>O were dissolved in deionized water under stirring with a mole ratio of P/Ni = 1.5/1. After stirring for 1 h, the solution was impregnated onto the SiO<sub>2</sub> using incipient wetness impregnation. Then, the wet solid were evaporated slowly to dehydrate, and were dried at 80 °C for 8 h to obtain the precursor. At the beginning of the thermal decomposition, the air in the reactor was removed by flowing Ar, after which the precursor was treated at 250 °C for 30 min in a static Ar atmosphere (heating rate: 5–20 °C min<sup>-1</sup>). The product was cooled to ambient temperature under Ar and was washed several times with deionized water to remove ion impurities, after which the wet material was dried at 120 °C for 3 h.

**2.1.2. Microwave method.** The preparation of bulk Ni<sub>2</sub>P is illustrated as follows. NiCl<sub>2</sub>·H<sub>2</sub>O and NaH<sub>2</sub>PO<sub>2</sub>·H<sub>2</sub>O were dissolved in deionized water under stirring with a mole ratio of P/Ni = 1.5/1. After stirring for 1 h, the solution was evaporated slowly to dehydrate, and was dried at 80 °C for 8 h to obtain the precursor. At the beginning of microwave radiation, the air in the reactor was removed by flowing Ar, after which the precursor was radiated at 230 °C for 5 min in a static Ar atmosphere (Heating power of CEM Discover reactor is 250–290 W). The product was cooled to ambient temperature under Ar and was washed several times with deionized water to remove ion impurities, after which the wet material was dried at 120 °C for 3 h.

The preparation of Ni<sub>2</sub>P/SiO<sub>2</sub> is illustrated as follows. NiCl<sub>2</sub>·H<sub>2</sub>O and NaH<sub>2</sub>PO<sub>2</sub>·H<sub>2</sub>O were dissolved in deionized water under stirring with a mole ratio of P/Ni = 1.5/1. After stirring for 1 h, the solution was impregnated onto the SiO<sub>2</sub> using incipient wetness impregnation. Then, the wet solid were evaporated slowly to dehydrate, and were dried at 80 °C for 8 h to obtain the precursor. At the beginning of microwave radiation, the air in the reactor was removed by flowing Ar, after which the precursor was radiated at 230 °C for 5 min in a static Ar atmosphere (Heating power of CEM Discover reactor is 250–290 W). The product was cooled to ambient temperature under Ar and was washed several times with deionized water to remove ion impurities, after which the wet material was dried at 120 °C for 3 h.

## 2.2. Characterization

The characterization was performed for passivated sample, which was exposed to the air and without any reduction treatment. Powder X-ray diffraction (XRD) was performed on a Bruker D8 focus diffractometer, with Cu K $\alpha$  radiation at 40 kV and 40 mA. The transmission electron microscope (TEM) images were purchased using a Philips Tecnai G<sup>2</sup> F-20 field emission gun TEM. Scanning electron microscope (SEM) images were obtained using a Tescan Vega3 SBH. Brunauer–Emmett–Teller (BET) specific surface areas were obtained using nitrogen adsorption/desorption measurements at 77 K with a BELSORP-Mini instrument. Samples were degassed at 300 °C for 3 h before measurement. The surface area was calculated using a multi-point BET model. X-ray photoelectron spectroscopy (XPS) was carried out using a Kratos Axis Ultra DLD spectrometer employing a monochromated Al-K $\alpha$  X-ray source (h $\nu$  = 1486.6 eV), hybrid (magnetic/electrostatic) optics and a multi-channel plate and delay line detector (DLD). All XPS spectra were recorded using an aperture slot of 300×700 microns, survey spectra were recorded with a pass energy of 80 eV, and high-resolution spectra with a pass energy of 40 eV. In order to subtract the surface charge effect, the C1s peak was fixed at a binding energy of 284.6 eV. The CO chemisorption was performed with Micromeritics Chemisorb 2750 gas-adsorption equipment. The sample was loaded into a quartz reactor and pretreated in 10% H<sub>2</sub>/Ar at 450 °C for 3 h. After cooling in He, pulses of 10% CO/He in a He carrier (25 mL (NTP) min<sup>-1</sup>) were injected at 35 °C through a loop tube.

## 2.3. Catalytic activity test

HDO catalytic activities were evaluated using 30 wt% methyl palmitate in decalin. HDO reaction was carried out in a fixed-bed microreactor. The catalyst was pelleted, crushed, and sieved with 20–40 mesh; 1.0 g of the catalyst was diluted with SiO<sub>2</sub> to a volume of 5.0 mL in the reactor. Prior to the reaction, catalysts were pretreated in situ with flowing H<sub>2</sub> (100 mL min<sup>-1</sup>) for 3 h. The testing conditions for the HDO reaction were 1 MPa, weight hourly space velocity (WHSV) = 6 h<sup>-1</sup>, and H<sub>2</sub>/oil = 1000. Liquid products were collected every hour after a stabilization period of 6 h. Both feed and products were analyzed with an Agilent 7890A/5975C GC–MS equipped with a flame ionization detector and a HP-5 column. The TOF was calculated using Eq. 2:

$$TOF = \frac{F_{A0} X_A}{W CO_{uptake}} \quad Eq. 2$$

where  $F_{A0}$  is the molar rate of reactant fed into the reactor ( $\mu\text{mol s}^{-1}$ ),  $W$  is the catalyst weight (g),  $CO_{uptake}$  is the uptake of chemisorbed CO ( $\mu\text{mol g}^{-1}$ ), and  $X_A$  is the reactant conversion (%).


## 3. Results and discussion

### 3.1. Synthesis of bulk and supported nickel phosphides


Similarly, NaH<sub>2</sub>PO<sub>2</sub>·H<sub>2</sub>O and NiCl<sub>2</sub>·6H<sub>2</sub>O were used as a raw material. Fig. 1a shows the XRD patterns of the samples prepared at different temperatures for 10 min from precursors with a P/Ni mole ratio of 1.5. The result indicates that Ni<sub>2</sub>P can be synthesized at 230 and 250 °C. The strong diffraction peaks

of NaCl were detected when the temperature is 200 °C, which indicates the precursor was not decomposed and 200 °C is lower than the lowest reaction temperature (Fig 1b). From the temperature curves of 230 and 250 °C, we can clearly see that this is an exothermic reaction, and the initial reaction temperature is between 202 and 206 °C. When a decomposition reaction occurred, the measured temperature suddenly increased, and then rapidly came down to the setting values.

In our previously published paper,<sup>20</sup> Ni<sub>2</sub>P was synthesized in the mole ratio of P/Ni range of 1.5 to 1.75 using a calcination method. To study the influence of the microwave irradiation deeply, a series of samples were prepared with different mole ratios of P/Ni. As shown in Fig. 2, we can clearly see that Ni<sub>2</sub>P can be synthesized at a mole ratio of P/Ni = 1.5. Similarly, the weak diffraction peaks of Ni<sub>12</sub>P<sub>5</sub> were detected when the mole ratio of P/Ni is 1.34 (Eq. 1). Different with our previous results, the diffraction peaks of Ni<sub>5</sub>P<sub>4</sub> were detected when the mole ratio of P/Ni is 1.75, which indicates that P is a slight excess for the synthesis of bulk Ni<sub>2</sub>P in this mole ratio. This result also shows that the microwave method has better utilization of phosphorus than calcination method.

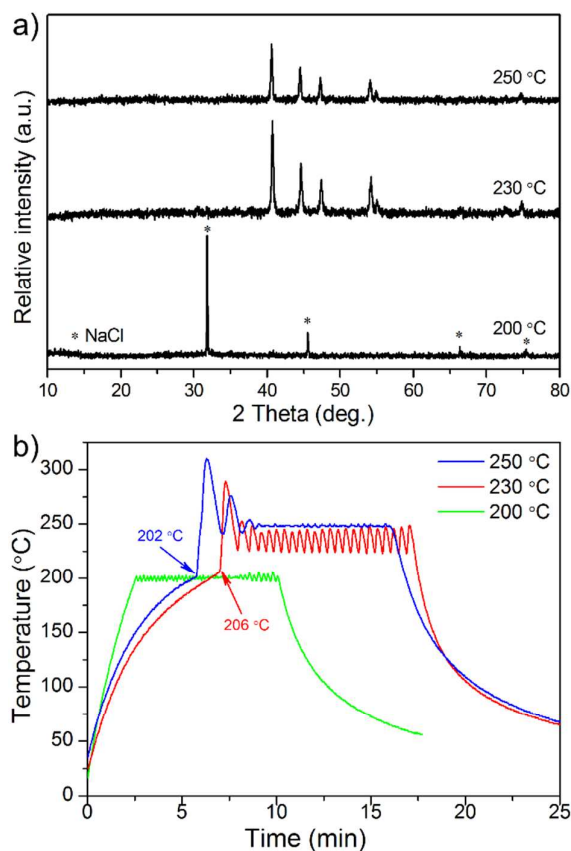


**Fig. 1.** (a) The XRD patterns of the samples prepared at different temperatures for 10 min from the precursors with a mole ratio of P/Ni = 1.5, (b) microwave temperature patterns of the samples in different setting values.

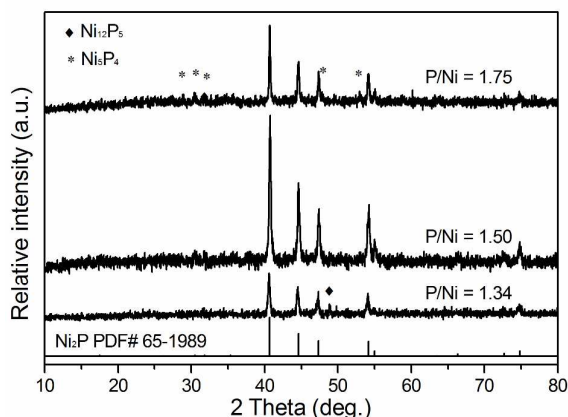


**Fig. 2.** The XRD patterns of bulk Ni<sub>2</sub>P prepared with different mole ratios of P/Ni (microwave radiation at 230 °C for 10 min).

To study the effect of irradiation time on the bulk Ni<sub>2</sub>P product, the precursors with different irradiation times at 230 °C were analysed by XRD. The diffraction peaks of Ni<sub>12</sub>P<sub>5</sub> were detected in the precursor after being radiated at 230 °C for 2 min, and these diffraction peaks disappeared after 5 min (Fig. 3). Crystal structure of Ni<sub>2</sub>P was not damaged when irradiation time extended to 10 minutes. The result indicates that there is a rapid crystal phase transition process from Ni<sub>12</sub>P<sub>5</sub> to Ni<sub>2</sub>P, and Ni<sub>2</sub>P can be synthesized in 5 min.

Fig. 4 shows the SEM images of bulk Ni<sub>2</sub>P prepared using different methods. Surprisingly, microwave radiation at 230 °C did not cause serious sintering of metal particles, which might because microwave radiation is very uniform. Although irradiation will cause sudden increase in temperature, but the apparent temperature does not exceed 300 °C. On the contrary, the average particle size of Ni<sub>2</sub>P synthesized using calcination method is significantly larger than that of synthesized using the microwave method.

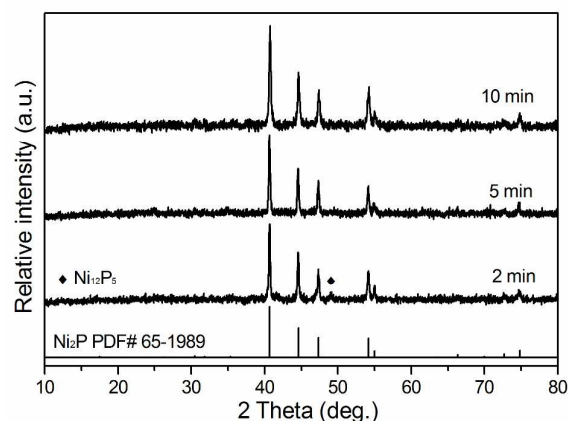


**Fig. 3.** The XRD patterns of bulk Ni<sub>2</sub>P prepared with different microwave radiation time (microwave radiation at 230 °C, P/Ni = 1.5).

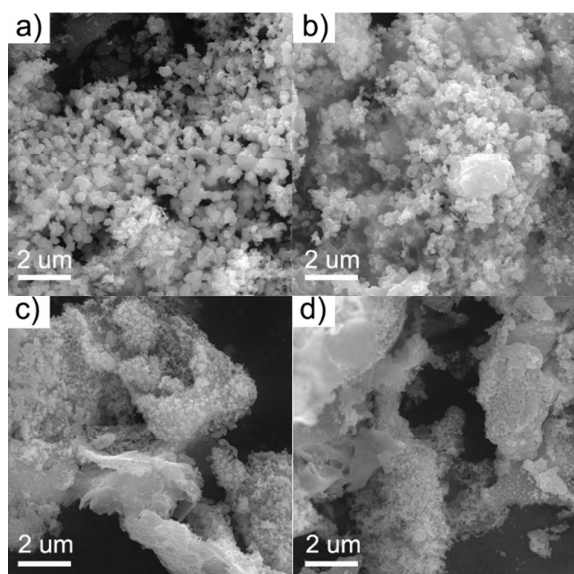


**Fig. 4.** The SEM images of bulk  $\text{Ni}_2\text{P}$  prepared using different methods, (a) and (b) prepared using calcination method ( $\text{P}/\text{Ni} = 1.5$ ,  $250\text{ }^\circ\text{C}$ , 30 min), (c) and (d) prepared using microwave method ( $\text{P}/\text{Ni} = 1.5$ ,  $230\text{ }^\circ\text{C}$ , 5 min).

Fig. 5 shows the XRD patterns and TEM images of 30 wt%  $\text{Ni}_2\text{P}/\text{SiO}_2$  catalysts prepared using different methods. Two supported catalysts having similar weak diffraction peaks of  $\text{Ni}_2\text{P}$  (PDF# 65-1989). The XRD results show that  $\text{Ni}_2\text{P}/\text{SiO}_2$  catalysts can be synthesized at a mole ratio of  $\text{P}/\text{Ni} = 1.5$  using different methods. From the TEM images, we can clearly see that  $\text{Ni}_2\text{P}$  particles prepared using microwave method had significantly better dispersion. Subsequent CO uptake and HDO test also show  $\text{Ni}_2\text{P}$  particles are well dispersed on  $\text{SiO}_2$ .

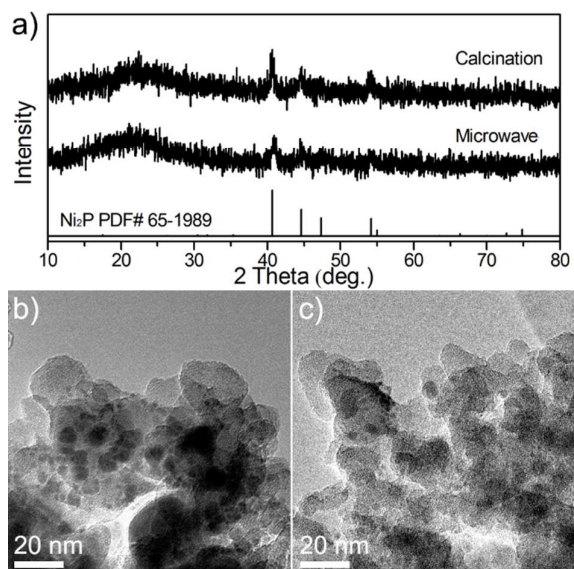

**Fig. 5.** The XRD patterns and TEM images of 30 wt%  $\text{Ni}_2\text{P}/\text{SiO}_2$  catalysts prepared using different methods, (a) XRD patterns, (b) prepared using calcination method ( $\text{P}/\text{Ni} = 1.5$ ,  $250\text{ }^\circ\text{C}$ , 30 min), and (c) prepared using microwave method ( $\text{P}/\text{Ni} = 1.5$ ,  $230\text{ }^\circ\text{C}$ , 5 min).


XPS analysis was carried out to observe the valence of Ni and P elements on 30 wt%  $\text{Ni}_2\text{P}/\text{SiO}_2$  surfaces (Fig. 6). The  $\text{Ni}2p$  spectrum of  $\text{Ni}_2\text{P}$  mainly involves two peaks. The first one is centered at 852.9 eV and assigned to  $\text{Ni}^{2+}$  of  $\text{Ni}_2\text{P}$ , and the second one is at 856.3 eV, corresponding to  $\text{Ni}^{2+}$  ions interacting possibly with phosphate ions as a consequence of a superficial passivation. For  $\text{P}2p$ , binding energy at 129.7 eV is attributed to  $\text{P}^{5-}$  of  $\text{Ni}_2\text{P}$  and 133.0 eV is attributed to surface nickel phosphate species.<sup>19, 26</sup> Some difference is that the binding energy of calcination sample shift slightly to a higher value than that of microwave sample. Temperature and time of synthesis of  $\text{Ni}_2\text{P}/\text{SiO}_2$  using calcination method are higher than that using the microwave method. The shift of binding energy may be explained by a stronger interaction between  $\text{Ni}_2\text{P}$  with  $\text{SiO}_2$  at high temperature.

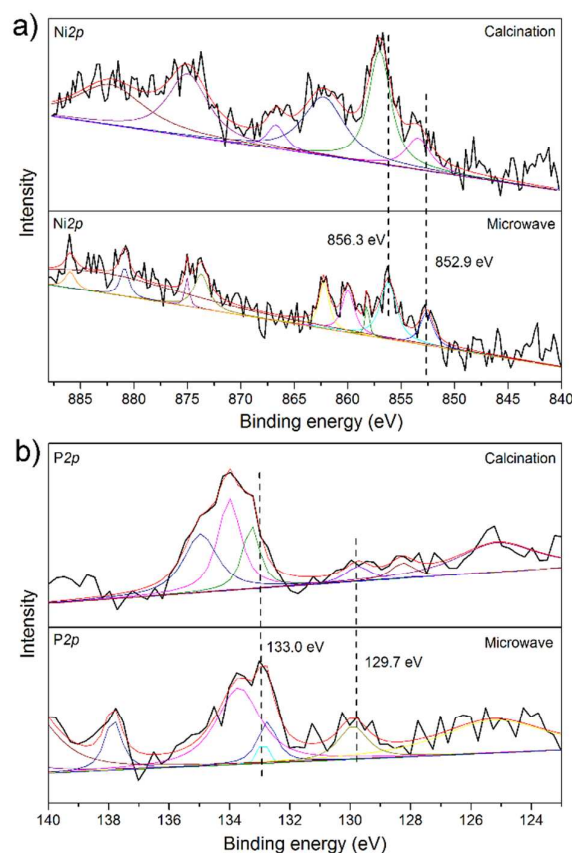

**Fig. 6.** The XPS spectra of 30 wt%  $\text{Ni}_2\text{P}/\text{SiO}_2$  catalysts prepared using different methods: (a)  $\text{Ni}2p$  core level spectra of  $\text{Ni}_2\text{P}/\text{SiO}_2$ , (b)  $\text{P}2p$  core level spectra of  $\text{Ni}_2\text{P}/\text{SiO}_2$ .


### 3.2. Catalytic activity

To study the effect of two preparation methods on catalyst performance, 30 wt%  $\text{Ni}_2\text{P}/\text{SiO}_2$  catalysts were synthesized and tested at different temperatures. HDO catalytic activities were evaluated using 30 wt% methyl palmitate in decalin (testing conditions: 1 MPa,  $\text{WHSV} = 6\text{ h}^{-1}$ ,  $\text{H}_2/\text{oil} = 1000$ ). According to published papers,<sup>9, 30-33</sup> we give a possible HDO route of methyl palmitate over  $\text{Ni}_2\text{P}/\text{SiO}_2$  (Scheme 1).

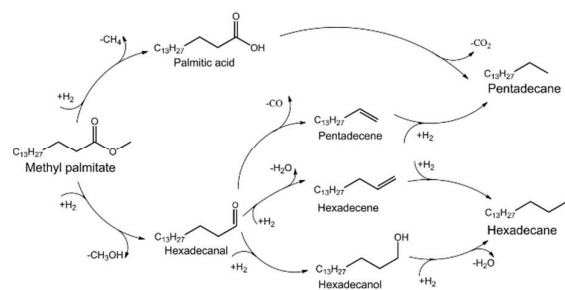

**Scheme 1.** The HDO route of methyl palmitate over Ni<sub>2</sub>P/SiO<sub>2</sub>.

As shown in Fig. 7, Ni<sub>2</sub>P/SiO<sub>2</sub> prepared using microwave method has a significantly higher HDO activity at low reaction temperatures. The principal products of the HDO reaction for two catalysts are pentadecane and hexadecane. Isomerization products were not detected, and the content of other by-products is very low (<1%). BET specific surface area of two catalysts was 117, and 120 m<sup>2</sup> g<sup>-1</sup>, respectively (Table 1). However, Ni<sub>2</sub>P/SiO<sub>2</sub> prepared using microwave method has higher CO uptake, which also indicates that catalyst prepared by microwave had a better dispersion of Ni<sub>2</sub>P particles. Two catalysts have similar TOF value at 290 °C, which is 0.18 and 0.19 s<sup>-1</sup>. For comparison, 30 wt% Ni/SiO<sub>2</sub> were prepared using the incipient wetness impregnation. As shown in Table 1, Ni/SiO<sub>2</sub> shows very low conversion (27.0%) and TOF value (0.08 s<sup>-1</sup>).

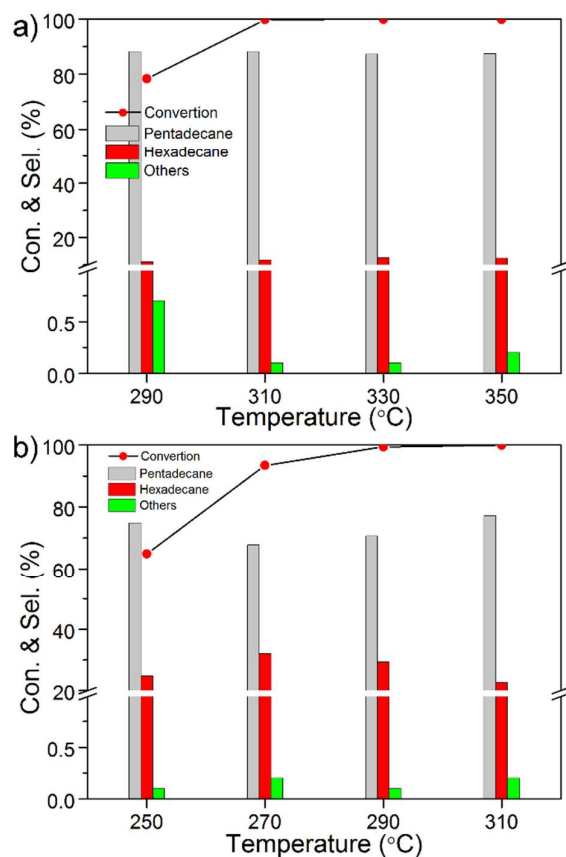


**Fig. 7.** The catalytic activities of 30 wt% Ni<sub>2</sub>P/SiO<sub>2</sub> catalysts at different temperatures (a) prepared using the calcination method (P/Ni = 1.5, 250 °C, 30 min), and (b) prepared using the microwave method (P/Ni = 1.5, 230 °C, 5 min).

To clearly understand the advantage of the microwave method, comparison chart of the two methods was given. As shown in Scheme 2, two methods use same precursor and protective gas. The difference is that the microwave method requires lower reaction temperature and shorter time. Including heating and cooling steps, the entire microwave process is only about fifteen minutes, which is far below the calcination method.

**Table 1.** The physical properties and HDO activities of different catalysts (testing conditions: 1 MPa, 290 °C, WHSV = 6 h<sup>-1</sup>, H<sub>2</sub>/oil = 1000).

Samples	$a_{s,BET}$ (m <sup>2</sup> g <sup>-1</sup> )	CO (μmol g <sup>-1</sup> )	Conver sion (%)	TOF (s <sup>-1</sup> )
SiO <sub>2</sub>	279	--	--	--
30 wt% Ni/SiO <sub>2</sub>	118	6.0	27.0	0.08
30 wt% Ni <sub>2</sub> P/SiO <sub>2</sub> (Calcination)	117	8.0	78.3	0.18
30 wt% Ni <sub>2</sub> P/SiO <sub>2</sub> (Microwave)	120	9.8	99.4	0.19

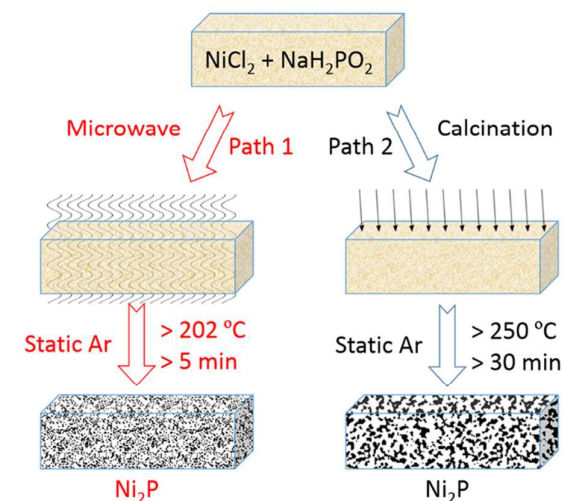

**Scheme 2.** Pathway of two methods.

## Conclusions

In this paper, Ni<sub>2</sub>P and Ni<sub>2</sub>P/SiO<sub>2</sub> were synthesized from nickel hypophosphite precursors at 230 °C for 5 min using a CEM Discover microwave reactor, and the initial reaction temperature is between 202 and 206 °C. The catalysts were characterized using XRD, TEM, SEM, XPS, BET, carbon

monoxide chemisorption, and catalytic performance was evaluated for HDO of methyl palmitate in a continuous flow fixed-bed reactor. Interestingly, microwave irradiation does not result in sintering of Ni<sub>2</sub>P particles. The principal products of the HDO reaction for two catalysts are pentadecane and hexadecane. Isomerization products were not detected, and the content of other by-products is very low (<1%). The HDO results demonstrate that the catalyst prepared using microwave having better activity than that prepared using calcination.

### Acknowledgements

This work was financially supported by the NSFC (21376123, U1403293), MOE (IRT-13R30 and 113016A), NSFT (15JCQNJC05500), and the Research Fund for 111 Project (B12015).

### References

- D. A. Ruddy, J. A. Schaidle, J. R. Ferrell, J. Wang, L. Moens and J. E. Hensley, *Green Chem.*, 2014, **16**, 454-490.
- S. T. Oyama, *J. Catal.*, 2003, **216**, 343-352.
- E. J. Popczun, J. R. McKone, C. G. Read, A. J. Biacchi, A. M. Wilttrout, N. S. Lewis and R. E. Schaak, *J. Am. Chem. Soc.*, 2013, **135**, 9267-9270.
- G. Shi, L. Su and K. Jin, *Catal. Commun.*, 2015, **59**, 180-183.
- S. T. Oyama, T. Onkawa, A. Takagaki, R. Kikuchi, S. Hosokai, Y. Suzuki and K. K. Bando, *Top. Catal.*, 2015, **58**, 201-210.
- A. Cho, A. Takagaki, R. Kikuchi and S. T. Oyama, *Top. Catal.*, 2015, **58**, 219-231.
- J. S. Moon, E. G. Kim and Y. K. Lee, *J. Catal.*, 2014, **311**, 144-152.
- A. Iino, A. Cho, A. Takagaki, R. Kikuchi and S. T. Oyama, *J. Catal.*, 2014, **311**, 17-27.
- Y. Yang, C. Ochoa-Hernández, V. A. de la Peña O'Shea, J. M. Coronado and D. P. Serrano, *ACS Catal.*, 2012, **2**, 592-598.
- K. L. Li, R. J. Wang and J. X. Chen, *Energy & Fuels*, 2011, **25**, 854-863.
- K. L. Stamm, J. C. Garno, G.-y. Liu and S. L. Brock, *J. Am. Chem. Soc.*, 2003, **125**, 4038-4039.
- X. Wang, P. Clark and S. T. Oyama, *J. Catal.*, 2002, **208**, 321-331.
- J. A. Cecilia, A. Infantes-Molina, E. Rodríguez-Castellón and A. Jiménez-López, *J. Catal.*, 2009, **263**, 4-15.
- Y. Xie, H. L. Su, X. F. Qian, X. M. Liu and Y. T. Qian, *J. Solid State Chem.*, 2000, **149**, 88-91.
- S. Yang, C. Liang and R. Prins, *J. Catal.*, 2006, **237**, 118-130.
- C. Qian, F. Kim, L. Ma, F. Tsui, P. Yang and J. Liu, *J. Am. Chem. Soc.*, 2004, **126**, 1195-1198.
- A. E. Henkes, Y. Vasquez and R. E. Schaak, *J. Am. Chem. Soc.*, 2007, **129**, 1896-1897.
- A. Wang, M. Qin, J. Guan, LiWang, H. Guo, X. Li, YaoWang, R. Prins and Y. Hu, *Angew. Chem. Int. Ed.*, 2008, **47**, 6052-6054.
- Q. Guan, X. Cheng, R. Li and W. Li, *J. Catal.*, 2013, **299**, 1-9.
- Q. Guan, W. Li, M. Zhang and K. Tao, *J. Catal.*, 2009, **263**, 1-3.
- J. Gopalakrishnan, S. Pandey and K. K. Rangan, *Chem. Mater.*, 1997, **9**, 2113-2116.
- V. T. da Silva, L. A. Sousa, R. M. Amorim, L. Andrini, S. J. A. Figueroa, F. G. Requejo and F. C. Vicentini, *J. Catal.*, 2011, **279**, 88-102.
- K.-S. Cho, H.-R. Seo and Y.-K. Lee, *Catal. Commun.*, 2011, **12**, 470-474.
- G. Shi and J. Shen, *J. Mater. Chem.*, 2009, **19**, 2295-2297.
- Z. Yao, M. Li, X. Wang, X. Qiao, J. Zhu, Y. Zhao, G. Wang, J. Yin and H. Wang, *Dalton Trans.*, 2015, **44**, 5503-5509.
- H. Song, M. Dai, H. Song, X. Wan and X. Xu, *Appl. Catal. A Gen.*, 2013, **462-463**, 247-255.
- W. Zhu, P. Liu, S. Xiao, W. Wang, D. Zhang and H. Li, *Appl. Catal. B Environ.*, 2015, **172**, 46-51.
- V. Sridhar, I. Lee, H.-H. Chun and H. Park, *Carbon*, 2015, **87**, 186-192.
- O. Muraza, A. Abdul-lateef, T. Tago, A. B. D. Nandiyanto, H. Konno, Y. Nakasaka, Z. H. Yamani and T. Masuda, *Microporous Mesoporous Mater.*, 2015, **206**, 136-143.
- J. Chen, H. Shi, L. Li, K. Li, *Appl. Catal. B Environ.* **2014**, **144**, 870-884.
- B. X. Peng, X. G. Yuan, C. Zhao, J. A. Lercher, *J. Am. Chem. Soc.* **2012**, **134**, 9400-9405.
- S. Brillouet, E. Baltag, S. Brunet, F. Richard, *Appl. Catal. B Environ.* **2014**, **148-149**, 201-211.
- R. W. Gosseink, S. A. W. Hollak, S.-W. Chang, J. Haveren, K. P. Jong, J. H. Bitter, D. S. van Es, *ChemSusChem* **2013**, **6**, 1576-1594.