

# RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## Preparation and characterisation of transparent and flexible PEDOT:PSS/PANI electrodes by ink-jet printing and electropolymerisation

Annalisa Vacca<sup>a\*</sup>, Michele Mascia<sup>a</sup>, Simone Rizzardini<sup>a</sup>, Simona Corgiolu<sup>a</sup>, Simonetta Palmas<sup>a</sup>,  
Monia Demelas<sup>b</sup>, Annalisa Bonfiglio<sup>b</sup>, Carlo Ricci<sup>c</sup>

<sup>a</sup> *Dipartimento di Ingegneria Meccanica Chimica e dei Materiali, Università degli Studi di Cagliari,  
Via Marengo 2, 09123 Cagliari, Italy*

<sup>b</sup> *Dipartimento di Ingegneria Elettrica ed Elettronica, Università degli Studi di Cagliari,  
Via Marengo 3, 09123 Cagliari, Italy*

<sup>c</sup> *Dipartimento di Fisica, Università degli Studi di Cagliari, Complesso Universitario di Monserrato,  
S.P. Monserrato-Sestu Km 0.700, 09042 Monserrato (CA), Italy*

\*Corresponding author

e-mail: annalisa.vacca@dimcm.unica.it

tel. +39 070 675 50 59

### Abstract

Novel flexible PEDOT:PSS/PANI bilayered thin-films electrodes were successfully prepared by ink-jet printing of PEDOT:PSS on PEN substrate and subsequent electrochemical polymerisation of PANI. Scanning electron microscopy (SEM), cyclic voltammetry (CV) and electrochemical impedance spectroscopy (EIS) were used to systematically investigate structure, morphology and electrochemical behaviour of the electrodes. The PEDOT:PSS/PANI bilayer nanofilms have been tested as pH sensors. As a comparison, either PEDOT:PSS or PANI electrodes have been tested for pH measurements. The results show that the sensitivity of PEDOT:PSS/PANI bilayer film is higher than that of PEDOT:PSS and PANI electrodes, indicating a synergistic effect of the two polymers. A reversible near-Nernstian behaviour of the open circuit voltage with pH was found, with a slope of 58.9 mV/pH unit in a wide range of pH from 2 to 14.

### Introduction

Conducting polymers have attracted much attention since their discovery in the late 1970's. Thanks to their outstanding characteristics such as light-weight and high flexibility, the use of polymer as

active materials in electronic devices may allow replacing the traditional metal-based devices and obtain fully-plastic electronic devices.<sup>1</sup> One of the technical challenges is due to very low conductivity of some solution-processible organic compounds, which can lower the device performance.

Among the others, poly(3,4-ethylenedioxythiophene) (PEDOT) presents very interesting properties including high electrical conductivity, environmental stability, and high transparency<sup>1-2</sup>, so that it has been proposed for different electronics applications, such as organic photovoltaic devices (OPVs)<sup>3</sup> and organic light emitting diodes (OLEDs).<sup>4</sup> Moreover, PEDOT could be patterned by ink-jet printing technique, which is a low-cost, simple, easy method to fabricate flexible devices.<sup>5</sup> However, PEDOT is not soluble in water, so that aqueous inks are usually prepared using poly(styrenesulfonic acid) (PSS): the formation of the polyelectrolyte complex of PEDOT:PSS enhances the dispersibility of particles in water.<sup>6</sup> The conductivity of the film depends on the ratio of PEDOT to PSS as well as on the size of the PEDOT:PSS particles dispersed in water; however, the pristine films present a very low conductivity ( $<1 \text{ S cm}^{-1}$ ) to be used as electrode material.<sup>7</sup> Several authors attribute the low conductivity of the PEDOT:PSS films to the formation of coil structures, in which PEDOT is surrounded by PSS, in a discontinuous granular system with low interconnections between the particles.<sup>1, 6, 8, 9</sup> To overcome this drawback, different compounds have been added during the preparation: noticeable increasing in conductivity (up to 2 or 3 orders of magnitude) has been obtained by using surfactants<sup>10</sup>, graphene oxide<sup>6-11</sup> or polar solvents<sup>12</sup> which can change the pristine structure. For example, by using ethylene glycol (EG) the de-doping process can partially remove the amorphous and insulating PSS phase improving the conductivity up to  $467 \text{ S cm}^{-1}$ .<sup>13</sup>

Another strategy is the combination of PEDOT:PSS with other conducting polymers, which can allow obtaining hybrid organic systems with tuneable properties: in particular polyaniline (PANI) presents very attractive characteristics including high conductivity and high active surface due to its porous structure. PANI is generally synthesized by chemical or electrochemical oxidative polymerisation of the monomer in acidic aqueous medium: however, the electrochemical polymerisation allows to a better control of the synthesis parameters. Many characteristics of the PANI depend on the redox equilibria of various reduced and oxidized forms, which take place in accordance with redox potential and pH of the media.<sup>14, 15</sup> In particular, the half-oxidized form of PANI originates the deprotonated emeraldine base and the protonated emeraldine salt which is the most electrically conductive form. PANI is then usually active at acidic pH while its activity decreases at neutral and alkaline pH. PANI can be easily combined with anionic polymers and polyelectrolytes to form layer-by-layer constructions: the formation of multi-layered complexes of

PANI with negatively charged components can enhance the redox activity of the polymer at higher pH.<sup>16</sup>

Combinations of different conducting polymers can allow obtaining composites which present novel properties and unique structures.<sup>17</sup> Composites based on PEDOT:PSS and PANI have been prepared following different strategies allowing to obtain powders or multilayer composites. Zhang and coworkers prepared PEDOT/PANI bilayer nanofibers by subsequent oxidative polymerization of the parent monomers in bulk solution: the obtained nanofibers were used as electrode after a drop-cast onto a glassy carbon.<sup>18</sup> Bilayered nanofilms of PEDOT/PANI have been synthesized by Shi and coworkers by electrochemical polymerization of PANI in a mixed alcohol solution on PEDOT:PSS nanofilm electrode prepared by spin coating of PEDOT:PSS/5% DMSO on glass.<sup>19</sup> Similarly, the same group prepared bilayered PEDOT/PANI electrodes starting from electrodes based on single-walled carbon nanotubes and PEDOT:PSS spin coated on glass.<sup>20</sup>

In this work, flexible and transparent fully organic hybrid electrodes have been prepared by ink-jet printing of PEDOT:PSS on Polyethylene Naphthalate (PEN) substrates followed by electrochemical polymerisation of PANI. This approach conjugates the ink-jet printing technique, which is a low-cost and easily scalable method to obtain flexible devices with the electrochemical polymerization which allows a good control and adhesion of the PANI layer on PEDOT:PSS.

### Experimental section

The PEDOT:PSS electrodes are fabricated on a Poly(ethylene 2,6-naphthalate (PEN) substrate, 125  $\mu\text{m}$  thick. Substrates are cleaned by subsequent 10 min of ultrasonic bath in water and in acetone; they are washed in deionized water, dried under nitrogen flow and then activated by means of a plasma treatment (10 sec at 100 W). The PEDOT:PSS layer is realized by ink-jet printing using the Fujifilm Dimatix Material Printer (DMP) 2800. The ink is prepared by sonicating for 20 minute a solution made of PEDOT:PSS (pH 500 provided from H. C. Starck). Three layers are printed by using three nozzles of a DMC-11601 cartridge (each nozzle generates 1 pL drop of ink) with a drop spacing of 15  $\mu\text{m}$ . During printing, substrates are kept at 45°C to facilitate the solvent evaporation. After printing, samples are annealed in an oven at 130°C for 15 min. After annealing, ethylene glycol is deposited by spin coating and dried in an oven at 130°C for 15 min. These electrodes are denoted as PEDOT:PSS (see figure 1).

The electrochemical experiments were performed at room temperature using an AUTOLAB PGSTAT302N (Metrohm, Switzerland) potentiostat/galvanostat equipped with a frequency response analyser controlled with the NOVA software. A conventional three-electrode cell (V=10 ml) was used in which Saturated Calomel Electrode (SCE) was the reference and Pt wire was used

as counter electrode. Polyaniline was electropolymerized on PEDOT:PSS electrodes from aqueous solutions of aniline (0.1 M) and  $\text{HNO}_3$  (1 M). Electropolymerisation was performed by cyclic voltammeteries from 0 to 0.95 V with a scan rate of 100 mV/s. Ten cycles were applied to obtain PANI films. The electrodes obtained by electropolymerisation on PEDOT:PSS are denoted as PEDOT:PSS/PANI (see figure 1).

#### FIGURE 1

The electrodes were characterized by cyclic voltammeteries (CVs), electrochemical impedance spectroscopies (EIS) and open circuit potential (OCP) measurements in solution with different pH. EIS were performed in solution with different pH by varying the frequency from 30 kHz down to 0.1 Hz at open circuit potential with an excitation amplitude of 10 mV. The impedance spectra were then fitted to an equivalent electrical circuit by using the software ZSimpWin 2.0 (EChem software). Scanning electron microscopy (NOVA 600, Nanolab dual beam) was used to characterize the structures of PEDOT:PSS and PEDOT:PSS/PANI electrodes. Focused ion beam (FIB) was also used to very precise cross sections of samples for subsequent imaging via SEM.

Raman measurements were performed in air at room temperature with a compact spectrometer BWTEK i-Raman Ex integrated system, excitation wavelength at 1064 nm (provided by a Nd:YAG laser), in back scattering geometry. The spectra were collected with very low power beam (< 5 mW) focalized in 1 mm<sup>2</sup> through a microscope objective Olympus x20 to avoid any heating or photodegradation effect. The threshold to observe the photodegradation of the sample (pure polyaniline) was observed for beam power higher than 15 mW.

### Results and Discussion

Figure 2 shows the cyclic voltammogram of aniline swept at 100 mV s<sup>-1</sup> during 10 scans in aqueous solution containing 0.1 M aniline and 1.0 M  $\text{HNO}_3$  at PEDOT:PSS working electrode. The electropolymerisation process of PANI on conducting electrodes (i.e. gold, platinum) usually exhibits well-defined redox peaks corresponding to a series of redox transitions, which are related to the polymerisation processes.<sup>21</sup> In the present case, two oxidation waves and one reduction wave can be identified (see inset of figure 1), although with difficult due to the low conductivity of the PEDOT electrode. Anyway, both oxidation and reduction currents progressively increase with the scans, thus evidencing the growing of a conductive film on the electrode surface. The thickness of the deposited layer of PANI can be estimated from the voltammetric charge associated to the oxidation of the monomer ( $Q_a$ ) by assuming a current yield of 1, as follows:<sup>22</sup>

$$h = \frac{Q_a M_w}{zFdA} \quad 1)$$

Where  $M_w$  is the molecular weight of aniline,  $z = 0.5$  (number of electrons/aniline),  $A$  is the area of the electrode,  $d$  is the specific density of aniline, and  $F$  is Faraday's constant. After ten cycles, the estimated thickness of the PANI coating is about 305 nm and a green layer is visible on the grey surface of PEDOT:PSS.

#### FIGURE 2

The surface morphology of the electrodes has been observed by SEM: Figure 3 shows the micrographs of ink-jet PEDOT:PSS and PEDOT:PSS/PANI films. As it can be seen, the PEDOT:PSS layer is uniform and relatively smooth; after the electropolymerisation of PANI a porous layer with a fibrous nanometric structure is visible, which covers the under-layer of PEDOT:PSS. The FIB cross section shows that the PEDOT:PSS layer is about 930 nm, while after the PANI electropolymerisation the overall thickness of the layer is 1300 nm with non-uniform profile.

#### FIGURE 3

Figure 4 reports the Raman spectra collected on PEDOT:PSS/PANI sample, and, for comparison, the spectrum of pure polyaniline and from PEDOT:PSS. As can be observed the Raman spectrum of the PEDOT:PSS/PANI film presents all the main vibrations of polyaniline: at  $1170 \text{ cm}^{-1}$  (C–H bending vibration of the quinoid/benzenoid ring), the C–N<sup>+</sup> vibration at  $1327 \text{ cm}^{-1}$ , the vibration due to delocalized polaron in the extended polymeric conformation at  $1365 \text{ cm}^{-1}$ , the band to the N–H vibration at about  $1500 \text{ cm}^{-1}$  and, finally the band at  $1595 \text{ cm}^{-1}$ , related to the stretching vibration of C–C in the benzenoid ring.<sup>23</sup> Moreover, the band related to the PEDOT:PSS at about  $1250 \text{ cm}^{-1}$  and at  $1422 \text{ cm}^{-1}$  are still visible. Actually, the IR laser beam at 1064 nm is not totally absorbed from the polyaniline thin film, being able to reach and stimulate the organic substrate. On the other hand, the low energy laser beam avoid any luminescence effect from polyaniline.

#### FIGURE 4

The presence of electroactive PANI layer on the PEDOT:PSS substrate can be evidenced by cyclic voltammeteries in monomer-free solutions. Figure 5 shows the voltammograms of PEDOT:PSS and PEDOT:PSS/PANI electrodes in 1M HNO<sub>3</sub>. The CV at PEDOT:PSS electrode shows a nearly rectangular shape, and only two redox shoulders are present at 0.6 and 0.26 V, indicating low faradic activity and highly capacitive behaviour.<sup>24</sup> Similar results have been already observed for PEDOT inkjet printed on flexible material without metal current collector, which are similar to

those used in the present work.<sup>25</sup> In the CV of PANI modified electrode, the typical peaks related to doping and undoping of protons and anions in the polymeric film, as well as to the transformation between different forms of PANI, are well visible. The oxidation peak around +250 mV is attributed to the conversion from leucoemeraldine into emeraldine form, while the second peak appearing around +800 mV is due to emeraldine/pernigraniline transformation.<sup>26-28</sup> Moreover, comparing the CVs of PEDOT:PSS and PEDOT:PSS/PANI it can be observed that the capacitance in presence of PANI is considerably larger than in case of PEDOT:PSS, thus indicating that PEDOT:PSS/PANI has higher electrochemical active area.

#### FIGURE 5

The electrochemical proprieties of the polymeric electrodes have been investigated by electrochemical impedance spectroscopy in aqueous solutions at different pH. Figure 6 shows the Nyquist plots of PEDOT:PSS and PEDOT:PSS/PANI, recorded in acidic solution at the OCP: as can be seen for PEDOT the impedance plot presents a 90° capacitive line in the low frequencies range, while at higher frequencies two deviations can be observed (see magnification of Nyquist plot in the inset of figure 6).

The high-frequency intercept of the semicircle with the real axis can be used to evaluate the internal resistance, which includes the resistance of the electrolyte solution, the intrinsic resistance of the active material, and the contact resistance at the electroactive material/current collector interface.<sup>29</sup> PEDOT:PSS and PEDOT:PSS/PANI show similar impedance spectra, but the second one is shifted to the left, indicating a less resistive behaviour. In order to investigate the effect of the presence of PANI over the PEDOT, some electrodes with an higher PANI load have been prepared by 20 cycles of voltammetric polymerisation (PEDOT:PSS/PANI20): the EIS spectrum of one of them is compared with the previous one in figure 6. As can be seen, the reduction of the resistivity due to PANI layer is emphasised in samples with higher PANI load.

In order to obtain the characteristic parameters of the electrodes, the impedance spectra have been modelled with the equivalent circuit proposed by Danielsson et al.<sup>31</sup> for PEDOT electrodes (see inset of figure 6). The following elements have been inserted in the circuit: the uncompensated resistance ( $R_u$ ), the charge transfer resistance ( $R_{ct}$ ), the double layer capacitance ( $C_{dl}$ ), the electronic contribution to the capacitance ( $C_d$ ) and the finite-length Warburg element ( $Z_D$ ) which represents the diffusion within a thin layer of electrolyte.  $Z_D$  includes a diffusion capacitance ( $C_D$ ), a diffusional time constant ( $\tau_D$ ) and a diffusion resistance ( $R_D = \tau_D/C_D$ ):<sup>32, 33</sup>

$$Z_D = \frac{(\tau_D/C_D) \coth(j\omega\tau_D)^{1/2}}{(j\omega\tau_D)^{1/2}} \quad 2)$$

where  $\omega$  is the angular frequency ( $2\pi f$ ) and  $j=(-1)^{1/2}$ .

All the impedance spectra obtained for PEDOT:PSS, PEDOT:PSS/PANI and PEDOT:PSS/PANI20 have been modelled with this equivalent circuit obtaining a very good fit of the impedance spectra ( $\chi^2 < 6 \times 10^{-5}$ ). The fitting curves of the Nyquist plots can be seen in figure 6, while Table 1 reports the values of the circuit parameters. As can be seen in table 1, the uncompensated resistance for PEDOT:PSS is 1180  $\Omega$ , indicating high intrinsic resistance of this electrode. After the electropolymerisation of PANI on PEDOT:PSS,  $R_u$  decreases: values of 900 and 733  $\Omega$  are obtained for PEDOT:PSS/PANI and PEDOT:PSS/PANI20 respectively. Similarly, the charge transfer resistance decreases after the PANI deposition and the lowest values correspond to the higher PANI load. As the capacitance is concerned, the total interfacial capacitance  $C_{tot}$  of the polymers can be evaluated combining in series the electronic contribution to the bulk capacitance  $C_d$  and the ionic contribution to the bulk capacitance  $C_D$  as follow: <sup>33, 34</sup>

$$C_{tot} = \frac{1}{1/C_d + 1/C_D}$$

As can be seen for PEDOT:PSS  $C_d \ll C_D$  meaning that the total interfacial capacitance is dominated by the electronic contribution: similar behaviour has been found by other authors for PEDOT:PSS electrodes. <sup>33, 34</sup> For PEDOT:PSS modified with PANI, the ionic contribution becomes more important due to the porous structure of PANI: as the PANI load increases the diffusional time constant increases indicating a slower access of the counter ions into the pores of polymer.

FIGURE 6

TABLE 1

The electrochemical activity of the organic bilayer has been tested via measurements of pH vs. OCP. Figure 7 shows the behaviour of PEDOT:PSS/PANI electrode at different pH: the potential equilibrium response shows a linear trend with pH in the range from 2 to 13.5, with a slope of 58.9 mV/pH unit which indicates a near-Nerstian behaviour of the organic bilayer. In order to investigate the reversibility of the response to pH, PEDOT:PSS/PANI electrode was tested with increasing and decreasing pH. As can be seen from figure 6 the potentiometric responses did not show significant dependence on the direction of pH changes indicating a very low hysteresis. Different results were obtained for PEDOT:PSS/PANI20: the trend of OCP vs. pH showed two slopes of 51.1 mV/pH unit and 8.9 mV/pH unit in acidic and neutral-alkaline pH, respectively.

FIGURE 7



Moreover, measurements of OCP vs. pH have been performed using electrodes of either PANI or PEDOT:PSS onto plastic substrates, without metallic current collector. PEDOT layers have been obtained by ink-jet printing, and PANI was dip-coated. As can be seen in figure 8, PEDOT shows a linear trend of the potential equilibrium response as a function of pH with a slope of 10.5 mV/pH unit indicating a very low sensitivity toward pH variations, which can be attributed to the low conductivity of the ink-jet printed film. As highlighted in the literature, appreciable increasing in conductivity has been obtained only when PEDOT:PSS was modified with ethylene glycol,<sup>35</sup> graphene oxide<sup>8</sup> and dimethyl sulfoxide<sup>1</sup>. As highlighted by different authors, the pristine PEDOT:PSS presents a coil structure where PEDOT grains are surrounded by a PSS insulating shield which prevents the interactions between the hydrophobic PEDOT and water.<sup>1, 6, 8, 9, 36</sup> Thus, the low pH responses may be attributed both to the low conductivity and to the inactivity of the  $\text{SO}_3^-$  groups of the PSS.

The dip-coated PANI shows a linear trend for pH between 2 and 7 with a slope of 50.7 mV/pH unit, while at higher values of pH the slope of OCP vs. pH decreases down to 7.7 mV/pH unit indicating a considerable loss of sensitivity at neutral-alkaline pH. It is well known that PANI is a conducting polymer that shows a very high sensitivity toward pH: a linear dependence of OCP from pH in acidic solutions has been found for PANI electropolymerized on different substrates.<sup>37-41</sup> At neutral or basic pH the sensitivity significantly decreased and, depending on the preparation conditions and on the substrates, the detection of pH is limited below 8-9, while in the acidic range of pH PANI usually presents a near-Nerstian or a sub-Nerstian behaviour.<sup>37-39, 42</sup> At higher values of pH, the sensitivity decreases and a reduction of the slope in pH vs. OPC curve has been often observed. In alkaline solution, the PANI becomes deprotonated and the conductivity of the films undergoes a dramatic decrease in magnitude.

#### FIGURE 8

Based on the above considerations, the high sensitivity of PEDOT:PSS/PANI in a wide range of pH, can be really attributed to a synergistic effect. In the low pH range the response is due to protonation/deprotonation of amino groups of conducting PANI. At neutral and alkaline pH the sensitivity of PEDOT/PANI can be explained considering that the ink-jet printed PEDOT:PSS contains large amounts of amorphous PSS as insulators which is added to dissolve PEDOT in water. When the PANI is electropolymerized on PEDOT:PSS, the positive charge in the PANI backbone may weaken the coulombic attraction between PEDOT and PSS creating conductive pathways which allows an increase of the conductivity of the pristine PEDOT:PSS structure (see scheme in figure 9), similarly to the results obtained with PEDOT:PSS treated with DMSO<sup>1</sup>,

graphene oxide<sup>6,8</sup> and ethylene glycol.<sup>9</sup> Thus, when PANI in the organic bilayer is in its insulating form at alkaline pH, the extended-coil conformation of PEDOT:PSS can guarantee higher conductivity while the negative charged groups  $\text{SO}_3^-$  can contribute to the responses at neutral and alkaline pH of the solution. It is worth observing that, when the PANI load increases, the behaviour of the bilayered film is similar to that of dip-coated PANI indicating that an excessive PANI load hinders the interactions between the negative charged groups  $\text{SO}_3^-$  and the solution.

FIGURE 9

### Conclusions

Hybrid polymeric electrodes were obtained by inkjet printing of PEDOT:PSS combined with electropolymerisation of aniline. With this approach we obtained a bilayer electrode in which PEDOT:PSS was both active material and current collector, since metallic components were not used.

A thin film of PANI onto PEDOT:PSS was evidenced by SEM and Raman analyses. The electrodes were characterised by electrochemical impedance spectroscopy, which evidenced a large increase in the specific surface and a reduction of resistivity after coating of PEDOT:PSS substrates with PANI.

The electrodes were tested as pH sensors: the results show that the hybrid structures have linear response in pH window larger than those of either PEDOT:PSS or PANI electrodes, as well as higher sensitivity.

### Acknowledgements

This work was partially funded by Regione Autonoma della Sardegna, Fundamental Research Programme, L.R. 7/2007 "Promotion of the scientific research and technological innovation in Sardinia" under grant agreement CRP- 59886 AMBROSIA Project and CRP-27388 BIOFET Project.

## References

1. C. Deetuum, D. Weise, C. Samthong, P. Praserttham, R. R. Baumann and A. Somwangthanaroj, *J. Appl. Polym. Sci.*, 2015, **132**, 42108-42117.
2. S. Rattan, P. Singhal and A. L. Verma, *Polym. Eng. Sci.*, 2013, **53**, 2045-2052.
3. M. Stavitska-Barba and A.M. Kelley, *J. Phys. Chem. C*, 2010, **114**, 6822-6830.
4. T. Y. Wu, Z. Y. Kuo, J. J. Jow, C. W. Kuo, C. J. Tsai, P. R. Chen and H. R. Chen, *Int. J. Electrochem. Sci.*, 2012, **7**, 8076-8090.
5. Z. Xiong and C. Liu, *Org. Electron.*, 2012, **13**, 1532-1540.
6. X. Wu, J. Liu, D. Wu, Y. Zhao, X. Shi, J. Wang, S. Huang and G. He, *J. Mater. Chem. C*, 2014, **2**, 4044-4050.
7. B. H. Zhang, G. P. Tan, Z. Y. Xie, W. Y. Wong, J. Q. Ding and L. X. Wang, *Adv. Mater.*, 2012, **24**, 1873-1877.
8. H. S. Dehsari, E. K. Shalamzari, J. N. Gavvani, F. A. Taromi and S. Ghanbary, *RSC Adv.*, 2014, **4**, 55067- 55076.
9. J. Zhou, E. Q. Li, R. Li, X. Xu, I. Aguilar Ventura, A. Moussawi, D. H. Anjum, M. N. Hedhili, D. Smilgies, G. Lubineau and S. T. Thoroddsen, *J. Mater. Chem. C*, 2015, **3**, 2528-2536.
10. Y. J. Xia, H. M. Zhang and J. Y. Ouyang, *J. Mater. Chem.*, 2010, **20**, 9740-9747.
11. W. Gaynor, G. F. Burkhard, M. D. McGehee and P. Peumans, *Adv. Mater.*, 2011, **2**, 2905-2910.
12. R. Jalili, J. M. Razal, P. C. Innis and G. G. Wallace, *Adv. Funct. Mater.*, 2011, **21**, 3363-3370.
13. H. Okuzaki, Y. Harashina and H. Yan, *Eur. Polym. J.*, 2009, **45**, 256-261.
14. T. Lindfors, S. Ervela and A. Ivaska, *J. Electroanal. Chem.*, 2003, **560**, 69-78.
15. R. Prakash, *J. Appl. Polymer Sci.*, 2002, **83**, 378-385.
16. H. C. Budnikov, G. A. Evtugyn and A. V. Porfireva, *Talanta*, 2012, **102**, 137-155.
17. H. Shi, C. Liu, J. Xu, H. Song, B. Lu, F. Jiang, W. Zhou, G. Zhang and Q. Jiang, *ACS Appl. Mater. Interfaces*, 2013, **5**, 12811-12819.
18. L. Zhang, H. Peng, P. A. Kilmartin, C. Soeller, and J. Travas-Sejdic, *Macromolecules*, 2008, **41**, 7671-7678.
19. H. Shi, C. Liu, J. Xu, H. Song, Q. Jiang, B. Lu, W. Zhou and F. Jiang, *Int. J. Electrochem. Sci.*, 2014, **9**, 7629-7643.
20. H. Shi, C. Liu, Q. Jiang, J. Xu, B. Lu, F. Jiang and Z. Zhu, *Nanotechnology*, 2015, **26**, 245401-245409.

21. N. Plesu, A. Kellenberger, M. Mihali and N. Vaszilcsin, *J. Non-Cryst. Solids*, 2010, **356**, 1081–1088.
22. H. Lu, Y. Zhou, S. Vongehra, K. Hu and X. Meng, *Synth. Met.*, 2011, **161**, 1368–1376.
23. Q. Wang, Q. Yao, J. Chang and L. D. Chen, *J. Mater. Chem.*, 2012, **22**, 17612-17618.
24. Q. Zhao, R. Jamal, L. Zhang, M. Wang, T. Abdiryim, *Nanoscale Res. Lett.*, 2014, **9**, 557-566.
25. L. Fan, N. Zhang and K. Sun, *Chem. Commun.*, 2014, **50**, 6789-6792.
26. J. J. Shi, G. H. Yang and J. J. Zhu, *J. Mater. Chem.*, 2011, **21**, 7343-7349.
27. M. H. Pournaghi-Azar and B. Habibi, *Electrochim. Acta*, 2007, **52**, 4222-4230.
28. H. K. Hassan, N. F. Atta and A. Galal, *Int. J. Electrochem. Sci.*, 2012, **7**, 11161 – 11181.
29. M. H. Yeh, C.P. Lee, C. Y. Chou, L. Y. Lin, H. Y. Wei, C.W. Chu, R. Vittal and K. C. Ho, *Electrochim. Acta*, 2011, **57**, 277–284.
30. D. J. Yun, H. Ra and S. W. Rhee, *Renew. Energy*, 2013, **50**, 692–700.
31. P. Danielsson, J. Bobacka, and A. Ivaska, *J. Solid State Electrochem.*, 2004, **8**, 809-817.
32. J. R. Macdonald, *Impedance spectroscopy - Emphasizing Solid Materials and Systems*, Wiley-Interscience, New York, 1987.
33. J. Bobacka, A. Lewenstam and A. Ivaska, *J. Electroanal. Chem.*, 2000, **489**, 17-27.
34. M. Asplund, H. von Holst and O. Inganas, *Biointerphases*, 2008, **3**, 83-93.
35. J. Y. Ouyang, C. W. Chu, F. C. Chen, Q. Xu, and Y. Yang, *J. Macromol. Sci. A*, 2004, **41**, 1497–1511.
36. Y. J. Xia and J. Y. Ouyang, *ACS Appl. Mater. Interfaces*, 2010, **2**, 474-483.
37. T. Lindfors and A Ivaska, *J. Electroanal. Chem.*, 2002, **531**, 43-52.
38. M. Kaempgen and S. Roth, *J. Electroanal. Chem.*, 2006, **586**, 72–76.
39. C. Ge, N. R. Armstrong, and S. Scott Saavedra, *Anal. Chem.*, 2007, **79**, 1401-1410.
40. A. A. Karyakin, O. A. Bobrova, L. V. Luckachova, and E. E. Karyakina, *Sens. Actuators, B: Chem.*, 1996, **33**, 34-38.
41. C. A. Lindino and L. O. S. Bulhoes, *Anal. Chim. Acta*, 1996, **334**, 317-322.
42. B. Lakard, G. Herlem, S. Lakard, R. Guyetant and B. Fahys, *Polymer*, 2005, **46**, 12233–12239.

**Figure captions**

Figure 1. Pictures of the ink-jet printed PEDOT:PSS and PEDOT:PSS/PANI electrodes.

Figure 2: Cyclic voltammograms recorded during PANI electropolymerisation in 0.1 M aniline + 1 M HNO<sub>3</sub> aqueous solution on PEDOT:PSS electrodes. Inset shows the first voltammetric cycle of polymerisation.

Figure 3. SEM micrograph of surfaces (A and C) and of the focused ion beam (FIB) cross sections (B and D) of PEDOT:PSS (A and B) and PEDOT:PSS/PANI (C and D) on PEN substrate.

Figure 4. Raman spectra of PEDOT:PSS/PANI (a), PANI (b) and PEDOT:PSS (c).

Figure 5. Cyclic voltammograms of PEDOT:PSS (grey line) and PEDOT:PSS/PANI (green line) electrodes performed in monomer-free solutions containing 1 M HNO<sub>3</sub>. Scan rate 100 mV/s.

Figure 6. Nyquist plots of PEDOT:PSS (triangles), PEDOT:PSS/PANI (circles) and PEDOT:PSS/PANI20 (squares) recorded in solution at pH = 2.8.

Figure 7. Trends of open circuit potentials (OCP) versus pH for PEDOT:PSS/PANI electrode (measurements performed from alkaline to acidic or from acidic to alkaline) and PEDOT:PSS/PANI20 electrode (measurements performed from acidic to alkaline).

Figure 8. Trends of open circuit potentials (OCP) versus pH for PEDOT:PSS (grey triangles) and PANI (green and blue circles) electrodes.

Figure 9. Sketch of the modifications of the conformation of pristine PEDOT:PSS after the electropolymerisation of PANI. The grey grain and the light blue lines stand for PEDOT and PSS respectively. The green fibers stand for PANI.

Table 1: Values of the elements calculated from model of the equivalent circuit fitted to impedance spectroscopy data at pH 2.8.

	PEDOT:PSS	PEDOT:PSS/PANI	PEDOT:PSS/PANI20
Ru (ohm)	1183	900	734.2
Cdl (mF)	0.33	0.40	0.66
Rct (ohm)	171.8	66	13.2
Cd (mF)	0.31	0.72	6.37
$\tau_D$ (s)	1.44	3.92	7.21
$C_D$ (mF)	2.26	4.81	34.77

Figure 1

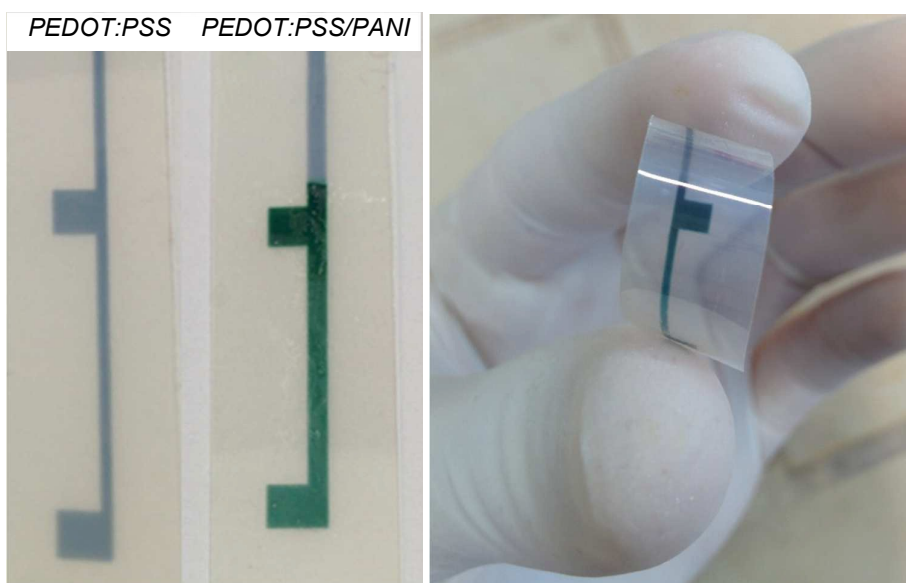


Figure 2

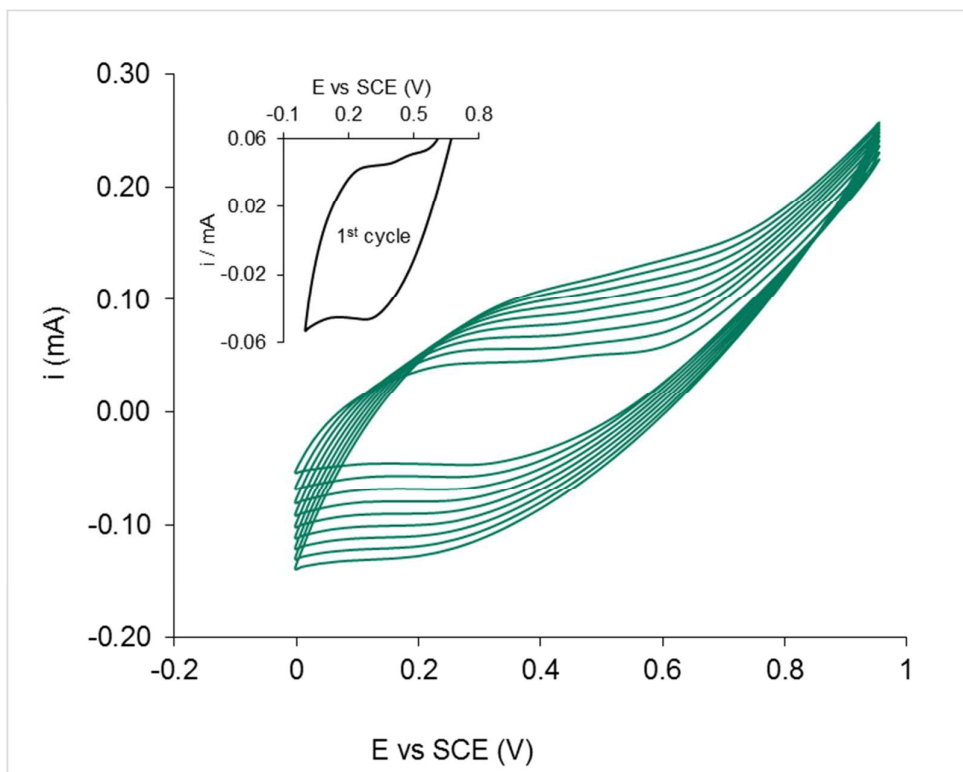




Figure 3.

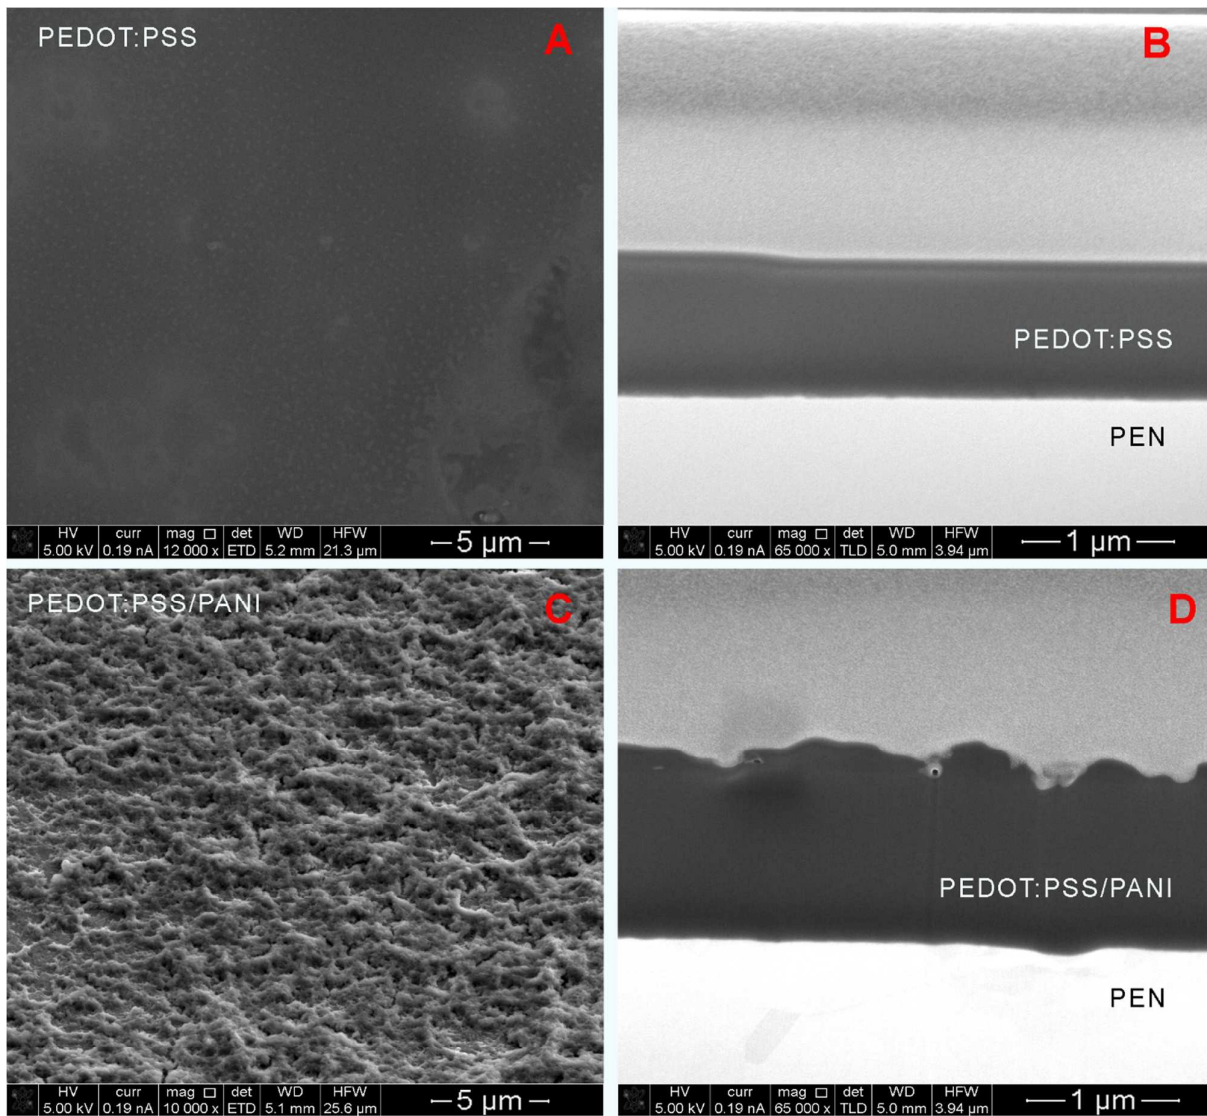


Figure 4.

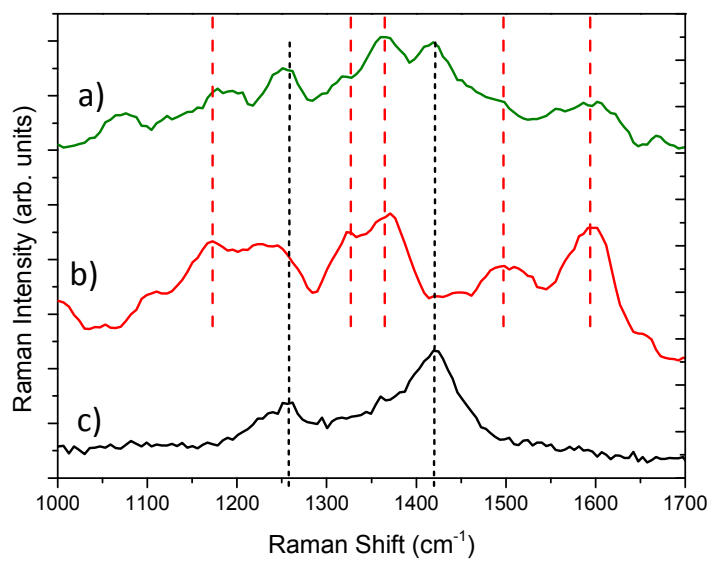


Figure 5

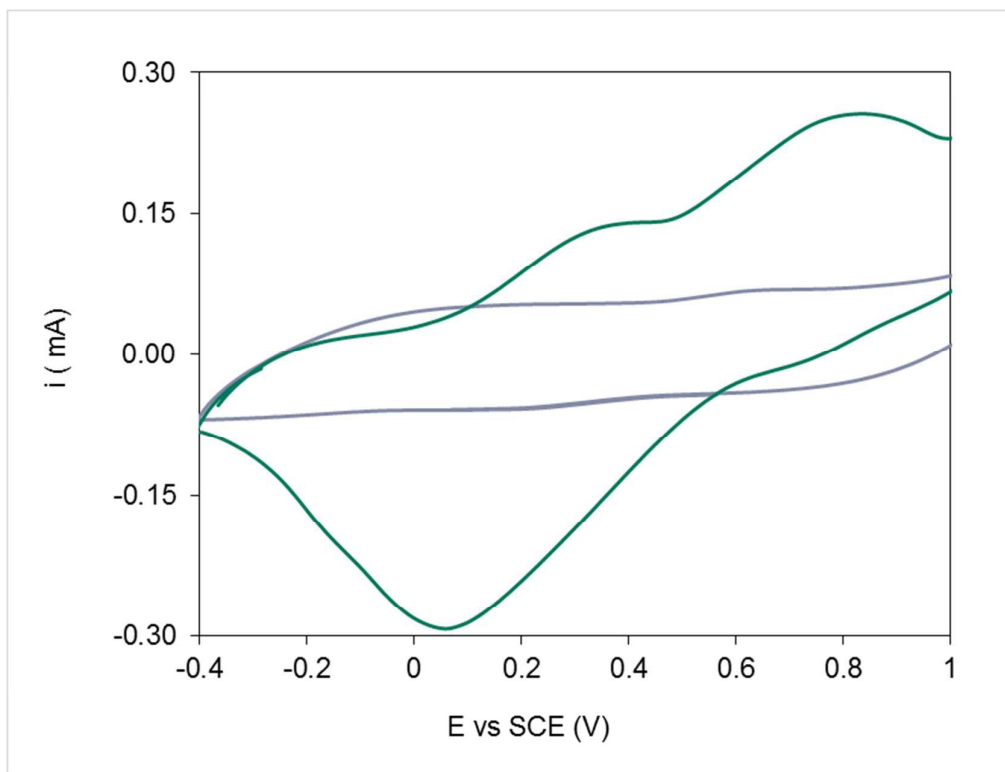


Figure 6

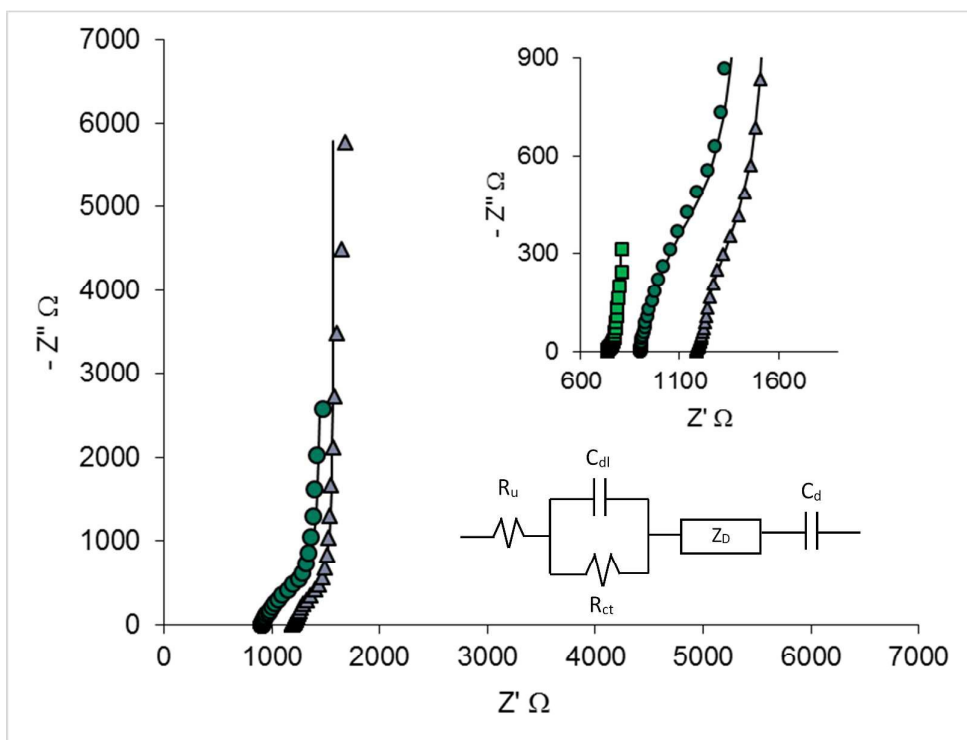


Figure 7

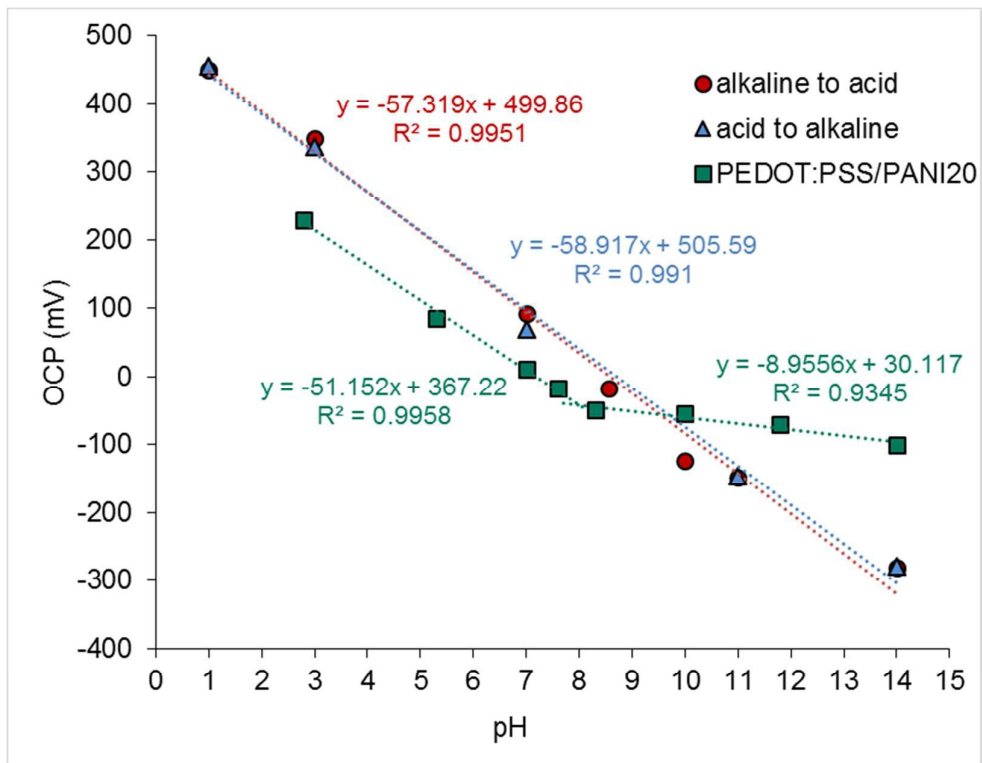


Figure 8

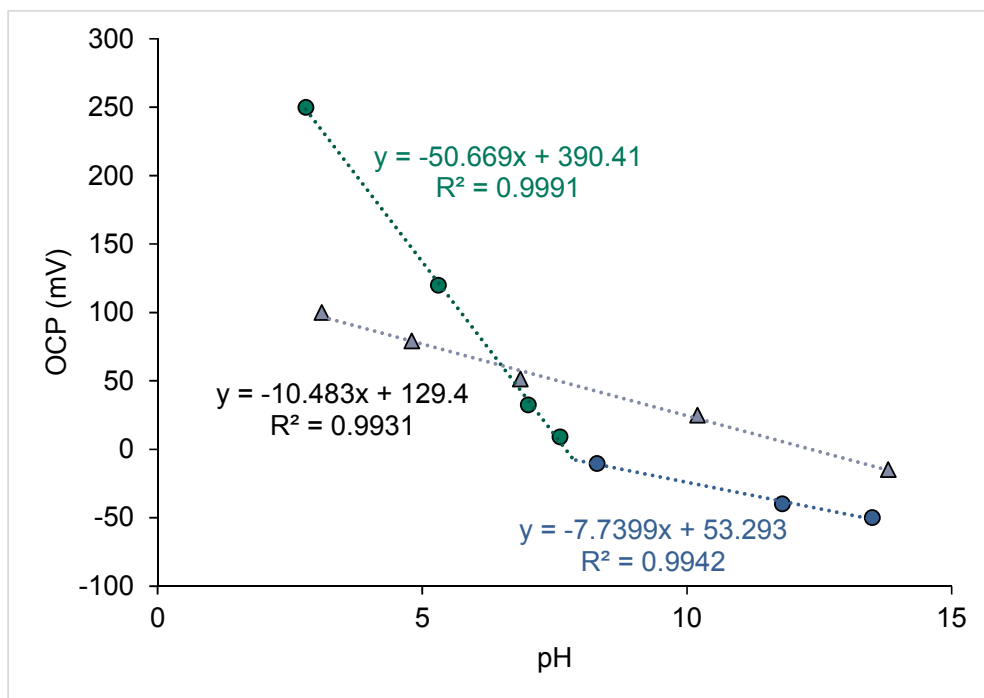


Figure 9

