

# RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

## Synthesis and Characterization of new Photoswitchable Azobenzene-containing poly( $\epsilon$ -caprolactones).

Appiah Clement<sup>a</sup>, Katrin R. Siefertmann<sup>b</sup>, Marcel Jorewitz<sup>b</sup>, Haitham Barqawi<sup>a</sup>, and Wolfgang H. Binder<sup>\*a</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

[www.rsc.org/](http://www.rsc.org/)

A novel and efficient strategy in obtaining series of mono- and bi-armed azobenzene-containing poly( $\epsilon$ -caprolactone)s is described, starting from a commercially available azobenzene dye via azide/alkyne-"click"-reactions. The attachment of alkyne-telechelic poly( $\epsilon$ -caprolactone)s (1 kDa and 3 kDa), followed by chromatographic separation allowed the attachment of either one or two PCL-chains to either side of the azobenzene-dye. The resulting mono- and bi-armed photo-switchable polymers are fully characterized by 2D-NMR techniques and show a high thermal stability. In particular, liquid chromatography at critical conditions (LCCC) coupled to ESI-TOF allowed to prove presence of either one or two polymer chains affixed onto the central azobenzene dye.

### Introduction

Polymeric based molecular switches have recently attracted much interest due to their wide range of applications ranging from nanomedicine such as affinity separations, enzyme recovery and drug delivery<sup>1,2</sup> to industrial applications including storage<sup>3</sup> and communication elements in optical devices<sup>4</sup>. The output of such a photoresponsive polymeric materials mainly depends on a complex interplay between the chromophore<sup>5</sup> (e.g. an azobenzene dye), the morphology of the polymeric network (amorphous, semicrystalline and liquid crystalline)<sup>3a</sup>, the thermomechanical properties of the material (glassy or rubbery state modulus), and the molecular geometry of the sample.<sup>6</sup> Thus, e.g. reversible solubility of azobenzene polymers<sup>7</sup> or reversible contractions of thin films<sup>8</sup> (see also e.g. the work of Eisenbach<sup>9</sup> and Blair<sup>10</sup>) have been

reported, stressing the importance of photochemically switchable polymers.

The photoresponsive properties of azobenzene-containing polymers are based on the photo-induced fast and reversible isomerization between *trans*- and *cis*-isomers of the azobenzene moiety upon exposure to UV or visible light, which can trigger significant changes in the physicochemical properties of the corresponding polymeric materials<sup>11,12,13</sup>. Similar to C=C double bonds, the azobenzenes display two geometric isomers (*cis* and *trans*) around the N=N double bond<sup>14</sup>, where the *trans* isomer is the more stable isomer. Isomerization to the *cis*-isomer is accomplished upon irradiation at a wavelength of ~320-350 nm. Due to the reversibility of this reaction, the *trans*-isomer can be easily recovered by irradiating the *cis*-isomer at a wavelength of 400-450 nm or via pure thermal relaxation<sup>14</sup>. These two photochemical reactions usually occur on picoseconds scales, while the thermal relaxation from *cis*- to *trans*-isomer is much slower (milliseconds to days).<sup>15,16,17</sup> It is important to mention that after the photo-isomerization process, characteristic changes in the physical properties of the two isomers affect the molecular geometry and the dipole moment of the dye.<sup>15,16</sup> Thus the attachment of

<sup>a</sup> Institute of Chemistry, Chair of Macromolecular Chemistry, Faculty of Natural Science II (Chemistry, Physics and Mathematics), Martin-Luther University Halle-Wittenberg, Halle (Saale) D-06120, Germany.

<sup>b</sup> Leibniz-Institute of Surface Modification, Permoserstrasse 15, Leipzig, Germany.

† Electronic supplementary information (ESI) available: Detailed NMR analysis of 4-azidobenzoic acid, 4-azidobenzoylchloride, PCL-alkyne3, cpd. 1, cpd. 2 and cpd. 3; H/H-COSY of polymer 1b; TGA curves; FTIR experiments and ESI-TOF MS of polymer-1.

polymeric chains onto the azobenzene in consequence leads to additional effects of the optoelectronic and relaxation properties of the dye,<sup>18,19</sup> often influenced by the value of the chemical linkage between the azo-dye and the polymer chain<sup>19</sup>. It has been demonstrated that the linkage between the azo chromophore and the polymer backbone can restrict both, the molecular mechanical properties and the motion of the azo-groups<sup>20</sup>: polymers linked via a rigid attachment to the azo chromophore can confine both, the chromophore's motion and its subsequent re-orientation, but also can induce an increased stability of the formed *cis*-isomer after the light has been turned off<sup>20</sup>. A large number of publications has been dealing with the influence of the polymeric chains on the physicochemical properties of the azo moiety<sup>21,22,23</sup>, such as an elongation of the *cis*-lifetime<sup>24,25</sup>. Lamarre and Sung<sup>25</sup> have studied the physical ageing and molecular motion of azochromophoric labels attached to the main chain poly(urethane)s, showing a lifetime of 4 days after switching to the *cis*-form. Furthermore, the conformational strain of macrocyclic azo compounds has also been used to lock the *cis* form for days<sup>24,26</sup>. Intermolecular interactions, such as hydrogen bonds to generate cyclic structures can also lead to largely increased lifetimes of the *cis*-form of up to ~40 days<sup>27</sup>.

Several synthetic strategies have so far been reported in obtaining azobenzene polymers either via the direct polymerization of a monovinyl azo monomer<sup>28,29</sup>, or via a postfunctionalization of a polymer onto an azo-dye<sup>3b,30</sup>. Based on this methodology both, side-chain<sup>31</sup> and main-chain<sup>32</sup> azobenzene polymers have been prepared, resulting in different architectures like block-<sup>32,33</sup>, brush-<sup>34,35</sup>, star-<sup>36</sup> and dendritic-<sup>37,38,39</sup> polymers. Besides a direct polymerization of suitable monomers, the subsequent attachment of azobenzenes onto polymer matrices<sup>40,41</sup> or the covalent attachment of polymers onto azobenzenes<sup>42,43</sup> has been reported. Despite the many reported methodologies, not always the expected polymers were obtained<sup>44,45,46</sup>, often due to some setbacks in their preparation and purification.

We hereby report an efficient strategy in preparing a series of azobenzene containing poly( $\epsilon$ -caprolactone)s by chemical modification of a commercially available azobenzene dye into poly( $\epsilon$ -caprolactone) backbone with different molecular weights

(see Fig. 1). The chemical separations and purification of the resulting azobenzene polymers are described in details.

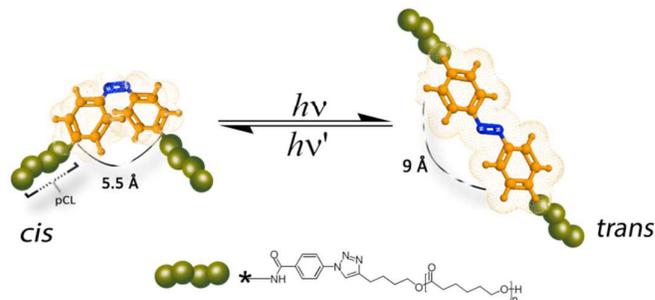


Figure 1: Isomerization of azobenzene polymers.

## EXPERIMENTAL

### Materials

All chemicals used for the synthesis were purchased from Sigma-Aldrich and CHEMOS chemicals.  $\epsilon$ -Caprolactone was stirred and distilled over calcium hydride (100 °C, 10 mbar). Tin(II)-2-ethylhexanoate and 5-hexyn-1-ol were also purified via the distillation procedures in the literature<sup>47,48</sup>. Cu(I)Br was stirred for 2 days in acetic acid/anhydride, washed with dry diethyl ether several times, and dried *in vacuo* under an argon atmosphere. *N,N*-Diisopropylethylamine (DIPEA), *N,N*-dicyclohexylcarbodiimide (DCC), *N,N*-dimethylamino-4-pyridine (DMAP) and 2,2'-bipyridine were used without further purification. Tetrahydrofuran (THF) was predried over sodium hydroxide (NaOH) for several days followed by heating over sodium/benzophenone and final distillation under an argon atmosphere before use.

### Measurements

**NMR spectroscopy** was recorded on a Varian Gemini 2000 FT-NMR spectrometer (400 MHz). Chloroform (99.8 atom % D) and dimethyl sulfoxide-d<sub>6</sub> (99.9 atom % D) were used as solvents, using Mestrec software version 4.7.0.0 for the FIDs analysis. Chemical shifts ( $\delta$ ) were recorded in parts per million (ppm) and referenced to residual protonated solvent (CDCl<sub>3</sub>: 7.26 ppm (<sup>1</sup>H), 77.0 ppm (<sup>13</sup>C), (CD<sub>3</sub>)<sub>2</sub>SO: 2.54 ppm (<sup>1</sup>H), 39.52 ppm (<sup>13</sup>C)); coupling constants (J) are given in

Hertz (Hz) using standard abbreviations (s = singlet, d = doublet, t = triplet, m = multiplet).

**GPC measurements** were conducted on a Viscotek GPCmax VE 2001 with a Styragel linear column GMHHR. THF was used as a carrier solvent at 1 mL/min at room temperature. The sample concentration was approximately 3 mg/mL. Poly(styrene) standards (in the range of 1050-1,870,000 g/mol) were used for conventional external calibration, using a Waters RI 3580 refractive index detector at 35 °C.

**FTIR spectra** were recorded with a Bruker Vertex70MIR spectrometer using an ATR Golden Gate unit with a diamond crystal. The scan number was 32 scans per spectrum with a resolution of 2 cm<sup>-1</sup>.

**MALDI-TOF-MS** was done on a Bruker Autoflex III Smartbeam using a nitrogen laser source ( $\lambda = 337$  nm) in reflection and linear modes. The polymer samples were dissolved in THF at a concentration of 20 mg/mL; 1,8,9-anthracenetriol in THF (20 mg/mL) was used as matrix material; sodium trifluoroacetate (NaTFA) in THF (20 mg/mL) was used as salt. The solutions of the polymer, the matrix, and the salt were mixed in a volume ratio of 100:20:2 and 2  $\mu$ L of this mixture were spotted on the MALDI target plate. The instrument was calibrated with a poly(ethylene glycol) standard ( $M_p = 2000$  g/mol) using a quadratic calibration method.

**ESI-TOF MS** measurements were carried out on a Bruker Daltonics microgel time-of-flight LC-MS system. Spectra were recorded in a positive mode with an accelerator voltage of 4.5 kV, a transfer line with 190 °C and a scan range of 50-7000 m/z at the spectral rate of 1 Hz. The spectra were processed on Bruker Daltonics ESI compass 1.3 for microTOF (Data Analysis 4.0). Samples were prepared by dissolving 1-5 mg of the respective compound in 1 ml mixture of THF/methanol (92/8).

**HPLC** measurements were performed on Elite LaChrom HPLC, Hitachi VWR, equipped with an autosampler, a quaternary gradient pump, a degasser, a diode array detector (UV-DAD) operating at 190 – 900 nm and a column oven with temperature control (temperature = 20 °C). Temperatures were maintained constant ( $\pm 0.2$  °C) throughout all experiments, and the injected sample

volume was 30  $\mu$ L. Liquid chromatography at critical conditions (LCCC) was carried out on a non polar reversed-phase Atlantis-RP C18 column, 100 Å, 5 $\mu$ m, dimension 4.6 $\times$ 250 mm; methanol/DCM = 8/92 was used as the mobile phase with a flow rate of 0.30 mL/min. The DAD signals were recorded on EZchrom Elite software version 3.3.2 SP2 with an operating wavelength from 190 to 900 nm at a sampling width of 200 ms to obtain sufficient data points across peaks.

#### Synthesis of alkyne-functionalized PCL (PCL-alkyne).

Alkyne-functionalized PCL was prepared via coordination insertion ring opening polymerization (ROP) using  $\epsilon$ -caprolactone as a monomer, 5-hexyn-1-ol as an initiator, and tin(II) 2-ethylhexanoate (Sn(Oct)<sub>2</sub>) as a catalyst according to the literature<sup>47</sup>. Briefly, a Schlenk flask was carefully dried by heating (500 °C), purged with argon, cooled down, charged with the initiator 5-hexyn-1-ol (55  $\mu$ L,  $5.0 \times 10^{-4}$  mol), adding the catalyst tin (II) 2-ethylhexanoate ( $6.0 \times 10^{-6}$  mol, 2  $\mu$ L), and a solvent mixture of 3 mL toluene and 1 mL THF. This mixture was stirred at room temperature for 30 min to promote the complex formation between catalyst and initiator. Afterward, the solution was treated with  $\epsilon$ -caprolactone (3 mL, 0.026 mol) and stirred at 110 °C for 3h. Finally, the product was dissolved in dry DCM (10mL) and precipitated into cold methanol (150 mL), filtered off and dried under vacuum overnight.

<sup>1</sup>H-NMR (400 MHz, CDCl<sub>3</sub>,  $\delta$ , ppm, PCL-alkyne3, DP = 29): 4.04 (t, 59H, J = 6.7 Hz), 3.63 (t, 2H, J = 6.5 Hz), 2.28 (t, 59H, J = 6.7 Hz), 1.94 (t, 1H, J = 2.6 Hz), 1.65 (m, 118H), 1.38 (m, 59H). <sup>13</sup>C-NMR (100 MHz, CDCl<sub>3</sub>,  $\delta$ , ppm, PCL-alkyne3): 173.4, 64.1, 34.1, 28.3, 25.5, 24.4.

#### Synthesis of 4-(azidobenzamido)-4'-(amino) azobenzene (2) and 4,4'-bis(benzamido) azobenzene (3)

To a solution of 4,4'-bis(amino)azobenzene (1) (1 mol eq.) and DIPEA (2.2 mol eq.) in THF at 0 °C was added 4-azidobenzoyl chloride (3 mol eq.) dissolved in THF. The mixture was stirred for 30 min, and finally warmed to room temperature with constant stirring

for 24 h. The obtained crude product was filtered and purified via column chromatography (DCM / ETOAc 3:1, Rf values: 4,4'-bis(benzamido) azobenzene = 0.82, 4-(azidobenzamido)-4'-(amino)azobenzene = 0.61).

Alternatively,<sup>49</sup> into a dried and nitrogen purged flask was added a solution of 4-azidobenzoic acid (2 mol eq.) and DCC (1 mol equiv.) in THF (5 ml). The mixture was stirred for 6 h at 0 °C to form bis-azidobenzoic anhydride. In a second dried round bottom flask a solution of 4,4'-bis(amino)azobenzene (1 mol equiv.) and DMAP (0.5 mol equiv.) in THF (5 ml) were added. The two solutions were then mixed and stirred at room temperature for 48 h. The obtained crude product was purified in a similar fashion as the previous method.

<sup>1</sup>H-NMR (400 MHz, DMSO,  $\delta$ , ppm, **2**): 10.42, (s, 1H), 8.04 (d, 2H, J = 8.03 Hz), 7.93 (d, 2H, J = 8.23 Hz), 7.76 (d, 2H, J = 8.30 Hz), 7.63 (d, 2H, J = 8.81 Hz), 7.28 (d, 2H, J = 8.02 Hz), 6.66 (d, 2H, J = 8.12 Hz), 6.00 (s, 2H). <sup>13</sup>C-NMR (100 MHz, DMSO,  $\delta$ , ppm, **2**): 165.0, 152.9, 148.8, 143.3, 140.8, 131.6, 130.2, 125.3, 122.8, 120.9, 119.5, 113.9.

<sup>1</sup>H-NMR (400 MHz, DMSO,  $\delta$ , ppm, **3**): 12.95, (s, 2H), 7.95 (d, 8H, J = 8.35 Hz), 7.20 (d, 4H, J = 8.48 Hz), 5.58 (d, 4H, J = 8.03 Hz). <sup>13</sup>C-NMR (100 MHz, DMSO,  $\delta$ , ppm, **3**): 207.0, 157.1, 131.6, 119.5.

IR (cm<sup>-1</sup>, **3**): 3385.8, 3074.8, 2989.9, 2811.2, 2703.9, 2407.8, 2119.8, 1649.9, 1601.9, 1420.5, 1345.1, 1313.2, 1180.0, 1129.4, 1098.1, 1067.9, 1037.7, 930.6, 851.2, 822.5, 773.8, 689.5, 570.5.

#### Synthesis of 4-(poly( $\epsilon$ -caprolactone)-benzamido)-4'-(amino)azobenzene (polymer-1a and polymer-1b) and 4,4'-bis(poly( $\epsilon$ -caprolactone)-benzamido)azobenzene (polymer-2a and polymer-2b)

The functionalization of PCL with 4-(azidobenzamido)-4'-(amino)azobenzene and 4,4'-bis(benzamido) azobenzene was conducted via an azide/alkyne click-reaction, using 2,2'-bipyridine as base and Cu(I)Br as a catalyst. The reaction was accomplished in a one-necked flask carefully dried and purged with argon. Alkyne-functionalized PCL (PCL-alkyne) (1 mol equiv) and azide-functionalized azobenzene dyes (4 mol equiv.) were dissolved in 6

mL of dry THF, then a solution of 2,2'-bipyridyl (20 mol equiv) in dry THF (2 mL) was added via a syringe and the mixture was degassed with argon for 30 min to remove oxygen. Subsequently, a catalytic amount of Cu(I)Br (1 mol equiv) was weighed into the flask. The flask was closed with a septum, and the mixture was degassed again with argon for another 30 min. The reaction proceeded for 24 h by stirring at 80 °C. Afterwards, the reaction mixture was cooled down to room temperature and the product was purified by chromatography via a silica gel packed column (ethyl acetate:DCM 1:3). The crude product was dissolved in 10 mL of DCM, slowly added into methanol (200 mL) and left overnight for complete precipitation. The precipitation step was repeated two more times to completely remove the excess of the azide-functionalized azobenzene dyes and the 2,2'-bipyridine, which are all well soluble in methanol. The pure products were filtered off and dried under vacuum for 3 days (yields: **1a** = 71 %, **1b** = 75 %, **2a** = 50 % and **2b** = 58 %)

<sup>1</sup>H-NMR (400 MHz, DMSO,  $\delta$ , ppm, **polymer-1b**): 10.55, (s, 1H), 8.70, (s, 1H), 8.17 (d, 2H, J = 8.03 Hz), 8.07 (d, 2H, J = 8.23 Hz), 7.96 (d, 2H, J = 8.30 Hz), 7.77 (d, 2H, J = 8.81 Hz), 7.64 (d, 2H, J = 8.02 Hz), 6.66 (d, 2H, J = 8.12 Hz), 6.00 (s, 2H), 4.30 (t, 2H, J = 6.5 Hz), 3.98 (t, 65H, J = 6.7 Hz), 3.28 (t, 2H, J = 6.4 Hz), 2.74 (t, 2H, J = 6.1 Hz), 2.24 (t, 65H, J = 6.7 Hz), 1.54 (m, 130H), 1.28 (m, 65H).

<sup>1</sup>H-NMR (400 MHz, DMSO,  $\delta$ , ppm, **polymer-2b**): 8.58, (s, 4H), 8.08 (m, 8H), 7.85 (m, 8H), 4.32 (t, 4H, J = 6.0 Hz), 3.94 (t, 238H, J = 5.9 Hz), 3.31 (m, 4H), 2.72 (m, 4H), 2.24 (t, 238H, J = 6.7 Hz), 1.54 (m, 476H), 1.28 (m, 238H).


IR (cm<sup>-1</sup>, **2b**): 3475.6, 2945.9, 2866.1, 2439.6, 1802.6, 1727.9, 1646.4, 1451.1, 1344.6, 1315.4, 1185.5, 1108.6, 1044.1, 963.1, 812.9, 741.7.

## RESULTS AND DISCUSSION

### Synthesis of photoswitchable PCL-azobenzene polymers

Conceptually, we planned to address possible synthetic strategies for obtaining switchable mono-functional polymers (**polymer-1**) and bi-functional polymers (**polymer-2**) via a grafting-to approach by

“click-chemistry” (see Scheme 1). For this purpose, polymerization of  $\epsilon$ -caprolactone using a coordination insertion ring opening polymerization<sup>47</sup> method was carried out as described in the experimental section. Subsequently, the polymers were attached to azido functionalized azobenzene dyes via the azide/alkyne “click” reaction<sup>50,51</sup>. The developed synthetic route is presented in Scheme 1. The first step for the synthesis of the photoswitchable polymeric compounds was an amidation reaction between a commercially available azobenzene dye (**1**) and 4-azidobenzoylchloride in the presence of a base (DIPEA) to yield a mono-substituted 4-(azidobenzamido)-4'-(amino)azobenzene (**2**) and a di-substituted 4,4'-bis(benzamido) azobenzene (**3**). Click-chemistry between the dyes (**2** and **3**) and an already synthesized **PCL-alkyne** (Table 1) with varying molecular weights (1000 g/mol and 3000 g/mol) were performed in THF to yield the products (**polymer-1a**, **polymer-1b**, **polymer-2a** and **polymer-2b**) respectively. After several purification techniques including column chromatography, precipitation, extraction, the final purified products were characterized using HPLC, ESI-TOF-MS, MALDI-TOF-MS, IR, <sup>1</sup>H-NMR <sup>1</sup>H-<sup>1</sup>H-COSY NMR and GPC techniques.

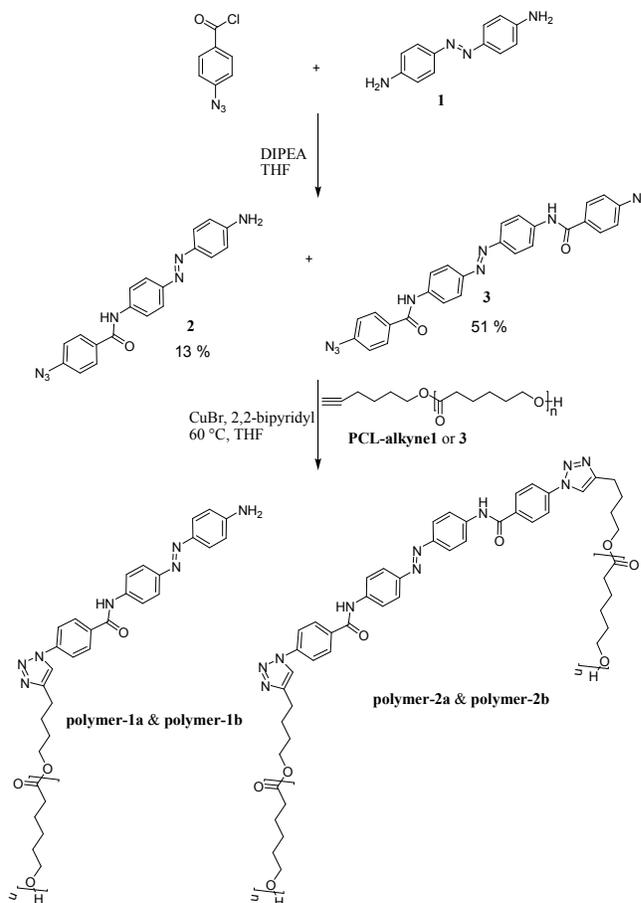

Scheme 1. Synthetic approach for the modified azobenzenes (**2** and **3**) and the polymer incorporated azobenzenes (**polymer-1** and **polymer-2**).

Table 1. Results of the synthesis of PCL-alkynes and the PCL-functionalized azobenzenes.


Samples	$M_n$ (NMR) (g/mol)	DP <sup>a</sup> (NMR)	$M_n$ (GPC) <sup>b</sup> (g/mol)	$M_w/M_n$ (GPC)	Yield <sup>c</sup> (%)
PCL-alkyne1	1111	9	985	1.2	95
PCL-alkyne3	3306	29	2900	1.1	98
polymer-1a	1920	9	1700	1.4	71
polymer-1b	3800	29	3220	1.2	75
polymer-2a	2850	18	2500	1.4	50
polymer-2b	7200	58	7100	1.1	58

<sup>a</sup>Degree of polymerization obtained via NMR spectroscopy, <sup>b</sup>Corrected molecular weight from GPC (correction factor = 0.59), <sup>c</sup>Isolated yields after purification

### Characterization of the photoswitchable PCL-azobenzenes

The structures of all the photoswitchable PCL-azobenzenes were initially confirmed by GPC and  $^1\text{H-NMR}$ . The GPC curves were monomodal with molecular weight distributions of 1.2-1.4. Figure 2 shows the  $^1\text{H-NMR}$  spectra of the synthesized compounds including the photoswitchable PCL-azobenzenes. All compounds showed the expected resonances in the NMR spectroscopy. Importantly the molecular weights from GPC and NMR of the photoswitchable PCL-azobenzenes matched well, proving a complete endgroup transformation of the compounds (Table 1). The degree of the end functionalization was obtained by comparing the intensity of the

signal 'h' and signal 'j' for the case of the mono-armed photoswitchable **polymer-1** and the peaks 'd' and 'c' for the bi-armed photoswitchable **polymer-2**. The result showed the completeness of the 'click' chemistry. The structures were further confirmed by FTIR spectroscopy (supporting information), in which the vibration peaks of  $-\text{OH}$  and  $-\text{NH}-$  (the broad peak at around  $3475\text{ cm}^{-1}$ ) both shifted to higher wavenumbers compared to their starting precursors ( $< 3300\text{ cm}^{-1}$ ).

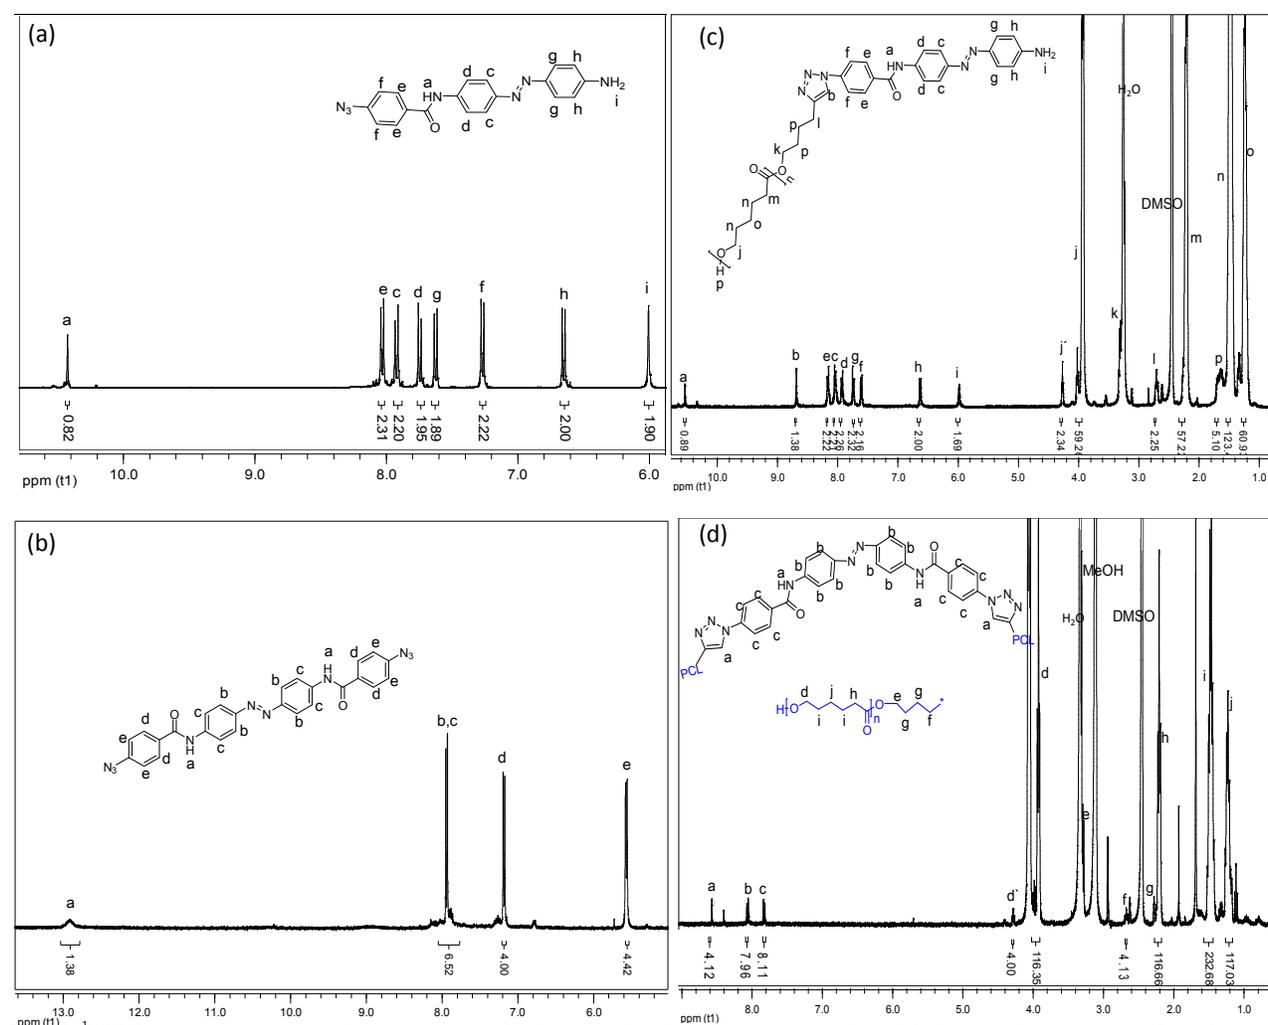

**Figure 2.**  $^1\text{H-NMR}$  spectra of all the synthesized compounds; a) 4-(azidobenzamido)-4'-(amino) azobenzene (**2**), b) 4,4'-bis(benzamido) azobenzene (**3**), c) 4-(poly( $\epsilon$ -caprolactone)-benzamido)-4'-(amino)azobenzene (**polymer-1b**), d) 4,4'-bis (poly ( $\epsilon$ -caprolactone)-benzamido)azobenzene (**polymer-2b**).

### Two-dimensional H/H COSY NMR analysis of the photoswitchable azobenzene polymers

Based on the complexity of the photoswitchable PCL-azobenzene polymers, we conducted 2D-NMR techniques, including  $^1\text{H}$ - $^1\text{H}$  COSY NMR. Figure 3 shows the proton homonuclear correlated 2-dimensional  $^1\text{H}$ - $^1\text{H}$  COSY NMR of **polymer-1b**. The backbone azobenzene moiety of this photoswitchable polymer could be traced through its J-coupling<sup>52</sup>. In the H,H-COSY of **polymer-1b**, a long-range coupling by arrangement of protons are observed between the doublet at 7.77 ppm (2H,  $J=8.81$  Hz) and the doublet at 6.66 ppm (2H,  $J=8.12$  Hz). The upfield shifted benzylic doublet is assigned to the protons *ortho*- to the amide functionality (i.e., 2H, signal-e) whereas the low field *doublet* is assigned to the protons

*ortho*- to the amine group (i.e., 2H, signal-h). The aromatic benzylic protons are associated to their neighboring protons via a 1,3 bond with a strong J-coupling distance of about  $\sim 8.03$  Hz. Protons a, b and i are being separated by their neighboring protons via a weak 1,4 bonding interaction and therefore show a very weak coupling effect, thus, appearing as singlet in the spectrum. While the coupling behavior of the mono-armed **polymer-1** is well observable in the COSY spectrum, the bi-armed polymers (**polymer-2**) are significantly more difficult to resolve. The signals appear as multiplets instead of individual doublet structures (see Figure 2d and supplementary). The COSY correlations helped to precisely assign the protons of the compounds observed in the 1-dimensional  $^1\text{H}$ -NMR especially in the mono-armed polymers and to further confirm the obtained structures.

Journal Name

ARTICLE


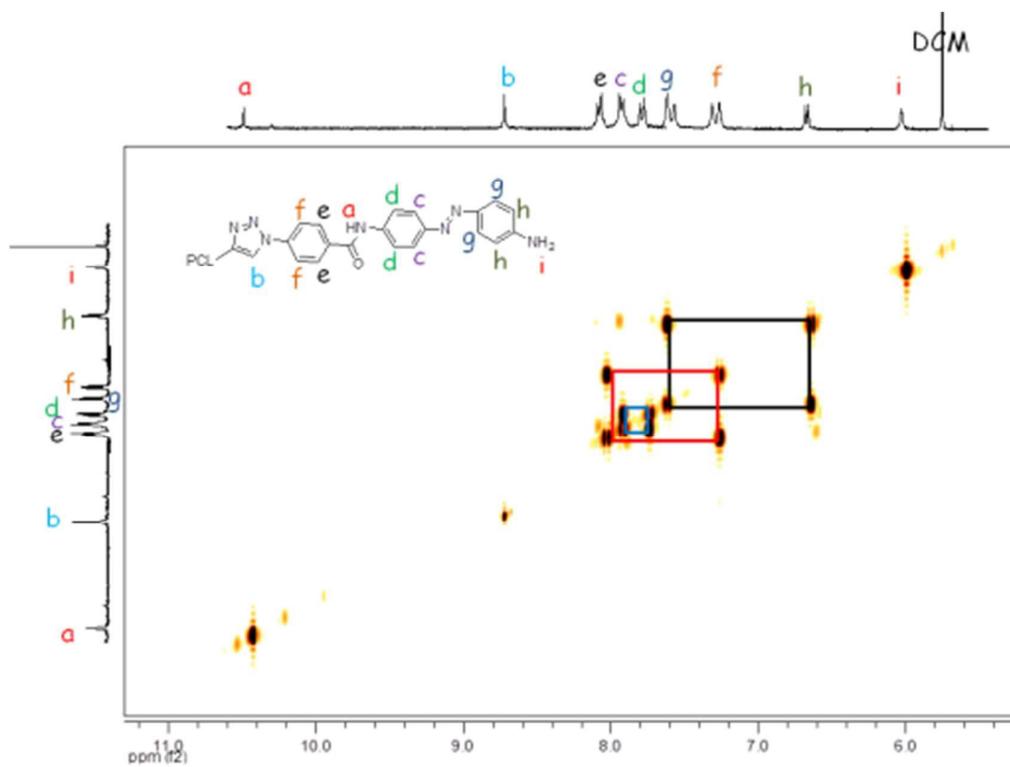



Figure 3. Expanded proton homonuclear correlated 2-dimensional <sup>1</sup>H-<sup>1</sup>H COSY NMR of polymer-1b

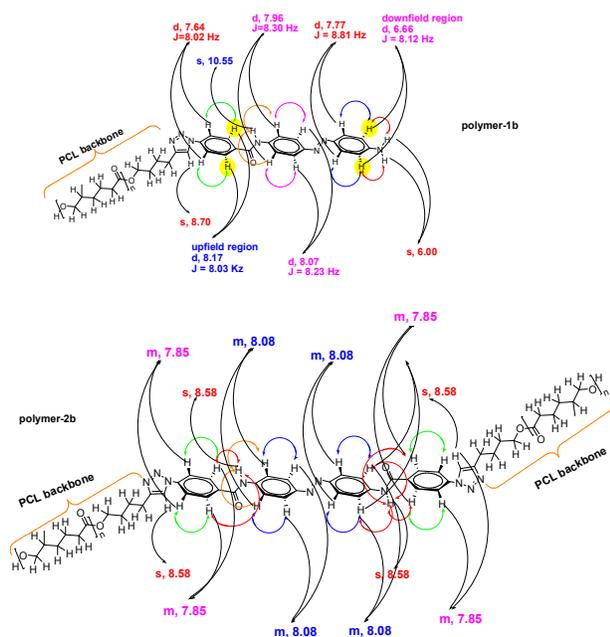

**Figure 4:** Main 2D-H/H-COSY correlations of polymer-1b and polymer-2b. The colored double headed arrows represent the long and short range couplings of protons from the H,H-COSY analysis, with the red ones showing the weak 1,4 coupling interactions.

### MALDI-TOF MS and ESI-TOF MS analysis of the photoswitchable azobenzene polymers.

In order to prove the expected chemical composition of the photoswitchable polymers, a straight forward MALDI-TOF-MS analysis was conducted. Figure 5, depicts the MALDI-TOF spectra of the photoswitchable polymers. Three main series are observed for **polymer-1a**, while **polymer-2a** shows four series. Each series shows a difference of 114 units, corresponding to the PCL repeating unit and is observed to be PCL containing the photoswitchable azobenzene dye moiety with different ions attached. According to Figure 5 the signal appearing at 2161.9 g/mol can be simply assigned to a PCL containing the photoswitchable dye moiety with the chemical formula  $[C_{109}H_{165}N_7O_{30}Ag]^+$  (with  $n = 14$ ), while the signal at 2131.0 g/mol can be represented by  $[M+2K]^+$ . The signal at 2115.7 g/mol is also identified by the chemical formula  $[M+Na+K]^+$ .

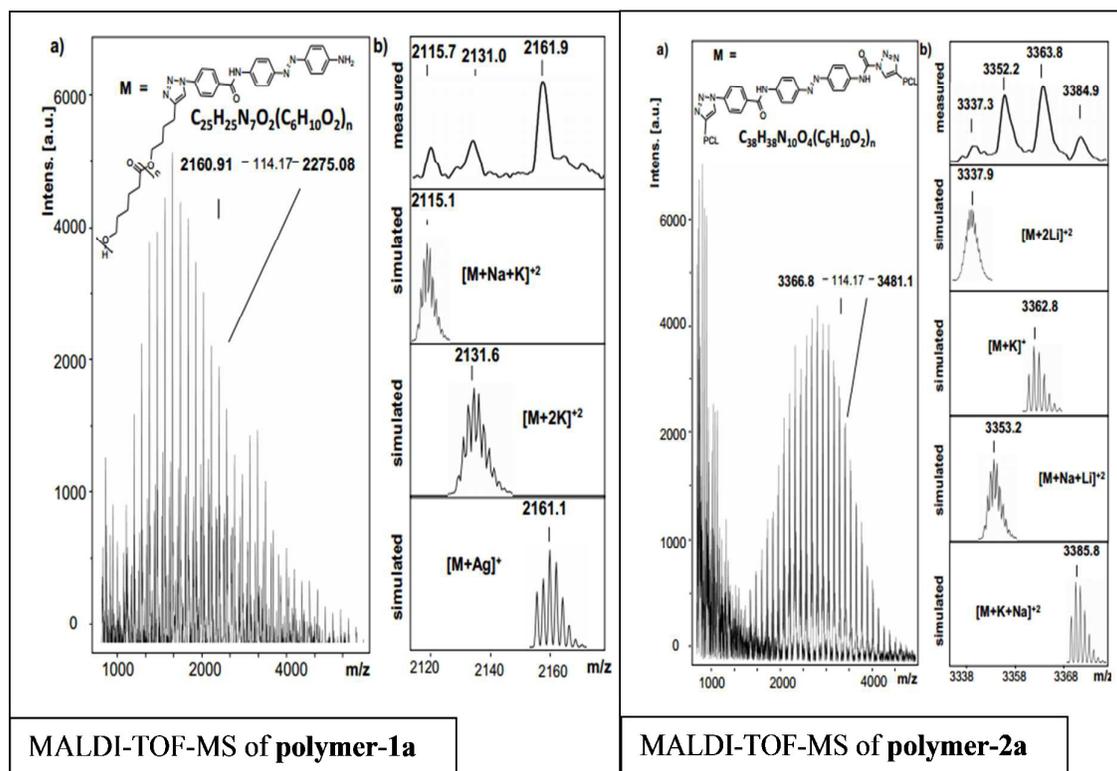


**Figure 5** (a) Full MALDI-TOF-MS spectrum of **polymer-1a** and **polymer-2a** and (b) measured and simulated patterns of different series observed.


However, to fully proof the structures being presented in scheme 1, we embarked on ESI-TOF MS investigations to further support the chemical composition of the two photoswitchable polymers. Figure 6 and Figure S12 (supplementary information) show detailed spectra of all the different series of **polymer-1a** and **polymer-2a**. Whereas the monofunctional **polymer-1a** shows a single charged state, the bifunctional **polymer-2a** shows multiple charged states (+1, +2 and +3 ions). All the observed peaks were successfully simulated to match to the corresponding species. Thus e.g. the isotopic peaks of **polymer-2a** at m/z value of 723.37 g/mol correspond to fragments generated during the analysis (see supplementary information for the fragmented structures). The

isotopic peak at m/z= 2036.20 g/mol with a charge state of +2 is observed to correspond to the species  $[M+H+CH_3OH]^+$ , while the molecular ions peak at m/z = 1283.75 g/mol is identified as the high charge state of +3, corresponding to the species  $[M+2Na+H]^+$ . The proof of an existence of a purely mono-armed polymer (**polymer-1**) and a bi-armed polymer (**polymer-2**) was evident from the presence of one detected 1,2,3-triazole group ( $C_2HN_3$ ) and two detected 1,2,3-triazole groups ( $2C_2HN_3$ ) for **polymer-1** and **polymer-2** respectively. From the measured and simulated pattern results, it was obvious that the ESI-TOF analysis truly confirmed the structures of the compounds being presented.

A) full ESI-TOF spectrum of polymer-2a, showing the various series

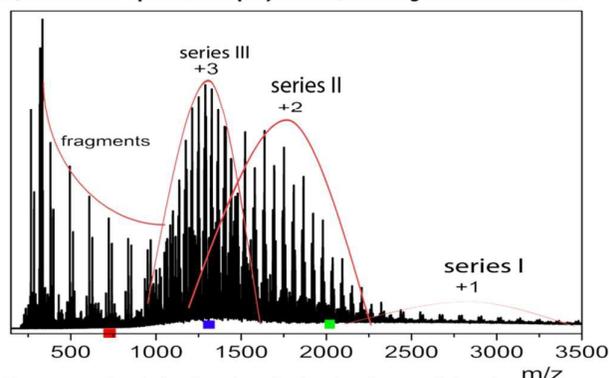

B) measured and simulated peaks for the observed signals

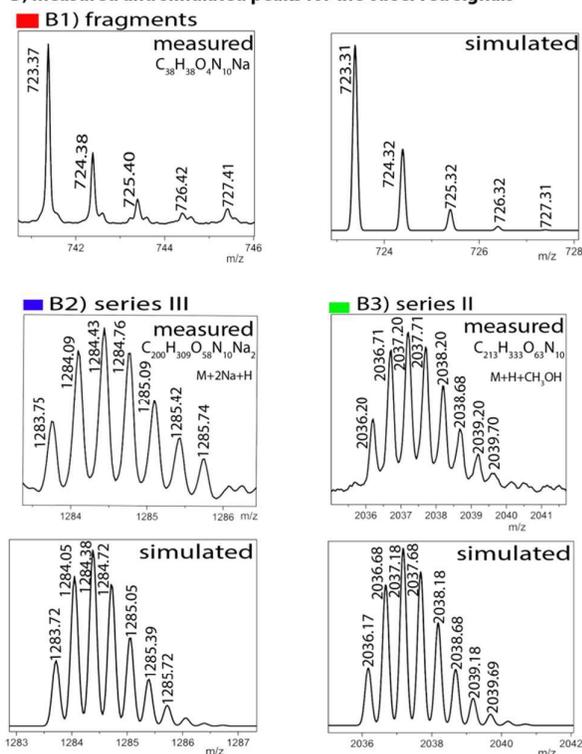

\*the distance between serial peaks suggested  $e^-$  CL units  
**series I:** similar structures as shown for series II and III

Figure 6. ESI-TOF MS spectra of the bifunctional photoswitchable polymer-2a, showing the observed and simulated signals.

### One-Dimensional Liquid Chromatography (SEC and HPLC) and UV-VIS investigations

#### SEC analysis

The photoswitchable polymers as well as the alkyne-functionalized PCL samples were examined using conventional size exclusion

chromatography (calibrated against PS standards) and HPLC analysis at LCCC conditions<sup>53</sup> (methanol:DCM = 8:92). Figure 7 shows the GPC traces of the photoswitchable polymers **-1b** and **-2b** as well as the alkyne-functionalized PCL precursors (**PCL-alkyne3**). The peak maximum of the polar sample **polymer-1b** shifted slightly towards higher retention time ( $R_t = 8.12$  min) compared to the retention time of **polymer-2b** ( $R_t = 7.74$  min). The symmetric monomodal distribution nature of the curves with different retention times, coupled to an exact match of the  $M_n$  values from NMR and GPC allowed the conclusion that the investigated samples were highly pure and were void of contaminants from their starting precursors.


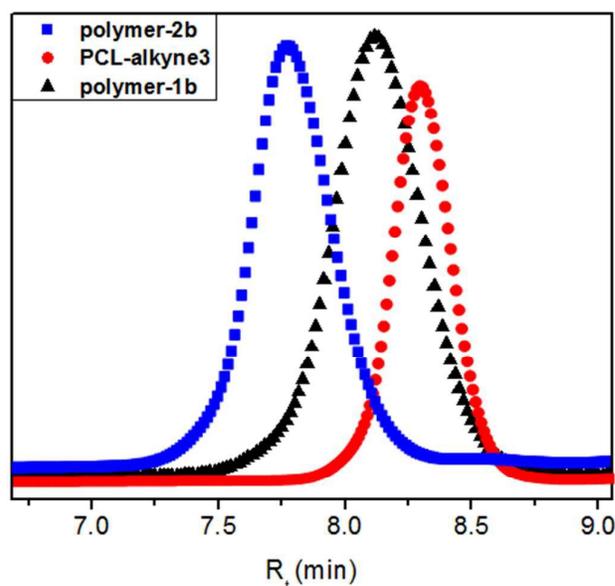


Figure 7. SEC traces of PCL-alkyne3, polymer-1b and polymer-2b.

#### HPLC analysis

Chromatographic techniques involving HPLC analysis at critical conditions<sup>53,54</sup> for the attached PCL-chains (methanol:DCM = 8:92, using non polar reverse phase Atlantis-RP C18 column) were furthermore conducted to confirm the purity of the obtained compounds, mainly to prove whether the structures presented in Scheme 1 were truly void of contaminants from their starting precursors and also not a mixture of the respective mono- and bi-substituted products. Figure 8 shows the HPLC separation chromatogram of **polymer-1b** and **-2b**, as well as their starting precursors (**2** and **3**). The elution peaks of both **polymer-1b** and


**polymer-2b** are well separated from each other. **Polymer-2b** elutes at a retention time of 10.2 min, 2.7 min higher than the retention time of **polymer-1b**. This difference is basically due to the PCL-unit being attached to the both ends of **polymer-2b**. Thus, incorporation of the PCL group onto both ends of **polymer-2b** reduces its polarity and hence leads to increased interaction within the Atlantis column, thereby resulting in higher retention times. The elution times of the polymers with similar functionalities (e.g. **polymer-2a** and **-2b**) were nearly the same, proving the LCCC conditions at these experiments.

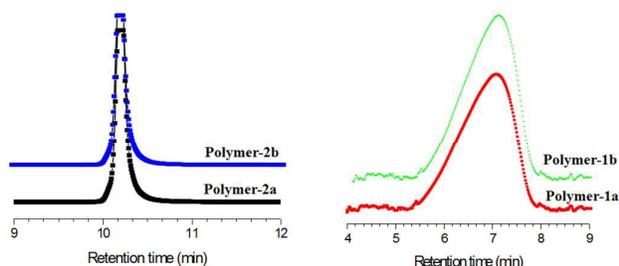

**Figure 8.** LC-UV traces analysis of the purified PCL-azobenzene polymers at LCCC conditions.

#### LC/ESI-TOF MS analysis

Gradient elution profile technique was also developed to characterize the azobenzene polymers (Figure 9). This technique involves the coupling of a liquid chromatography (LC) at LCCC conditions to an ESI-TOF MS source<sup>53,54</sup>. Thus the LC method separates the polymers based on their functionality at a specific retention time. The separated polymers subsequently enters directly into the ESI-TOF MS source for detailed structure elucidation: if mixtures with the polymers should be present (thus, e.g. possible contaminants in the case of our investigated samples or mixtures of bi-armed and mono-armed samples and azobenzene compounds **1**, **2** and **3**), then different peaks from the LC chromatogram should result, leading to a mixture of different structures in the ESI-TOF MS spectrum and thus a more complex spectrum. However, in the case of e.g. **polymer-2a**, one observes a single LC chromatogram (Figure 9a) and the recorded ESI-TOF MS spectrum (Figure 9b), demonstrating a functionality distribution of the polymer with repeating units of 114 g/mol, 57 g/mol and 38 g/mol assigned to a singly, doubly and triply charged desorbed ion states respectively. In all peaks of the ESI-TOF only one species, indicative of the bifunctional structure of **polymer-2a** could be detected.

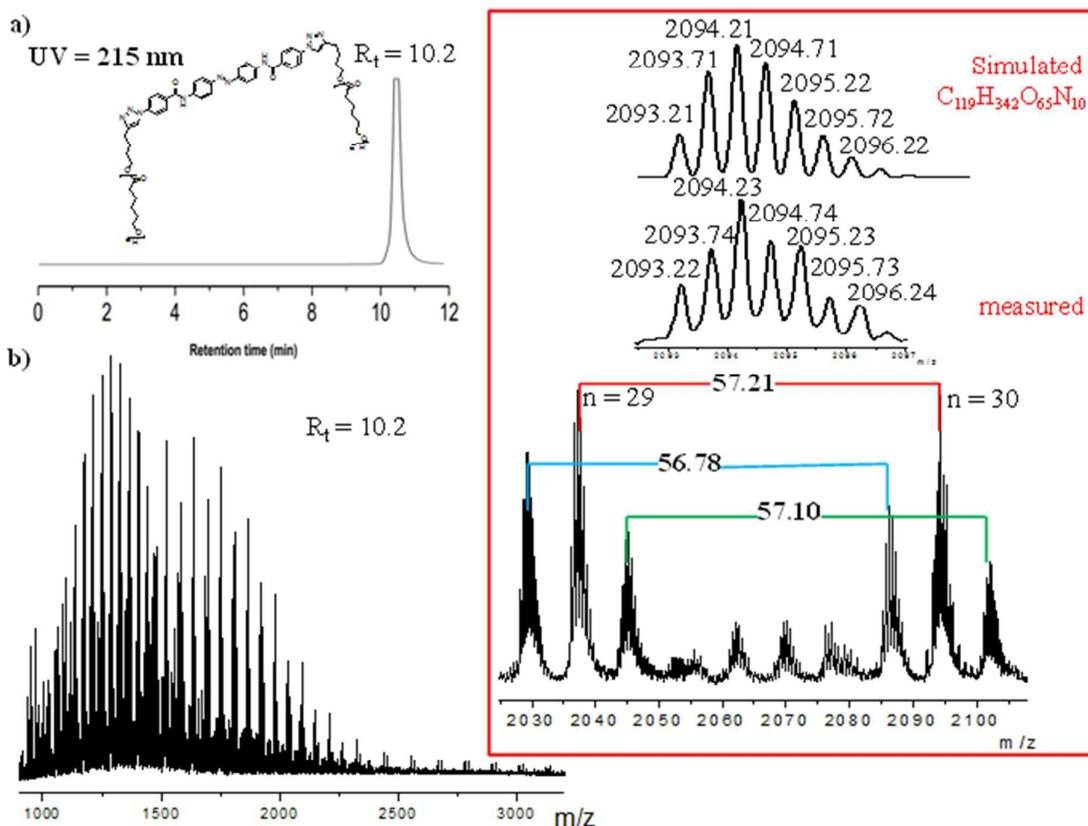


**Figure 9.** (a) LC-ESI-TOF-MS of **polymer-2a** indicating the purity of the sample. (b) Comparison between the measured and simulated isotopic pattern of a doubly charged species ( $R_t = 10.2$  min) proving the final structure.

### Multidimensional chromatography (2D-LC/SEC) of the photoswitchable polymers.

2D LC/SEC experiments were also conducted on the azobenzene polymers (see Figure 10) with different molecular weights and end group functionalities. Figure 10b shows the experiments on **polymer-1a** and **-1b**, having similar end group functionalities but different molecular weights. Thus on the LC-trace one observes nearly equal elution volume for the two polymers at  $\sim 0.97$  mL retention volume. This shows the experiments are under LCCC conditions and the retention times of the polymers at this point are independent on the molecular masses. Thus changes in the

functionalities of the compounds should be the only means to result in a noticeable shift in the 2D contour diagram. Hence a comparison between **polymer-1** and **-2** having different endgroup functionalities should result in a significant change in the retention times. Figure 10a shows a comparison of **polymer-1a** and **-2a** having different endgroup functionalities. The experiments unveiled a complete separation of the two photoswitchable polymers based on their functionality type distributions. Thus, as **polymer-1a** elutes at retention volume of 0.97 mL, **polymer-2a** elutes at 1.43 mL retention volume, which clearly indicates that the two polymers were different in terms of their functionalities and also proves the

structures presented in scheme 1 to be pure and void of contaminants from each other.

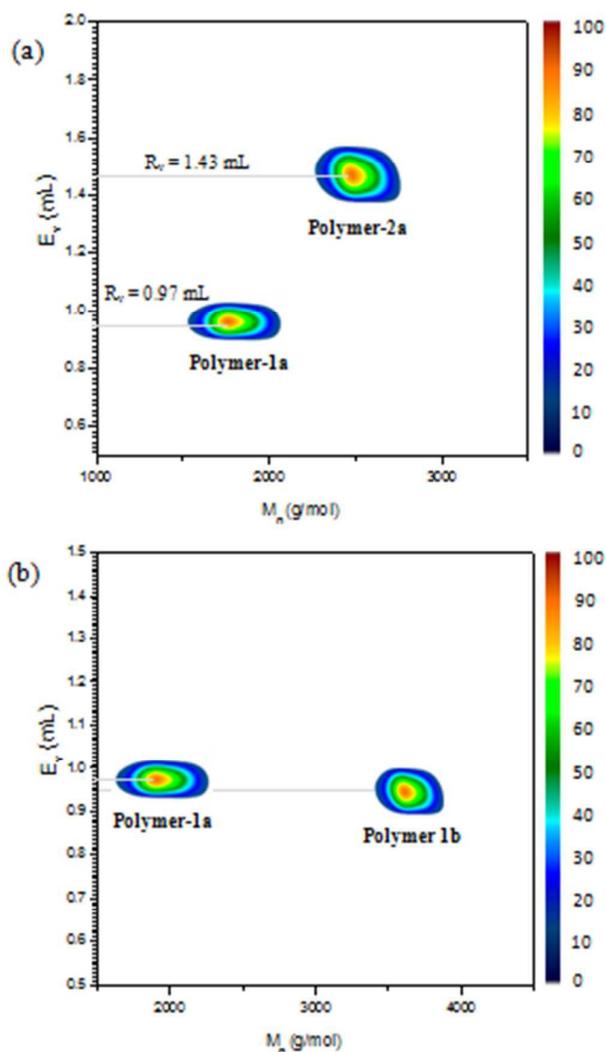

**Figure 10.** 2D LC/SEC plots of a) **polymer-1a** and **polymer-2a** showing separation based on their functionalities and b) **polymer-1a** and **polymer-2a** with similar endgroup functionalities showing a no noticeable changes in their LC-retention volumes, but a significant difference in their molecular weight in SEC.

## CONCLUSION

We here report a simple and efficient synthesis to obtain mono- and bi-armed azobenzene-containing polymers using “click” chemistry. The mono- and bi-armed PCL-azobenzene polymers were synthesized using the copper catalyzed azide-alkyne Huisgen cycloaddition reactions, attaching different molecular weights, ranging from 1000 g/mol to 7000 g/mol, onto the azobenzene-

backbone. The structure of the mono- and bi-armed polymers was proven via chromatographic techniques (HPLC under LCCC-conditions, LC/ESI-TOF MS) as well as 2D H/H COSY NMR experiments, also proving the purity of all of the samples and the excellent separation of the mono-armed polymers (**polymer 1**) from the bi-armed polymers (**polymer 2**). The investigated samples showed a significant thermal stability, when compared to their starting PCL-alkyne precursors.

## ACKNOWLEDGMENTS

The authors express thanks for Grant SFB TRR 102 (CA, WHB) (Project A03) for financial support.

## REFERENCES

- Jochum, F. D.; Theato, P. *Chem. Soc. Rev.* **2013**, *42*, 7468.
- Jochum, F. D.; zur Borg, L.; Roth, P. J.; Theato, P. *Macromolecules* **2009**, *42*, 7854.
- (a) García-Amorós, J.; Velasco, D. *Beilstein J. Org. Chem.* **2012**, *8*, 1003.  
(b) Fang, L.; Zhang, H.; Li, Z.; Zhang, Y.; Zhang, Y.; Zhang, H. *Macromolecules* **2013**, *46*, 7650.
- Moller, S.; Pliquet, U.; Hoffmann, C. *RSC Adv.* **2012**, *2*, 4792.
- Yu, H. J. *Mater. Chem. C* **2014**, *2*, 3047.
- Lee, B. K. M.; Koerner, H.; Wang, D. H.; Tan, L.-S.; White, T. J.; Vaia, R. A. *Macromolecules* **2012**, *45*, 7527.
- Irie, M.; Tanaka, H. *Macromolecules* **1983**, *16*, 210.
- Agolini, F.; Gay, F. P. *Macromolecules* **1970**, *3*, 349.
- Eisenbach, C. D. *Polymer* **1980**, *21*, 1175.
- Blair, H. S.; Pague, H. I.; Riordan, J. E. *Polymer* **1980**, *21*, 1195.
- Li, X.; Wen, R.; Zhang, Y.; Zhu, L.; Zhang, B.; Zhang, H. J. *Mater. Chem.* **2009**, *19*, 236.
- Weber, C.; Liebig, T.; Gensler, M.; Pithan, L.; Bommel, S.; Bléger, D.; Rabe, J. P.; Hecht, S.; Kowarik, S. *Macromolecules* **2015**, *48*, 1531.
- Yager, K. G.; Barrett, C. J. *J. Photochem. Photobiol. A: Chem.* **2006**, *182*, 250.
- (a) Stuart, C. M.; Frontiera, R. R.; Mathies, R. A. *J. Phys. Chem. A* **2007**, *111*, 12072.  
(b) Fanghänel, D.; Timpe, G.; Orthman, V. In *Organic Photochromes*; El'tsov, A. V., Ed.; Consultants Bureau: New York, **1990**; chap. 3.
- Yager, K. G.; Barrett, C. J. *RSC* **2008**, 424.
- Cembran, A.; Bernardi, F.; Garavelli, M.; Gagliardi, L.; Orlandi, G. *J. Am. Chem. Soc.* **2004**, *126*, 3234.
- Crecca, C. R.; Roitberg, A. E. *J. Phys. Chem. A* **2006**, *110*, 8188.
- Barrett, C.; Natansohn, A.; Rochon, P. *Chem. Mater.* **1995**, *7*, 899.
- Kumar, G. S.; Neckers, D. C. *Chem. Rev.* **1989**, *89*, 1915.
- Meng, X.; Natansohn, A.; Rochon, P. *J. Polym. Sci. Part B: Polym. Phys.* **1996**, *34*, 1461.
- Kim, H.-K.; Wang, X.-S.; Fujita, Y.; Sudo, A.; Nishida, H.; Fujii, M.; Endo, T. *Macromol. Rapid Comm.* **2005**, *26*, 1032.
- Lambeth, R. H.; Moore, J. S. *Macromolecules* **2007**, *40*, 1838.
- Lomadze, N.; Kopyshv, A.; Rühle, J.; Santer, S. *Macromolecules* **2011**, *44*, 7372.

- 24 Norikane, Y.; Kitamoto, K.; Tamaoki, N. *J. Org. Chem.* **2003**, *68*, 8291.
- 25 Lamarre, L.; Sung, C. S. P. *Macromolecules* **1983**, *16*, 1729.
- 26 Nagamani, S. A.; Norikane, Y.; Tamaoki, N. *J. Org. Chem.* **2005**, *70*, 9304.
- 27 Vollmer, M. S.; Clark, T. D.; Steinem, C.; Ghadiri, M. R. *Angew. Chem. Int. Ed. Engl.* **1999**, *38*, 1598.
- 28 Ho, M. S.; Barrett, C.; Paterson, J.; Esteghamatian, M.; Natansohn, A.; Rochon, P. *Macromolecules* **1996**, *29*, 4613.
- 29 Natansohn, A.; Rochon, P.; Pezolet, M.; Audet, P.; Brown, D.; To, S. *Macromolecules* **1994**, *27*, 2580.
- 30 Wang, X.; Balasubramanian, S.; Kumar, J.; Tripathy, S. K.; Li, L. *Chem. Mater.* **1998**, *10*, 1546.
- 31 Gallot, B.; Fafiotte, M.; Fissi, A.; Pieroni, O. *Macromol. Rapid Comm.* **1996**, *17*, 493.
- 32 Viswanathan, N. K.; Yu Kim, D.; Bian, S.; Williams, J.; Liu, W.; Li, L.; Samuelson, L.; Kumar, J.; K. Tripathy, S. *J. Mater. Chem.* **1999**, *9*, 1941.
- 33 Meng, X.; Natansohn, A.; Barrett, C.; Rochon, P. *Macromolecules* **1996**, *29*, 946.
- 34 Sisido, M.; Ishikawa, Y.; Itoh, K.; Tazuke, S. *Macromolecules* **1991**, *24*, 3993.
- 35 Sisido, M.; Ishikawa, Y.; Harada, M.; Itoh, K. *Macromolecules* **1991**, *24*, 3999.
- 36 Campbell, V. E.; In, I.; McGee, D. J.; Woodward, N.; Caruso, A.; Gopalan, P. *Macromolecules* **2006**, *39*, 957.
- 37 Momotake, A.; Arai, T. *Polymer* **2004**, *45*, 5369.
- 38 del Barrio, J.; Oriol, L.; Alcalá, R.; Sánchez, C. *Macromolecules* **2009**, *42*, 5752.
- 39 Ma, H.; Liu, S.; Luo, J.; Suresh, S.; Liu, L.; Kang, S. H.; Haller, M.; Sassa, T.; Dalton, L. R.; Jen, A. K. Y. *Adv. Funct. Mater.* **2002**, *12*, 565.
- 40 Birabassov, R.; Landraud, N.; Galstyan, T. V.; Ritcey, A.; Bazuin, C. G.; Rahem, T. *Appl. Opt.* **1998**, *37*, 8264.
- 41 Lagugné Labarthe, F.; Buffeteau, T.; Sourisseau, C. *J. Phys. Chem. B* **1998**, *102*, 2654.
- 42 Shinkai, S.; Minami, T.; Kusano, Y.; Manabe, O. *J. Am. Chem. Soc.* **1983**, *105*, 1851.
- 43 Willner, I.; Rubin, S. *Angew. Chem. Int. Ed. Engl.* **1996**, *35*, 367.
- 44 Yu, X.; Luo, Y.; Deng, Y.; Yan, Q.; Zou, G.; Zhang, Q. *Eur. Polym. J.* **2008**, *44*, 881.
- 45 Xu, C.; Wu, B.; Becker, M. W.; Dalton, L. R.; Ranon, P. M.; Shi, Y.; Steier, W. H. *Chem. Mater.* **1993**, *5*, 1439.
- 46 Irie, M.; Schnabel, W. *Macromolecules* **1981**, *14*, 1246.
- 47 Ostas, E.; Schröter, K.; Beiner, M.; Yan, T.; Thurn-Albrecht, T.; Binder, W. H. *J. Polym. Sci. Part A: Polym. Chem.* **2011**, *49*, 3404.
- 48 Appiah, C.; Akbarzadeh, J.; Peterlik, H.; Binder, W. H. *Euro. Polym. J.* **2015**, *64*, 138.
- 49 Mespouille, L.; Vachaud, M.; Suriano, F.; Gerbaux, P.; Coulembier, O.; Dege'e, P.; Flammang, R.; Dubois, P. *Macromol. Rapid Commun.* **2007**, *28*, 2151.
- 50 Barqawi, H.; Binder, W. H. *J. Polym. Sci. Part A: Polym. Chem.* **2010**, *48*, 4855.
- 51 Stojanovic, A.; Appiah, C.; Dohler, D.; Akbarzadeh, J.; Zare, P.; Peterlik, H.; Binder, W. H. *J. Mater. Chem. A* **2013**, *1*, 12159.
- 52 Baptiste, B. t.; Douat-Casassus, C. l.; Laxmi-Reddy, K.; Godde, F. d. r.; Huc, I. *J. Org. Chem.* **2010**, *75*, 7175.
- 53 Barqawi, H.; Ostas, E.; Liu, B.; Carpentier, J.-F.; Binder, W. H. *Macromolecules* **2012**, *45*, 9779.
- 54 Barqawi, H.; Schulz, M.; Olubummo, A.; Saurland, V.; Binder, W. H. *Macromolecules* **2013**, *46*, 7638.

TOC

