

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Improved adsorption properties of granulated copper hexacyanoferrate with multi-scale porous networks

Received 00th January 20xx,
Accepted 00th January 20xx

Kyoung-Moo Lee^a, Tohru Kawamoto^a, Kimitaka Minami^a, Akira Takahashi^a, Durga Parajuli^a,
Gentoku Kido^b, Kazunori Yoshino^b and Hisashi Tanaka^a

DOI: 10.1039/x0xx00000x

www.rsc.org/

Designed porous copper hexacyanoferrate micro-capsule beads (CuHCF-MCB) were prepared using freeze-drying (FD). Multi-scale porous networks composed of Angstrom, nanometer, and micrometer sizes were obtained in the desired shapes using a simple drying process. They provide special benefits such as fast kinetics and high capacity. The Cs adsorption equilibrium and kinetics fit the pseudo-second-order kinetic model well. The adsorption rate of FD-CuHCF-MCB was improved to about 15 times higher than that of heat-drying process because of the highly multi-scale porous structure of FD-CuHCF-MCB, which facilitated solution flow and rapid ion-diffusion inside the MCB.

Porous coordinated polymers (PCPs) such as metal organic frameworks (MOFs) and Prussian blue analogues (PBAs) have attracted attention during the past two decades because of their potential applications for storage^{1,2}, separation^{3,4}, recovery^{5,6}, and catalysis⁷⁻⁹ in gas and liquid phases. Among the various PCP applications, they have been studied mainly as an adsorbent because of their particular properties.¹⁰⁻¹³ Success in adsorbents are related to the following specific attributes of these materials: (1) high surface area and large pore volume; (2) rapid sorption; (3) good selectivity; (4) environmental safety; and (5) high stability. This functionality of PCPs results from their high porosity, as shown in crystal structure of Fig. 1. In fact, PCPs have often been used in fine powder form (e.g. nanoparticles).¹⁴⁻¹⁸ However, materials of fine powders present shortcomings such as difficulty of handling and safety hazards resulting from inhaling nanoparticles. For easier and safer practical use of PCP fine powders, a form improvement such as granulation is absolutely necessary. Therefore, many researchers have reported

various materials immobilizing nanoparticles on filter matrixes with binders such as organic and inorganic polymers.¹⁹⁻²⁴ In such cases, because the binder often obstructs the liquid-gas flow path and covers the adsorbent surface, the adsorption rate tends to be lower because of lower accessibility or contact probability between the adsorbent and adsorbed substance (gas or liquid, etc.). Therefore, for improvement of the sorption rate, tuning of the porous structure including the matrix is important to raise permeability.²⁵⁻²⁸

The IUPAC defines porosity size as presented in Fig. 1 and as follows: microporous means smaller than 2 nm diameter, mesoporous is 2–50 nm diameter, and macroporous is larger than 50 nm.²⁹ The micropore size determines the PCP basic functions. The mesopores and macropores formed by the agglomerated secondary particles and the matrix binder supporting PCPs are important for the liquid-gas flow path. For adsorbent use in water, the minimum necessary pore size is larger than sub-micrometer size at atmospheric pressure.³⁰⁻³²

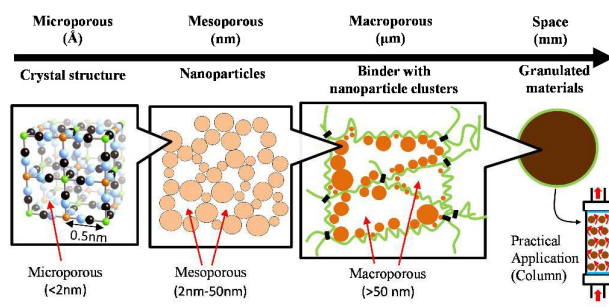


Fig. 1 Schematic presentation of porous designed micro-capsule beads for practical application.

An organic polymer, metal alginate, has been used frequently as a supporting material on a matrix or as a matrix itself.^{33,34} Alginate and divalent or multivalent cations form ionotropic gels such as Ca^{2+} /alginate. One such fabrication, heat-air dried micro-capsule beads (MCBs) was reported³⁵ and the MCB of metal

^a Nanomaterials Research Institute (NMRI), National Institute of Advanced Industrial Science and Technology (AIST), 1-1-1 Higashi, Tsukuba, Ibaraki 305-8565, Japan Tel.: +81 298 61 4603; fax: +81 298 61 6288; E-mail: hisashi.tanaka@aist.go.jp

^b Central Research Laboratory, Technology & Development Division, Kanto Chemical Incorporated Company, 7-1, Inari 1-chome, Soka, Saitama 340-0003, Japan

Electronic Supplementary Information (ESI) available. See DOI: 10.1039/x0xx00000x

hexacyanoferrate (MHCF) became commercially available from Kanto Chemical Co. Inc.

After the Fukushima Daiichi Nuclear Plant accident in 2011, practical decontamination studies of radionuclides were conducted for various targets such as contaminated water, soil, plants, ash, and sewage sludge.^{36–39} Radioactive cesium is an especially harmful nuclear fission product because of its long half-life and large amounts released to the environment. Therefore, a good adsorbent material with high Cs selectivity has been requested, even from water, such as seawater, containing high alkali metal contents. One potential Cs adsorbent is copper hexacyanoferrate (CuHCF) because of its high Cs selectivity, high capacity, rapid sorption, good thermal and radiation stability, low cost, low toxicity, and chemical stability in a wide pH range.^{40–43} Additionally, the basic adsorption performance of the CuHCF was improved by nanoparticulation and surface modification method, as we reported previously.^{44,45} For the practical use of nanoparticle of CuHCF, such as a column packing adsorbent (Fig. 1), it is necessary to make it granulate. However, the granulation is often lowered the adsorption rate because of the slow diffusion rate of inner beads.

In this paper, our strategy for the improvement of adsorption rate is to tune the permeability of adsorbent by simple processes, that is, granulated by MCB method and dried using different processes of heat-drying (HD) and freeze-drying (FD). FD method has advantage to keep the original porous structures without degradation. We discussed the effects on the adsorption rate by desired multi-scale porous networks used to maintain the liquid–gas flow path.

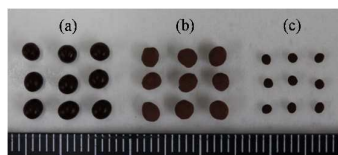


Fig. 2 Photograph of wet-MCB (a) and dried MCBs, both FD- (b) and HD- (c).

Insoluble CuHCF ($K_2Cu_3[Fe(CN)_6]_2$) slurry **1** was synthesized by mixing copper (II) sulfate pentahydrate ($CuSO_4 \cdot 5H_2O$) and potassium hexacyanoferrate (II) trihydrate ($K_4[Fe(CN)_6] \cdot 3H_2O$). For bead preparation, sodium alginate ($(NaC_6H_7O_6)_n$; Kanto Chemical Co. Inc.) and calcium chloride ($CaCl_2$; Wako Pure Chemical Industries Ltd.) were used. High-purity water produced using a Milli-Q integral water purification system was used for all experiment processes. The CuHCF dispersion solution (6.0 wt%) **2** was prepared by re-dispersing the CuHCF powder **3**, which was obtained by drying **1** with an evaporator, in Milli-Q water, with stirring by a homogenizer (T.K. Robomix; PRIMIX Corp., Japan) at 16,000 rpm for 10 min. The sol solution of CuHCF **4** was prepared by mixing 120 g of dispersion solution (6.0 wt%) **2** and 60 g of sodium alginate solution (3 wt%) (CuHCF : alginate = 8 : 2). After the CuHCF sol solution **4** was dropped into the 400 g of calcium chloride solution (2 wt%), gelation occurs immediately upon the contact of the alginate and Ca^{2+} , forming homogeneous spherical beads. The resulting beads were washed with 100 ml of Milli-Q water four times on a vacuum filter to remove residual ions until the conductivity of washing solution dropped below 0.4 mS/cm.

The wet CuHCF-MCB ($K_2Cu_3[Fe(CN)_6]_2 \cdot (Ca(C_6H_7O_6)_2)_x$) **5** (Fig. 2(a)) was dried using two methods. One commonly uses heat-drying (HD) process **6** drying in 60°C oven for 2 h. (Fig. 2(c)) The other is a freeze-drying (FD) process **7**: 20 g of **5** was quickly frozen by liquid nitrogen and vacuumed using a freeze dryer (FZ-Compact; Labconco Corp., USA) for more than 10 h (Fig. 2(b)). Hereafter the HD- and FD-CuHCF-MCB are abbreviated as HD- and FD-MCB, respectively.

Chemical compositions of CuHCF powder **3** and HD-MCB **6** were ascertained using MP-AES (4100 MP-AES; Agilent Technologies Inc., USA) with pre-decomposition using a microwave (MW, Multiwave 3000; PerkinElmer Corp., USA). The crystal structures of the alginate, CuHCF powder and MCBs were evaluated using XRD (D2 phazer; Bruker Analytik, Germany) using $Cu K\alpha$ ($\lambda = 1.54 \text{ \AA}$) radiation in the 2θ range of 10–70°. The crystal–particle size was evaluated using Scherrer's equation. General vibrational information was evaluated using FT-IR (Nicolet iS5; Thermo Scientific, USA) with pellets made from the mixed sample with KBr.

Cross-sectional images of MCBs were observed with a FE-SEM (S-4800; Hitachi Ltd., Japan). The SEM images were taken at 5 kV accelerating voltage after Pt coating (6.5 nm) using an ion sputter coater (E-1030; Hitachi Ltd., Japan). The porosity, pore size, and its distribution on MCBs were measured using mercury intrusion porosimetry (MIP, Autopore IV 9500; Micromeritics, USA) with the diameter range of 0.0065–423 μm . The pore size was calculated as a function of pressure using and equation of a report⁴⁶ of a study using parameter of Hg surface tension (0.485 N/m) and contact angle between Hg and the sample (140°).

For kinetic studies, each 37.5 mg (30 mg CuHCF included) of both MCBs was shaken in 30 mL solutions of different initial Cs^+ concentration (1 mg/L) at 25°C and 600 rpm frequency with intermittent movement for several setting times, 10, 20, and 30 min, and 1, 4, 8, and 24 h. Additionally, a shaking experiment for the equilibrium studies was done to achieve equilibrium for 72 h in the conditions described above. Each 37.5 mg of both MCBs were shaken in 30 mL of 200 mg/L $CsNO_3$ solution for 72 h. The concentration of residual Cs in the liquid phase was determined using an ICP-MS (NexION300D; PerkinElmer Inc., USA).

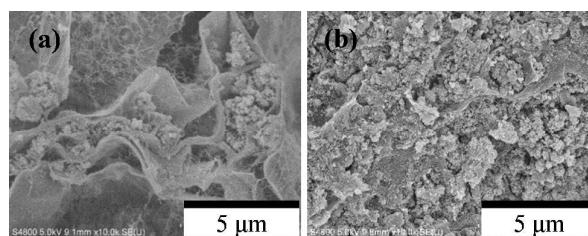


Fig. 3 Cross-sectional FE-SEM images of FD- (a) and HD- (b) MCB.

Chemical composition analysis revealed that the CuHCF powder **3**, HD-MCB **6**, and the FD-MCB **7** composition were identical to that of the HD one, and were determined respectively as $K_{2.18}Cu_{2.94}[Fe(CN)_6]_2$ and $K_{2.28}Cu_{3.04}[Fe(CN)_6]_2 \cdot 0.34Ca(C_6H_7O_6)_2$. The Cu/Fe and K/Fe ratios are 1.47 and 1.09 for CuHCF powder **3**, and 1.52, 1.14 for MCB **6**, respectively. No significant difference

was found between them except for the composition of calcium alginate. Details of results related to the XRD and FT-IR measurements are presented in Supplementary Information (SI). Examinations of FD- and HD-MCB using XRD and FT-IR revealed that few differences existed before and after granulation. Results confirmed that the mixing and granulate process with alginate or drying process of MCB does not affect the CuHCF characteristics or its nanoparticle size.

The FE-SEM images of the FD- and HD-MCBs are shown in Fig. 3. The macroporous size images differ greatly. Both MCBs have a structure of the small cells made from alginate polymer and the nanoparticle CuHCF supported on the cells. In images of HD-MCB (Fig. 3(b)), however, because the alginate cells are tightly folded and the CuHCF powders are compressed, little vacant space exists. In contrast, results from images in Fig. 3(a) confirmed that macroporous spaces exist in FD-MCB. Here the BET specific surface area (m^2/g) was measured by gas adsorption measurement (BELSORP-max, MicrotracBEL Corp., Japan) in order to confirm the space area in the MCBs, and it was calculated by N_2 adsorption isotherm at 77K. The value of FD-MCB and CuHCF powder were obtained to $67 \text{ m}^2/\text{g}$ and $300 \text{ m}^2/\text{g}$, respectively. On the other hand, the value of HD-MCB could not be obtained because of the quite slow equilibrium adsorption. To clarify the porous properties, MIP was used. It is widely used for characterizing pore volumes and sizes in porous solids.

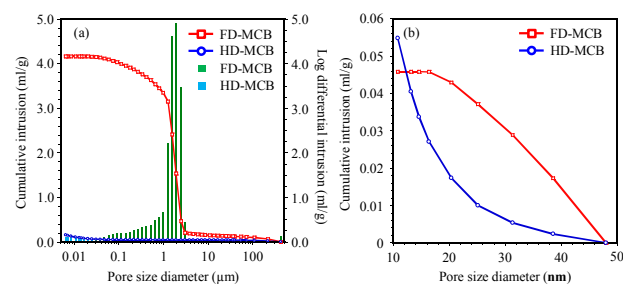


Fig. 4. Porous distribution of FD-MCB and HD-MCB. Cumulative (left Y axis) and log differential (right Y axis) intrusion volumes of whole range data (a) and 10–50 nm range (set the value to zero the 48 nm of X axis) (b).

In Fig. 4(a), the cumulative and log differential intrusion volumes by MIP are shown as a function of the pore size diameter.⁴³ A large distribution around 1–3 μm for FD-MCB is apparent from the log differential intrusion results, although only a small distribution was observed for HD-MCB. The micrometer-scale porous distribution was also confirmed from the FE-SEM images shown in Fig. 3. The total of cumulative intrusion volume in FD-MCB is almost 27 times larger than that of HD. Additionally, although the cumulative volume of mesopores of about 20–50 nm in the FD-MCB was higher than that of HD-MCB, the volume of HD-MCB increased rapidly below about 20 nm (Fig. 4(b)). According to the capillary size and pressure relation, the permeable pore size was calculated from the surface tension and contact angle of materials. For the Cs adsorption, water was used as a solvent. The water-permeable minimum pore radius was estimated as 1.437 μm . The water surface tension in atmospheric pressure is 72.88 mN/m (20°C). The wet state can be

expressed as $\theta = 0$, as described in SI Relationship between capillary pressure and pore size. According to the MIP result, the FD-MCB is suited to water treatment. However, mesopores smaller than 50 nm are permeable materials with low surface tension, such as CO_2 .

For this study, Cs adsorption experiments were conducted by shaking for 72 h with various Cs concentrations. The Cs maximum sorption capacity q_{max} (mg/g) of the MCBs was calculated using Langmuir model fitting.⁴⁷ The Langmuir model includes the assumptions that adsorption occurs at structurally homogeneous sites and that all sorption sites are energetically identical. The values of q_{max} are calculated from the slope and are tabulated. The values of q_{max} of FD-MCB and HD-MCBs respectively exhibit 172.4 and 169.5 mg/g (Fig. S2).

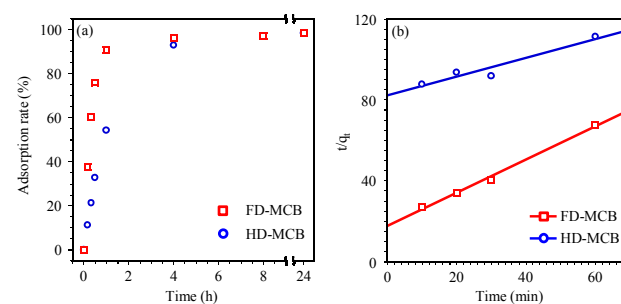


Fig. 5 Adsorption rate (%) (a) and the Pseudo-second-order kinetic model (b) for the Cs^+ ion sorption onto FD-MCB and HD-MCB.

For evaluation of the adsorption rate of the HD-MCB and FD-MCBs, Cs adsorption experiments were conducted by shaking for 24 h. Although both MCBs adsorb more than 98% of Cs ions after 24 h, obvious differences were found between the adsorption rate within 1 h, as presented in Fig. 5(a).

Kinetic models provide useful data to elucidate the sorption mechanism. Among the many models, pseudo-second-order models have often been used to calculate adsorbent kinetics.^{48,49} A pseudo-second-order kinetic model is presented and discussed for the adsorption rate using shaking test data for 24 h. Actually, K_2 and q_e can be determined from the t/q_t versus the t plot (Fig. 5(b)). The calculated pseudo-second-order model parameters are summarized respectively in Table 1 and SI. Application of the kinetic model to the adsorption of MCBs revealed that the values of K_2 by FD-MCB were improved about 15 times higher than those of HD-MCB. The results of these adsorption tests demonstrated that marked differences exist between the adsorption rates of HD- and FD-MCB. However, the maximum sorption capacity was not so influenced by the pore size distribution caused by dry processes.

Table 1 Parameters of pseudo-second-order kinetic models

	FD-MCB	HD-MCB
K_2 ($\text{g}/\text{mg}\cdot\text{min}$)	0.0382	0.0026
R^2	0.9938	0.9206

Considering the structures and adsorption properties, control of the micrometer-scale porosity is effective for improving Cs adsorption. The highly macroporous (micrometer-scale porous) structure of FD-MCB increases water permeability into the inside of

alginate cells and the contact changes between the Cs solution and CuHCF nanoparticles. Consequently, the pore size for water permeation requires approximately several-micrometer size. Considering FD-MCB results, the adsorption rate depends strongly on the pore size because the accessibility or contact probability of solution including Cs ions toward inner MCB is an important parameter. As described above, the mesopores also affect ion diffusion in the secondary particles, as presented in Fig. 1. Considering these results, mesopores are apparently necessary for gas phase applications.

In summary, multi-scale porous CuHCF-MCB with a high adsorption rate was prepared by freeze-drying. Applying pseudo-second kinetic models to the adsorption of Cs to the CuHCF-MCB, the K_2 of MCB by FD process were improved to about 15 times higher than that of HD process. The rational design and tune porosity of the textural materials by freeze drying are expected to contribute to the practical application of various PCP materials.

Notes and references

- C.P. Krap, J. Balmaseda, B. Zamora and E. Reguera, *Int. J. Hydrogen Energ.*, 2010, **35**, 10381.
- I. Spanopoulos, P. Xydias, C. D. Malliakas and P. N. Trikalitis, *Inorg. Chem.*, 2013, **52**, 855.
- J.-R. Li, R. J. Kuppler and H.-C. Zhou, *Chem. Soc. Rev.*, 2009, **38**, 1477.
- H. Mimura, M. Kimura, K. Akiba and Y. Onodera, *J. Nucl. Sci. Technol.*, 1999, **36**, 307.
- F. Cao, C. Zhang, Y. Xiao, H. Huang, W. Zhang, D. Liu, C. Zhong, Q. Yang, Z. Yang and X. Lu, *Ind. Eng. Chem. Res.*, 2012, **51**, 11274.
- N. Janssens, L. H. Wee, S. Bajpe, E. Breynaert, C. E. A. Kirschhock and J. A. Martens, *Chem. Sci.*, 2012, **3**, 1847.
- J.Y. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S.B. T. Nguyen and J. T. Hupp, *Chem. Soc. Rev.*, 2009, **38**, 1450.
- G. Selvarani, S.K. Prashant, A.K. Sahu, P. Sridhar, S. Pitchumani and A.K. Shukla, *J. Power Sources*, 2008, **178**, 86.
- M. Ranocchiari and J. A. Bokhoven, *Phys. Chem. Chem. Phys.*, 2011, **13**, 6388.
- B. Hu, B. Fugetsu, H. Yua and Y. Abe, *J. Hazard Mater.*, 2012, **217**, 85.
- A. K. Vipin, B. Hu and B. Fugetsu, *J. Hazard Mater.*, 2013, **258**, 93.
- S. Cavenati, C. A. Grande and A. E. Rodrigues, *Ind. Eng. Chem. Res.*, 2008, **47**, 6333.
- J.P. Marco-Lozar, J. Juan-Juan, F. Suarez-Garcia and D. Cazorla-Amoros, A. Linares-Solano, *Int. J. Hydrogen Energ.*, 2012, **37**, 2370.
- A. Ranft, S. B. Betzler, F. Haase and Bettina V. Lotsch, *Cryst. Eng. Comm.*, 2013, **15**, 9296.
- R. Chen, H. Tanaka, T. Kawamoto, M. Asai, C. Fukushima, M. Kurihara, M. Watanabe, M. Arisaka and T. Nankawa, *Electrochem. Commun.*, 2012, **25**, 23.
- L. He, Y. Liu, J. Liu, Y. Xiong, J. Zheng, Y. Liu and Z. Tang, *Angew. Chem. Int. Ed.*, 2013, **52**, 3741.
- T. A. R. J. Joseyphus, *J. Mater. Sci.*, 2014, **49**, 7014.
- L. D. O'Neill, H. Zhang and D. Bradshaw, *J. Mater. Chem.*, 2010, **20**, 5720.
- G. Chen, Y. Chang, X. Liu, T. Kawamoto, H. Tanaka, A. Kitajima, D. Parajuli, M. Takasaki, K. Yoshino, M. Chen, Y. Lo, Z. Lei and D. Lee, *Sep. Purif. Technol.*, 2015, **143**, 146.
- S. Aguado, J. Canivet and D. Farrusseng, *Chem. Commun.*, 2010, **46**, 7999.
- T. Yasutaka, T. Kawamoto, Y. Kawabe, T. Sato, M. Sato, Y. Suzuki, K. Nakamura and T. Komai, *J. Nucl. Sci. Technol.*, 2013, **50**, 674.
- C. Dwivedi, A. Kumar, J. K. Ajish, K. K. Singh, M. Kumar, P. K. Watal and P. N. Bajaj, *RSC Adv.*, 2012, **2**, 5557.
- C. Dwivedi, S. K. Pathak, M. Kumar, S. C. Tripathi and P. N. Bajaj, *RSC Adv.*, 2013, **3**, 22102.
- C. Dwivedi, S. K. Pathak, M. Kumar, S. C. Tripathi and P. N. Bajaj, *Environ. Sci. Water Res. Technol.*, 2015, **1**, 153.
- D. Wu, F. Xu, B. Sun, R. Fu, H. He, and K. Matyjaszewski, *Chem. Rev.*, 2012, **112**, 3959.
- F. M. Plieva and B. Mattiasson, *Ind. Eng. Chem. Res.* 2008, **47**, 4131.
- C. Delchet, A. Tokarev, X. Dumail, G. Toquer, Y. Barre, Y. Guari, C. Guerin, J. Larionova, and A. Grandjean, *RSC Advances*, 2012, **2**, 5707.
- T. Vincent, C. Vincent, Y. Barre, Y. Guari, G. L. Saoutd, and E. Guibal, *J. Mater. Chem. A*, 2014, **2**, 10007.
- J. Rouquerol, D. Avnir, C. W. Fairbridge, D. H. Everett, J. H. Haynes, N. Pernicone, J. D. F. Ramsay, K. S. W. Sing and K. K. Unger, *Pure Appl. Chem.*, 1994, **66**, 1739.
- M. H. A. Alnaief, Ph.D. Thesis, Hamburg University of Technology, 2011.
- M. Tong, L. Li, W. Wang and Y. Jiang, *Geophysics*, 2006, **71**, N33.
- F. Yang, F. F. Hingerl, X. Xiao, Y. Liu, Z. Wu, S. M. Benson and M. F. Toney, *Sci. Rep.*, 2015, **5**, 10635.
- T. Guo, Y. Hu, X. Gao, X. Ye, H. Liu and Z. Wu, *RSC Adv.*, 2014, **4**, 24067.
- T. Vincent, J.-M. Taulemesse, A. Dauvergne, T. Chanut, F. Testa and E. Guibal, *Carbohydr. Polym.*, 2014, **99**, 517.
- D. Parajuli, A. Takahashi, H. Noguchi, A. Kitajima, H. Tanaka, M. Takasaki, K. Yoshino, and T. Kawamoto, *Chem. Eng. J.*, 2016, **283**, 1322.
- A. Kitajima, H. Ogawa, T. Kobayashi, T. Kawasaki, Y. Kawatsu, T. Kawamoto and H. Tanaka, *Environ. Sci. Process. Impacts*, 2014, **16**, 28.
- D. Parajuli, A. Takahashi, H. Tanaka, M. Sato, S. Fukuda, R. Kamimura and T. Kawamoto, *J. Environ. Radioact.*, 2015, **140**, 78.
- I. Tsushima, M. Ogoshi, H. Yamashita and I. Harada, *J. J. Society Water Environ.*, 2013, **36**, 23.
- N. Kozai, S. Suzuki, N. Aoyagi, F. Sakamoto and T. Ohnuki, *Water Res.*, 2015, **68**, 616.
- A. Nilchi, R. Saberi, M. Moradi, H. Azizpour and R. Zarghami, *Chem. Eng. J.*, 2011, **172**, 572.
- J. Causse, A. Tokarev, J. Ravau, M. Moloney, Y. Barre and A. Grandjean, *J. Mater. Chem.*, 2014, **2**, 9461.
- R. Chen, H. Tanaka, T. Kawamoto, M. Asai, C. Fukushima, Haitao Na, M. Kurihara, M. Watanabe, M. Arisaka and T. Nankawa, *Electrochim. Acta.*, 2013, **87**, 119.
- R. Chen, M. Asai, C. Fukushima, M. Ishizaki, M. Kurihara, M. Arisaka, T. Nankawa, M. Watanabe, T. Kawamoto and H. Tanaka, *J. Radioanal. Nucl. Chem.*, 2015, **303**, 1491.
- A. Takahashi, N. Minami, H. Tanaka, K. Sue, K. Minami, D. Parajuli, K.-M. Lee, S. Ohkoshi, M. Kurihara, and T. Kawamoto, *Green Chem.*, 2015, **17**, 4228.
- K.-M. Lee, A. Takahashi, H. Tanaka, K. H. Kim, M. Kawamura, Y. Abe, M. Ishizaki, M. Kurihara, and T. Kawamoto, *Bull. Chem. Soc. Jpn.* 2015, **88**, 1561.
- E. Vennat, C. Bogicevic, J.-M. Fleureau, M. Degrange, *Dent. Mater.*, 2009, **25**, 729.
- C. Chen, *Open Chem. Eng. J.*, 2013, **7**, 24.
- S. Cataldo, G. Cavallaro, A. Gianguzza, G. Lazzara, A. Pettignano, D. Piazzese, I. Villaescusa, *J. Environ. Chem. Eng.*, 2013, **1**, 1252.
- A.E. Ofomaja, A. Pholosi, E.B. Naidoo, *Int. Biodeter. Biodegr.*, 2014, **92**, 71.

