

Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/chemicalscience

EDGE ARTICLE

A Single Crystalline Porphyrinic Titanium Metal–Organic Framework†

Cite this: DOI: 10.1039/x0xx00000x

Shuai Yuan^{a,‡}, Tian-Fu Liu^{a,‡}, Dawei Feng^a, Jian Tian^a, Kecheng Wang^a, Junsheng Qin^a, Qiang Zhang^a, Ying-Pin Chen^a, Mathieu Bosch^a, Lanfang Zou^a, Simon J. Teat^b, Scott J. Dalgarno^c and Hong-Cai Zhou^{*}

Received 00th January 201X,

Accepted 00th January 201X

DOI: 10.1039/x0xx00000x

www.rsc.org/

We successfully assembled the photocatalytic titanium–oxo cluster and photosensitizing porphyrinic linker into a metal–organic framework (MOF), namely PCN-22. A preformed titanium–oxo carboxylate cluster is adopted as the starting material to judiciously control the MOF growth process to afford single crystals. This synthetic method is useful to obtain highly crystalline titanium MOFs, which has been a daunting challenge in this field. Moreover, PCN-22 demonstrated permanent porosity and photocatalytic activities toward alcohol oxidation.

Introduction

Metal–organic frameworks (MOFs) are a promising class of highly ordered porous materials with potential applications in gas storage, catalysis, and photoelectric devices.^{1–8} For heterogeneous catalytic processes, the accessible external surface of the solid-state catalyst usually plays a decisive role on the catalytic efficiency.^{9, 10} MOFs provide a platform to synthesize new heterogeneous catalysis with highly accessible external and internal surface and evenly distributed active sites.¹¹ In addition, MOFs offer a bottom-up approach to tune their structures and functionalities by judicious design of inorganic building units and/or organic linkers.^{12–16} In previous studies, the functionalization of MOFs has mainly relied on the modification of organic linkers, whereas the functionalization of inorganic nodes has not been well explored thus far, except for utilization of open metal sites as Lewis acid for catalysis.^{17–22} The main reason for this is that catalytic processes involving labile coordinated metal centers can potentially compromise the structural integrity of the MOFs. Therefore, constructing a stable MOF with reactive metal nodes poses a great challenge. The development of titanium MOF MIL-125 represents an important breakthrough in the utilization of metal nodes as functional moieties.²³ The titanium–oxo clusters in MIL-125 not only form strong bonds with benzenedicarboxylate (BDC) linkers to afford a highly stable framework, but also endow the material with photocatalytic activity. Nevertheless, the BDC linker in MIL-125 did not contribute to the catalytic process. Efforts were made to

functionalize the BDC linker with amino groups acting as photosensitizers in MIL-125; however, the incorporation of efficient photosensitizers for visible-light-induced catalysis remains a challenge.^{24–26}

Porphyrin-sensitized TiO₂ has been widely investigated as a photocatalyst due to its high catalytic efficiency and chemical stability.^{27–31} This inspired us to mimic dye-sensitized TiO₂ in a MOF matrix. The titanium–oxo clusters can act as photoactive sites with the porphyrinic ligands acting as photosensitizers to extend the optical response of MOF into the visible region through a dye sensitized mechanism.³² In this way, the organic and inorganic components of MOF can work cooperatively, making it an integrated dye-sensitized photoactive system. By incorporating the porphyrin-sensitized TiO₂ system into a highly ordered porous material, the resulting porphyrinic titanium MOF has the following advantages: First, the titanium–oxo clusters can be periodically arranged and separated by organic linkers on the molecular level, leading to a much higher accessible surface compared to that of bulk TiO₂. Second, the visible light photo-responsiveness of the porphyrinic titanium MOF would be much more sensitive than that of MIL-125 and its derivatives because of the high efficiency of the porphyrin antenna. Meanwhile, the Ti⁴⁺ ion has a high Z/r value, which forms a strong electrostatic interaction with the carboxylate ligand, resulting in an ultra-stable framework. The exceptional stability and visible light photocatalytic activity should make porphyrinic titanium MOF a suitable platform for visible-light driven photocatalysis.

Despite all these merits, only two titanium MOFs (MIL-125 and NTU-9) have been reported previously.^{23, 33} The underdevelopment of titanium MOFs is due to the difficulty in achieving high crystallinity. To obtain single crystals, a reversible bond association /dissociation process is required to allow sufficient structure reorganization and defect repair. The strong Ti–O bond, however, makes the bond dissociation extremely difficult during MOF growth. Our previous work has demonstrated that the reversibility of the MOF crystallization process can be promoted by increasing the temperature,

^a Department of Chemistry, Texas A&M University, College Station, Texas 77842-3012, USA.

^b Advanced Light Source, Lawrence Berkeley National Laboratory Berkeley, CA 947240, USA.

^c Institute of Chemical Sciences, Heriot-Watt University Riccarton, Edinburgh EH14 4AS, U.K.

‡S.Y. and T.L. contributed equally to this work.

†Electronic Supplementary Information (ESI) available: See DOI: 10.1039/c000000x/

using metal clusters as precursors and carboxylic acids as competing reagents.³⁴ With the adoption of a preformed titanium–oxo carboxylate cluster as the metal source, TCPP (TCPP = tetrakis(4-carboxyphenyl)porphyrin) as the organic linker and benzoic acid as a modulating reagent, a single crystalline titanium MOF has been successfully obtained, designated as PCN-22 (PCN = porous coordination network). To the best of our knowledge, this is the first single crystalline titanium MOF based on carboxylate linkers.³⁵ This work is a breakthrough in the synthesis of highly crystalline titanium MOF, which would be conducive to the development of titanium MOF chemistry. Moreover, the single crystalline product provides an opportunity to thoroughly characterize the structure and understand the relationship between structure and properties, which will be instructive for future design and synthesis of functional titanium MOFs. Moreover, PCN-22 demonstrates an example of mimicking the porphyrin-sensitized TiO₂ in a porous MOF matrix. It shows photocatalytic activities toward alcohol oxidation with extensive optical response in the visible-light region, illustrating the synergetic effect of combining inorganic and organic components in a tailored framework.

Results and discussion

PCN-22 was prepared by the reaction of Ti₆O₆(OⁱPr)₆(abz)₆ (abz = 4-aminobenzoate),³⁶ TCPP and benzoic acid under solvothermal conditions. The preformed Ti₆O₆(OⁱPr)₆(abz)₆ cluster was used as a starting material instead of the titanium salt, which not only slows down the crystallization process but also effectively diminishes the hydrolysis of Ti⁴⁺ ions, avoiding the formation of TiO₂. Moreover, the air stable titanium–oxo carboxylate clusters were also easier to handle compared to titanium salts. When reactions were conducted with Ti(OⁱPr)₄ or TiCl₄ instead of titanium–oxo clusters under identical conditions, no crystalline products were obtained. At the same time, an excess amount of benzoic acid was added as a competing reagent,

which could further slow down the forward reaction during the MOF growth process, favoring the formation of crystalline products.

Single-crystal X-ray diffraction analyses revealed that PCN-22 crystallizes in the monoclinic *P2₁/m* space group. Three Ti atoms are jointed into a Ti₃O₃ cluster by a μ₃-O²⁻ ion and six carboxylates. A pair of Ti₃O₃ clusters is further bridged by a Ti atom to form an unprecedented Ti₇O₆ cluster (Figure 1b). Overall, the 12-connected Ti₇O₆ cluster is composed of seven Ti⁴⁺ ions, two μ₃-O²⁻ ions, two terminal O²⁻ ions, two terminal OH⁻ ions and two bridging DEF molecules. Each Ti₃O₃ subunit is connected with six TCPP linkers to construct a two dimensional layer. The adjacent 2D layers are further linked by bridging Ti atoms, forming a 3D framework. A tetragonal channel with a diameter of ~1.5 nm is observed in PCN-22. Topologically, each Ti₃O₃ can be regarded as a 6-connected node and a TCPP linker can be seen as a 4-connected node. The overall structure is simplified into a novel (4, 6) connected net with a point symbol of {4⁴.6²}₃{4⁹.6¹²}₂, which has never been reported to the best of our knowledge.

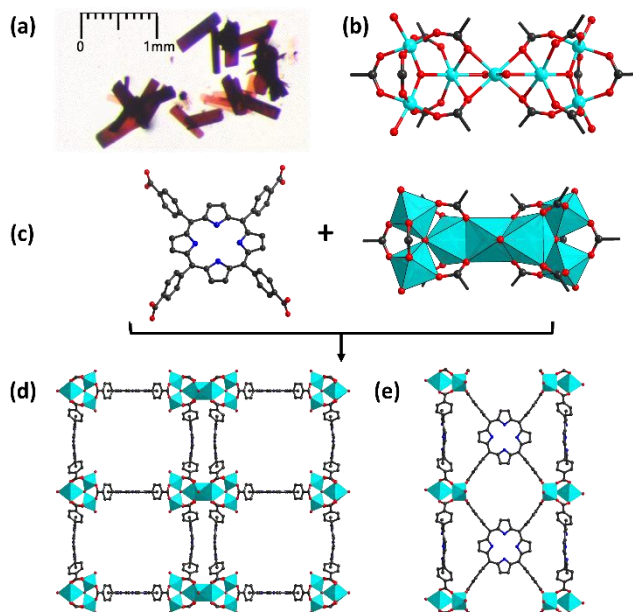


Figure 1. (a) Microscope image of PCN-22 crystals; (b) structure of the Ti₇O₆ cluster (only O atoms of DEF molecules are shown for clarity); (c) Representation of the tetratopic TCPP linker (left) and 12-connected Ti₇O₆ cluster (right); (d) views of the structure of PCN-22 along *a*-axis and (e) *b*-axis. Color scheme: red, O; black, C; blue, N; and cyan, Ti. H atoms are omitted for clarity.

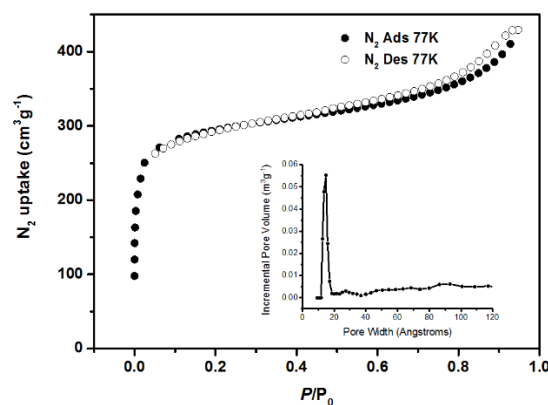


Figure 2. The N₂ adsorption isotherm of PCN-22 at 77 K, 1 atm. The inset shows DFT pore size distribution of PCN-22 using data measured with N₂ at 77 K.

The phase purity of PCN-22 was confirmed by comparison of the powder X-ray diffraction pattern and the simulated pattern from the crystal structure (Figure S5). The porosity of PCN-22 was examined by nitrogen sorption experiments at 77 K (Figure 2). A N₂ uptake of 430 cm³ g⁻¹ (STP) and a Brunauer-Emmett-Teller (BET) surface area of 1284 m² g⁻¹ were observed for PCN-22. Density Functional Theory (DFT) calculations from the N₂ sorption curve indicate that there is one type of pore with a diameter of 1.5 nm (Figure S6) assigned to the solvent accessible tetragonal channel, which is consistent with the crystallographic data when van der Waals radius is considered (Figure S8).

PCN-22 was obtained as dark red crystals (Figure 1a). The diffuse reflectance UV-vis spectrum of PCN-22 shows a broad range of absorption from 200 nm to 640 nm (Figure S10). The calculated band-gap of PCN-22 from the Tauc plot³⁷ is 1.93 eV, which is smaller than the reported Ti-based MOFs MIL-125 (3.6 eV) and MIL-125-NH₂ (2.6 eV).²⁴⁻²⁶ The photocurrent profile of PCN-22 indicates that this material is active under visible light (>450 nm) illumination (Figure 3a). The Mott-Schottky measurement was performed to further reveal the flat-band potential of PCN-22. The positive slope of the obtained C⁻² to potential plot is consistent with that of typical n-type semiconductors (Figure 3b). It can be observed that the flat-band potential (V_{fb}) of PCN-22 is -0.47 V vs. Ag/AgCl (-0.26 V vs. NHE). These results indicate that PCN-22 should be a suitable candidate for light harvesting and photo-induced catalysis.

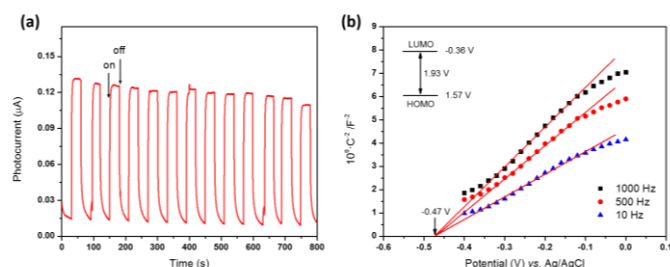


Figure 3. (a) Transient photocurrent responses of PCN-22 in 0.5 M Na₂SO₄ aqueous solution at a bias of 0.5 V vs. Ag/AgCl under visible light irradiation; (b) Mott-Schottky plot of PCN-22 in 0.5 M Na₂SO₄ aqueous solution.

In order to test the catalytic activity of PCN-22, we designed a PCN-22/TEMPO system (Scheme 1) for a photocatalyzed alcohol oxidation reaction (TEMPO = 2,2,6,6-tetramethylpiperidinyloxy). According to the relevant research on a dye/TiO₂/TEMPO system,³⁸ we proposed a probable mechanism for the PCN-22/TEMPO system. The TCPP linkers are excited by visible light to inject electrons into Ti₇O₆ clusters, yielding [TCPP]⁺. Meanwhile, TEMPO is oxidized to TEMPO⁺ by [TCPP]⁺, which then selectively oxidizes alcohol into aldehyde by a two-electron-transfer mechanism. The conversion of a benzyl alcohol to the corresponding benzaldehyde reaches 28% under visible-light irradiation in two hours with high selectivity (almost 100%). The turnover number (TON) is over 100, indicating a catalytic process. Moreover, as a heterogeneous catalyst, PCN-22 can be easily recovered by centrifugation without obvious decrease in activity and selectivity after three successive runs (Table S2). For comparison, the catalytic performances of TiO₂, TCPP, a mechanical mixture of TiO₂ and TCPP, as well as PCN-224³⁹ (a previously reported zirconium porphyrinic MOF) were examined under the same conditions. As shown in Figure 4, PCN-22 stands out to be the most efficient photocatalyst among these materials. PCN-224 is composed of Zr₆O₈ clusters and TCPP ligands. It contains a channel of 1.9 nm which is similar to that of PCN-22. However, PCN-224 shows low photocatalytic activity which can be attributed to the large energy gap and fast charge recombination of the Zr₆O₈ cluster. The low activity observed by the physical mixture of TiO₂ and TCPP can be simply ascribed to the aggregation of the active sites. In contrast, the highly porous structure of PCN-22 makes each catalytic center accessible to

the substrates. In addition, the titanium-oxo clusters in PCN-22 are periodically arranged and well separated by photosensitizers, which favors fast electron transfer from the photosensitizers to the titanium-oxo clusters and enhances the catalytic performance. The better performance of PCN-22 demonstrates that the incorporation of porphyrin sensitizer and titanium-oxo clusters into MOF matrix provides a new platform for the synthesis of photocatalysts.

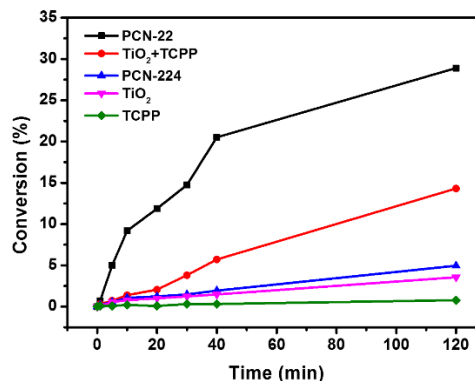


Figure 4. Time course of the benzyl alcohol oxidation reaction catalyzed by different catalyst

Conclusions

In summary, we report the first single crystalline titanium MOF, PCN-22, which was synthesized from preformed titanium-oxo carboxylate clusters and porphyrinic ligands. PCN-22 possesses high porosity and photocatalytic activity. It represents an important step towards mimicking dye sensitized TiO₂ in MOFs, which will extend the potential applications of MOFs to clean energy generation.


Experimental section

Materials and instrumentation

Methyl 4-formylbenzoate was purchased from Oakwood Products, Inc. Pyrrole, propionic acid, Titanium (IV) isopropoxide (Ti(OCH(CH₃)₂)₄), *N,N'*-diethylformamide (DEF), benzoic acid were purchased from Alfa Aesar. 5,10,15,20-Tetrakis (4-methoxycarbonylphenyl) porphyrin (TPPCOOMe) was prepared according to procedures described in S2. All commercial chemicals were used without further purification unless otherwise mentioned.

Powder X-ray diffraction (PXRD) was carried out with a BRUKER D8-Focus Bragg-Brentano X-ray Powder Diffractometer equipped with a Cu sealed tube ($\lambda = 1.54178 \text{ \AA}$) at 40 kV and 40 mA. Thermogravimetric analyses (TGA) were carried out on a Shimadzu TGA-50 thermal analyzer from room temperature to 600 °C at a ramp rate of 5 °C/min in a flowing nitrogen atmosphere. Fourier transform infrared (IR) measurements were performed on a SHIMADZU IR Affinity-1 spectrometer. Nuclear magnetic resonance (NMR) data were collected on a Mercury 300 spectrometer. Samples were activated by supercritical carbon dioxide using MADRIDE prior to gas adsorption. Gas sorption measurements were conducted on a Micromeritics ASAP 2020 system. Energy dispersive X-ray spectroscopy was carried out by JEOL JSM-7500F with Oxford EDS system equipped with X-ray mapping.

Synthesis

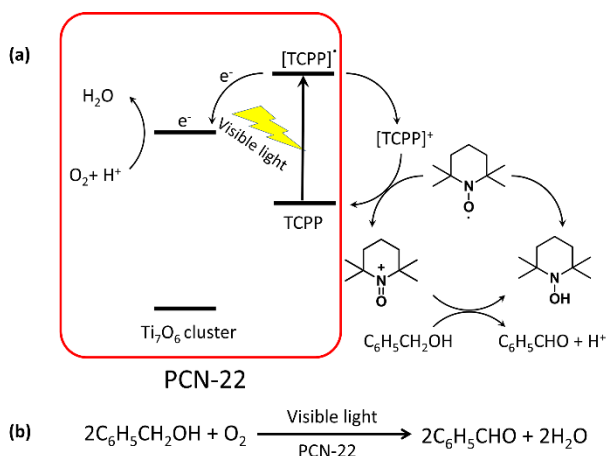

Ti₆O₆(OⁱPr)₆(abz)₆: The Ti₆O₆(OⁱPr)₆(abz)₆ cluster (Habz=4-aminobenzoic acid) was synthesized according to a reported procedure.³⁴ To a 2-propanol solution (6.0 mL) containing 4-aminobenzoic acid (192.1 mg, 1.40 mmol) added was titanium(IV) isopropoxide (103.6 μL). After stirring for 30 min at RT, the orange-colored slurry was heated to 100 °C for 77 h inside a sealed glass tube. The bright yellow crystalline product was collected, washed with 2-propanol and dried under vacuum for 3 h.

PCN-22: Ti₆O₆(OⁱPr)₆(abz)₆ cluster (4 mg), TCPP ligand (10 mg), benzoic acid (100 mg) and DEF 2mL were charged in a 4 mL Pyrex vial. The mixture was heated in 150 °C oven for 48 h. After cooling to room temperature, dark red, plate-like crystals were harvested.

Photoelectrochemical Studies

To prepare the working electrode, 10 mg PCN-22 was ground and dispersed in 2 ml acetone by sonication for 30 min. About 10 μL of the obtained slurry was coated on fluorine-doped tin oxide (FTO) glass with a fixed area of 0.5 cm². The electrode was dried in air at 85 °C for 10 min. The photoelectrochemical tests were performed using an electrochemical workstation (CHI 830b). The photocurrent test was carried out using a three-electrode setup, in which the working electrode (PCN-22/FTO electrode) and the counter electrode (Pt plate electrode) were short-circuited. The 0.5 M Na₂SO₄ solution was used as the electrolyte. A 30 W fluorescent light bulbs was used as the visible light source. The Mott-Schottky curves were measured in dark using a three-electrode cell at frequencies of 10 Hz. The Pt plate was used as counter electrode and Ag/AgCl electrode (3 M KCl) was used as reference electrode. The flat band position (*V*_{fb}) determined from the intersection is approximately -0.47 V vs. Ag/AgCl (*i.e.* -0.26 V vs. NHE) for PCN-22. Since it is generally believed that the bottom of the conduction band in many n-type semiconductors is more negative by about 0.10 V than the flat band potential, the conduction band (LUMO) of PCN-22 can be estimated to be -0.36 V vs. NHE. According to a band gap of 1.93 eV as described above, the valence band (HOMO) can be calculated to be 1.57 V vs. NHE.

Alcohol Oxidation Reaction

The photocatalytic selective oxidation of benzoic alcohol was performed as follows. A mixture of benzyl alcohol (200 μL, 1.78 mmol), PCN-22 (10 mg) and TEMPO (3 mg, 0.02 mmol) in CH₃CN was transferred into a 30 mL Pyrex bottle and purged with 30 mL/min O₂ flow for 5 minutes. For controlled experiments, 10 mg of TiO₂, TCPP, PCN-224, as well as a mechanical mixture of TiO₂ (2 mg) and TCPP (8 mg) were used instead of PCN-22 under the same conditions. The suspension was continuously stirred and irradiated by a 300 W Xe lamp with a light filter to cut off light of wavelength < 450 nm. Every 5 minutes, the reaction mixture was sampled with a 20 μL pipettor after 1, 5, 10, 20, 30, 40 and 120 minutes respectively. The samples were analyzed with HPLC (Shimadzu HPLC System with LC-20AD pump, SIL-20A Autoinjector and SPD-20A UV-vis Detector). The concentration of benzyl alcohol and benzaldehyde are calibrated by standard samples. The conversion and selectivity after two hours for three successive runs is shown in Table S2. There was no obvious decrease in activity and selectivity after three successive runs, demonstrating a good recyclability of PCN-22 as a recyclable heterogeneous catalyst.

Acknowledge

The photophysical studies of this research was supported by the Center for Gas Separations Relevant to Clean Energy Technologies, an Energy Frontier Research Center funded by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences under Award Number DE-SC0001015. Structural analyses were supported by Office of Naval Research under Award Number N000141310753. The Advanced Light Source is supported by the Director, Office of Science, Office of Basic Energy Sciences, of the U.S. Department of Energy under contract no. DE-AC02-05CH11231. The authors also acknowledge the financial supports of ARPA-e project funded by the U.S. Department of Energy under Award Number DE-AR0000249 and Welch Foundation under Award Number A-1725.

Notes and references

- H. C. Zhou, J. R. Long and O. M. Yaghi, *Chem. Rev.*, 2012, **112**, 673-674.
- L. J. Murray, M. Dinca and J. R. Long, *Chem. Soc. Rev.*, 2009, **38**, 1294-1314.
- J. R. Li, R. J. Kuppler and H. C. Zhou, *Chem. Soc. Rev.*, 2009, **38**, 1477-1504.
- K. Sumida, D. L. Rogow, J. A. Mason, T. M. McDonald, E. D. Bloch, Z. R. Herm, T. H. Bae and J. R. Long, *Chem. Rev.*, 2012, **112**, 724-781.
- L. E. Kreno, K. Leong, O. K. Farha, M. Allendorf, R. P. Van Duyne and J. T. Hupp, *Chem. Rev.*, 2012, **112**, 1105-1125.
- L. Ma, C. Abney and W. Lin, *Chem. Soc. Rev.*, 2009, **38**, 1248-1256.
- Q.-L. Zhu and Q. Xu, *Chem. Soc. Rev.*, 2014, **43**, 5468-5512.
- L.-L. Tan, H. Li, Y.-C. Qiu, D.-X. Chen, X. Wang, R.-Y. Pan, Y. Wang, S. X.-A. Zhang, B. Wang and Y.-W. Yang, *Chem. Sci.*, 2015, **6**, 1640-1644.
- A. L. Linsebigler, G. Lu and J. T. Yates, *Chem. Rev.*, 1995, **95**, 735-758.
- G. A. Somorjai, *Chem. Rev.*, 1996, **96**, 1223-1236.
- J. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chem. Soc. Rev.*, 2009, **38**, 1450-1459.
- Z. Wang and S. M. Cohen, *Chem. Soc. Rev.*, 2009, **38**, 1315-1329.
- H. G. T. Nguyen, N. M. Schweitzer, C.-Y. Chang, T. L. Drake, M. C. So, P. C. Stair, O. K. Farha, J. T. Hupp and S. T. Nguyen, *ACS Catal.*, 2014, **4**, 2496-2500.
- H. Deng, C. J. Doonan, H. Furukawa, R. B. Ferreira, J. Towne, C. B. Knobler, B. Wang and O. M. Yaghi, *Science*, 2010, **327**, 846-850.
- M. H. Beyzavi, R. C. Klet, S. Tussupbayev, J. Borycz, N. A. Vermeulen, C. J. Cramer, J. F. Stoddart, J. T. Hupp and O. K. Farha, *J. Am. Chem. Soc.*, 2014, **136**, 15861-15864.
- P. Deria, J. E. Mondloch, E. Tylianakis, P. Ghosh, W. Bury, R. Q. Snurr, J. T. Hupp and O. K. Farha, *J. Am. Chem. Soc.*, 2013, **135**, 16801-16804.
- S. M. Cohen, *Chem. Rev.*, 2012, **112**, 970-1000.
- T. R. Cook, Y.-R. Zheng and P. J. Stang, *Chem. Rev.*, 2012, **113**, 734-777.
- X. Kong, H. Deng, F. Yan, J. Kim, J. A. Swisher, B. Smit, O. M. Yaghi and J. A. Reimer, *Science*, 2013, **341**, 882-885.
- W. Lu, Z. Wei, Z.-Y. Gu, T.-F. Liu, J. Park, J. Park, J. Tian, M. Zhang, Q. Zhang, T. Gentle Iii, M. Bosch and H.-C. Zhou, *Chem. Soc. Rev.*, 2014, **43**, 5561-5593.
- F. Vermoortele, B. Bueken, G. Le Bars, B. Van de Voorde, M. Vandichel, K. Houthoofd, A. Vimont, M. Daturi, M. Waroquier, V. Van Speybroeck, C. Kirschhock and D. E. De Vos, *J. Am. Chem. Soc.*, 2013, **135**, 11465-11468.
- J. Park, J.-R. Li, Y.-P. Chen, J. Yu, A. A. Yakovenko, Z. U. Wang, L.-B. Sun, P. B. Balbuena and H.-C. Zhou, *Chem. Commun.*, 2012, **48**, 9995-9997.
- M. Dan-Hardi, C. Serre, T. Frot, L. Rozes, G. Maurin, C. Sanchez and G. Férey, *J. Am. Chem. Soc.*, 2009, **131**, 10857-10859.
- C. H. Hendon, D. Tian, M. Fontecave, C. Sanchez, L. D'Arras, C. Sassoey, L. Rozes, C. Mellot-Draznieks and A. Walsh, *J. Am. Chem. Soc.*, 2013, **135**, 10942-10945.
- M. A. Nasalevich, M. G. Goesten, T. J. Savenije, F. Kapteijn and J. Gascon, *Chem. Commun.*, 2013, **49**, 10575-10577.

26. Y. Fu, D. Sun, Y. Chen, R. Huang, Z. Ding, X. Fu and Z. Li, *Angew. Chem. Int. Ed.*, 2012, **51**, 3364-3367.
27. S. O. Obare, T. Ito and G. J. Meyer, *J. Am. Chem. Soc.*, 2005, **128**, 712-713.
28. S. Ardo, D. Achey, A. J. Morris, M. Abrahamsson and G. J. Meyer, *J. Am. Chem. Soc.*, 2011, **133**, 16572-16580.
29. A. J. Mozer, M. J. Griffith, G. Tsekouras, P. Wagner, G. G. Wallace, S. Mori, K. Sunahara, M. Miyashita, J. C. Earles, K. C. Gordon, L. Du, R. Katoh, A. Furube and D. L. Officer, *J. Am. Chem. Soc.*, 2009, **131**, 15621-15623.
30. C. Y. Lee, O. K. Farha, B. J. Hong, A. A. Sarjeant, S. T. Nguyen and J. T. Hupp, *J. Am. Chem. Soc.*, 2011, **133**, 15858-15861.
31. H.-J. Son, S. Jin, S. Patwardhan, S. J. Wezenberg, N. C. Jeong, M. So, C. E. Wilmer, A. A. Sarjeant, G. C. Schatz, R. Q. Snurr, O. K. Farha, G. P. Wiederrecht and J. T. Hupp, *J. Am. Chem. Soc.*, 2012, **135**, 862-869.
32. A. Hagfeldt, G. Boschloo, L. Sun, L. Kloo and H. Pettersson, *Chem. Rev.*, 2010, **110**, 6595-6663.
33. J. Gao, J. Miao, P. Z. Li, W. Y. Teng, L. Yang, Y. Zhao, B. Liu and Q. Zhang, *Chem. Commun.*, 2014, **50**, 3786-3788.
34. D. Feng, K. Wang, Z. Wei, Y.-P. Chen, C. M. Simon, R. K. Arvapally, R. L. Martin, M. Bosch, T.-F. Liu, S. Fordham, D. Yuan, M. A. Omary, M. Haranczyk, B. Smit and H.-C. Zhou, *Nat. Commun.*, 2014, **5**, 5723.
35. J. Gao, J. Miao, P. Z. Li, W. Y. Teng, L. Yang, Y. Zhao, B. Liu and Q. Zhang, *Chem. Commun.*, 2014, **50**, 3786-3788.
- Note: We noticed that single crystal of a 2D MOF based on single Ti node and DOBDC ligands (DOBDC = 1, 4-dioxido-2, 5-benzenedicarboxylate) was reported recently. However, in this MOF the Ti is chelated by an oxygen atom from the phenol group and another carbonyl oxygen on the adjacent carboxylic group. No permanent porosity was demonstrated for such a MOF that might be unstable toward desolvation.
36. K. Hong and H. Chun, *Inorg. Chem.*, 2013, **52**, 9705-9707.
37. J. Tauc, *Mater. Res. Bull.*, 1968, **3**, 37-46.
38. M. Zhang, C. Chen, W. Ma and J. Zhao, *Angew. Chem. Int. Ed. Engl.*, 2008, **47**, 9730-9733.
39. D. Feng, W.-C. Chung, Z. Wei, Z.-Y. Gu, H.-L. Jiang, Y.-P. Chen, D. J. Darensbourg and H.-C. Zhou, *J. Am. Chem. Soc.*, 2013, **135**, 17105-17110.

Entry for the Table of Contents:

We synthesized a single crystalline porphyrinic titanium MOF, in which the Ti-oxo clusters and porphyrinic ligands are combined into an inherent dye-sensitized photoactive system. PCN-22 represents an important step towards mimicking dye sensitized TiO₂ in MOFs.

