

# Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

## Cellulose-Supported Chiral Rh Nanoparticles as Sustainable Heterogeneous Catalysts for Asymmetric Carbon-Carbon Bond-Forming Reactions

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Tomohiro Yasukawa, Hiroyuki Miyamura, and Shū Kobayashi\*

Cellulose-supported chiral Rh nanoparticle (NP) catalysts have been developed. The Rh NPs, which were well dispersed on cellulose, catalyzed the asymmetric 1,4-addition of arylboronic acids to enones and enoates, one of representative asymmetric carbon-carbon bond-forming reactions, in the presence of chiral diene ligands, providing the corresponding adducts in high yields with outstanding enantioselectivities without metal leaching. The solid state NMR analysis of chiral NP system directly suggested interactions between the Rh NPs and the chiral ligand on the cellulose. This is the first example of polysaccharide-supported chiral metal nanoparticles for asymmetric carbon-carbon bond-forming reactions.

### Introduction

The development of heterogeneous chiral catalysts for asymmetric C–C bond-forming reactions is an imperative research subject for both academia<sup>1</sup> and industry.<sup>2</sup> The advantages of these systems, such as ease of separation and reusability, can reduce the amount of scarce resources that are required, including precious metal-based catalysts. Although much effort has been devoted to this area in the last two decades, it is still challenging to obtain truly efficient and sustainable heterogeneous chiral catalysts. Recently, the great potential of chiral ligand-modified metal nanoparticles (NPs) as robust heterogeneous chiral catalysts has been demonstrated. Metal NPs can be deposited on solid supports to form stable heterogeneous catalysts, and such systems often show unique activity and selectivity that are distinct from those of homogeneous metal complexes.<sup>3</sup> We have recently developed nanocomposites of polystyrene-based copolymer with a cross-linking moiety and carbon black-incarcerated bimetallic Rh/Ag NPs catalysts (PI/CB Rh/Ag), and found that PI/CB Rh/Ag catalyzed the asymmetric 1,4-addition of arylboronic acids to  $\alpha,\beta$ -unsaturated carbonyl compounds in the presence of a chiral diene ligand.<sup>4,5</sup> Although high yields and enantioselectivities have been realized by using these catalyst systems and the robustness of PI/CB Rh/Ag has been demonstrated, Ag might not be crucial for the catalytic cycle and the polystyrene-based copolymer is originally derived

from petroleum, which is not a sustainable resource. Thus, the removal of the dopant as well as the use of more abundant and recyclable materials as supports are preferable for developing next-generation catalysts.

We focused on the use of cellulose as a support because this material has several advantages: 1) it has high stability and insolubility in common solvents; 2) it bears many hydroxyl groups that are expected to stabilize metal NPs effectively; and 3) it is abundant and is an environmentally benign biomass-derived material. Indeed, cellulose and its derivatives (polysaccharides) are very useful materials that are incorporated into a range of versatile products,<sup>6</sup> and the application of such materials in catalytic systems has also been realized. An early example of the use of cellulose as a support for the immobilization of a Pd complex catalyst for Tsuji–Trost reaction was reported in 2001.<sup>7</sup> Kunitake and coworkers reported the immobilization of various monodisperse metal NPs on cellulose fibers by NaBH<sub>4</sub>-mediated reduction of cellulose fibers immersed in metal salt.<sup>8</sup> After these reports, the application of cellulose-supported metal NPs to catalysis was explored by many groups. For example, it was reported that Pd NPs catalyzed coupling reactions,<sup>9</sup> hydrogenations,<sup>9f</sup> and Tsuji–Trost reactions,<sup>10</sup> Au NPs catalyzed aerobic oxidations<sup>11</sup> and reductions,<sup>12</sup> and Cu NPs catalyzed C–N couplings,<sup>13</sup> aza-Michael additions,<sup>14</sup> and reductions.<sup>15</sup> However, the applications of polysaccharide-supported catalysts to asymmetric transformations are limited to reports on the use of functionalized cellulose derivatives or chitosan as organocatalysts<sup>16</sup> or as chiral ligands for metal complexes.<sup>17</sup> To our knowledge, there have been no reports on asymmetric catalysis by using polysaccharide-supported metal NPs as heterogeneous catalysts.<sup>18</sup> Herein, we report the first example of cellulose-supported chiral Rh NP catalysts as an efficient and

Department of Chemistry, School of Science, The University of Tokyo, Hongo, Bunkyo-ku, Tokyo 113-0033 (Japan)

E-mail: shu\_kobayashi@chem.s.u-tokyo.ac.jp.

† Electronic supplementary information (ESI) available: General procedures, materials, and instrumentation; synthesis, characterization and relevant spectra/charts; procedures and results for optimization and additional experiments. See DOI: 10.1039/x0xx00000x

sustainable chiral catalyst system for asymmetric 1,4-addition reactions.

## Results and discussion

Cellulose-supported Rh NP catalysts were prepared in THF by using  $\text{Rh}_2(\text{OAc})_4$  and  $\text{NaBH}_4$  as reductant, based on our previous methods that were used to immobilize metal NPs on supports such as polystyrene-based copolymers and polysilanes (Table 1).<sup>4b,19</sup> NPs were immediately deposited on cellulose as soon as the solution of Rh salt was added to the suspension of cellulose.<sup>20</sup> Successive heating and washing with water and organic solvents afforded Rh-Cell I. By using this method, Rh NPs were successfully immobilized on cellulose (entry 1). A bimetallic Rh/Ag NP catalyst was prepared from  $\text{Rh}_2(\text{OAc})_4$  and  $\text{AgSbF}_6$  by using the same method, and high loading of each metal was observed (entry 2). Scanning transmission electron microscope (STEM) analysis of Rh-Cell I revealed that although several NPs were sometimes assembled, the size of each NP was relatively small (2–5 nm) and NPs were well dispersed.<sup>21</sup> In Rh/Ag-Cell, larger NPs were observed, indicating that the silver dopant caused aggregation in the case of cellulose-supported catalysts.<sup>21</sup> Anhydrous  $\text{RhCl}_3$  was also examined as a Rh source for the preparation of the catalyst. Given the poor solubility of this Rh salt in common solvents, 1 M NaOH aq. was used (entry 3). STEM analysis of the obtained catalyst Rh-Cell II revealed better size distributions of the smaller NPs (ca. 3 nm) in Rh-Cell II.<sup>21</sup> To clarify whether the use of  $\text{RhCl}_3$  or NaOH aq. mainly affected the size distribution, the catalyst was prepared from  $\text{Rh}_2(\text{OAc})_4$  in the presence of NaOH aq. (entry 4). Because  $\text{Rh}_2(\text{OAc})_4$  did not dissolve in 1 M NaOH aq., the latter was added first followed by the addition of a solution of  $\text{Rh}_2(\text{OAc})_4$  in THF to form Rh-Cell III. Based on STEM images of the obtained catalyst,<sup>21</sup> particle sizes of Rh-Cell III were larger than those of Rh-Cell II. It was therefore evident that the choice of metal source was a major factor that determined the size distribution. When Rh/Cell IV was prepared from  $\text{Rh}_2(\text{OAc})_4$  in the presence of water instead of NaOH aq., lower loading was obtained (entry 5) and no significant change of size distribution of nanoparticles was observed.<sup>21</sup>

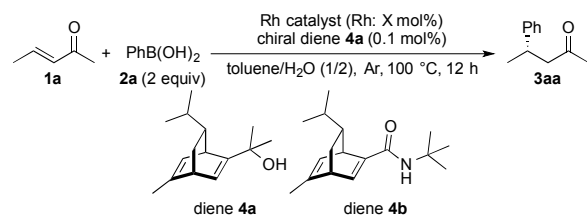
Notably, both Rh NPs and Rh/Ag NPs were stabilized and immobilized on cellulose. Several control studies using partially methylated cellulose and d-glucose as supports showed that similar metal loadings and STEM images to those of Rh-Cell were obtained in both supported catalysts.<sup>21</sup> This observation suggests that there was no formation of strong bonds, such as covalent bonds or hydrogen bonds, between Rh NPs and the supports, and that Rh NPs might be stabilized and immobilized by interactions between the metals and oxygen atoms of cellulose and derivatives.<sup>8</sup>

**Table 1** Preparation of polysaccharide-supported Rh NP catalysts.

Entry	Catalyst	Reagents	Rh/(Ag) loading (mmol/g) <sup>a</sup>
1	Rh-Cell I	$\text{Rh}_2(\text{OAc})_4$ in THF	0.0622
2	Rh/Ag-Cell	$\text{Rh}_2(\text{OAc})_4$ and $\text{AgSbF}_6$ in THF	0.0693/0.0672
3	Rh-Cell II	$\text{RhCl}_3$ in 1 M NaOH aq.	0.0651
4	Rh-Cell III	1 M NaOH aq. then $\text{Rh}_2(\text{OAc})_4$ in THF	0.0651
5	Rh-Cell IV	$\text{H}_2\text{O}$ then $\text{Rh}_2(\text{OAc})_4$ in THF	0.0554

<sup>a</sup> Determined by ICP analysis.

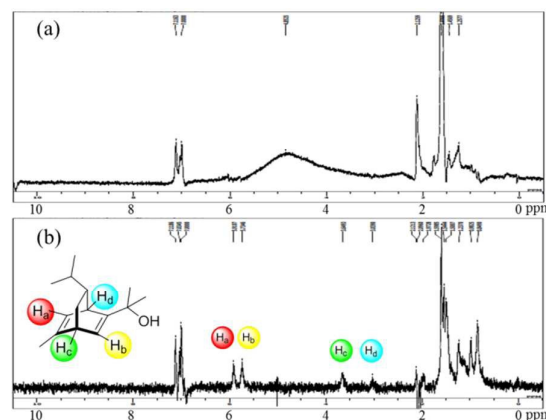
The catalytic activity of these NPs was then tested in the asymmetric 1,4-addition of phenylboronic acid (**2a**) to aliphatic enone **1a** in the presence of chiral diene **4a** (Table 2). Rh-Cell I showed high catalytic performance, affording the desired product **3aa** in high yield and excellent enantiomeric excess (ee) and no metal leaching was observed (entry 1). The catalyst loading of Rh-Cell I could be reduced to 0.5 mol% without loss of yield, with a negligible level of metal leaching (entry 2). In contrast to the PI/CB system, the bimetallic catalyst Rh/Ag-Cell showed lower activity than that of Rh-Cell I, probably because of the larger size of the NPs in Rh/Ag-Cell (entry 3). In spite of the formation of smaller NPs, lower catalytic activity and a significant amount of metal leaching were observed in the reaction with Rh-Cell II (entry 4). Further heating or washing treatments of this catalyst failed to prevent the leaching.<sup>21</sup> Rh/Cell III showed good catalytic activity with 0.5 mol% catalyst loading and no metal leaching was observed (entry 5), whereas Rh-Cell IV suffered metal leaching under the same reaction conditions (entry 6), indicating that the addition of NaOH during the catalyst preparation is important not only to immobilize Rh NPs in high loading but also to prevent metal leaching. Although the effect of NaOH is unclear, the negatively charged cellulose might be able to interact with Rh strongly and efficiently stabilize NPs under the basic conditions; indeed, a slightly higher negative zeta potential of cellulose under basic conditions than that under neutral conditions was observed by Haruta and coworkers.<sup>11</sup> Given that the method of preparation of Rh-Cell III was relatively straightforward and considering that an excellent result was obtained in the model reaction, Rh-Cell III was established as the best catalyst. Further optimization<sup>21</sup> using Rh-Cell III revealed that the use of secondary amide-substituted chiral diene **4b**<sup>4a</sup> gave a higher ee and that the amount of chiral diene could be reduced to 0.05 mol% without affecting the yield or the extent of metal leaching (entry 7).

**Table 2** Asymmetric 1,4-addition to enone.

Entry	Catalyst	X (mol%)	Yield (%) <sup>a</sup>	ee (%) <sup>b</sup>	Rh leaching (%) <sup>c</sup>
1	Rh-Cell I	1.5	93	95	ND
2	Rh-Cell I	0.5	95	95	0.27
3	Rh/Ag-Cell	0.5	54	–	0.30
4	Rh-Cell II	0.5	65	–	3.0
5	Rh-Cell III	0.5	86	96	ND
6	Rh-Cell IV	0.5	84	–	0.78
7 <sup>[d]</sup>	Rh-Cell III	0.5	91	98	ND

<sup>a</sup> Determined by GC analysis. <sup>b</sup> Determined by HPLC analysis. <sup>c</sup> Determined by ICP analysis (ND = not detected). The values express the percentage of the total amounts of Rh that was employed to the reaction. Detection limit of Rh leaching is 0.1% (entry 1), 0.22% (entry 5) and 0.17% (entry 7). [d] Diene **4b** (0.05 mol%) was used instead of **4a**.

High yield and excellent enantioselectivity were obtained by using the Rh-Cell catalyst and chiral diene **4a** or **4b**. For high catalytic performance, an appropriate interaction of Rh NPs, cellulose, and the chiral diene is crucial, and such interaction was suggested by swollen-resin magic angle spinning (SR-MAS) NMR<sup>22</sup> analysis of the catalyst system. Solid-state NMR analysis with the addition of a solvent to swell the sample, so-called SR-MAS NMR, is a powerful tool to analyze heterogeneous systems. To confirm the formation of chiral NPs, characterization of the chiral diene adsorbed on the surface of Rh NPs was undertaken on a mixture of Rh-Cell I, chiral ligand **4a**, and toluene by conducting SR-MAS experiments, the pulse sequence of which consisted of a diffusion filter and isotropic mixing.<sup>21,23</sup> The diffusion filter can suppress signals from the molecules with high mobility such as a solvent and a chiral diene in the solution phase. The signal derived from **4a** (3–6 ppm) was completely suppressed by using the diffusion filter, and the signals derived from cellulose remained due to the lower diffusion coefficient of the polymer (Figure 1a). Isotropic mixing can introduce an exchange between the remaining magnetization to nearby molecules with low mobility and the magnetization of cellulose is expected to exchange for nearby molecules that would be anchored in the catalyst. The signals derived from **4a** were enhanced after diffusion filter followed by isotropic mixing (Figure 1b). The same phenomenon was not observed for samples containing only cellulose and **4a** in toluene,<sup>21</sup> which suggests that the molecules adsorbed on Rh NPs were observed selectively by this method.


**Figure 1** SR-MAS analysis of the mixture of Rh-Cell and chiral diene **4a** (a) with diffusion filter and (b) with diffusion filter and isotropic mixing.

We then surveyed the substrate scope of the asymmetric 1,4-addition of arylboronic acids to enones with Rh-Cell III under the optimized conditions (Table 3). Cyclic enone **1b** and branched acyclic enone **1c** were smoothly converted into the products in high yields and excellent ee's with 1.5 equiv **2a** (entries 2 and 3). Excellent yield and ee were also observed in the reaction with acyclic enone **1d**, aromatic enone **1e**, and cyclic enone **1f**, with a five-membered ring, when the reaction time was prolonged to 20 h (entries 4–6). The substrate generality of the arylboronic acid part was examined by using **1b**. Irrespective of the substitution position, a range of arylboronic acids with either an electron-donating or electron-withdrawing group was suitable, and the reaction afforded the products in high yields and outstanding ee's (entries 7–11).

**Table 3** Substrate scope of the asymmetric 1,4-addition to enones.

Entry	Product	Time (h)	X (equiv)	Yield (%) <sup>a</sup>	ee (%) <sup>b</sup>
1	<b>3aa</b>	12	2.0	95 <sup>c</sup>	98
2	<b>3ba</b>	12	1.5	95	99
3	<b>3ca</b>	12	1.5	86	98
4	<b>3da</b>	20	2.0	94	98
5	<b>3eb</b>	20	2.0	87	96
6	<b>3fa</b>	20	1.5	90	99
7	<b>3bb</b>	20	1.5	83	99
8	<b>3bc</b>	20	1.5	84	97
9	<b>3bd</b>	20	1.5	89	98
10	<b>3be</b>	20	1.5	86	98
11	<b>3bf</b>	20	1.5	87	99

<sup>a</sup> Isolated yield. <sup>b</sup> Determined by HPLC analysis. <sup>c</sup> Determined by GC analysis.

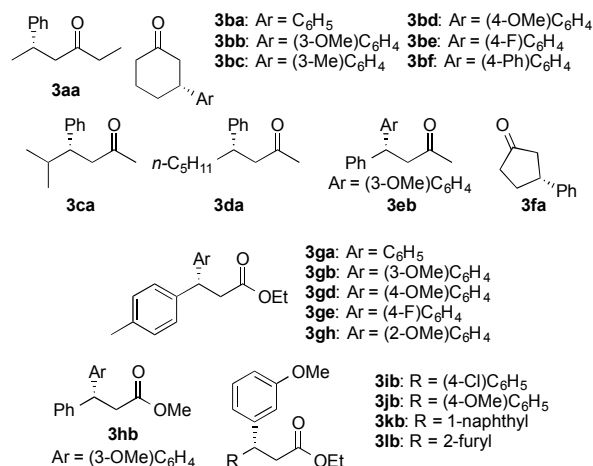

Scheme 1 List of the products

The catalyst system with Rh-Cell III was also applied to the asymmetric 1,4-addition to  $\alpha,\beta$ -unsaturated esters (Table 4). When the use of aromatic unsaturated ethyl ester **1g** was examined, the desired products were obtained in high yields and excellent ee's under the same conditions after 20 h in the reactions with a range of arylboronic acids (entries 1–4). In the case of *ortho*-substituted boronic acid **2h**, 1 equiv of base was required to achieve a high yield (entry 5). The addition of base also promoted the reaction with aromatic unsaturated methyl ester **1h** (entry 6). Aromatic unsaturated ethyl esters with substituents and substrates bearing a naphthyl group were smoothly converted into the products in high yields with excellent ee's (entries 7–9). Heteroarene-substituted substrates could be converted into the product in high yield and excellent ee in the presence of a base (entry 10).

Rh-Cell III could be recovered by filtration and the reusability of the catalyst was tested in the reaction of **1a** with

Table 4 Substrate generality of the reaction with  $\alpha,\beta$ -unsaturated esters.

Entry	Product	Additive	Yield (%) <sup>a</sup>	ee (%) <sup>b</sup>
1	<b>3ga</b>	–	96	98
2	<b>3gb</b>	–	93	99
3	<b>3gd</b>	–	92	98
4	<b>3ge</b>	–	81	99
5	<b>3gh</b>	1.0 equiv K <sub>2</sub> CO <sub>3</sub>	81	>99
6	<b>3hb</b>	0.1 equiv K <sub>2</sub> CO <sub>3</sub>	91	98
7 <sup>c</sup>	<b>3ib</b>	–	81	99
8	<b>3jb</b>	–	91	98
9	<b>3kb</b>	–	95	99
10 <sup>c</sup>	<b>3lb</b>	0.1 equiv K <sub>2</sub> CO <sub>3</sub>	81	98

<sup>a</sup> Isolated yield. <sup>b</sup> Determined by HPLC analysis. <sup>c</sup> **4b** (0.1 mol%) and **III** (Rh: 1.0 mol%) were used.

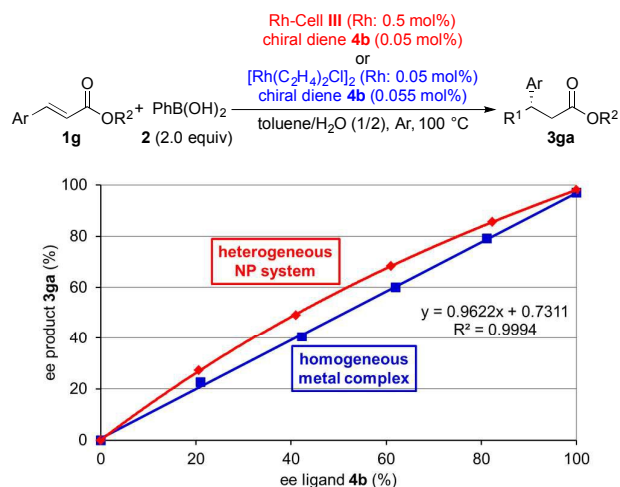


Figure 2 Non-linear effect analysis

**2a.** The recovered catalyst, when washed with acidic media (THF/1 M TfOH aq., 99:1) between runs, maintained its catalytic activity to afford **3aa** in >95% yield over three cycles. The new portion of chiral diene was employed every runs and the enantioselectivity was 98% ee in all cases. It is possible that TfOH neutralizes and removes basic impurities.<sup>24</sup> Rh loading of the recovered catalyst after several runs was almost unchanged from that of the catalyst before use, indicating that no metal leaching occurred either during the reactions or upon washing in acidic media.

Finally, we performed nonlinear effect (NLE) analysis<sup>25</sup> to obtain information about the nature of the active species in the current catalyst system. We previously discovered that a positive NLE was observed in the PI/CB Rh/Ag system, whereas a linear relationship between the enantiomeric excess of the ligand and that of the product was observed in the homogeneous metal complex system.<sup>4a</sup> These results clearly distinguished the nature of the active species involved in the two systems. In the case of the Rh-Cell system, similar positive NLE as that in the PI/CB Rh/Ag system was observed, and the characteristic nature of the current cellulose-based heterogeneous NP system that was distinct from the nature of homogeneous metal complex system was confirmed (Figure 2).

## Conclusions

Cellulose, as a readily available and abundant material, was found to be an excellent support for Rh NP catalysts. The procedure used for the preparation of Rh-Cell is straightforward and Rh NPs were well dispersed over the cellulose. The combination of Rh-Cell with chiral diene ligand showed excellent catalytic performance for asymmetric 1,4-additions to enones and  $\alpha,\beta$ -unsaturated esters without the addition of silver to afford the desired products in high yields with outstanding ee's without metal leaching. This is the first example of polysaccharide-supported chiral metal nanoparticles for asymmetric carbon-carbon bond-forming reactions. We believe that this cellulose-supported chiral Rh

NP catalyst system is a truly sustainable asymmetric catalyst system.

## Acknowledgements

This work was partially supported by a Grant-in-Aid for Science Research from the Japan Society for the Promotion of Science (JSPS), the Global COE Program, the University of Tokyo, the Japan Science and Technology Agency (JST), and the Ministry of Education, Culture, Sports, Science and Technology (MEXT, Japan). We thank Mr. Kenji Takasugi (The University of Tokyo and JEOL) for his support and discussion on SR-MAS analysis and Mr. Noriaki Kuramitsu (The University of Tokyo) for STEM and EDS analyses.

## Notes and references

- (a) T. Tsubogo, T. Ishiwata and S. Kobayashi, *Angew. Chem., Int. Ed.*, 2013, **52**, 6590.; (b) A. F. Trindade, P. M. P. Gois and C. A. M. Afonso, *Chem. Rev.*, 2009, **109**, 418; (c) M. Heitbaum, F. Glorius and I. Escher, *Angew. Chem., Int. Ed.*, 2006, **45**, 4732; (d) P. McMorn and G. J. Hutchings, *Chem. Soc. Rev.*, 2004, **33**, 108.
- (a) H. U. Blaser, H.-J. Federsel, *Asymmetric Catalysis on Industrial Scale: Challenges, Approaches and Solutions*, Wiley-VCH, Weinheim, 2010; (b) C. Lucarelli and A. Vaccari, *Green Chem.*, 2011, **13**, 1941; (c) C. A. Busacca, D. R. Fandrick, J. J. Song and C. H. Senanayake, *Adv. Synth. Catal.*, 2011, **353**, 1825; (d) B. Pugin and H.-U. Blaser, *Top. Catal.*, 2010, **53**, 953.
- (a) T. Yasukawa, H. Miyamura and S. Kobayashi, *Chem. Soc. Rev.*, 2014, **43**, 1450; (b) L. L. Chng, N. Erathodiyil and J. Y. Ying, *Acc. Chem. Res.*, 2013, **46**, 1825; (c) E. Gross, J. H. Liu, S. Alayoglu, M. A. Marcus, S. C. Fakra, F. D. Toste, G. Somorjai, A. J. Am. Chem. Soc., 2013, **135**, 3881; (d) K. V. S. Ranganath, J. Kloesges, A. H. Schäfer and F. Glorius, *Angew. Chem., Int. Ed.*, 2010, **49**, 7786; (e) B. M. Choudary, K. V. S. Ranganath, U. Pal, M. L. Kantam and B. Sreedhar, *J. Am. Chem. Soc.*, 2005, **127**, 13167; (f) S. Jansat, M. Gómez, K. Philippot, G. Muller, E. Guiu, C. Claver, S. Castillon and B. Chaudret, *J. Am. Chem. Soc.*, 2004, **126**, 1592; (g) Y. Orito, S. Imai, S. Niwa and G. H. Nguyen, *J. Synth. Org. Chem. Jpn.*, 1979, **37**, 173.
- (a) T. Yasukawa, A. Suzuki, H. Miyamura, K. Nishino and S. Kobayashi, *J. Am. Chem. Soc.*, 2015, **137**, 6616; (b) T. Yasukawa, H. Miyamura and S. Kobayashi, *J. Am. Chem. Soc.*, 2012, **134**, 16963.
- (a) K. Okamoto, T. Hayashi and V. H. Rawal, *Chem. Commun.*, 2009, 4815; (b) K. Okamoto, T. Hayashi and V. H. Rawal, *Org. Lett.*, 2008, **10**, 4387.
- D. Klemm, B. Heublein, H. P. Fink and A. Bohn, *Angew. Chem. Int. Ed.*, 2005, **44**, 3358.
- F. Quignard and A. Choplin, *Chem. Commun.*, 2001, 21.
- J. H. He, T. Kunitake and A. Nakao, *Chem. Mater.*, 2003, **15**, 4401.
- (a) M. Rezayat, R. K. Blundell, J. E. Camp, D. A. Walsh and W. Thielemans, *ACS Sustainable Chem. Eng.*, 2014, **2**, 1241; (b) A. Molnar and A. Papp, *Catal. Sci. Technol.*, 2014, **4**, 295; (c) P. Zhou, H. Wang, J. Yang, J. Tang, D. Sun and W. Tang, *RSC Adv.*, 2012, **2**, 1759; (d) P. Zhou, H. Wang, J. Yang, J. Tang, D. Sun and W. Tang, *Ind. Eng. Chem. Res.*, 2012, **51**, 5743; (e) Q. Du and Y. Li, *Beilstein J. Org. Chem.*, 2011, **7**, 378; (f) C. M. Cirtiu, A. F. Dunlop-Briere and A. Moores, *Green Chem.*, 2011, **13**, 288; (g) K. R. Reddy, N. S. Kumar, P. S. Reddy, B. Sreedhar and M. L. Kantam, *J. Mol. Catal. A: Chem.*, 2006, **252**, 12.
- B. R. Vaddula, A. Saha, R. S. Varma and J. Leazer, *Eur. J. Org. Chem.*, 2012, 6707.
- T. Ishida, H. Watanabe, T. Bebeko, T. Akita and M. Haruta, *Appl. Catal., A*, 2010, **377**, 42.
- (a) H. Koga, E. Tokunaga, M. Hidaka, Y. Umemura, T. Saito, A. Isogai and T. Kitaoka, *Chem. Commun.*, 2010, **46**, 8567; (b) A. Azetsu, H. Koga, A. Isogai and T. Kitaoka, *Catalysts*, 2011, **1**, 83.
- K. R. Reddy, N. S. Kumar, B. Sreedhar and M. L. Kantam, *J. Mol. Catal. A: Chem.*, 2006, **252**, 136.
- K. R. Reddy and N. S. Kumar, *Synlett*, 2006, 2246.
- Z. Zhou, C. Lu, X. Wu and X. Zhang, *RSC Adv.*, 2013, **3**, 26066.
- (a) C. Gioia, A. Ricci, L. Bernardi, K. Bourahla, N. Tanchoux, M. Robitzer and F. Quignard, *Eur. J. Org. Chem.*, 2013, 588; (b) L. Yang, D. Zhou, C. Qu and Y. Cui, *Catal. Lett.*, 2012, **142**, 1405; (c) Y. Qin, W. Zhao, L. Yang, X. Zhang and Y. Cui, *Chirality*, 2012, **24**, 640; (d) T. Ikai, M. Moro, K. Maeda and S. Kanoh, *React. Funct. Polym.*, 2011, **71**, 1055; (e) A. Ricci, L. Bernardi, C. Gioia, S. Vierucci, M. Robitzer and F. Quignard, *Chem. Commun.*, 2010, **46**, 6288; (f) H. Zhang, W. Zhao, J. Zou, Y. Liu, R. Li and Y. Cui, *Chirality*, 2009, **21**, 492.
- (a) M. Babin, R. Clement, J. Gagnon and F.-G. Fontaine, *New J. Chem.*, 2012, **36**, 1548; (b) L. Xue, D.-J. Zhou, L. Tang, X.-F. Ji, M.-Y. Huang and Y.-Y. Jiang, *React. Funct. Polym.*, 2004, **58**, 117; (c) B. W. Mao, A. G. Zhao, M. Y. Huang and Y. Y. Jiang, *Polym. Adv. Technol.*, 2000, **11**, 250; (d) K. Kaneda, H. Yamamoto, T. Imanka and S. Teranishi, *J. Mol. Catal.*, 1985, **29**, 99; (e) Y. Kawabata, M. Tanaka and I. Ogata, *Chem. Lett.*, 1976, **5**, 1213.
- Recently, highly crystalline cellulose nanocrystals-supported Pd catalyst for asymmetric hydrogenation was reported. In this article, cellulose itself worked as a chiral inducer to give hydrogenated products in moderate ee. See: M. Kaushik, K. Basu, C. Benoit, C. M. Cirtiu, H. Vali and A. Moores, *J. Am. Chem. Soc.*, 2015, **137**, 6124.
- H. Oyamada, T. Naito, S. Miyamoto, R. Akiyama, H. Hagio and S. Kobayashi, *Org. Biomol. Chem.*, 2008, **6**, 61.
- When the order of the addition of the reagents was changed (Rh salt was added firstly followed by the addition of the reductant), the loading of Rh decreased. The "pre-stirring" step might be important for good reproducibility to achieve the high metal loading probably due to efficient formation of the borate species between sodium borohydride and hydroxyl groups on cellulose. If the reduction of Rh salts occurred with these borate species, the Rh nanoparticles might generate near cellulose and would be immediately stabilized by cellulose.
- See the Electronic Supplementary Information for details.
- (a) S. Kobayashi, R. Akiyama, T. Furuta and M. Moriwaki, *Mol. Online*, 1998, **2**, 35; (b) J.-F. Soulé, H. Miyamura and S. Kobayashi, *J. Am. Chem. Soc.*, 2013, **135**, 10602.
- J. A. Chin, A. Chen and M. J. Shapiro, *J. Comb. Chem.*, 2000, **2**, 293.
- M. Kumar, G. B. Hammond and B. Xu, *Org. Lett.*, 2014, **16**, 3452.
- T. Satyanarayana, S. Abraham and H. B. Kagan, *Angew. Chem., Int. Ed.*, 2009, **48**, 456.