

# Soft Matter

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## COMMUNICATION

## Bijels stabilized using rod-like particles

Cite this: DOI: 10.1039/x0xx00000x

Niek Hijnen,<sup>a</sup> Dongyu Cai<sup>a</sup> and Paul S. Clegg<sup>a\*</sup>Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/


**Bicontinuous interfacially jammed emulsion gels, in short ‘bijels’, rely on a trapped layer of colloidal particles for their stability. These structures have traditionally been created using spherical colloidal particles. Here we show for the first time the use of rod-shape particles to stabilize bijels. We show that domain size decreases more rapidly with particle concentration in the case of rods compared to spheres. Large-scale analysis and detailed examination of images show that the packing fraction of rods is much higher than expected, in part, due to the role of ‘flippers’.**

Bijels are a new class of soft materials with two tortuous interpenetrating fluid domains sharing an interface which is jammed with colloidal particles.<sup>1</sup> They were predicted by computer simulations in 2005<sup>2</sup> and experimentally realized in 2007.<sup>3</sup> The formation process of the bijel relies on the spinodal decomposition of a binary liquid mixture in presence of the colloidal particles (for different systems and approaches, see <sup>4,5,6</sup>). When equally wetted by the two emerging liquid phases (i.e. contact angle close to 90°), these particles are trapped on the percolating interface without imposing any preferred interfacial curvature. As a result of the jammed particles, coarsening of the spinodal structure slows to a stop, and the bijel, a soft solid, is formed. Bijels are not only interesting to physicists as a state trapped far from equilibrium, but also to a broader audience who are interested in new materials for potential applications. For example, the bijel has been suggested for application as a cross-flow microreaction medium.<sup>1</sup> Additionally, selective polymerization of one of the fluid domain loaded with monomers followed by the removal of all liquids has been used to obtain porous polymeric materials without losing the original bijel structure.<sup>7,8</sup>

So far, it is known that the properties of bijels are crucially dependent on the colloidal particles including their size, concentration and particle-particle interactions.<sup>3,9</sup> However, this has been established based on experiments with spherical particles alone. We anticipate that the shape of the particles will play a major role as well. Recently, Imperiali et al reported the use of plate-shaped

graphene oxide to arrest the bijel structure. They argued that 2D nature of graphene oxide sheets led to the formation of highly elastic layers at the interface giving a different mechanism for arrest of the bijel structure in contrast to the jamming of spherical particles.<sup>10</sup> Here, we focus on the use of 1D rod-like particles to stabilize bijels, which has not yet been explored experimentally. To maximize the removed area of liquid-liquid interface, the long axes of rods will lie parallel to the interface. We believe that rod-like particles will behave very differently from spherical particles, since they will have a preferred orientation with respect to cylindrical regions of interface and they tend to induce significant deformations of an otherwise flat interface, leading to strong capillary interactions.<sup>11,12</sup> Another striking feature of colloidal rods at liquid-liquid interfaces is that, in response to compression, the rods can flip out of the plane, and also be expelled from the interface prior to buckling, contrasting with behaviour of spherical particles.<sup>13</sup> Recently, computer simulations of bijels stabilized using rods,<sup>14-16</sup> have shown that at constant particle number and volume fraction, increasing particle aspect ratio leads to smaller domains,<sup>14</sup> furthermore rod-like particles allow the generation of more stable emulsions than spherical particles.<sup>16</sup> In this Communication, we present the first experimental realization of bijels stabilized using colloidal rods. We have imaged the packing of the rods on the interface using confocal microscopy, and we compare, quantitatively, the role of particle shape in dictating final bijel structures. More broadly, the methodology presented in this study could be reproduced for exploring the structure of bijels arrested by even more exotic particles.

To realize the rod-stabilized bijels, a pair of partially miscible liquids (nitromethane (NM)/ethylene glycol (EG)<sup>17</sup>) was selected to host the akaganéite-silica core-shell rods. The phase diagram of NM and EG is shown in **Figure 1a**. The preparation of the rods follows our method reported in Ref [18]. Akaganéite cores provide the required shape, while the silica shells offer the essential functionality. For the purpose of imaging, only a thin inner layer of silica shell is labelled with Fluorescein isothiocyanate (FITC), leaving the surface chemistry of the outer unlabelled silica layer unaffected. The average dimensions of length (L) = 3.05 μm, diameter (D) = 0.32 μm, aspect

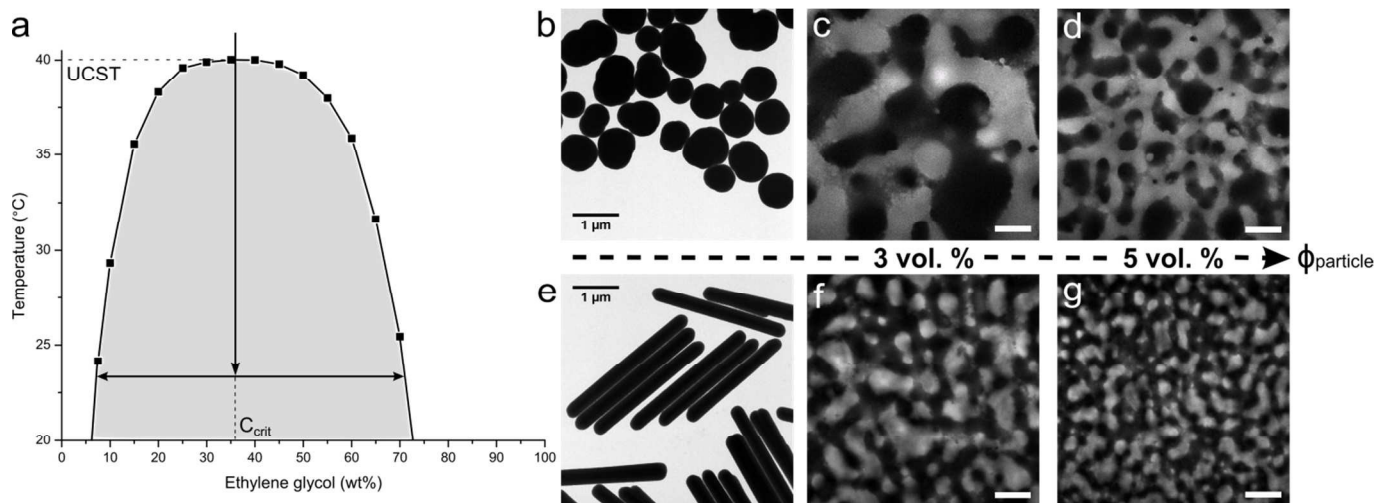

**Fig. 1** (a) The phase diagram of nitromethane (NM) and ethylene glycol (EG),<sup>19</sup> with an arrow roughly indicating the temperature quench applied in experiments; TEM images of the (b) spheres and (e) rods used to produce NM/EG bijels; the confocal images of NM/EG bijels stabilized by (c) 3vol.% and (d) 5vol.% spheres, respectively; the confocal images showing the bijels stabilized by (f) 3 vol.% and (g) 5vol.% rods. The scale bar is 50 micron.

ratio (AR) = 9.6 are determined by TEM e.g. image shown in **Figure 1e**. The TEM image of Stöber silica particles used for comparison is also presented in **Figure 1b**. These near-spherical particles have an average radius  $R = 0.37 \mu\text{m}$  and are labelled with Rhodamine B isothiocyanate (RITC).

To create rod surfaces with equal wetting characteristics with the two solvents, the surface chemistry is tuned via a silanization reaction between the outer layer of silica and hexamethyldisiloxane (HMDS).<sup>17</sup> To follow the changes in contact angle, bijel formation is attempted with every batch of modified rods using the quench route indicated by the vertical arrow in **Figure 1a**. The aim of these experiments is to pinpoint the optimum concentration of HMDS to give bijel formation; the best surface treatments give rise to the bijels shown in **Figure 1f,g**. These bijels were static and stable on the timescale of these experiments (at least 24 hours). The experimental details are available in Supplementary Information. It can be seen that, when increasing the particle concentration from 3 to 5 vol.%, rods take up more interfacial area, leading to smaller liquid domains, reflecting an earlier structural arrest of spinodal decomposition. For comparison, **Figure 1c,d** show the bijels prepared with spherical Stöber silica particles. Here, the EG-rich channel is observed using Fluorescein dye. We note that volume per particle ( $V_{particle}$ ) is nearly the same for the rods and spheres, and this allows us to make a direct comparison of the domain sizes. It is clearly seen that rod-stabilized bijels exhibit much smaller domain sizes for similar particle concentration (comparing, in **Figure 1**, image c & d with f & g, respectively). However, the particle shape does not result in an obvious change in domain shape. In water/2,6-lutidine bijels, the particle structure can remain intact after re-mixing of the liquids.<sup>9</sup> The resulting material was termed a ‘monogel’. 20 min of aging is the key step for monogel formation, which drives particles to overcome repulsive barrier into their primary van der Waals minimum. In contrast, successful monogel formation in NM/EG was here observed upon prolonged aging of samples. (Monogel formation has now also been observed in polymer-based bijels.<sup>20</sup>) The results presented in Figure S4 indicate that the monogel is eventually formed with 19-day aging treatment. This is similar to the observation for sphere-based NM/EG bijels [8], in which the solvation of the HMDS graft layer by deprotonated NM molecules is

regarded as a possible reason for an increased repulsive barrier. However, we still require a detailed understanding of why in NM/EG such long aging is required for monogel formation.


Next we consider the scaling of the domain size with particle concentration. In the following,  $\phi_{particle}$  refers to the volume fraction of rods (or spheres). For a fixed  $\phi_{particle}$ , the final domain size will depend solely on the effective area covered by the jammed layer of colloidal particles trapped at the interface. The situation can be approximated by a spherical droplet being fully covered by colloidal particles, which is contained within a liquid of a volume equal to that of the droplet.<sup>21</sup> This is similar to spinodal decomposition, since the volumes of the two phases are roughly equal; the droplet diameter ( $L$ ) represents the domain size. For the case of spherical particles that are neutrally wetted we find that  $L = 2vd_{sphere}(\phi_{sphere})^{-1}$  (1) where  $v$  is the packing fraction of the particles at the interface, and  $\phi_{sphere}$  = volume fraction of spheres. As observed qualitatively in **Figure 1**, this indeed shows that the domain size can be reduced by increasing the particle concentration. Additionally, decreasing the particle diameter offers an alternative route to smaller domains.<sup>17</sup> That the domain size indeed scales as  $L \propto \phi_{sphere}^{-1}$  has previously been demonstrated in experiments.<sup>3</sup>

Changing colloid shape from spheres to rods at fixed particle volume will change the above scaling relation. This reflects changes to both the area taken up by a single particle and the 2D packing fraction. For a clear comparison of the influence of particle shape alone, similar particle volume is important. Spheres with an equivalent volume per particle to the rods used would have a diameter of approximately 776 nm. With  $d_{sphere} = 750 \text{ nm}$ , the spheres used here are nearly perfect. The maximum packing fraction of spherocylinders of aspect ratio  $A$  on a flat interface (see Supplementary Information) is:  $\nu = [1 - (1 - \pi/4)/A]/[1 - (1 - \sqrt{3}/2)/A]$ . Obviously, the change in the area taken up by single particles also depends on the aspect ratio. For instance, a neutrally wetted cylinder takes up twice as much interfacial area when its aspect ratio is increased from 1 to 8 at fixed volume. Using the same scenario as described above for spheres, to approximate the relation between domain size and colloid concentration, for cylindrical particles



$L = \frac{3}{4} \nu d_{rod} (\phi_{rod})^{-1}$  (2) is found, where  $d_{rod}$  is the full width of a cylinder. Surprisingly, the particle aspect ratio only appears in the packing fraction.


To compare the pre-factors outlined above to the scaling of our bijels, we present a simple approach to quantify the domain size of created bijels via ImageJ software.<sup>22</sup> This approach involves extracting the domain size of the bijels from 2D Fourier transforms of the low magnification confocal images like those shown in **Figure 2a,b**. The dominant length scale in the sample is represented by a knee in the curve at the corresponding wave vector ( $q$ ). More details are given in the Supplementary Information, which demonstrates a reliable way for obtaining value of  $q_{knee}$ . The obtained domain sizes can be plotted against the inverse volume fraction for comparison. The graph in **Figure 2** shows a linear increase which agrees with the scaling relations. Fits through the origin give the slopes, and reveal a significantly faster reduction of the domain size for rod-stabilized bijels. For the spherical particles we take  $\nu = \frac{\pi}{2\sqrt{3}}$ , the maximum packing of discs on a plane, and the experimentally determined particle diameter; the relation (1) can then be compared for these two samples. In previous experiments order of magnitude agreement was obtained.<sup>3</sup> Of course, the pre-factor of the relation between  $L$  and  $\phi_{particle}$  depends on the shape of the domains, which was in this case approximated by a sphere. Other experimental factors introduce uncertainties including particle polydispersity, the fraction of particles trapped at the interface, and possible inhomogeneities in quench or particle distribution. Here, the slope found for spheres (1.44  $\mu\text{m}$ ) is in relatively good agreement with the value resulting from the relation (1) (1.36  $\mu\text{m}$ ) when using the current particle size. A similar result is found for a second batch of silica particles (labelled spheres 2).

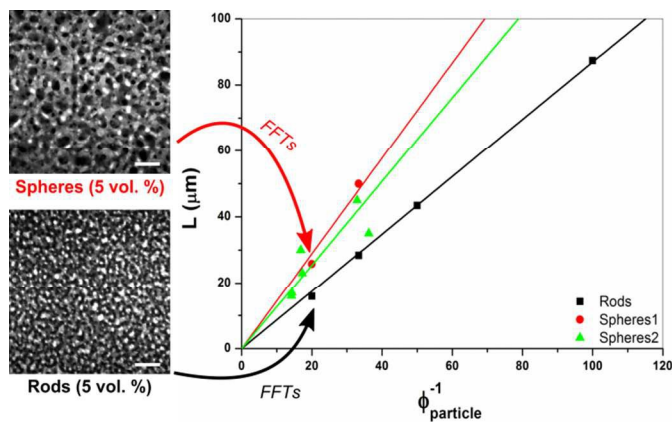

**Fig. 2** Low magnification confocal microscopy images of bijels stabilized by 5vol.% (a) spheres and (b) rods, respectively. Observed fluorescence is from (a) Nile Red in the NM-rich phase, and (b) Fluorescein in the EG-rich phase. The graph shows the domain sizes plotted as a function of  $\phi_{particle}^{-1}$ , fitted with a straight line through the origin. The scale bar is 100 micron. Note: spheres 1 and 2 are two batches of Stöber silica particles with less than 10% size difference.

According to the graph in **Figure 2**, plotting data against  $\phi_{colloids}^{-1}$  a slope of 0.87  $\mu\text{m}$  is found for rod-stabilized bijels, compared to 1.44  $\mu\text{m}$  for sphere-stabilized bijels. Based on the aspect ratio,  $\nu=0.99$  and  $d_{rod}$  determined with TEM, the relation (2) gives a value of 0.75  $\mu\text{m}$  for the slope. This demonstrates a larger discrepancy with the experimental result than for the sphere-stabilized bijels. The difference is unlikely to originate from the assumed  $\nu$  for sphere-

cylinders, as it can only be adjusted to lower values, resulting in a larger difference. The scaling relation suggests that  $\nu > 1$ . This could be related to the observation that, at the interface of the bijel, particles poke out and overlap. Their potential to reduce the interfacial area is thus not fully used, and the gain from changing particle shape is smaller than expected from simple geometrical arguments.

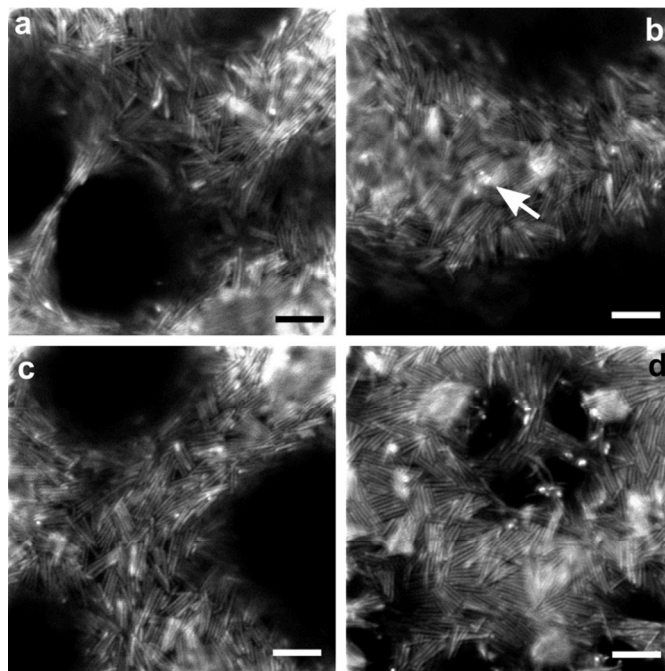

**Fig. 3** Selection of high magnification images (a-c) showing FITC fluorescence from the rods, of the 2vol.% sample, and high magnification, composite images (d) showing both FITC and Nile Red fluorescence, taken from the 5vol.% sample. The scale bar is 5 micron.

Our design of rods allows us to directly observe packing at the interface of the two continuous liquid domains. Images showing the packing of rods on droplets are provided in the SI. In the confocal images of the bijel with 2vol.% rods (**Figure 3(a-c)**), the rods can be seen via the FITC fluorescence of the inner shell. Individual rods can be distinguished due to the inner fluorescent shells being separated by the thicker, unlabelled outer silica layers. **Figure 3(d)** shows the confocal images of the bijels with 5vol.% rods using the combination of FITC fluorescence from the rods and Nile Red from the NM-rich phase which enhances the visualization of the rod packing. (Although combining channels reduces the visibility of gaps in the packing.) From these images, it is clear that there is no long-range translational or orientational ordering of the rods. On fluid necks there is some enhancement to rod alignment. This occurs both parallel and perpendicular to the length of the necks, which might well be related to whether a neck was stretched or compressed prior to structural arrest. We note that the ability of rods to align along a thinning neck results in some very thin liquid bridges (e.g. **Figure 3a**).<sup>18</sup> When the packing is studied more closely, it is found that several rods regularly form small side-by-side stacks, and significantly, often triangular gaps result from the random

orientation of these tightly-packed structural elements. We also occasionally observe some tiny bright dots (as highlighted in **Figure 3b**) which very likely indicate that some rods are sticking out of the interface and even are perpendicular to the interface.

It seems likely that rapid jamming is the main driving force behind the final arrangement of the rods. As a result the overall structure is mostly isotropic, and the packing contains many cases where particles are forced into energetically unfavourable arrangements. The latter includes flippers, and gives rise to gaps. Flippers have been observed for ellipsoidal particles at interfaces, just before a compressed monolayer buckles, and on droplets.<sup>13,23</sup> The situation during domain coarsening involves the compression of a monolayer of rods at a curved interface. It is easy to imagine a scenario where two rods collide head-on, but still at an angle due to the curved interface, one of them might well end up on top of the other, and be forced off the interface. Apparently an event somewhat like this probably results in flippers, as well as less extreme arrangements. While flat interfaces induce bistable arrangements of jammed rods, either parallel or perpendicular to the interface, here we find some rods tilted to an intermediate extent which might well be related to the curvature of the interface. Furthermore, as has been shown recently for magnetic rods perturbed by an applied magnetic field perpendicular to the interface,<sup>24</sup> flipping becomes more energetically expensive as the aspect ratio increases. Hence we believe that fewer flippers would be observed if we employed rods of even higher aspect ratio. This might mean that the interface separation would agree better with predictions at higher aspect ratios.

Naturally, the packing of the rods at the interface links to the scaling of the domain size with colloid concentration, as it determines how much of the interfacial area the rods effectively take up. Structural features such as the observed flippers, stacks and gaps are of importance here. Gaps would lower  $v$ , while particles sticking out of the interface would increase  $v$ . In both cases, the effect of the specific interfacial structuring on domain size scaling will be relatively small compared to the effect of changing the particle shape from spheres to rods. However, as discussed above, on a large scale, the shape of particles does not appear to play a significant role in changing the domain size of bijels. This reflects the overall isotropic organization of the rods at the interface, caused by a rapid jamming on the curved interface. Only on a smaller scale can the shape of the rods make a difference, where thin liquid bridges are a striking example. It appears that their ability to align does allow the stabilization of smaller necks.

## Conclusions

In this study, bijels were created with colloidal rods (aspect ratio  $\approx 10$ ) and spheres (aspect ratio 1). After describing in some detail the route towards the preparation of rod-stabilized bijels, the scaling of the domain size with colloid concentration was presented and discussed. Since, due to their shape, the rods take up a larger area of the interface, jamming occurs at lower interface separations than with the same volume fraction of spheres. Scaling relations based on simple geometrical arguments show reasonable qualitative agreement. No clear difference in domain shapes could be pointed out between the two counterparts. This demonstrated that, on a large scale, the type of bijel structure is not significantly altered by changing spherical particles into rods. Thus, a different domain-size scaling is the main structural effect.

After establishing this, the confocal imaging was employed to elucidate packing of rods. Several characteristic structural features

were identified. The packing contained side-by-side stacks of several particles, the formation of which could well have involved capillary interactions, judging from previous studies. Overall organization is isotropic due to a rapid jamming after phase separation, resulting in significant gaps where packing is frustrated, as well as some particles being partially ejected from the interface. In places very thin necks are observed, which are only a single rod wide. All of these features have consequences for the domain-size scaling. Particles flipping and being pushed off the interface undermines, if only slightly, the gain in packing efficiency given by changing spheres into rods.

## Acknowledgements

We are grateful to Andrew Schofield for synthesizing the spherical silica particles and to Katherine Rumble for providing data for Fig. 2. This work was supported by the Marie Curie Initial Training Network COMPLOIDS no. 234810 and EPSRC grant EP/J007404/1.

## Notes and references

<sup>a</sup> School of Physics and Astronomy, University of Edinburgh. Peter Guthrie Tait Road, Edinburgh, EH9 3FD, UK

\* Corresponding author P.S. Clegg (paul.clegg@ed.ac.uk)

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/c000000x/

- 1 M. E. Cates and P. S. Clegg, *Soft Matter*, 2008, **4**, 2132.
- 2 K. Stratford, R. Adhikari, I. Pagonabarraga, J. C. Desplat and M. E. Cates, *Science*, 2005, **309**, 2198.
- 3 E. M. Herzig, K. A. White, A. B. Schofield, W. C. K. Poon and P. S. Clegg, *Nat. Mater.*, 2007, **6**, 966.
- 4 H.-J. Chung, K. Ohno, T. Fukuda and R. J. Composto, *Nano Lett.*, 2005, **5**, 1878.
- 5 H. Firoozmand, B. S. Murray, and E. Dickinson, *Langmuir*, 2009, **25**, 1300.
- 6 M. Cui, T. Emrick, and T. P. Russell, *Science*, 2013, **342**, 460.
- 7 M. N. Lee and A. Mohraz, *Adv. Mater.* 2010, **22**, 4836.
- 8 M. N. Lee, J. H. J. Thijssen, J. A. Witt, P. S. Clegg and A. Mohraz, *Adv. Funct. Mater.*, 2013, **23**, 417.
- 9 E. Sanz, K. A. White, P. S. Clegg and M. E. Cates, *Phys. Rev. Lett.*, 2009, **103**, 255502.
- 10 L. Imperiali, C. Clasen, J. Fransaer, C. W. Macosko and J. Vermant, *Mater. Horiz.*, 2014, **1**, 139.
- 11 J. C. Loudet, A. Alsayed, J. Zhang and A. Yodh, *Phys. Rev. Lett.*, 2005, **94**, 018301.
- 12 E. P. Lewandowski, M. Cavallaro, L. Botto, J. C. Bernate, V. Garbin and K. J. Stebe, *Langmuir*, 2010, **26**, 15142.
- 13 M. G. Basavaraj, G. G. Fuller, J. Fransaer and J. Vermant, *Langmuir*, 2006, **22**, 6605.
- 14 F. Günther, F. Janoschek, S. Frijters and J. Harting, *Comput Fluids*, 2013, **80**, 184.
- 15 T. L. Cheng and Y. U. Wang, *J. Colloids Interf. Sci.*, 2013, **402**, 267.
- 16 F. Günther, S. Frijters and J. Hartings, *Soft Matter*, 2014, **10**, 4977.
- 17 J. W. Tavacoli, J. H. J. Thijssen, A. B. Schofield and P. S. Clegg, *Adv. Funct. Mater.*, 2011, **21**, 2020.
- 18 N. Hijnen and P. S. Clegg, *Chem. Mater.* 2012, **24**, 3449.

- 19 J. M. Sørensen, W. Arlt, in liquid-liquid Equilibrium Data Collection, (Eds: D. Behrens, R. Eckermann), Vol. 5, Part 1, Dechema, Frankfurt/Main, Germany, 1979, p29.
- 20 L. Bai, J. Fruehwirth, X. Cheng, C. W. Macosko, *Soft Matter*, *submitted* <http://arxiv.org/abs/1502.00165>.
- 21 E. M. Herzig, PhD thesis, University of Edinburgh, 2008, 112.
- 22 W. S. Rasband US National Institute of Health: Bethesda, Maryland, USA, 1997–2006; <<http://rsb.info.nih.gov/ij/>>.
- 23 B. Madivala, J. Fransaer and J. Vermant, *Langmuir*, 2009, **25**, 2718.
- 24 B. J. Newton, K. A. Brakke and D. M. A. Buzza, *Phys. Chem. Chem. Phys.*, 2014, **16**, 26051.