

# Soft Matter

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Cite this: DOI: 10.1039/xxxxxxxxxx

## Reconfigurable assembly of superparamagnetic colloids confined in thermo-reversible microtubes<sup>†</sup>

Ping Liu,<sup>a</sup> Julius W. J. de Folter,<sup>a,b</sup> Andrei V. Petukhov,<sup>a</sup> and Albert P. Philipse<sup>\*a</sup>Received Date  
Accepted Date

DOI: 10.1039/xxxxxxxxxx

www.rsc.org/journalname

Structural transformations of superparamagnetic colloids confined within self-assembled microtubes are studied by systematically varying tube-colloid size ratios and external magnetic field directions. A magnetic field parallel to microtubes may stretch non-linear chains like zigzag chains into linear chains. Non-parallel fields induce new structures including repulsive chains of single colloids, kinked chains and repulsive dimers, which are not observed for unconfined magnetic colloids in bulk. Formed colloidal structures are confirmed with model calculations which account for tube-colloid size ratio effects and their reconfigurability with field direction. Furthermore, structures are formed that allow controllable switching between a helical and non-helical state. All observed field-induced transformations in microtubes are reversible provided the microtubes are not completely filled with colloids. In addition, we demonstrate magnetic field-responsive 2D crystallization by extending control over colloidal configurations in single microtubes to multiple well-aligned microtubes.

### 1 Introduction

Magnetic colloidal assembly attracts interest because of potential applications for bioimaging, biosensing, photonic crystals, separation and drug delivery.<sup>1–8</sup> Recently non-linear magnetic assembly was reported for new types of magnetic colloids with uneven distributions of dipoles.<sup>9–16</sup> Examples of these colloids are asymmetric dumbbells with a magnetic “waist”, and paramagnetic colloidal peanuts; both types of non-spherical colloids may form chiral structures and zigzag chains in a homogeneous external magnetic field<sup>9,10,16</sup>. Interestingly, also colloidal spheres may assemble to zigzag or zipper chains in an external field, provided the magnetic dipole distribution inside the spheres is anisotropic. This magnetic anisotropy is found in Janus colloids and in spheres with off-centered magnetic cubes.<sup>11–13</sup> Besides that, the most intriguing phase of non-linear magnetic chains - helix can be fabricated by assembling paramagnetic spheres in a precessing magnetic field.<sup>17</sup>

The studies quoted above rely on the developments in colloid synthesis or the design of more complicated dynamic magnetic fields to achieve non-linear magnetic assembly. There clearly re-

mains a need for an efficient method to tune magnetic assembly. The aim of this paper is to report such a method based on the confinement of magnetizable spheres in thermo-reversible microtubes.

These microtubes self-assemble in a solution of sodium dodecyl sulfate (SDS) and  $\beta$ -cyclodextrin.<sup>18</sup> Our previous work has shown that they act as facile and versatile templates to make helical and other new colloidal structures by incorporating non-magnetic spherical and anisotropic colloids as reported in refs. 19,20. In comparison with our previous work we gain additional control over colloidal interactions and configurations which are switchable by a magnetic field and its orientations. The tubes (with or without incorporated colloids) reversibly melt and re-assemble upon heating and subsequent cooling of the aqueous solution. Such a dynamic, thermo-reversible tubular confinement of colloids clearly differs from static confinements such as carbon nanotubes, rigid channels, porous membranes, optical tweezer trappings and block copolymer cylinders.<sup>21–30</sup> The possibility to melt and form confining microtubes at will gives an additional parameter to tune magnetic colloid structures, in addition to the orientation of an external magnetic field and the ratio of colloid to tube diameter. It is also important that tube and colloids can be monitored in aqueous solution with optical microscopy such that structure formation and dissolution can be imaged *in situ* on single-particle level.

In this article, we investigate structure transformations of superparamagnetic colloids confined within microtubes upon applying a magnetic field, thereby examining the interplay between

<sup>a</sup>Van 't Hoff Laboratory for Physical and Colloid Chemistry, Debye Institute for Nanomaterials Science, Utrecht University, Padualaan 8, 3584CH, The Netherlands. Fax: +31 302533870; Tel: +31 302533518; E-mail: a.p.philipse@uu.nl

<sup>b</sup>Unilever Research and Development, Olivier van Noortlaan 120, 3133AT, Vlaardingen, The Netherlands.


<sup>†</sup> Electronic Supplementary Information (ESI) available: [1 movie showing thermo-reversible process upon magnetic field for superparamagnetic colloids inside microtubes]. See DOI: 10.1039/b000000x/

magnetic interactions and tubular confinement. We systematically vary tube-colloid size ratios and directions of external magnetic field. This strategy allows for the formation of a range of novel magnetic field-induced reconfigurable colloidal structures. A theoretical model is presented in the Appendix that accounts for experimentally observed attractive and repulsive colloidal configurations in parallel and perpendicular magnetic fields. In addition, the co-assembly of microtubes and magnetic colloidal chains, induced by applying a magnetic field before tube formation, is tracked by optical microscopy *in situ*. We anticipate that our study will further assist the development of advanced functional materials relying on controlled magnetic colloidal assembly.

## 2 Experimental

### 2.1 Materials


Sodium dodecyl sulfate (SDS, 99%) was purchased from Sigma-Aldrich and was used as received.  $\beta$ -cyclodextrin ( $\beta$ -CD) was bought from Sigma-Aldrich with water content of 14% and was dried before use. The typical morphology of superparamagnetic colloids used in this work is illustrated in Fig. 1. The core of the colloid contains well-separated superparamagnetic nanoparticles (NPs) of typical sizes between 5 and 15 nm inside a nonmagnetic material used in the synthesis or stabilization of the NPs. The core is surrounded by a shell of non-magnetic material (here silica or polystyrene). The surface of the colloid may have functionalization specific for each application. Detailed properties of superparamagnetic colloids are given in Table 1. Dynabeads (Life Technologies) with diameter 1.05  $\mu\text{m}$  were in stock concentration of 10 mg/mL. The smaller superparamagnetic particles (SiO<sub>2</sub>-MAG-S2560, 583 nm in diameter and PS-MAG-S1984-1, 506 nm in diameter, microParticles GmbH, Germany) were supplied in stock concentration of 25 mg/mL in water. In what follows the medium-size silica spheres will be denoted as "M-silica spheres" and the smallest polystyrene particles as "S-polystyrene spheres".

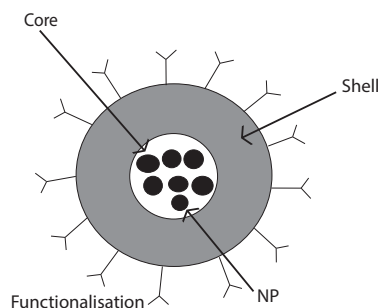

**Fig. 1** Cartoon showing the typical structure of superparamagnetic colloids composed of a core containing magnetic nano-particles and a functionalized shell.

The microtubes were synthesized following ref. 18. Desired amounts of SDS,  $\beta$ -CD and Millipore water were weighed into a vessel to give a mixture with a total concentration of SDS and  $\beta$ -CD of 10 wt% and a molar ratio between SDS and  $\beta$ -CD of 1:2. The mixture was heated to 60 °C to obtain a transparent,

isotropic solution, which was then cooled to room temperature to allow for the formation of microtubes in a viscous and turbid suspension. After staining 1 g of microtubes by 50  $\mu\text{L}$  of fluorescent dye (Nile Red) solution in acetone with concentration of 1 mg/mL, the microtubes were imaged in aqueous solution by confocal laser scanning microscopy (CLSM) in fluorescence mode. In Fig. 2a, these uniform tubes fill up the whole field of view, exhibiting diameters around 0.9  $\mu\text{m}$  (thus termed as microtubes). Fig. 2b shows the distribution of the tube diameters as collected from fluorescence images. By fitting with a Gaussian profile, a mean tube diameter of 884 nm with a standard deviation of 183 nm (22%) is obtained.

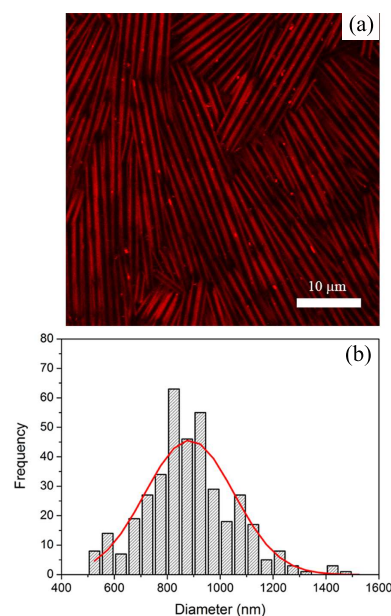

**Fig. 2** A CLSM image of microtubes (a) and histogram of the diameter distribution of the microtubes (b).

### 2.2 Co-assembly of the superparamagnetic colloids and microtubes

An aqueous suspension of superparamagnetic colloids was centrifuged at 1800 rpm for 15 min, followed by removal of the supernatant water. Typically, 0.1 g of microtube suspension was added to the centrifuge tube to give a final microtube/colloid mixture containing 5 wt% superparamagnetic colloids. The sample was heated to 60 °C to melt the microtubes and was sonicated to disperse the particles. Then the sample was cooled to room temperature. Upon cooling, the sample was gently rotated to avoid sedimentation of the particles.

### 2.3 *In situ* microscopy of magnetic field-induced colloidal assembly


The response of magnetic colloids inside microtubes was investigated by using a permanent magnet (NdFeB Magnet, 20\*20\*10 mm<sup>3</sup>, N42, 1.33 T), as illustrated in Fig. 3. The magnetic field strength when placing the magnet 1 cm away from the sample is roughly 50 mT as measured by a Gaussmeter, and correspond-

**Table 1** Properties of superparamagnetic colloids used in this work

Colloids type	Code	Diameters (nm)	Polydispersity	Iron content (ferrites/g dry solid)	Magnetization at 50 mT (emu/g)	Functionality	$\lambda^1$
Dynabeads	Dynabeads	1050	<3%	37%	12	Carboxyl	6939
Microparticles							
SiO <sub>2</sub> -MAG-S2560	M-silica spheres	583	2.7%	>30%	8	Plain	520
Microparticles							
PS-MAG-S1984-1	S-polystyrene spheres	506	3.8%	>30%	20	Plain	2157

<sup>1)</sup> magnetic coupling parameter defined in eq. (2) in Appendix.

ing magnetizations for each type of superparamagnetic colloids are listed in Table 1. The microtube/colloid mixture was usually placed in glass capillaries (Vitrocom, 0.10\*2.00\*50 mm<sup>3</sup>), with both ends sealed by UV-curing epoxy glue. The magnet was moved around the sample in the sample stage plane from a parallel position to a perpendicular position, as indicated in Fig. 3. In the parallel (perpendicular) position the magnetic field direction is parallel (perpendicular) to the long axis of the microtubes. As can be seen in Fig. 2a, microtubes orient in different directions. For imaging one patch of parallel oriented microtubes was selected. The magnet was placed at the parallel position at the beginning and then moved gradually to the perpendicular position. The structure transformations were monitored by a Nikon inverted optical microscope equipped with oil immersion 100x Nikon objective (numerical aperture is 1.4). Images were taken with a Lumenera InfinityX CCD camera. The thermal behavior of the samples was investigated using a Linkam THMS600 microscope heating stage.

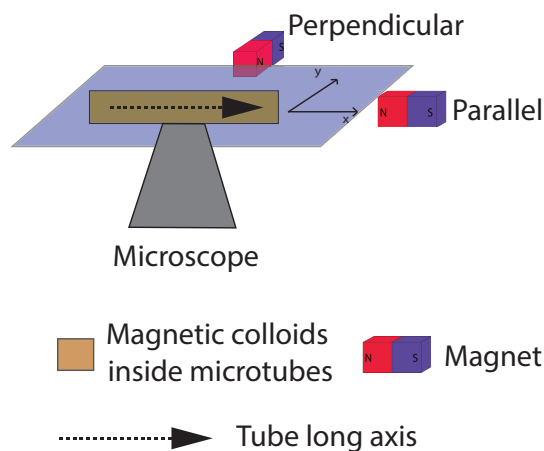

**Fig. 3** Schematic diagram of experimental setup for observation of the magnetic response of superparamagnetic colloids inside microtubes.

In the setup of Fig. 3, the magnetic field may be slightly inhomogeneous with a negligible effect on structure formation as can be shown as follows. Approximating the field generated by the magnet as the dipole field, the strongest gradient will be observed in the longitudinal direction with  $B \propto 1/r^3$ . Thus,  $\left| \frac{\Delta B}{B} \right| \sim 3 \left| \frac{\Delta r}{r} \right|$  can be expected, where  $B$  is the magnetic field strength in Tesla and  $r$  represents the distance between the observed region and the magnet. For instance, the percent of difference of the magnetic field in one typical image region of 50  $\mu\text{m}$  by 50  $\mu\text{m}$  when placing a magnet 1 cm away from the sample is around 1.5%. It indicates

that the effect of gradient is very small, so it will have little effect on the observed structures in an external magnetic field.

## 3 Results and Discussion


### 3.1 Magnetic response of tube-confined chain configurations

Since there is no exchange of colloids after complete colloid-in-tube assembly, each microtube can be regarded as an independent subsystem with its own colloidal chain configuration. Single chains, zigzag chains, zipper chains and helical chains can be obtained by tuning tube-colloid size ratios, similar to those observed in ref. 19. More importantly, these structures are dynamic, which allows us to further tune them by an external magnetic field. In what follows, a “parallel field” always denotes a magnetic field that is parallel to the microtube’s long axis. Similarly, a “perpendicular field” is always oriented perpendicular to the tube’s long axis, see also Fig. 3. The effect of a perpendicular field on tube-confined, fully magnetized spheres is calculated in the Appendix; these calculations will be used later to underpin observed structural transitions.

#### 3.1.1 Single chains.

Figure 4 shows optical microscopy images of structure transformations in magnetic field of a typical colloidal single chain composed of Dynabeads. The tube-colloid size ratio for Dynabeads inside microtubes is about 1.0, therefore single chains of Dynabeads are found throughout the sample volume, with schematic structure shown in Fig. 4a. Fig. 4(b-i) illustrate the continuous variations of structures by applying perpendicular and parallel fields. In Fig. 4b, colloids tend to close packing in zero field. If a perpendicular magnetic field is applied, neighbouring colloids repel each other immediately with maximum contact repulsion of  $\lambda$  which describes the dipole coupling parameter as defined in eq. 2 in the Appendix. It can be observed that the distance between colloids at both ends of the chain is larger than that between colloids in the middle part of the chain in Fig. 4(c-e). Because of the confinement effect of microtubes, colloids that are close to the end of the chain have more free space available and detach first. Then all space available in the microtubes is equally divided between neighbouring colloids to minimize the repulsion energy. Finally, upon application of a perpendicular magnetic field, colloids in the single chain transform from a close packing state to a repulsive state, where individual colloids detach and arrange.

Once a parallel magnetic field is applied by rotating the former perpendicular magnetic field, the dipole moments of superparamagnetic colloids all change direction and align with the long axis

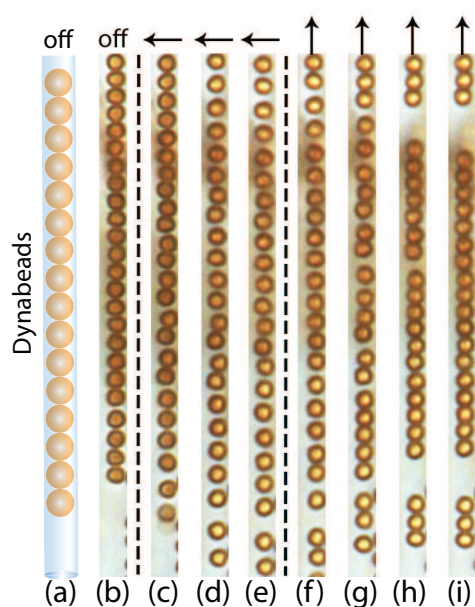


**Fig. 4** Schematic image of single chain pattern (a) and optical microscopy images of structure transformations of a colloidal single chain composed of superparamagnetic Dynabeads with size ratio of around 1.0 in zero-field (b) and in perpendicular (c-e, time intervals between each frame are 5 and 12 seconds from c to e respectively) and parallel magnetic fields(f-i, with time intervals of 1, 6 and 1 second between each frame from f to i respectively).

of the microtubes. Hence, the interactions between the colloids become attractive, with a maximum attraction of  $-2\lambda$  referring to Fig. 14 in Appendix. It is observed that the neighbouring colloids form close packed chains, as shown in Fig. 4(f-i). It is worth noting that these transformation images are taken with intervals of seconds which are indicated in the figure caption. The transition agrees with the model in the Appendix for a tube-colloid diameter ratio close to unity. Magnetic response of colloids of single chains in multiple well-aligned neighbouring tubes will be discussed in Section 3.3.

### 3.1.2 Zigzag chains.

To explore the magnetic response of chain configurations more complex than single chains, tube-colloid size ratios are tuned by incorporating smaller colloids into the same microtubes. Colloid-in-tube assembly from smaller spheres (M-silica spheres) with diameters of 583 nm displays mainly zigzag chain configurations, as shown in Fig. 5b. Fig. 5a shows the schematic zigzag configuration. When a parallel magnetic field is applied, part of the zigzag chain is firstly stretched into a single chain, and then the whole zigzag chain is completely stretched into a straight single chain (Fig. 5(c-e)). After removal of the magnetic field, colloids are subject to Brownian motion and re-assemble back into a zigzag chain configuration (Fig. 5(f-h)), accomplishing a reversible and magnetically switchable transformation from zigzag chains to single straight chains.


After zigzag chains are stretched into single chains (Fig. 6a) by a parallel field, the magnetic response of the stretched single chain upon rotating field from parallel to perpendicular step by

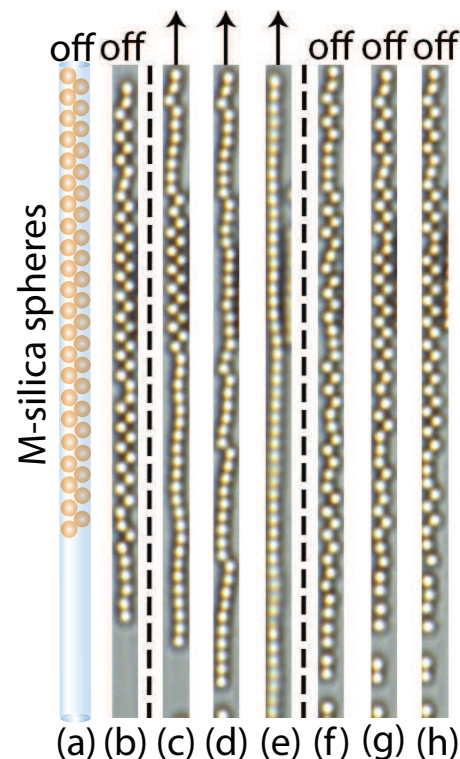

**Fig. 5** Schematic image of a zigzag chain pattern (a) and optical microscopy images of structure transformations of zigzag chain in zero-field (b) composed of superparamagnetic M-silica spheres with a diameter of 583 nm (the size ratio is around 1.52) in a parallel field (c-e) and without magnetic field (f-h).

step is illustrated in Fig. 6(b-d). In Fig. 6b, single chains become kinked chains when slowly rotating the magnetic field away from parallel position. Upon further rotation, kinked pieces become even shorter, as indicated in Fig. 6(c-d), and end up with tilted dimers under a perpendicular magnetic field (Fig. 6e).

Rotations of dipole moments of superparamagnetic colloids are not restricted and their preferential orientations are always parallel to the external magnetic field. Once zigzag chains are imposed by a parallel magnetic field, all the dipole moments in zigzag chains align along microtubes. Note that the angle between each dipole and the line connecting adjacent dipoles is appropriate to allow superparamagnetic colloids in zigzag configurations to become attractive in parallel field as indicated in Fig. 14 in the Appendix. The size ratio between M-silica spheres and microtubes is around 1.52, which corresponds to an attractive interaction of  $-1.19\lambda$  in our theoretical description. Therefore, zigzag chains are able to be stretched into single chains with head-to-tail attractive colloids. Upon slowly rotating parallel magnetic field to perpendicular direction, attractive chains of colloids cannot rotate as a whole due to the confinement imposed by the microtubes. Instead they transform into kinked chains. The length of kinked pieces is controlled by magnetic directions. In a perpendicular field, they reduce to tilted dimers. Configurations may vary depending on colloid concentration per microtube.

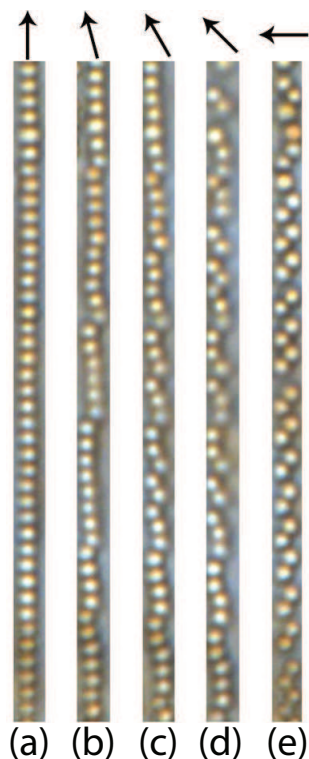


**Fig. 6** Optical microscopy images of structure transformations of a colloidal single chain stretched from zigzag chain composed of superparamagnetic M-silica spheres with a diameter of 583 nm in magnetic field with different directions.

### 3.1.3 From zipper chains to repulsive dimers.

Colloidal configurations in microtubes are very sensitive to tube-colloid size ratio. If it is increased to around 1.8 by using smaller colloids than those in zigzag chains, configurations like zipper chains or even helical chains could form.<sup>31</sup> Fig. 7 shows optical microscopy pictures of structure transformations of zipper chains of S-polystyrene spheres with diameter of 506 nm (size ratio is around 1.75) under a magnetic field. Upon application of a magnetic field, the configurational response of the colloids is different from the case of zigzag chains. Fig. 7c indicates that a parallel magnetic field does not stretch a zipper chain into a straight single chain. Upon rotating the magnetic field from parallel to perpendicular, superparamagnetic colloids in the zipper chain assemble into repulsive dimers, as shown in Fig. 7(d-e). Upon rotating the magnetic field back to parallel, these repulsive dimers arrange into a single chain (Fig. 7(f-i)). After removal of the magnetic field, single chains relax and re-assemble back into zipper chains (Fig. 7(j-l)).

In a zigzag chain, every colloid only has two contact colloids, and the interactions between these colloids are attractive in a parallel field. However, in a zipper chain, there are four contact colloids for one targeted colloid (Fig. 7m). In a parallel field, two of these contact colloids on the same side of targeted colloid impose strongest attractive interactions of  $-2\lambda$ , which is similar to single chains of Dynabeads in a parallel magnetic field. The other two adjacent colloids (indicated by blue colors in Fig. 7m) exert a weaker attraction force of  $-0.31\lambda$  to the targeted colloid, which

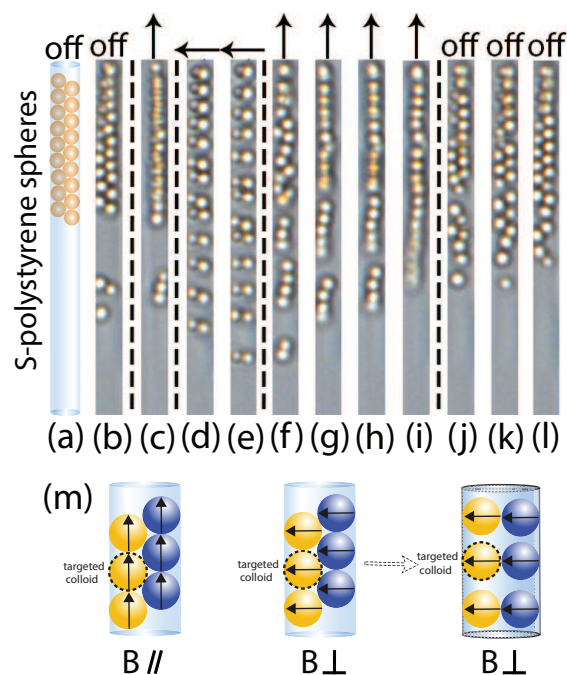

**Fig. 7** Schematic image of zipper pattern (a) and optical microscopy images of structure transformations of zipper chain composed of S-polystyrene spheres with a diameter of 506 nm (the size ratio is around 1.75) from a attractive chain in a parallel field (c, f-i) to repulsive dimers in a perpendicular field (d-e) and back to original zipper chain after removal of the field (j-l). Illustration of dipole interactions in parallel and perpendicular fields (m).


is marked for S-polystyrene spheres in a parallel field in Fig. 14. The weaker attraction force cannot overcome the strongest attraction, as a result, the zipper chains cannot be stretched into single chains in a parallel field.

Starting from the zipper configuration, we can employ a magnetic field to get new assembled structures like repulsive dimers upon application of a perpendicular field. Fig. 7(d-e) shows these adjacent colloids re-assemble into dimers in a perpendicular field. As shown in the Appendix, for tube-colloid size ratio larger than 1.58, the interactions between two contact colloids become attractive, which corresponds to an attraction of  $-0.67\lambda$  for S-polystyrene spheres in a perpendicular field (see Figs. 13 and 14). Fig. 7m also illustrates the dipole directions of four contact colloids with targeted colloids in a perpendicular field. The two colloids on the same side of targeted colloids has the strongest repulsive interactions of  $\lambda$ , which is similar to single chains of Dynabeads in a perpendicular magnetic field; the other two contact colloids impose an attraction interaction to the targeted colloid. The outcome of both repulsive and attraction interactions lead to formation of repulsive dimers in microtubes. Because molecular SDS/2 $\beta$ -CD microtubes form a soft confinement template, they could apparently be deformed somewhat to allow for nearly perpendicular orientation of the dimers in the microtubes. When applying a parallel magnetic field to these repulsive dimers, colloids assemble into single chain configurations. This is because repulsive dimers have more space than colloids in initial zipper chains, and they can re-orient themselves with confinement to

keep their dipole moment along the magnetic field. The head-to-tail dipole configuration is energetically favorable. However, the configuration of side-by-side two parallel dipoles is energetically unfavorable.<sup>32</sup> After removal of the magnetic field, colloids are subject to thermal motion and re-assemble back to the zipper chain configurations.

### 3.1.4 Reconfigurable helical chains.

In our previous work<sup>19</sup> we have shown that helical colloidal structures may be formed by confining isotropic spheres in tubular confinement at specific tube-colloid size ratios. Here we demonstrate that by using magnetic spheres helical structures may be formed that can be switched 'on' and 'off' from a helical to a non-helical state depending on the application of a magnetic field. Fig. 8 displays optical microscopy images of structure transformations of a colloidal helical chain (a) composed of S-polystyrene spheres with a diameter of 506 nm in a perpendicular field (c-f) and parallel field (g-i) and zero field (b, j-k).

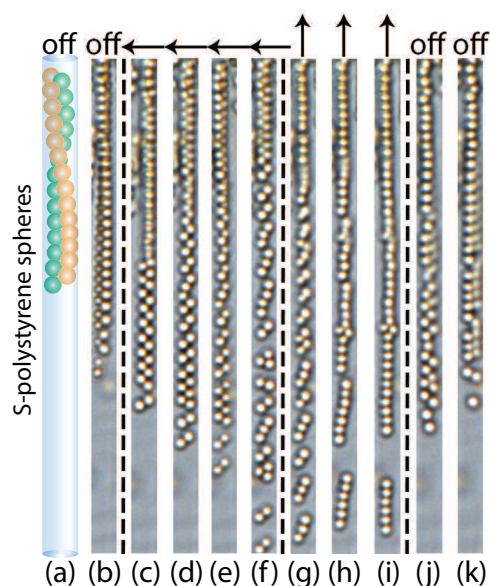

**Fig. 8** Optical microscopy images of structure transformations of a colloidal helical chain composed of superparamagnetic colloids with a diameter of 506 nm (the size ratio is around 1.75) under different magnetic conditions at different time.

For S-polystyrene spheres, the tube-colloid size ratio is around 1.75, typical chain configurations are zipper chains. However, due to polydispersity in diameters of S-polystyrene spheres (3.8%) and microtubes (22%), the tube-colloid size ratio has a quite wide propagating polydispersity which results in the range of 1.3 - 2.2. As simulated by Pickett *et al.*<sup>31</sup> for close-packed cylindrically confined hard spheres, when the tube-colloid size ratio is larger than 1.866, helical chains could be obtained. Although the helical chains are not dominant configurations for S-polystyrene spheres, in this work we mainly focus on colloids in subsystem of only one microtube. Therefore we could use helical chains made of S-polystyrene spheres to study the effect of size ratio on magnetic response of different chain configurations.


Upon application of a perpendicular magnetic field, helical

chains melt in time, as indicated in Fig. 8(c-f). Colloids at the end of the chain where they have more free space start to detach first, resulting in zigzag configuration in Fig. 8(c-d). Sequentially, the melting extends to the other end of the chain (f). Upon changing the direction of the applied magnetic field from perpendicular to parallel, a single chain of attractively interacting colloids is obtained as shown in Fig. 8i. After removal of the magnetic field, colloids relax and re-assemble into a helical configuration.

Figure 8a shows the schematic image of a helical chain in zero field. In this case the dipole moments of magnetic colloids cannot be regarded in the same plane. So once applying a magnetic field, the dipole interactions become more complicated than that for the planar arrangements discussed above such as single chains, zigzag chains and zipper chains. In the Appendix, we only take planar arrangements into account. For the 3D structures such as helices a more complicated model is needed that is subject of future work.

### 3.2 Comparison of magnetic behavior of magnetic colloids in microtubes and in bulk

In the previous Section 3.1, the focus was on magnetized spheres confined in tubes. Now we will compare these confined spheres to spheres free in solution. Fig. 9 compares field-induced structures of confined magnetic spheres (panels a-c) to structures formed by Dynabeads in an unconfined bulk solution (panels d-f).

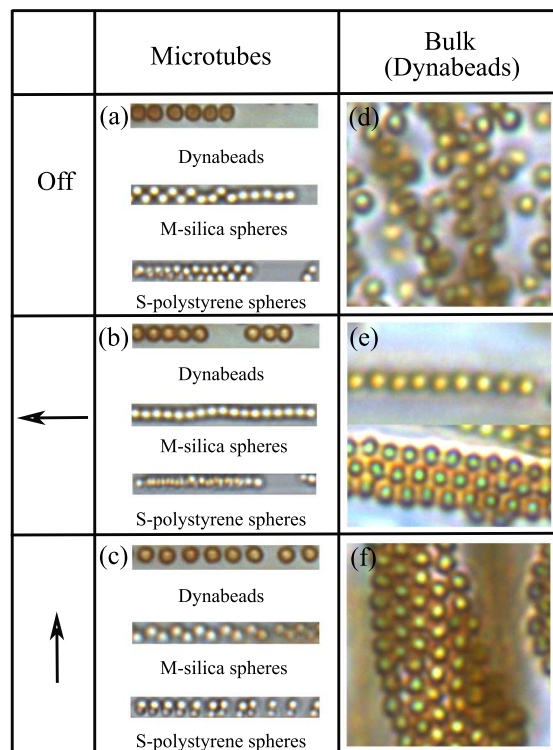

**Fig. 9** Comparisons of magnetic response of superparamagnetic colloids inside microtubes (for example, zigzag chain formation) and the response of unconfined Dynabeads in either parallel magnetic field or perpendicular field.

When free, unconfined spheres are magnetized, they form


chains that weakly attract each other<sup>33</sup> such that they eventually form sheets<sup>34,35</sup> (Fig. 9e). This sheet formation is prohibited by tube-confinement of chains because the already weak inter-chain attraction is further reduced by the tubes. This situation resembles that of dipolar magnetite chains incorporated in magnetotactic bacteria, an incorporation that also prohibits aggregation of magnetic chains, as discussed in detail in ref. 33. Here we also investigate the effect of magnetic field directions: magnetic chains and sheets rotate as a whole to keep the head-to-tail configuration, as can be seen in Fig. 9(e, f) for unconfined Dynabeads. However, confined magnetic chains cannot follow the magnetic field rotation because the confining rigid tubes form a densely packed highly viscous structure. This shows that microtubes are rigid and that they cannot be reoriented. The magnetic response of colloids in bulk matches other studies in literature. Faraudo *et al.*<sup>36,37</sup> have recently reported that the superparamagnetic particles can form single chains in a very short time after the application of the gradient magnetic field. When the magnetic field is kept for a longer time, magnetic chains drift until they come across another chain to form bundles. If the direction of the magnetic field is changed, these magnetic bundles rotate to keep head-to-tail configuration parallel to the field.

### 3.3 Magnetic response of colloids confined in parallel neighbouring tubes

So far we have only considered colloid confinement in a single tube; we now explore the interesting structures in neighbouring parallel tubes in which spheres from different tubes have a strong dipole interaction. The magnetic responses of Dynabeads in two and three neighbouring chains are shown in, respectively, Fig. 10(a-c) and Fig. 10(d-f). In the absence of a magnetic field, Dynabeads from different chains form a triangular lattice in 2D plane (Fig. 10(a, d)). When applying a perpendicular magnetic field to microtubes, Dynabeads in one microtube repel each other, as discussed in 3.1. However, interactions between colloids from different microtubes are attractive. The combination of these effects results in a square lattice arrangement of colloids in a 2D plane (Fig. 10(b,e)). In other words, square lattice is more stable in perpendicular field. In a unit of square lattice, colloids from the same microtubes are repulsive with each other, but the colloids from different microtubes are attractive. Both repulsive and attractive forces stabilize the square lattice. The co-existence of repulsive and attractive interactions is ascribed to the confinement effect from microtubes. The spacing between repulsive colloids may vary depending on the particle concentration in the microtubes. At the same time, these square lattices can reversibly transform back to triangular lattices by tuning the direction of the magnetic field from perpendicular to parallel (Fig. 10(c, f)), as illustrated in Fig. 10g. In this way parallel attractions are optimized while lateral repulsions are reduced.


### 3.4 Magnetic response of chains with different volume fractions of superparamagnetic colloids inside microtubes

The above cases are studied for the case that the subsystems of microtubes are not completely filled with colloids. So these have

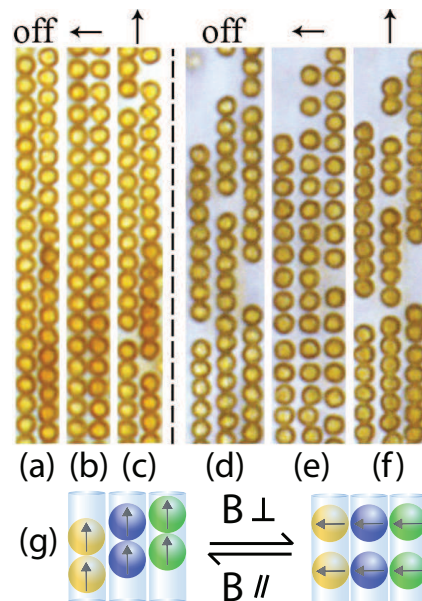

**Fig. 10** Optical microscopy images of magnetic response of superparamagnetic colloids (Dynabeads) in neighbouring well-aligned double microtubes (a-c) and triple microtubes (d-f) under either a parallel magnetic field or a perpendicular one. The cartoon in (g) illustrates the reversible transition from the triangular lattice in parallel field to the square lattice in perpendicular field.

space available for self-diffusion and respond to an applied magnetic field. However, when microtubes are completely filled with colloids, these colloid configurations cannot make any detectable changes. The differences of magnetic response of colloids in different microtubes with various volume fractions of colloids are shown in Fig. 11. The colloids in a single, zigzag and zipper chain configuration that cannot respond to a magnetic field due

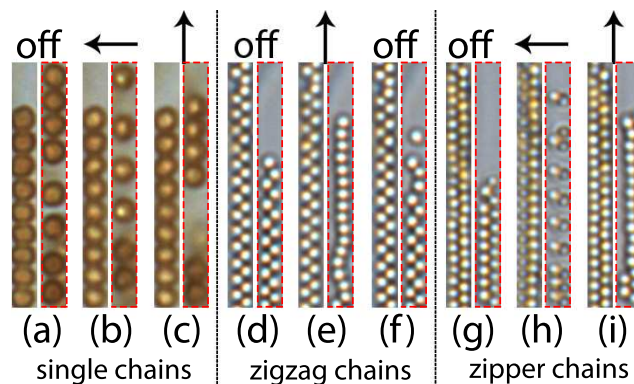

**Fig. 11** Optical microscopy images of different magnetic response of single chains (a-c), zigzag chains (d-f) and zipper chains (g-i) with different volume fractions under either parallel field or perpendicular field.

to a high volume fraction of colloids in the microtubes are shown in left parts in Fig. 11(a-i). Colloidal configurations that can respond to a magnetic field are shown in right parts and are typically found in microtubes with a lower colloid concentration. For the magnetic colloids in completely filled microtubes, although the induced magnetic dipole interactions are the same, they can-



not make any movement.<sup>32</sup> This is simply because particle concentration is too high in the same microtube such that the particles do not have space to move. For lower particle concentration, colloids from single chains (Fig. 11b) and zipper chains (Fig. 11h) form repulsive singles and dimers in a perpendicular field. Colloids in zigzag chains (Fig. 11e) become attractive and form single chains in a parallel magnetic field.


### 3.5 Application of magnetic field before microtubes formation

Up to now we have studied the assembled structures inside microtubes upon applying a magnetic field. Let us now discuss how the system responds to a thermal treatment since the microtubes are temperature-sensitive. It is possible to apply a magnetic field to a mixture of particles, SDS and  $\beta$ -CD before the formation of microtubes. We start with the structures of the Dynabeads inside the microtubes at room temperature and with the magnetic field along the long axis of the microtubes in the optical microscopy image domain (Fig. 12A). As the temperature is increased, the tubes start to melt and some of the Dynabeads are released from the microtubes. Because the magnetic field is applied, the colloids form chains after melting of the microtubes, as shown in Fig. 12B. At 45°C, the microtubes disappear and the solution becomes isotropic, during which the viscosity decreases dramatically from a very viscous state (can be distinguished by naked eye) to a low-viscosity fluid like water. In Fig. 12(C, D), it can be seen clearly that as the Dynabeads chains are kept at the high temperature for a longer time, the length of the Dynabead chains can be extended further. At that point, the sample is cooled down at the fastest speed (5°C/min); then the long Dynabeads chains fall apart into shorter pieces which could still be incorporated into the microtubes. And finally the structure ends up with relatively longer chains in the microtubes than the starting state, see Fig. 12F.

The magnetic behavior of Dynabead before microtube formation is the same as of superparamagnetic colloids suspensions under magnetic fields. Here we tried to cool down the system before the formation of bundles of Dynabeads, even though the bundles of two chains could also be seen in Fig. 12D. For more details, see the movie directly recorded with optical microscopy (see Movie 1 in ESI†). Note that long chains cannot be incorporated into the microtubes. Instead, they break apart into smaller chains by the self-assembly force exerted by the forming of microtubes during the cooling process.

## 4 Conclusions

We have studied the reversible magnetic response of superparamagnetic colloids confined in self-assembled microtubes and identified new morphologies including zigzag chains, zipper chains, helical chains, field-induced kinked chains and repulsive dimers. Straight chains can be transformed into a repulsive chain of separate colloids upon application of a perpendicular magnetic field. Zigzag chains can be stretched directly by a parallel magnetic field into linear chain configurations, which is not the case for zipper and helical chains. The latter can only be stretched in a parallel

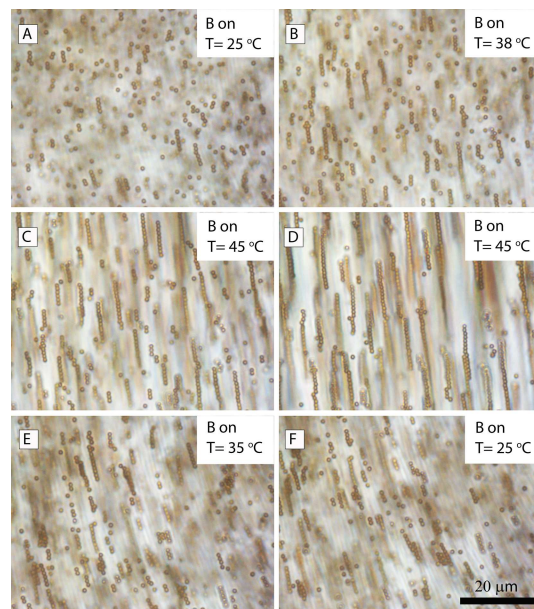

**Fig. 12** Optical microscopy images of melting and cooling processes of magnetic colloids (Dynabeads) inside the microtubes in a magnetic field parallel to the microtubes.

field after applying a perpendicular field. Stretched single chains may form kinked chains in a rotating magnetic field. In a perpendicular field, these chains may transform into repulsive dimers, as is also the case for zipper chains. All observed field-induced transformations in confinement clearly differ from those in a bulk suspension of the magnetizable colloids. To have tunable structures, the microtubes should not be completely filled with magnetic colloids. The colloidal configurations observed under the application of a parallel or perpendicular magnetic field are underpinned by model calculations which confirm that tube-colloid size ratio strongly influences the magnetic interactions between colloids in 1D confinement.

We have extended one microtube system to multiple well-aligned microtubes system to achieve magnetic field tunable 2D crystallization. We have also exploited the thermo-reversibility of microtube self-assembly to steer the assembly of magnetic colloidal chains: when applying a magnetic field before formation of microtubes, the assembly of microtubes tears apart magnetic chains into shorter fragments to have them incorporated inside, which is studied *in situ* under optical microscopy.


In this study we have demonstrated additional control over colloidal structures by facile, reconfigurable self-assembly. This is achieved in a thermo-reversible matrix of confining microtubes self-organized from readily available molecular species. Colloidal configurations can be tuned by colloid concentration, tube-colloid size ratio and the application of magnetic fields with different directions. The combination of confinement and the magnetic field response of the colloids results in novel structures that can deliberately be switched 'on' and 'off'. For instance, magnetic spheres may assemble into reversible helical structures that can be activated or deactivated to a non-helical state depending on the application of a magnetic field. Externally controlled formation and

disruption of targeted colloidal configurations may open new directions for data storage applications.

## Appendix

### Effect of tube-colloid size ratio on magnetic interactions of tube-confined superparamagnetic spheres

Consider two magnetisable spheres with diameter  $\sigma$  that are permanently magnetized by an external magnetic field  $\vec{B}$ ; the spheres are confined in a tube with diameter  $D$  and the field is perpendicular to the tube (Fig. 13). We ask for the interaction energy for the two spheres at contact, as a function of the tube diameter  $D$  or - more precisely - as a function of the ratio  $D/\sigma$ .

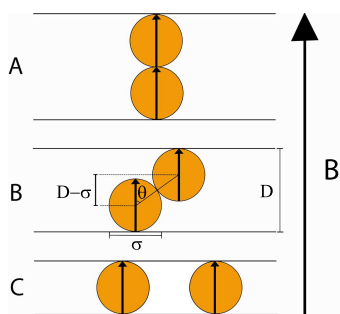

**Fig. 13** Magnetic spheres are magnetized to full saturation by a permanent magnetic field  $\vec{B}$  perpendicular to a tube that confines the spheres. When the tube diameter  $D$  equals twice the orange sphere diameter  $\sigma$ , the two spheres are in the head-to-tail configuration (A) with maximal attraction. Upon decreasing the tube diameter the attraction decreases (B) until maximal repulsion is reached when  $D = \sigma$  (C).

The interaction energy between two permanent dipoles with equal magnetic moments  $\mu$  at a center-to-center distance  $r$  is

$$\frac{V(\vec{r}, or)}{kT} = \lambda \left(\frac{\sigma}{r}\right)^3 [\hat{\mu}_1 \cdot \hat{\mu}_2 - 3(\hat{\mu}_1 \cdot \hat{r})(\hat{\mu}_2 \cdot \hat{r})]. \quad (1)$$

Here

$$\lambda = \frac{\mu_0 \mu^2}{4\pi kT \sigma^3} \quad (2)$$

is the dipolar coupling parameter, comprising the thermal energy  $kT$  and the magnetic vacuum permeability  $\mu_0$ . The values of  $\lambda$  for superparamagnetic colloids used in this study are listed in Table 1. In (1) “or” represents the orientations of the two dipoles specified by the unit vectors  $\hat{\mu}_1$  and  $\hat{\mu}_2$ ;  $\hat{r}$  is the unit vector of the center-to-center vector  $\vec{r}$ . For magnetic moments that are always parallel as in Fig. 13, the interaction (1) simplifies to

$$\frac{V(\vec{r}, \theta)}{kT} = \lambda \left(\frac{\sigma}{r}\right)^3 (1 - 3\cos^2\theta), \quad (3)$$

where  $\theta$  is the angle between  $\vec{\mu}$  and  $\vec{r}$  (Fig. 13). On inspection of Fig. 13B we realize that

$$\cos\theta = \frac{D - \sigma}{\sigma} \quad (4)$$

such that the interaction at contact ( $r = \sigma$ ) becomes

$$\frac{V}{kT} = \lambda \left[ 1 - 3 \left( \frac{D}{\sigma} - 1 \right)^2 \right]; \quad 1 \leq \frac{D}{\sigma} \leq 2. \quad (5)$$

This is the contact interaction as a function of the tube-sphere ratio  $D/\sigma$ . From (5) we find the maximal attraction

$$\frac{V}{kT} = -2\lambda, \quad \text{for } \frac{D}{\sigma} = 2 \quad (6)$$

and the maximal contact repulsion when the tube tightly confines the spheres

$$\frac{V}{kT} = \lambda, \quad \text{for } \frac{D}{\sigma} = 1. \quad (7)$$

From (5) one also easily verifies when the contact interaction is zero (Fig. 14)

$$\frac{V}{kT} = 0, \quad \text{for } \frac{D}{\sigma} = 1 + \sqrt{\frac{1}{3}} \approx 1.58. \quad (8)$$

Note that for a large coupling constant  $\lambda \gg 1$ , the two spheres will jump into contact when the tube diameter increases, or spring apart when the tube decreases, upon passing  $D/\sigma = 1.58$ . Note also that the amount of energy  $\Delta V$  that can be gained in going from purely-repulsive side-to-side configuration ( $D = \sigma$ ) to attractive head-to-tail configuration ( $D = 2\sigma$ ) is

$$\frac{\Delta V}{kT} = \frac{V(\sigma)}{kT} - \frac{V(2\sigma)}{kT} = 3\lambda. \quad (9)$$

This implies that for  $\lambda \gg 1$  repulsive spheres exert a considerable expansive force on the tube wall.

The smaller magnetic spheres used here have diameters of 506 nm (S-polystyrene spheres) and 583 nm (M-silica spheres); for a tube with  $D = 884$  nm (see Fig. 2) this implies  $D/\sigma = 1.75$  and  $D/\sigma = 1.52$ . The contact interactions in a perpendicular field are

$$\frac{V}{kT} = -0.67\lambda, \quad \text{for } \frac{D}{\sigma} = 1.75$$

$$\frac{V}{kT} = 0.20\lambda, \quad \text{for } \frac{D}{\sigma} = 1.52$$

Thus, for the larger spheres we are close to the zero point in a perpendicular field, as shown by a solid line in Fig. 14.

In a parallel field, the magnetic interaction energy can be examined in the same manner as for a perpendicular field. We only need to change the angle  $\theta$  between  $\vec{\mu}$  and  $\vec{r}$  into  $90^\circ - \theta$ . Then the eq. (3) and eq. (5) can be rewritten as

$$\frac{V(\vec{r}, \theta)}{kT} = \lambda \left(\frac{\sigma}{r}\right)^3 (1 - 3\sin^2\theta), \quad (10)$$

$$\frac{V}{kT} = \lambda \left[ -2 + 3 \left( \frac{D}{\sigma} - 1 \right)^2 \right]; \quad 1 \leq \frac{D}{\sigma} \leq 2. \quad (11)$$

Figure 14 also shows the sketch of the magnetic contact energy in a parallel field, indicated by a dashed line. From (11) we find the maximal attraction

$$\frac{V}{kT} = -2\lambda, \quad \text{for } \frac{D}{\sigma} = 1 \quad (12)$$

and the maximal contact repulsion when the tube tightly confines the spheres in a close-packed configuration

$$\frac{V}{kT} = \lambda, \quad \text{for } \frac{D}{\sigma} = 2. \quad (13)$$


From (11) one also easily verifies when the contact interaction is zero (Fig. 14)

$$\frac{V}{kT} = 0, \quad \text{for} \quad \frac{D}{\sigma} = 1 + \sqrt{\frac{2}{3}} \approx 1.82. \quad (14)$$

The smaller magnetic spheres used here have diameters of 506 nm (S-polystyrene spheres) and 583 nm (M-silica spheres); for a tube with  $D = 884$  nm this implies  $D/\sigma = 1.75$  and  $D/\sigma = 1.52$ . The interactions in a parallel field are:

$$\frac{V}{kT} = -0.31\lambda, \quad \text{for} \quad \frac{D}{\sigma} = 1.75$$

$$\frac{V}{kT} = -1.19\lambda, \quad \text{for} \quad \frac{D}{\sigma} = 1.52$$

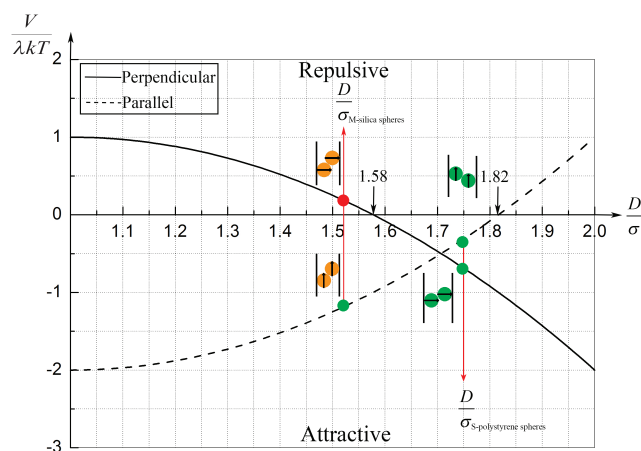

**Fig. 14** Sketch of the magnetic contact interaction from eq. (5) and eq. (11); the interaction is zero at  $D/\sigma = 1.58$  and  $1.82$ . In a perpendicular field (solid line), at larger  $D/\sigma$ , the spheres attract whereas below this zero point the spheres repel. In a parallel field (dashed line), at larger  $D/\sigma$ , the spheres repel whereas below this zero point the spheres attract.

## Acknowledgement

P. L. is supported by a scholarship under State Scholarship Fund (File No. 201206920001) from the Chinese government.

## References

- R. M. Erb, H. S. Son, B. Samanta, V. M. Rotello and B. B. Yellen, *Nature*, 2009, **457**, 999–1002.
- G. Friedman and B. Yellen, *Curr. Opin. Colloid Interface Sci.*, 2005, **10**, 158–166.
- D. Jańczewski, Y. Zhang, G. K. Das, D. K. Yi, P. Padmanabhan, K. K. Bhakoo, T. T. Y. Tan and S. T. Selvan, *Microsc. Res. Tech.*, 2011, **74**, 563–576.
- M. Wang, L. He, S. Zorba and Y. Yin, *Nano Lett.*, 2014, **14**, 3966–3971.
- J. Ge, Y. Hu and Y. Yin, *Angew. Chem. Int. Ed.*, 2007, **119**, 7572–7575.
- O. Velev and E. Kaler, *Langmuir*, 1999, **15**, 3693–3698.
- O. D. Velev and S. Gupta, *Adv. Mater.*, 2009, **21**, 1897–1905.
- A. Pal, V. Malik, L. He, B. H. Ern e, Y. Yin, W. K. Kegel and A. V. Petukhov, *Angew. Chem. Int. Ed.*, 2015, **54**, 1803–1807.
- D. Zerrouki, J. Baudry, D. Pine, P. Chaikin and J. Bibette, *Nature*, 2008, **455**, 380–382.
- S. H. Lee and C. M. Liddell, *Small*, 2009, **5**, 1957–1962.
- J. Yan, M. Bloom, S. C. Bae, E. Luijten and S. Granick, *Nature*, 2012, **491**, 578–581.
- S. K. Smoukov, S. Gangwal, M. Marquez and O. D. Velev, *Soft Matter*, 2009, **5**, 1285–1292.
- S. Sacanna, L. Rossi and D. J. Pine, *J. Am. Chem. Soc.*, 2012, **134**, 6112–6115.
- J. Ge, Y. Hu, T. Zhang and Y. Yin, *J. Am. Chem. Soc.*, 2007, **129**, 8974–8975.
- L. He, Y. Hu, H. Kim, J. Ge, S. Kwon and Y. Yin, *Nano Lett.*, 2010, **10**, 4708–4714.
- G. Singh, H. Chan, A. Baskin, E. Gelman, N. Reprin, P. Kr al and R. Klajn, *Science*, 2014, **345**, 1149–1153.
- N. Casic, N. Quintero, R. Alvarez-Nodarse, F. G. Mertens, L. Jibuti, W. Zimmermann and T. M. Fischer, *Phys. Rev. Lett.*, 2013, **110**, 168302.
- L. Jiang, Y. Peng, Y. Yan, M. Deng, Y. Wang and J. Huang, *Soft Matter*, 2010, **6**, 1731–1736.
- L. Jiang, J. W. J. de Folter, J. Huang, A. P. Philipse, W. K. Kegel and A. V. Petukhov, *Angew. Chem. Int. Ed.*, 2013, **52**, 3364–3368.
- J. W. J. de Folter, P. Liu, L. Jiang, A. Kuijk, H. E. Bakker, A. Imhof, A. van Blaaderen, J. Huang, W. K. Kegel, A. P. Philipse and A. V. Petukhov, *Part. Part. Syst. Charact.*, 2015, **32**, 313–320.
- Y. Yin and Y. Xia, *J. Am. Chem. Soc.*, 2003, **125**, 2048–2049.
- B. Gates, Y. Yin and Y. Xia, *Chem. Mater.*, 1999, **11**, 2827–2836.
- J. H. Moon, S. Kim, G.-R. Yi, Y.-H. Lee and S.-M. Yang, *Langmuir*, 2004, **20**, 2033–2035.
- A. N. Khlobystov, D. A. Britz, A. Ardavan and G. A. D. Briggs, *Phys. Rev. Lett.*, 2004, **92**, 245507.
- I. Kretschmar and J. H. K. Song, *Curr. Opin. Colloid Interface Sci.*, 2011, **16**, 84–95.
- G.-R. Yi, T. Thorsen, V. N. Manoharan, M.-J. Hwang, S.-J. Jeon, D. J. Pine, S. R. Quake and S.-M. Yang, *Adv. Mater.*, 2003, **15**, 1300–1304.
- T. O. Skinner, H. M. Martin, D. G. Aarts and R. P. Dullens, *Soft Matter*, 2013, **9**, 10586–10591.
- A. V. Straube, A. A. Louis, J. Baumgartl, C. Bechinger and R. P. Dullens, *EPL Europhys. Lett.*, 2011, **94**, 48008.
- A. V. Straube, R. P. Dullens, L. Schimansky-Geier and A. A. Louis, *J. Chem. Phys.*, 2013, **139**, 134908.
- S. Sanwaria, A. Horechyy, D. Wolf, C.-Y. Chu, H.-L. Chen, P. Formanek, M. Stamm, R. Srivastava and B. Nandan, *Angew. Chem. Int. Ed.*, 2014, **53**, 9090–9093.
- G. T. Pickett, M. Gross and H. Okuyama, *Phys. Rev. Lett.*, 2000, **85**, 3652.
- R. Paranjpe and H. Elrod, *J. Appl. Phys.*, 1986, **60**, 418–422.
- A. P. Philipse and D. Maas, *Langmuir*, 2002, **18**, 9977–9984.

- 34 V. Malik, A. V. Petukhov, L. He, Y. Yin and M. Schmidt, *Langmuir*, 2012, **28**, 14777–14783.
- 35 M. Klokkenburg, B. H. Ern , J. D. Meeldijk, A. Wiedenmann, A. V. Petukhov, R. P. Dullens and A. P. Philipse, *Phys. Rev. Lett.*, 2006, **97**, 185702.
- 36 J. Faraudo and J. Camacho, *Colloid Polym. Sci.*, 2010, **288**, 207–215.
- 37 J. Faraudo, J. S. Andreu and J. Camacho, *Soft Matter*, 2013, **9**, 6654–6664.


## Reconfigurable Assembly of Superparamagnetic Colloids Confined in Thermo-reversible Microtubes

Ping Liu, Julius W. J. de Folter,<sup>†</sup> Andrei V. Petukhov, and Albert P. Philipse<sup>\*</sup>

*Van 't Hoff Laboratory for Physical and Colloid Chemistry, Debye Institute for Nanomaterials Science, Utrecht University, Padualaan 8, 3584CH, The Netherlands.*

E-mail: A.P.Philipse@uu.nl

Combination of confinement and external magnetic field results in switchable structure formation of magnetizable colloidal spheres.

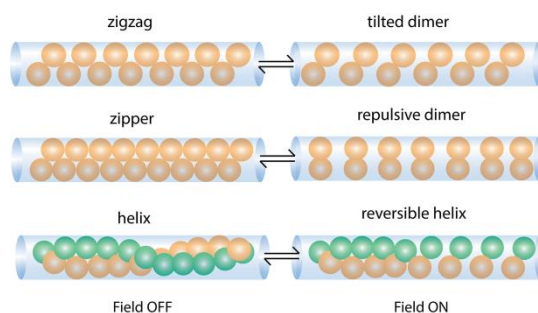

<sup>†</sup> Present Address: Unilever Research and Development, Olivier van Noortlaan 120, 3133AT, Vlaardingen, The Netherlands.

<sup>\*</sup> To whom correspondence should be addressed