

# Soft Matter

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



## FULL PAPER SUBMISSION

*Where physics meets chemistry meets biology for fundamental soft matter research*

2014 Impact factor: **4.029**

[www.rsc.org/softmatter](http://www.rsc.org/softmatter)

*Soft Matter* has a global circulation and interdisciplinary audience with a particular focus on the interface between physics, biology, chemical engineering, materials science and chemistry.

The following paper has been submitted to *Soft Matter* for consideration as a **full paper**.

*Soft Matter* aims to publish **high quality** papers reporting on the generic science underpinning the properties, applications, and phenomena of soft matter. The primary criterion for acceptance of a contribution for publication is that it must report high-quality new science and make a significant contribution to its field. *Soft Matter* is an **interdisciplinary** journal and suitable papers should cross disciplines or be highly significant within the field from which they originate.

**Routine or incremental** work, however competently researched and reported, should not be recommended for publication if it does not meet our expectations with regard to novelty and impact.

Thank you for your effort in reviewing this submission. It is only through the continued service of referees that we can maintain both the high quality of the publication and the rapid response times to authors.

We would greatly appreciate if you could review this paper in **ten days**. Please let us know if that will not be possible. Please support all comments with scientific justifications or we may be unable to use your report/ask for extra feedback.

Once again, we appreciate your time in serving as a reviewer. To acknowledge this, the RSC offers a **25% discount** on its books: <http://www.rsc.org/Shop/books/discounts.asp>. Please also consider submitting your next manuscript to *Soft Matter*.

Best wishes,

Nicola Wise, Executive Editor, *Soft Matter*

# Ion specific effects on the stability of layered double hydroxide colloids

Marko Pavlovic,<sup>a</sup> Robin Huber,<sup>a</sup> Monika Adok-Sipiczki,<sup>a</sup> Corinne Nardin<sup>a,b</sup> and Istvan Szilagyi<sup>a\*</sup>

<sup>a</sup> *Department of Inorganic and Analytical Chemistry, University of Geneva, 30 Quai Ernest-Ansermet, CH-1205 Geneva, Switzerland*

<sup>b</sup> *Institut des Sciences Analytiques et de Physicochimie pour l'Environnement et les Matériaux, Université de Pau et des Pays de l'Adour, 2 Avenue du Président Angot, F-64053 Pau, France*

\* Corresponding author. E-mail: [istvan.szilagyi@unige.ch](mailto:istvan.szilagyi@unige.ch). Phone: + 41 22 3796031.

## Abstract

Positively charged layered double hydroxide particles composed of  $\text{Mg}^{2+}$  and  $\text{Al}^{3+}$  layer-forming cations and  $\text{NO}_3^-$  charge compensating anions (MgAl- $\text{NO}_3$ -LDH) were synthesized and the colloidal stability of their aqueous suspensions was investigated in the presence of inorganic anions of different charges. The formation of the layered structure was confirmed by X-ray diffraction, while the charging and aggregation properties were explored by electrophoresis and light scattering. The monovalent anions adsorb on the oppositely charged surface to a different extent according to their hydration state leading to the  $\text{Cl}^- > \text{NO}_3^- > \text{SCN}^- > \text{HCO}_3^-$  order in surface charge densities. The ions on the right side of the series induce aggregation of the MgAl- $\text{NO}_3$ -LDH particles at lower concentrations, whereas in the presence of the left ones, the suspensions are stable even at higher salt levels. Adsorption of the multivalent anions gave rise to charge neutralization and charge reversal at appropriate concentrations. For some di, tri and tetravalent ions, the charge reversal resulted in restabilization of the suspensions in the intermediate salt concentration regime. Stable samples were also observed at low salt levels. Particle aggregation was fast near the charge neutralization point and at high concentrations. These results, which evidence the colloidal stability of MgAl- $\text{NO}_3$ -LDH in the presence of various anions, are of prime fundamental interest. These are also critical for applications to develop stable suspensions of primary particles for water purification processes, being the aim the removal of similar anions by ion exchange.



## Introduction

Layered double hydroxides (LDHs) are anionic clays composed of mixed positively charged lamellar hydroxides of divalent (e.g.,  $\text{Mg}^{2+}$ ,  $\text{Zn}^{2+}$  or  $\text{Ca}^{2+}$ ) and trivalent (e.g.,  $\text{Al}^{3+}$ ,  $\text{Fe}^{3+}$  or  $\text{Cr}^{3+}$ ) metal ions with charge compensating anions between the layers.<sup>1</sup> LDH particles and their composite materials are widely used in energy storage,<sup>2,3</sup> medical treatments,<sup>4-6</sup> coating,<sup>7</sup> catalysis<sup>8-10</sup> and removal of water pollutants.<sup>11-13</sup> For the latter application, their relatively high anion exchange capacity is utilized to capture various types of anions (e.g.,  $\text{NO}_3^-$ ,  $\text{SO}_4^{2-}$ ,  $\text{SeO}_4^{2-}$ ,  $\text{PO}_4^{3-}$  and  $\text{AsO}_4^{3-}$ ) during water purification processes. Ion exchange can take place by intercalation between the layers and also by adsorption on the particle surface. To achieve high efficiencies of these procedures, stable LDH suspensions containing primary particles are required during the ion exchange process. In addition, the particles have to be aggregated at a later stage for their facile removal from the reaction mixture. The effect of anions on the colloidal stability thus needs to be comprehensively understood to control particle aggregation.

The classical theory developed for aqueous suspensions of charged colloidal particles by Derjaguin, Landau, Verwey and Overbeek (DLVO) has proven to be suitable to predict colloidal stability in the presence of electrolytes.<sup>14,15</sup> It states that the acting interparticle force is the superposition of repulsive double layer and attractive van der Waals forces. The first one originates from the overlap of the electrical double layers forming around the charged particles dispersed in a salt solution. Its magnitude weakens with increasing the ionic strength due to the screening effect of the counterions on the surface charge. The attractive van der Waals forces are independent of the electrolyte concentration and only depend on the size and composition of the particles. Accordingly, aqueous colloids are stable at low ionic strength and unstable at higher

electrolyte concentrations, while these stability regimes are separated by the critical coagulation concentration (CCC).<sup>16</sup>

The presence of simple salts of different composition can lead to different CCCs. This ion specificity on particle aggregation usually follows the tendency described by the Hofmeister series<sup>17-19</sup> for anions and cations as



For the correct interpretation of this order, one has to consider the charge and the hydrophobicity of the particle surface. Accordingly, ions located on the right side of the series (e.g.,  $\text{SCN}^-$  and  $\text{Ca}^{2+}$ ) stabilize negatively charged, hydrophobic particles in aqueous suspensions leading to higher CCC, while the ions on the left side (e.g.,  $\text{SO}_4^{2-}$  and  $\text{N}(\text{CH}_3)_4^+$ ) aggregate the particles at lower concentrations (direct Hofmeister series). The order is reversed (indirect Hofmeister series) for negatively charged, hydrophilic particles. These tendencies were established by aggregation studies with negatively charged latex,<sup>20,21</sup> clay<sup>22,23</sup>, silver iodide<sup>24</sup> and titania<sup>25</sup>. For positively charged, hydrophobic particles, the indirect Hofmeister series has to be considered, i.e., ions on the right side of the series induce aggregation at low concentrations, whereas the ones on the left side are able to destabilize the suspensions only at high CCC. The order is reversed and the direct Hofmeister series is valid for positively charged, hydrophilic particles. Interaction of latex,<sup>20,26,27</sup> peptide<sup>28</sup> and gold<sup>29</sup> particles of positive charge with ions from the Hofmeister series followed the rule.

The effects of sodium salts of different anions ( $\text{SCN}^-$ ,  $\text{Br}^-$ ,  $\text{Cl}^-$ ,  $\text{SO}_4^{2-}$ ,  $\text{HPO}_4^{2-}$  and  $\text{CO}_3^{2-}$ ) within the Hofmeister series on the aggregation of weakly charged LDHs have been also investigated.<sup>30</sup> The reported CCC values showed good agreement with the tendency predicted by the indirect Hofmeister series for positively charged, hydrophobic particles. However, only a weak dependence on the type of salts was discovered for monovalent ions. The presence of multivalent anions decreased the CCCs significantly. This fact indicates the importance of the counterion valence on colloidal stability of the particles, which has to be treated differently from the monovalent case.

Although the DLVO theory takes the valence of ions into account through the ionic strength, the type of salts (i.e., ion specificity) is not considered. Accordingly, electrical double layer forces decrease with the valence of counterions at the same salt concentrations and such a decrease leads to a dependence of the CCCs on the valence ( $z$ ) as

$$\text{CCC} \propto \frac{1}{z^n} \quad (1)$$

This is the so-called Schulze-Hardy rule<sup>31,32</sup> and  $n$  can vary between 2 and 6 depending on the surface charge density of the particles.<sup>33-35</sup> Aggregation of latex,<sup>35-39</sup> iron oxide,<sup>40,41</sup> clay,<sup>22,30,42</sup> and carbon derivative<sup>43,44</sup> particles was investigated in the presence of multivalent ions and a similar decrease in the CCCs was observed indicating the effectiveness of multivalent ions in destabilization of aqueous colloids. It was pointed out in these studies that adsorption of multivalent ions decreases the surface charge density more effectively and hence, the CCCs were shifted towards lower concentrations since less salt is needed to screen the repulsive double layer forces.

For LDH particles, interactions with multivalent anions (e.g.,  $\text{CO}_3^{2-}$ ,  $\text{SO}_4^{2-}$ ,  $\text{CrO}_4^{2-}$ ,  $\text{PO}_4^{3-}$  and  $\text{AsO}_4^{3-}$ ) have been extensively investigated to determine the adsorbed amount and to clarify the adsorption mechanism.<sup>45-51</sup> In spite of the large number of such studies, no comprehensive investigation on the effect of anion adsorption on aggregation kinetics and related colloidal stability has been published yet.

In the present research, we aimed at investigating the surface charge properties and aggregation of LDH particles composed of  $\text{Mg}^{2+}$  and  $\text{Al}^{3+}$  metal ions and  $\text{NO}_3^-$  interlayer anions (denoted as  $\text{MgAl-NO}_3\text{-LDH}$ ) in the presence of the  $\text{K}^+$  salts of various mono and multivalent anions. The  $\text{NO}_3^-$  intercalated LDHs are widely applied, since other anions can be easily intercalated between the layers by ion exchange. Electrophoretic and dynamic light scattering experiments were performed in aqueous suspensions to explore possible ion specific effects on colloidal stability of the samples over wide range of electrolyte concentrations. On the basis of the measured CCCs, we have clarified the Hofmeister series and the Schulze-Hardy rule for LDH particles.

## Experimental section

### Materials

Analytical grade  $\text{KCl}$ ,  $\text{KSCN}$ ,  $\text{K}_2\text{HPO}_4$  (Acros Organics),  $\text{KHCO}_3$  (Alfa Aesar),  $\text{KNO}_3$ ,  $\text{K}_2\text{SO}_4$ ,  $\text{K}_2\text{HAsO}_4$ ,  $\text{K}_3\text{Fe}(\text{CN})_6$  and  $\text{K}_4\text{Fe}(\text{CN})_6 \times 3\text{H}_2\text{O}$  (Sigma-Aldrich) were used. The salt solutions were prepared by dissolving the calculated amount of solid in ultrapure water (Millipore) and the pH was adjusted to 9 with 0.1 M  $\text{KOH}$  (Sigma-Aldrich) solution. This pH was also maintained in all stock suspensions and water used for sample preparation throughout the experiments. The protonation constants (pK) of the inorganic anions together with their actual charge at pH 9 are



presented in Table 1. All stock solutions were filtered with a 0.1  $\mu\text{m}$  pore-size filter (Millipore) prior to sample preparation and the measurements were carried out at 25  $^{\circ}\text{C}$ .

The MgAl-NO<sub>3</sub>-LDH particles were prepared by the coprecipitation method.<sup>52-55</sup> The solutions of Mg(NO<sub>3</sub>)<sub>2</sub> and Al(NO<sub>3</sub>)<sub>3</sub> (Sigma-Aldrich) were added dropwise under vigorous stirring to N<sub>2</sub>-blanketed 1.0 M NaOH (Acros Organics) until the final pH reached 10. The resulting suspension was subjected to hydrothermal treatment at 120  $^{\circ}\text{C}$  for 16 h in a teflon chamber embedded in a high-pressure steel reactor (Columbia International). The solid materials was rapidly filtered with a caustic resistant vacuum filter unit (Nalgene) equipped with a 0.45  $\mu\text{m}$  membrane (Versapor) and washed thoroughly with ultrapure water. The MgAl-NO<sub>3</sub>-LDH was then redispersed in pH 9 water resulting in a stock suspension of 10 g/L, which was later diluted to reach the suitable particle concentration for the experiments. The X-ray diffraction (XRD) patterns, recorded on a STADI-P transmission powder diffractometer system (Stoe), unambiguously confirmed the LDH formation (Fig. 1). Accordingly, all patterns can be indexed to a 3R<sub>1</sub> polytype where 3 is the number of layers stacked along the c-axis of the elementary cell, R refers to the rhombohedral symmetry and 1 indicates the trigonal prismatic assembly of the hydroxyl groups in the neighboring layers. This information was derived from the (012), (015) and (018) reflections. Such a polytype form is commonly used for description of LDH structures.<sup>56</sup> The lattice parameters were calculated from the observed peaks. An *a* dimension of 0.3 nm, which represents the shortest distance between two cations in the LDH layer, was calculated as twice the position of the (110) reflection.<sup>56</sup> A *c* parameter of 2.4 nm was obtained from the (003) reflection and it represents the thickness of three layers plus the interlayer space between them. The average thickness of the particles ( $\nu$ ) were calculated by the Scherrer equation as

$$\nu = K\lambda / \beta \cos \theta_B \quad (2)$$

where  $K$  is the shape factor,  $\lambda$  is the wavelength of the laser and  $\beta$  is the line broadening at the full width at half maximum. We found that  $\nu = 17.4$  nm.

### Electrophoretic mobility and stability ratio measurements

Electrophoretic mobilities were measured with a ZetaNano ZS (Malvern) device. The experiments were performed in plastic capillary cells (Malvern). For sample preparation, the calculated amount of electrolyte stock solution was mixed with ultrapure water to obtain the desired salt concentration. In the last step, the particle stock suspension was added. The final volume (5 mL) and the MgAl-NO<sub>3</sub>-LDH concentration (5 mg/L) were kept constant in the experiments. The suspensions were equilibrated overnight at room temperature and the electrophoretic mobilities were measured five times and the average values were reported. The standard deviation was always below 5%.

Dynamic light scattering (DLS) measurements were performed with a compact goniometer system (ALV/CGS-3) at 90° scattering angle using borosilicate glass cuvettes (Kimble Chase). A hydrodynamic radius of 168 nm and a polydispersity index of 0.39 were obtained for the MgAl-NO<sub>3</sub>-LDH particles in stable aqueous suspensions. Time-resolved DLS experiments were carried out to explore particle aggregation. Fig. 2 shows some typical measurements, in which the hydrodynamic radius ( $R_h$ ) was measured for 24 minutes under different experimental conditions. The initial increase in size was used to calculate the apparent aggregation rate ( $\Delta$ ) as

$$\Delta = \left. \frac{dR_h(t)}{dt} \right|_{t \rightarrow 0} \quad (3)$$

where  $t$  is the time of the experiment. The colloidal stability was expressed in terms of the stability ratio ( $W$ ) via the following equation<sup>57-59</sup>

$$W = \frac{\Delta_{fast}}{\Delta} \quad (4)$$

where *fast* refers to diffusion controlled aggregation, which was achieved in 1 M KCl solutions. The final sample volume was always 2 mL prepared by mixing calculated amount of salt solutions with the MgAl-NO<sub>3</sub>-LDH stock suspension to get a final particle concentration of 5 mg/L. The salt concentration range and particle dose were the same for both the electrophoretic and the DLS experiments, while the pH was kept at 9 and checked before and after the measurements.

## Results and discussion

Surface charge properties and aggregation of positively charged MgAl-NO<sub>3</sub>-LDH particles were studied by electrophoresis and DLS to investigate the suspension stability in the presence of simple inorganic electrolytes over wide range of concentrations. The type and the charge of the anions were systematically varied to explore ion specific effects on the colloidal stability of the samples. The anions are the counterions, whereas the K<sup>+</sup> coion was used throughout all experiments. Monovalent anions within the Hofmeister series<sup>17</sup> were investigated first, followed

by di, tri and tetravalent ones to establish the validity of the Schulze-Hardy rule<sup>31</sup> for anions interacting with the MgAl-NO<sub>3</sub>-LDH particles.

### **Effect of monovalent anions**

Electrophoretic mobilities of the MgAl-NO<sub>3</sub>-LDH particles were measured in the presence of K<sup>+</sup> salts of different monovalent anions such as Cl<sup>-</sup>, NO<sub>3</sub><sup>-</sup>, SCN<sup>-</sup> and HCO<sub>3</sub><sup>-</sup> (Fig. 3A). The shape of the curves was similar for the first three anions. The mobilities were positive at low concentrations due to the structural charge of the particles and passed through a maximum, which can be predicted by the standard electrokinetic model.<sup>60</sup> Further increasing the salt concentration, the electrophoretic mobilities decreased and were close to zero at high electrolyte levels due to the screening effect on the surface charge and the adsorption of the anions on the oppositely charged surface. The latter effect gave rise to slightly negative mobilities in case of SCN<sup>-</sup> at high electrolyte levels. Such a charge reversal has already been observed with this anion and other colloidal particles.<sup>20,21</sup> The electrophoretic mobilities also decreased at the same concentration in the Cl<sup>-</sup> > NO<sub>3</sub><sup>-</sup> > SCN<sup>-</sup> order indicating specific adsorption of the ions. However, the surface charge properties of the particles are significantly different in the presence of HCO<sub>3</sub><sup>-</sup> anion. Its adsorption led to charge neutralization at the isoelectric point (IEP) and subsequent charge reversal at higher concentrations. The latter phenomenon was the most significant in this case among the monovalent anions due to the high affinity of the HCO<sub>3</sub><sup>-</sup> to the MgAl-NO<sub>3</sub>-LDH surface. The strong interaction between carbonate or carboxylate containing anions and LDH particles is well-known and has been also reported in other systems.<sup>2,51,61</sup> Finally, the mobilities start decreasing in magnitude at higher salt levels due to the screening effect of the K<sup>+</sup> ions on the negative surface charge.

Light scattering has been proved as a suitable method to follow aggregation processes,<sup>62-</sup><sup>66</sup> therefore, DLS was used to determine stability ratios in the above systems under the same experimental conditions (Fig. 3B). In general, high stability ratios and stable suspensions were observed at low salt concentrations, whereas fast aggregation and unstable suspensions at high electrolyte levels were witnessed. These two regimes were separated by the CCCs, which is the concentration at which the sharp transition between slow and fast aggregation occurs. The aggregation remains rapid after the CCC irrespectively of the type of anions used. The shape of the stability ratio versus salt concentration curves was very similar in the presence of  $\text{Cl}^-$ ,  $\text{NO}_3^-$  and  $\text{SCN}^-$ , whereas the slope in the slow aggregation regime was higher for  $\text{HCO}_3^-$  due to its strong adsorption which modified the MgAl- $\text{NO}_3$ -LDH surface significantly.

The observed tendency is qualitatively in good agreement with the classical DLVO theory.<sup>14</sup> Accordingly, the overlap of the electrical double layers surrounding the particles leads to repulsive forces at low salt concentrations, which transcend the attractive van der Waals forces giving rise to stable suspensions. The double layer forces weaken progressively with the increasing electrolyte level due to surface charge screening by the salts. In addition, anion adsorption on the positively charged MgAl- $\text{NO}_3$ -LDH surface leads to reduced surface charge density and hence, to weaker double layer forces. Therefore, attractive van der Waals forces become predominant at high salt concentrations leading to aggregation of the particles and the formation of unstable samples.

The CCC values were determined from the stability plots and they decrease in the  $\text{Cl}^- > \text{NO}_3^- > \text{SCN}^- > \text{HCO}_3^-$  order (Fig. 4A and Table 2). The tendency for the first three ions agrees adequately with the indirect Hofmeister series for positively charged, hydrophobic particles.<sup>20</sup> The poorly hydrated  $\text{SCN}^-$  anions adsorb on the hydrophobic particles leading to lower surface

charge, weaker repulsive forces and the lowest CCC. The well hydrated  $\text{Cl}^-$  anions prefer to stay in the bulk and hardly adsorb on the MgAl- $\text{NO}_3$ -LDH giving rise to higher surface charge and the highest CCC within the anions investigated. A similar tendency was observed in other systems containing these anions and positively charged colloidal particles.<sup>18,20,21,27</sup> The situation in the  $\text{HCO}_3^-$  case is more complicated. Considering the indirect Hofmeister series, one would expect the highest CCC in the presence of this anion. It is however the opposite, the lowest CCC was measured. This is due to the specific affinity of the  $\text{HCO}_3^-$  ions to the MgAl- $\text{NO}_3$ -LDH surface of alkaline nature leading to strong adsorption on the oppositely charged particles. This adsorption induced a significant charge reversal as shown in the mobility curve (Fig. 3A). The strong interaction is due to electrostatic attraction and hydrogen bonding between the  $\text{HCO}_3^-$  anions and the hydroxyl groups of the surface.<sup>56</sup>

The anionic exchange capacity (AEC) of LDHs is typically in the range of 1-5 meq/g.<sup>47,67,68</sup> Given the low particle concentration (5 mg/L) in our experiments, only a small fraction (always below 1.5%) of the monovalent anions are involved in the ion exchange process. In addition, the AEC includes both intercalation and adsorption on the outer surface, but we are not able to distinguish these processes in our experiments. However, we believe that charging and aggregation of MgAl- $\text{NO}_3$ -LDH platelets are mostly sensitive to the adsorption and the tendencies obtained are related to this process rather than to anion intercalation.

To further clarify the aggregation mechanism, surface charge densities of the MgAl- $\text{NO}_3$ -LDH particles were determined and their relation to the CCCs was examined. For this, electrophoretic mobility ( $u$ ) was converted to electrokinetic potential using the Smoluchowski equation as<sup>14</sup>

$$\zeta = \frac{u\eta}{\varepsilon\varepsilon_0} \quad (5)$$

where  $\eta$  is the viscosity of water,  $\varepsilon_0$  is the permittivity of vacuum and  $\varepsilon$  is the dielectric constant. The surface charge density ( $\sigma$ ) was determined by fitting the potentials at different ionic strengths with the Debye-Hückel model developed for the charge-potential relationship as follows<sup>14</sup>

$$\sigma = \varepsilon\varepsilon_0\kappa\zeta \quad (6)$$

where  $\kappa$  is the inverse Debye length, which describes the contribution of all ionic species. The CCC was estimated from the DLVO theory as<sup>14,33</sup>

$$\text{CCC} = \frac{0.365}{N_A L_B} (H\varepsilon\varepsilon_0)^{-2/3} \sigma^{4/3} \quad (7)$$

where  $N_A$  is the Avogadro number,  $H$  is the Hamaker constant and  $L_B$  is the Bjerrum length, which is 0.72 nm for monovalent electrolytes in water. By fitting the experimental data with Equation 7, a Hamaker constant of  $H = 4.0 \times 10^{-20}$  J was found.

The calculated surface charge densities varied between +1 and +22 mC/m<sup>2</sup> for the different monovalent anions (Fig. 4B). This range is similar to that reported for LDHs of various compositions.<sup>61,69-72</sup> The obtained sequence in the surface charge densities was  $\text{Cl}^- > \text{NO}_3^- > \text{SCN}^- > \text{HCO}_3^-$  which follows the indirect Hofmeister series with the exception of the  $\text{HCO}_3^-$ . As

discussed above, this anion has high affinity to the MgAl-NO<sub>3</sub>-LDH surface leading to significant adsorption and reduced surface charge.

An excellent agreement was found between the experimental CCCs and the calculated ones. This fact confirms that the predominating interparticle forces are of DLVO origin and the ion specificity plays an important role in the adsorption mechanism. Accordingly, the well hydrated anions such as Cl<sup>-</sup> do not or only weakly adsorb on the MgAl-NO<sub>3</sub>-LDH particles and the surface charge density as well as the CCC is high in the presence of this anion. For poorly hydrated ions such as SCN<sup>-</sup>, stronger adsorption leads to low surface charge density and CCC. In case of HCO<sub>3</sub><sup>-</sup>, the adsorption is further enhanced with specific interaction between the anion and the surface hydroxyl groups through mainly hydrogen bonds giving rise to the lowest CCC among the anions investigated. Although the adsorption processes resulted in different surface charge densities, the interparticle forces are still of DLVO origin as one can realize it from the excellent agreement between the experimental and calculated CCCs (Fig. 4B). A similar observation was also made on the basis of direct force and aggregation rate measurements for positively charged latex particles in the presence of similar anions.<sup>26</sup>

### **Effect of divalent anions**

Charging and aggregation of the MgAl-NO<sub>3</sub>-LDH particles were also studied in the presence of divalent anions such as SO<sub>4</sub><sup>2-</sup>, HAsO<sub>4</sub><sup>2-</sup> and HPO<sub>4</sub><sup>2-</sup> with the K<sup>+</sup> cation. Although LDHs of different composition are widely used to capture these anions in water purification processes,<sup>12,13</sup> their effect on colloidal stability has not been studied in detail to date.

Electrophoretic mobilities were positive at low salt concentrations due to the positive structural charge of the particles (Fig. 5A). Increasing the dose of the divalent anions, the



mobilities decreased rapidly and reached the IEP in each case. Pronounced charge reversal occurred with all of the anions indicating their large affinity to the surface. Such charge reversal has been already reported for other LDHs in the presence of divalent anions.<sup>30,47,51</sup> However, the adsorption of  $\text{HPO}_4^{2-}$  led to the most negative electrophoretic mobilities, while very similar values were measured for  $\text{SO}_4^{2-}$  and  $\text{HAsO}_4^{2-}$ . A previously reported competitive adsorption study also confirmed that  $\text{HPO}_4^{2-}$  has greater affinity to the LDH surface than the  $\text{HAsO}_4^{2-}$  ions.<sup>45</sup> Further increasing the salt concentration, the mobilities increased due to the screening effect of the  $\text{K}^+$  cations on the surface charge. Note that  $\text{K}^+$  is the counterion of the negatively charged particles in this concentration regime.

The tendency in the stability ratios was very similar to the monovalent case for  $\text{SO}_4^{2-}$  and  $\text{HAsO}_4^{2-}$  anions (Fig. 5B), which behaved alike in the aggregation experiments. Slow and fast aggregation regimes were separated by well-defined CCCs, which were lower than for the monovalent anions (Table 2). This aggregation behaviour can be explained with the DLVO theory. Nevertheless, the stability curve was found to be very different for the  $\text{HPO}_4^{2-}$  anions, as one would expect from the results of the electrophoretic mobility measurements performed with the same systems. Three CCC values were obtained. Accordingly, stable MgAl- $\text{NO}_3$ -LDH suspensions were observed at low salt concentrations and the aggregation became fast at higher  $\text{HPO}_4^{2-}$  level (first CCC). The stability ratios increased (second CCC) in the intermediate regime and reached a plateau. At higher concentrations, the aggregation rates increased and fast aggregation occurred again (third CCC). Such restabilization effect is typically induced by polyelectrolytes and multivalent ions in the presence of oppositely charged colloidal particles<sup>15,38,39,61,73</sup> and can be explained as follows. The high stability at low salt level is due to the sufficiently strong repulsive double layer forces, which weaken with increasing salt

concentration, since the adsorption of the anions reduces the surface charge. The double layer forces vanish at the IEP and the particles rapidly aggregate after the first CCC due to the attractive van der Waals forces. The aggregation slows down after the second CCC where the charge reversal phenomenon occurs and the high negative charge induces the formation of the electrical double layers, which leads to repulsive interparticle forces. Further increasing the salt concentration, the aggregation becomes faster and unstable suspensions can be observed after the third CCC due to the screening effect of the  $K^+$  ions on the negative surface charge. For the  $SO_4^{2-}$  and  $HAsO_4^{2-}$  anions, the charge reversal did not result in sufficiently high surface charge density (as one can see in Fig. 5A), therefore, the restabilization did not happen.

### **Effect of multivalent anions**

The surface charge and colloidal stability of the MgAl-NO<sub>3</sub>-LDH particles were studied in the presence of  $Fe(CN)_6^{3-}$  and  $Fe(CN)_6^{4-}$ , as tri and tetravalent anions. The effect of these anions on the electrophoretic mobilities was similar to the divalent case. Accordingly, the particles were positively charged at low salt concentrations, while strong adsorption of the multivalent ions led to charge neutralization at the IEP and subsequent charge reversal at appropriately high electrolyte levels (Fig. 6A). The extremely low IEP and the large extent of the charge reversal indicated higher affinity of the  $Fe(CN)_6^{4-}$  for the surface, while the behaviour of  $Fe(CN)_6^{3-}$  was very similar to the  $HPO_4^{2-}$ . For the tetravalent anions, the magnitude of the electrophoretic mobilities was more than twice higher than for the bare MgAl-NO<sub>3</sub>-LDH particles, similar to the case of adsorption of polyelectrolytes on oppositely charged surfaces.<sup>15,51,61</sup> The mobilities started to increase after the minimum at higher concentrations due to the screening effect of the counterions which are  $K^+$  for the negatively charged particles.

Similar to  $\text{HPO}_4^{2-}$ , three CCCs were observed for the tri and tetravalent ions (Fig. 6B and Table 2). The first CCC occurred due to charge neutralization, the second CCC originated from the charge reversal induced restabilization, while the third CCC is the result of the screening effect on the negative surface charge by the  $\text{K}^+$  cations. The behaviour of the  $\text{Fe}(\text{CN})_6^{3-}$  is so analogous with the  $\text{HPO}_4^{2-}$  in both electrophoretic and aggregation experiments that one could assume that the  $\text{HPO}_4^{2-}$  anions deprotonate upon adsorption and show the characteristic surface charge features for a trivalent anion. However, no unambiguous experimental evidence confirms this assumption. For the  $\text{Fe}(\text{CN})_6^{4-}$  anions, the particles were highly negative due to the overcharging process in the intermediate concentration regime, which resulted in highly stable samples, such that stability ratios could not be measured. Therefore, the stability ratios after the second CCC are not connected to the ones before the third CCC in Fig. 6B, since the expected maximum is above the detection limit of the experiment. Accordingly,  $\text{Fe}(\text{CN})_6^{4-}$  anions are powerful aggregating agents for LDHs and suspensions can be stabilized or destabilized by varying the salt concentration. The first CCC is much below the typical AEC value for LDHs, therefore, we assume that adsorption of the tetravalent anions on the outer particle surface plays the key role in the charging and aggregation processes of  $\text{MgAl-NO}_3\text{-LDH}$  platelets, while intercalation between the layers can hardly take place due to the short experiment time.

Let us compare now the CCCs in the presence of anions of different valence such as  $\text{Cl}^-$ ,  $\text{SO}_4^{2-}$ ,  $\text{Fe}(\text{CN})_6^{3-}$  and  $\text{Fe}(\text{CN})_6^{4-}$  (Fig. 7). For the first two anions, only one CCC was observed since restabilization did not occur (Fig. 3B and 5B), while three CCCs were determined for the tri and tetravalent ones. The first CCC decreases with the valence due to the increasing affinity and stronger adsorption on the  $\text{MgAl-NO}_3\text{-LDH}$  surface. The second CCCs for  $\text{Fe}(\text{CN})_6^{3-}$  and  $\text{Fe}(\text{CN})_6^{4-}$  also decreases with the valence. However, a higher third CCC was determined for the

tetravalent ion than for the trivalent one. This behaviour can be correlated with the extent of charge reversal. The adsorption of  $\text{Fe}(\text{CN})_6^{4-}$  induced a much larger charge reversal and particles of highly negative charge were formed. Therefore, more  $\text{K}^+$  counterions are needed to screen the surface charge leading to a higher third CCC in case of the  $\text{Fe}(\text{CN})_6^{4-}$  than for the  $\text{Fe}(\text{CN})_6^{3-}$  anions. The stability map shows that the suspensions are stable in the low concentration region and unstable at high salt levels for all valences. The peninsula on the right side indicates another stable regime due to the restabilization at intermediate concentrations induced by the strong adsorption of the tri and tetravalent ions. Similar stability maps were reported for charged latex particles in the presence of multivalent ions.<sup>38,39,73</sup>

As discussed above, multivalent ions are more powerful in the destabilization of  $\text{MgAl-NO}_3\text{-LDH}$  suspensions. Fig. 8 shows the relative CCCs normalized for the  $\text{Cl}^-$  case for all the anions investigated in the present study together with some data from the literature<sup>39,41,73,74</sup> and with expected CCCs from the Schulze-Hardy rule.<sup>31,32</sup> The CCC values from the present work are systematically lower than the ones predicted by the  $z^{-6}$  dependence. The difference is the most significant for  $\text{HPO}_4^{2-}$  and  $\text{Fe}(\text{CN})_6^{4-}$ , for which extremely low CCCs were observed indicating high affinity of these ions to the surface. Some of the literature data (e.g., for the hematite and latex particles) are also below the line predicted by the Schulze-Hardy rule. Such tendency is a bit surprising, since the  $z^{-6}$  dependence can be derived from the DLVO theory only for highly charged particles, whereas for surfaces of low surface charge density and surface potential (e.g.,  $\text{MgAl-NO}_3\text{-LDH}$  in our system), the DLVO theory predicts  $z^{-2}$  dependence.<sup>33-35</sup> On the other hand, direct measurements of surface forces and aggregation rates with colloidal latex particles revealed that although some additional forces are also present, the DLVO theory can describe the interparticle forces relatively well, even in the case of multivalent ions.<sup>36,73</sup>

These facts indicate specific interaction between the anions and the particles surface, which enhances the adsorption and hence, decreases the surface charge density leading to lower CCCs. Therefore, the observed deviation from the expected dependence of the CCC on the valence is due to the high affinity of anions to the MgAl-NO<sub>3</sub>-LDH, while the interparticle forces are still of DLVO origin. One of the reasons for the high affinity is the strong hydrogen bonding network between the anions and the hydroxyl groups of the surface, which can be different for ions of different ability (e.g., electronegativity) to form hydrogen bonds. Besides, the hydration state of the anions plays also a crucial role. Poorly hydrated anions tend to adsorb on the hydrophobic surfaces stronger leading to lower CCCs, whereas well hydrated ones adsorb only weakly and remain in solution giving rise to higher CCCs. The knowledge generated by these results can be certainly applied wherever LDH particles are used as adsorbents for anion capture in aqueous samples, since colloidal stability of the suspensions can be predicted and tuned according to the desired goals.

## Conclusions

Ion specific effects on charging and aggregation of positively charged MgAl-NO<sub>3</sub>-LDH particles were investigated. The type of monovalent anions significantly affects the surface charge density and also the CCCs, which both decrease in the Cl<sup>-</sup> > NO<sub>3</sub><sup>-</sup> > SCN<sup>-</sup> > HCO<sub>3</sub><sup>-</sup> order. This tendency agrees with the indirect Hofmeister series only in part, since the HCO<sub>3</sub><sup>-</sup> ion should be located on the left side. This deviation is due to the high affinity of the HCO<sub>3</sub><sup>-</sup> for the particle surface, which leads to strong adsorption and charge reversal at appropriately high salt concentrations. The extent of adsorption weakens towards the left side of the series due to the hydration level,

which increases in this direction and hence, well hydrated ions such as  $\text{Cl}^-$  adsorb only weakly and prefer to stay in the solution giving rise to the highest CCC.

Multivalent ions were found to be powerful destabilizing agents. Their adsorption led to charge neutralization and significant charge reversal in each case and restabilization of the suspensions also occurred for  $\text{HPO}_4^{2-}$ ,  $\text{Fe}(\text{CN})_6^{3-}$  and  $\text{Fe}(\text{CN})_6^{4-}$  in the intermediate concentration regimes. The CCCs decreased with the valence even more significantly than the ones predicted by the Schulze-Hardy rule. The present results indicate that multivalent inorganic anions show strong affinity for the MgAl- $\text{NO}_3$ -LDH surface through electrostatic attraction, hydrophobic interactions and hydrogen bonds forming between the anions and the hydroxyl groups of the surface. However, the predominant interparticle forces can be well described with the DLVO theory.

In conclusion, effective LDH-based adsorbent systems can be proposed for water treatment processes, considering that the colloidal stability of the aqueous suspensions can be controlled with the valence (or actual charge under the pH applied) and the concentration of the ions.

## Acknowledgements

This research was supported by the Swiss National Science Foundation (150162), Swiss Secretariat for Education, Research and Innovation (C15.0024) and COST Actions CM1303 and MP1106. The authors thank Professor Michal Borkovec for providing access to the light scattering instruments in his laboratory.

## References

- 1 C. Forano, U. Costantino, V. Prevot and C. Taviot Gueho In *Handbook of Clay Science*; F. Bergaya and G. Lagaly, Eds.; Elsevier: Amsterdam, 2013; Vol. 5A, p 745-782.
- 2 Z. Gu, J. J. Atherton and Z. P. Xu, *Chem. Commun.*, 2015, **51**, 3024-3036.
- 3 Y. G. Li, M. Gong, Y. Y. Liang, J. Feng, J. E. Kim, H. L. Wang, G. S. Hong, B. Zhang and H. J. Dai, *Nat. Commun.*, 2013, **4**, 1805.
- 4 A. Deak, L. Janovak, S. P. Tallosy, T. Bitó, D. Sebok, N. Buzas, I. Palinko and I. Dekany, *Langmuir*, 2015, **31**, 2019-2027.
- 5 K. Ladewig, Z. P. Xu and G. Q. Lu, *Expert Opin. Drug Deliv.*, 2009, **6**, 907-922.
- 6 G. Choi, O. J. Kwon, Y. Oh, C. O. Yun and J. H. Choy, *Sci. Rep.*, 2014, **4**, 4430.
- 7 A. L. Troutier-Thuilliez, H. Hintze-Bruening, C. Taviot-Gueho, V. Verney and F. Leroux, *Soft Matter*, 2011, **7**, 4242-4251.
- 8 S. Pausova, J. Krysa, J. Jirkovsky, C. Forano, G. Mailhot and V. Prevot, *Appl. Catal. B*, 2015, **170**, 25-33.
- 9 H. F. Liang, F. Meng, M. Caban-Acevedo, L. S. Li, A. Forticaux, L. C. Xiu, Z. C. Wang and S. Jin, *Nano Lett.*, 2015, **15**, 1421-1427.
- 10 S. Meszaros, J. Halasz, Z. Konya, P. Sipos and I. Palinko, *Appl. Clay Sci.*, 2013, **80-81**, 245-248.
- 11 S. L. Ma, L. Huang, L. J. Ma, Y. Shim, S. M. Islam, P. L. Wang, L. D. Zhao, S. C. Wang, G. B. Sun, X. J. Yang and M. G. Kanatzidis, *J. Am. Chem. Soc.*, 2015, **137**, 3670-3677.
- 12 F. L. Theiss, S. J. Couperthwaite, G. A. Ayoko and R. L. Frost, *J. Colloid Interface Sci.*, 2014, **417**, 356-368.
- 13 K. H. Goh, T. T. Lim and Z. Dong, *Water Res.*, 2008, **42**, 1343-1368.
- 14 D. F. Evans and H. Wennerstrom, *The Colloidal Domain*, John Wiley, New York, 1999.
- 15 I. Szilagyi, G. Trefalt, A. Tiraferri, P. Maroni and M. Borkovec, *Soft Matter*, 2014, **10**, 2479-2502.
- 16 M. Elimelech, J. Gregory, X. Jia and R. A. Williams, *Particle Deposition and Aggregation: Measurement, Modeling, and Simulation*, Butterworth-Heinemann Ltd., Oxford, 1995.
- 17 D. F. Parsons, M. Bostrom, P. Lo Nostro and B. W. Ninham, *Phys. Chem. Chem. Phys.*, 2011, **13**, 12352-12367.
- 18 J. M. Peula-Garcia, J. L. Ortega-Vinuesa and D. Bastos-Gonzalez, *J. Phys. Chem. C*, 2010, **114**, 11133-11139.
- 19 N. Schwierz, D. Horinek and R. R. Netz, *Langmuir*, 2010, **26**, 7370-7379.
- 20 T. Oncsik, G. Trefalt, M. Borkovec and I. Szilagyi, *Langmuir*, 2015, **31**, 3799-3807.
- 21 T. Lopez-Leon, J. L. Ortega-Vinuesa and D. Bastos-Gonzalez, *ChemPhysChem*, 2012, **13**, 2382-2391.
- 22 G. Lagaly and S. Ziesmer, *Adv. Colloid Interface Sci.*, 2003, **100**, 105-128.
- 23 R. Tian, G. Yang, H. Li, X. D. Gao, X. M. Liu, H. L. Zhu and Y. Tang, *Phys. Chem. Chem. Phys.*, 2014, **16**, 8828-8836.
- 24 B. H. Bijsterbosch and J. Lyklema, *Adv. Colloid Interface Sci.*, 1978, **9**, 147-&.
- 25 F. Dumont, J. Warlus and A. Watillon, *J. Colloid Interface Sci.*, 1990, **138**, 543-554.

- 26 F. J. M. Ruiz-Cabello, G. Trefalt, T. Oncsik, I. Szilagyi, P. Maroni and M. Borkovec, *J. Phys. Chem. B*, 2015, **119**, 8184-8193.
- 27 T. Lopez-Leon, J. M. Lopez-Lopez, G. Odriozola, D. Bastos-Gonzalez and J. L. Ortega-Vinuesa, *Soft Matter*, 2010, **6**, 1114-1116.
- 28 T. B. Schuster, D. D. Ouboter, E. Bordignon, G. Jeschke and W. Meier, *Soft Matter*, 2010, **6**, 5596-5604.
- 29 V. Merk, C. Rehbock, F. Becker, U. Hagemann, H. Nienhaus and S. Barcikowski, *Langmuir*, 2014, **30**, 4213-4222.
- 30 G. Lagaly, O. Mecking and D. Penner, *Colloid Polym. Sci.*, 2001, **279**, 1090-1096.
- 31 J. T. G. Overbeek, *Pure Appl. Chem.*, 1980, **52**, 1151-1161.
- 32 J. Lyklema, *J. Colloid Interface Sci.*, 2013, **392**, 102-104.
- 33 G. Trefalt, I. Szilagyi and M. Borkovec, *J. Colloid Interface Sci.*, 2013, **406**, 111-120.
- 34 G. Trefalt, F. J. Montes Ruiz-Cabello and M. Borkovec, *J. Phys. Chem. B*, 2014, **118**, 6346-6355.
- 35 T. Oncsik, G. Trefalt, Z. Csendes, I. Szilagyi and M. Borkovec, *Langmuir*, 2014, **30**, 733-741.
- 36 F. J. M. Ruiz-Cabello, G. Trefalt, Z. Csendes, P. Sinha, T. Oncsik, I. Szilagyi, P. Maroni and M. Borkovec, *J. Phys. Chem. B*, 2013, **117**, 11853-11862.
- 37 C. Schneider, M. Hanisch, B. Wedel, A. Jusufi and M. Ballauff, *J. Colloid Interface Sci.*, 2011, **358**, 62-67.
- 38 I. Szilagyi, A. Polomska, D. Citherlet, A. Sadeghpour and M. Borkovec, *J. Colloid Interface Sci.*, 2013, **392**, 34-41.
- 39 A. Sadeghpour, I. Szilagyi and M. Borkovec, *Z. Phys. Chemie-Int. J. Res. Phys. Chem. Chem. Phys.*, 2012, **226**, 597-612.
- 40 K. L. Chen, S. E. Mylon and M. Elimelech, *Langmuir*, 2007, **23**, 5920-5928.
- 41 K. E. Verrall, P. Warwick and A. J. Fairhurst, *Colloid Surf. A*, 1999, **150**, 261-273.
- 42 Y. Mori, K. Togashi and K. Nakamura, *Adv. Powder Technol.*, 2001, **12**, 45-59.
- 43 L. Wu, L. Liu, B. Gao, R. Munoz-Carpena, M. Zhang, H. Chen, Z. H. Zhou and H. Wang, *Langmuir*, 2013, **29**, 15174-15181.
- 44 M. Sano, J. Okamura and S. Shinkai, *Langmuir*, 2001, **17**, 7172-7173.
- 45 A. Violante, M. Pucci, V. Cozzolino, J. Zhu and M. Pigna, *J. Colloid Interface Sci.*, 2009, **333**, 63-70.
- 46 R. L. Frost, A. W. Musumeci, J. T. Klopogge, M. O. Adebajo and W. N. Martens, *J. Raman Spectrosc.*, 2006, **37**, 733-741.
- 47 M. Jobbagy and A. E. Regazzoni, *J. Colloid Interface Sci.*, 2013, **393**, 314-318.
- 48 J. Hong, Z. L. Zhu, H. T. Lu and Y. L. Qiu, *RSC Adv.*, 2014, **4**, 5156-5164.
- 49 T. Bujdoso, A. Patzko, Z. Galbacs and I. Dekany, *Appl. Clay Sci.*, 2009, **44**, 75-82.
- 50 K. Kuzawa, Y. J. Jung, Y. Kiso, T. Yamada, M. Nagai and T. G. Lee, *Chemosphere*, 2006, **62**, 45-52.
- 51 Z. P. Xu, Y. G. Jin, S. M. Liu, Z. P. Hao and G. Q. Lu, *J. Colloid Interface Sci.*, 2008, **326**, 522-529.



- 52 J. He, M. Wei, B. Li, Y. Kang, D. G. Evans and X. Duan In *Layered Double Hydroxides*; X. Duan and D. G. Evans, Eds. 2006; Vol. 119, p 89-119.
- 53 D. Sranko, A. Pallagi, E. Kuzmann, S. E. Canton, M. Walczak, A. Sapi, A. Kukovecz, Z. Konya, P. Sipos and I. Palinko, *Appl. Clay Sci.*, 2010, **48**, 214-217.
- 54 Q. Wang and D. O'Hare, *Chem. Rev.*, 2012, **112**, 4124-4155.
- 55 X. D. Sun and S. K. Dey, *J. Colloid Interface Sci.*, 2015, **458**, 160-168.
- 56 D. G. Evans and R. C. T. Slade In *Layered Double Hydroxides*; X. Duan and D. G. Evans, Eds. 2006; Vol. 119, p 1-87.
- 57 H. Holthoff, S. U. Egelhaaf, M. Borkovec, P. Schurtenberger and H. Sticher, *Langmuir*, 1996, **12**, 5541-5549.
- 58 M. Owczarz, A. C. Motta, M. Morbidelli and P. Arosio, *Langmuir*, 2015, **31**, 7590-7600.
- 59 E. Tombacz and M. Szekeres, *Appl. Clay Sci.*, 2004, **27**, 75-94.
- 60 M. Borkovec, S. H. Behrens and M. Semmler, *Langmuir*, 2000, **16**, 5209-5212.
- 61 M. Pavlovic, M. Adok-Sipiczki, C. Nardin, S. Pearson, E. Bourgeat-Lami, V. Prevot and I. Szilagy, *Langmuir*, 2015, **31**, 12609-12617.
- 62 K. K. Norrfors, M. Bouby, S. Heck, N. Finck, R. Marsac, T. Schafer, H. Geckeis and S. Wold, *Appl. Clay Sci.*, 2015, **114**, 179-189.
- 63 A. Zaccone, H. Wu, M. Lattuada and M. Morbidelli, *J. Phys. Chem. B*, 2008, **112**, 1976-1986.
- 64 R. Ferretti, S. Stoll, J. W. Zhang and J. Buffle, *J. Colloid Interface Sci.*, 2003, **266**, 328-338.
- 65 A. Zaccone, J. J. Crassous, B. Beri and M. Ballauff, *Phys. Rev. Lett.*, 2011, **107**.
- 66 E. Tombacz, C. Csanaky and E. Illes, *Colloid Polym. Sci.*, 2001, **279**, 484-492.
- 67 J. H. Choy, M. Park and J. M. Oh, *Curr. Nanosci.*, 2006, **2**, 275-281.
- 68 S. Vial, V. Prevot, F. Leroux and C. Forano, *Microporous Mesoporous Mat.*, 2008, **107**, 190-201.
- 69 M. Pavlovic, L. Li, F. Dits, Z. Gu, M. Adok-Sipiczki and I. Szilagy, *RSC Adv.*, 2016, **6**, 16159-16167.
- 70 R. Rojas Delgado, M. Arandigoyen Vidaurre, C. P. De Pauli, M. A. Ulibarri and M. J. Avena, *J. Colloid Interface Sci.*, 2004, **280**, 431-441.
- 71 R. Rojas Delgado, C. P. De Pauli, C. B. Carrasco and M. J. Avena, *Appl. Clay Sci.*, 2008, **40**, 27-37.
- 72 R. B. Leggat, S. A. Taylor and S. R. Taylor, *Colloid Surf. A*, 2002, **210**, 69-81.
- 73 P. Sinha, I. Szilagy, F. J. M. Ruiz-Cabello, P. Maroni and M. Borkovec, *J. Phys. Chem. Lett.*, 2013, **4**, 648-652.
- 74 E. Matijevic and M. Kerker, *J. Phys. Chem.*, 1958, **62**, 1271-1276.
- 75 P. M. May, D. Rowland, E. Konigsberger and G. Hefter, *Talanta*, 2010, **81**, 142-148.

**Table 1.** Protonation constants and calculated actual charges of the inorganic anions used in the present study.


Anions <sup>a</sup>	pK <sub>1</sub> <sup>b</sup>	pK <sub>2</sub> <sup>b</sup>	pK <sub>3</sub> <sup>b</sup>	Valence at pH 9 <sup>c</sup>
Cl <sup>-</sup>	-0.71	–	–	1.00
NO <sub>3</sub> <sup>-</sup>	-1.40	–	–	1.00
SCN <sup>-</sup>	-2.10	–	–	1.00
CO <sub>3</sub> <sup>2-</sup>	10.33	6.35	–	1.04
SO <sub>4</sub> <sup>2-</sup>	1.98	-2.00	–	2.00
AsO <sub>4</sub> <sup>3-</sup>	11.50	6.94	2.19	1.99
PO <sub>4</sub> <sup>3-</sup>	12.35	7.21	2.14	1.98
Fe(CN) <sub>6</sub> <sup>3-</sup>	–	–	–	3.00
Fe(CN) <sub>6</sub> <sup>4-</sup>	4.20	2.00	-1.00	4.00

<sup>a</sup> Chemical formula in the deprotonated form. <sup>b</sup> The pK values were obtained from the JESS (Joint Expert Speciation System) database<sup>75</sup> at infinite dilution and 25 °C. <sup>c</sup> The valence was calculated on the basis of the protonation equilibria at pH 9 using the reported pK values.


**Table 2.** CCC values of the MgAl-NO<sub>3</sub>-LDH particles in the presence of K<sup>+</sup> salts of various anions.<sup>a</sup>

Anions <sup>b</sup>	first CCC (M)	second CCC (M)	third CCC (M)
Cl <sup>-</sup>	$5.4 \times 10^{-2}$	–	–
NO <sub>3</sub> <sup>-</sup>	$2.2 \times 10^{-2}$	–	–
SCN <sup>-</sup>	$1.3 \times 10^{-2}$	–	–
CO <sub>3</sub> <sup>2-</sup>	$1.9 \times 10^{-3}$	–	–
SO <sub>4</sub> <sup>2-</sup>	$3.2 \times 10^{-5}$	–	–
AsO <sub>4</sub> <sup>3-</sup>	$4.0 \times 10^{-5}$	–	–
PO <sub>4</sub> <sup>3-</sup>	$2.0 \times 10^{-7}$	$3.1 \times 10^{-6}$	$5.2 \times 10^{-1}$
Fe(CN) <sub>6</sub> <sup>3-</sup>	$1.1 \times 10^{-6}$	$3.0 \times 10^{-5}$	$6.0 \times 10^{-2}$
Fe(CN) <sub>6</sub> <sup>4-</sup>	$1.0 \times 10^{-13}$	$2.5 \times 10^{-13}$	$2.5 \times 10^{-1}$


<sup>a</sup> The CCCs were determined from the stability ratio versus salt concentration plots. The method has an error of about 10%. <sup>b</sup> Chemical formula in the deprotonated form.

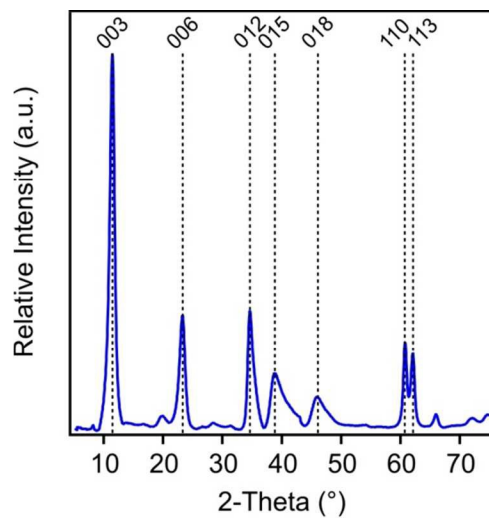


**Fig. 1** Powder XRD pattern of the MgAl-NO<sub>3</sub>-LDH particles synthesized by coprecipitation and subjected to hydrothermal treatment.

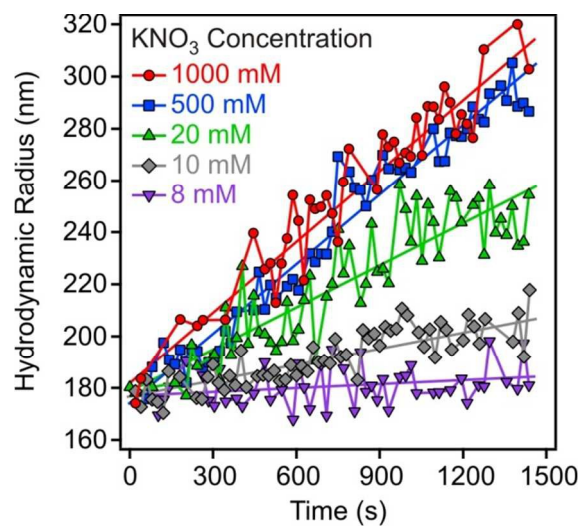


**Fig. 2** Hydrodynamic radius of MgAl-NO<sub>3</sub>-LDH particles (5 mg/L) as a function of the time of the experiment measured at different KNO<sub>3</sub> concentrations.

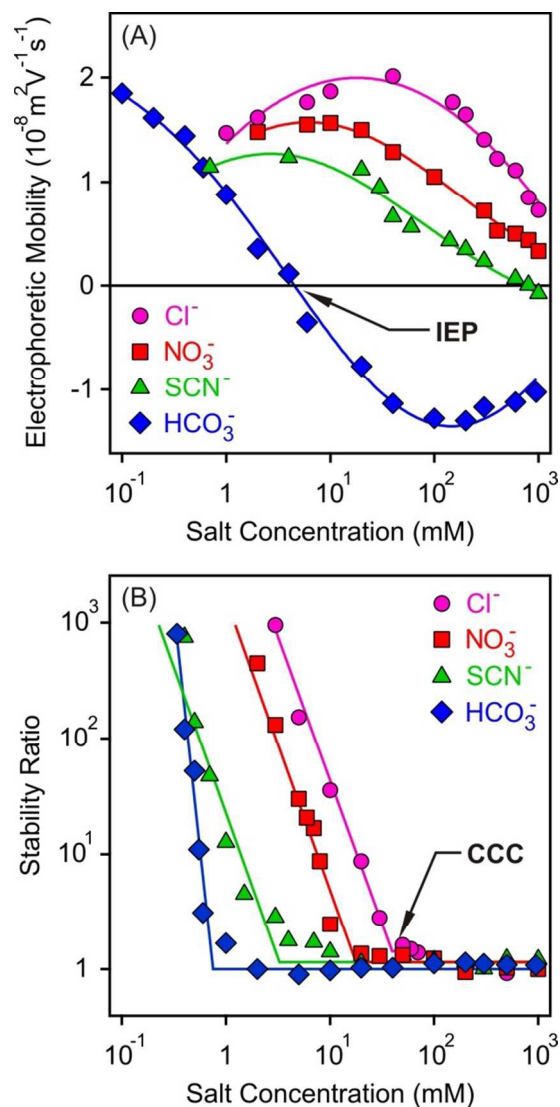

**Fig. 3** Electrophoretic mobility (A) and stability ratio (B) values for MgAl-NO<sub>3</sub>-LDH particles at different concentrations of monovalent anions. Stability ratios close to unity indicate rapid particle aggregation, while higher values refer to more stable suspensions. The lines are just to guide the eyes.

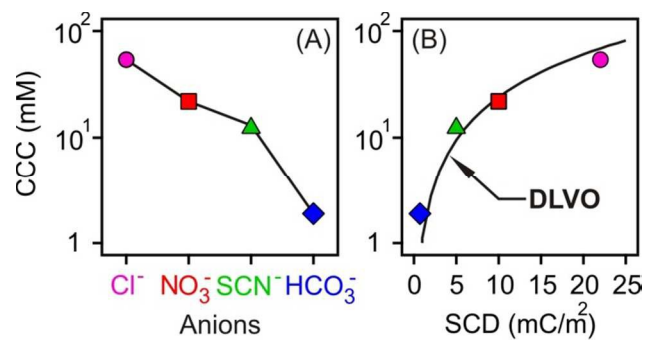


**Fig. 4** CCC values of positively charged MgAl-NO<sub>3</sub>-LDH particles in the presence of different monovalent anions (A) and as a function of the surface charge density (B). The solid line in (A) serves to guide the eyes, while in (B) it shows the DLVO prediction calculated by Equation 7.

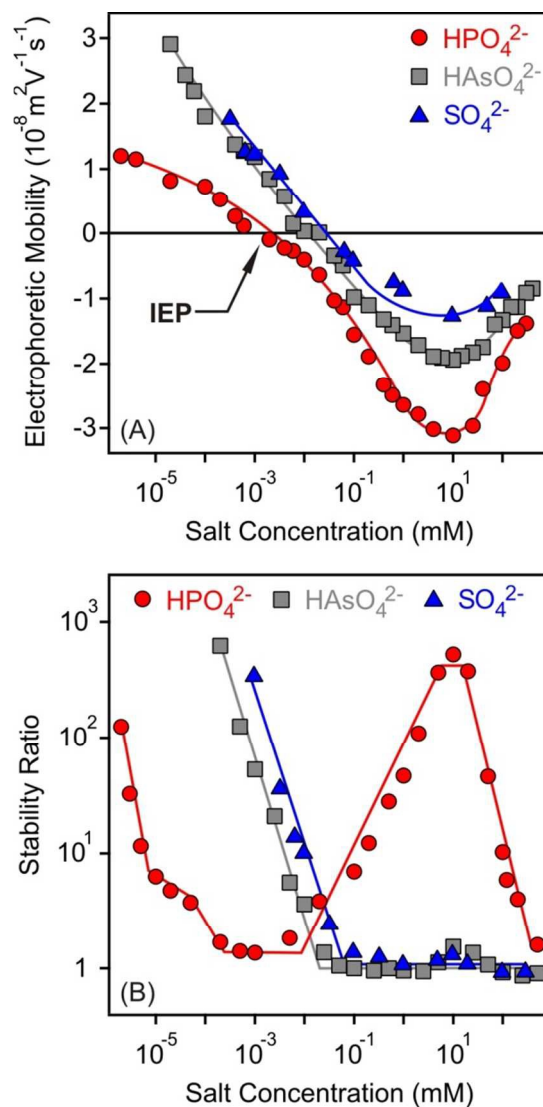


**Fig. 5** Electrophoretic mobility (A) and stability ratio (B) values of MgAl-NO<sub>3</sub>-LDH as a function of the salt concentration using K<sup>+</sup> salts of divalent anions. The lines are just to guide the eyes.




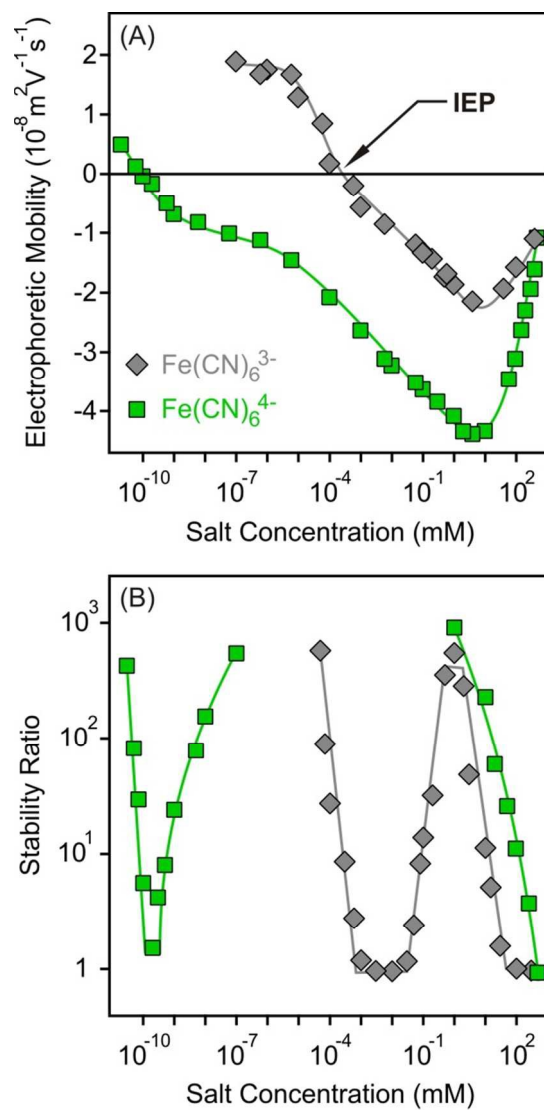


**Fig. 6** Electrophoretic mobility (A) and stability ratio (B) values of MgAl-NO<sub>3</sub>-LDH particles versus the salt concentration for K<sup>+</sup> salts of tri and tetra-valent anions. The lines serve to guide the eyes.

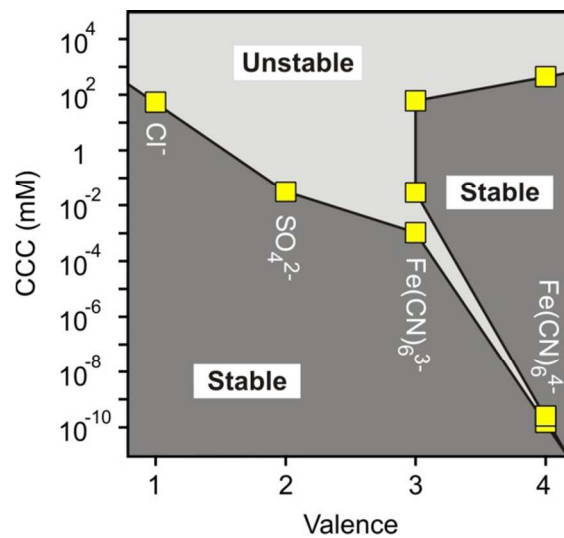

**Fig. 7** Stability map of MgAl-NO<sub>3</sub>-LDH suspensions in the presence of anions of different valence. The stability of the different regions is also indicated. The CCCs were obtained from the aggregation versus salt concentration plots.

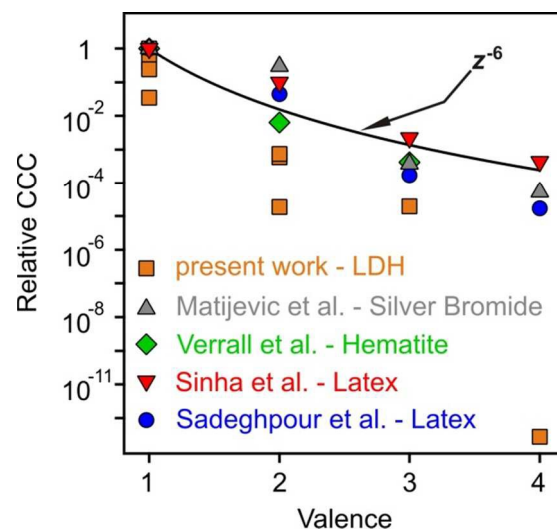

**Fig. 8** Relative CCCs, normalized to its value for  $\text{Cl}^-$  ion in the present system and for the monovalent case in the others reported in the literature, as a function of the valence (actual charge under the experimental conditions applied). The solid line shows the dependence expected from the Schulze-Hardy rule (Equation 1). Literature data include positively charged silver bromide,<sup>74</sup> hematite<sup>41</sup> and amidine functionalized polystyrene latex<sup>39,73</sup> particles in the presence of various anions.

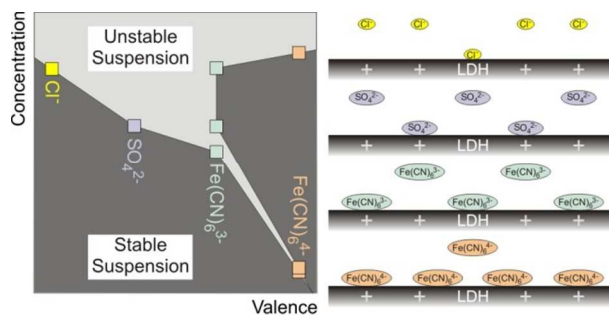

Graphical abstract for web presentation only