

# Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.


*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Table of Contents Entry

Colour graphic:

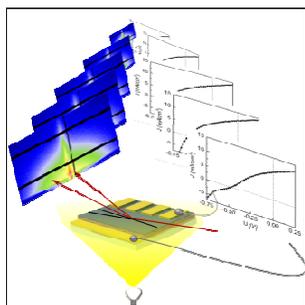

Text:

Stable morphology of inverted solar cells during operation is revealed by in-operando GISAXS, which results to the stable photovoltaic performance.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

## In-Operando Morphology Investigation of Inverted Bulk Heterojunction Organic Solar Cells with GISAXS

Weijia Wang,<sup>a</sup> Christoph J. Schaffer,<sup>a</sup> Lin Song,<sup>a</sup> Volker Körstgens,<sup>a</sup> Stephan Pröller,<sup>a,b</sup> Efi Dwi Indari,<sup>a</sup> Tianyi Wang,<sup>a</sup> Amr Abdelsamie,<sup>a</sup> Sigrid Bernstorff<sup>c</sup> and Peter Müller-Buschbaum<sup>\*a</sup>

<sup>5</sup> Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

Highly stable poly(3-hexylthiophene-2,5-diyl) (P3HT): phenyl-C61-butyric acid methyl ester (PCBM) bulk heterojunction solar cells are fabricated by using an inverted geometry. The direct correlation between the morphology of the active layer and the device performance during continuous operation under illumination is revealed by in-operando grazing incidence small angle X-ray scattering (GISAXS) and I-V measurements. Other than in devices with normal geometry, it is found that the P3HT:PCBM active layer shows a stable morphology during early operation times, which leads to an improved stability of the short circuit current and accordingly of the power conversion efficiency of the inverted solar cell. Furthermore, the inverted P3HT:PCBM solar cells are long-term stable without encapsulation if they are stored in ambient dark condition. It reveals that the power conversion efficiency preserves around 88% of the initial value after more than 150 days.

### Introduction

Over the last few decades, organic solar cells have been intensively investigated since they allow for easy power generation even where use of conventional inorganic photovoltaic devices is not feasible. Organic solar cells can be made from branches of organic semiconductors, which provide them unique properties.<sup>1-4</sup> The main advantages associated with organic solar cells are low weight, mechanical flexibility, less energy consumption and manufacturing costs as compared to other photovoltaic technologies, and a wide variety of production methods including roll-to-roll printing techniques.<sup>5-8</sup> This promising prospect of organic solar cells encourages massive research on developing new organic material systems or designing new solar cell architectures to make their photovoltaic performance comparable to traditional inorganic solar cells based on silicon.<sup>9</sup> Remarkable progress has been made to improve the power conversion efficiency (PCE) of organic solar cells. By utilizing low band gap polymers, the PCE of the polymer-fullerene bulk heterojunction (BHJ) solar cell has exceeded 8-10%.<sup>10-12</sup> Recently, a PCE around 10% has been achieved through using an inverted geometry.<sup>13</sup> Although high performances are achieved, the short lifetimes of organic solar panels still impede their commercialization.<sup>14-17</sup> Thus, improvements to achieve long term stability are highly desirable, which in turn will become easier with a better understanding of the degradation processes.

Poly(3-hexylthiophene-2,5-diyl) (P3HT): phenyl-C61-butyric acid methyl ester (PCBM) BHJ organic solar cells with a standard geometry is the most investigated system today, which is frequently used to investigate the structure-property

relationships.<sup>18-23</sup> In order to improve the stability of these devices, many of the processes leading to degradation have been identified. Thus, some general mechanisms of device degradation were proposed, including oxidation of the conjugated polymer and the top electrode, diffusion of water and oxygen molecules into solar cells, erosion of bottom electrodes made from indium tin oxide (ITO) and physical degradation such as morphological degradation of the P3HT:PCBM active layer.<sup>14,24-27</sup> By utilizing optimized encapsulation, several of these processes can be retarded or suppressed, which gives a significant increase in lifetime of the solar cells.<sup>28</sup> Moreover, it was demonstrated that an efficient approach to minimize the degradation process is to adopt the construction of P3HT:PCBM solar cells in the so-called inverted geometry.<sup>29,30</sup> Compared to the standard geometry, charge carriers are extracted at the opposite electrodes, where positive charge carriers flow from P3HT to the bottom electrode and negative charge carriers transfer to the top electrode. Hau et al. demonstrated an inverted P3HT:PCBM solar cell using zinc oxide (ZnO) as hole blocking layer retaining more than 80% efficiency over 40 days and attributed this long term stability to the less air sensitive high work function metal (silver) as the top electrodes.<sup>29</sup> Inverted solar cells with a ZnO/poly(ethylene glycol) (PEG) hybrid hole blocking layer, which was prepared via low temperature route, also showed a relatively low level of 23% degradation of the PCE after 14 days.<sup>31</sup>

Among the work related to inverted P3HT:PCBM BHJ solar cells, most work has been dedicated to the improvement of solar cell performance or extending the lifetime. Only a few general statements were proposed to explain the stability benefits from the inverted geometry. One of the viewpoints is that the replacement of the acidic poly(3,4-ethylenedioxythiophene):

poly(styrenesulfonate) (PEDOT:PSS) layer with a compact titanium dioxide (TiO<sub>2</sub>) or ZnO layer on ITO can help to overcome the erosion of the bottom electrodes.<sup>32,33</sup> Additionally, the P3HT:PCBM active layer can be protected from degradation induced by ultraviolet (UV) light illumination as the compact hole blocking layer (TiO<sub>2</sub> or ZnO) absorbs UV light before reaching the active layer.<sup>34</sup> The general build-up in the inverted geometry implies that the active layer is sandwiched between two blocking layers, which could reduce polymer oxidation caused by contact with air. All these statements are based on the minimization of the chemical degradation. However, to our knowledge, detailed fundamental understanding from the perspective of the physical stability, such as the stability of the active layer morphology, is still unclear. For devices with normal geometry, our previous work have already showed that the nanomorphology of the photoactive P3HT:PCBM layer is not stable.<sup>14</sup> We observed a morphological degradation, where smaller domains in the active layer vanished and larger ones grew. These changes in the nanomorphology caused a reduction of the effective area for electrical power conversion and accordingly the degradation of the solar cell's short circuit current ( $J_{SC}$ ), which plays the most important role in degradation of standard P3HT:PCBM solar cells.<sup>14</sup> In the present work, the direct correlation between morphology and device performance of inverted P3HT:PCBM BHJ solar cells is investigated during operation for the first time.

In order to probe the morphological evolution of the P3HT:PCBM inverted solar cells during operation under continuous air-mass 1.5 global (AM1.5G) sunlight illumination, in-operando grazing incidence small angle X-ray scattering (GISAXS) is used. GISAXS is an advanced scattering technique which provides information about the nanomorphology of thin film samples.<sup>35,36</sup> By selecting a suitable sample-detector distance (SDD), structures on length scales ranging from several nanometers up to a micrometer can be addressed.<sup>4,37,38</sup> Meanwhile, the in-situ current-voltage (I-V) characteristics of the inverted P3HT:PCBM solar cell are also characterized under the same conditions. In order to compare with the previous work on standard geometry devices, the same experimental design was used during in-operando GISAXS and I-V measurements, which minimize the degradation from oxygen and moisture.<sup>14</sup> Through in-operando GISAXS and I-V measurements on inverted devices during continuous operation, it is observed that the morphology of the solar cell is stable over time and the PCE of the solar cell is preserved to 75% after 240 minutes. By comparing the stability of photovoltaic parameters ( $J_{SC}$ ; open circuit voltage ( $V_{OC}$ ) and fill factor (FF)) in standard and inverted P3HT:PCBM solar cells during operation, it is clear that the stability of  $J_{SC}$  is the most enhanced parameter, while the others stay similar to the ones in standard devices. The photovoltaic parameters of standard P3HT:PCBM solar cell were reported in our previous work.<sup>14</sup> Thus, the improved stability of the inverted P3HT:PCBM solar cell is attributed to the stabilization of  $J_{SC}$ . As a consequence, the improved stability of the P3HT:PCBM inverted solar cells is mainly attributed to a stable morphology of the active layer as we demonstrate in the present investigation. Additionally, the long term stability of the P3HT:PCBM inverted solar cells without encapsulation, stored in dark, ambient conditions, is examined by

measuring the I-V characteristics periodically. If not operated continuously, the solar cells show 88% PCE preserved after more than 150 days. Therefore, to our knowledge, the probed inverted P3HT:PCBM solar cells are among the most stable reported P3HT:PCBM solar cells.


## Experimental section

### Materials

Poly(3-hexylthiophene-2,5-diyl) (P3HT) was purchased from Rieke Metals, Inc with an average molecular weight  $M_w$  of 50 kg/mol. Phenyl-C61-butyric acid methyl ester (PCBM) was purchased from Nano-C. Poly(3,4-ethylenedioxythiophene):poly(styrenesulfonate) (PEDOT:PSS) solution (PH1000) was purchased from Ossila. The solvents (chlorobenzene, isopropanol), from Carl Roth, were used as supplied, as were the active materials. Solar cells were fabricated on fluorine-doped tin oxide (FTO) substrates which were purchased from Solaronix with the size of (2.2×2.2) cm<sup>2</sup>.

### Sample preparation


The FTO was partly removed from the substrates by chemical etching and used as bottom electrode for the inverted solar cells. The substrates were then cleaned consecutively with alconox® solution, ethanol, acetone and isopropanol in an ultrasonic bath and treated with oxygen plasma. The hole blocking layer composed of a compact titanium dioxide film was prepared with the method reported in the work of Yu et al.<sup>39</sup> To prepare the P3HT:PCBM solution, P3HT was firstly dissolved in chlorobenzene until completely dissolved and then added to dry PCBM. Solutions were stirred overnight. The concentration of the blends was 24 mg/mL with a polymer:fullerene ratio of 1:1. The solution was spin-coated on the titanium dioxide layer with a rotation speed of 2000 rpm for 30 seconds. As reported by Weickert et al., diluted PEDOT:PSS solution is suitable for preparing the electron blocking layer by spray-coating.<sup>40</sup> Thus, the PEDOT:PSS solution as obtained was filtered by a PVDF filter (with the pore size of 0.45 μm) and then diluted with isopropanol at the ratio of 1:10. The diluted PEDOT:PSS solution was spray-coated for 15 seconds on the P3HT:PCBM layer by a commercial airbrush gun (Harder & Steenbeck) with 5 cm distance normal to the sample surface. Oil-free nitrogen with a pressure of 1 bar was used as the carrier gas. Afterwards, the sample was spin-dried with a rotation speed of 2000 rpm for 60 seconds. Gold electrodes were deposited on top of the PEDOT:PSS layer by physical vapor deposition, followed by thermal annealing at 140 °C for 10 min in a closed environment with a constant nitrogen flow. The scheme of the final device layer structure is shown in Fig. 1 to illustrate the inverted geometry.

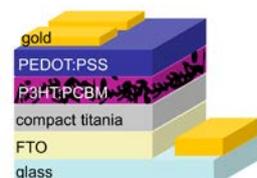

**Fig. 1** Scheme of inverted P3HT:PCBM solar cell layer structure used in the present investigation.

### In-operando grazing incidence small angle X-ray scattering (GISAXS)

The in-operando GISAXS experiments were performed at the Austrian SAXS beamline of the Elettra synchrotron source in Trieste, Italy. The X-ray wavelength was 0.154 nm. The sample-detector distance was 1776 mm. An incident angle of  $0.53^\circ$  was selected, which is above the critical angle of all polymers involved in the solar cell,  $\text{TiO}_2$  and FTO. The sample was fully penetrated at this incident angle, therefore both surface and inner film structures were probed. The set-up employed for mounting the solar cell for in-operando GISAXS measurement followed the one described in our previous work.<sup>14</sup> Thus, the solar cell was mounted in an evacuated chamber which enabled simultaneous I-V measurements and GISAXS characterization.<sup>14</sup> Since the scattering signal of the gold electrode outweighed the signal with the structural evolution of the P3HT:PCBM layer, the scattering data were collected at three positions close to the gold electrode.

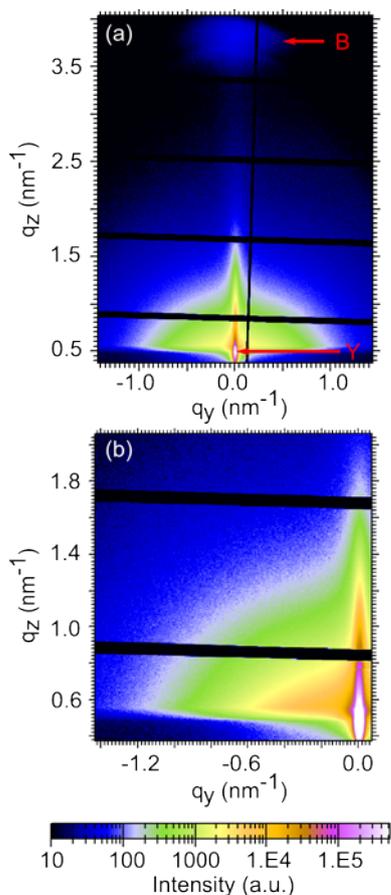

**Fig. 2** (a) Initial 2D GISAXS data of a P3HT:PCBM inverted solar cell before illumination with well pronounced Yoneda peak (Y) and (100) Bragg peak (B). (b) Zoom into the Yoneda region of the 2D GISAXS data.

The exposure time of each single measurement was 40 s. No X-ray irradiation damage or influence on the I-V measurements were observed for the measurements. The solar cell was operated continuously under the illumination by a 150 W Xenon short arc lamp (Perkin Elmer PX5) employing a constant intensity of  $100 \text{ mW/cm}^2$ . The GISAXS data were obtained before illumination,

denoted as 0 min, and then after 3 min, 10 min, 15 min, 30 min, 60 min, 120 min, 180 min and 240 min. In order to analyze the horizontal line cuts, a model in the framework of the distorted wave Born approximation (DWBA) and the local monodisperse approximation (LMA) was applied, which is based on contributions from three substructures each described by a form factor (average structure size) and a structure factor (average center-to-center distance) according to a 1d paracrystal as proposed by Hosemann et al.<sup>41</sup>

The current-voltage characteristics of the inverted solar cell were recorded constantly each 16 seconds by a source meter Keithley 2400 for 240 min. A silicon based reference solar cell was used to calibrate the applied AM1.5 conditions. By using a calibrated microscope, the solar cell pixel size was measured.

#### Long term stability measurements

The inverted P3HT:PCBM solar cells were stored in air under ambient condition without any encapsulation in the dark. The efficiency measured directly after solar cell preparation was denoted as the initial efficiency. Later, the long term stability was investigated by measuring I-V characteristics periodically.

### Results and discussion


#### Morphology evolution

The inverted P3HT:PCBM solar cells are built following a layered architecture of FTO/  $\text{TiO}_2$ / P3HT:PCBM/ PEDOT:PSS/ gold without additional encapsulation (see figure 1). As is known, the nanomorphology of the photo active layer is crucial for the solar cell performance.<sup>42,43</sup> To investigate the nanomorphology of the BHJ layer evolution during the first 240 min of operation under solar illumination ( $100 \text{ mW/cm}^2$ ), in-operando GISAXS is performed. It has been proven to be a powerful technique to probe the morphological degradation on a nanometer scale in polymer solar cells.<sup>14</sup> Therefore, in-operando GISAXS measurements on the P3HT:PCBM inverted solar cell are carried out to track the evolution of the morphology. In order to compare with our previous work about the morphological evolution of P3HT:PCBM in a standard geometry, the inverted device was installed in the same chamber that was evacuated to minimize the influence of oxygen and moisture. Through excluding the different influence from these two main factors on standard and inverted solar cell degradation, the investigation is mainly focused on the degradation due to changes of the nanomorphology of the BHJ layer.

The two dimensional (2D) GISAXS data are taken before illumination (denoted as 0 min) and after 3 min, 10 min, 15 min, 30 min, 60 min, 120 min, 180 min and 240 min of illumination. The initial 2D GISAXS data is shown in Fig. 2 as an example. The Yoneda peaks are observed at the critical angles, which clearly display as a bright region at the bottom of the 2D GISAXS pattern. Additionally, the P3HT (100) Bragg reflection is observed at the top of the pattern, which shows a spot-like feature. It reveals that P3HT crystallites exist in the photo active layer. Within all in-operando GISAXS measurements, the GISAXS patterns have not change significantly.

In order to obtain the structural information normal to the film, surface vertical line cuts are extracted from the 2D GISAXS data measured before illumination (0 min) and after 3 min, 10 min, 15

min, 30 min, 60 min, 120 min, 180 min and 240 min illumination at the position  $q_y = 0$  and plotted in Fig. 3a. For improved statistics three data points are averaged in the presentation. To clearly visualize the evolution of the vertical line cuts as function of illumination time, all curves are plotted on top of each other. The Yoneda peak of P3HT is visible for all the vertical line cuts, located at around  $q_z = 0.48 \text{ nm}^{-1}$ , and denoted by an arrow in the inset of Fig. 3a. The Yoneda peak belonging to FTO ( $q_z = 0.63 \text{ nm}^{-1}$ ) is not visible as it is superimposed by that of the P3HT:PCBM blend film. Since the vertical line cuts show identical features (Fig. 3a), we can conclude that the vertical film composition is stable. Besides, there is no indication for molecular diffusion arising during 240 min operating time under illumination since the Yoneda peak region, which reveals the material composition, remains unchanged.<sup>44</sup>

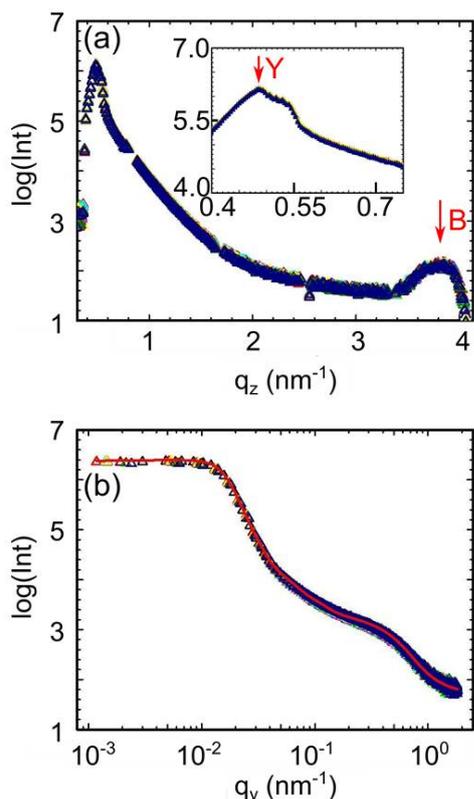


**Fig. 3** (a) Vertical line cuts and (b) horizontal line cuts (triangles) and corresponding fits (solid red line) of the 2D GISAXS data measured before the illumination (0 min) and after 3 min, 10 min, 15 min, 30 min, 60 min, 120 min, 180 min and 240 min. To visualize the absence of changes in the line cuts as function of illumination time, all cuts are plotted on top of each other. Different colors of the symbols denote different illumination times. In (a) three data points are averaged for better visualization and a zoom into the Yoneda region of the vertical line cuts is shown as inset.

Additionally, the P3HT (100) Bragg reflection peak is visible (Fig. 3a), located at  $q_z = 3.75 \text{ nm}^{-1}$ , which corresponds to a lattice constant of 1.68 nm. This value is in good agreement with previous investigations.<sup>43,45-47</sup> The FWHM value of  $0.63 \pm 0.05$  is obtained by fitting this Bragg peak and corresponds to the correlation length of  $10 \pm 0.8 \text{ nm}$  in the (100) direction, as

determined by using the Scherrer equation. The (100) peak does not change with illumination time, indicating that the P3HT crystalline order is stable with respect to the edge-on orientation in the inverted polymer solar cell during 240 min operating time under solar illumination.

Lateral structure information can be obtained by performing horizontal line cuts to the 2D GISAXS data.<sup>37</sup> Hereby, the material shows the most pronounced scattering intensity at its Yoneda peak position.<sup>48</sup> Since the morphology of the photo active P3HT:PCBM layer plays the most important role for photovoltaic performance of the solar cell,<sup>49</sup> all the horizontal line cuts are applied at the critical angle of P3HT (around  $0.16^\circ$ ) to emphasize on this material. Similarly to the way of displaying all the vertical line cuts, the horizontal line cuts of the in-operando study are also plotted on top of each other, as shown in Fig. 3b. It is noticed that all these curves completely overlap, which suggests that the morphology of P3HT:PCBM layer is stable during 240 min operating time under illumination. However, Schaffer et al. reported that P3HT domains grow with the time in a polymer solar cell with a standard geometry.<sup>14</sup> Compared to that, the morphology of the P3HT:PCBM layer in the inverted device is fully stabilized. This highly improved stability may be enabled by the  $\text{TiO}_2$  layer underneath. On the one hand, less P3HT chain scission caused by UV light illumination may occur due to the absorbance of the  $\text{TiO}_2$  layer underneath. Accordingly, the chain mobility of P3HT stays low and does not allow for structure relaxation when the chains retain their molecular weight. On the other hand, the interactions between the P3HT:PCBM film and the layer underneath also have strong influence on the morphology as described by Campoy-Quiles et al.<sup>50</sup> Zhao et al. also revealed that the P3HT films on conductive substrates show

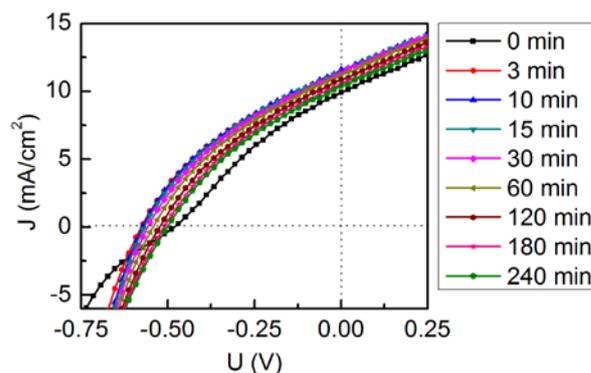

**Fig. 4** I-V curves of P3HT:PCBM inverted solar cell as the function of illumination time. I-V curves are recorded constantly every 16 seconds under continuous illumination for 240 min. The selected curves are matching the times of the in-operando GISAXS study as indicated by the color code.

significantly retarded degradation and preservation of the chemical and morphological features as compared to P3HT films on glass substrates.<sup>51</sup>

The average structure sizes and the distances of P3HT can be extracted from the fitting of the horizontal line cuts. One fitting matches for all the horizontal line cuts from the in-operando investigation, as shown in Fig. 3b. The average P3HT structure sizes of  $2.5 \pm 0.2$ ,  $19 \pm 1$  and  $82 \pm 4 \text{ nm}$  can be observed, with corresponding average distances of  $45 \pm 5$ ,  $180 \pm 30$  and  $420 \pm$


100 nm. In summary, the morphology of the P3HT:PCBM layer and the P3HT crystalline order are both fully stable in an inverted polymer solar cell on a time scale of several hours of operation.

### In-situ current-voltage characterization

In the inverted polymer solar cell, the morphology of P3HT:PCBM layer is stable during the first 240 min operating time under continuous solar illumination. In order to probe the stability of the photovoltaic performance during this time the cell is investigated simultaneously in terms of I-V tracking. I-V sweeps are hereby recorded every 16 seconds during illumination. Selected I-V curves (at the beginning of the illumination (denoted as 0 min) and after 3 min, 10 min, 15 min, 30 min, 60 min, 120 min, 180 min and 240 min) are shown in Fig. 4. These I-V curves represent the state at the times when the 2D GISAXS data have been recorded. The initial one (0 min) shows an S-shaped curve, owing the smallest  $J_{SC}$  and  $V_{OC}$  as compared to all the other measurements. Then, the S-shaped curve transits towards a generally more rectangle-like curve during the operation, which suggests a self-healing process that occurs during operation. Lloyd et al. have observed a similar behavior in an inverted organic photovoltaic device. They have attributed this initial improvement to the evolution of the interface between the active layer and the silver electrode.<sup>52</sup> The I-V curves recorded at 3 min and at 10 min appear similar, which indicates a stable photovoltaic performance of the device in this stage of operation. After 10 min of illumination, the I-V curves decay slowly with the illumination time, showing a continuously decreasing  $J_{SC}$  and  $V_{OC}$ .

The photovoltaic parameters of  $J_{SC}$ ,  $V_{OC}$ , FF and PCE are extracted from each I-V measurement and plotted as a function of illumination time in Fig. 5. For improved statistics five data points are averaged in this presentation. All the parameters increase dramatically during the first few minutes and then stay nearly constant until roughly 10 min. After that, a slow but continuous decay of all the parameters follows. The decay of PCE results from degradation of all three other photovoltaic parameters. Compared to the standard device,<sup>14</sup>  $V_{OC}$  decays similarly. A potential reason can be the change in temperature, as it is known that the temperature has a strong influence on  $V_{OC}$ . During the measurements, the temperature on the device was increased by only 10 °C, which still might explain the observed decay of  $V_{OC}$ . Guo et al. had also observed a voltage decrease with increasing temperature.<sup>23</sup> They attributed the reason to the degradation of the photoactive layer caused by photochemical reactions in polymer.

In contrast, the FF decays extremely slowly, thereby showing the same trend as observed in a standard device.<sup>14</sup> However, since the absolute FF values are quite small, a stronger decay might occur in device which exhibit higher FF values. In a standard geometry device, the morphological transition of the P3HT:PCBM layer can fully explain the degradation of  $J_{SC}$ .<sup>14</sup> In contrast, in this work  $J_{SC}$  still slowly decreases even with a stable P3HT:PCBM layer morphology, which might hint to some fundamental differences between standard and inverted geometry.

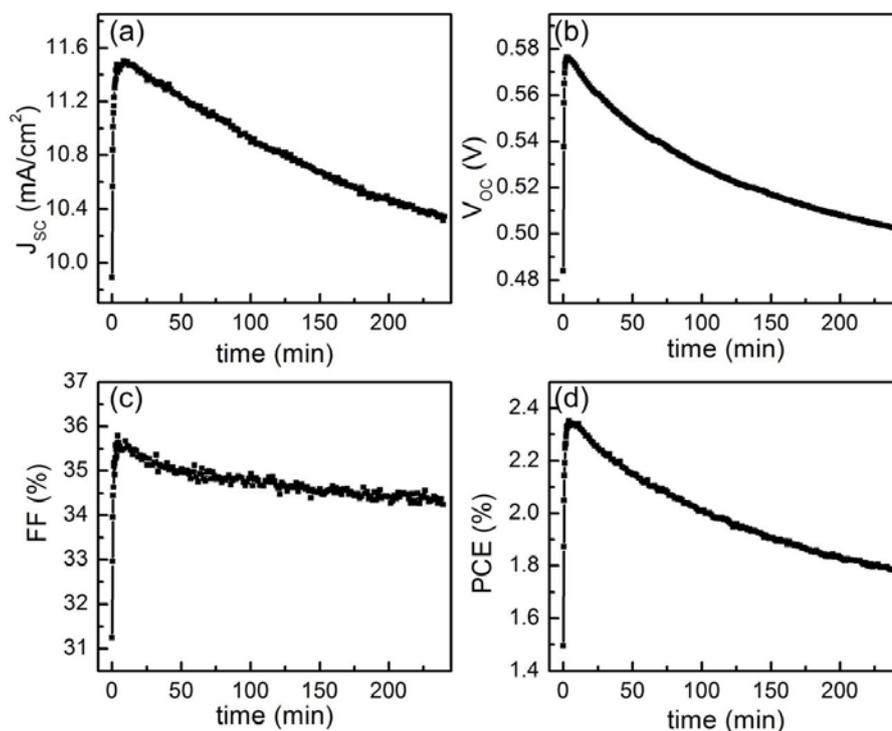


**Fig. 5** Time evolution of the photovoltaic characteristics of (a)  $J_{SC}$ , (b)  $V_{OC}$ , (c) FF and (d) PCE of the P3HT:PCBM inverted solar cell. The devices have been measured constantly every 16 seconds under continuous illumination for 240 min during the in-operando GISAXS study. Five data points are averaged for better visualization.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

## ARTICLE TYPE

In order to clearly illustrate the contributions of  $J_{SC}$ ,  $V_{OC}$  and FF to the decay of PCE, all the parameters are normalized to their maximum values and depicted in Fig. 6. As compared to a standard P3HT:PCBM solar cell,<sup>14</sup> PCE and  $J_{SC}$  show the most improved stability in the inverted geometry while FF and  $V_{OC}$  exhibit a similar decay behavior. The  $J_{SC}$  and PCE are preserved above 90% and 75% after 240 min of operation, whereas for cells in standard geometry around 80% and 65% were reported after 240 min of operation.<sup>14</sup> It implies that the improvement of the PCE stability mainly benefits from the stabilization of  $J_{SC}$ .

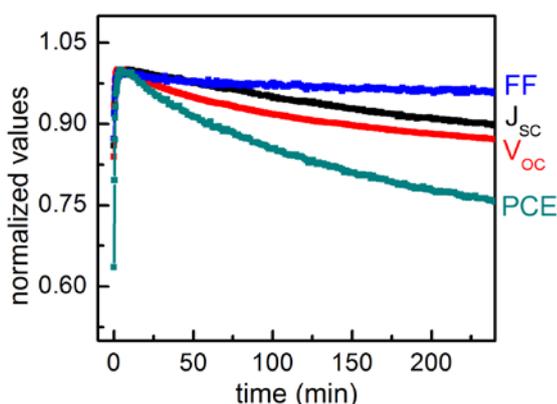

**Fig. 6** Time evolution of the normalized photovoltaic characteristics ( $J_{SC}$ ,  $V_{OC}$ , FF and PCE) of the P3HT:PCBM inverted solar cell probed during the in-operando GISAXS study.  $J_{SC}$ ,  $V_{OC}$ , FF and PCE are normalized to their maximum values. Five data points are averaged for better visualization.

Related to the above investigation on the morphology via in-operando GISAXS measurements, it is inferred that the strongly improved stability of  $J_{SC}$  is caused by a stable morphology of the active layer of P3HT:PCBM in an inverted geometry. Similarly, Schaffer et al. concluded that the change in the nanomorphology of P3HT:PCBM layer is an extremely important pathway of the  $J_{SC}$  decay.<sup>14</sup> Based on our investigations, we conclude that the stabilized P3HT:PCBM active layer contributes to a highly improved stability of  $J_{SC}$ , while it has no prominent influence on the temporal evolution of FF and  $V_{OC}$ . Accordingly, the stability of PCE is improved as compared to a standard solar cell.

Furthermore, the long term stability of inverted P3HT:PCBM solar cells was examined. An inverted device was kept in air under ambient conditions in the dark. The I-V measurements were carried out periodically. The PCE of the inverted device preserves 88% compared to its maximum value after more than 150 days. In summary, a significant improvement in the long-term stability of the device is obtained by using an inverted geometry, also when stored in air under ambient conditions.

## Conclusion

In this work we demonstrate a highly stable P3HT:PCBM BHJ solar cell in an inverted geometry. To understand the correlation between the morphology and the device performance during continuous operation under illumination, in-operando GISAXS and I-V characteristic measurements are performed. Around 75% of PCE is preserved after 240 min continuous operation, which is higher than that observed in a standard solar cell. This improvement results from an increased stability of  $J_{SC}$ . A stable morphology of the P3HT:PCBM layer, which benefits from the inverted geometry of the device, is revealed by the in-operando GISAXS measurements. This stabilization of the P3HT:PCBM layer is directly correlated with an improved stability of  $J_{SC}$  of the solar cell for the first time. Moreover, no prominent influence is observed on the decay behavior of the FF and  $V_{OC}$ . Moreover, the inverted solar cell is long term stable, when it is kept in air under dark, ambient conditions and measured periodically. Surprisingly, the PCE of the inverted device preserves around 88% after more than 150 days compared to its maximum value if not measured continuously. Thus, the present investigation shows that proper tuning of the stability of the morphology of the active layer, such as using an inverted geometry, can contribute to highly stable polymer solar cells.

## Acknowledgements

This work is financially supported by TUM.solar in the frame of the Bavarian Collaborative Research Project "Solar technologies go Hybrid" (SolTec), the GreenTech Initiative (Interface Science for Photovoltaics - ISPV) of the EuroTech Universities, the German Research Foundation (DFG) in the "SPP1355: Elementary processes of organic photovoltaics", and the Nanosystems Initiative Munich (NIM). W.W. and L.S. thank the China Scholarship Council (CSC) and E.D.I., T.W. and A.A. thank the Erasmus Mundus "MaMaSELF" program. Funding by the Bavarian State Ministry of Education, Science and the Arts via the International Graduate School "Materials Science of Complex Interfaces" (CompInt) is acknowledged by C.J.S. and via the project "Energy Valley Bavaria" by V.K.. Thanks D. Magerl for introducing the fitting model for horizontal line cuts in 2D GISAXS data.

## Notes and references

- <sup>a</sup> Technische Universität München, Physik-Department, Lehrstuhl für Funktionelle Materialien, James-Frank-Str. 1, 85748 Garching, Germany. Fax: +49-89-289-12473; Tel: +49-89-289-12451; E-mail: muellerb@ph.tum.de
- <sup>b</sup> Technische Universität München, Munich School of Engineering, Herzog Group, Lichtenbergstr. 4, 85748 Garching, Germany.
- <sup>c</sup> Elettra - Sincrotrone Trieste S.C.p.A., Strada Statale 14 - km 163,5 in AREA Science Park, Basovizza, 34149 Trieste, Italy.

1 S. B. Darling and F. You, *RSC Adv.*, 2013, **3**, 17633.

- 2 C. J. Brabec, N. Serdar Sariciftci and J. C. Hummelen, *Adv. Funct. Mater.*, 2001, **11**, 15.
- 3 M. Kaltenbrunner, M. S. White, E. D. Glowacki, T. Sekitani, T. Someya, N. Serdar Sariciftci and S. Bauer, *Nat. Commun.*, 2012, **3**, 770.
- 4 M. A. Ruderer and P. Müller-Buschbaum, *Soft Matter*, 2011, **7**, 5482.
- 5 B. C. Thompson and J. M. J. Fréchet, *Angew. Chem. Int. Ed.*, 2008, **47**, 58.
- 6 T. Ameri, T. G. Dennler, C. Lungenschmied and C. J. Brabec, *Energy Environ. Sci.*, 2009, **2**, 347.
- 7 M. C. Scharber and N. S. Sariciftci, *Prog. Polym. Sci.*, 2013, **38**, 1929.
- 8 F. Nickel, T. Haas, E. Wegner, D. Bahro, S. Salehin, O. Kraft, P. A. Gruber and A. Colmann, *Sol. Energy Mater. Sol. Cells*, 2014, **130**, 317.
- 9 L. Lu and L. Yu, *Sol. Adv. Mater.*, 2014, **26**, 4413.
- 10 Z. He, C. Zhong, X. Huang, W.-Y. Wong, H. Wu, L. Chen, S. Su and Y. Cao, *Adv. Mater.*, 2011, **23**, 4636.
- 11 M. A. Green, K. Emery, Y. Hishikawa, W. Warta and E. D. Dunlop, *Prog. Photovolt: Res. Appl.*, 2014, **22**, 701.
- 12 J.-D. Chen, C. Cui, Y.-Q. Li, L. Zhou, Q.-D. Ou, C. Li, Y. Li and J.-X. Tang, *Adv. Mater.*, DOI: 10.1002/adma.201404535.
- 13 Z. He, C. Zhong, S. Su, M. Xu, H. Wu and Y. Cao, *Nature Photon.*, 2011, **6**, 591.
- 14 C. J. Schaffer, C. M. Palumbiny, M. A. Niedermeier, C. Jendrzewski, G. Santoro, S. V. Roth and P. Müller-Buschbaum, *Adv. Mater.*, 2013, **25**, 6760.
- 15 B. Lechêne, J. Leroy, O. Tosoni, R. de Bettignies and G. Perrier, *J. Phys. Chem. C*, 2014, **118**, 20132.
- 16 A. Moujoud, S. H. Oh, J. J. Hye and H. J. Kim, *Sol. Energy Mater. Sol. Cells*, 2011, **95**, 1037.
- 17 C. H. Peters, I. T. Sachs-Quintana, J. P. Kastrop, S. Beaupré, M. Leclerc and M. D. McGehee, *Adv. Energy Mater.*, 2011, **1**, 491.
- 18 R. D. Bettignies, J. Leroy, M. Firon and C. Sentein, *Synth. Met.*, 2006, **156**, 510.
- 19 J. A. Hauch, P. Schilinsky, S. A. Choulis, R. Childers, M. Biele and C. J. Brabec, *Sol. Energy Mater. Sol. Cells*, 2008, **92**, 727.
- 20 M. O. Reese, A. J. Morfa, M. S. White, N. Kopidakis, S. E. Shaheen, G. Rumbles and D. S. Ginley, *Sol. Energy Mater. Sol. Cells*, 2008, **92**, 746.
- 21 C. Lungenschmied, G. Dennler, H. Neugebauer, S. N. Sariciftci, M. Glatthaar, T. Meyer and A. Meyer, *Sol. Energy Mater. Sol. Cells*, 2007, **91**, 379.
- 22 S. Guo, M. A. Ruderer, M. Rawolle, V. Körstgens, C. Birkenstock, J. Perlich and P. Müller-Buschbaum, *ACS Appl. Mater. Interfaces*, 2013, **5**, 8581.
- 23 S. Guo, C. Brandt, T. Andreev, E. Metwalli, W. Wang, J. Perlich and P. Müller-Buschbaum, *ACS Appl. Mater. Interfaces*, 2014, **6**, 17902.
- 24 M. Jørgensen, K. Norrman and F. C. Krebs, *Sol. Energy Mater. Sol. Cells*, 2008, **92**, 686.
- 25 K. Norrman and F. C. Krebs, *Sol. Energy Mater. Sol. Cells*, 2006, **90**, 213.
- 26 B. Conings, S. Bertho, K. Vandewal, A. Senes, J. D'Haen, J. Manca and R. A. J. Janssen, *Appl. Phys. Lett.*, 2010, **96**, 163301.
- 27 K. Norrman, M. V. Madsen, S. A. Gevorgyan and F. C. Krebs, *J. Am. Chem. Soc.*, 2010, **132**, 16883.
- 28 R. Tipnis, J. Bernkopf, S. Jia, J. Krieg, S. Li, M. Storch and D. Laird, *Sol. Energy Mater. Sol. Cells*, 2009, **93**, 442.
- 29 S. K. Hau, H.-L. Yip, N. S. Baek, J. Zou, K. O'Malley and A. K.-Y. Jen, *Appl. Phys. Lett.*, 2008, **92**, 253301.
- 30 M. T. Lloyd, D. C. Olson, P. Lu, E. Fang, D. L. Moore, M. S. White, M. O. Reese, D. S. Ginley and J. W. P. Hsu, *J. Mater. Chem.*, 2009, **19**, 7638.
- 31 T. Hu, F. Li, K. Yuan and Y. Chen, *ACS Appl. Mater. Interfaces*, 2013, **5**, 5763.
- 32 L.-M. Chen, Z. Xu, Z. Hong and Y. Yang, *J. Mater. Chem.*, 2010, **20**, 2575.
- 33 S. Lattante, *Electronics*, 2014, **3**, 132.
- 34 H. Sun, J. Weickert, H. C. Hesse and L. Schmidt-Mende, *Sol. Energy Mater. Sol. Cells*, 2011, **12**, 3450.
- 35 G. Renaud, R. Lazzari and F. Leroy, *Surf. Sci. Rep.*, 2009, **64**, 255.
- 36 A. Hexemer and P. Müller-Buschbaum, *IUCrJ*, 2015, **2**, 106.
- 37 P. Müller-Buschbaum, *Anal. Bioanal. Chem.*, 2003, **376**, 3.
- 38 P. Müller-Buschbaum, *Adv. Mater.*, 2014, **26**, 7692.
- 39 H. Yu, S. Zhang, H. Zhao, G. Will and P. Liu, *Electrochim. Acta*, 2009, **54**, 1319.
- 40 J. Weickert, H. Sun, C. M. Palumbiny, H. C. Hesse and L. Schmidt-Mende, *Sol. Energy Mater. Sol. Cells*, 2010, **94**, 2371.
- 41 R. Hosemann, W. Vogel, D. Weick and F. J. Baltá-Calleja, *Acta Cryst.*, 1981, **37**, 85.
- 42 P. Kohn, Z. Rong, K. H. Scherer, A. Sepe, M. Sommer, P. Müller-Buschbaum, R. H. Friend, U. Steiner and S. Hüttner, *Macromolecules*, 2013, **46**, 4002.
- 43 M. A. Ruderer, S. Guo, R. Meier, H.-Y. Chiang, V. Körstgens, J. Wiedersich, J. Perlich, S. V. Roth and P. Müller-Buschbaum, *Adv. Funct. Mater.*, 2011, **21**, 3382.
- 44 Y. Yoneda, *Phys. Rev.*, 1963, **131**, 2010.
- 45 S. Hugger, R. Thomann, T. Heinzl and T. Thurn-Albrecht, *Colloid Polym. Sci.*, 2004, **282**, 932.
- 46 Z. Wu, A. Petzold, T. Henze, T. Thurn-Albrecht, R. H. Lohwasser, M. Sommer and M. Thelakkat, *Macromolecules*, 2010, **43**, 4646.
- 47 K. Sethuraman, S. Ochiai, K. Kojima and T. Mizutani, *Appl. Phys. Lett.*, 2008, **92**, 183302.
- 48 G. Renaud, R. Lazzari and F. Leroy, *Surf. Sci. Rep.*, 2009, **64**, 255.
- 49 D. Chirvase, J. Parisi, J. C. Hummelen and V. Dyakonov, *Nanotechnology*, 2004, **15**, 1317.
- 50 M. Campoy-Quiles, T. Ferenczi, T. Agostinelli, P. G. Etchegoin, Y. Kim, T. D. Anthopoulos, P. N. Stavrinou, D. D. C. Bradley and J. Nelson, *Nature Mater.*, 2008, **7**, 158.
- 51 Y. Zhao, A. Sugunan, T. Schmidt, A. Fornara, M. S. Toprak and M. Muhammed, *J. Mater. Chem. A*, 2014, **2**, 13270.
- 52 M. T. Lloyd, C. H. Peters, A. Garcia, I. V. Kauvar, J. J. Berry, M. O. Reese, M. D. McGehee, D. S. Ginley and D. C. Olson, *Sol. Energy Mater. Sol. Cells*, 2011, **95**, 1382.