

Journal of Materials Chemistry C

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Aggregation Induced Emission Based Fluorescence pH and Temperature Sensors: Probing Polymer Interactions in Poly(*N*-isopropyl acrylamide-co-tetra(phenyl)ethene acrylate)/Poly(methacrylic acid) Interpenetrating Polymer Networks

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Hui Zhou,^a Feng Liu,^b Xiaobai Wang,^a Hong Yan,^a Jing Song,^a Qun Ye,^a Ben Zhong Tang^{*c} and Jianwei Xu^{*a}

Aggregation induced emission (AIE) active copolymers **P1-6** with high molecular weights (14,000-17,000) and low polydispersity indices (1.3-1.4) were prepared through copolymerization of *N*-isopropyl acrylamide (NIPAM) and tetra(phenyl)ethene (TPE)-based acrylate monomers. Copolymers **P1-6** show comparable thermal stability to poly(*N*-isopropylacrylamide) (PNIPAM), while their glass transition temperatures are higher by 7-9 °C than that of pristine PNIPAM. Copolymers **P1-6** are soluble in common organic solvents as well as in water. They retain the similar thermal sensitivity to PNIPAM, but their lower critical solution temperatures (LCST) are reduced with increase of TPE content. By changing the molar ratio of **P1-6**/poly(methacrylic acid) (PMAA) and pH, complexes **P1-6**/PMMA were studied by fluorescence spectroscopy and dynamic light scattering (DLS). The complexes are non-emissive in THF, and their fluorescence can be turned on upon addition of water. Moreover, their fluorescence is enhanced with the decrease in pH values due to the formation of interpenetrating polymer networks (IPNs) through inter-polymer hydrogen bonding. Fluorescence spectroscopy and DLS results also reveal that the phase transition behaviour of IPNs upon heating could be significantly modified by pH change. Reduction in pH value from 7.0 to 4.0 leads to the decrease in LSCT of IPNs by up to 5 °C with respect to PNIPAM. By tuning pH value to dissociate the formed inter-polymer hydrogen bonds, the formed IPNs would be able to fold cooperatively to a compact structure without a loss of solubility at temperatures below the LCST. Thus, these novel IPNs with AIE active moieties would be used as a drug delivery system, in which the release process could be readily monitored by fluorescence spectroscopy.

ARTICLE

Introduction

Over the last few decades, dual or multi-responsive polymers have been receiving more attentions with a special emphasis on the temperature and pH sensitiveness.¹ Polymer hydrogels are water-swollen polymer networks which are cross-linked through physical or chemical bonding. Some of hydrogels exhibit sensitive response to external stimuli, such as pH and temperature. Due to their potential applications in biological systems, those hydrogels have been extensively investigated in many areas, such as controlled drug delivery,² molecular separation,³ tissue culture substrates,⁴ and enzyme activity controlling systems.⁵

Typically, copolymers with multi-responsive characteristics, which are usually prepared through copolymerization of at least two monomers with respective peculiarities, are employed to generate interpenetrating polymer networks (IPNs) with multi-responsive properties.⁶ An alternative method has received more attentions, in which the combined property can be easily tuned by chain interpenetration of two polymers with respective properties.⁷ Each polymer retains its own property while proportion of each can be varied independently of the other, because there is no chemical bonding between two polymers.

Poly(methacrylic acid) (PMAA) is an ionizable hydrophilic polymer due to ionization/deionization of carboxylic acid groups, and thus its swelling behavior is greatly pH-dependent. At a low pH condition, $-COOH$ groups are not ionized and cling to PMAA network at its collapsed state through hydrogen bonding. While at a high pH condition, the $-COOH$ groups are ionized and the charged $-COO^-$ groups repel each other, leading to PMAA swelling. Poly(*N*-isopropyl acrylamide) (PNIPAM) is a temperature-sensitive polymer, which shows drastic swelling transition at its lower critical solution temperature (LCST) of 32 °C.⁸ At a low T (< 32 °C) the gel is swollen, while at a high T (> 32 °C) the polymer dehydrates to the collapsed state due to breakdown of the delicate hydrophilic/hydrophobic balance in the network structure. IPNs generated by PMAA and PNIPAM exhibited combined pH- and temperature-sensitivity. Due to the potential application in the real controlled drug delivery, the formation and interactions of such IPNs were investigated by several analytical methods, such as attenuated total reflectance Fourier transform infrared spectroscopy,⁹ viscometric method,¹⁰ equilibrium swelling and oscillatory swelling studies,¹¹ and high-sensitivity differential scanning calorimetry.¹² However, those methods did not easily track the status of IPNs and thus unable to real-time monitor the controlled drug delivery. The fluorescence methodology may be ideal for those purposes due to its ultrahigh sensitivity, superfast response and convenient process.

Recently, although fluorescence probes have attracted increasing interest, the formation and interaction of IPNs formed from PMAA and PNIPAM have been rarely investigated by fluorescence spectroscopy mainly due to lack of suitable luminogens which exhibit sensitive response to external stimuli

especially in an aqueous solution.¹³ Several fluorophores, such as pyrene, rhodamine and tetraphenylethene (TPE), were covalently attached to PNIPAM chains to investigate their thermal transitions by fluorescence methodology. The fluorescence spectrum of the pyrene containing copolymer in general comprises monomer and excimer emissions, in which the ratio of these two types of emissions varies with temperature change.¹⁴ The rhodamine system displays a temperature dependent fluorescence, which is caused by the PNIPAM dehydration at high temperatures under acidic conditions.¹⁵ However, those common luminogens are not supreme models for the fluorescence probes since the aggregation-caused quenching effect is undesirable to a practical application, leading to reduction in efficiencies and sensitivities of sensors or probes. TPE is an unusual luminogen system in which aggregation works constructively rather than destructively in a conventional system, which exhibits high sensitivity to environment changes, such as temperature, hydrophobicity and steric hinderance.¹⁶ The emission is induced by aggregate formation, and thus this phenomenon is termed as aggregation induced emission (AIE). Due to the uniqueness of AIE luminogens that are emissive in the solid state, their applications for optoelectronics,¹⁷ fluorescence sensors,¹⁸ cell imaging,¹⁹ and explosive chemicals detection²⁰ have been increasingly paid attentions recently.

By covalently attaching TPE into PNIPAM chain through a triazole linkage, PNIPAM displayed high fluorescence sensitivity on the thermally induced chain aggregation of PNIPAM under neutral condition, which was used as a fluorescent thermometer to monitor the thermal transition of PNIPAM in water.^{16a} While the conformation of PNIPAM chain is very sensitive to its structure, even a subtle modification in the structure can lead to a huge change.²¹ In order to minimize this negative effects, we here incorporated TPE with alkyl linkage into PNIPAM chains through copolymerization of monomer with TPE (**M1-3**) and *N*-isopropyl acrylamide (NIPAM). The resultant copolymers could function as a fluorescence probe to track the interaction of PMAA and PNIPAM during IPNs formation under different conditions, including pH, component ratio and temperature.

Experimental**General.**

All synthetic manipulations were carried out under an atmosphere of dry argon gas using standard vacuum-line Schlenk techniques. All solvents were degassed and purified before use according to standard literature methods. Diethyl ether, hexanes, tetrahydrofuran, and toluene were purchased from Aldrich Chemical Co. Inc. and distilled from sodium/benzophenone ketyl before use.

Materials.

NIPAM was purchased from Aldrich and purified by crystallization before use. 2,2'-azoisobutyronitrile (AIBN) was purchased from Aldrich and purified by crystallization before use. Other commercially available reagents and solvents were used as received. PMAA was purchased from Aldrich, and the molecular weight is 9.5 kDa according to GPC.

Instrumentation.

^1H and ^{13}C nuclear magnetic resonance (NMR) spectra were recorded on a Bruker DRX 400-MHz NMR spectrometer in CDCl_3 at room temperature using tetramethylsilane (TMS) as an internal standard. Operating frequencies of the NMR spectrometer were 400.13 MHz (^1H) and 100.61 MHz (^{13}C). High resolution MS (HRMS) were recorded using a Micromass 7034E mass spectrometer. Elemental analysis was conducted on a Perkin-Elmer 240C elemental analyzer for C, H, and N determination. UV-vis and fluorescence spectra were obtained using a Shimadzu UV3101PC UV-vis-NIR spectrophotometer and a Perkin-Elmer LS 50B luminescence spectrometer with a Xenon lamp as light source, respectively. Thermal analysis was performed on a Perkin-Elmer thermogravimetric analyzer (TGA 7) in nitrogen or in air at a heating rate of $20\text{ }^\circ\text{C}/\text{min}$ and on a TA Instruments Differential Scanning Calorimetry (DSC) 2920 at a heating rate and a cooling rate of $5\text{ }^\circ\text{C}/\text{min}$ in nitrogen. Dynamic light scattering experiments were performed on a Brookhaven 90 plus spectrometer with a temperature controller. An argon ion laser operating at 633 nm was used as light source.


Preparation of interpolymer complexes.

Stock solutions of copolymer and PMAA in a water or buffer solution were used for preparation of inter-polymer complexes. They were prepared by a drop wise addition of the PMAA stock solution to copolymer stock solution under continuous stirring. The mixtures were incubated at room temperature for 1 day prior to the experiment. Polymer composition in the complexes was presented by the polymer molar ratio r , i.e., the ratio of molar concentrations of PNIPAM and PMAA. Inter-polymer composition of copolymer was kept constant as 0.50 mg/mL. The pH of the complexes was varied by using appropriate buffers solution: 10 mM buffer system of sodium phosphate and citric acid, pH ranging from 2.8 to 7.0.

Synthesis of compounds and polymers.

4-(1,2,2-triphenylvinyl)phenyl acrylate (M1). 4-(1,2,2-triphenylvinyl)phenol (522.6 mg, 1.5 mmol) was dissolved in dry dichloromethane (10.0 mL). After adding 3.0 equiv. of triethylamine (607.0 μL , 4.5 mmol) to the solution, 2.0 equiv. of acryloyl chloride (235.0 μL , 3.0 mmol) were added drop wise at $0\text{ }^\circ\text{C}$. The mixture was then stirred at room temperature for 4 h. The ammonia salts were filtered off and the solvent was evaporated. The crude product was purified on silica gel using column chromatography with a dichloromethane and hexane (1:2) mixture as the eluent, giving the desired product as white solids 567.8 mg (yield: 94.0%). ^1H NMR (CDCl_3): δ 7.14-7.06 (m, 17H), 6.91 (d, 2H, $J = 8.0$ Hz), 6.58 (d, 1H, $J = 16.8$ Hz), 6.30 (dd, 1H, $J = 6.8, 10.5$ Hz), 5.99 (d, 1H, $J = 10.5$ Hz). ^{13}C NMR (CDCl_3): δ 164.2, 149.1, 143.7, 143.6, 141.5, 141.4, 140.1, 132.5,

132.4, 131.5, 131.4, 128.1, 127.9, 127.8, 126.7, 126.6, 120.8. IR (thin film): $\nu = 3075, 3049, 3120, 2924, 1952, 1903, 1805, 1745, 1739, 1638, 1598, 1503, 1492, 1443, 1297, 1248, 1199, 1170, 1147, 1022, 997, 902, 764, 753, 701, 614\text{ cm}^{-1}$. HRMS (ESI): $[\text{M} + \text{Na}^+]$ calcd for $\text{C}_{29}\text{H}_{22}\text{O}_2\text{Na}$, m/z 425.1517; found, m/z 425.1534.

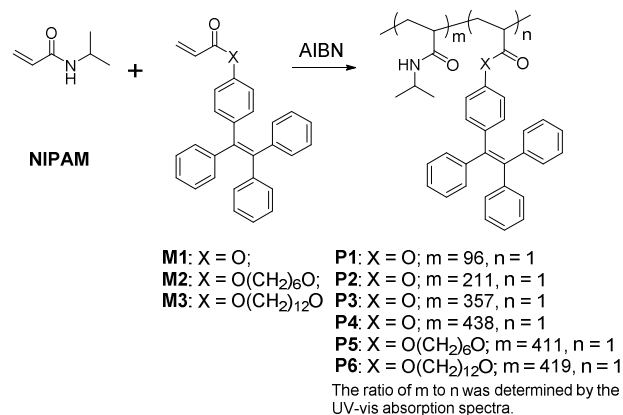

Scheme 1. Synthetic route of monomer copolymers (**P1-6**).

General procedure for copolymerization.

All polymers were prepared by free radical polymerization of the corresponding monomers in the presence of AIBN. A solution of 0.50 mmol of monomer and 1.5 mg of AIBN dissolved in 1.0 mL of dry THF was degassed by three freeze/thaw cycles. The solutions were stirred for 48 h at $70\text{ }^\circ\text{C}$ in sealed vessels. The reaction mixture was added dropwise into diethyl ether with stirring, and then the precipitate was collected by filtration. This purification process was repeated several times to ensure all unreacted starting materials were removed. The polymer was re-dissolved in 5.0 mL of THF and re-precipitated with Et_2O to afford a white solid. The polymer was then filtered and dried under vacuum at $40\text{ }^\circ\text{C}$ for 72 hours for further analysis.

Table 1. Molecular weight, polydispersity (*PDI*) and thermal data of PNIPAM and **P1-6**.^a

Polymers	Feed ratio x : y	Experimental m : n	M_w (10^4)	M_n (10^4)	<i>PDI</i>	T_d^b	T_g
PNIPAM	-	-	1.48	1.01	1.4	357	130
P1	100 : 1	96 : 1	1.62	1.23	1.3	361	138
P2	200 : 1	211 : 1	1.46	1.13	1.3	360	137
P3	300 : 1	357 : 1	1.49	1.15	1.3	357	138
P4	400 : 1	438 : 1	1.60	1.18	1.4	359	139
P5	400 : 1	411 : 1	1.63	1.19	1.4	360	138
P6	400 : 1	419 : 1	1.61	1.19	1.4	361	140

^a M_w : the weight-average molecular weight. M_n : the number-average molecular weight. ^b T_d : the decomposition temperature at which 5% weight loss occurs.

Copolymer **P1**. Yield: 85%; ^1H -NMR (CDCl_3): δ 3.99-3.88 (m, 2H), 2.23-1.40 (m, 3H), 1.14 (s, 6H). Anal. Calcd for $(\text{C}_6\text{H}_{11}\text{NO})_n$: C, 63.69; H, 9.80; N, 12.38. Found: C, 63.74; H, 9.68; N, 12.37. IR (thin film): $\nu = 3436, 3300, 3077, 2974, 2936, 2877, 1651, 1548, 1459, 1388, 1368, 1276, 1172, 1131, 701\text{ cm}^{-1}$.

Copolymer **P2**. Yield: 87%; ^1H -NMR (CDCl_3): δ 3.99-3.73 (m, 2H), 2.23-1.40 (m, 3H), 1.14 (s, 6H). Anal. Calcd for $(\text{C}_6\text{H}_{11}\text{NO})_n$: C, 63.69; H, 9.80; N, 12.38. Found: C, 63.73; H,

9.82; N, 12.36. IR (thin film): $\nu = 3437, 3299, 3077, 2974, 2936, 2877, 1651, 1549, 1459, 1388, 1368, 1277, 1173, 1131, 702 \text{ cm}^{-1}$.

Copolymer **P3**. Yield: 84%; $^1\text{H-NMR}$ (CDCl_3): δ 3.99 (br, 2H), 2.23-1.40 (m, 3H), 1.14 (s, 6H). Anal. Calcd for $(\text{C}_6\text{H}_{11}\text{NO})_n$: C, 63.69; H, 9.80; N, 12.38. Found: C, 63.72; H, 9.81; N, 12.37. IR (thin film): $\nu = 3440, 3301, 3077, 2975, 2936, 2877, 1652, 1549, 1459, 1388, 1368, 1277, 1173, 1131, 701 \text{ cm}^{-1}$.

Copolymer **P4**. Yield: 88%; $^1\text{H-NMR}$ (CDCl_3): δ 3.99 (br, 2H), 2.23-1.40 (m, 3H), 1.14 (s, 6H). Anal. Calcd for $(\text{C}_6\text{H}_{11}\text{NO})_n$: C, 63.69; H, 9.80; N, 12.38. Found: C, 63.70; H, 9.82; N, 12.38. IR (thin film): $\nu = 3441, 3300, 3077, 2975, 2937, 2877, 1652, 1550, 1459, 1388, 1368, 1278, 1173, 1131, 701 \text{ cm}^{-1}$.

Copolymer **P5**. Yield: 79%; $^1\text{H-NMR}$ (CDCl_3): δ 3.99-3.88 (m, 2H), 2.26-1.43 (m, 3H), 1.14 (s, 6H). Anal. Calcd for $(\text{C}_6\text{H}_{11}\text{NO})_n$: C, 63.69; H, 9.80; N, 12.38. Found: C, 63.71; H, 9.83; N, 12.37. IR (thin film): $\nu = 3441, 3299, 3080, 2975, 2937, 2877, 1647, 1551, 1460, 1388, 1369, 1280, 1244, 1173, 1132, 701, 668 \text{ cm}^{-1}$.

Copolymer **P6**. Yield: 86%; $^1\text{H-NMR}$ (CDCl_3): δ 3.98 (s, 1H), 3.56 (s, 2H) 2.26-1.43 (m, 2H), 1.14 (s, 6H). Anal. Calcd for $(\text{C}_6\text{H}_{11}\text{NO})_n$: C, 63.69; H, 9.80; N, 12.38. Found: C, 63.70; H, 9.81; N, 12.36. IR (thin film): $\nu = 3438, 3300, 3081, 2975, 2937, 2878, 1650, 1550, 1459, 1389, 1369, 1336, 1280, 1245, 1173, 1132, 701, 668 \text{ cm}^{-1}$.

Results and Discussion

Synthesis and characterization of monomers and related copolymers.

The synthetic routes leading to copolymers **P1-6** are shown in Scheme 1. **M1** could be prepared in a yield of 94% by reaction of 4-(1,2,2-triphenylvinyl)phenol with acryloyl chloride in presence of triethylamine in dry dichloromethane. Monomers **M2** and **M3** was prepared according to our previous work (Scheme S1). Poly(N-isopropyl acrylamide-co-tetra(phenyl)ethene acrylate) **P1-6** were prepared from a mixture of monomers **M1-3** and NIPAM in different ratios by radical polymerization using AIBN as a radical initiator. **P1-6** were purified by re-precipitation twice in diethyl ether to give white solids with 79-85% isolated yields.

P1-6 are not only soluble in many common organic solvents, such as tetrahydrofuran (THF), dichloromethane, chloroform, methanol and dimethyl sulfoxide (DMSO), but also in water. **P1-6** were structurally characterized by various spectroscopic methods and elemental analysis. Using **P1** as an example, the ^1H NMR spectrum of **P1** is illustrated in Figure S1 (ESI). The presence of signals at δ 7.00-6.52 corresponding to protons of TPE indicated that the TPE residues remained intact during the radical polymerization and purification process. The molecular weights of those copolymers against polystyrene standards were determined by gel permeation chromatography (GPC) and the data are summarized in Table 1. **P1-6** have high molecular weights of 14,600-16,300 with relatively narrow polydispersity index of 1.3-1.4. Those polymers exhibit high thermal stability with decomposition temperatures ranging from 357 to 361 °C under nitrogen, which are comparable to 357 °C of PNIPAM (Figure S2a). The DSC study indicates that **P1-6** exhibit glass transition temperature of 138-140 °C under nitrogen, which is slightly higher than that of PNIPAM ($\Delta T_g > 7$ °C, ESI, Figure

S2b). The ratio of TPE to NIPAM was determined by UV-vis absorption spectra (ESI, Figure S3).

AIE properties of copolymers.

P1-6 were non-emissive when dissolved in THF, which is a good solvent for both of TPE and NIPAM. **P1-6** with different degrees of TPE labelling also showed similar AIE properties. Taking **P4** solution in THF as an example (Figure S4), the fluorescence started to become obvious when a large amount of H_2O (> 70%) was added, indicating that TPE maintained its AIE activity after being incorporated into the polymer NIPAM, which were further evidenced by the strong emission of films fabricated from **P1-6** and **M1-3** (ESI, Figure S5). When compared to **P1-6** films, obvious red-shifts (4-6 nm) in emission spectra were found for the **M1-3** films, implying their better stacking in solid state. The AIE property of **P4**/PMAA complex in THF/ H_2O mixture was studied. As shown in Figure 1, the mixture showed very good solubility in pure THF and was non-emissive. While increasing water content, the fluorescence could be turned on when water content is 60%, and finally reached the maximum fluorescence intensity in 100% water. The **P4**/PMAA complex showed similar AIE properties to **P4**, but emitted 1.5-fold stronger fluorescence than that of neat **P4** with the same concentration, because the polymer interaction suppressed the molecular motions of TPE.^{16a} Another possibility to restrict the TPE motion is that the entangling of polymer chains may lead to the enhancement in fluorescence. No obvious increase in fluorescence intensity in a non-hydrogen-bonded system **P4**/polystyrene indicates that entangling of polymer chains has no effect on the fluorescence enhancement (ESI, Figure S6).

Considering the good fluorescence response of TPE to the phase change of polymer chain, TPE could be used as a fluorescence probe to investigate the formation of hydrogen bond in PMAA and PNIPAM interpenetrating polymer networks.

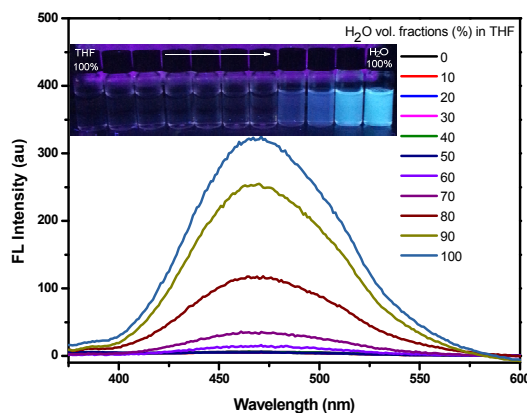


Figure 1. Fluorescence spectra of **P4**/PMAA in THF/ H_2O ; $\lambda_{\text{ex}} = 318 \text{ nm}$; [**P4**] = 0.5 mg/mL, 5.0 equiv. of PMAA, 20 °C, inserts are photographs of **P4**/PMAA solutions taken under UV illumination (365 nm).

The thermally induced fluorescence of copolymers.

Figure 2a shows the effect of temperature on **P1-6** fluorescence in an aqueous solution. Taken **P4** for example, a small change for

the emission intensity was observed when **P4** was heated from 14.0 to 25.0 °C, and a continuous increase in fluorescence intensity was recorded in the range of 25.0 to 30.0 °C, finally the fluorescence intensity reached the maximum at 32.5 °C. Further heating to 50.0 °C led to no change in the fluorescence intensity. When cooled down from 50.0 to 14.0 °C, a reversible temperature-dependent fluorescence curve was obtained with the same trend in the same temperature regions (ESI, Figure S6a). This phenomenon is supported by dynamic light scattering (DLS) and solution turbidity measurements (Figure 2b and Figure S6b), which shows the reversible temperature-dependent particle size and solution turbidity curves, implying **P4** chains swell well in water at the beginning and start to collapse at 22.5 °C due to dehydration, and particle reaches the smallest size at 32.5 °C.

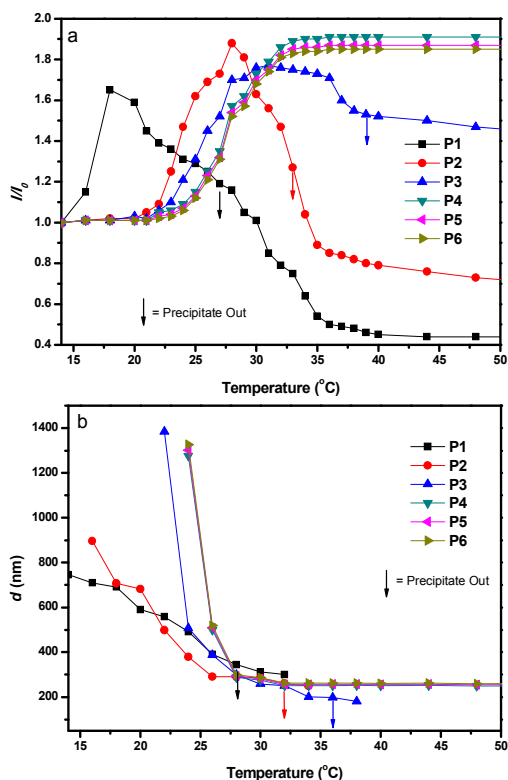


Figure 2. (a) Plot of I/I_0 vs temperature of **P1-P6** in H_2O . (b) The particle size vs temperature of **P1-P6** in H_2O . Concentration of polymer is 0.50 mg/mL, I_0 = intensity at 469 nm at 14 °C, excited at 318 nm.

As shown in Figure 2, **P1-3** with higher degree of labeled TPE, display down-shift LSCT and easily precipitate out when heating. It is well-known that the conformation of PNIPAM chain is very sensitive to its structure, and even a subtle modification in the structure can result in a huge change.²¹ Thus, by tuning the degree of labelled TPE, the conformation of PNIPAM chain could be modified well, and **P4-P6** with a very low degree of labeled TPE keep the similar conformation of PNIPAM.


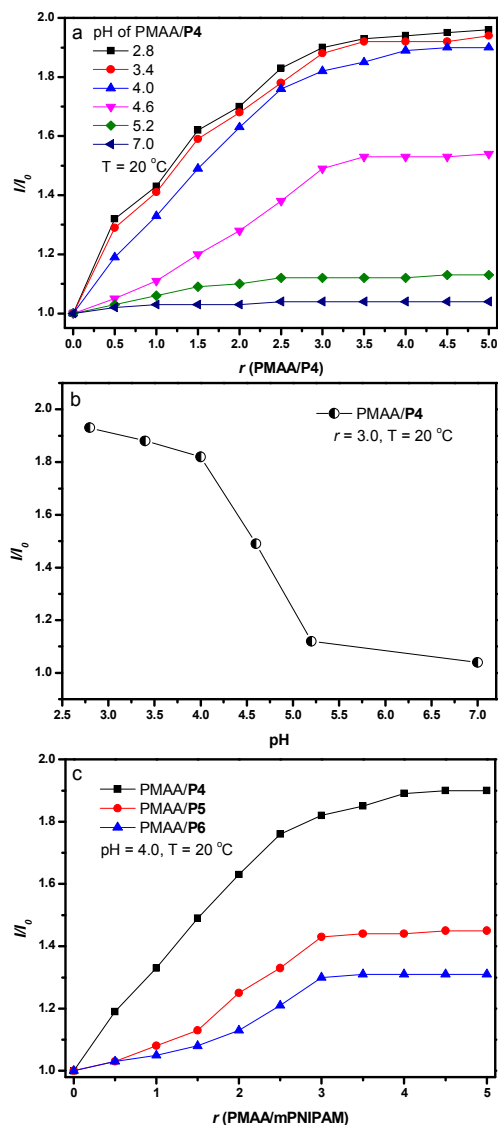


Figure 3. (a) Plot of I/I_0 vs ratio of PMMA and **P4** at different pH, $r = 0-5.0$, $pH = 2.8-7.0$. (b) Plot of I/I_0 vs pH at $r = 3.0$. (c) Plot of I/I_0 vs ratio of PMMA and **P4-6** at $pH = 4.0$. [Copolymer] = 0.5 mg/mL, 10.0 mM Na_2HPO_4 -citric acid buffer, I_0 = intensity at 469 nm at 20 °C, $\lambda_{ex} = 318$ nm.

The starting point of fluorescence enhancement for **P4** little relates to its concentration, e.g. from 0.1 to 1.0 mg/mL (ESI, Figure S7). However, the fluorescence intensity of polymers with a higher concentration, such as 1.0 mg/mL solution, decreased swiftly on heating from 37.0 to 50.0 °C, due to its precipitation at a higher temperature than LCST. Moreover, as shown in Figure 2, **P1-3** with higher TPE labeling degrees showed lower LSCT of 30.0, 28.5 and 18.0 °C, respectively. As the hydrophobic interaction between the TPE residues may enable the aggregation of PNIPAM chains to conglobulate.^{16a} While **P5** and **P6** functioned similarly as **P4**, and the LSCTs were not changed, although TPE was attached into PNIPAM chain through an alkyl linkage. Thus, **P4-6** with a lowest degree of TPE maintained the same LSCT as PNIPAM, and the LSCT of copolymers could be tuned by adjusting the degree of TPE residues in copolymers.

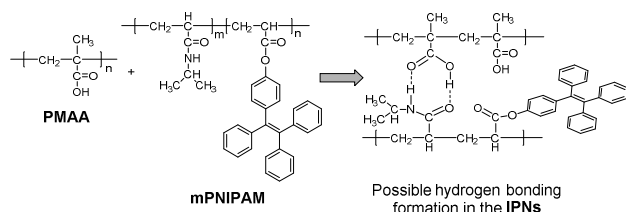

Scheme 2. The illustration of PMAA, PNIPAM and the hydrogen-bond formation between the two networks in the IPNs.

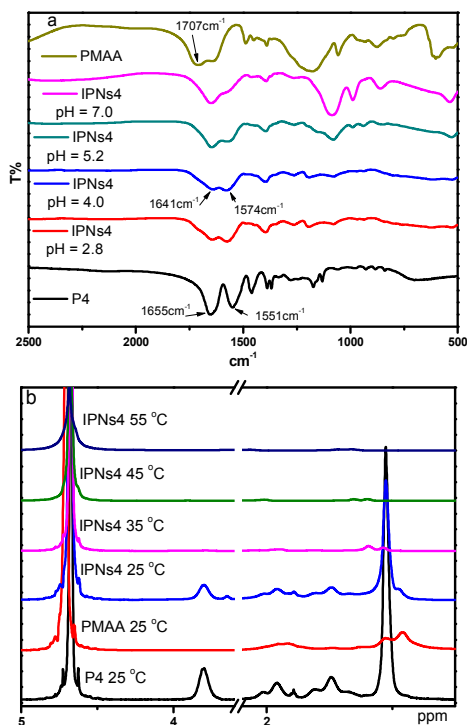


Figure 4. (a) FTIR Spectra of solid **P4** and IPNs4 at different pH conditions. IPNs4 solid samples were prepared from solutions by freeze drying to remove water. (b) ^1H NMR spectra of **P4**, PMAA and IPNs4 in D_2O at various temperatures, $[\text{P4}] = 0.50 \text{ mg/mL}$, $r = 3.0$.

Formation of interpenetrating polymer networks.

Scheme 2 illustrates the hydrogen bond formation in IPNs formed by **P4** and PMAA. The formation and interaction of hydrogen bonding between PMAA and **P4** was investigated by fluorescence spectroscopy in the pH range of 2.8-7.0, and concentration of **P4** was set as 0.50 mg/mL. Figure 3a summarizes the fluorescence spectra of PMAA/**P4** complex with different compositions at pH 2.8, 3.4, 4.0, 4.6, 5.2 and 7.0, respectively. Pronounced changes in fluorescence intensity were observed upon PMAA addition at pH values less than 5.2, and fluorescence was further enhanced until the ratio of PMAA and polymer (r) is 3.0. As shown in Figure 3b, fluorescence enhancement fold reached maximum of 1.93 at pH 2.8. When the pH was increased to 7.0, fluorescence enhancement was not observed even with addition of high excess of PMAA (ca. 10-fold), suggesting no strong interaction takes place between **P4** and PMAA. In another words, no inter-polymer complexes are formed between **P4** and PMAA although mixed in the solution.

This phenomenon could be related to the high ionization degree of PMAA at pH 7.0 that it is not able to form hydrogen bond with PNIPAM, because PMAA has a related low pK_{int} of 4.85.²² All fluorescence changes occurred in a narrow range of r from 1.0 to 3.0, indicative of the cooperative character of IPNs4 formation. However, **P5** and **P6** labeled with TPE units through a longer alkyl chain displayed much lower fluorescence enhancement upon PMAA addition (Figure 3c). FTIR spectra was widely used to verify the formation of hydrogen bonds.²³ Using **P4** and its IPNs as examples, FTIR spectra of **P4**, PMAA and IPNs4 at different pH values were studied. As shown in Figure 4a, the peak at 1707 cm^{-1} represents the carbonyl ($-\text{C}=\text{O}$) stretching vibration in the carboxylic acid groups of PMAA. The peaks at 1655 and 1551 cm^{-1} belong to $-\text{C}=\text{O}$ stretching vibration and $-\text{N}-\text{H}$ deformation in the amide groups in **P4**, respectively. Their mixture, for example, IPNs4 at pH 4.0, exhibits two signals at 1641 and 1574 cm^{-1} , corresponding to the red-shifted $-\text{C}=\text{O}$ stretching vibration of carboxylic acid and amide group of **P4**, and blue-shifted $-\text{N}-\text{H}$ deformation in the amide group, indicating the formation of hydrogen bond between **P4** and PMAA.

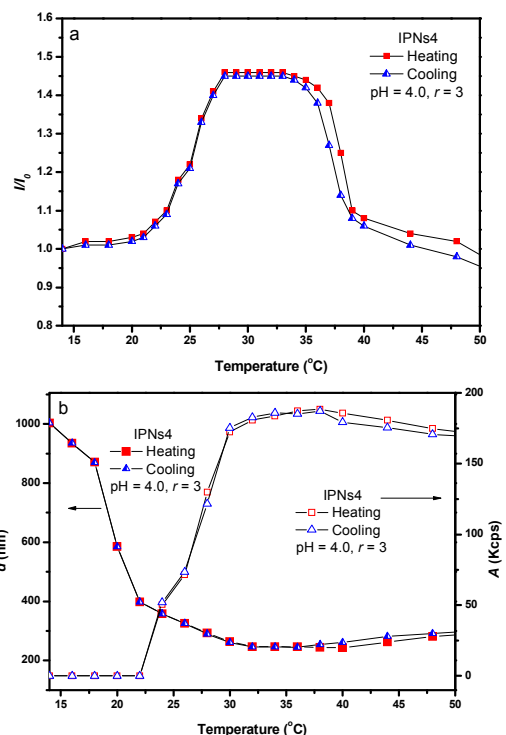


Figure 5. (a) Plot of I/I_0 vs temperature of IPNs4 during a heating and cooling cycle at pH = 4 and $r = 3$. (b) The particle size and solution turbidity (kcps) vs temperature of IPNs4. $[\text{P4}] = 0.50 \text{ mg/mL}$, $r = 3.0$, pH = 4.0, 10.0 mM Na_2HPO_4 -citric acid buffer. I_0 = intensity at 469 nm at $14 \text{ }^\circ\text{C}$, $\lambda_{\text{ex}} = 318 \text{ nm}$.

The temperature dependent fluorescence transition of IPNs4 at a constant mixture composition ($r = 3.0$, Figure 5a) was examined. At pH 4.0, a noticeable difference of fluorescence trend was observed, which could be split to three stages. A big bump in the emission intensity of IPNs4 was found when it is heated from 20.0 to $27.5 \text{ }^\circ\text{C}$, and fluorescence intensity reached

the maximum at 27.5 °C. In the range from 27.5 to 35.0 °C, a stable fluorescence intensity region was recorded, indicating its thermal tolerance during this temperature range. While further heating to 50 °C, a continuous decrease in fluorescence density was observed due to thermally activated molecular motions of TPE,^{16a} which was supported by DLS results that particle sizes became smaller but no precipitation was produced during this heating process (Figure 5b). When cooled down from 50.0 to 14.0 °C, a coincided fluorescence intensity–temperature curve and particle size curve were obtained, implying its good thermal reversibility. The fluorescence and DLS measurements showed the LCST of IPNs4 at 27.5 °C, which was 5.0 °C lower than that of **P4**. The ¹H NMR spectra of IPNs4 are measured in D₂O at various temperatures to give insight into its thermal transitions (Figure 4b). IPNs4 start to dehydrate at 25 °C but still swell well in H₂O. The protons of chains could be identified in the ¹H NMR spectra when temperature is at 25 °C. However, when IPNs4 solution is heated up to 35 °C or higher, IPNs4 collapse to form compact particles and thus lead to gradual decrease in intensity of NMR peaks.

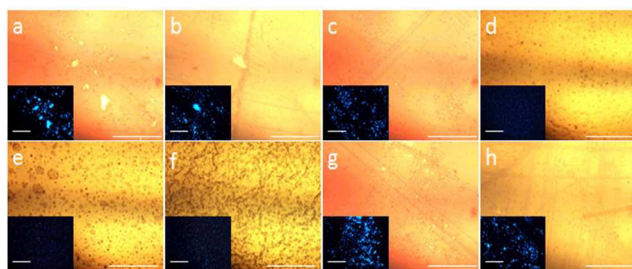


Figure 6. Optical microscopy images and fluorescence microscopy images (inserted photos) of IPNs4 particles under different pH and temperatures: (a) 2.8, 20 °C; (b) 3.4, 20 °C; (c) 4.0, 20 °C; (d) 4.6, 20 °C; (e) 5.2, 20 °C; (f) 7.0, 20 °C; (g) 4.0, 35 °C; (h) 4.0, 50 °C. The fluorescence microscopy images of particles were taken under a fluorescence microscope with a 337 nm excitation; scale bar is 50 μm. [**P4**] = 0.50 mg/mL, $r = 3.0$, 10.0 mM Na₂HPO₄-citric acid buffer.

IPNs4 particles under different pH and temperatures were examined (Figure 6). The IPNs4 particles with a bright blue emission which resembles the stars in the galaxy could be clearly observed upon excitation with UV light (excitation wavelength: 378 nm). Figures 6c, 6g and 6h displayed the IPNs4 particles at 20, 35 and 50 °C, respectively, which is consistent with observations in Figure 5a. Under low pH (2.8, 3.4 and 4.0), IPNs4 formed crystal-like particles with strong fluorescence emission due to the more efficient hydrogen bonding at a lower pH. While at a higher pH than 4.0, IPNs4 become amorphous and emitted less fluorescence.

At higher pH values than pK_{int} (4.85) as shown in Figure 7a, IPNs4 tended to display similar fluorescence behavior to **P4** because of the weaker hydrogen bonding interaction caused by ionization in different degrees of PMAA. On the other hand, decrease in pH from 7.0 to 4.6 led to gentle reduction in LCST from 32.5 to 29.0 °C. For pH 3.4 and 2.8, IPNs4 showed a slight opalescence and started to precipitate out on heating up to 28.0 °C (Figure 7b).

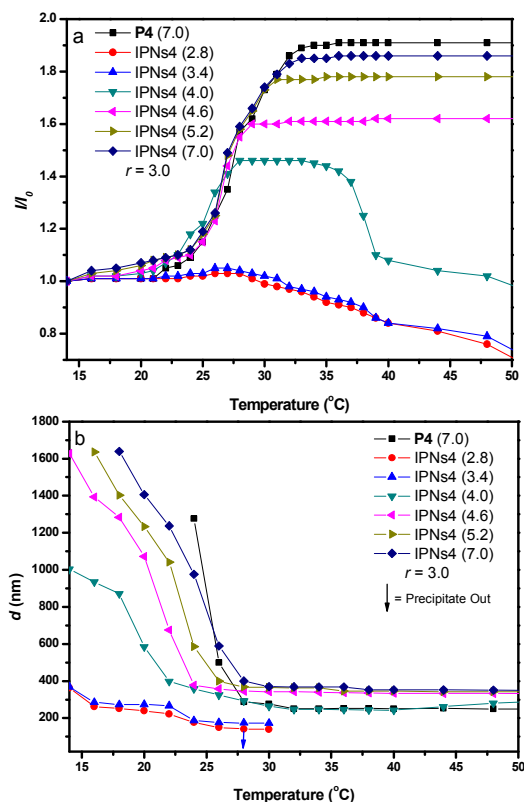


Figure 7. (a) Plot of I/I_0 vs temperature of IPNs4. (b) Plot of the particle size of IPNs4 vs temperature. [**P4**] = 0.50 g/mL, $r = 3.0$, pH = 2.8–7.0, 10.0 mM Na₂HPO₄-citric acid buffer. I_0 = intensity at 469 nm at 14 °C, $\lambda_{ex} = 318$ nm.

Considering the down-shift LSCT together with the fluorescence transition, the effect of mixture composition and pH value on the structure of IPNs4 is illustrated in Figure 8. When pH (7.0, and 5.2) > pK_{int} , less hydrogen bonds between PMAA and PNIPAM were formed because most of carboxylic groups in PMAA were ionized. Even the PMAA content in a mixture was very high (for example, $r = 10.0$), LCST of PNIPAM were only changed slightly. In this case, the length of the hydrophobic PNIPAM blocks in the complexes was long enough to provide high cooperativity of the phase transition of PNIPAM, and thus fluorescence transitions of mixtures show similar trends to **P4**. At pH (4.6, 4.0, 3.4 and 2.8) < pK_{int} , due to the fact that more carboxylic groups in PMAA were protonated, more hydrogen bonds between PNIPAM were generated to form IPNs4. In this condition, the phase transition of PNIPAM will be affected even though PMAA content is low. In the complex of IPNs4, the hydrophobic blocks are much shorter, consequently resulting in the low transition cooperativity. Thus, the down shifts of LSCT for IPNs4 were observed with the increase of pH values.

Overall, the ionized PMAA chains introduced more charges to the mixture of PMAA/**P4**, which improved the solubility of IPNs4 and maintained the cooperativity of phase transition of **P4**. In contrast, PNIPAM chains could be hydrophilized by conjugation with more hydrophilic PMAA to generate IPNs4 though the formation of hydrogen bonding, leading to a decrease in LSCT and **P4** lost its original features as PNIPAM.

Conclusions

In summary, a new type of IPNs was formed through the intermolecular hydrogen bonding interaction between PMAA and PNIPAM containing AIE active TPE. The TPE moieties that were covalently linked to PNIPAM chain displayed highly sensitive response to the phase transition of IPNs, which could be used as a fluorescence probe to track the IPNs' structure changes caused by external pH and temperature. By adjusting pH, the formed IPNs would be able to fold cooperatively to a compact structure without a loss of solubility at temperatures below the LCST. Thus, these IPNs would be used as a convenient drug delivery system, in which the release process can be monitored by fluorescence spectroscopy in situ.

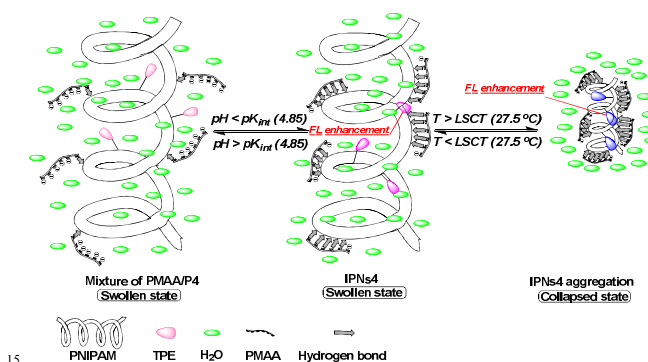


Figure 8. Schematic illustration for the structures of P4/PMAA complexes at different pH and temperatures.

Acknowledgement

The authors would like to acknowledge the financial support (Grant No.: 1321760011) from the Institute of Materials Research and Engineering (IMRE), Agency for Science, Technology and Research (A*STAR).

Notes and references

^a Institute of Materials Research and Engineering, A*STAR (Agency for Science, Technology and Research), 3 Research Link, Singapore 117602, Republic of Singapore. jw-xu@imre.a-star.edu.sg (Jianwei Xu)

^b Department of Chemistry, National University of Singapore, 3 Science Drive 3, Singapore 117543, Republic of Singapore.

^c Department of Chemistry, The Hong Kong University of Science & Technology, Clear Water Bay, Kowloon, Hong Kong, China. tangbenz@ust.hk (Ben Zhong Tang)

- (a) C. M. Chopko, E. L. Lowden, A. C. Engler, L. G. Griffith, P. T. Hammond, *ACS Macro Lett.*, 2012, **1**, 727; (b) C. Zhang, M. Maric, *J. Polym. Sci., Part A: Polym. Chem.*, 2012, **50**, 4341; (c) D. Fournier, R. Hoogenboom, H. M. L. Thijs, R. M. Paulus, U. S. Schubert, *Macromolecules*, 2007, **40**, 915; (d) B. S. Lokitz, A. W. York, J. E. Stempka, N. D. Treat, Y. Li, W. L. Jarrett, C. L. McCormick, *Macromolecules*, 2007, **40**, 6473.
- (a) J. Zhang, L. Wu, F. Meng, Z. Wang, C. Deng, H. Liu, Z. Zhong, *Langmuir*, 2012, **28**, 2056; (b) D. Schmaljohann, *Adv. Drug Delivery Rev.*, 2006, **58**, 1655; (c) C. Ramkissoon-Ganorkar, A. Gutowska, F. Liu, M. Baudys, S. W. Kim, *Pharm. Res.*, 1999, **16**, 819.
- H. Feil, Y. H. Bae, J. Feijen, S. W. Kim, *J. Membr. Sci.*, 1991, **64**, 283.
- T. Takezawa, Y. Mori, K. Yoshizato, *Biotechnology*, 1990, **8**, 854.

- F. Liu, G. L. Tao, R. X. Zhuo, *Polym. J.*, 1993, **25**, 561.
- (a) P. Shi, Q. Li, X. He, S. Li, P. Sun, W. Zhang, *Macromolecules*, 2014, **47**, 7442; (b) R. T. Pearson, N. J. Warren, A. L. Lewis, S. P. Armes, G. Battaglia, *Macromolecules*, 2013, **46**, 1400; (c) K. Bauri, S. Pant, S. G. Roy, P. De, *Polym. Chem.*, 2013, **4**, 4052; (d) J. Qian, F. Wu, *J. Mater. Chem. B*, 2013, **1**, 3464; (e) C. T. Huynh, M. K. Nguyen, J. H. Kim, S. W. Kang, B. S. Kim, D. S. Lee, *Soft Matter*, 2011, **7**, 4974; (f) Z. Xing, C. Wang, J. Yan, L. Zhang, L. Li, L. Zha, *Soft Matter*, 2011, **7**, 7992; (g) C. Ramkissoon-Ganorkar, A. Gutowska, F. Liu, M. Baudys, S. W. Kim, *Pharm. Res.*, 1999, **16**, 819; (h) Y. H. Lim, D. Kim, D. S. Lee, *J. Appl. Polym. Sci.*, 1997, **64**, 2647; (i) C. S. Brazel, N. A. Peppas, *J. Controlled Release*, 1996, **39**, 57; (j) G. Chen, A. S. Hoffman, *Nature*, 1995, **373**, 49.
- (a) D. Klemmner, K. C. Frisch, Eds. *Advances in Interpenetrating Polymer Networks*; Technomic: Lancaster, PA, 1994; (b) L. H. Sperling, *Interpenetrating Polymer Networks and Related Materials*; Plenum: New York, 1981.
- (a) Z. M. O. Rzaev, S. Dincer and E. Piskin, *Prog. Polym. Sci.*, 2007, **32**, 534; (b) G. Zhang and C. Wu, *Adv. Polym. Sci.*, 2006, **195**, 101; (c) H. G. Schild, *Prog. Polym. Sci.*, 1992, **17**, 163; (d) H. Inomata, S. Goto and S. Saito, *Macromolecules*, 1990, **23**, 4887.
- J. Zhang, N. A. Peppas, *J. Appl. Polym. Sci.*, 2001, **82**, 1077.
- G. Staikos, K. Karayanni, Y. Mylonas, *Macromol. Chem. Phys.*, 1997, **198**, 2905.
- J. Zhang, N. A. Peppas, *Macromolecules*, 2000, **33**, 102.
- T. V. Burova, N. V. Grinberg, V. Ya. Grinberg, E. V. Kalinina, V. I. Lozinsky, V. O. Aseyev, S. Holappa, H. Tenhu, A. R. Khokhlov, *Macromolecules*, 2005, **38**, 1292.
- (a) T. Swift, L. Swanson, S. Rimmer, *RSC Adv.*, 2014, **4**, 57991; (b) W. Zheng, L. He, *Biomater. Sci.*, 2014, **2**, 1471; (c) A. Aied, B. Glynn, H. Cao, Y. Zheng, H. Tai, A. Pandit, W. Wang, *Polym. Chem.*, 2012, **3**, 332; (d) X. Ji, Y. Yao, J. Li, X. Yan, F. Huang, *J. Am. Chem. Soc.*, 2013, **135**, 74.
- F. M. Winnik, *Macromolecules*, 1990, **23**, 233.
- Y. Shiraishi, R. Miyamoto, X. Zhang and T. Hirai, *Org. Lett.*, 2007, **9**, 3921.
- (a) L. Tang, J. K. Jin, A. Qin, W. Z. Yuan, Y. Mao, J. Mei, J. Z. Sun, B. Z. Tang, *Chem. Comm.*, 2009, 4974; (b) B. Z. Tang, X. Zhan, G. Yu, P. S. Lee, Y. Liu, D. Zhu, *J. Mater. Chem.*, 2001, 2974; (c) J. Luo, Z. Xie, J. W. Y. Lam, L. Cheng, C. Qiu, H. D. Kwok, X. Zhan, Y. Liu, D. Zhu, B. T. Tang, *Chem. Comm.*, 2001, 1740.
- (a) Z. Zhao, S. Chen, J. W. Y. Lam, P. Lu, Y. Zhong, K. S. Wong, H. S. Kwok, B. Z. Tang, *Chem. Commun.*, 2010, **46**, 2221; (b) V. S. Vyas, R. Rathore, *Chem. Commun.*, 2010, **46**, 1065.
- (a) X. Shen, Y. Shi, B. Peng, K. Li, J. Xiang, G. Zhang, Z. Liu, Y. Cheng and D. Zhang, *Macromol. Biosci.*, 2012, **12**, 1583; (b) M. Wang, G. Zhang, D. Zhang, D. Zhu and B. Z. Tang, *J. Mater. Chem.*, 2010, **20**, 1858; (c) Y. Hong, H. Xiong, J. W. Y. Lam, M. Haessler, J. Liu, Y. Yu, Y. Zhong, H. H. Y. Sung, I. D. Williams, K. S. Wong and B. Z. Tang, *Chem.-Eur. J.*, 2010, **16**, 1232; (d) Y. Liu, Y. Tang, N. N. Barashkov, I. S. Irgibaeva, J. W. Y. Lam, R. Hu, D. Birimzhanova, Y. Yu and B. Z. Tang, *J. Am. Chem. Soc.*, 2010, **132**, 13951; (e) Y. Hong, M. Haessler, J. W. Y. Lam, Z. Li, K. K. Sin, Y. Dong, H. Tong, J. Liu, A. Qin, R. Renneberg and B. Z. Tang, *Chem.-Eur. J.*, 2008, **14**, 6428; (f) T. L. Andrew and T. M. Swager, *J. Am. Chem. Soc.*, 2007, **129**, 7254; (g) S. J. Toal, K. A. Jones, D. Magde and W. C. Trogler, *J. Am. Chem. Soc.*, 2005, **127**, 11661.
- (a) F. Mahtab, Y. Yu, J. W. Y. Lam, J. Liu, B. Zhang, P. Lu, X. Zhang and B. Z. Tang, *Adv. Funct. Mater.*, 2011, **21**, 1733; (b) M. Faisal, Y. Hong, J. Liu, Y. Yu, J. W. Y. Lam, A. Qin, P. Lu and B. Z. Tang, *Chem.-Eur. J.*, 2010, **16**, 4266; (c) W. C. Wu, C. Y. Chen, Y. Tian, S. H. Jang, Y. Hong, Y. Liu, R. Hu, B. Z. Tang, Y. T. Lee, C. T. Chen, W. C. Chen and A. K. Y. Jen, *Adv. Funct. Mater.*, 2010, **20**, 1413; (d) J. Liu, J. W. Y. Lam and B. Z. Tang, *J. Inorg. Organomet. Polym. Mater.*, 2009, **19**, 249; (e) S. Kim, H. E. Pudavar, A. Bonoiu and P. N. Prasad, *Adv. Mater.*, 2007, **19**, 3791.
- (a) H. Zhou, J. Li, M. H. Chua, H. Yan and B. Z. Tang, *J. Xu. Polym. Chem.*, 2014, **5**, 5628; (b) H. Zhou, Q. Ye, W. T. Neo, J. Song, H. Yan, Y. Zong, B. Z. Tang, T. S. A. Hor, J. Xu, *Chem. Commun.*, 2014, **50**, 13785; (c) J. Li, J. Liu, Jacky, W. Y. Lam, B. Z. Tang, *RSC Advances*, 2013, **3**, 8193; (d) R. Hu, J. L. Maldonado, M. Rodriguez,

- C. Deng, C. K. W. Jim, Jacky, W. Y. Lam, M. M. F. Yuen, G. Ramos-Ortiz, B. Z. Tang, *J. Mater. Chem.*, 2012, **22**, 232; (e) X.-M. Hu, Q. Chen, D. Zhou, J. Cao, Y.-J. He, B.-H. Han, *Polym. Chem.*, 2011, **2**, 1124; (f) J. Liu, Y. Zhong, P. Lu, Y. Hong, J. W. Y. Lam, M. Faisal, Y. Yu, K. S. Wong and B. Z. Tang, *Polym. Chem.*, 2010, **1**, 426; (g) A. Qin, J. W. Y. Lam, L. Tang, C. K. W. Jim, H. Zhao, J. Sun, B. Z. Tang, *Macromolecules*, 2009, **42**, 1421.
- 21 (a) Z. M. O. Rzaev, S. Dincer and E. Piskin, *Prog. Polym. Sci.*, 2007, **32**, 534; (b) G. Zhang and C. Wu, *Adv. Polym. Sci.*, 2006, **195**, 101; (c) H. G. Schild, *Prog. Polym. Sci.*, 1992, **17**, 163; (d) H. Inomata, S. Goto and S. Saito, *Macromolecules*, 1990, **23**, 4887.
- 22 C. Tanford, *Physical Chemistry of Macromolecules*; John Wiley & Sons: New York, 1961; p 550.
- 23 (a) D. Cai, Z. Wu, J. Jiang, Y. Wu, H. Feng, I. G. Brown, P. K. Chu and Z. Yu, *Sci. Rep.*, 2014, **4**, DOI: 10.1035.srep03665; (b) Y.-S. Wu, Y.-C. Wu and S.-W. Kuo, *Polymers*, 2014, **6**, 1827; (c) J. Xu, C. L. Toh, X. Lu, S. Wang, C. He and X. Lu, *Macromolecules*, 2005, **38**, 1684; (d) J. Xu, C. He, K. C. Toh and X. Lu, *Macromolecules*, 2002, **23**, 8846.

20

Graphic Abstract

Aggregation Induced Emission Based Fluorescence pH and Temperature Sensors: Probing Polymer Interactions in Poly(*N*-isopropyl acrylamide-co-tetra(phenyl)ethene acrylate)/Poly(methacrylic acid) Interpenetrating Polymer Networks

Hui Zhou,[†] Feng Liu,[‡] Xiaobai Wang,[†] Hong Yan,[†] Jing Song,[†] Qun Ye,[†] Ben Zhong Tang*,[§] and Jianwei Xu*,^{†,‡}

[†]Institute of Materials Research and Engineering, A*STAR (Agency for Science, Technology and Research), 3 Research Link, Singapore 117602, Republic of Singapore.

[‡]Department of Chemistry, National University of Singapore, 3 Science Drive 3, Singapore 117543, Republic of Singapore.


[§]Department of Chemistry, The Hong Kong University of Science & Technology, Clear Water Bay, Kowloon, Hong Kong, China.

*Corresponding author: Jianwei Xu and Ben Zhong Tang
Email address: jw-xu@imre.a-star.edu.sg; tangbenz@ust.hk

Mailing address: 3 Research Link, Singapore 117602

Tel: 65-6872-7543

Fax: 65-6872-7528

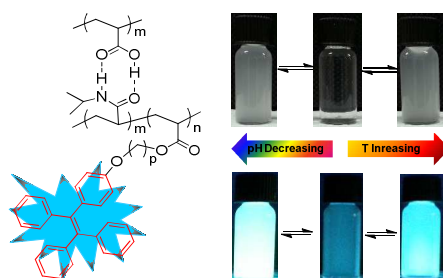

Aggregation induced emission active tetra(phenyl)ethene units are incorporated into poly(*N*-isopropyl acrylamide) to be used as a probe for interpenetrating polymer networks.