

Journal of Materials Chemistry C

Accepted Manuscript




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

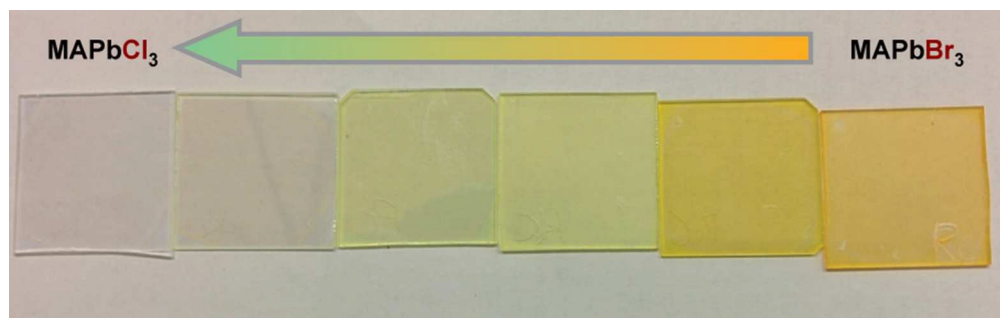

Color tunability in mixed Br/Cl lead-based perovskite thin films



Structural, optical, and electronic studies of wide-bandgap lead halide perovskites

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Riccardo Comin^{†,a}, Grant Walters^{†,a}, Emmanuel Thibau^b, Oleksandr Voznyy^a, Zheng-Hong Lu^b, Edward H. Sargent^{a,*}

We investigate the family of mixed Br/Cl organolead halide perovskites which enable light emission in the blue-violet region of the visible spectrum. We report the structural, optical and electronic properties of this air-stable family of perovskites, demonstrating full bandgap tunability in the 400-550 nm range and enhanced exciton strength upon Cl substitution. We complement this study by tracking the evolution of the band levels across the gap, thereby providing a foundational framework for future optoelectronic applications of these materials.

Introduction

Organometallic lead halide thin films have been attracting an ever-growing interest from the photovoltaic scientific community following breakthroughs in solar-to-electric power conversion efficiencies,^{1,2} which have recently risen to 20.1%³ in a remarkably short timeframe. While the predominant research thrusts have since been oriented towards the use of these materials as active layers in light-harvesting devices, more recent studies have demonstrated optoelectronic applications of perovskite thin films in light-emitting-devices (LEDs),^{4,5} lasers,⁶⁻⁸ photodetectors,⁹ and photocatalysts.¹⁰ The physical chemistry of these compounds is particularly tolerant to mixed-halide synthesis^{2,11}, which can lead to pure or mixed phases according to the structural compatibility of the different anions¹²⁻¹⁷, an aspect which is key to the impressive versatility characterizing this class of materials. While wide-bandgap

perovskites are not suitable for photovoltaic applications due to their transparency to most of the solar spectrum, LED technology can fully leverage the optical tunability and spectral purity that can be simultaneously engineered in Br- and Cl-based lead halide perovskites. The optical tunability, in particular, is a direct consequence of the negative electronic compressibility of these systems, whereby a compression of the unit cell – implemented via anion substitution – can be used to increase the bandgap over a wide spectral range. In this context, recent studies have shown promising prospects for the use of lead halide perovskite films in light emission devices whose spectral response can be chemically tuned across the entire visible spectrum.^{4,5} While extensive efforts are underway to optimize the efficiency of red and green perovskite LEDs, Cl-based films for blue-violet light emission have only been studied to a somewhat peripheral extent,^{5,6} partly due to the lack of information on the electronic band levels. While earlier works have preliminarily addressed certain aspects of the near-gap bandstructure and related optical response in Cl- and Br- based thin films,^{18,19} a detailed and systematic study of the electronic structure

^a Department of Electrical and Computer Engineering, University of Toronto. 10 King's College Road, Toronto, Ontario, M5S 3G4, Canada.
E-mail: ted.sargent@utoronto.ca

^b Department of Materials Science and Engineering, University of Toronto. 184 College Street, Toronto, Ontario M5S 3E4, Canada.

[†] These authors contributed equally

Electronic supplementary information (ESI) available: Supplementary Figures

in the entire range of halide substitution is, to date, still lacking.

We therefore sought to shed light on the electronic structure of wide-bandgap MAPbBr_{3-x}Cl_x thin film perovskites. Here we investigate the evolution of the structural and optical properties, as well as of the valence and conduction band levels, as a function of Cl/Br substitution using x-ray, optical, and photoelectron methods.

Results and discussion

For this study, we used solution processing routes to synthesize thin films of methylammonium (MA = CH₃NH₃) lead halide perovskite MAPbBr_{3-x}Cl_x with Cl concentration values $x = 0, 0.6, 1.2, 1.8, 2.4, 3$ (see Supplementary Information for more details). For the pure-Cl compound, different chemical precursors have been used during synthesis, resulting in films showing no appreciable differences in the properties discussed hereafter (a comparison of the surface morphology is presented Figure S1, Supplementary Information).

Structural properties

For the study of structural properties we used x-ray diffraction (XRD), with corresponding scans shown in **Figure 1a**. Multiple reflections can be seen that are associated with the cubic $Pm\bar{3}m$ space group. The lack of certain Bragg peaks for $x \geq 1.8$ is likely due to a higher degree of orientation in the film, confirmed by the presence of flat-lying cuboids in MAPbCl₃ (see again Figure S1, Supplementary Information). Most remarkably, we find a smooth evolution of the lattice structure across the entire concentration range, as demonstrated by the monotonic variation in the angular position of all Bragg reflections. The inset of Figure 1a shows a zoomed view of the (001) Bragg peak as a function of x , which implies a contraction of the perovskite cage as the smaller anion Cl is substituted for Br. The cubic lattice constant a is extracted from

the angular position of the (001) Bragg reflection θ_B using $\lambda/2a = \sin(\theta_B/2)$, and the average (shortest) grain dimension D is calculated from $D = 0.9 \cdot \lambda / (\Delta\theta_B \cdot \cos \theta_B)$ where $\Delta\theta_B$ is the Bragg peak linewidth and λ is the x-ray wavelength (see Figure S2, Supplementary Information). The lattice constant is plotted in **Figure 1b** together with the intensity of the Br-3d core levels measured with x-ray photoemission spectroscopy (XPS) (see also Figure S3, Supplementary Information). The monotonic trend in the lattice constant, which increases by ~5% from MAPbBr₃ to MAPbCl₃, confirms the progressive expansion of the unit cell. The variation over time of the sample structure and crystallinity is presented in **Figure 1c** for the case of MAPbCl₃. The negligible evolution of the peak intensity and broadening combines with the absence of any sign of decomposition (inferred from the lack of peaks from the metal precursor PbCl₂) to provide evidence for an excellent structural stability in ambient conditions over more than 5 months.

Optical properties

We then proceeded to study the optical properties of MAPbBr_{3-x}Cl_x films using absorption and photoluminescence (PL) spectroscopy. **Figure 2a** shows a sequence of thin films on glass with compositions varying from pure Br- to pure Cl-perovskite, and where the change in the optical response is clearly discernible. The change in color indicates the increase in the bandgap as Br is replaced with Cl, consistent with the trend observed in the Br/I mixed halide perovskites,²⁰ and more generally expected due to the reduced covalency of the lead-halide bonds within the network of Pb-X₆ (X = Cl, Br, I) corner-sharing octahedra. Optical absorbance spectra, as well as PL scans, have been measured for films deposited on Spectrosil® substrates (the latter enable an extended spectral range of perovskite film investigation thanks to their high-energy absorption onset at $\lambda \sim 200$ nm) and are plotted in **Figure 2b**. The

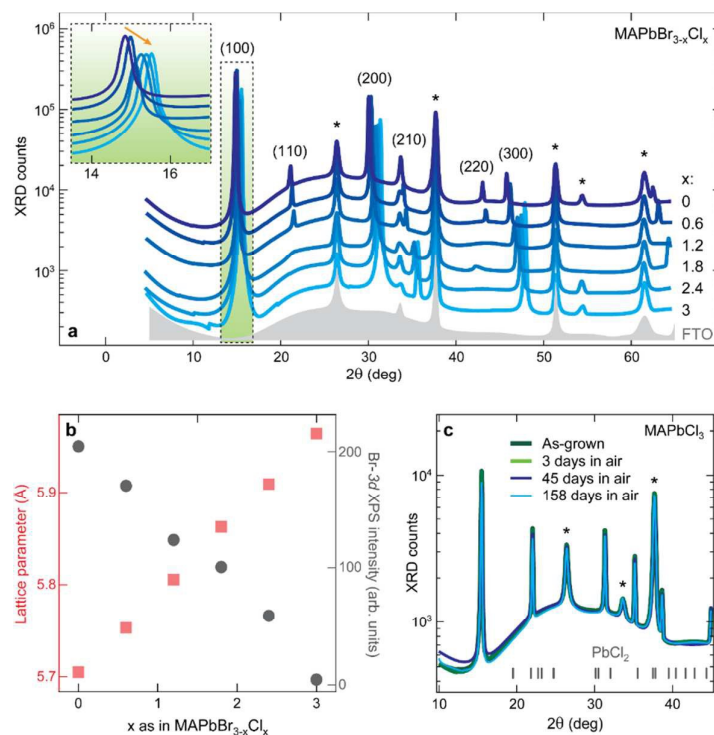


Figure 1. a) X-ray diffraction scans of $\text{Pb}(\text{Ac})_2$ -based thin films of $\text{MAPbBr}_{3-x}\text{Cl}_x$ (continuous lines) on fluorine-doped tin oxide (FTO). Shaded area: background signal from a pure FTO substrate (corresponding peaks are marked with a star). Inset: magnified view of the (100) diffraction peak. b) Evolution of the lattice parameter and Br-3d peak intensity vs. x . c) XRD pattern of PbCl_2 -based MAPbCl_3 over time, demonstrating structural stability of pure-Cl films in atmosphere. The bottom bars mark the angular position of the powder XRD peaks in PbCl_2 .

gradual evolution in the absorption edge is consistent with the continuous structural change observed with XRD, while at the same time the excitonic pre-peak is found to increase in intensity, a behavior which is related to an increasing exciton binding strength as discussed in more detail below. Consistent with the high degree of stability seen using XRD, the optical response remains unaltered over extended periods of time and up to 1 month after fabrication (see Figure S4, Supplementary Information), confirming the overall stability of these materials in ambient conditions. **Figure 2c** shows the normalized PL spectra, featuring a complementary progression in the emission wavelength, which blue-shifts from the green-emitting MAPbBr_3 to the deep-violet MAPbCl_3 , thus confirming the controllable color tunability upon halogen substitution. The raw PL data, as well as the PL quantum efficiency (defined as the ratio of

emitted to absorbed photons), are shown in Figure S5, Supplementary Information.

The absorbance profile, shown in **Figure 2d** for the case of MAPbCl_3 , is comprised of two main contributions: an excitonic peak at lower energies, and an extended absorption edge representing the continuum of valence-to-conduction band electronic excitations. **Equation 1** is used to model the excitonic absorption term using an asymmetric lineshape (to account for the higher-lying exciton levels as well as the interaction between the latter and the particle-hole continuum²¹) in the form of a hyperbolic secant:

$$\alpha_{exc}(E) = I_{exc} \cdot E^{-1} \cdot \left[\exp\left(\frac{E-E_{exc}}{\Gamma(E-E_{exc})}\right) + \exp\left(\frac{E_{exc}-E}{\Gamma(E-E_{exc})}\right) \right]^{-1} \quad (1)$$

where I_{exc} and E_{exc} represent the exciton intensity and energy respectively, and $\Gamma(E) = 2 \cdot \Gamma_{exc} \cdot (1 + e^{aE})^{-1}$ is a generalized, energy-dependent linewidth. The exciton energy is related to the

exciton binding energy G by $E_{exc} = E_g - G/n^2$ (E_g is the electronic bandgap) and here we use a single line corresponding to the exciton ground state ($n = 1$). For the main absorption edge, we use a modified version²² of the canonical lineshape for direct transitions²³ (Equation 2):

$$\alpha_{cont}(E) = I_{cont} \cdot \sqrt{G} \cdot E^{-1} \cdot [1 - \exp(-\pi\sqrt{G/E - E_g})]^{-1} \cdot h(E) \cdot \theta(E - E_g) \quad (2)$$

where I_{cont} represents the intensity of the absorption edge, $\theta(E)$ is the Heaviside step function, and the function $h(E) = [1 - b(E - E_g)]^{-1}$ parametrizes the deviation from the parabolic band regime

(following Ref. 22). The expression for the absorption edge in Equation 1 is subsequently convoluted with a hyperbolic secant function with constant linewidth Γ_{cont} . The experimental data are fitted with the sum of the excitonic and continuum terms, and the

resulting profile (together with the individual components) is shown in **Figure 2d** (for the other compositions see Figure S6, Supplementary Information). In general, we make use of the fact that the same parameter G controls both the position of the exciton line and the lineshape of the main absorption edge to provide a reliable estimate for the bandgap as well as the exciton binding energy. The results for the bandgap, the Stokes shift (defined as $E_{exc} - E_{PL}$, where E_{PL} is the PL peak energy), and the exciton binding energy G are reported in **Figure 2e**, as well as in **Table 1**. As already noted from the absorption spectra, G increases with Cl content, which reflects the more pronounced ionic character in Cl-based perovskites. In pure MAPbCl₃ we determine an exciton binding energy of about 50 meV, more than double the value for MAPbBr₃ ($G \sim 21$ meV), while in general our absolute values are compatible or slightly lower than previous optical studies on I-based perovskite.^{22,24}

Electronic structure


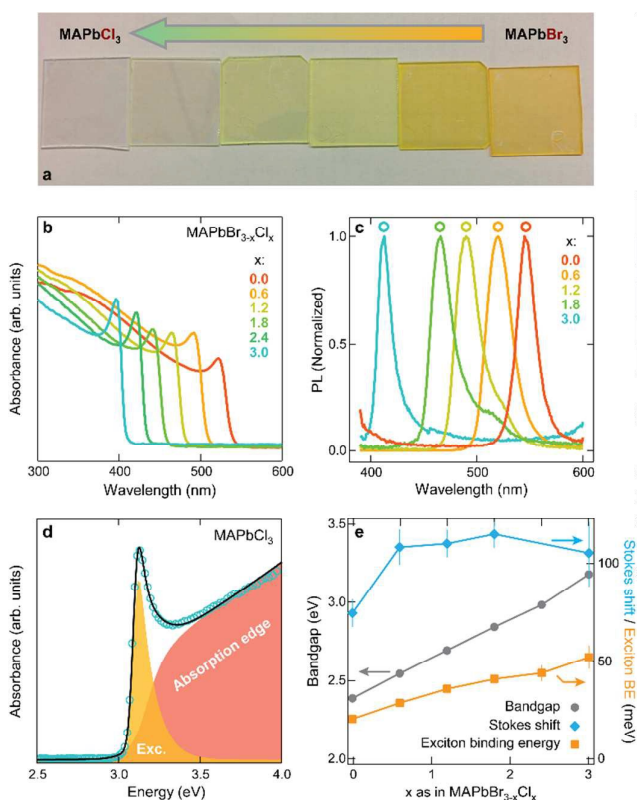


Figure 2 a) Photograph of Br/Cl mixed films on glass, visibly showing the progressive change in optical properties. b,c) Optical absorbance and photoluminescence spectra (370 nm excitation) of $\text{MAPbBr}_{3-x}\text{Cl}_x$ films on Spectrosil[®]. d) Plot of the absorbance (blue markers) of MAPbCl_3 as a function of energy with two-component (exciton and band-to-band absorption) fit overlaid (black line). e) Evolution of the electronic bandgap (grey circles), Stokes shift (blue diamonds), and exciton binding energy (orange squares) as a function of Cl content x .

In order to map the conduction and valence band levels as a function of halide content, we have further investigated the energetics of occupied states using Ultraviolet Photoemission Spectroscopy (UPS). Photoemission not only measures the binding energy (E_B) of valence electrons with respect to the chemical potential, but also provides a means for determining the work function (ϕ) of the material which sets the minimum kinetic energy (E_K) required for photoelectrons to escape the film according to $E_K = h\nu - \phi - |E_B|$, where $h\nu$ is the photon energy. Therefore, since E_K must be positive, a drop in the photoelectron signal in the form of an intensity cutoff occurs at $|E_B| = h\nu - \phi$, which is clearly visible in the photoelectron traces shown in **Figure 3a**, and measured using a UV source ($h\nu = 21.2$ eV). Linear fits to the pre-

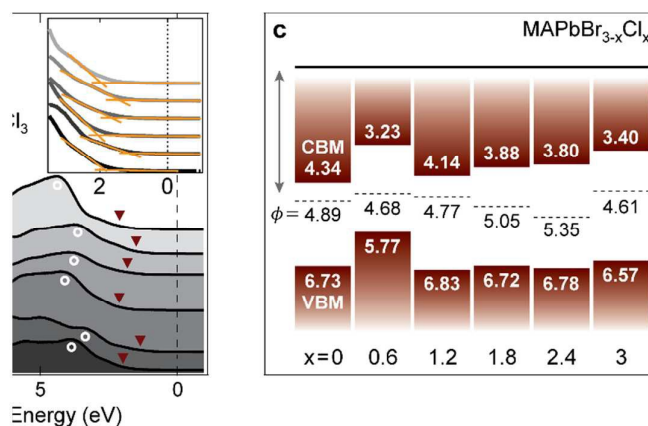

measured using x-ray photoemission; arrows are located at the intersection of the traces. b) Valence band photoemission spectra near the Fermi energy E_F with iron signal as determined by linear fits (orange traces). In the main graph, red arrows indicate the position of the lowest-energy peak, respectively. c) Schematics of the electronic band structure vs. Cl concentration x , showing the conduction band minimum (CBM) and valence band maximum (VBM) values.

and post-cutoff regions are used to estimate the energy onset from which the work function can be derived (values listed in Table 1). The valence band photoemission spectra are displayed in **Figure 3b**, with a magnified view near the Fermi level shown in the inset plot. Again, linear fits below and above the onset of the occupied density of states are used to locate the valence band maximum, as measured with respect to the Fermi energy E_F . The resulting band structure vs. Cl concentration is summarized in the schematic presented in **Figure 3c** (all energies are referred to the vacuum level). A close inspection of this diagram leads to the following conclusions: (i) the pure-Br perovskite exhibits an ostensible asymmetry in the position of the band edges, consistent with previous findings;²⁵ (ii) when Cl is substituted for Br, the material develops a more intrinsic electronic structure, which might suggest a cleaner bandgap with lower defect density; (iii) for increasing Cl content, the valence band position shows little variation, while a monotonic trend is found for the conduction band edge (with the exception of $x = 0.6$); (iv) the work function does not follow a specific trend with halide substitution, and in all cases ranges around 5 eV.

Conclusions

Thin films of mixed-halide wide-bandgap perovskites reveal a number of interesting characteristics. Structural measurements show that Cl can be seamlessly substituted for Br, attributable to the lattice compatibility of the pure-halide compounds. The smooth structural evolution translates to a full tunability of optical properties, a behavior which enables the fabrication of spectrally-tunable lead halide perovskites having bandgaps in the 400 to 550 nm wavelength range. In light of the promising radiative performance of I-based perovskites,⁴ the increased ionicity of Cl-containing perovskites suggests that the latter might represent a compelling platform for efficient, air-stable, light-emitting devices in the blue-violet region of the visible spectrum. Our photoemission results ultimately provide a comprehensive mapping of the electronic levels to guide future device design strategies in these materials.

Experimental

Synthesis of lead halide perovskite thin films

Metal salt precursors Pb(Ac)₂ (Ac = CH₃COO), PbBr₂ and PbCl₂ (99.999% purity) were purchased from Sigma Aldrich. The organic salt precursor CH₃NH₃Br (CH₃NH₃Cl) was synthesized by the reaction of methylamine aqueous solution and the corresponding hydrobromide (hydrochloride) acid in a round-bottom flask at 0 °C for 2 h with stirring. The precipitate was recovered by placing the solution on a rotary evaporator and carefully removing the solvents. The raw product CH₃NH₃X was re-dissolved in absolute ethanol and

precipitated with the addition of diethyl ether for recrystallization.

After filtration, the previous step was repeated again. Finally, the solid product was collected and dried at 60 °C in a vacuum oven for 24 h.

All substrates were chemically washed prior to film deposition.

Substrates were immersed and sonicated in baths of Triton X-100 cleaning solution, isopropanol, and deionized water sequentially.

After each bath, substrates were rinsed with deionized water. The substrates were then dried in an oven at 90 °C for 1.5 to 2 hours.

This was followed by a final soak in an isopropanol bath for six hours and subsequent drying with nitrogen gas. After chemical washing, glass and Spectrosil[®] substrates were plasma treated for five minutes with an oxygen plasma in order to improve film wetting. Following plasma treatment, films were immediately deposited on the substrates using a one-step or a two-step method.

For one-step syntheses, lead precursor [Pb(Ac)₂, PbBr₂, or PbCl₂] and methylammonium halide were weighed and added together in a vial such that the molar ratio of lead to halide was 1:3. Solvent was then added to the powder precursors. For two-step syntheses, lead precursor and methylammonium halide were weighed out separately and solvent was added to each powder individually.

Unless stated otherwise, dimethyl sulfoxide (DMSO) was used as the solvent and the concentration of Pb²⁺ was 0.6 M/L in all experiments. Solutions were vortexed and then sonicated for ~20 min. For one-step syntheses, 150 μL of solution were deposited on clean substrates for spin-coating. Samples were spun at 4000 rpm for 1 minute. For two-step syntheses, ten drops of lead precursor solution were spun using the same procedure; spin coating was then repeated with ten drops of methylammonium halide solution. In the case of anti-solvent rapid crystallization, a 50 μL aliquot of chlorobenzene was deposited onto the spinning sample after

Journal Name

Energy & Environmental Science

spinning at 10000 rpm for 10 seconds and 30 seconds at 5000 rpm; spinning was continued for 30 seconds at 5000 rpm after chlorobenzene addition. All samples were immediately annealed for 45 minutes at 100 °C on a hotplate. The entire fabrication procedure was performed in a room-temperature nitrogen atmosphere.

Characterization of perovskite thin films

X-ray diffraction (XRD). XRD scans have been acquired on a Rigaku MiniFlex 600 diffractometer equipped with a NaI scintillation counter and using monochromatized Cu- K_{α} radiation ($\lambda = 1.5406 \text{ \AA}$), with a detector angle (2θ) step of 0.03° . The angular resolution is $\Delta_{2\theta} \sim 0.1^{\circ}$, as determined from diffraction on LaB₆ single crystals.

X-ray photoelectron spectroscopy (XPS). The Cl concentration values in mixed Br/Cl perovskite films have been obtained from the analysis of XPS spectra. The latter have been measured using a PHI-5500 setup using a monochromatized Al- K_{α} x-ray anode (1486.7 eV) to excite photoelectrons in an ultrahigh vacuum atmosphere ($\sim 10^{-9}$ Torr). The binding energy scale was calibrated using the Au- $4f_{7/2}$ peak (83.98 eV) and the Cu- $2p_{3/2}$ peak (932.67 eV) of sputter-cleaned Cu.

Scanning electron microscopy (SEM). A Quanta FEG 250 environmental scanning electron microscope was used to collect SEM images. Images were acquired with an Everhart-Thornley secondary electron detector, under high vacuum, and with a 10.0 kV accelerating voltage. Cross-sectional samples were lightly carbon-coated prior to imaging in order to prevent sample charging.

Optical absorption: Optical absorption scans have been acquired with a PerkinElmer Lambda 950 UV/Vis/NIR spectrophotometer

equipped with a 150 mm integrating sphere, in the wavelength range 250 – 900 nm and using 2 nm incremental steps.

Photoluminescence (PL) spectra. PL emission profiles have been measured using a Horiba Fluorolog setup equipped with a monochromatized Xe lamp and with a photon detection unit featuring a double-grating spectrometer and a photomultiplier tube covering the spectral range 300 – 850 nm. All PL datasets have been acquired using $\lambda = 370 \text{ nm}$ excitation and in reflection geometry (at an incidence angle of 30° from the sample surface, to avoid spurious reflections of the incident light into the spectrometer). The raw data have been subsequently corrected for the experimentally-determined spectral sensitivity of the photon detector.

Ultraviolet photoemission spectroscopy (UPS). Photoelectron Spectroscopy (PES) was performed in a PHI5500 Multi-Technique system using monochromatic Al- K_{α} radiation (XPS, $h\nu = 1486.7 \text{ eV}$) and non-monochromatized He- I_{α} radiation (UPS, $h\nu = 21.22 \text{ eV}$). All workfunction and valence band measurements were performed at a take-off angle of 88 degrees, and the chamber pressure was approximately 10^{-9} torr. During measurement, the sample was held at a constant bias of -15 V relative to the spectrometer in order to improve the low energy photoelectron signal. Note that the samples have been exposed to atmosphere for a brief period of time (~ 5 minutes) in order to apply carbon-tape conductive contacts to the films (to avoid charging effects) prior to loading into the photoemission chamber.

Acknowledgments

This publication is based in part on work supported by Award KUS-11-009-21, made by the King Abdullah University of Science and Technology (KAUST), by the Ontario Research Fund Research

Excellence Program, and by the Natural Sciences and Engineering Research Council.

Musinu, F. Quochi, A. Mura and G. Bongiovanni, *Nat. Commun.*, 2014, **5**, 5049.

23 R. J. Elliott, *Phys Rev*, 1957, **108**, 1384–1389.

24 V. D'Innocenzo, G. Grancini, M. J. P. Alcocer, A. R. S. Kandada, S. D. Stranks, M. M. Lee, G. Lanzani, H. J. Snaith and A. Petrozza, *Nat. Commun.*, 2014, **5**.

25 P. Schulz, E. Edri, S. Kirmayer, G. Hodes, D. Cahen and A. Kahn, *Energy Environ. Sci.*, 2014, **7**, 1377–1381.

Notes and references

- 1 J. Burschka, N. Pellet, S. J. Moon, R. Humphry-Baker, P. Gao, M. K. Nazeeruddin and M. Grätzel, *Nature*, 2013, **499**, 316–9.
- 2 M. Liu, M. B. Johnston and H. J. Snaith, *Nature*, 2013, **501**, 395–398.
- 3 W. S. Yang, J. H. Noh, N. J. Jeon, Y. C. Kim, S. Ryu, J. Seo and S. I. Seok, *Science*, 2015, aaa9272.
- 4 Z. K. Tan, R. S. Moghaddam, M. L. Lai, P. Docampo, R. Higler, F. Deschler, M. Price, A. Sadhanala, L. M. Pazos, D. Credgington, F. Hanusch, T. Bein, H. J. Snaith and R. H. Friend, *Nat Nanotechnol*, 2014, **9**, 687–92.
- 5 Y.-H. Kim, H. Cho, J. H. Heo, T.-S. Kim, N. Myoung, C.-L. Lee, S. H. Im and T.-W. Lee, *Adv. Mater.*, 2014.
- 6 G. Xing, N. Mathews, S. S. Lim, N. Yantara, X. Liu, D. Sabba, M. Grätzel, S. Mhaisalkar and T. C. Sum, *Nat. Mater.*, 2014, **13**, 476–480.
- 7 F. Deschler, M. Price, S. Pathak, L. E. Klintberg, D.-D. Jarausch, R. Higler, S. Hüttner, T. Leijtens, S. D. Stranks, H. J. Snaith, M. Atatüre, R. T. Phillips and R. H. Friend, *J. Phys. Chem. Lett.*, 2014, **5**, 1421–1426.
- 8 B. R. Sutherland, S. Hoogland, M. M. Adachi, C. T. O. Wong and E. H. Sargent, *ACS Nano*, 2014, **8**, 10947–10952.
- 9 L. Dou, Y. (Micheal) Yang, J. You, Z. Hong, W.-H. Chang, G. Li and Y. Yang, *Nat. Commun.*, 2014, **5**, 5404.
- 10 J. Luo, J.-H. Im, M. T. Mayer, M. Schreier, M. K. Nazeeruddin, N.-G. Park, S. D. Tilley, H. J. Fan and M. Grätzel, *Science*, 2014, **345**, 1593–1596.
- 11 S. D. Stranks, G. E. Eperon, G. Grancini, C. Menelaou, M. J. P. Alcocer, T. Leijtens, L. M. Herz, A. Petrozza and H. J. Snaith, *Science*, 2013, **342**, 341–344.
- 12 K. Yamada, K. Nakada, Y. Takeuchi, K. Nawa and Y. Yamane, *Bull. Chem. Soc. Jpn.*, 2011, **84**, 926–932.
- 13 E. Mosconi, A. Amat, M. K. Nazeeruddin, M. Grätzel and F. De Angelis, *J. Phys. Chem. C*, 2013, **117**, 13902–13913.
- 14 S. Colella, E. Mosconi, P. Fedeli, A. Listorti, F. Gazza, F. Orlandi, P. Ferro, T. Besagni, A. Rizzo, G. Calestani, G. Gigli, F. De Angelis and R. Mosca, *Chem. Mater.*, 2013, **25**, 4613–4618.
- 15 E. Edri, S. Kirmayer, M. Kulbak, G. Hodes and D. Cahen, *J. Phys. Chem. Lett.*, 2014, **5**, 429–433.
- 16 B. Suarez, V. Gonzalez-Pedro, T. S. Ripolles, R. S. Sanchez, L. Otero and I. Mora-Sero, *J. Phys. Chem. Lett.*, 2014, **5**, 1628–1635.
- 17 S. Colella, E. Mosconi, G. Pellegrino, A. Alberti, V. L. P. Guerra, S. Masi, A. Listorti, A. Rizzo, G. G. Condorelli, F. De Angelis and G. Gigli, *J. Phys. Chem. Lett.*, 2014, **5**, 3532–3538.
- 18 N. Kitazawa, Y. Watanabe and Y. Nakamura, *J. Mater. Sci.*, 2002, **37**, 3585–3587.
- 19 M. Zhang, H. Yu, M. Lyu, Q. Wang, J.-H. Yun and L. Wang, *Chem. Commun.*, 2014, **50**, 11727–11730.
- 20 J. H. Noh, S. H. Im, J. H. Heo, T. N. Mandal and S. I. Seok, *Nano Lett.*, 2013, **13**, 1764–1769.
- 21 C. Bellabarba, J. Gonzalez and C. Rincon, *Phys Rev B*, 1996, **53**, 7792–7796.
- 22 M. Saba, M. Cadelano, D. Marongiu, F. Chen, V. Sarritzu, N. Sestu, C. Figus, M. Aresti, R. Piras, A. G. Lehmann, C. Cannas, A.