

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

COMMUNICATION

Unraveling a two-step oxidation mechanism in electrochemical Cu-MOF synthesis

Received 00th January 20xx,
Accepted 00th January 20xx

Philipp Schäfer^a, Monique A. van der Veen^{b,*} and Katrin F. Domke^{a,**}

DOI: 10.1039/x0xx00000x

www.rsc.org/

To employ the full potential of electrochemical (ec) synthesis to grow metal-organic frameworks (MOFs) in more complex organizations at the mesoscale, it is vital to understand the underlying crystallization reaction pathway. For the MOF most typically grown electrochemically, CuBTC, we systematically investigated the role of oxygen species in the synthesis.

Metal-organic frameworks (MOFs) attract significant interest as versatile materials for gas separation¹ and storage,² and more recently as light harvesters for novel energy conversion schemes.^{3,4} Their topology (crystal structure, pore size, pore connectivity) and functionality (chemistry at reactive sites, luminescence/absorption properties of framework, guest donor/acceptor moieties) can, in principle, be tuned to desire by making use of the wealth of metal ion and organic linker combinations the chemist's tool kit provides. While classically, MOFs are synthesized solvothermally at elevated pressure and/or temperature,^{5,6} recently, novel anodic and cathodic⁷⁻¹² electrochemical (ec) fabrication protocols are emerging as electro-synthesis offers milder conditions, greater energy efficiency and energetic control over the MOF growth.^{7,13,14} It has been shown that by applying an appropriate synthesis potential, the size of MOF crystals can be directly controlled in the sub- to 5 μm size range,^{7,8} or that different linkers can be built in on demand to fabricate multi-functionality MOFs in situ.¹⁰ These cases demonstrate the extraordinary possibilities electro-synthesis offers for controlled MOF growth. However, generalizing the ec approach requires a detailed understanding of the underlying reaction mechanisms which have to date only been speculated on.^{7,15} Questions regarding the chemical species involved, the role of the substrate surface and the

energetics and kinetics of the overall reaction pathway of ec MOF formation need to be answered to mature ec synthesis into a readily available tool for rational MOF design.

In this work, we unravel the reaction mechanism of the ec formation of a showcase MOF, CuBTC (HKUST-1; Cu 1,3,5 tricarboxylic acid). Prepared according to the original protocol from 2005, electrosynthesized CuBTC, finds large-scale application e.g. for carbon dioxide/methane¹⁶ or propylene/propane¹⁷ gas mixture separation, or in novel sensors and electronic devices.¹⁸ Despite CuBTC being one of the most extensively studied MOFs,^{7,19} its ec formation mechanism has not yet been unraveled, hindering full exploitation of electro-synthetic MOF design possibilities. It has been postulated that, Cu is anodically oxidized in one step to Cu²⁺ followed by linker coordination in solution.^{7,15} Other groups, however, have observed MOF crystals intergrown with the surface that suggest on-surface growth.²⁰

To solve the prevailing controversy and open a route for rational MOF topology and functionality design, we set out to identify the chemical species involved in CuBTC electro-synthesis and unravel the reaction mechanism. We systematically varied the experimental conditions such as the Cu source, the presence of O₂ and the applied potential (Table 1), generally following the protocol found in literature:^{7,21} a Cu plate was immersed at open circuit in a mixture of 100 mL absolute EtOH, 3 g BTC linker and 1 g methyl tributyl ammonium methyl sulfate electrolyte. After electrode immersion, a potential of $E = 1 \text{ V}$ vs Ag/AgCl was applied for 20 min. To prevent Cu₂O formation on the Cu electrode from ambient aerobic corrosion in O₂-free experiments, EtOH was degassed with Ar for 20 min prior to Cu immersion, and the ec cell was constantly kept under Ar. To remove the natural oxide layer (comprised mainly of Cu₂O and a small amount of CuO and Cu(OH)₂²²), the Cu electrode was etched with 25 % HNO₃ and 25 % HCl²³ before transfer to the synthesis cell.

The resulting topography and chemical composition of each sample type was characterized to determine whether CuBTC grows under the respective conditions. CuBTC is known to form octahedral crystals that can be seen with scanning

^a Max Planck Institute for Polymer Research, Molecular Spectroscopy Department, Ackermannweg 10, D 55128 Mainz, Germany

^b Delft University of Technology, Faculty of Applied Sciences, Chemical Engineering Department, Section of Catalysis Engineering, Julianalaan 136, NL 2628 BL Delft, Electronic Supplementary Information (ESI) available: Materials and Methods (Raman, XRD, SEM data); Characterization of Samples F. Current transients. DOI: 10.1039/x0xx00000x

* M.A.vanderVeen@tudelft.nl

** domke@mpip-mainz.mpg.de

electron microscopy (SEM).²⁴ Raman in-plane ring bending vibrations at 743 and 825 cm^{-1} of the BTC moiety in CuBTC confirm the presence of CuBTC (Fig. S12 and Table S1).²⁵ X-ray diffraction (XRD) was used for CuBTC identification where a sufficient amount of MOF crystals was obtained (see Supporting Information, SI, for experimental details).

Fig. 1 shows the SEM and Raman results for the different sample types under investigation. Samples A were fabricated under synthesis conditions similar to the ec synthesis protocols found in literature,^{7,21} i.e. starting from a Cu-electrode with a natural oxide layer and taking no precautions to avoid the presence of O_2 . As expected, octahedral crystals of CuBTC of $<1 \mu\text{m}$ to $5 \mu\text{m}$ in diameter form (Fig. 1A). Electrode coverage is incomplete at ~ 20 particles/ $100 \mu\text{m}^2$, likely due to the low potential of 1 V. An increased synthesis time should improve surface coverage. The corresponding Raman spectrum in the inset of Fig. 1A displays the characteristic bending vibrations of CuBTC at 743 and 825 cm^{-1} , and XRD diffractograms confirm the successful synthesis of CuBTC (Fig. S11A). Note that the Raman spectrum also shows a significant contribution of Cu_2O (see Fig. S13A, broad peaks at 525 and 626 cm^{-1}).

Samples B were produced under oxide- and O_2 -free conditions, thus void of all components unnecessary for the Cu^{2+} dissolution-coordination mechanism proposed in literature. The SEM image (Fig. 1B) shows parallel Cu tracks due to the acidic etching of the surface. With exception of only about 1 particle/ $100 \mu\text{m}^2$ of ca. 0.5 to $1 \mu\text{m}$ diameter, no CuBTC crystals are visible. The CuBTC response in the Raman spectra can hardly be distinguished from the noise (Fig. 1B inset), and no XRD signal of CuBTC was obtained (Fig. S11B).

To find the smallest set of components required to enable CuBTC synthesis, we electrochemically oxidized the surface of the Cu plate on purpose by immersing it in the electrolyte solution and applying a potential of 1 V vs Ag/AgCl for 25 min prior to O_2 -free MOF synthesis (Samples C). SEM, Raman and XRD confirm the successful synthesis of CuBTC (Figs 1C, S11C); the Raman spectrum shows a significant Cu_2O contribution (Fig. S13C). Samples C are covered with a mixture of about 5

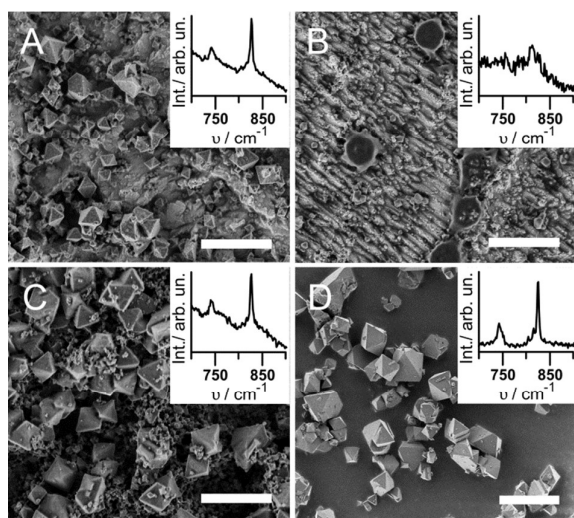


Fig. 1 SEM micrographs and Raman spectra of Samples A to D. Scale bar: 10 μm .

Table 1 Experimental conditions, sample overview

Sample type	Cu source	O_2 presence	E^* / reaction time	CuBTC formation
A	Cu with natural oxide layer	Yes	1 V / 20 min	Yes
B	Cu, oxide free	No	1 V / 20 min	No
C	Cu with artificial oxide layer	No	1 V / 20 min	Yes
D	Cu_2O	Yes	No / 16 hours	Yes
E	Cu_2O	low amount	No / 16 hours	Yes (truncated)
F**	CuO	Yes	No / 16 hours	No

* Potentials reported vs Ag/AgCl/3 M KCl; ** SEM/Raman characterization in SI

crystals/ $100 \mu\text{m}^2$ of octahedral crystals of 3 to $5 \mu\text{m}$ diameter and ca. 50 particles/ $100 \mu\text{m}^2$ in the sub- μm diameter range. At some spots, the smaller crystals cover the larger particles.

From experiments A to C, we learn that oxygen plays an important role in ec CuBTC synthesis as CuBTC crystals do not grow under O_2 -oxygen free conditions and Cu_2O is always present on the electrodes. To further investigate the role of oxygen, we used pure oxides as precursors for CuBTC growth. For Samples D, we immersed Cu_2O powder in an ethanolic solution of 0.15 M BTC without any other additions for 14 hrs under ambient conditions. No potential was applied. A blue powder was isolated by centrifugation and characterized. The SEM micrograph in Fig. 1D shows octahedral crystals of 1 to $5 \mu\text{m}$ diameter that are intergrown into larger agglomerates of 10 to $15 \mu\text{m}$ length. Raman spectra (Fig. 1D inset) and XRD (Fig. S11D) confirm CuBTC synthesis. Interestingly, an analogous experiment with CuO powder as starting material did not produce any CuBTC (Samples F, SI).

To identify the necessary oxidation agent for the oxidation of Cu(I) to Cu(II) in absence of an applied potential, Samples E were synthesized like Samples D, but in an O_2 -deficient environment. The solution was degassed for 15 min, but during transfer into a glove box, some O_2 could re-dissolve. The SEM micrographs show about 10% of the Cu_2O surface covered with octahedral crystals of diameters between 0.3 and $0.7 \mu\text{m}$, and partly with what seem to be incomplete CuBTC crystals with diameters of 100 to 200nm (Fig. 2, red). This is the only Sample for which we observe incomplete CuBTC octahedrons. It is unlikely that these crystals deposited onto the Cu_2O substrate during centrifugation; rather they must have grown at the surface, and their growth was halted prematurely due to lack of O_2 . Similarly, also the few octahedral crystals (Fig. 2, blue) are visibly attached to the Cu_2O substrate. From these results, we conclude that O_2 is the necessary oxidant for the oxidation of Cu_2O to CuBTC without ec potential. Furthermore, the visible connection between the CuBTC and the Cu_2O indicates that CuBTC nucleation likely takes place directly at the Cu_2O solid/liquid interface. Summing up, the first step to ec CuBTC formation is the oxidation of Cu to Cu^{1+} achieved either by ec oxidation of the Cu anode or by providing O_2 and/or H_2O (H_2O enables CuBTC synthesis even under inert conditions.²⁰) as reactant. Cu_2O is the predominant


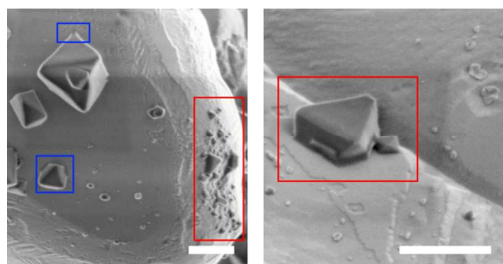


Fig. 2

SEM of Samples E. Red: truncated crystals; blue: intergrowth with surface. Scale bar: 500 nm.

oxidation product of Cu in ethanol.²⁶ Note that also Cu(OH)₂ readily converts into CuBTC in presence of the linker.²⁷ While Cu(OH)₂ as an intermittent, short-lived reaction intermediate cannot be excluded, our spectroscopic data does not indicate stable Cu(OH)₂ formation (i.e. no Raman band at 460 cm⁻¹, Fig. S12b). Furthermore, CuBTC forms directly from Cu¹⁺₂O powder while Cu²⁺O does not convert to CuBTC under the given experimental conditions.

As known from literature, Cu₂O can be produced from Cu by the following oxidation reactions with H₂O or O₂:^{22,28}



A positive applied potential facilitates the net release of electrons in reaction (1). Excess electrons are transferred to the counter electrode where a not-further specified counter reaction takes place. Reaction (2) represents the aerobic oxidation of Cu that takes place in the presence of O₂. In Samples B, both (1) and (2) were blocked by using dry EtOH and by degassing the electrolyte with Ar. Since all surface oxides were removed by acidic etching, no Cu₂O – and thus no CuBTC – could be formed.

Instead of using O₂ or H₂O as oxidant, Cu can be electrochemically oxidized. In absence of O₂ and H₂O, the amount of available Cu¹⁺₂O is expected to limit the CuBTC yield. Indeed, for Samples C, we did not observe continuous detachment of large MOF crystals from the electrode into the solution phase, indicating that CuBTC growth stopped after all provided Cu₂O had been consumed.

For the second oxidation step of Cu¹⁺₂O to Cu²⁺BTC, we propose the following ec half reaction:



H₂O is a likely product that can be produced from the oxygen released from Cu₂O and the protons released from BTC. In the ec synthesis, this oxidation half-reaction takes place at the Cu anode. (A corresponding, not further specified reduction reaction takes place at the counter electrode.) With the production of H₂O, the reaction should be self-sustaining after a certain threshold H₂O concentration is reached. For aerobic Cu₂O oxidation (Samples D), CuBTC growth occurs at the Cu₂O/solution interface. CuBTC synthesis from Cu₂O without applied potential is only possible in the presence of O₂, as shown by the greatly reduced amount of CuBTC in Samples E. Likely, O₂ is reduced to H₂O in a counter reaction



Equation (3) as the key step in ec CuBTC synthesis as derived

from our results is fully consistent with synthesis facts reported in literature: Van Assche et al. showed that CuBTC cannot be produced electrochemically in electrolytes that contain more than 50% H₂O.²⁰ The suppression of the reaction by H₂O is consistent with H₂O formation on the product side of (3), leading to an increase of the oxidation potential of the reaction while increasing the propensity for the formation of H₂O-containing catena-triaqua-μ-CuBTC.²⁰

Direct oxidation of solid Cu₂O to CuBTC at the ec solid/liquid interface to start crystal nucleation likely explains the tight attachment of CuBTC crystals to the electrode as previously observed⁷ as well as the incomplete CuBTC crystals visibly bound to Cu₂O that we observe under oxygen-limited conditions; however, a dissolution process with Cu₂O as intermittent cannot be completely excluded. It remains unclear whether further crystal growth happens at the Cu₂O-CuBTC-electrolyte interface or continues through a solution-based process with Cu²⁺ ions attaching to the outer facets of the growing crystal. Campagnol et al. show that electrosynthesized Cu isonicotinate grows at the MOF-electrolyte interface.²⁹ The significant amount of water (50%)³⁰ that makes Cu²⁺ ions more soluble in the form of [Cu(H₂O)₆]²⁺ could explain a solution-based process. The lack of H₂O in our system, however, makes a direct comparison difficult.

Let us summarize the reaction mechanism for the ec oxidation of Cu⁰ to CuBTC: In presence of O₂ and/or H₂O, Cu is oxidized in a one-electron step to Cu₂O. A second oxidation step from Cu¹⁺ to Cu²⁺ in the presence of BTC directly converts Cu₂O to CuBTC. Involvement of an intermediate Cu(I) reaction step has not been proposed so far and opens up new pathways to increase control of the synthesis.

Our newly gained knowledge that CuBTC crystallization proceeds through Cu₂O formation allows us to suggest a novel method to fabricate patterned MOF devices (Fig. 3A). As a proof of principle, we prepared a Cu substrate with both Cu and Cu₂O present by ec oxidizing the surface in the presence of NaOH.³¹ Then, we selectively removed Cu₂O in a spot of ~1 cm diameter in the centre of the sample by pipetting a drop of 10% HCl. After removal of that drop and subsequent rinsing with EtOH, the Cu plate was covered with Cu₂O except for the acid-etched blank Cu area. Under synthesis conditions B (O₂ exclusion, 1V), CuBTC was grown solely on the oxide-covered part of the sample as discernible in the white-light image (Fig. 3B). The left part of the image where surface oxides were removed by acidic etching shows the pristine Cu surface. To the right of the image, outside the area of the acid droplet, CuBTC has visibly grown and is spectroscopically detectable. Raman band integration of the 800 to 850 cm⁻¹ region provides the relative amounts of CuBTC at different sample positions (Fig 3C; error bars are standard errors of the mean of three measurements taken at roughly the top, middle and bottom of the white-light image). This facile oxide-based pre-patterning approach can serve as starting point to develop improved synthesis protocols for CuBTC patterning. Current patterning approaches require the use of Cu electrodes in the desired shape (i.e. printed circuit boards⁸ or Cu meshes²⁰). Our approach offers the possibility to subsequently activate parts

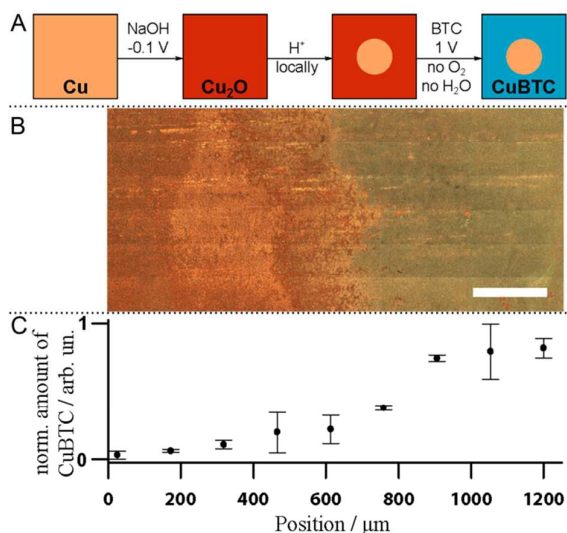


Fig. 3 Scheme for the fabrication of patterned CuBTC devices by oxide patterning; B: light-microscopy image of a Cu sample (left) partly covered with CuBTC (right). Scale bar: 200 μm ; C: normalized amount of CuBTC across sample.

of a Cu substrate. It is easy to imagine how established ways to deposit Cu_2O as nanoparticles or films^{32,33} or to selectively remove Cu oxide, as shown here, can be converted into a versatile basis for the fabrication of arbitrarily patterned surfaces on nm to mm length scales to create devices covered with MOF of controlled sizes at predetermined spots.

To conclude, we unravelled CuBTC electrosynthesis to proceed in a two-step oxidation mechanism at the electrode surface: Cu is first oxidized to Cu^{1+}_2O in the presence of H_2O or O_2 . Cu_2O is further oxidized to Cu^{2+}BTC in presence of the linker at the cuprite-electrolyte interface. The MOF octahedrons nucleate directly at the electrode surface and not in solution, rendering the ec mechanism different from the one of solvothermal syntheses with metal salts.^{34,35} We demonstrate how the gained knowledge can be used for a novel quick and versatile approach to produce patterned CuBTC devices.

Notes and references

We thank G. Glasser for SEM measurements, M. Steiert and B. Norder for XRD measurements and the Max Planck Graduate Center and the Studienstiftung des deutschen Volkes for funding. KFD acknowledges generous support through the Emmy Noether Program of the DFG (#DO1691/1-1).

- J. Teufel, H. Oh, M. Hirscher, M. Wahiduzzaman, L. Zhechkov, A. Kuc, T. Heine, D. Denysenko and D. Volkmer, *Adv. Mater.*, 2013, **25**, 635-639.
- A. U. Czaja, N. Trukhan and U. Müller, *Chem. Soc. Rev.*, 2009, **38**, 1284-1293.
- X. Zhang, W. Wang, Z. Hu, G. Wang and K. Uvdal, *Coord. Chem. Rev.*, 2015, **284**, 206-235.
- M. A. Nasalevich, M. van der Veen, F. Kapteijn and J. Gascon, *Cryst. Eng. Comm.*, 2014, **16**, 4919-4919.
- M. G. Goesten, F. Kapteijn and J. Gascon, *Cryst. Eng. Comm.*, 2013, **15**, 9249-9249.
- Y.-R. Lee, J. Kim and W.-S. Ahn, *Korean J. Chem. Eng.*, 2013, **30**, 1667-1680.

- A. Martinez Joaristi, J. Juan-Alcañiz, P. Serra-Crespo, F. Kapteijn and J. Gascon, *Cryst. Growth Des.*, 2012, **12**, 3489-3498.
- R. Ameloot, L. Stappers, J. Fransaer, L. Alaerts, B. F. Sels and D. E. De Vos, *Chem. Mater.*, 2009, **21**, 2580-2582.
- I. Hod, W. Bury, D. M. Karlin, P. Deria, C. W. Kung, M. J. Katz, M. So, B. Klahr, D. N. Jin, Y. W. Chung, T. W. Odom, O. K. Farha and J. T. Hupp, *Adv. Mater.*, 2014, **26**, 6295-6300.
- M. Li and M. Dincă, *Chem. Sci.*, 2014, **5**, 107-107.
- M. Li and M. Dincă, *Chem. Mater.*, 2015, **27**, 3203-3206.
- I. Stassen, M. Styles, T. R. C. Van Assche, N. Campagnol, J. Fransaer, J. F. M. Denayer, J. C. Tan, P. Falcaro, D. E. De Vos and R. Ameloot, *Chem. Mater.*, 2015, **27**, 1801-1807.
- N. Campagnol, T. R. C. Van Assche, T. Boudewijns, J. F. M. Denayer, K. Binnemans, D. E. De Vos and J. Fransaer, *Journal of Materials Chemistry A*, 2013, **1**, 5827-5827.
- M. Li and M. Dincă, *Journal of the American Chemical Society*, 2011, **133**, 12926-12929.
- H. Al-Kutubi, J. Gascon, E. J. R. Sudhölter and L. Rassaei, *ChemElectroChem*, 2015, **2**, 462-474.
- T. Asadi, M. R. Ehsani, A. M. Ribeiro, J. M. Loureiro and A. E. Rodrigues, *Chem. Eng. Technol.*, 2013, **36**, 1231-1239.
- J.-W. Yoon, I.-T. Jang, K.-Y. Lee, Y.-K. Hwang and J.-S. Chang, *Bull. Koran Chem. Soc.*, 2010, **31**, 220-223.
- J. Gascon and F. Kapteijn, *Angew. Chem. Int. Ed.*, 2010, **49**, 1530-1532.
- B. Panella, M. Hirscher, H. Pütter and U. Müller, *Adv. Funct. Mater.*, 2006, **16**, 520-524.
- T. R. C. Van Assche, G. Desmet, R. Ameloot, D. E. De Vos, H. Terryn and J. F. M. Denayer, *Microporous Mesoporous Mater.*, 2012, **158**, 209-213.
- T. R. C. Van Assche and J. F. M. Denayer, *Chem. Eng. Sci.*, 2013, **95**, 65-72.
- I. Platzman, R. Brenner, H. Haick and R. Tannenbaum, *J. Phys. Chem. C*, 2008, **112**, 1101-1108.
- L. C. Hall, C. P. Major, J. J. Steppan, J. A. Roth and B. K. Vaughen, *J. Electrochem. Soc.*, 1987, **134**, 1902-1902.
- Q. Min Wang, D. Shen, M. Bülow, M. Ling Lau, S. Deng, F. R. Fitch, N. O. Lemcoff and J. Semanscin, *Microporous Mesoporous Mater.*, 2002, **55**, 217-230.
- C. Prestipino, L. Regli, J. G. Vitillo, F. Bonino, a. Damin, C. Lamberti, a. Zecchina, P. L. Solari, K. O. Kongshaug and S. Bordiga, *Chem. Mater.*, 2006, **18**, 1337-1346.
- B. Stypuła, J. Banaś, M. Starowicz, H. Krawiec, A. Bernasik and A. Janas, *J. Appl. Electrochem.*, 2006, **36**, 1407-1414.
- G. Majano and J. Perez-Ramirez, *Adv. Mater.*, 2013, **25**, 1052-1057.
- H. Y. H. Chan, C. G. Takoudis and M. J. Weaver, *J. Phys. Chem. B*, 1999, **103**, 357-365.
- N. Campagnol, T. R. C. Van Assche, L. Stappers, J. F. M. Denayer, K. Binnemans, D. E. De Vos and J. Fransaer, *ECS Transactions*, 2014, **61**, 25-40.
- B. Van de Voorde, R. Ameloot, I. Stassen, M. Everaert, D. E. De Vos and J.-C. Tan, *J. Mater. Chem. C*, 2013, **1**, 7716-7716.
- J. C. Hamilton, J. C. Farmer and R. J. Anderson, *J. Electrochem. Soc.*, 1986, **133**, 739-739.
- P. E. de Jongh, D. Vanmaekelbergh, J. J. Kelly and P. E. D. Jongh, *Chem. Mater.*, 1999, **11**, 3512-3517.
- D. P. Singh, N. R. Neti, A. S. K. Sinha and O. N. Srivastava, *J. Phys. Chem. C*, 2007, **111**, 1638-1645.
- V. Stavila, J. Volponi, A. M. Katzenmeyer, M. C. Dixon and M. D. Allendorf, *Chem. Sci.*, 2012, **3**, 1531-1531.
- O. Shekhah, H. Wang, D. Zacher, R. A. Fischer and C. Wöll, *Angew. Chem. Int. Ed.*, 2009, **48**, 5038-5041.