

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

COMMUNICATION

## Non-coordinating anions assemble cyanine amphiphiles into ultra-small fluorescent nanoparticles

Received 00th January 20xx,  
Accepted 00th January 20xx

Ievgen Shulov,<sup>a,b</sup> Youri Arntz,<sup>a</sup> Yves Mély,<sup>a</sup> Vasyli G. Pivovarenko<sup>b</sup> and Andrey S. Klymchenko<sup>a,\*</sup>

DOI: 10.1039/x0xx00000x

www.rsc.org/

**Non-coordinating anion, fluorinated tetraphenylborate, assembles specially designed cationic cyanine amphiphiles into 7-8 nm fluorescent nanoparticles that are >40-fold brighter than a single cyanine dye. This kind of anions, combining hydrophobic and electrostatic forces in aqueous media, constitutes promising building blocks in self-assembly of functional nanomaterials.**

Molecular self-assembly is a powerful bottom-up approach to generate a large variety of nanoscopic and mesoscopic functional materials.<sup>1, 2, 3</sup> However, self-assembly exploits a quite limited number of non-covalent interactions:<sup>4</sup> (1) H-bonding and (2) metal-coordination, featuring high directionality, (3) hydrophobic and (4) pi-stacking interactions, which are especially strong in aqueous media, (5) electrostatic interactions, and (6) van der Waals interactions. A successful bottom-up assembly in aqueous media requires combination of several types of these interactions together, as it is successfully realized in preparation of supramolecular nanoparticles, (NPs),<sup>3, 5</sup> fibers and tubes.<sup>1, 6</sup> Combination of electrostatic and hydrophobic interactions is a fruitful approach, because the former is very efficient in apolar media. Therefore, ionic self-assembly of functional nanostructures<sup>7</sup> exploits surfactants bearing charged and hydrophobic moieties to assemble charged dyes, polyelectrolytes, etc.<sup>8</sup> A promising direction is to use non-coordinating anions, which are highly hydrophobic and weakly hydrated ions.<sup>9</sup> The key representatives are tetraphenylborates (TPB) anions bearing hydrophobic aromatic groups. Their fluorinated analogues are particularly interesting due to super-hydrophobic nature of fluorinated compounds,<sup>10</sup> and are successfully used in phase transfer catalysis and as charge carriers inside electrodes.<sup>9</sup> Our

recent works showed that tetraphenyl borates can help encapsulation of organic dyes inside polymer<sup>11</sup> and lipid<sup>12</sup> matrixes of nanocarriers. Importantly, in the presence of non-coordinating anions, cationic dyes can form nanoparticles, called ion-associated NPs<sup>13, 14</sup> or GUMBOS.<sup>15</sup> Fluorination of these counterions is crucial to achieve high fluorescence quantum yield of NPs and sufficient stability in biological media.<sup>16</sup> In all these examples formation of NPs is kinetically controlled, because relatively hydrophobic cationic dyes and non-coordinating anions give highly hydrophobic salts that rapidly precipitate in aqueous media. However, so far these non-coordinating hydrophobic counterions have never been used to induce assembly of amphiphiles into micelles, which is a fundamental thermodynamically controlled process giving ultra-small NPs.<sup>17</sup> Assembly of organic dyes into micelles is particularly interesting because it enables preparation of fluorescent NPs,<sup>18</sup> which have enormous potential for bioimaging applications.<sup>19</sup> However, concentrating dyes at the nanoscale leads to aggregation caused quenching (ACQ),<sup>20</sup> so that the reported examples of ultra-small micelles from organic dye amphiphiles display relatively low fluorescence quantum yields. In this respect, fluorinated counterions that can prevent cationic dyes from ACQ are of particular importance to generate bright fluorescent micellar NPs.

In the present work, we show that non-coordinating counterions can trigger the assembly of amphiphilic cyanine-3 and cyanine-5 dyes into ultra-small fluorescent nanoparticles. We selected cyanines, because they are cationic dyes with a positive charge delocalized within large hydrophobic aromatic structure. This should allow combining hydrophobic and electrostatic interactions for assembly with the non-coordinating anions. Moreover, these are bright dyes owing to high molar absorption coefficients and good fluorescence quantum yields. We prepared symmetric gemini-like amphiphiles containing two hydrophilic PEG groups and two apolar hydrocarbon chains (Fig. 1). This design should enable preparation of micelles where cyanine dyes are oriented parallel to the micelle surface with freedom to form emissive J- or non-emissive H-aggregates, well known for cyanines.<sup>21</sup> The


<sup>a</sup> Laboratoire de Biophotonique et Pharmacologie, UMR 7213 CNRS, Université de Strasbourg, Faculté de Pharmacie, 74, Route du Rhin, 67401 ILLKIRCH Cedex, France. E-mail: andrey.klymchenko@unistra.fr; Tel: +33 368 85 42 55

<sup>b</sup> Organic Chemistry Department, Chemistry Faculty, Taras Shevchenko National University of Kyiv, 01601 Kyiv, Ukraine.

† Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: materials and methods and some experimental data. See DOI: 10.1039/x0xx00000x

final Cy3A and Cy5A amphiphiles were synthesized in multiple steps, where Cy3 and Cy5 derivatives bearing two carboxylic groups were corresponding intermediates (Scheme S1).

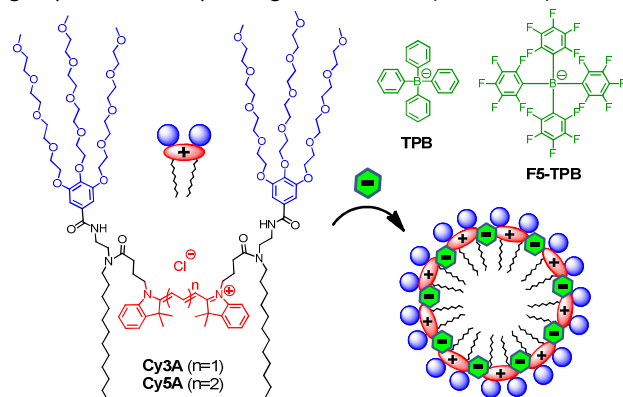


**Figure 1.** Cyanine amphiphiles and their expected assembly into micelles in the presence of non-coordinating anions.

First, we studied the capacity of Cy-amphiphiles to assemble in aqueous media using absorption spectroscopy (Fig. 2). At increasing concentrations of Cy3A and Cy5A in water, the contribution of the short-wavelength shoulder in respect to the peak maximum  $A_{sh}/A_{max}$  was found to increase, whereas in methanol this ratio was constant (Figs. S1 and S2, ESI). This increased shoulder suggests that both dyes at higher concentrations (1–5  $\mu\text{M}$ ) may form H-aggregates, characterized by short-wavelength absorption.<sup>13, 21</sup> The addition of non-coordinating anions TPB and F5-TPB increased the  $A_{sh}/A_{max}$  ratio in the absorption spectra of Cy3A and Cy5A, shifting the whole absorption band slightly to the red (Figs. 2 and S2, ESI). In case of Cy3A,  $A_{sh}/A_{max}$  increased gradually with anion concentration (Fig. 2B), reaching saturation at anion/dye ratio 1–2, so that counterions induced assembly of Cy3A at equimolar ratio. Similar, but less pronounced effect was observed for Cy5A (data not shown). At 10 mole excess of TPB and F5-TPB anions, the  $A_{sh}/A_{max}$  remained stably high for Cy3A/Cy5A concentrations  $>0.5 \mu\text{M}$  (Figs. S1 and S2, ESI), indicating that with these counterions the assembly took place below 0.5  $\mu\text{M}$ . The  $A_{sh}/A_{max}$  ratio for TPB was larger than for F5-TPB, showing some differences in the dye assembly.

The most interesting effects were observed in fluorescence (Figs. 2B and S2, ESI). At 1/1 counterion/Cy3A molar ratio the emission maximum shifted to the red (Fig. S3, ESI), while the fluorescence quantum yield (QY) dropped strongly for both TPB and F5-TPB (Fig. 2B), indicating an aggregation-caused quenching. Further increase in TPB concentration produced small increase in QY, whereas for F5-TPB it increased many-fold (Fig. 2B). At 10 mole excess of F5-TPB, the QY values were larger than in water reaching 25 and 8% for Cy3A and Cy5A, respectively, and their emission maxima were red shifted (Table 1). To confirm that this efficient fluorescence is observed from self-assembled nanostructures, we performed fluorescence anisotropy measurements. In dye assemblies, the migration of energy (exciton diffusion) can produce a strong decrease of fluorescence anisotropy as the energy hops within

dyes of different orientation.<sup>22</sup> In the absence of non-coordinating anion, our fluorescent amphiphiles showed an anisotropy value in water close to that in methanol, thus reflecting the rotation of free dye molecules (Table 1). Remarkably, in the presence of F5-TPB the anisotropy decreased 5–8 fold for both dyes, confirming that the counterion induced their assembly into emissive multi-fluorophore nanostructures.

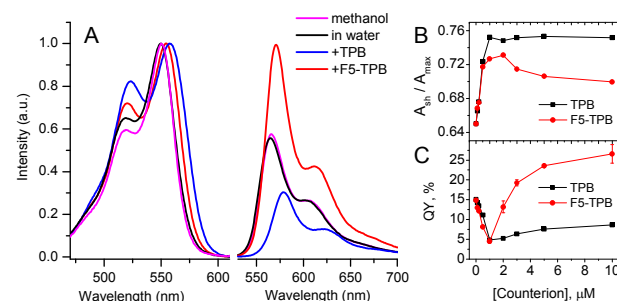

**Fig. 2.** (A) Absorption (normalized) and fluorescence spectra of 1  $\mu\text{M}$  solutions of Cy3A in methanol and water in the presence of TPB or F5-TPB (10 mol. eq.). Emission spectra were normalized to the same absorbance at 520 nm.  $\lambda_{ex} = 520 \text{ nm}$ . (B) The ratio of the absorption bands  $A_{sh}/A_{max}$  and (C) the fluorescence quantum yield of 1  $\mu\text{M}$  Cy3A in water vs. counterion concentration.


**Table 1.** Spectroscopic properties of Cy3A and Cy5A in molecular and micellar forms.<sup>a</sup>

Sample	$\lambda_{abs}$ (nm)	$\lambda_{em}$ (nm)	FWHM (nm)	QY (%)	Anisotropy
Cy3A/MeOH	550	566	40	15	0.153
Cy3A	550	565	57	15	0.171
Cy3A/F5-TPB	555	572	59	25	<0.02
Cy3A/TPB	557	581	66	8	0.034
Cy5A/MeOH	646	666	40	39	0.115
Cy5A	647	667	44	4	0.140
Cy5A/F5-TPB	651	687	39	8	<0.02
Cy5A/TPB	655	697	46	1	0.017

<sup>a</sup>FWHM – full width at half maximum; QY – fluorescence quantum yield measured using reference dyes (ESI).

Dynamic light scattering (DLS) measurements suggested that Cy3A in the presence of 10-fold excess of TPB and F5-TPB formed particles of  $7 \pm 1 \text{ nm}$  (polydispersity index, PDI=0.18) and  $12 \pm 3 \text{ nm}$  (PDI=0.22) hydrodynamic diameter, respectively. Remarkably, the zeta potential of Cy3A/F5-TPB NPs was strongly negative ( $-80 \pm 15 \text{ mV}$ ), likely due to adsorption at their surface of F5-TPB counterions, present in the excess. At 1/1 counterion/Cy3A ratio, the particle size was larger for both counterions ( $\sim 20 \text{ nm}$ ), likely due to aggregation of neutral NPs, in line with the drop in the QY values at this ratio (Fig. 2B). Cy5A samples were not measured, because of their direct excitation by the DLS laser source. Then, our NPs were studied by Atomic Force Microscopy (AFM). The dye amphiphiles in the presence of TPB or F5-TPB counterions were deposited on mica in aqueous solution of calcium chloride to bridge the


negatively charged NPs with the negatively charged glass surface. The best images were obtained for Cy3A with F5-TPB counterion, where relatively homogeneous NPs of 7 nm height were observed (Fig. 3), in line with the DLS data suggesting formation of ultra-small NPs. Taking into account that the length of Cy3A amphiphile (from the end of alkyl chain till the end of PEG chain) is about  $\sim 3$  nm, this small size suggests a micellar organization of NPs. In these micelles, the alkyl chains, the dye and the counterions form the core, while the PEG groups play a role of polar shell exposed to water (Figure 1). Other combinations of amphiphile/counterion gave similar sizes (Fig. 3C), though particles appeared more heterogeneous and larger in the XY directions (Figs. S4 and S5, ESI), which could be related to their aggregation at the mica surface.

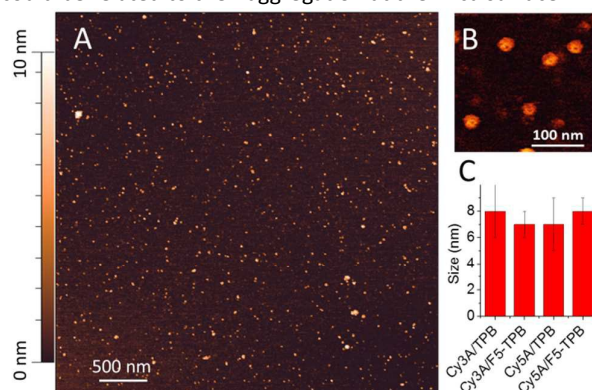

**Figure 3.** Atomic force microscopy of NPs formed by Cy3A and F5-TPB (10 mol. eq.) (A), a zoomed image (B) and particle sizes measured by AFM (height) for different samples (C).

Then, to evaluate their single particle properties, we performed fluorescence correlation spectroscopy (FCS). This unique technique, which measures diffusion of emissive species through a focal volume, provides direct access to the size, concentration and brightness of NPs.<sup>23,24</sup> As we used two-photon excitation source, we were able to study only Cy3A samples, which present appreciable two-photon absorption cross-section at 760 nm.<sup>25</sup> Only solutions of Cy3A with F5-TPB displayed stable FCS signal, which could be measured and analyzed. FCS data suggested that the size of NPs was 6.5 nm (Table S1, ESI), in perfect line with the AFM data (Figure 3B). Taken together, all used techniques suggest an ultra-small size of Cy3A/F5-TPB NPs, confirming our hypothesis on their micellar organization. Moreover, the brightness of these particles is close to 6 molecules of tetramethyl-rhodamine (TMR). Taking into account the two-photon absorption cross-section ( $\sigma_2$ ) of rhodamine at 760 nm (85 GM) and its quantum yield in water (0.4) and those for Cy3A dye (25 GM and 0.2, respectively),<sup>25</sup> we calculated that 6 rhodamines are equivalent to 41 Cy3A dyes. This calculation suggests that the micelle contains around 41 dyes, which is a typical aggregation number of amphiphiles (25-100). Finally, from the concentration of emissive species measured by FCS, and the total Cy3A concentration, we could find that the number of dyes per micelle is 25, in agreement with the number obtained from the single particle brightness.

To generate Förster Resonance Energy Transfer (FRET) inside our micelles, we prepared them from the mixtures of Cy3A (donor) and Cy5A (acceptor) in the presence of F5-TPB. Increasing the acceptor concentration (i.e. decrease in the donor/acceptor ratio) resulted in an increase of the acceptor emission and a decrease in the donor emission (Fig. 4A), a typical signature of FRET. The relative FRET efficiency ( $I_A/(I_D+I_A) \times 100$ ) increased with a decrease in the donor/acceptor ratios up to ratios 20/1 (Fig. 4B). Below this ratio, the relative FRET efficiency remained stable around 80%. Probably, at the donor/acceptor ratios  $\leq 20/1$  each micelle contained at least one acceptor, in line with the aggregation number  $>20$  estimated by FCS. Moreover, at donor/acceptor ratio  $\leq 20/1$ , we cannot exclude a partial donor/acceptor phase separation, described for other dye NPs.<sup>26</sup> Due to efficient FRET from multiple donors to a single acceptor, our micelles behave like a light-harvesting system. The antenna effect (AE) of our micelles, calculated as the ratio of intensities of donor and acceptor dyes in the excitation spectra, reached value of 30 (Fig. 4C). Based on the expression of antenna effect (see ESI) and assuming one acceptor per particle for high donor/acceptor ratios, estimated number of donors per particle is 63. The latter value is close to the aggregation number estimated by other methods (41 and 23), though some discrepancies are clearly related to the limitations of the methods and assumptions used.

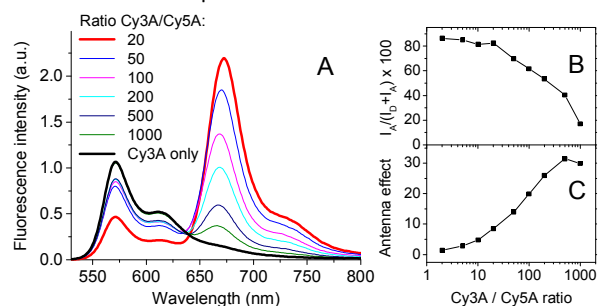

**Figure 4.** Fluorescence spectra showing FRET from Cy3A to Cy5A co-assembled with F5-TPB (10 mol. eq.) at different donor/acceptor ratios (A). The relative FRET efficiency (B) and antenna effect (C) as a function of donor/acceptor ratio. Concentrations of Cy3A was systematically 1  $\mu$ M.  $\lambda_{ex}$  = 520 nm.

As FRET is sensitive to the donor-acceptor distance, it can be used to study the integrity of nanostructures.<sup>24,27</sup> Remarkably, dilution up to 1000-fold of our FRET NPs originally prepared at 1  $\mu$ M concentration produced only minor modifications in their dual emission (Fig. S6, ESI), indicating that NPs remained nearly intact. Therefore, in the presence of F5-TPB the critical micellar concentration of Cy3A should be  $<1$  nM, whereas Cy3A alone does not aggregate well even at 1  $\mu$ M (Fig. S1, ESI). This result shows that charged amphiphiles having poor capacity to self-assemble could be brought together into stable nanostructures by non-coordinating anions. Finally, we verified whether the counterion-assembled cyanine micelles were stable over time by following the absorbance values of these solutions in plastic cuvettes (Fig. S7, ESI). For both Cy3A and Cy5A with chloride and TPB anions, the



absorbance clearly decreased over time, suggesting sedimentation of the particles and their adsorption on the walls of the cuvette. In sharp contrast, both Cy3A and Cy5A in the presence of highly fluorinated F5-TPB anion displayed almost negligible decrease in the absorbance, indicating a much higher stability of the obtained micelles.

In conclusion, using non-coordinating anion fluorinated tetraphenylborate, specially designed amphiphilic cyanine dyes were assembled into ~7-8 nm fluorescent NPs with minimized self-quenching. The obtained cyanine-3-based micelles were >40-fold brighter than the single cyanine dye. They exhibited efficient FRET to a single acceptor as well as stability to dilution up to 1 nM of the amphiphiles. The non-coordinating anions function as glue and spacer of dye amphiphiles, leading to small, stable and highly emissive fluorescent NPs. Thus, non-coordinating anions, especially fluorinated analogues, provide superior control for assembly of charged dye amphiphiles into functional nanomaterials.

I.S. acknowledges support from French Embassy. This work was supported by ERC Consolidator grant BrightSens 648528.

## Notes and references

1. T. Aida, E. W. Meijer and S. I. Stupp, *Science*, 2012, **335**, 813-817.
2. K. Ariga, J. P. Hill, M. V. Lee, A. Vinu, R. Charvet and S. Acharya, *Sci. Technol. Adv. Mater.*, 2008, **9**; S. Furukawa, J. Reboul, S. Diring, K. Sumida and S. Kitagawa, *Chem. Soc. Rev.*, 2014, **43**, 5700-5734.
3. C. Stoffelen and J. Huskens, *Small*, 2016, **12**, 96-119.
4. J. M. Lehn, *Science*, 2002, **295**, 2400-2403.
5. L. Graña Suárez, W. Verboom and J. Huskens, *Chem. Commun.*, 2014, **50**, 7280-7282.
6. T. Shimizu, M. Masuda and H. Minamikawa, *Chem. Rev.*, 2005, **105**, 1401-1443; J. D. Hartgerink, E. Beniash and S. I. Stupp, *Science*, 2001, **294**, 1684-1688.
7. C. F. J. Faul, *Acc. Chem. Res.*, 2014, **47**, 3428-3438; C. F. J. Faul and M. Antonietti, *Adv. Mater.*, 2003, **15**, 673-683.
8. R. Ahmed, S. K. Patra, I. W. Hamley, I. Manners and C. F. J. Faul, *J. Am. Chem. Soc.*, 2013, **135**, 2455-2458; Y. Huang, Y. Yan, B. M. Smarsly, Z. Wei and C. F. J. Faul, *J. Mater. Chem.*, 2009, **19**, 2356-2362; Y. Guan, M. Antonietti and C. F. J. Faul, *Langmuir*, 2002, **18**, 5939-5945; M. Antonietti and C. Goltner, *Angew. Chem. Int. Ed.*, 1997, **36**, 910-928.
9. I. Krossing and I. Raabe, *Angew. Chem. Int. Ed.*, 2004, **43**, 2066-2090.
10. M. Cametti, B. Crousse, P. Metrangolo, R. Milani and G. Resnati, *Chem. Soc. Rev.*, 2012, **41**, 31-42.
11. A. Reisch, P. Didier, L. Richert, S. Oncul, Y. Arntz, Y. Mely and A. S. Klymchenko, *Nat. Commun.*, 2014, **5**.
12. V. N. Kilin, H. Anton, N. Anton, E. Steed, J. Vermot, T. E. Vandamme, Y. Mely and A. S. Klymchenko, *Biomaterials*, 2014, **35**, 4950-4957.
13. H. Yao and K. Ashiba, *RSC Adv.*, 2011, **1**, 834-838.
14. H. Yao, M. Yamashita and K. Kimura, *Langmuir*, 2009, **25**, 1131-1137.
15. D. K. Bwambok, B. El-Zahab, S. K. Challa, M. Li, L. Chandler, G. A. Baker and I. M. Warner, *ACS Nano*, 2009, **3**, 3854-3860; A. N. Jordan, S. Das, N. Siraj, S. L. de Rooy, M. Li, B. El-Zahab, L. Chandler, G. A. Baker and I. M. Warner, *Nanoscale*, 2012, **4**, 5031-5038.
16. I. Shulov, S. Oncul, A. Reisch, Y. Arntz, M. Collot, Y. Mely and A. S. Klymchenko, *Nanoscale*, 2015, **7**, 18198-18210.
17. J. N. Israelachvili, D. J. Mitchell and B. W. Ninham, *J. Chem. Soc. Faraday Trans. 2*, 1976, **72**, 1525-1568.
18. X. Zhang, Z. Chen and F. Würthner, *J. Am. Chem. Soc.*, 2007, **129**, 4886-4887; R. Abbel, R. van der Weegen, E. W. Meijer and A. P. H. J. Schenning, *Chem. Commun.*, 2009, 1697-1699; A. Kaeser and A. P. H. J. Schenning, *Adv. Mater.*, 2010, **22**, 2985-2997; K. Petkau, A. Kaeser, I. Fischer, L. Brunsveld and A. P. H. J. Schenning, *J. Am. Chem. Soc.*, 2011, **133**, 17063-17071; J. H. Olivier, J. Widmaier and R. Ziessel, *Chem. Eur. J.*, 2011, **17**, 11709-11714; X. Zhang, D. Görl and F. Würthner, *Chem. Commun.*, 2013, **49**, 8178-8180; G. Chadha, Q. Z. Yang and Y. Zhao, *Chem. Commun.*, 2015, **51**, 12939-12942.
19. S. Fery-Forgues, *Nanoscale*, 2013, **5**, 8428-8442; K. Li and B. Liu, *Chem. Soc. Rev.*, 2014, **43**, 6570-6597; O. S. Wolfbeis, *Chem. Soc. Rev.*, 2015, **44**, 4743-4768; A. Reisch and A. S. Klymchenko, *Small*, 2016, DOI: 10.1002/smll.201503396.
20. Y. Hong, J. W. Y. Lam and B. Z. Tang, *Chem. Soc. Rev.*, 2011, **40**, 5361-5388; G. Battistelli, A. Cantelli, G. Guidetti, J. Manzi and M. Montalti, *Wiley Interdiscip. Rev.-Nanomed. Nanobiotechnol.*, 2016, **8**, 139-150; Y. Niko, Y. Arntz, Y. Mely, G.-i. Konishi and A. S. Klymchenko, *Chem. Eur. J.*, 2014, **20**, 16473-16477.
21. F. Würthner, T. E. Kaiser and C. R. Saha-Moeller, *Angew. Chem. Int. Ed.*, 2011, **50**, 3376-3410.
22. M. N. Berberan-Santos, P. Choppinet, A. Fedorov, L. Jullien and B. Valeur, *J. Am. Chem. Soc.*, 1999, **121**, 2526-2533; K. A. Colby, J. J. Burdett, R. F. Frisbee, L. Zhu, R. J. Dillon and C. J. Bardeen, *J. Phys. Chem. A*, 2010, **114**, 3471-3482; E. K. L. Yeow, K. P. Ghiggino, J. N. H. Reek, M. J. Crossley, A. W. Bosnian, A. P. H. J. Scheming and E. W. Meijer, *J. Phys. Chem. B*, 2000, **104**, 2596-2606.
23. K. Koynov and H. J. Butt, *Curr. Opin. Colloid Interface Sci.*, 2012, **17**, 377-387.
24. A. S. Klymchenko, E. Roger, N. Anton, H. Anton, I. Shulov, J. Vermot, Y. Mely and T. F. Vandamme, *RSC Adv.*, 2012, **2**, 11876-11886.
25. C. Xu and W. W. Webb, *J. Opt. Soc. Am. B*, 1996, **13**, 481-491.
26. A. Kaeser, I. Fischer, R. Abbel, P. Besenius, D. Dasgupta, M. A. J. Gillisen, G. Portale, A. L. Stevens, L. M. Herz and A. P. H. J. Schenning, *ACS Nano*, 2013, **7**, 408-416.
27. S. W. Morton, X. Zhao, M. A. Quadir and P. T. Hammond, *Biomaterials*, 2014, **35**, 3489-3496.