

Catalysis Science & Technology

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Catalysis Science & Technology

ARTICLE

Factors affecting the long-term stability of mesoporous nickel-based catalysts in combined steam and dry reforming of methane

K. Jabbour,^{a,b} N. El Hassan,^{a*} A. Davidson,^b S. Casale^{b,c} and P. Massiani^{b,c*}

Received 00th January 2016,
Accepted 00th January 2016

DOI: 10.1039/x0xx00000x

www.rsc.org/

An ordered mesoporous "one-pot" nickel-alumina catalyst (5 wt% Ni) was synthesized using the evaporation-induced self-assembly method. Compared to an impregnated and to a non-porous catalysts, the ordered "one-pot" Ni-alumina sample displayed, after *in-situ* reduction, the highest and the most stable catalytic performances along 40h of run at 800°C in combined steam and dry reforming of methane, with conversion and selectivity values close to the thermodynamic expected-ones. Both the confinement of well-dispersed Ni-nanoparticles within the structured Al₂O₃ framework and the strengthened Ni-support interaction compared to other catalysts are shown to be key factors accounting for the high catalytic activity and stability. Contrarily to alumina that appears as an effective support of Ni for catalytic combined methane reforming, neither mesoporous (SBA-15) nor macroporous (CeliteS, diatoms) silica are appropriate ones due to rapid deactivation by partial reoxidation of the metallic Ni⁰ active phase in the conditions of reaction.

1. Introduction

Nowadays, combined steam and dry reforming of methane (CSDRM) to synthesis gas (syngas, H₂ and CO mixture) is gaining significant attention. This process enables the production of syngas from renewable energy sources such as biogas whose main components are methane, carbon dioxide and water.¹ Simultaneously, this reaction allows the conversion of two major greenhouse gases (CH₄ and CO₂) into valuable gaseous mixtures, largely utilized as feedstock for the production of synthetic fuels and of chemical intermediates in petrochemical industries.² The product ratio of hydrogen to carbon monoxide is 3 in conventional steam reforming of methane (SRM, CH₄ + H₂O → 3H₂ + CO) and 1 in dry reforming of methane (DRM, CH₄ + CO₂ → 2H₂ + 2CO). However, applications involving syngas for subsequent utilization in methanol synthesis (syngas being then called metgas) require a H₂/CO product ratio close to 2 (2H₂ + CO → CH₃OH).¹ Such ratio may be also desired in some Fisher-Tropsch (FT) operations (e.g. (2n+1)H₂ + nCO → C_nH_(2n+2) + nH₂O) where the optimum reactant ratio (H₂/CO: (2n+1)/n) should be around 2 for large n values.^{1,3} In such case, the CSDRM process (CH₄ + 1/3 CO₂ + 2/3 H₂O → 8/3 H₂ + 4/3 CO) appears as a promising one-step approach giving an H₂/CO ratio around 2 and it is nowadays considered as an effective alternative to other reforming reactions,⁴ also allowing easy adjustment of the initial CH₄/CO₂/H₂O feed composition.^{1c,5} By comparison, both

methane partial oxidation (POM, CH₄ + 1/2O₂ → 2H₂ + CO) and auto-thermal reforming (ATR, CH₄ + 1/4O₂ + 1/2H₂O → 5/2H₂ + CO) can also produce a ratio near 2, but these processes, which involve oxygen, are more expensive and more difficult to control since the reactions can lead to local hot spots with associated dangers of explosions.⁴

Various supported monometallic catalysts have been studied for CSDRM and the available literature is summarized in Table 1. Amongst already tested active phases, a patent by Yagi et al.⁶ devoted to noble-metals (Ru /or Rh) supported on a basic support revealed steady performances for extended periods of time (up to 1000 h) at elevated pressures. However, with consideration of the high cost and limited availability of noble metals, their substitution by transition ones, such as Ni or Co, is desirable for large-scale applications and several works report high initial activities (table 1). Transition metals are, however, less stable than noble metals even if several tactics were already employed to enhance their time on stream (TOS) performances by limiting the sintering and/or coke deposition processes known to be the main causes of potential deactivation. Olah et al.^{1a,1b} developed effective Ni (or Co) dispersed on MgO catalysts for the targeted reaction (called bireforming in their papers) and reported performances significantly higher than those obtained on a Rh/MgO catalyst.^{5b,5c} The high activity was attributed to the formation of a solid-solution between the metal and the MgO support, leading to a stabilization of the nanoparticles during the run. Besides MgO, hydrotalcite like-materials decomposed into mixed oxides stand out as typical supports for Ni species (Table 1) with high activity and selectivity in CSDRM.^{9(a,c)} Similarly, Roh et al.^{5a} and Koo et al.^{9a} ascribed the enhanced performance of their hydrotalcite-based catalysts compared to Al₂O₃, CeO₂ and ZrO₂ based-ones (Table 1) to a higher dispersion of nickel nanoparticles resulting in an enhanced metal-support interaction (MSI).

^a Department of Chemical Engineering, Faculty of Engineering, University of Balamand, POBox 100, Tripoli, Lebanon, nissrine.hassan@balamand.edu.lb

^b Sorbonne Universités, UPMC Université Paris 06, Laboratoire de Réactivité de Surface, 4 place Jussieu, 75005 Paris, France.

^c CNRS UMR 7197, UPMC, Laboratoire de Réactivité de Surface, 4 place Jussieu, 75005 Paris, France, pascal.massiani@upmc.fr

Table 1 Bibliographic listing of the different types of already tested monometallic supported catalysts and of their performances in CSDRM.

Catalytic support	Active phase			Reactivity, selectivity				Rr**	T (°C)	P (bar)	Remarks		Ref
	Metal	wt%	Deposition*	X (%)		H ₂ /CO	Stability/selectivity***				Cat.	Improving method	
				CH ₄	CO ₂								
MgO	Ni	15		71	72	1.99		830	7	SS	---	1a	
	Ni	15		88	92	1.97		830	1	SS	---	1b	
	Co	15	Imp.	70	64	1.96	1/0.4/0.8	830	7	SS	---	1b	
	Ni	12		60	n.m.	n.m.		800	1	---	Change support to MgO-Al ₂ O ₃	5a	
	Ru	0.5		70	n.m.	n.m.	1/0.3/0.7	900	1	---	n.m.	5(b, c)	
Basic (n.m.)	Ru,Rh	n.m.	n.m.	n.m.	n.m.	n.m.	n.m.	n.m.	20	SS	---	6	
Al ₂ O ₃	Ni	n.m.	n.m.	72	n.m.	n.m.	1/0.4/0.8	800		---	Change support to MgO-Al ₂ O ₃	5a	
	Co	5		95	71	1.20	1/1/0.2	700		SS	---	7a	
		10		81	n.m.	n.m.		800		---	Change support to CeO ₂ -ZrO ₂	7b	
		12		75	n.m.	n.m.		750		---	20 wt% MgO	7c	
		12		61	50	n.m.	1/0.4/0.8	700		---	6 wt% CeO ₂	7d	
	Ni	7	Imp.	94	76	2.08		850	1	---	Treatment step	7e	
		7		98 ^[A]	83 ^[A]	2.02 ^[A]		850		SS	---	7e	
		4		89	49	1.49	1/0.3/0.7	750		S	---	7f	
		15		95	90	1.10	1/1/0.16	750		---	12 wt% MgO	7g	
		10	O.P.	92	76	2.70	1/0.3/0.7	800		S	n.m.	7h	
		Ni,Ti ^[A]	n.m.	n.m.	n.m.	n.m.	n.m.	n.m.	n.m.	n.m.	SS	---	8
	MgO _(x) -Al ₂ O ₃ _(y) x: 30,y: 70 wt%		12	Imp.	92	n.m.	n.m.		800		SS	---	5a
			n.m.	n.m.	91	90	1.90		800		---	Calcination T(°C)	9a
		12	Imp.	92	93	1.90		800		SS	---	9a	
		10		77	62	2.20	1/0.4/0.8	700	1	---	2.5 wt% CeO ₂	9b	
				97 ^[A]	7 ^[A]	2.10 ^[A]		750		---	(Mg/Al) ratio	9c	
		12		97	84	2.00		750		SS	---	9c	
				85	47	2.27		850		---	4 wt% CeO ₂	9d	
		15		74	35	2.22	1/0.4/1	850	10	---	15 wt%(CeO ₂ -ZrO ₂)	9e	
				95	90	n.m.	1/1/0.16	750	1	---	10 wt% La ₂ O ₃	9f	
		10	O.P.	94	74	2.80	1/0.3/0.7	800		S	n.m.	7h	
CeO ₂	Ni	12	Imp.	57	n.m.	n.m.	1/0.4/0.8	800	1	---	Change support to MgO-Al ₂ O ₃	5a	
		15		58	n.m.	n.m.		800		---	Change support to CeO ₂ -ZrO ₂	10	
ZrO ₂	Ni	12	Imp.	64	n.m.	n.m.	1/0.4/0.8	800	1	---	Change support to MgO-Al ₂ O ₃	5a	
		15		63	n.m.	n.m.		800		---	Change support to CeO ₂ -ZrO ₂	10	
Ce _(x) Zr _(y) O ₂ x: 80,y: 20 wt%	Ni	15	O.P.	97	80	n.m.	1/0.4/0.8	800	1	SS	---	7b	
			Imp.	94	n.m.	n.m.		800		SS	---	10	
SiO ₂	Ni,Ti ^[A]	n.m.	n.m.	n.m.	n.m.	n.m.	n.m.	n.m.	n.m.	SS	---	8	
	Ni	10	Imp.	98 ^[I]	86 ^[I]	1.74 ^[I]	1/0.5/0.75	850	1	---	3 wt% MgO	11	
Nd ₂ O ₃	Co	29	O.P.	73	86	2.40	1/0.35/0.7	850	1	S	n.m.	5d	
CaO	Ni	23	O.P.	92	80	1.58	1/0.5/0.5	800	1	SS	---	5e	
MgO-SA-525 ^[S]	Ni	13.6	Imp.	98	82	1.70	1/0.5/0.5	800	1	SS	---	5f	
Carbide	Mo			91 ^[I]	n.m.	2.00 ^[I]	1/0.3/0.7	900	8.7	SS	---	5g	
	W	5	O.P.	92 ^[I]	n.m.	1.97 ^[I]				SS	---	5g	
Al ₂ O ₃ _(x) -SiC _(y) x: 10,y: 95 wt%	Ni	12	Imp.	96	48	1.84	1/0.34/1.2	850	1	SS	---	12	
pNirb+MgO _(x) ^[#] x: 4 wt%	Ni	4	Imp.	57	n.m.	1.84	1/0.65/1.2	750	1	S	n.m.	13	
Ni plate	Ni	n.m.	O.P.	94	-19	3.40	1/0.33/1	750	1	S	n.m.	14	
ZrO ₂ -La ₂ O ₃	Ru	4	Imp.	25	n.m.	n.m.	1/1/5 vol%	500	1	SS	---	15a	

*: Metal deposited by post-impregnation (Imp.) on the support or by one-pot (O.P.) in the course of support synthesis

**: Molar composition of feeding reactants (CH₄/CO₂/H₂O- mol/mol/mol)

***: Catalysts (Cat.) stable and selective (SS) or stable but not selective (S) under reaction conditions; proposed routes of amelioration

n.m.: not mentioned

[+]: In addition to the mentioned metals, the list includes: V, Mn, Ga, Ca, Mo, Bi, Co, Nb, Zr, La, Sn

[A]: Steam pretreated Ni/Al₂O₃ sample. Preparation details are mentioned in the corresponding reference[-]: Ni/(MgO-Al₂O₃) with Mg/Al (molar ratio) of 3.5

[I]: Designate catalysts having supports with organized porous structures (micro and/or mesostructure)

[S]: MgO-SA-525 support is composed mainly of alumina (86.1 wt%) and silica (11.8 wt%) and is pre-coated with a layer of MgO (5.1 wt%)

[#]: pNirb+xMgO stands for porous nickel ribbon coated with MgO layer

In addition to the incorporation of promoters with specific properties (Table 1), some of the newest strategies for the development of stable and selective catalysts involve the usage of "original" supports able to improve MSI, such as silicon carbide

(SiC)¹² or porous Ni-plates,¹³ yet considered and in an extensive way in the case of DRM and SRM reactions.

The list of reforming catalysts based on Ni dispersed on different supports includes as well the conventional oxide that is alumina, which generally provides superior initial activities (in terms of CH₄ and CO₂ conversions)⁷ than those recorded on CeO₂,^{5a,10} ZrO₂,^{5a,10} or

MgO^{5a} under stoichiometric feed of gases. Nevertheless, in addition to patented studies, many works point out that, due to the high endothermic character of the reaction¹⁵ (generally conducted at $T \geq 750^\circ\text{C}$, Table 1), Ni dispersed on Al₂O₃ catalysts currently suffer from the major drawback of deactivation, thus resulting in rapid losses of activity.^{5a,7(a,c,d,e,g)} Even if stable, some Al₂O₃-based catalysts also demonstrated lack of selectivity, giving H₂/CO molar ratios different from 2 in spite of conditions expected to favor such ratio.^{7(f,h)} As lately reviewed by Li et al.,^[16] the main orientation towards catalytic development is shifting towards monometallic supported catalysts characterized by highly dispersed metallic nanoparticles and strengthened MSI. Achieving such properties should effectively hinder the deactivation process by providing continuous accessibility to the active sites, along with reduced coking kinetics over size-controlled particles smaller than a "critical size". However, maintaining a high dispersion of Ni-particles with nano-scale dimensions over the support under harsh reduction and reaction conditions is a challenging task, yet it is a priority for reforming reactions especially those conducted in presence of steam where sintering becomes highly favored.¹⁷ In this context, an improved Ni/Al₂O₃ catalyst was developed by Son et al.^{7e} by enhancing the interaction of Ni with their commercial alumina support after an additional steam treatment session (H₂/H₂O) following a H₂-reduction one, and they obtained an effective combined reforming catalyst with enhanced coking and sintering limitations.

Another promising approach is the confinement of well-dispersed nano-particles within standard oxides having ordered mesoporous channels, to stabilize and minimize their growth during reaction and thus allow preserving a stable reactivity on TOS. In the previous literature, Ni-loaded mesoporous catalysts based on SBA-15 silica or mesoporous Al₂O₃ displayed ascendant catalytic activity for both the dry and the steam reforming reactions^{18,19} owing to the special structural features of these supports. Despite the particular properties of ordered-structured materials and the expectation of promising performances even in combined reforming conditions,^{5g} the literature dealing with the preparation of such oxides for their application in CSDRM is still very limited (table 1). In addition, there exists to our knowledge no work establishing correlation between the catalytic performances and the physicochemical properties of such reduced materials.

Based on this state of the art, the purpose of the present work was to understand the eventual role of the porous network in promoting the catalytic performances in CSDRM by comparing a non-porous and two mesoporous (obtained either by direct synthesis or by impregnation) alumina-based catalysts with same Ni content (5 wt%). As far as we know, even though Ni on alumina catalysts have been widely studied (Table 1), structured alumina was never investigated as support of Ni in combined methane reforming. Our goal when applying different preparation methods was also to identify the effect of the syntheses conditions towards stability of the metallic nickel nanoparticles dispersed over (or in) the alumina support. Two methods were thus applied: post-impregnation by the two-solvents technique²² and a direct synthesis approach expected to favor the formation of strong Ni-alumina interaction²⁰ in principle favorable to Ni stabilization during combined reforming.^{7e} A special attention was addressed as well to

the fine characterization of the reduced materials (active form for the reaction). To understand the impact of the support on the physicochemical properties and on their consequences on catalysis, we also tested two silica supports, for comparison: an ordered mesoporous SBA-15 (prepared by typical sol-gel method)²³ and a natural, low-cost, and widely available, macroporous diatomite (CeliteS). The selection of these supports was based on our recent results^{18(a,b),21} showing promising catalytic behaviors in DRM for both Ni/SBA-15 and Ni/diatoms catalysts.

2. Experimental

2.1 Catalysts preparation

Syntheses of "one-pot" alumina-based materials: The mesoporous nickel containing alumina was prepared via "one-pot" evaporation-induced self-assembly (EISA) method by fine control of the evaporation process, based on literature reported previously.²⁰ The amount of Ni was fixed at 5 wt% as for all Ni-containing samples investigated in this study. The synthesis procedure consisted in dissolving 1.0 g of (EO)₂₀(PO)₇₀(EO)₂₀ triblock copolymer (Pluronic P123, M_n= 5800, Sigma Aldrich, 43546-5) at room temperature (RT) in 20 ml absolute ethanol under vigorous stirring, mixing it with 1.6 ml of 65.0 wt% nitric acid (HNO₃, Johnson Matthey S.A., extra pure), then adding simultaneously into the stirred solution 1.94 g of aluminium isopropoxide (Al(OPr)₃ 98+%, Sigma Aldrich, 220418) and 1.02 g of nickel nitrate hexahydrate (Ni(NO₃)₂·6H₂O, Sigma Aldrich, 13478-007); this corresponds to a total (Al + Ni) molar composition of 10 mmol. This final mixture was covered with a polyethylene (PE) film, continuously stirred at RT for at least 7 hours until complete dissolution, and finally transferred into a beaker placed in a digital auto-regulator water-bath (Stuart SWB6D) set at 60°C to undergo the slow evaporation process (ethanol, acid) for 48 hours straight. The obtained light green xerogel (due to the presence of tetrahedral Ni²⁺ ions) was calcined slowly in air at 600°C for 5 hours (heating rate 0.5°C·min⁻¹) to give the Ni_{5%}Al₂O₃(meso) sample. The exact same procedure applied without addition of nickel precursor (but increasing the amount of aluminium isopropoxide to 10 mmol to keep constant overall concentrations) led to mesoporous Al₂O₃(meso) (used below as support). In addition, a non-porous reference sample, labeled Ni_{5%}Al₂O₃(np), was synthesized by following the above described methodology but in absence of the structuring (BASF P123) agent.

Preparation of silica supports: The mesoporous SBA-15 silica support was synthesized according to a standard procedure described by Zhao et al.^{23a} A double jacketed beaker of 2 L with an integrated stirring rod was used to obtain a homogenous texture, despite the large batch size. The batch was prepared using 60 g of P123 dissolved in 1.1 L of 0.3 mol·L⁻¹ HCl solution, before adding drop-by-drop 129 g of tetraethyl orthosilicate (TEOS 98+%, Sigma Aldrich, 13190-3) as silica source. Stirring was stopped just after TEOS addition, as recommended to favor the formation of isolated silica grains.^{23b} After 24 hours at 35°C, the hybrid product (solid and synthesis liquor) was introduced inside a stainless steel autoclave with an internal cover of Teflon and kept at 130°C for 24 hours. The solid fraction was next isolated by filtration on paper, washed with distilled water (6 L), then calcined in air (thin bed) at 500°C for 9

hours (heating rate $2^{\circ}\text{C min}^{-1}$) to liberate the pores from the P123 template and to thus give sample SBA-15. For comparison purpose, a commercial diatomite natural silica sample, called CeliteS (Sigma Aldrich, 61790-532), was also used as support.

Preparation of impregnated samples: Impregnation of nickel was carried out on the Al_2O_3 (meso), SBA-15 and CeliteS supports using the “two solvents” loading method detailed elsewhere²²: briefly, 1g of each type of support was suspended in 35 ml of cyclohexane (C_6H_{12} , Sigma Aldrich, 17919-1) under stirring for 2-3 minutes. Then 0.7 ml of an aqueous nickel solution containing 0.05g of Ni was added dropwise, using $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ as nickel precursor. The suspension was left to dry at RT (cyclohexane and water evaporation) before undergoing calcination in air (thin bed) at 450°C for 5 hours (heating rate $0.5^{\circ}\text{C.min}^{-1}$) for removal of the adsorbed nitrates by oxidative desorption. The resulting samples are designated as $\text{Ni}_{5\%}\text{Al}_2\text{O}_3$ (imp), $\text{Ni}_{5\%}\text{SBA-15}$ (imp) and $\text{Ni}_{5\%}\text{CeliteS}$ (imp), respectively.

2.2 Catalysts characterizations

N_2 adsorption-desorption isotherms were obtained at -196°C on a Micromeritics ASAP 2020 instrument. Prior to measurement, the samples (40 mg) were degassed under vacuum for 3 hours at $T = 300^{\circ}\text{C}$. The Brunauer-Emmett-Teller (BET) surface areas were calculated from BET equation for a relative pressure (P/P_0) range between 0.05 and 0.25. The single point pore volume was calculated from the adsorption isotherm at a relative pressure of 0.990, pore size distribution was calculated using the Barrett-Joyner-Halenda (BJH) method for the adsorption branch of the isotherm, otherwise clearly specified.

Powder X-ray diffraction (XRD) measurements were performed on a PANalytical XPERT³ diffractometer using $\text{Cu K}\alpha$ radiation ($\lambda = 1.5405$ nm) at RT from 2θ of 20.0 to 90.0° (WAXS for wide angle X-ray scattering). The measurements were conducted at a voltage of 30 kV, the current was set at 10 mA and the step size was 0.02° . Crystalline phase identification was based on comparison with standard powder XRD files published by the international center for diffraction data (ICDD). Coherent domain sizes were calculated using the Scherrer equation: $D_{(hkl)} = (K\lambda/\beta\cos\theta)$, where $K = 0.9$ is the shape factor for spherical particles, λ is the X-ray wavelength ($\lambda = 1.5405$ nm for $\text{Cu K}\alpha$), β is the full width at half maximum (FWHM) of the diffraction peak and θ is the peak position. The small angle X-Ray scattering (SAXS) measurements were recorded from 2θ of 0.5 to 4.0° (time per step: 1 s) on a BRUKER type D8 ADVANCE diffractometer equipped with a $\text{Cu K}\alpha$ irradiation source ($\lambda = 1.5418$ nm) and operating at 40 kV and 30 mA.

Temperature programmed reduction (H_2 -TPR) was performed on an Autochem 2920 unit, Micromeritics. The sample powder (100 mg) was loaded in a U-shaped quartz reactor and heated from RT up to 900°C at a rate of $7^{\circ}\text{C.min}^{-1}$ under a 5vol% H_2/Ar flow (30 ml.min^{-1}). The overall H_2 consumption was constantly recorded by thermal conductivity detection (TCD). Before arrival to the detector, the gas flow was passed through a cold trap (made of ice and NaCl) to remove any water generated during reduction and thus insure detection of the sole reduction process.

High-resolution transmission electron microscopy (HRTEM) images were taken on a JEOL-JEM 200 electron microscope operating at 200 KeV (LaB₆ gun) and equipped with an energy dispersive

spectroscopy (EDS) probe for local chemical analyses. In order to determine average particle sizes and compare them with the estimation based on XRD, the software “Comptage de Particules (LRS)” was used considering at least 500 particles for each sample. TGA-DSC was performed to quantify carbon deposition amounts on the spent catalysts on a TA SDT Q600 thermal analyzer instrument from RT to 900°C (heating rate $10^{\circ}\text{C.min}^{-1}$) in flowing air (50 ml.min^{-1}). The exhaust gas was analyzed by online gas spectrometry (MKS, ThermoSTAR) by following the masses (m/z) for CO (28) and CO_2 (44).

2.3 Reactivity measurements

The catalytic test facility consisted of mass flow controllers, a water generator unit (Syringe pump, Teledyne ISCO, D-series, model 5000), a reactor unit (Microactivity, PID Eng and Tech) and a gas analysis unit (Inficon Micro-GC) equipped with a TCD and two columns in parallel for the detection of CH_4 , CO and H_2 (molecular sieve column) and CO_2 (plot U column). Catalytic reactions for combined steam and dry reforming of methane were conducted at atmospheric pressure ($P = 1$ atm) in a vertical fixed-bed continuous flow stainless steel (SS310) reactor. Prior to reaction, each sample (100mg, non-diluted, calcined form) was *in-situ* pre-treated (reduced) at 800°C for 3 hours under a flow (30 ml.min^{-1}) of 5 vol% H_2/Ar . The flow was then switched to the reactants mixture $\text{CH}_4/\text{CO}_2/\text{H}_2\text{O}/\text{Ar} = 1/0.4/0.8/12$. This feed composition, with CH_4/CO_2 ratio (1/0.4) slightly different from the stoichiometric one (1/0.33, see CSDRM reaction detailed in section 1), was chosen because it is best suited (due to side reactions) to produce a syngas with H_2/CO ratio close to 2, based on bibliography^{1a,5a,5b,5c} and on the HSC 7.1 simulation software (H, S and C stand for enthalpy, entropy and heat capacity, respectively) used to calculate (i) thermodynamic conversion (CH_4 and CO_2) levels and (ii) expected products (H_2 and CO) contents at the applied conditions of temperature, pressure and composition (considering also dilution and carbon deposition). The gas hourly space velocity (GHSV) was $69 \text{ L.g}_{\text{cat}}^{-1}.\text{hr}^{-1}$. Water was introduced by a pump in the form of liquid water ($0.005 \text{ ml.min}^{-1}$) that underwent evaporation (6.15 ml.min^{-1}) at 180°C (hotbox temperature) and was then mixed with the other gases and fed into the reactor. The reforming reaction was carried out at 800°C for 40 h. The reaction temperature was controlled using a thermocouple placed in the middle of the reforming catalyst bed. The effluent was passed through a gas/liquid separator for condensing the residual steam before analyzing the gaseous mixture (H_2 , CO products and unreacted CH_4 and CO_2) by Micro-GC. Catalytic measurements were repeated twice over each catalyst to check the reproducibility of the data. The conversion of CH_4 (X_{CH_4}) and CO_2 (X_{CO_2}) and the obtained syngas ratio (H_2/CO) were calculated using Eqs. (1)-(3):

$$X_{\text{CH}_4}(\%) = \frac{[\text{CH}_4]_{\text{in}} - [\text{CH}_4]_{\text{out}}}{[\text{CH}_4]_{\text{in}}} \times 100 \quad (1)$$

$$X_{\text{CO}_2}(\%) = \frac{[\text{CO}_2]_{\text{in}} - [\text{CO}_2]_{\text{out}}}{[\text{CO}_2]_{\text{in}}} \times 100 \quad (2)$$

$$\frac{\text{H}_2}{\text{CO}} = \frac{\text{mol of H}_2 \text{ produced}}{\text{mol of CO produced}} \quad (3)$$

3. Results and discussion

3.1 Reducibility of the calcined Ni-based catalysts

The overall experimental H₂-uptake at 900°C (Table 2) was consistent with the complete reduction of the targeted amount of Ni-species (circa 900 μmol.g⁻¹ for 5 wt% Ni) over each of the studied samples. The types and relative abundances of reducible Ni-species were directly correlated to their degree of interaction with the support as revealed from their reduction temperature on TPR profiles (Fig. 1).

SiO ₂ -based samples	Total H ₂ uptake (μmol.g ⁻¹)	Relative amount of Ni ²⁺ species ⁽⁺⁾ (%)			
		T < 450°C	T > 450°C		
Ni _{5%} CeliteS(imp)	940	49	51		
Ni _{5%} SBA-15(imp)	892	30	70		
Al ₂ O ₃ -based samples					
Al ₂ O ₃ -based samples	Total H ₂ uptake (μmol.g ⁻¹)	T < 500°C			
		T > 500°C			
		Ni _{5%} Al ₂ O ₃ (np)	958	78	22
		Ni _{5%} Al ₂ O ₃ (imp)	901	20	80
Ni _{5%} Al ₂ O ₃ (meso)	941	3	97		

(+) Determined by H₂-TPR analysis as a function of reduction temperature.

Concerning the Ni-based silica samples, two types of species were distinguished: (i) those undergoing reduction within a temperature range below 450°C, attributable to easily reducible free NiO and (ii) Ni species with enhanced interaction with silica, reduced at higher temperatures, typically above 450°C.²⁴ For Ni_{5%}CeliteS(imp) (Fig. 1A, profile (a)), Ni tended to be equally distributed (Table 2) between the two categories. With Ni_{5%}SBA-15(imp) (Fig. 1A, profile (b)), the dominant contribution corresponded to species with enhanced interaction with silica. This difference might be the result of different availabilities in SiO₂ surface sites, related to the distinct surface areas and pore volumes between both silica supports (as introduced in section 3.3): indeed, the smaller available surfaces on CeliteS would limit the formation of mixed phases during the impregnation steps.²⁵

A similar reducibility classification could be adopted for nickel on alumina-based samples, with characteristic temperature ranges depending upon the interaction between nickel and alumina. Ni_{5%}Al₂O₃(np) (Fig. 1B, profile (c)) presented peaks at T > 600°C, attributed to the reduction of nickel strongly interacting with the support, better described as nickel-aluminate spinel phases. The peaks centered at T < 600°C (starting above 500°C, Fig. 1B) were mainly assigned to free and easily reducible NiO particles having low MSI.²⁶ Based on quantifications (Table 2), it is clear that the non-porous sample housed notably higher amounts of free NiO species compared to impregnated Ni_{5%}Al₂O₃(imp) (Fig. 1B, profile (d)) and to "one-pot" Ni_{5%}Al₂O₃(meso) (Fig. 1B, profile (e)). Interestingly, Ni_{5%}Al₂O₃(meso) displayed peaks located generally at temperatures higher than 600°C suggesting that all Ni-species are in strong interacting with the structured alumina matrix. This is in agreement with previous results obtained by Xu et al.^{18e} reporting absence of dissociated or of free nickel oxides having no interaction with the support. Similarly, Morris et al.^{20a} studied the solid state ²⁷Al MAS NMR (nuclear magnetic resonance spectroscopy) spectra of mesoporous "one-pot" Ni-Al₂O₃ samples and deduced that nickel atoms, deposited in the course of alumina precipitation, replaced tetrahedrally coordinated aluminum atoms generating, as a

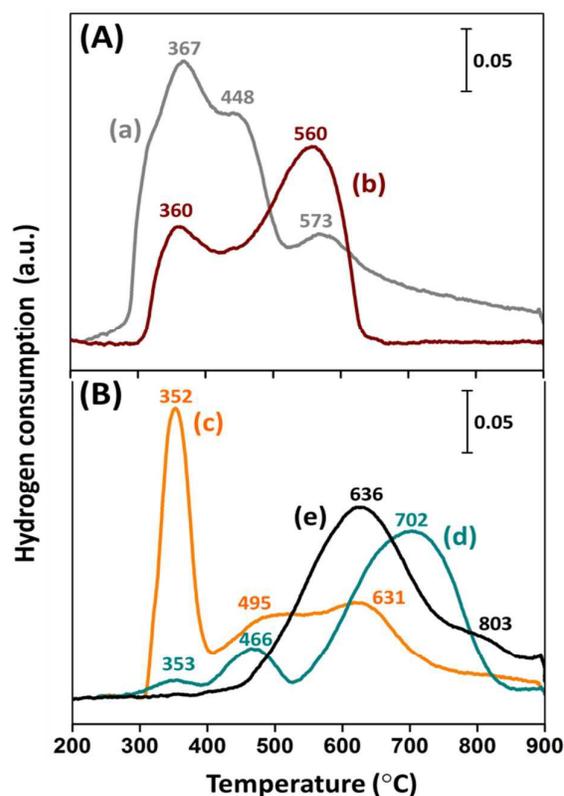


Fig. 1 H₂-TPR profiles of (A) calcined silica-based samples: (a) Ni_{5%}CeliteS(imp), (b) Ni_{5%}SBA-15(imp) and (B) calcined alumina-based samples: (c) Ni_{5%}Al₂O₃(np), (d) Ni_{5%}Al₂O₃(imp) and (e) Ni_{5%}Al₂O₃(meso).

consequence, solid solutions of Ni inside alumina in the form of Ni-O-Al structures. Hence, the relatively high reduction temperature of the "one-pot" Ni_{5%}Al₂O₃(meso) sample originated from Ni species characterized by strong MSI. As for impregnated Ni_{5%}Al₂O₃(imp), the route of its preparation generated both types of species (Ni-aluminates and free NiO species). With respect to the slight temperature differences observed for the main peaks between the two samples, it should be recalled that TPR is carried out in dynamic conditions, far from equilibrium, which potentially affects the overall reduction signature depending on the size and location of the species involved. The importance of establishing strong MSI between Ni and alumina is expected to inhibit sintering of metallic particles whereas NiO species, with weaker interaction with Al₂O₃, should present a greater tendency to deactivate by sintering as was recently demonstrated by Fang et al.^{18d} in DRM conditions.

3.2 Catalytic reactivity in combined reforming of methane

Before catalytic tests, the calcined samples were *in-situ* reduced to generate the metallic Ni⁰ particles required for the reaction. Catalytic performances in terms of reactivity and selectivity as a function of test duration are displayed in Fig. 2.

Under our reaction conditions (CH₄/CO₂ molar ratio of 1/0.4) and based on thermodynamic calculations, a higher CH₄ conversion (by almost 6%) should be a priori expected compared to that of CO₂. For both silica-based catalysts, the initial CO₂ conversion largely exceeds, on the contrary, that of CH₄ (curves (a,b), Fig. 2(A,B)), suggesting strong occurrence of the reverse water gas shift (RWGS,

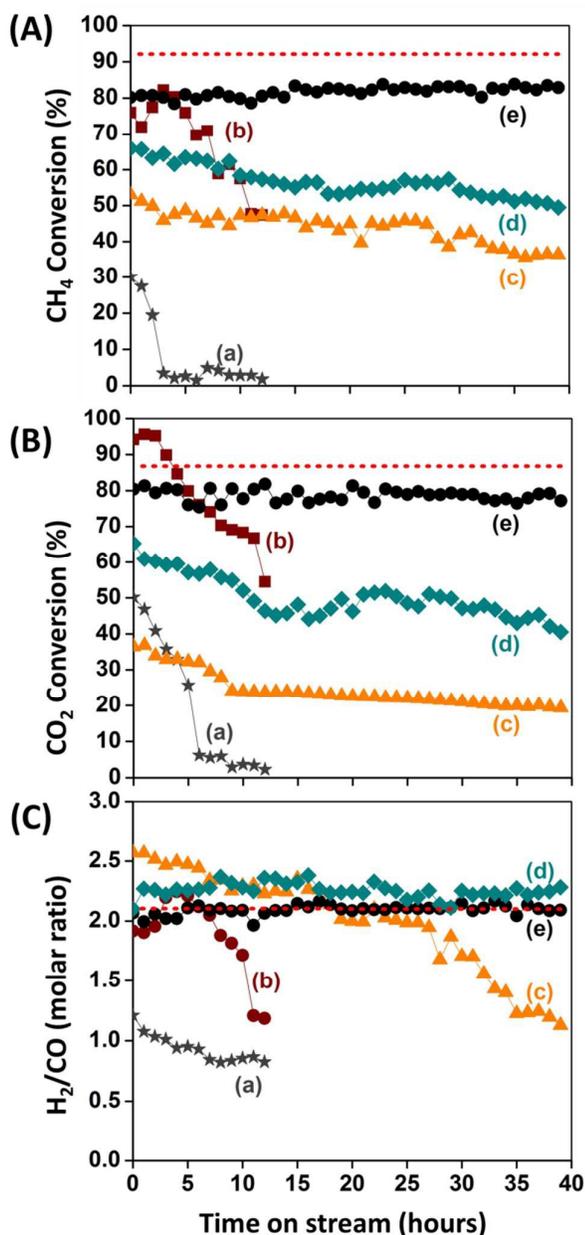


Fig. 2 (A) CH₄ and (B) CO₂ conversions and (C) molar H₂/CO product ratio during combined methane reforming (T= 800°C and P= 1 atm) over *in situ* reduced (a) Ni_{5%}CeliteS(imp), (b) Ni_{5%}SBA-15(imp), (c) Ni_{5%}Al₂O₃(np), (d) Ni_{5%}Al₂O₃(imp) and (e) Ni_{5%}Al₂O₃(meso). Thermodynamic values (pointed-lines) are calculated with the HSC 7.1 software.

CO₂ + H₂ → H₂O + CO) side-reaction. This agrees with the low H₂/CO product ratios (curves (a,b), Fig. 2C) compared to the expected one for CSDRM. Conversions on both catalysts continuously decrease with time on stream (being however significantly higher on Ni_{5%}SBA-15(imp)) and the H₂/CO ratios drop down to values close to 1 indicating that simultaneous dry and steam reforming reactions are no longer taking place. Instead, strong deactivation occurs, due to reoxidation of metallic nickel nanoparticles as will be deduced later on from spent catalysts characterizations (section 3.5).

In the alumina-based catalysts family, Ni_{5%}Al₂O₃(np) suffers since the very beginning from rapid deactivation with respect to both CH₄ and CO₂ conversions (curves (c), Fig. 2(A,B)), along with a severe decline in the molar product ratio from 2.5 to 1.1 (curve (c), Fig. 2C). The initial H₂/CO ratio was similarly slightly above 2 (close to 2.2) for impregnated Ni_{5%}Al₂O₃(imp), but this value remained at this level even during progressive deactivation on stream (curves (d), Fig. 2A-C). Also, slight fluctuations (both in H₂/CO ratios and in CO₂ conversions) along with CH₄ conversions higher than CO₂ ones by more than 6% were seen, possibly indicating an imbalance in the combined reaction with SRM occurring preferentially with respect to DRM.^{7f,7h,15b} The higher CH₄ than CO₂ conversion could also be due to methane decomposition to C(s), but the former assumption is most likely since low amounts of carbon were observed over these 2 samples (see section 3.5). Concerning the Ni_{5%}Al₂O₃(meso) catalyst (curves (e), Fig. 2A-C), it maintained the most active, stable and selective behaviour, with moreover reactivity values close to the maximum expected ones with respect to thermodynamic equilibrium data (red-pointed lines).

Thus the performances of the "one-pot" Ni_{5%}Al₂O₃(meso) catalyst appear highly promising, and this stands also when compared to bibliographic performances obtained by other teams over alumina based-catalysts, even at higher Ni loadings. It is worth recalling that deactivation is commonly reported for nickel alumina-based catalysts (Table 1) and extensive studies continue to be carried out to overcome the drawbacks of coking and Ni sintering generally encountered on conventional alumina supports. For instance, basic hydrotalcite^{5a} or mixed CeO₂-ZrO₂^{7b} oxides were proposed as more suitable than alumina for nickel species dispersion. Moreover, addition of promoters having basic (MgO)^{7c,7e} or redox (CeO₂)^{7d} properties on Ni/Al₂O₃ catalysts was proved to be beneficial towards coking and sintering limitations (by enhancing MSI). Additionally, García-Diéguez et al.^{7f} used a nano-fibrous high surface area alumina to improve Ni dispersion and found high initial CH₄ conversion but low CO₂ conversion and consequently a H₂/CO ratio far from 2 (Table 1) even after doping with Rh (0.04 wt%). Similarly, Kang et al.^{7g} proceeded towards the protection of nickel particles from agglomeration and coking by synthesizing a core-shell sample with Ni⁰ nanoparticles coated by Al₂O₃. Their 10 wt% Ni/Al₂O₃ catalyst exhibited high and stable CH₄ conversion but low CO₂ conversion as well as low selectivity with respect to metgas production (Table 1), due to SRM dominance relatively to DRM and to decay in the reactions leading to CO formation. Finally, Son et al.^{7e} developed a stable and selective 7 wt% Ni/Al₂O₃ catalyst by Ni impregnation on a commercial Al₂O₃ support but its preparation required extensive post-synthesis treatments. Therefore, the above "one-pot" Ni_{5%}Al₂O₃(meso) catalyst, obtained by direct (one-step) synthesis and by using a mono-metallic standard type of support (alumina), represents a highly effective candidate for CSDRM, offering the advantage of avoiding post-synthesis treatments and secondary metals (eventually expensive) incorporation.

3.3 Structure and porosity of calcined and reduced samples

The textural and structural properties of the calcined and of the reduced (similar reduction treatment as before reaction) samples were evaluated by SAXS analysis (Fig. 3(A,B)) and N_2 adsorption measurements (Table 3, Fig. 3(C,D)).

For all SBA-15 based-samples, a well-resolved high intensity (100) peak accompanied with two tiny (110) and (200) peaks were seen, all characteristic of an highly ordered hexagonal $p6mm$ mesoporous structure.^{22a} the network of the parent SBA-15 support (pattern c, Fig. 3A) was thus preserved after impregnation followed by calcination (pattern d, Fig. 3A) as well as after high temperature reduction (pattern d', Fig. 3A). Some collapse (lower peaks intensities) and some pore shrinking (regular shift to higher angles) were however noted along successive thermal treatments as also confirmed below based on N_2 sorption data. Concerning the diatomite family (patterns (a,b,b'), Fig. 3A) no evidence of any ordered-porosity was detected, even over the (Ni free) CeliteS support.

Concerning the mesoporous alumina family (Fig. 3B), a diffraction peak at circa 0.94° and a weak one at circa 1.5° , respectively ascribed to the (100) and (110) plane reflections of a well-ordered alumina based-mesostructure,²⁰ were systematically visible, with however a slight intensity decrease

when going from (Ni free) Al_2O_3 (meso) (pattern a) to calcined (pattern d) then reduced (pattern d') $Ni_{5\%}Al_2O_3$ (meso). These observations indicate that the Ni incorporation in the synthesis medium did not strongly affect the 2D hexagonal alumina structure ($p6mm$ symmetry) and that the "one-pot" ordered nickel alumina sample had a very good thermal stability (even under high temperature reduction). In this series of samples, a shift of the main peak also detected between (Ni free) Al_2O_3 (meso) and $Ni_{5\%}Al_2O_3$ (meso) suggests a slightly higher pore opening in the Ni containing sample, as will be indeed confirmed latter on. Contrarily, diffraction peaks were no longer detected for impregnated $Ni_{5\%}Al_2O_3$ (imp) (patterns (c,c'), Figs. 3B) implying that the long-range ordered mesopores of the parent Al_2O_3 (meso) support had been blocked (partially damaged) during the impregnation process. Finally, $Ni_{5\%}Al_2O_3$ (np) presented no SAXS peaks (patterns (a,a'), Fig. 3B) in line with the absence of structuring agent in its course of synthesis.

Complementary to SAXS, N_2 -sorption analysis demonstrated typical type IV isotherms with H_1 -type hysteresis loops, reflected by the appearance of capillary condensation steps at $P/P_0 = 0.6-0.8$ for the parent SBA-15 and Al_2O_3 (meso) supports (curves (c,a), Figs. 3(C,D), respectively) and for the $Ni_{5\%}$ -SBA-15

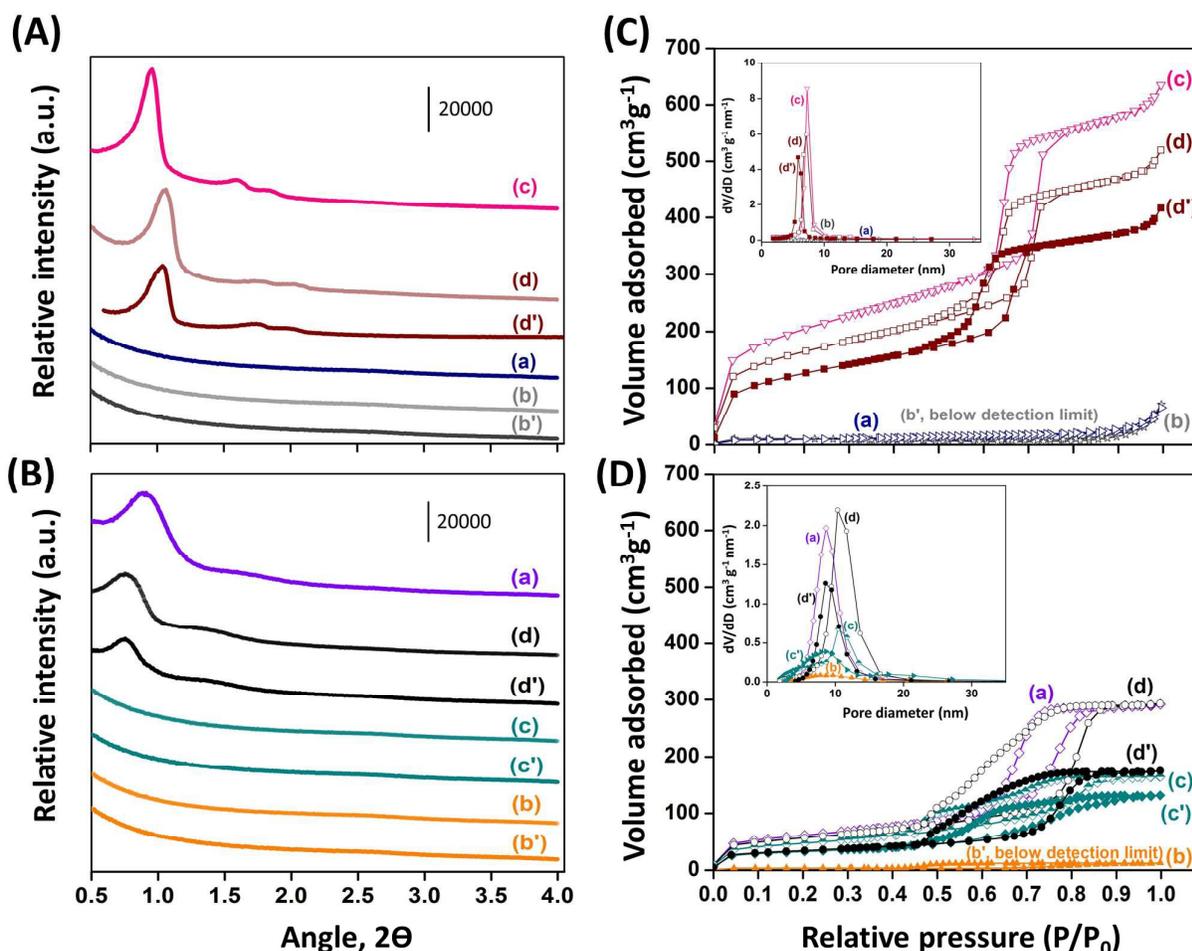


Fig. 3 (A,B) SAXS patterns and (C,D) N_2 adsorption-desorption isotherms and pore size distributions (inset figures) of calcined and reduced (b',d'), (b'-d') silica (A,C) and alumina (B,D) based-samples. SiO_2 -based samples: (a) CeliteS, (b,b') $Ni_{5\%}$ CeliteS(imp), (c) SBA-15 and (d,d') $Ni_{5\%}$ SBA-15; Al_2O_3 -based samples: (a) Al_2O_3 (meso), (b,b') $Ni_{5\%}Al_2O_3$ (np), (c,c') $Ni_{5\%}Al_2O_3$ (imp) and (d,d') $Ni_{5\%}Al_2O_3$ (meso). For XRD patterns, an offset was applied along Y-axis for the sake of clarity.

Table 3 Textural properties of the silica and alumina -based samples

Samples	BET specific surface area (m ² .g ⁻¹)	Pore volume (m ³ .g ⁻¹)	Average pore diameter (nm)
Calcined			
CeliteS	30	0.11	---
Ni _{5%} CeliteS(imp)	21	0.09	---
SBA-15	672	0.87	7
Ni _{5%} SBA-15(imp)	540	0.72	6.5
Al ₂ O ₃ (meso)	225	0.46	8.4
Ni _{5%} Al ₂ O ₃ (np)	18	0.02	---
Ni _{5%} Al ₂ O ₃ (imp)	170	0.31	6.8
Ni _{5%} Al ₂ O ₃ (meso)	215	0.45	9.5
In-situ reduced (H₂)			
Ni _{5%} CeliteS(imp)	---	---	---
Ni _{5%} SBA-15(imp)	424	0.61	6.2
Ni _{5%} Al ₂ O ₃ (np)	---	---	---
Ni _{5%} Al ₂ O ₃ (imp)	104	0.21	7.7
Ni _{5%} Al ₂ O ₃ (meso)	111	0.33	9.0

and Ni_{5%}Al₂O₃(meso) samples (curves d, Figs. 3(C,D), respectively).

Their pore size distributions PSD (inset figures and Table 3) were quite sharp and uniformly located within the conventional range of mesopores with textural values (Table 3) in accordance with previous studies on similar materials.^{18a,18c}

Yet, the larger pore diameter of Ni_{5%}Al₂O₃(meso) (calcined form) compared to that of nickel free Al₂O₃(meso) (Table 3) follows a trend similar to that already reported by Morris et al.^{20a} It can be the result of nickel incorporation into the mesoporous alumina structure, probably in the form of Ni-O-Al²⁷ (in line with the TPR analysis).

Moreover, it is worth noting that the desorption branch of the “one-pot” sample was typical of “ink-bottle” interconnected pores with different size distributions of cavities and necks²⁸ (corresponding PSD, not shown, revealing 3 categories of pores at circa 6.6, 4.4 and a narrow one at 3.4 nm). On the other hand, the condensation steps for impregnated Ni_{5%}SBA-15(imp) and Ni_{5%}Al₂O₃(imp) samples (curves (d,c) Figs. 3(C,D), respectively) shifted to lower P/P_0 values along with a decrease in pore volumes and pore diameters compared to their respective SBA-15 and Al₂O₃(meso) supports (Table 3). This behaviour is typical of partial plugging and of a restricted access to mesopores, supporting the presence, after impregnation then calcination treatments, of oxide nanoparticles inside the pores. Nevertheless, Al₂O₃(meso) presented a higher structural sensibility to post-impregnation than SBA-15: it indeed suffered from almost 32 and 19% losses of porous volume and average pore diameter, respectively, compared to only 17 and 7% for SBA-15 (Table 3). Thus, in agreement with SAXS observations, a potential damage was encountered upon impregnation in the case of ordered alumina whereas the SBA-15 maintained a perfectly structured porous system.

With respect to CeliteS, Ni_{5%}CeliteS(imp) (curves (a,b), Fig. 3A) and Ni_{5%}Al₂O₃(np) (curve b, Fig. 3B) materials, all displayed an increase in adsorbed N₂ only at high relative pressures (P/P_0 0.7-0.95), typical of non-ordered macroporous systems with insignificant pore volumes and wide PSD. The signal became

below the limit of detection (BET surface are <10m².g⁻¹) after reduction (Table 3, related inset figures).

Compared to their calcined forms, all reduced Ni_{5%}SBA-15(imp), Ni_{5%}Al₂O₃(meso) and Ni_{5%}Al₂O₃(imp) exhibited smaller specific surface areas and pore volumes (Table 3), mainly attributable to thermal contraction and/or condensation by dehydration and dehydroxylation during high temperature (800°C) treatment of either silica or alumina frameworks.²⁹ In addition to structural transitions, easily detectable for alumina based-samples (wide-angle X-ray diffraction, see section 3.4), particles migration to the external surface and/or agglomeration with consecutive pores plugging could be another a reason for such porosity loss.

Furthermore, in line with partial shrinkage of the alumina skeleton, an increase and a widening in the average pore diameter (6.8 to 7.7 nm) were observed for reduced Ni_{5%}Al₂O₃(imp) (Table 3). Nevertheless, such shrinkage was not observed for “one-pot” Ni_{5%}Al₂O₃(meso) which PSD remained narrow, as for Ni_{5%}SBA-15(imp), both being in the same range as for their calcined versions, (inset curves (b',c'), Figs. 3(C,D), respectively). The quite well (even if partially) preserved uniform structure of reduced Ni_{5%}Al₂O₃(imp), verified as well by SAXS, emphasizes the potential application of this mesoporous catalysts in the high temperature reforming reaction.

3.4 Structure, size and location of supported nanoparticles

Structural information on the deposited metal species in calcined, reduced and spent catalysts was gained from wide-angle X-ray diffraction. The patterns are presented in Figs. 4 and 5 for SiO₂ and Al₂O₃-based samples, respectively. Accordingly, the estimated particle sizes of the Ni species at the various successive stages of samples preparation are listed in Table 4.

Catalysts	Calcined		Reduced		Spent	
	Ø NiO (nm)		Ø Ni ⁰ (nm)		Ø Ni ⁰ / Ø NiO (nm)	
	XRD	XRD [#]	TEM	XRD [#]	TEM	
SiO ₂ -based catalysts						
Ni _{5%} CeliteS(imp)	7	22	23	n.d.*	36	
Ni _{5%} SBA-15(imp)	9	11	11	n.d.*	18	
Al ₂ O ₃ -based catalysts						
Ni _{5%} Al ₂ O ₃ (np)	14	22	25	48	50	
Ni _{5%} Al ₂ O ₃ (imp)	n.d.	10	9.5	18	19	
Ni _{5%} Al ₂ O ₃ (meso)	n.d.	n.d.	3.0	n.d.	5.5	

Calculated using Scherrer's equation at 2θ= 51.8°, [200] indexed plane
n.d.: not determined, n.d.*: not determined due to overlapping between Ni⁰ and NiO peaks, both present on spent samples.

The silica supports (patterns (a,c), Fig. 4A) with amorphous SiO₂ walls gave a broad signal centered at about 22°, with additional peaks of crystallized silica cristobalite (ICDD file # 85-0462) in the case of natural diatomite. The additional peaks visible for reduced Ni_{5%}SBA-15(imp) and Ni_{5%}CeliteS(imp) (patterns (b,d), Fig. 4B) are all characteristics of metallic Ni⁰ with face centered cubic (FCC) unit cell (ICDD file # 65-0380). The globally higher peak intensity along with smaller broadening for the Ni diatomite sample reveals the formation

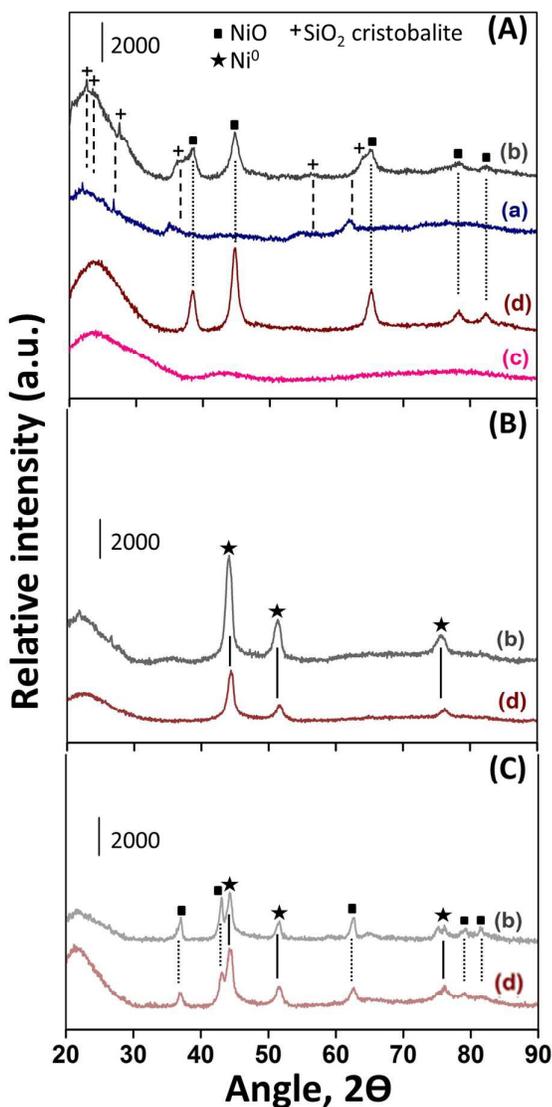


Fig. 4 Wide-angle XRD patterns of (A) calcined, (B) reduced and (C) spent samples: (a) CeliteS, (b) Ni_{5%}CeliteS(imp), (c) SBA-15 and (d) Ni_{5%}SBA-15. An offset was applied along Y-axis for the sake of clarity.

of significantly larger Ni⁰ nanoparticles on the macroporous compared to mesoporous silica support (Table 4). This is confirmed as well by TEM images showing evidence of big particles in reduced Ni_{5%}CeliteS(imp), assembled heterogeneously on the external surface of the macroporous spherules (pores with average openings around 100 nm, Fig. 6A), while the Ni species appear smaller and better dispersed in reduced Ni_{5%}SBA-15(imp) (occluded in the ordered channels, Fig. 6B, Table 4) even if few large Ni species are also present on the outside of the silica grains (black dots on the external surface). Such distribution between internal and external nanoparticles suggests that some species might have migrated from the channels to the surface during calcination and/or have sintered during harsh reduction treatments.³⁰

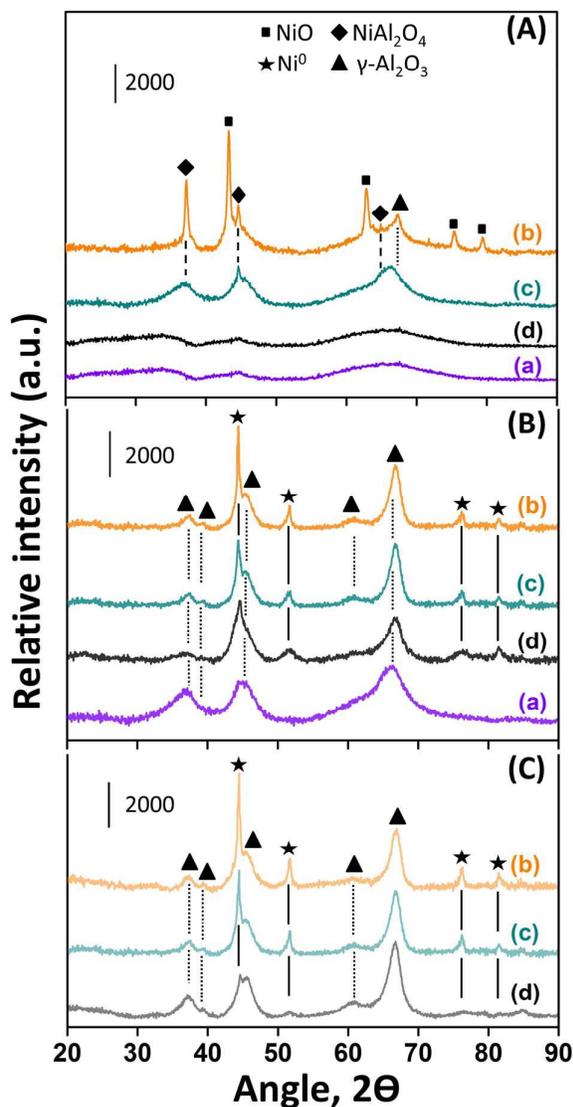


Fig. 5 Wide-angle XRD patterns of (A) calcined, (B) reduced and (C) spent samples: (a) Al₂O₃(meso), (b) Ni_{5%}Al₂O₃(np), (c) Ni_{5%}Al₂O₃(imp) and (d) Ni_{5%}Al₂O₃(meso). An offset was applied along Y-axis for the sake of clarity.

The relatively enhanced dispersion over SBA-15 was verified as well by local EDS analysis performed over several grains for a given sample. Indeed, the local atomic Ni/Si ratios in Ni containing zones were quite heterogeneous (between 0.03 and 0.06) in Ni_{5%}CeliteS(imp) compared to rather homogeneous (in the range of 0.07-0.09) in Ni_{5%}SBA-15(imp); note that the lower values on the macroporous diatomite supported sample fully agree with the presence of very big isolated non-supported external Ni particles (observable by SEM analysis),²¹ not counted during such EDS analysis of individual diatomite grains. Accordingly, the initial higher catalytic reactivity of Ni_{5%}SBA-15(imp) compared to Ni_{5%}CeliteS(imp) (Fig. 2) could be directly associated to the smaller and easily accessible metallic centers preserved within

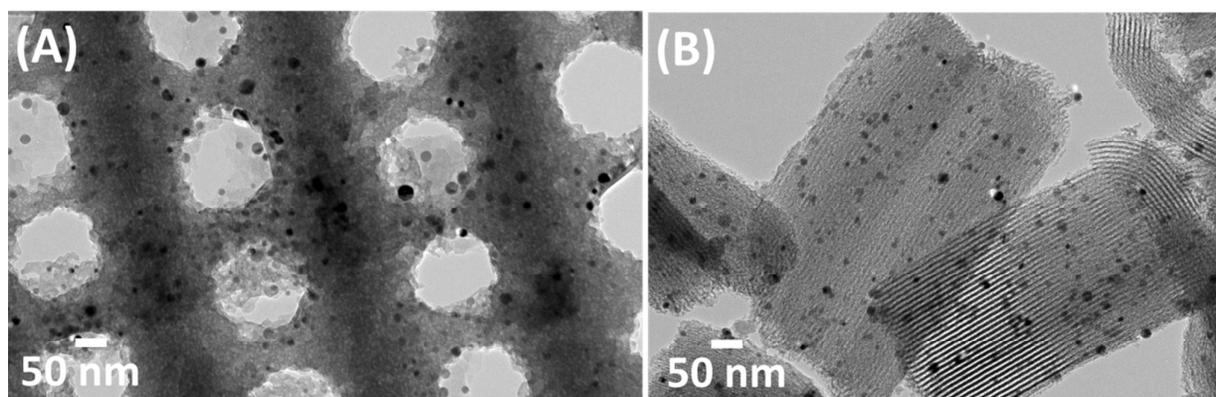


Fig. 6 Representative TEM micrographs of the *in-situ* reduced (800°C/3h) catalysts: (A) Ni_{5%}CeliteS(imp) and (B) Ni_{5%}SBA-15(imp)

the pores of structured SBA-15 compared to the sintered-ones over macroporous CeliteS.

Concerning the alumina based-materials, the synthesis method was demonstrated to have a crucial influence on the textural properties (as observed by SAXS and N₂-sorption) and this also stands regarding the dispersion and location of the Ni species. It is of special interest to note the absence of NiO diffraction peaks for “one-pot” prepared Ni_{5%}Al₂O₃(meso) (pattern d, Fig. 5A), attesting a very high Ni-species dispersion within the mesoporous alumina framework. The diffraction pattern was in fact quite similar to that of (Ni free) Al₂O₃(meso) (pattern a,

Fig. 5A), showing only weak signals coming from the amorphous walls of the ordered mesoporous alumina. For both Ni-free and Ni-containing one-pot mesoporous materials, a phase transition to crystalline Al₂O₃ γ-phase (ICDD file # 10-0425) was observed after reduction at 800°C (patterns (a,d), Fig. 5B) along with the appearance, for reduced Ni_{5%}Al₂O₃(meso), of tiny and broad Ni⁰ diffraction peaks (indexed as □ on the pattern) indicating some sintering, although very limited, and thus an effective stabilization of the Ni species.

Consistently, the preserved dispersion was confirmed by TEM/EDS

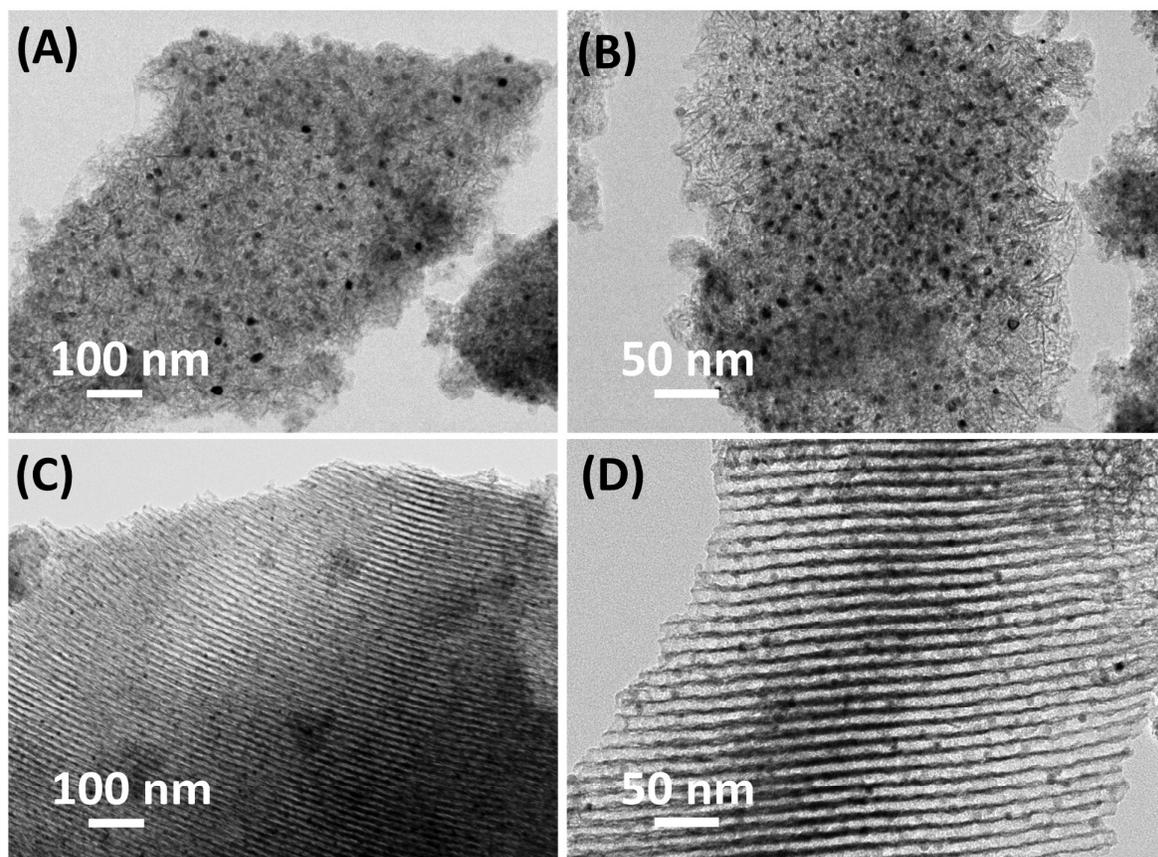


Fig. 7 Representative TEM micrographs of the *in-situ* reduced (800°C/3h) catalysts: (A,B) Ni_{5%}Al₂O₃(imp) and (C,D) Ni_{5%}Al₂O₃(meso).

observations (Figs. 7C,D) that revealed an average Ni^0 particle size of approximately 3 nm (Table 4) and Ni/Al atomic ratios around 0.09 over all of the considered grains zones. All of the population of nanoparticles (appearing as very small dark spots on the grey alumina matrix) was visibly homogeneously located inside the regular hexagonal arrangement of the porous structure (Figs. 7C,D). On the contrary, $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{np})$ (calcined form) displayed intense $\gamma\text{-Al}_2\text{O}_3$ peaks together with peaks of spinel Ni-aluminate phase (pattern (b), Fig. 5A) as well as apparent and measurable (Table 4) NiO diffraction peaks (FCC, ICDD file # 089-7130), consistent with the poor Ni dispersion expected on such non-porous support. A spinel phase was also detected, although to a much lower extent, in impregnated $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ (pattern b, Fig. 5A) where neither NiO nor alumina X-ray diffraction peaks were found, illustrating again the easier metal dispersion on a mesoporous support. It is worth adding that the spinel Ni-aluminate phase was not detected for mesoporous "one-pot" $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$ (pattern (d), Fig. 5A) although high TPR reduction temperatures (pattern (e), Fig. 1B) revealed predominant presence of Ni-O-Al species in this sample. This suggests a highly dispersed (or amorphous) state of such species in the walls of the mesoporous $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$ network. Upon heating $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{np})$ and $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ in H_2 at 800°C , both types of nickel species (either free or present in spinel structures) were reduced to Ni^0 (pattern (b,c), Fig. 5B), the obtained metallic nanoparticles being still smaller over the impregnated sample compared to the non-porous one (Table 4). In line with SAXS and N_2 -sorption, TEM images of reduced $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ (Figs. 7A,B) exhibited "sponge-like" (Fig. 7A) and in some regions "worm-like" appearances (Fig. 7B), with no evidence of pore arrangements within the structure. Such shape contrasts with the initial organized mesoporous network of the used $\text{Al}_2\text{O}_3(\text{meso})$ support and reveals a partial structural damage during preparations steps (even when performed carefully), in line with above-mentioned drastic decrease of mean pores size (Table 3). Such type of damage, already reported for potassium-modified mesoporous alumina preparations,³¹ may result from a rather high sensitivity of the ordered alumina network (higher than for ordered silica) to the treatments carried out during preparation, namely impregnation (involving aqueous solution) and subsequent thermal oxidative treatment (removal by decomposition of the

nitrate from the initial Ni precursor). In the structurally partially damaged $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ sample, the metallic nanoparticles appear randomly deposited (Ni/Al atomic ratios between 0.01-0.2) on the external surface (spherical dots, Figs. 7A,B), with an average particle size around 9 nm (calculated from both XRD and TEM). This value is three times higher than the 3 nm mentioned above for homogeneously dispersed Ni^0 in "one-pot" $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$, accentuating on the effectiveness of the "one-pot" synthesis approach compared to conventional impregnation.

From all above discussed data, it can be seen that the order of conversions on alumina-based catalysts ($\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso}) > \text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp}) > \text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{np})$, Fig. 2) follows the same order as that of Ni^0 dispersion (i.e. opposite to particle sizes order, Table 4). Even if expected, this observation strongly emphasizes the importance of ensuring high Ni dispersion through appropriate conditions of sample preparation and catalytic testing. Moreover, not only the conversions levels but also the selectivity varies with Ni dispersion: thus, all catalysts with poorly dispersed Ni ($\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{np})$ and $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$) lead to H_2/CO ratios above 2 at initial reaction stages (followed by a decrease down to 1 for the non-porous sample), whereas $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$ with enhanced Ni dispersion yields the expected product ratio value of 2. These observations demonstrate the occurrence of side-reactions on the poorly dispersed catalysts, such as steam and dry reforming (that both take place at high temperature), SRM occurring probably preferentially compared to DRM in view of the easier activation of H_2O and CH_4 compared to that of inert CO_2 ^{15(b,e)}. In contrast, combined methane reforming (the targeted reaction) takes place continuously on the highly dispersed, stable and selective mesoporous $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$ catalyst.

3.5 Deactivation analysis of the SiO_2 and Al_2O_3 -based catalysts

Herein, the reacted (40h spent) catalysts were characterized by XRD, TEM and thermogravimetry to check further the deactivation causes.

The wide-angle XRD patterns showed the presence of both Ni^0 (active phase) and NiO crystalline phases on the silica-based catalysts (Fig. 4C), revealing partial nickel *in-situ* reoxidation during CSDRM on both silica supports. For $\text{Ni}_{5\%}\text{CeliteS}$, this is in

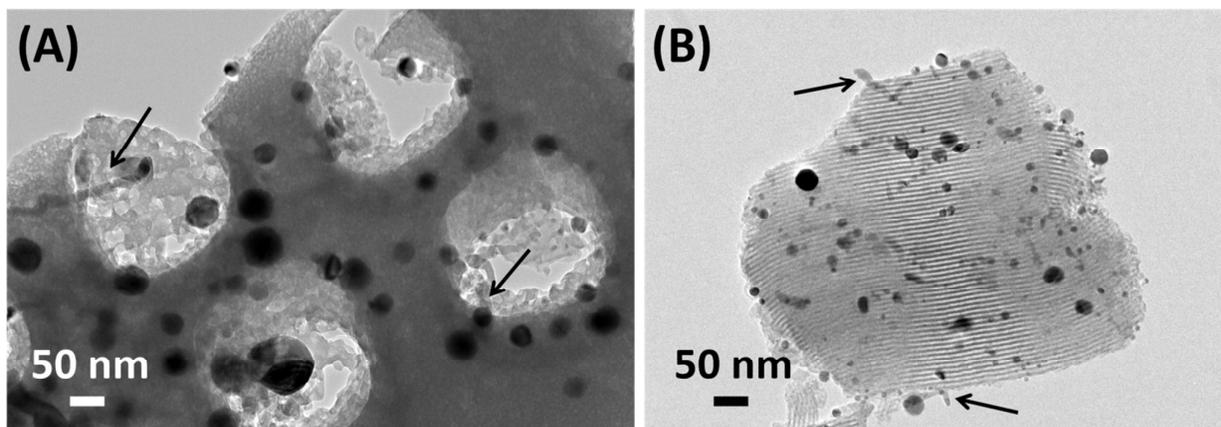


Fig. 8 Representative TEM micrographs of the spent ($800^\circ\text{C}/20\text{h}$, $\text{CH}_4/\text{CO}_2/\text{H}_2\text{O} = 1/0.4/0.8/12$) catalysts: (A) $\text{Ni}_{5\%}\text{CeliteS}(\text{imp})$ and (B) $\text{Ni}_{5\%}\text{SBA-15}(\text{imp})$. Carbon is marked with arrows.

accordance with our recent DRM studies on Ni/diatoms carried out at 650°C.²¹ Actually, these previous materials presented high sensibility to steam and were deactivated via reoxidation of Ni⁰ to NiO by water generated from the RWGS side-reaction. Such nickel reoxidation occurred also on Ni_{5%}SBA-15(imp) during CSDRM, even though it was absent on similar Ni/SBA-15 after DRM reaction.^{18(a,b)} Such partial reoxidation on both silica-based catalysts having distinct Ni dispersion shows that reoxidation is not size dependent (Table 4). Very interestingly, and contrarily to spent silica catalysts, alumina-based ones presented solely Ni⁰ X-ray diffraction signatures (Fig. 5C) indicating full preservation of the reduced nickel state after reaction. For both families of catalysts, no peaks corresponding to carbonaceous deposits were found, indicating either their presence in low amount (below detection limit) and/or their amorphous type.³²

Typical TEM images of spent Ni_{5%}CeliteS(imp) (Fig. 8A) revealed extremely large Ni nanoparticles (difficult to distinguish whether Ni⁰ or NiO), in accordance with the thin XRD peaks (pattern (b), Fig. 4C), and some carbon deposition (mainly in the form of short nanotubes with big metallic Ni⁰ tips, see arrows in Fig. 8A). In the case of Ni_{5%}SBA-15(imp) (Fig. 8B), the hexagonal array of SBA-15 silica was still clearly visible and partially filled by nanoparticles, but agglomerated Ni species were also found on the external surface along with few very short nanotubes (arrows, Fig. 8B). Deactivation was therefore mainly associated with partial reoxidation (XRD data) and sintering (Table 4) rather than with coking.

Ni deactivation by reoxidation on silica supports, under similar reaction conditions in steam and at high temperature, was recently observed by Nieva et al.^{33a} in parallel to much resistant Ni on Al₂O₃, MgAl₂O₄ or ZnAl₂O₄. Likewise, Matsumura et al.^{33b} found that Ni on Al₂O₃ and ZrO₂ catalysts were deactivated by carbon deposition without reoxidation whereas reoxidation occurred over silica-based catalyst. Moreover, deactivation was reported on core-shell Ni/SiO₂ catalysts.^{33c} Also, partial nickel reoxidation of Ni/SBA-15 during SRM was deduced from XRD patterns of spent catalysts.^{33(d,e)} In CSDRM, one study (Table 1) dealing with Ni/SBA-15 is accessible, reporting

deactivation by reoxidation, as well.¹¹

The origin of the Ni⁰ reoxidation on silica-based materials and not on alumina ones is not clearly addressed yet. We tentatively associate it to the distinct chemical properties of the used supports. A first reason most probably relies on the distinct acidic and/or basic features of these two oxides, alumina presenting both basic and acidic behaviours whereas silica is predominantly acidic. Another explanation could be the higher propensity of the alumina surface (compared to silica) to be hydroxylated and / hydrated upon contact with water (present in CSDRM as reactant and as possible side-reaction product),³⁴ steam being therefore less available for oxidizing the metallic Ni nanoparticles as occurs on silica.^{33b} To increase the reactivity of silica, we have tried, but without success, to include a hydrothermal treatment session³⁵ during the SBA-15 synthesis (detailed in experimental section). Continuous work is in progress to clarify these points.

Concerning the "one-pot" Ni_{5%}Al₂O₃(meso) (best) catalyst, its high and stable performances are explained not only by the preservation of its Ni⁰ reduced state along reaction (as already stated above) but also by its excellent Ni dispersion also maintained after 40h of testing. Indeed, the intensities of the Ni⁰ diffraction peaks of spent Ni_{5%}Al₂O₃(meso) (pattern d, Fig. 5C) are similar to those before test (reduced catalyst (pattern d, Fig. 5B), except for a small contribution at 44.5°, signifying that the agglomeration of Ni nanoparticles was effectively avoided at a degree. As shown on a representative micrograph of spent Ni_{5%}Al₂O₃(meso) (Fig. 9E), the Ni metallic nanoparticles remained very small (5.5 nm), emphasizing the essential role of the initial nickel insertion within the ordered oxide framework ("one-pot" synthesis) towards avoiding metal nanoparticles growth during run. Such a confinement was furthermore confirmed by TEM images (Fig. 9F) showing Ni species as small as before run (Table 4), and by the corresponding Ni/Al atomic ratio 0.09-0.1. It seems therefore reasonable to correlate the stable performances of the mesoporous "one-pot" catalyst to the dominant initial presence of spinel nickel-aluminate phases exhibiting high MSI (as detected by TPR): these species lead, after reduction, to strongly anchored reduced Ni-species that are stabilized within the ordered Al₂O₃, having strong resistance against sintering (and against reoxidation) even in presence of steam at

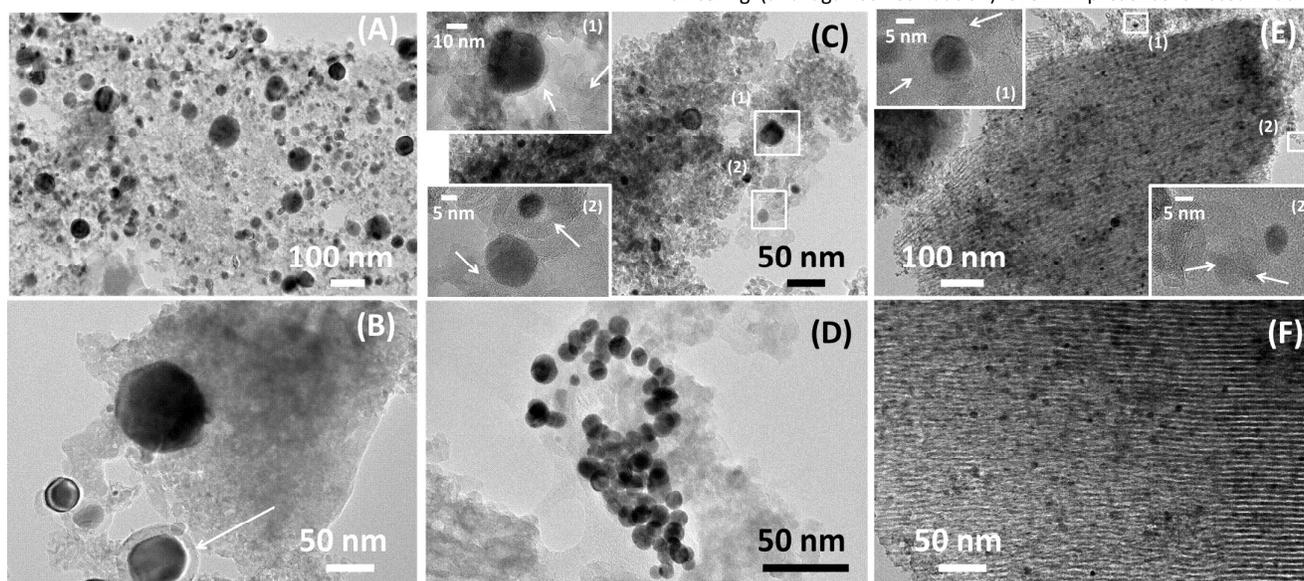


Fig. 9 Representative TEM micrographs of the spent (800°C/40h, CH₄/CO₂/H₂O = 1/0.4/0.8/12) catalysts: (A,B) Ni_{5%}Al₂O₃(np), (C,D) Ni_{5%}Al₂O₃(imp) and (E,F) Ni_{5%}Al₂O₃(meso) catalysts. Carbon is marked with arrows.

800°C. A similar positive effect was recently found in DRM over a catalyst containing solely mixed phases of Ni in Al_2O_3 .³⁶


Finally, for spent $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$, the partial collapse of its alumina mesostructure already present during preparation and reduction continued, and was even accentuated under the severe CSDRM testing conditions, causing further agglomeration of the already large Ni^0 nanoparticles (very thin and intense peaks in pattern c, Fig. 5C; mean size values in Table 4). The nickel active phase is then no longer confined in a porous structure (Fig. 9C) and metal dispersion becomes highly heterogeneous (Ni/Al atomic ratios between 0.01 and 0.5), with some zones enriched in agglomerates of Ni nanoparticles co-present whereas others appear Ni free (Fig. 9D). The situation was even worse with the "one-pot" non-porous catalyst that displayed the strongest Ni-metallic diffraction peaks after reaction (pattern b, Fig. 5C) and the highest degree of sintering with an average metallic particle sizes as big as 48-50 nm (as obtained from both XRD and TEM, Table 4). Similarly to the impregnated sample, very large as well as small species were visible on the external surface (Figs. 9 (A,B)), without any evidence of regular arrangement between them.

Finally, TGA/DTA/MS analyses of spent catalysts were carried out (data not detailed) to confirm the low coke contents suggested by all TEM pictures of spent samples (coke deposits rarely observed). They revealed a $C_{(s)}$ wt% loss decreasing in the following order: (6%) $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso}) \sim (5\%) \text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp}) > (0.5\%) \text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{np})$. Their matching DTA profiles, particularly those of "one-pot" $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$ and $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ spent catalysts, showed a main exothermic peak at about 600°C, attributed to the oxidation of graphitic carbon.³⁷ The absence of any corresponding XRD diffraction peak was in line with the low contents of $C_{(s)}$ measured over all spent materials. However, it is worth noting that carbon formation was totally hindered inside the Al_2O_3 pores of the "one-pot" $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$ (Figs. 9 (E,F)) due to steric constraints and stabilization of small Ni^0 nanoparticles within the porous network during reaction. The very few particles that contributed in carbon formation appeared drift away from the support once the carbon nucleus was formed (insets in Fig. 9E). In the case of spent $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ and $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{np})$, some agglomerated Ni^0 species were seen completely encapsulated by multi-walled nano-onion carbon (insets in Fig. 9C and arrow on Fig. 9B), being no longer accessible to reactants.³⁶ The lowest amount of $C_{(s)}$ -deposits measured over the most deactivated sample (non-porous catalyst) is in line with its very poor activity.

4. Conclusion

A series of monometallic 5 wt% Ni and porous or non-porous silica or alumina based-catalysts were successfully prepared and their reactivity was investigated in the combined methane reforming reaction at 800°C. Reoxidation of the Ni^0 active phase leading to deactivation was observed during reaction for silica based catalysts while the metallic nickel state was preserved in all alumina-based ones, even after 40h under stream. Mesoporous "one-pot" $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$ compared to non-porous "one-pot" $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{np})$ (both synthesized by EISA technique) showed significantly enhanced Ni-alumina interaction as well as much smaller and well-confined Ni nanoparticles. This leads to a strongly improved sintering-resistance

and to an excellent catalytic stability with CSDRM performances still close to the thermodynamic ones after 40h on stream. The influence of the synthesis method was also considered by preparing a conventional impregnated Ni on mesoporous alumina catalyst $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ that was found much less efficient. For clarification, Scheme 1 summarizes the main differences, in terms of state of the active phase, characterizing the alumina-based catalysts obtained by either "one-pot" synthesis approach or by traditional impregnation method. The metallic nickel nanoparticles are present both inside and outside the porous structure after post-impregnation whereas the "one-pot" technique favors a highly homogenous dispersion within the alumina matrix and consequently much smaller Ni^0 nanoparticles with strengthened interaction with the support. The weakly attached Ni species (present mainly in the impregnated $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ catalyst) tend to sinter during both activation and reaction, resulting in agglomerated species which accelerate the rate of deactivation. The ordered "one-pot" mesoporous $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$, synthesized by a simple one step method, appears as a very promising catalyst for combined methane reforming reaction.

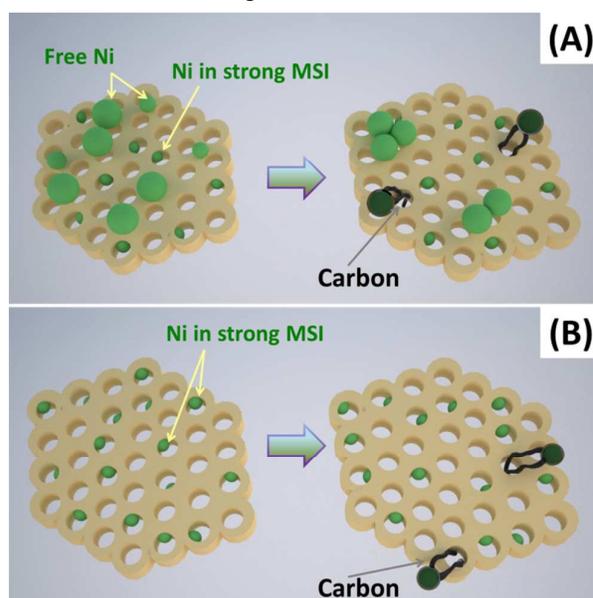

Scheme. 1 A graphical representation of: (A) impregnated $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{imp})$ and (B) "one-pot" $\text{Ni}_{5\%}\text{Al}_2\text{O}_3(\text{meso})$ catalysts before (left) and after (right) the combined steam and dry reforming reaction.

Acknowledgements

The "Agence Universitaire de la Francophonie" and the Research Council of the University of Balamand are strongly acknowledged for partial K. Jabbour PhD funding (AUF fellowship and UOB 01/2013 BIRG, respectively). The authors are also sincerely grateful to the French-Lebanese CEDRE Hubert Curien program (PHC) for financial support to mobility (project number 30962ZH, 2014-2015).

References

- a) G. A. Olah, G. S. Prakash, A. Goeppert, M. Czaun, T. Mathew, *J. Am. Chem. Soc.*, 2013, **135**, 10030; b) G. A. Olah, A. Goeppert, M. Czaun, T. Mathew, R. B. May, G. S. Prakash, *J. Am. Chem. Soc.*, 2015, **137**, 8720; c) G. A. Olah, A. Goeppert, M. Czaun, G. S. Prakash, *J. Am. Chem. Soc.*, 2013, **135**, 648.
- W. Wang, S. Wang, X. Ma, J. Gong, *Chem. Soc. Rev.*, 2011, **40**, 3703.
- a) F. Pompeo, N. N. Nichio, M. M. V. M. Souza, D. V. Cesar, O. A. Ferretti, M. Schmal, *Appl. Catal. A*, 2007, **316**, 175; b) M. C. J. Bradford, M. A. Vannice, *Catal. Rev. Sci. Eng.*, 1999, **41**, 1.
- T. V. Choudhary, V. R. Choudhary, *Angew. Chem.*, 2008, **47**, 1828.
- a) H. S. Roh, K. Y. Koo, J. H. Jeong, Y. T. Seo, D. J. Seo, Y. S. Seo, W. L. Yoon, S. B. Park, *Catal. Lett.*, 2007, **117**, 85; b) D. Qin, J. Lapszewicz, *Catal. Today*, 1994, **21**, 551; c) D. Qin, J. Lapszewicz, X. Jiang, *J. Catalysis*, 1996, **159**, 140; d) V. R. Choudhary, K. C. Mondal, *Appl. Energy*, 2006, **83**, 1024; e) V. R. Choudhary, A. M. Rajput, *Ind. Eng. Chem. Res.*, 1996, **35**, 3934; f) V. R. Choudhary, B. S. Uphade, A. S. Mamman, *Appl. Catal. A*, 1998, **168**, 33; g) J. B. Claridge, A. P. York, A. J. Brungs, *J. Catal.*, 1998, **180**, 85.
- F. Yagi, A. Nagumo, Y. Wada, M. Shimura, US Pat. 6,387,843B1.
- a) S. S. Itkulova, G. D. Zakumbaeva, Y. Y. Nurmakanov, A. A. Mukazhanova, A. K. Yermaganbetova, *Catal. Today*, 2014, **228**, 194; b) H. S. Roh, K. Y. Koo, U. D. Joshi, W. L. Yoon, *Catal. Lett.*, 2008, **125**, 283; c) K. Y. Koo, H. S. Roh, Y. T. Seo, D. J. Seo, W. L. Yoon, S. B. Park, *Appl. Catal. A*, 2008, **340**, 183; d) K. Y. Koo, H. S. Roh, U. H. Jung, W. L. Yoon, *Catal. Today*, 2012, **185**, 126; e) I. H. Son, S. J. Lee, A. Soon, H. S. Roh, H. Lee, *Appl. Catal. B*, 2013, **134**, 103; f) M. García-Diéguez, I. S. Pieta, M. C. Herrera, M. A. Larrubia, L. J. Alemany, *Catal. Today*, 2011, **172**, 136; g) J. Mehz, K. J. Jozani, A. N. Pour, Y. Zamani, *React. Kinet. Catal. Lett.*, 2002, **75**, 267; h) K. M. Kang, I. W. Shim, H. Y. Kwak, *Fuel. Process. Technol.*, 2012, **93**, 105.
- a) G. A. Olah, G. K. S. Prakash, US Pat. 7,906,559; b) G. A. Olah, G. K. S. Prakash, US Pat. 8,133,926; c) G. A. Olah, G. K. S. Prakash, US Pat. 8,440,729; d) G. A. Olah, G. K. S. Prakash, US Pat. 8,697,759; e) G. A. Olah, G. K. S. Prakash, US Pat. 8,980,961; f) G. A. Olah, G. K. S. Prakash, European Pat. 2,167,451A1.
- a) K. Y. Koo, H. S. Roh, Y. T. Seo, D. J. Seo, W. L. Yoon, S. B. Park, *Int. J. Hydrogen Energy*, 2008, **33**, 2036-2043; b) K. Y. Koo, S. H. Lee, U. H. Jung, H. S. Roh, W. L. Yoon, *Fuel. Process. Technol.*, 2014, **119**, 151; c) K. Y. Koo, H. S. Roh, U. H. Jung, D. J. Seo, Y. S. Seo, W. L. Yoon, *Catal. Today*, 2009, **146**, 166; d) S. C. Baek, J. W. Bae, J. Y. Cheon, K. W. Jun, K. Y. Lee, *Catal. Lett.*, 2011, **141**, 224; e) J. W. Bae, A. R. Kim, S. C. Baek, K. W. Jun, *React. Kinet. Catal. Lett.*, 2011, **104**, 377; f) A. N. Pour, Y. Z. Kheirolah, J. Jozani, J. Y. Mehr, *React. Kinet. Catal. Lett.*, 2005, **86**, 157.
- H. S. Roh, K. Y. Koo, W. L. Yoon, *Catal. Today*, 2009, **146**, 71.
- B. Huang, X. Li, S. Ji, B. Lang, F. Habimana, C. Li, *J. Nat. Gas. Chem.*, 2008, **17**, 225.
- a) A. R. Kim, H. Y. Lee, D. H. Lee, B. W. Kim, C. H. Chung, D. J. Moon, E. J. Jang, C. Pang, J. W. Bae, *Energy Fuels*, 2015, **29**, 1055.
- M. M. Danilova, Z. A. Fedorova, V. A. Kuzmin, V. I. Zaikovskii, A. V. Porsin, T. A. Krieger, *Catal. Sci. Technol.*, 2015, **5**, 2761; b) M. M. Danilova, Z. A. Fedorova, V. I. Zaikovskii, A. V. Porsin, V. A. Kirillov, T. A. Krieger, *Appl. Catal. B*, 2014, **147**, 858.
- S. K. Ryi, S. W. Lee, J. W. Park, D. K. Oh, J. S. Park, S. S. Kim, *Catal. Today*, 2014, **236**, 49.
- a) M. A. Soria, C. Mateos-Pedrero, A. Guerrero-Ruiz, I. Rodríguez-Ramos, *Int. J. Hydrogen Energy*, 2011, **36**, 15212; b) Ş. Özkara-Aydinoğlu, *Int. J. Hydrogen Energy*, 2010, **35**, 12821; c) Y. Sun, T. Ritchie, S. S. Hla, S. McEvoy, W. Stein, J. H. Edwards, *J. Nat. Gas. Chem.*, 2011, **20**, 568; d) M. Jafarbegloo, A. Tarlani, A. W. Mesbah, S. Sahebdehfar, *Int. J. Hydrogen Energy*, 2015, **40**, 2445; e) B. A. Santos, J. M. Loureiro, A. M. Ribeiro, A. E. Rodrigues, A. F. Cunha, *Can. J. Chem. Eng.*, 2015, **93**, 510.
- S. Li, J. Gong, *Chem. Soc. Rev.*, 2014, **43**, 7245.
- a) J. Sehested, J. A. P. Gelten, I. N. Remediakis, H. Bengaard, J. K. Nørskov, *J. Catal.*, 2004, **223**, 432; b) J. Sehested, J. A. P. Gelten, S. Helveg, *Appl. Catal. A*, 2006, **309**, 237.
- a) M. N. Kaydouh, N. El. Hassan, A. Davidson, S. Casale, P. Massiani, *Micropor. Mesopor. Mat.*, 2015, **220**, 99; b) M. N. Kaydouh, N. El Hassan, A. Davidson, S. Casale, H. Zakhem, P. Massiani, *C. R. Chim.*, 2015, **18**, 293; c) N. Wang, Z. Xu, J. Deng, K. Shen, X. Yu, W. Qian, W. Chu, F. Wei, *ChemCatChem*, 2014, **6**, 1470; d) X. Fang, C. Peng, H. Peng, W. Liu, X. Xu, X. Wang, C. Li, W. Zhou, *ChemCatChem*, 2015, **7**, 3753; e) L. Xu, H. Sonf, L. Chou, *Catal. Sci. Technol.*, 2011, **1**, 1032.
- a) W. Shen, K. Komatsubara, T. Hagiwara, A. Yoshida, S. Naito, *Chem. Comm.*, 2009, **42**, 6490; b) K. Wang, X. Li, S. Ji, X. Shi, J. Tang, *Energy Fuels*, 2008, **23**, 25; c) H. Wan, X. Li, S. Ji, B. Huang, K. Wang, C. Li, *J. Nat. Gas. Chem.*, 2007, **16**, 139.
- a) S. M. Morris, P. F. Fulvio, M. Jaroniec, *J. Am. Chem. Soc.*, 2008, **130**, 15210; b) Q. Yuan, A. X. Yin, C. Luo, L. D. Sun, Y. W. Zhang, W. T. Duan, H. C. Liu, C. H. Yan, *J. Am. Chem. Soc.*, 2008, **130**, 3465.
- a) K. Jabbour, K., N. El Hassan, A. Davidson, P. Massiani, S. Casale, *Chem. Eng. J.*, 2015, **264**, 351.
- a) M. Imperor-Clerc, D. Bazin, M. Appay, P. Beaunier, A. Davidson, *Chem. Mater.*, 2004, **16**, 1813; b) I. Lopes, N. El Hassan, H. Guerba, G. Wallez, A. Davidson, *Chem. Mater.*, 2006, **18**, 5826; c) J. Van der Meer, I. Bardez-Giboire, C. Mercier, B. Revel, A. Davidson, R. J. Denoyel, *J. Phys. Chem. C*, 2010, **114**, 3507.
- a) D. Zhao, J. Feng, Q. Huo, N. Melosh, G. H. Fredrickson, B. F. Chmelka, G. D. Stucky, *Science* 1998, **279**, 548; b) A. Sayari, A. Sayari, B. H. Han, Y. Yang, *J. Am. Chem. Soc.*, 2004, **126**, 14348.
- T. Xie, L. Shi, J. Zhang, D. Zhang, *Chem. Comm.*, 2014, **50**, 7250.
- J. A. C. Dias, J. M. Assaf, *Catal. Today*, 2003, **85**, 59.
- a) A. Zhao, W. Ying, H. Zhang, H. Ma, D. Fang, *Catal. Commun.*, 2012, **17**, 34; b) X. Zou, X. Wang, L. Li, K. Shen, X. Lu, W. Ding, *Int. J. Hydrogen energy*, 2010, **35**, 12191; c) J. Zhang, H. Xu, X. Jin, Q. Ge, W. Li, *Appl. Catal. A*, 2005, **290**, 87.
- a) P. V. D. Voort, M. Benjelloun, E. F. Vansant, *J. Phys. Chem. B*, 2003, **106**, 9027; b) J. Seo, M. Youn, D. Park, J. Jung, I. Song, *Catal. Lett.*, 2009, **132**, 395.
- A. Grosman, C. Ortega, *Langmuir*, 2008, **24**, 3977.
- a) S. A. Bagshaw, I. J. Bruce, *Micropor. Mesopor. Mat.*, 2008, **109**, 199; b) S. Y. Chen, C. Y. Tang, J. F. Lee, L. Y. Jang, T. Tatsumi, S. Cheng, *S. J. Mater. Chem.*, 2011, **21**, 2255.
- D. Kantorovich, L. Haviv, L. Vradman, M. V. Landau, *Stud. Surf. Sci. Catal.*, 2005, **156**, 147.
- L. B. Sun, J. Yang, J. H. Kou, F. N. Gu, Y. Chun, Y. Wang, J. H. Zhu, Z. G. Zou, *Angew. Chem. Int. Ed.*, 2008, **47**, 3418.
- a) J. Z. Luo, Z. L. Yu, C. F. Ng, C. T. Au, *J. Catal.* 2000, **194**, 198; b) B. Kitiyanan, W. E. Alvarez, J. H. Harwell, D. E. Resasco, *Chem. Phys. Lett.*, 2000, **317**, 497.
- a) M. A. Nieva, M. M. Villaverde, A. Monzón, T. F. Garetto, A. J. Marchi, *Chem. Eng. J.*, 2014, **235**, 158; b) Y. Matsumura, T.

- Nakamori, *Appl. Catal. A*, 2004, **258**, 107; c) J. Majewski, J. Wood, W. Bujalski, *Int. J. Hydrogen Energy*, 2013, **38**, 14531; d) H. Wan, X. Li, S. Ji, B. Huang, K. Wang, C. Li, *J. Nat. Gas. Chem.*, 2007, **16**, 139; e) K. Wang, X. Li, S. Ji, X. Shi, J. Tang, *Energy Fuels*, 2008, **23**, 25; f) R. Takahashi, S. Sato, T. Sodesawa, M. Yoshida, S. Tomiyama, *Appl. Catal. A*, 2004, **273**, 211.
- 34 a) Z. Liu, Y. Wang, J. Li, R. Zhang, *RSC Advances*, 2014, **26**, 225; b) L. Garcia, R. French, S. Czernik, E. Chornet, *Appl. Catal. A*, 2000, **201**, 225.
- 35 F. Zhang, Y. Yan, H. Yang, Y. Yan, C. Yu, B. Tu, D. Zhao, *J. Phys. Chem. B*, 2005, **109**, 8723.
- 36 L. Zhou, L. Li, N. Wei, J. Li, J. M. Basset, *ChemCatChem*, 2015, **16**, 2508.
- 37 X.-Y. Quek, D. Liu, W. N. E. Cheo, H. Wang, Y. Chen, Y. Yang, *Appl. Catal. B*, 2010, **95**, 374.

