

Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/dalton



Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Mechanochemically Synthesized Fluorides: Local Structures and Ion Transport

Florian Preishuber-Pflügl^b and Martin Wilkening^a

The performance of new sensors or advanced electrochemical energy storage devices strongly depends on the active materials chosen to realize such systems. In particular, their morphology may greatly influence overall macroscopic properties. Many times, however, current limitations in classical ways of chemical preparation routes hamper the development of materials with tailored properties. Fortunately, such hurdles can be overcome by mechanochemical synthesis. The versatility of mechanochemical synthesis allows the provision of compounds that are not available through common synthesis routes. Mechanical treatment of two or three starting materials in high-energy ball mills enables the synthesis not only of new compounds but also of nanocrystalline materials with unusual properties such as enhanced ion dynamics. Fast ion transport is of crucial importance in electrochemical energy storage. Worth noting, mechanochemical synthesis also provides access to metastable phases that cannot be synthesized by conventional solid state synthesis. Ceramic synthesis routes often yield the thermally, *i.e.*, thermodynamically, stable products rather than metastable compounds. In this perspective we report about mechanochemical synthesis of nanocrystalline fluoride ion conductors that serve as model substances to understand the relationship between local structures and ion dynamics. While ion transport properties were complementarily probed via conductivity spectroscopy and nuclear magnetic relaxation, local structures of the phases prepared were investigated by high-resolution ¹⁹F NMR spectroscopy carried out at fast magic angle spinning. The combination of nuclear and non-nuclear techniques also helped us to shed light on the mechanisms controlling mechanochemical reactions in general.

Introduction

A chemical reaction which is induced by the absorption of mechanical energy is called a *mechanochemical* reaction. It constitutes its own class of chemical synthesis routes. Chemical reactions are usually driven by other sources of energy such as heat, light or by the difference in electrochemical potentials of the materials involved, *i.e.*, through electric energy.

Mechanochemistry offers access to nanocrystalline compounds and metastable phases that are often characterized by non-equilibrium structures. In many cases these materials cannot be obtained through conventional approaches such as solid state synthesis which require high sintering temperatures, for example. Compared to other preparation routes, mechanochemical synthesis, *e.g.*, when carried out in high-energy planetary mills, represents a highly versatile way of preparation that benefits

from its facile realization and so-called one-pot conditions. This advantages as well as the possibility to synthesize materials with yet inaccessible properties led to a rapid increase of applications of mechanochemical techniques. In particular, this growing interest is highlighted by the increasing number of publications reporting on mechanochemical reactions as well as by several comprehensive reviews that appeared over the last couple of years.¹⁻³ While recent reviews focused on, *e.g.*, the synthesis of non-equilibrium oxides, the present one puts emphasis on the preparation of inorganic, nanocrystalline fluorides, *i.e.*, ternary and quaternary ionic conductors, in particular. Here, we focus on the direct synthesis of complex fluorides by milling binary fluorides under dry conditions in high-energy ball mills.

Besides the effect of nanostructuring, the impact of mechanical stress yields materials with a high concentration of defects and a large volume fraction of so-called interfacial regions anticipated to be structurally disordered. In the case of Li⁺ and F⁻ ionic conductors defects are necessary to facilitate both self-diffusion and long-range ion transport. From an application point of view, fast ion conductors are urgently needed to develop powerful electrochemical sensors or energy storage devices that may also take advantage of fluoride as the main ionic

^a Institute for Chemistry and Technology of Materials, DFG-SPP 1415, Graz University of Technology (NAWI Graz), Stremayrgasse 9/Z4, 8010 Graz, Austria.
preishuber-pfluegl@tugraz.at; wilkening@tugraz.at

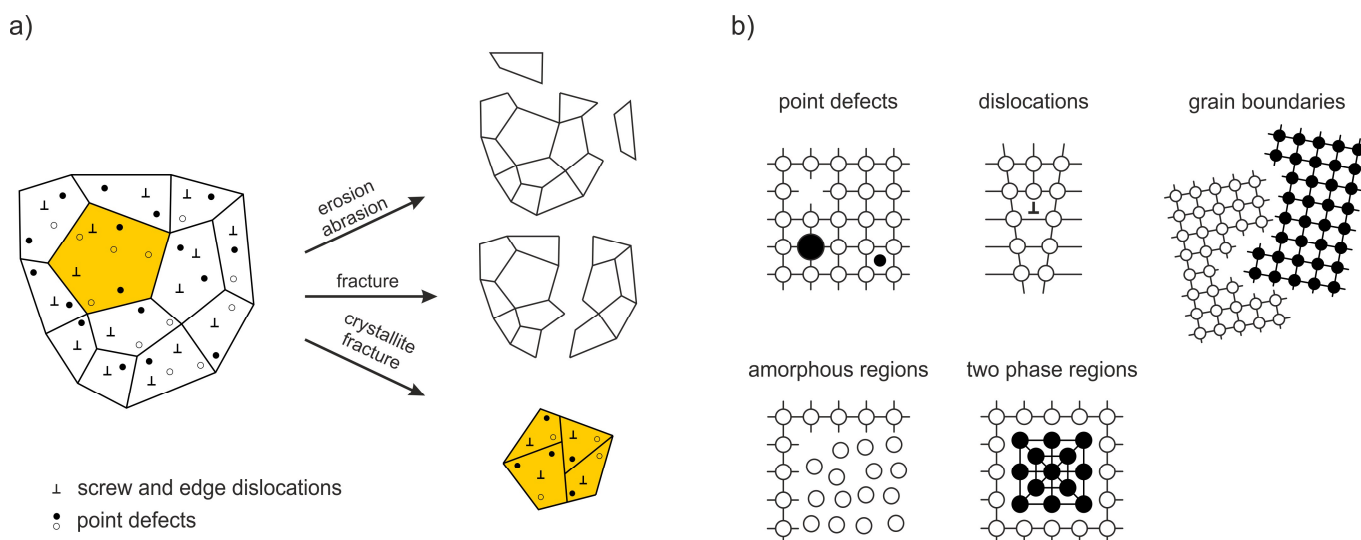


Fig. 1: a) What happens during mechanical treatment? An overview of the complex processes simultaneously taking place during high-energy ball milling. Most importantly, defects are introduced that will significantly govern the properties of the final nanocrystalline and structurally disordered product. b) Possible defect structures generated in crystalline solids treated mechanically. Illustration adapted from ref. 12.

charge carrier.⁴ In this regard, mechanochemistry has also been employed for the direct synthesis of current electrode materials for lithium-ion batteries.⁵⁻⁸

For the characterization of materials synthesized via mechanochemical routes, nuclear magnetic resonance (NMR) techniques and impedance spectroscopy have proven as powerful tools to investigate both ion dynamics on short-range as well as long-range length scales. Considering local structures, high-resolution solid-state NMR under the condition of very fast magic angle spinning (MAS) can be used to follow possible microstructural changes taking place as a function of milling time.

Mechanochemically Induced Changes: What Happens during High-Energy Ball Milling?

First results on mechanochemically induced reactions were reported by Wilhelm Ostwald, Michael Faraday and Carey Lea.^{9, 10} Lea carried out systematic investigations on silver halides upon exposure to light or mechanical force, which finally led to the differentiation of mechanochemistry as a separate branch in chemical synthesis. Initially this phenomenon was discovered in the area of inorganic solid state chemistry, but applications of this method spread on many other fields of applications including biomaterials, metal organic frameworks, catalysts, organics and pharmaceuticals, in particular.^{1, 9, 11}

In terms of solid state chemistry, such as the direct synthesis of nanocrystalline fluoride ion conductors under dry conditions, the processes during mechanical treatment can affect the starting material in two different ways: (i) altering the defect structure without any chemical reaction induced, *i.e.*, conserving the initial crystal structure and (ii) changing the crystal chemical structure by chemical reactions, that is, inducing a structural conversion by breaking and forming chemical bonds.

Figure 1 provides an overview of the possible macroscopic and microscopic structural changes taking place during severe high-energy ball milling.¹² Shear, friction and impact forces lead

to abrasion and fracture of the solid particles into smaller ones. This drastic reduction in crystallite size — usually the mean crystallite size reached after some hours of milling is in the order of 20 nm — results in a high ratio between the remaining bulk material and the structurally disordered surface-near regions.¹³ The bulk regions of a mechanochemically synthesized phase, however, are also expected to differ from those of the starting material since mechanical impact does not only introduce structural disorder in the boundary layers but also generates defects and dislocations in the interior of the small crystallites.

From the point of view of ion dynamics those ions that are located in or near these interfacial regions often move much faster than those in the bulk material. In favourable cases the quickly jumping ions can be revealed by NMR line shape studies (Figure 2).¹⁴ In particular, this has been demonstrated for single-phase nanocrystalline Li_2O and the two-phase composites $\text{Li}_2\text{O}:\text{X}_2\text{O}_3$ with $x = \text{Al, B}$.¹⁵⁻¹⁷ In the latter, the compaction of two nanocrystalline materials, an ion conductor and an ionic insulator, lead to an interfacial network of homo-contacts ($\text{Li}_2\text{O}:\text{Li}_2\text{O}$) and hetero-contacts ($\text{Li}_2\text{O}:\text{X}_2\text{O}_3$), see Figure 3 for comparison. Compared to the situation in the bulk regions of nano- Li_2O the two-component interfacial regions provide fast diffusion pathways in their vicinity.¹⁵ The same is anticipated in other dispersed ion conductors such as $\text{LiI}-\text{Al}_2\text{O}_3$ which was the first example of its class.¹⁸ Other nanostructured ion conductors^{19, 20} also benefit from so-called non-trivial size effects that are based on the formation of space charge zones²¹ which in some cases influence the dynamic properties of the whole nanocrystallite, *i.e.*, its interior regions. Maier introduced the term artificial ion conductor to describe the electrochemical situation created in nano-ionics.^{22, 23}

Apart from ion dynamics, the element distribution in grain boundary regions might be different from that in the bulk state. In particular, this holds for non-equilibrium compounds as described by Šepelák et al.² the inhomogeneous distribution of

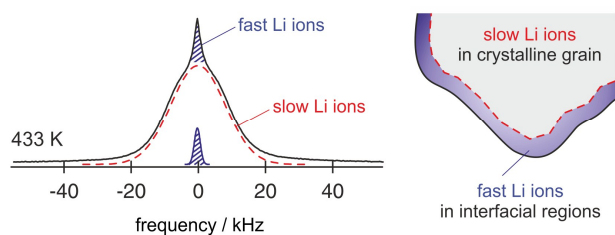


Fig. 2: ${}^7\text{Li}$ NMR spectrum of nanocrystalline Li_2O prepared by high-energy ball milling. The line is composed of two contributions reflecting the slow and the fast ions in either the bulk or in/near the interfacial regions. Figure adapted from ref. 14.

cations in the grain boundaries is referred to mechanical treatment. The authors presented detailed analysis techniques for such non-equilibrium phenomena in oxides.

The second aspect of mechanochemistry is the direct conversion of the reagents into the desired product without the need of any further processing or purification steps. As mentioned above, it is feasible to prepare materials which are not accessible through conventional synthesis techniques such as thermochemistry, precipitation techniques or sol-gel methods. Worth mentioning, such metastable phases allow to overcome miscibility gaps giving rise to solid-solutions being characterized by an enhanced concentration of vacancies, interstitials or other defects that are necessary to enable high ionic conductivities.²⁴

The underlying reaction mechanism of a mechanochemical synthesis is still under discussion. Besides the various microstructural changes taking place, localized reactions induced by heat and pressure are anticipated to lead to the final conversion of the starting material. In contrast to any high temperature solid state reaction, where the entire material is heated to a certain temperature, a mechanochemical reaction is thought to occur at localized spots where the material is stressed by the milling tools. Boden, Tabor and Yoffe proposed a 'hot-spot theory' that suggests temperatures as high as 1000 K for a time period of 10^{-4} to 10^{-3} s due to friction at surfaces of about $1 \mu\text{m}^2$.²⁵⁻²⁷ The magma-plasma model predicts even higher temperatures of up to 10^4 K and a molten-like state of the reactants in the impact zone of the particles.²⁸

The common finding in both theories is a localized development of thermal energy that promotes the solid state reactions. As the reactants are thoroughly mixed on the nm-scale, the diffusion pathways between the reactants are some orders of magnitude smaller compared to μm -sized grains. For such a localized reaction, the energy delivered by mechanical treatment might be sufficient to completely convert the starting materials into a new product. As an example, for the synthesis of BaMgF_4 , as is presented below, a quantitative reaction in a planetary ball mill required extremely high rotational speeds.²⁹ The fact that the overall temperature inside the milling beaker is much lower compared to high temperature solid state methods represents a clear advantage. At low temperatures the transformation of the products into thermodynamically stable phases is suppressed; for example, this concerns phase separations of usually immiscible solids. Hence, mechanochemistry enables indeed a

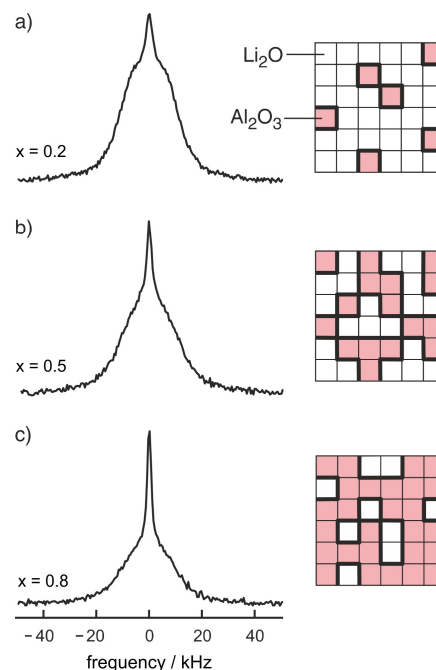


Fig. 3: ${}^7\text{Li}$ NMR spectra of the nanocrystalline composite $x\text{Li}_2\text{O}:(1-x)\text{Al}_2\text{O}_3$, a) $x = 0.2$, b) $x = 0.5$, and c) $x = 0.8$. The more hetero-contacts per formula unit of Li_2O are formed, the larger the fraction of the motionally narrowed NMR line superimposing the broad main signal. Figure adapted from ref. 14.

powerful method to prepare highly metastable, *i.e.*, non-equilibrium compounds.

Characterization Techniques: Making use of X-Rays, Spins and Charge Carriers

For the characterization of (nano-)crystalline materials, diffraction techniques such as X-ray powder diffraction (XRPD) are commonly employed to determine the crystal structures. Mechanochemically synthesized materials, however, often show patterns that deviate from single crystalline or coarse grained materials. Broadening of the reflections due to extremely small mean crystallite sizes leads to overlapping of the reflections or hides impurities and secondary phases. In addition, the signals can be shifted because of variations of the mean lattice parameters. Moreover, they can show different intensities which complicates a certain determination of the product. The milling process may also yield amorphous fractions lacking in periodicity in order that they cannot be identified by X-ray diffraction methods.

To overcome the drawbacks of X-ray diffraction, solid state NMR is the method of choice to uncover amorphous components and to collect information on local magnetic and electric fields at the nuclear sites. In particular, NMR is able to determine polyhedra distortions being a result of mechanical impact. In general, local distortions as well as outspread structural disorder can also be regarded as a metastable state of the product obtained. ${}^{19}\text{F}$ NMR benefits from the excellent receptivity of the fluorine nuclei. The good sensitivity as well as fast spin-lattice

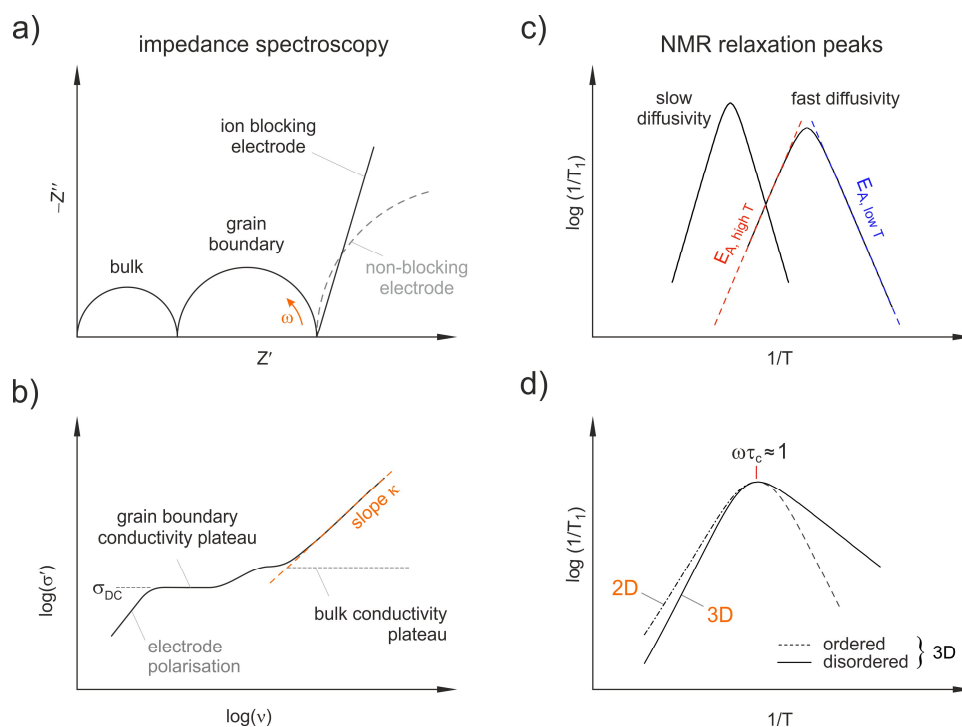


Fig. 4: Overview of important representations of impedance spectroscopy and solid state NMR data. a) Nyquist plot of the real part vs the imaginary part of the complex impedance. In the ideal case electrical responses of bulk and grain boundary regions can be distinguished; electrode effects are expected to show up at low frequencies. A spike at low frequencies results from the piling up of ions at the blocking electrode interface; conducting electrodes usually appear as large semicircles. b) The conductivity isotherm reveal the same features: at the highest frequencies a disperse regime shows up that includes forward-backward jumps. Each plateau reflects an individual transport process. c) Arrhenius plot of the NMR spin-lattice relaxation rate $1/T_1$; the higher the diffusivity the more the peak is sifted towards lower T . The flanks yield activation energies reflecting local ($E_{A, low T}$) and long-range ion dynamics ($E_{A, high T}$). d) Structural disorder results in asymmetric rate peaks with a lower slope in the low- T regime. Dimensionality effects influence the NMR rates at higher temperatures only.

relaxation of the ^{19}F nuclei due to relatively strong dipole-dipole interactions results in short acquisition times further underlining the advantages of the ^{19}F NMR spectroscopy. In order to achieve high resolution in the solid state magic angle spinning (MAS) is applied. With current NMR probes spinning speeds as high as 100 kHz are available. Since NMR spectroscopy senses the magnetic environment of each nucleus it is also applicable to amorphous compounds (see below). Thus, it is a valuable tool to help identify by-products or impurities that remain unresolved or as such invisible by XRPD. Fortunately, MAS NMR does not require special sample preparation methods; air sensitive materials can be filled into the desired rotors using a dry box with inert atmosphere. Fluorine NMR, in particular, benefits from a very broad chemical shift range with the result that the individual signals can be well distinguished and, later, assigned to the crystallographic positions.

Besides structural characterisation via XRPD and NMR on both the macroscopic length scale and the angstrom lengths scale, ion transport properties of mechanosynthesized compounds are of particular interest since they may be largely different from those of their coarse-grained counterparts. Taken together, broadband impedance spectroscopy and solid-state time-domain NMR techniques are powerful tools that enable a complementary characterization of ion dynamics by sensing the hopping processes on different time scales. In terms of jump

rates the accessible dynamic window ranges from the Hz to the GHz regime

Complex conductivities and dielectric permittivities, if measured over a wide frequency range, contain valuable information on ion hopping dynamics taking place on different length scales. In general, average hopping barriers are available from variable-temperature experiments when analysing the results in the frame of the law of Arrhenius, *i.e.*, by plotting, *e.g.*, $\log(\sigma'T)$ vs the inverse temperature $1/T$; σ' denotes the real part of the complex conductivity. Nyquist diagrams, which are obtained when the real part (Z') of the complex impedance is plotted vs the imaginary part (Z''), and the analysis of modulus peaks M'' are helpful to distinguish bulk from grain boundary contributions to the total conductivity. Of course, from the various representations of impedance data (see Figure 4) electrical relaxation rates can be deduced that are useful for comparisons with results from other micro- and macroscopic techniques.

In many cases NMR relaxometry and NMR exchange spectroscopy are able to complement broadband impedance studies. For example, time-domain NMR spin-lattice relaxation measurements,^{30, 31} if performed in the so-called low- T range of NMR relaxometry, are sensitive to short-range ion dynamics that are usually accessed by AC impedance spectroscopy carried out at sufficiently high frequencies. This regime in NMR relaxometry is characterized by jump rates $1/\tau$ that are much lower than the Larmor frequency applied to carry out the experiment.

If we assume an irregularly formed potential landscape the jumping ion is exposed to, the method senses local jumps of the ions between neighbouring sites in the crystal lattice connected by low energy barriers. In this regime the relaxation rate is also sensitive to correlation effects such as structural disorder and Coulomb interactions of the hopping ions.^{30, 32}

At higher temperatures, this is the regime where the mean jump rates exceeds the angular Larmor frequency ω_0 , the spin-lattice relaxation rate is sensitive to long-range ion dynamics. This is because during the time interval $1/\omega_0$ the ions perform many jumps that can be sampled. These hops may also include jump processes where the ions have surmount higher energy barriers. Provided all diffusion processes present contribute to the spin-lattice relaxation rate, the activation energy deduced from measurements in this T -range is comparable with that of DC conductivity measurements. In the case of low-dimensional diffusion, the NMR rates are expected to depend on the Larmor frequency applied. Moreover, the slope of the respective flank is lower than in the case of 3D motion for which no frequency dependence should be observed.^{30, 33}

If dynamically distinct processes are stepwise activated with increasing temperature, NMR is able to identify these: if widely separated on the dynamic time window they should show up as multiple relaxation rate peaks in an Arrhenius diagram.³⁴ The maxima allow an almost model-independent estimation of mean jump rates by means of the maximum condition linking ω_0 and $1/\tau$: $\omega_0\tau \approx 1$.³⁰ A thorough analysis, however, would require a specific relaxation model to interpret the data further, *e.g.*, in terms of diffusion pathways the ions chose. As mentioned above, if the number density of spins in the interfacial regions is large enough, as it is the case for nanocrystalline ceramics, NMR is able to separately probe ion dynamics of the ions residing in or near these zones.

Applications in Electrochemical Energy Storage

The aforementioned aspects of mechanochemistry makes it a highly promising method to prepare materials useful in electrochemical energy storage, in particular. Besides electrochemical stability, ionic conductivity belongs to the key parameters of a good solid electrolyte. The electrolyte is the region that should guarantee extremely fast ion exchange between the two electrodes of a battery.

The same applies to electrode materials as well, both fast ion dynamics and fast insertion kinetics crucially determine the performance of a battery, *i.e.*, to accept (ultra-)high charging rates being necessary for today's portable electronics or electric vehicles, for example. At last, facile and environmentally friendly preparation methods are needed abandoning hazardous chemicals.

As an example, electrode materials for rechargeable Li-ion batteries with aprotic liquid electrolytes were prepared by mechanochemical synthesis by Liao *et al.*, who tested LiFe_2F_6 as an intercalation compound.⁶ A similar approach to use Na_3FeF_6 as cathode material in Na-ion batteries was reported by Shakoor and co-workers.⁵ In terms of solid state batteries, the fast Li^+ conducting electrolyte $\text{Li}_7\text{P}_3\text{S}_{11}$ can be obtained through

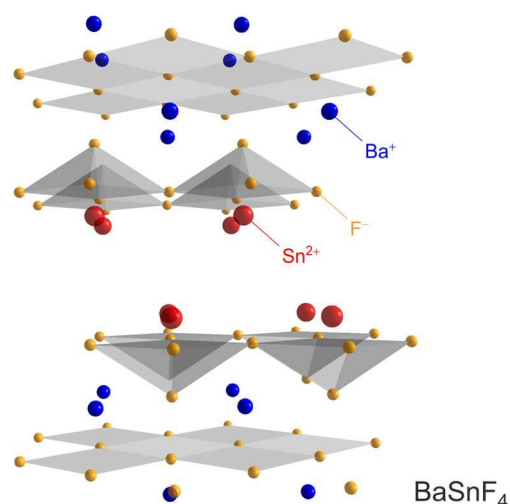


Fig. 5: Crystal structure of layered BaSnF_4 which belongs to one of the fastest F anion conductors known so far.

ball milling of Li_2S and P_2S_5 followed by a soft annealing step to yield a crystalline product.^{7, 8}

Research on anion conduction in solids has a long tradition; it was initiated by an experiment of Michael Faraday in 1834. In his experiments Faraday observed electrical conductivity of lead fluoride (PbF_2) at high temperatures. Around 1975 Schoonman, Kennedy, Hunter and others³⁵ report on first results to prepare solid-state electrochemical cells based on F ion chemistry. The large change in free enthalpy in reactions of fluorine with metals and the potentially high voltage in a battery encouraged researchers to prepare a rechargeable cell based on F ion chemistry in 2011.³⁶ One significant drawback of the system, however, was the low mobility of F ions at ambient temperature which triggered research to develop fast solid fluorine ion conductors. From the point of view of fluorine solid electrolytes, the present paper complements an earlier review by Sorokin and Sobolev that was restricted to ion conductivity in coarse-grained $\text{MF}_2\text{-RF}_3$ fluorides ($M = \text{Ba}$, ($M = \text{Ca}$, Sr , Ba , Cd , or Pb ; $R = \text{Sc}$, Y , or La-Lu) prepared by solid state synthesis.⁴

Case studies: Ion diffusion in mechano-synthesized complex fluorides

The small size and the single negative charge enable F anions to quickly move in solids. To date, $\text{MF}_2\text{-SnF}_2$ ($M = \text{Pb}$, Ba) systems are considered as the fastest F^- conductors.^{37, 38} This property is attributed to their layered structure which is the consequence of ordering effects of the cations, see Figure 5. Cation ordering is caused by the steric demand of the unpaired electrons of the Sn atoms.^{39, 40} PbSnF_4 and BaSnF_4 can be prepared by means of solid state synthesis at high temperatures;⁴¹⁻⁴³ alternatively, the ternary fluorides can be synthesized by mechanochemical means as well.⁴³⁻⁴⁶ In the case of BaSnF_4 , the highest conductivity was reached if a mechanochemical milling route was chosen.^{43, 46} The same holds for SnF_2 : if treated in a high-energy ball

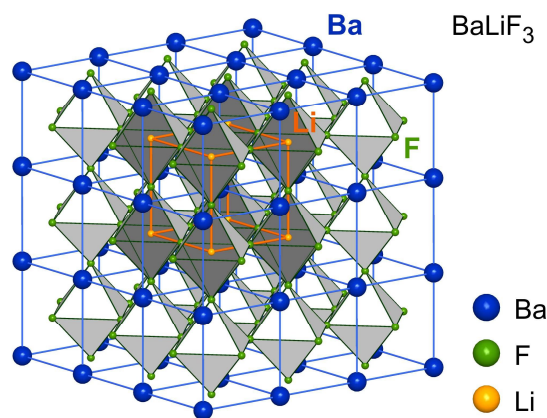


Fig. 6: Crystal structure of the inverse perovskite BaLiF_3 , the smaller Sr-atoms in $(\text{Ba,Sr})\text{LiF}_3$ occupy the same sites as Ba. This leads to lattice contraction and local distortions affecting fluorine ion dynamics. Figure adapted from ref. 55.

its conductivity can be increased by almost two orders of magnitude.⁴⁷

Unfortunately, SnF_2 -based fluorides are highly reactive, *i.e.*, unstable under electrochemical conditions complicating practical applications. Metals from the early groups of the periodic table are considered as more stable and usually possess only one oxidation/reduction state. Usually, the conductivity of these metal fluorides in the form of single crystals or polycrystalline materials is relatively low. It can be enhanced, however, by changing the morphology of the materials, *e.g.*, via nanostructuring including both bottom-up and top-down approaches such as milling.⁴⁸

In order to increase the number of defects aliovalent doping can be used to facilitate ion dynamics. As an example, mixtures of BaF_2 and LaF_3 have been extensively studied over the past years.^{24, 36, 49, 50} SrF_2 represents another substituent to manipulate ion transport in LaF_3 ⁵¹; to the best of our knowledge, such samples have, however, not been prepared mechanochemically as yet. In the following we will present case studies^{48, 50, 52-54} including isovalent and aliovalent ion-mixed compounds such as $\text{Ba}_{1-x}\text{Sr}_x\text{LiF}_3$, $\text{Ba}_{1-x}\text{Ca}_x\text{F}_2$ and $\text{Ba}_{1-x}\text{La}_x\text{F}_{2+x}$. Special emphasis will be put on the interplay of (local) structural effects with hopping ion dynamics. Whenever possible comparisons between mechano-synthesized and conventionally prepared materials are drawn.

The Inverse Perovskite $(\text{Ba,Sr})\text{LiF}_3$

Joint milling of cubic BaF_2 and LiF results in phase BaLiF_3 crystallizing with the inverse perovskite structure (Figure 6).⁵⁵ In a normal perovskite the cation with the higher charge is octahedrally coordinated while the cation with the lower charge is cuboctahedrally coordinated, see, *e.g.*, BaTiO_3 . In BaLiF_3 , however, the lower charged cation (Li^+) is octahedrally coordinated while Ba^{2+} is located in-between the octahedra. If BaF_2 is partially replaced by SrF_2 a mixed compound is formed, $\text{Ba}_{1-x}\text{Sr}_x\text{LiF}_3$, (x can reach values of up to 0.3) that decomposes at elevated temperatures (393 K). Thus, it cannot be prepared by thermochemical routes. Above $x > 0.32$, X-ray reflections of pure BaF_2 and SrF_2 appear in

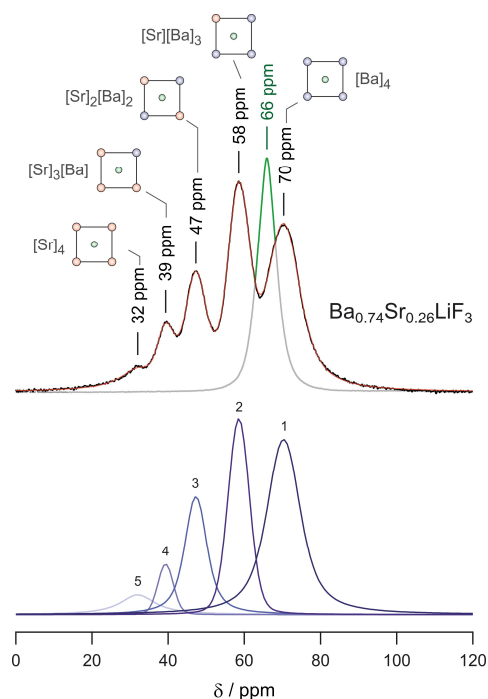


Fig. 7: ^{19}F MAS NMR spectrum of $\text{Ba}_{0.74}\text{Sr}_{0.26}\text{LiF}_3$ revealing the individual NMR signals of the different environments of the F ions. Since in BaLiF_3 the F sites are magnetically equivalent only a single signal shows. Depending on the number of Sr atoms in the direct vicinity of the ^{19}F nucleus the chemical shift ranges from 70 to 32 ppm. Figure taken from ref. 52.

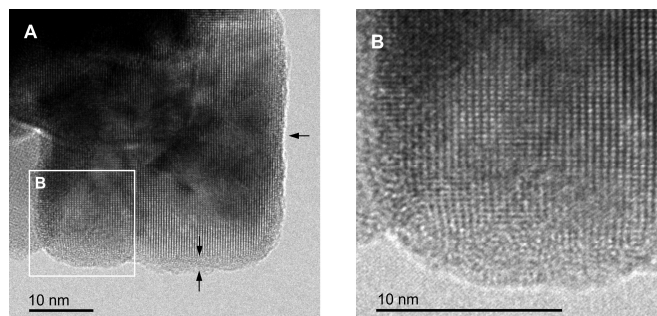


Fig. 8: High-resolution TEM image of nanocrystalline $(\text{Ba,Sr})\text{LiF}_3$ directly obtained by high-energy ball milling. The enlargement (B) reveal structurally disordered regions at the grain boundaries. Figure taken from ref. 52.

the X-ray pattern indicating the upper limit of miscibility. Interestingly, a comparative XRPD and ^{19}F NMR study showed that the mechanochemical reaction proceeds stepwise, starting with the formation of BaLiF_3 with subsequent incorporation of Sr^{2+} into the ternary fluoride.⁵² ^{19}F MAS NMR turned out to be extremely helpful to reveal the local chemical environments of the F nuclei and to unravel the formation mechanism of the quaternary compound.

As an example, in Figure 7 the ^{19}F MAS NMR spectrum of mechano-synthesized $\text{Ba}_{0.74}\text{Sr}_{0.26}\text{LiF}_3$ is shown. Whereas Sr-free BaLiF_3 is characterized by a single NMR line,⁵⁵ that of earth-alkaline mixed $\text{Ba}_{0.74}\text{Sr}_{0.26}\text{LiF}_3$ is composed of 5 signals representing the different $[\text{Sr}]_d[\text{Ba}]_b$ configurations formed ($a+b = 4$, $a, b \in \mathbb{N} \cup \{0\}$). Note that in the inverse perovskite structure Ba- and Sr-ions occupy the corner-positions of the cubic unit cells. The

face centred fluorine ions span octahedra that host the lithium ions. The more Sr ions reside in the direct vicinity of ^{19}F the more the isotropic NMR chemical shift value δ_{iso} is shifted towards positive ppm values as is illustrated in Figure 7. As an example, for the $[\text{Sr}]_4$ environments in $\text{Ba}_{0.74}\text{Sr}_{0.26}\text{LiF}_3$ $\delta_{\text{iso}} = 32$ ppm is obtained. The areas under the NMR lines, which can be well resolved at spinning speeds as high as 60 kHz, reveal the cation distribution in $\text{Ba}_{0.74}\text{Sr}_{0.26}\text{LiF}_3$.⁵²

Since Sr^{2+} is smaller than Ba^{2+} its incorporation into the BaLiF_3 lattice leads to a reduction of the lattice constant with increasing Sr content. Hence, the formation of $\text{Ba}_{1-x}\text{Sr}_x\text{LiF}_3$ can be followed by the shift of the XRPD reflections of BaLiF_3 towards larger diffraction angles. The variations in chemical environments for each fluorine site results in an irregular potential landscape with a distribution of local energy barriers. Obviously, such a distribution facilitates F anion hopping since higher conductivities are reported for the mixed compounds as compared to Sr-free BaLiF_3 .⁵² In addition to local strain throughout the bulk structure, disordered regions may be found near the interfacial regions in nanocrystalline $\text{Ba}_{1-x}\text{Sr}_x\text{LiF}_3$. While the interior of the nanocrystallites reveal an ordered structure, the surface regions are affected by dislocations, as it is shown by the TEM images in Figure 8.⁵²

Fluorides Crystallizing with Cubic Symmetry: $(\text{Ba,Ca})\text{F}_2$

BaF_2 and CaF_2 do not form a solid solution by high temperature synthesis routes. This observation is due to the large difference in ionic radii of Ba^{2+} (1.42 Å) and Ca^{2+} (1.12 Å). The formation of $\text{Ba}_x\text{Ca}_{1-x}\text{F}_2$, however, can be forced by treating the fluorides in a high-energy planetary ball mill (see Figure 9).^{48, 54} Isovalent mixing yields a metastable ternary fluoride with cubic symmetry (Figure 10 a)) whose ionic conductivity is by about two orders of magnitude higher than that of nanocrystalline, pure BaF_2 .⁵³ Ion conductivity values derived from impedance spectroscopy are

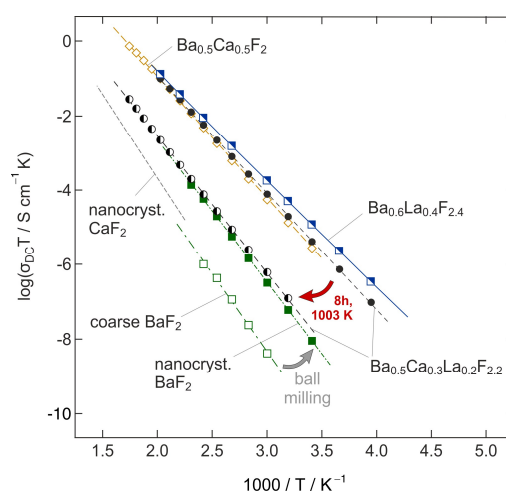


Fig. 9: Overview of the ionic conductivities of several BaF_2 -derived compounds. Ball milling of coarse-grained BaF_2 yields a nanocrystalline sample which shows a conductivity that is almost two orders of magnitudes higher compared to the non-milled material. Ion conductivity can be further improved by mixing BaF_2 and CaF_2 yielding a non-equilibrium phase taking advantage of local disorder and strain introduced when missing cations of different sizes. The highest values are found for $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$, which was studied by NMR relaxometry in detail, see below.

in the order of 1.16×10^5 S/cm at 413 K, see also Figure 10 that shows the variation of conductivity with x .

If a mixture of BaF_2 and CaF_2 is milled sufficiently long in high-energy ball mills, the XRPD unequivocally reveals the formation of a $(\text{Ba,Ca})\text{F}_2$ solid solution.⁵³ This results in complex ^{19}F MAS NMR spectra being composed of several NMR lines associated with the $[\text{Ba}]_a[\text{Ca}]_b$ environments formed (see Figure 10 c)). Differential scanning calorimetry measurements showed that the compound prepared is stable up to ca. 680 K.⁵⁴ In contrast,

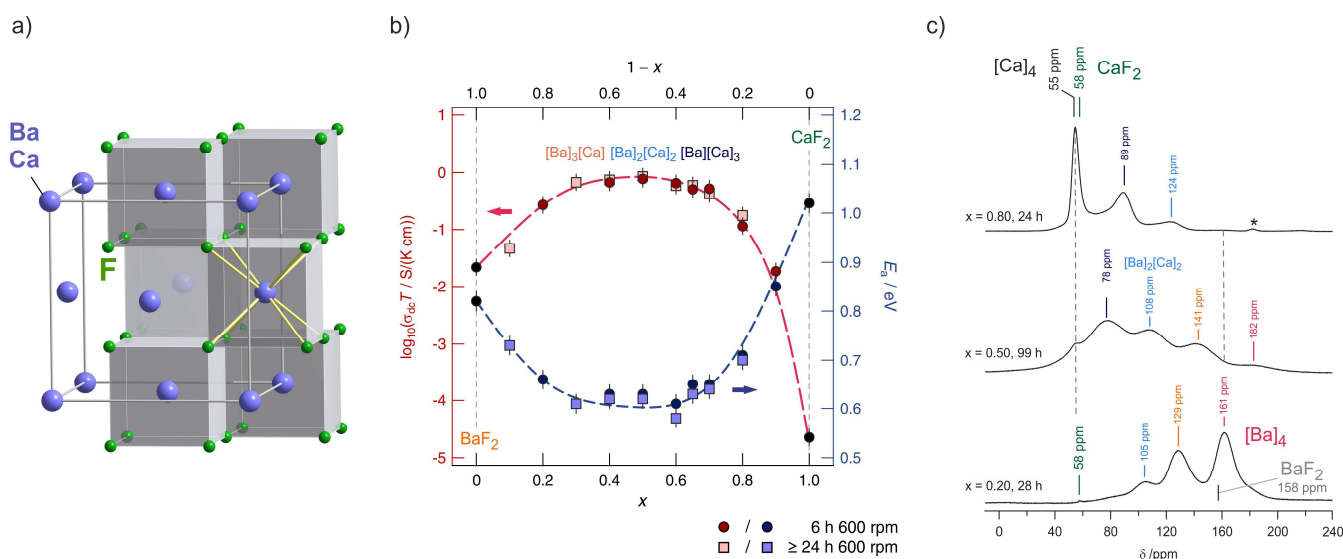


Fig. 10: a) Cubic crystal structure of $(\text{Ba,Ca})\text{F}_2$. b) Variation of conductivity and activation energies for $\text{Ba}_x\text{Ca}_{1-x}\text{F}_2$ samples mechanically prepared by milling the starting materials for 6 h and > 24 h in a planetary mill. c) ^{19}F MAS spectra revealing the local magnetic environments sensed by the F anions. The maximum in structural disorder is reached if $x = 0.5$. Figures b,c) adapted from ref. 53.

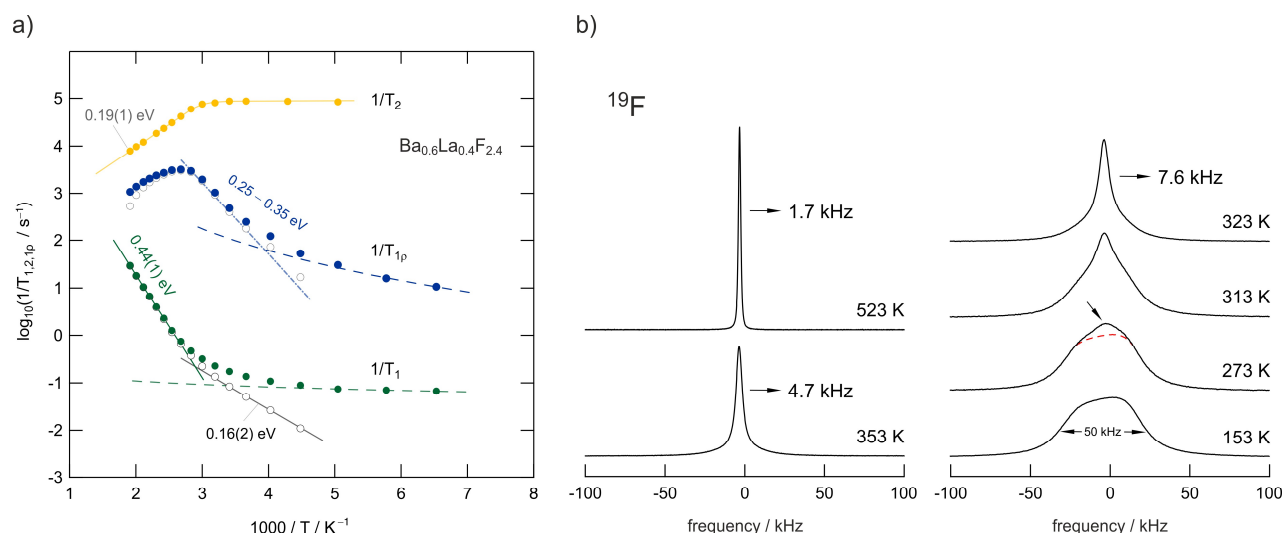


Fig. 11: a) F anion dynamics in $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$ as seen via NMR relaxometry. The rates $1/T_1$ and $1/T_{1p}$ are sensitive to different ionic motions. The same holds for T_2 which refers to the transversal decay of magnetization. Most importantly, the $1/T_{1p}(1/T)$ peak can be understood as a superposition of a range of sub-peaks that reflect dynamically distinct diffusion processes occurring in the same temperature range. Presumably, the distribution of activation energies found, *i.e.*, the heterogeneous dynamics seen, results from local structural disorder introduced by mixing the Ba^{2+} and La^{3+} cations that differ in size and charge. b) ^{19}F NMR lines of for $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$. At low temperatures, the exchange between the individual F ion positions in the crystal is ‘frozen’ in so that the different environments appear as a superposition of several processes comparable to the relaxation data in Fig. 6. Figure adapted from ref. 50.

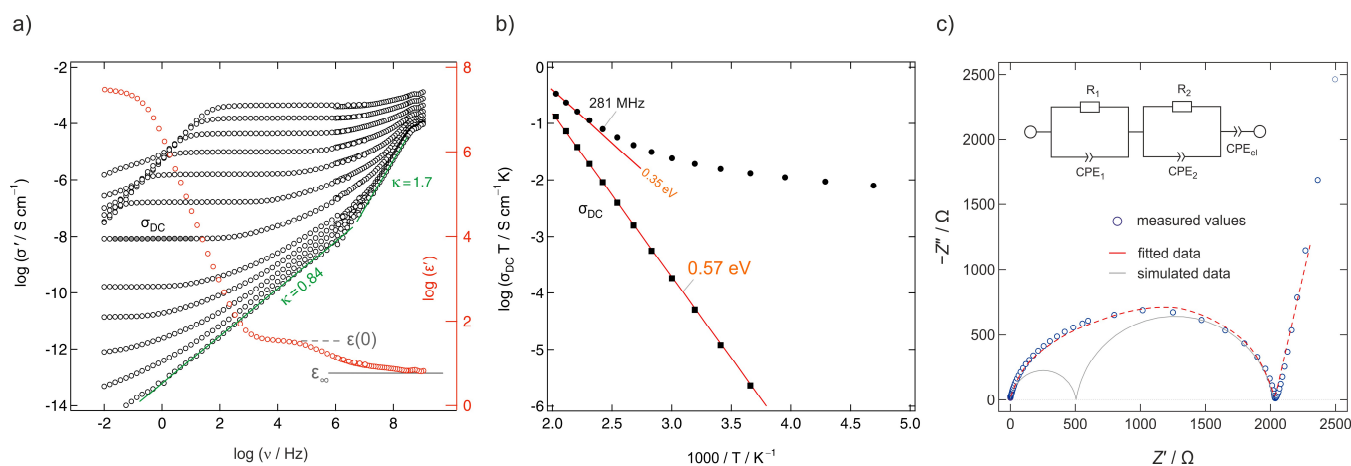


Fig. 12: a) Conductivity isotherms of $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$ measured at frequencies ranging from 10 MHz up to 3 GHz (153 K to 513 K in steps of 20 K). At frequencies above 100 MHz the individual isotherms collapse on a high frequency-plateau that show localized motions of the mobile charge carriers. The ions perform forward-backward jumps due to the short time scale at such frequencies. The chemical environment cannot adjust as fast and the process is almost independent of temperature. b) Arrhenius diagram highlighting overall DC and AC conductivities determined from data of the real part of the conductivity (σ') in the DC regime and at 281 MHz. The latter frequency is similar to the NMR Larmor frequency used to acquire the relaxation rates. Figures adapted from ref. 50. c) Complex-plane plot of the impedance determining ion transport in $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$ at 413 K (10 MHz to 1 GHz). The data can be represented by two R-CPE units (CPE: constant phase element) connected in parallel representing distinct dynamic contributions. Electrode polarization is taken into account with a third CPE.

lanthanum fluoride forms a stable solution with BaF_2 . As an example, ionic conductivity in $\text{Ba}_{0.5}\text{Ca}_{0.3}\text{La}_{0.2}\text{F}_{2.2}$, which was prepared under almost the same conditions turns out to be very similar compared to $\text{Ba}_{0.5}\text{Ca}_{0.5}\text{F}_2$. In both cases CaF_2 starts to segregate at high temperatures causing the conductivity to drop off. Interestingly, XRPD gave no indications for any LaF_3 that was precipitated at higher T . Thus, the lower conductivity is attributed to crystallite growth, structural relaxation processes including the ‘healing’ of defects.

Fluorides with Tysonite Structure: $\text{Ba}_{1-x}\text{La}_x\text{F}_{2+x}$

BaF_2 and LaF_3 are miscible in almost any molar ratio and form stable solutions up to high temperatures which enables thermal as well as mechanochemical syntheses routes. The benefit of mechanochemistry, however, is the creation of defects necessary to yield higher conductivities compared to the highly ordered, crystalline counterparts. $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$, which shows the highest conductivity among the $\text{Ba}_{1-x}\text{La}_x\text{F}_{2+x}$ solid solutions,²⁴ was chosen as a model substance to study ion dynamics by both NMR (see Figure 11) and impedance spectroscopy (Figure 12).⁵⁰

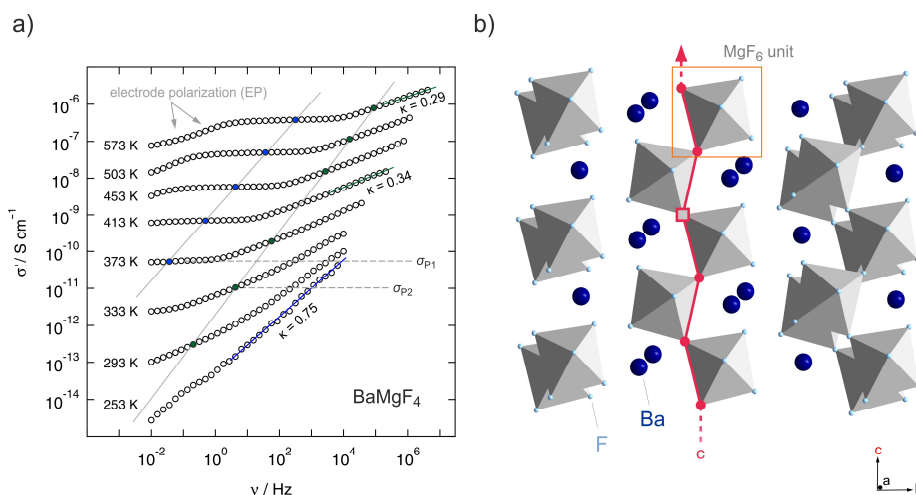


Fig. 13: a) Conductivity isotherms of mechano-synthesized BaMgF_4 in a one-pot route. The slope of the isotherms at higher temperatures was close to 0.3 which is associated with low dimensional (1D) transport. b) Crystal structure of BaMgF_4 : the corner sharing MgF_6 -octahedra form a diffusion pathway along the c -axis. Kannan *et al.* investigated oriented single crystals and reported on the highest conductivity along the c -axis. Figures adapted from ref. 29.

Mechano-synthesized $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$ is characterized by broad XRPD reflections pointing to structural disorder and strain introduced during its preparation.^{24, 50} Static ^{19}F NMR line shapes support this finding; besides dipolar broadening the lines recorded can be understood as a superposition of many lines representing the variety of magnetically distinct F environments. Variable-temperature NMR measurements, including line shape studies and relaxation measurements, as well as conductivity measurements reveal complex ion dynamics. Depending on the time scale the NMR method applied is sensitive to, activation energies obtained range from 0.16 eV to 0.44 eV. In particular, the presence of several hopping processes is highlighted in the Arrhenius diagram of Figure 11 that summarizes NMR relaxometry data on mechano-synthesized $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$. While with T_1 NMR measurements only the low- T flank of the diffusion-induced rate peak is accessible, the analogous rate $1/T_{1\rho}$ passes through a maximum; the corresponding peak is, however, unusually broad on the $1/T$ axis. It directly reflects a wide distribution of ion jump processes occurring on a very similar timescale. Compared to DC conductivity measurements, NMR relaxometry is a probe to uncover local jump processes, *i.e.*, it is possible to reveal the low energy barriers of an irregularly shaped potential landscape the ions have to surmount.

For comparison, conductivity spectroscopy, if DC plateau values were considered, points to a mean activation energy of 0.57 eV (Figure 12) being a typical value found for migration processes that are mainly driven by anion vacancies.⁵⁶ On the other hand, analysing AC conductivities recorded at frequencies similar to the NMR Larmor frequency yield activation energies being in agreement with those extracted from NMR (Figure 12 b)). At high frequencies σ' is sensitive to local (forward-backward) jumps, *i.e.*, both methods are able to access dynamic parameters on the same time scale. This similarity is also valid in the regime of very low T : the responses of the two spectroscopic techniques indicate the presence of strictly localized,

within-site motions. The latter observation points to a highly irregular distribution of energy barriers in mechano-synthesized $\text{Ba}_{0.6}\text{La}_{0.4}\text{F}_{2.4}$.⁵⁰

Channel-Structured Fluorides: BaMgF_4

Besides the formation of structurally disordered solid solutions taking advantage of aliovalent and isovalent ion mixing, mechano-synthesis can be used to prepare functional materials with remarkable purity. BaMgF_4 , which is a channel-structured ternary fluoride, is accessible via mechanical treatment of BaF_2 and MgF_2 under extremely harsh conditions, *i.e.*, at very high rotation speeds.²⁹ Ion transport is influenced by the spatial confinement of the crystal structure. BaMgF_4 crystallizes in the orthorhombic $Cmc2_1$ structure and consists of strands of corner-sharing MgF_6 -octahedra that are separated by Ba-ions. These MgF_6 -octahedra run in parallel with the c -axis of the unit cell and provide a 1-dimensional pathway which is preferred for the conduction of F-ions (see Figure 13).⁵⁷

The material, which usually requires high temperatures to be synthesized from a mixture of BaF_2 and MgF_2 ,⁵⁷ could be prepared in a planetary ball mill at rotation speeds as high as 1000 rpm.²⁹ At lower rotation speeds the synthesis remains unsuccessful. We attribute this finding to the strong heat development at the contact region of the milling media (balls/beaker walls) that induces the solid state reaction finally yielding BaMgF_4 as the only phase.

The synthesis was followed by XRPD and ^{19}F MAS NMR spectroscopy which is presented in Figure 14.²⁹ Switching off the mill after immediately interrupts the synthesis process; hence, the evolution of the product can directly be followed as a function of milling time. Interestingly, whereas the XRPD patterns recorded only show reflections of the product formed, ^{19}F MAS NMR reveals a high amount of the starting materials, MgF_2 and BaF_2 , still being present. Again, this demonstrates the benefits if both methods are used in combination. The increase of the signal intensity in the X-ray powder pattern at low diffraction

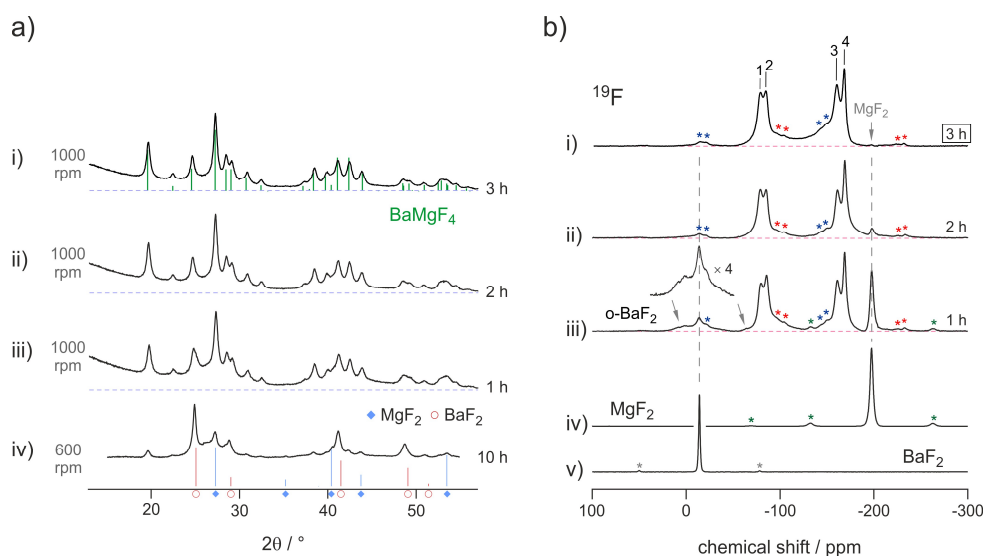


Fig. 14: Comparison of the information obtained from a) X-ray powder diffraction and b) ^{19}F solid state MAS NMR. The residual starting materials cannot be identified by XRPD (a) but were identified by MAS NMR. The latter one was used to follow the synthesis procedure, which was finished after three hours, as no noteworthy amounts of pure BaF_2 or MgF_2 could be identified any longer. Figures adapted from ref. 29.

angles points to amorphous material that could be attributed to MgF_2 . Indeed, non-reacted MgF_2 is clearly visible in the corresponding ^{19}F MAS NMR spectrum, but is missing or superimposed by the signals of the product in X-ray diffraction. The signal of BaF_2 is also likely to be hidden under the broad XRPD reflections of the product. After milling the mixture for three hours the ^{19}F MAS NMR lines attributed to the starting materials completely vanished; according to NMR, at this stage the reaction is completed.

As expected, the MAS NMR spectra show four different lines each representing one of the magnetically non-equivalent F sites in BaMgF_4 . The lines partly overlap as a result from local disorder introduced during milling. For comparison, thermochemical approaches or post annealing of the product yields well separated signals due to grain growth and healing of defects.⁵⁸

Worth noting, conductivity spectroscopy indeed indicates a quasi-1-dimensional migration pathway the ions chose to jump over long distances.²⁹ In general, low-dimensional ion transport influences the power law exponent κ describing the dispersive region of the conductivity *isotherms* (see Figure 4). In the present case, the low κ values of approximately 0.3 (see the isotherms shown in Figure 13 a)) indeed point to F anion migration along the aligned corner-sharing MgF_6 units. This finding is in agreement with the results of Kannan *et al.* who investigated BaMgF_4 single crystals.⁵⁷

Two-Dimensional Ion Conduction: Layer-structured BaSnF_4

Besides using mechanochemistry to prepare defect-rich materials, it is also a valuable tool to mechanically activate the reactants: the final product is only obtained after a subsequent annealing step. If heat treatment is carried out in a moderate way, defects may be frozen, *i.e.*, partly preserved. The residual defects are anticipated to greatly govern ion transport even in the

annealed samples characterized by larger grains. Tetragonal, layer-structured BaSnF_4 represents such an example.

BaSnF_4 is one of the fastest F anion conducting materials known today.³⁸ Similar to BaMgF_4 , it shows anisotropic conduction characteristics. This behaviour is related to the alternating double-layer structure of BaSnF_4 yielding three different types of interlayers built up of either Ba-Ba, Ba-Sn, or Sn-Sn cations. The F anions are distributed between these cation layers with each showing different diffusion characteristics depending on

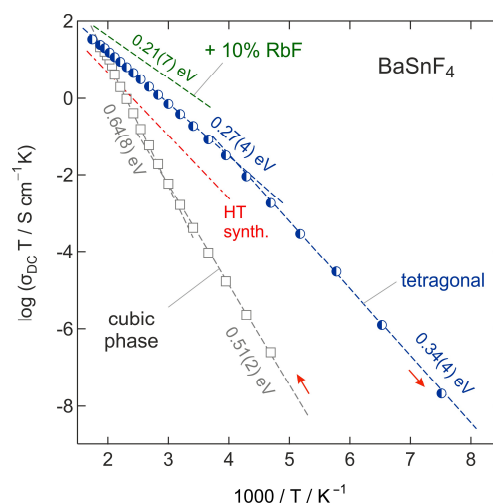


Fig. 15: Arrhenius diagram of the ionic conductivity of BaSnF_4 samples. The mechanochemical synthesis yield a metastable, cubic modification that starts to transform into the highly conductive tetragonal form at 483 K which can be seen by the inflection of the data points (grey empty cubes). The nanocrystalline tetragonal modification shows the highest conductivity of BaSnF_4 reported in the literature so far. The red, dotted line corresponds to the same material synthesized by high temperature (HT) methods. The conductivity of the material can be further increased by substitution of Ba^{2+} with monovalent Rb^+ , which is represented by the green line in the diagram.

the surrounding cations. Because of the highly ordered environment one can distinguish between fluorine ions located close to Sn-ions or close to Ba-ions. At room temperature, two spin reservoirs were found by ^{19}F MAS NMR spectroscopy, see the work by Grey and co-workers.³⁹ The anions which are distributed in the more rigid Ba-Ba interlayer do not exchange very much with those in the neighbouring Ba-Sn layer; the ions residing in the Ba-Sn layer are the most mobile ones. As was shown for PbSnF_4 compounds,⁵⁹ the occupation of fluorine ions in the Sn-Sn layer is rather low. This observation can be explained by the steric demand of the lone-pairs of the Sn ions.⁵⁹ Similar anisotropic properties, which will largely affect ion dynamics, are also expected for BaSnF_4 .

Considering ionic conductivity, the values for mechanochemically synthesized BaSnF_4 are the highest reported in the literature so far.⁴⁶ In contrast to other preparation methods reported, even after the annealing step at 573 K the average crystallite size of BaSnF_4 remains small, namely < 25 nm according to the equation introduced by Scherrer. This fact might explain the high conductivity found, most likely remaining defects and large interfacial areas substantially govern F ion dynamics.

To investigate possible effects of Ba^{2+} -substitution on the conduction behaviour, 10% of the BaF_2 was replaced with RbF . The comparable ionic radius of Rb^+ was expected to be rather compatible with the Ba^{2+} -environment than the smaller Sn^{2+} . The replacement of bivalent Ba^{2+} with monovalent Rb^+ is expected to introduce vacancies and thus to enhance the dynamics of the rigid BaF_2 -derived sublayer. Indeed, the total conductivity could be increased by about 10% reaching 3 mS/cm at room temperature, as it is illustrated in Figure 15. This value is one of the highest ever reported for BaSnF_4 .

Summary

This perspective represents a brief overview about the local structures and ion dynamics in defect-rich fluorides recently prepared via mechanochemically routes. Without doubt mechanochemistry, in some cases combined with soft annealing steps, is as a powerful synthesis method that enables a facile preparation of complex fluorides, as well as oxides and sulphides that could serve as fast ion conducting materials. In particular, it allows a direct preparation of nanocrystalline powders that can be processed in a straightforward way, *i.e.*, without the need of further purification steps. In many cases, due to structural disorder or non-equilibrium effects, the compounds synthesized benefit from improved ion transport properties if compared to conventionally prepared solids. Furthermore, as no high temperatures are needed, metastable compounds can be synthesized that are not accessible by other synthesis routes.

Considering fluorine-bearing compounds ^{19}F solid-state MAS NMR, carried out at extremely fast spinning speeds, has been demonstrated as a versatile method to reveal local magnetic structures and hence to shed light on the evolution of the final compounds with increasing milling time. In contrast to X-ray diffraction methods, MAS NMR is not only sensitive to crystalline materials, it is also possible to obtain information about amorphous fractions. In particular, due to the excellent

receptivity of the ^{19}F nucleus, fluorides represent highly suitable model compounds to study mechanochemical reactions.

The use of solid state NMR spectroscopy is, however, not limited to explore structural details of disordered solids, but also to investigate ion dynamics. In combination with impedance measurements and conductivity investigations the various spin-relaxation methods can be used to study short- as well as long range ^{19}F ion transport. Via the application of both methods the information obtainable range from elementary jump processes to long-range (through-going) ion dynamics and contain activation energies, jump rates and diffusion coefficients, respectively. In addition, the data retrieved from NMR relaxometry can also provide information on possible spin reservoirs differing in ion dynamics. This means that in favourable cases a separation of dynamically distinct ions in the bulk and grain boundary regions is possible.

To conclude, a thorough understanding of formation mechanisms as well as properties of (nano-)crystalline compounds prepared via mechanochemical may open the field for future work including preparation of new fluorides as well as their application in modern energy storage systems, in particular.

Acknowledgements

The present work is financially supported by the German Science Foundation DFG within the framework of the Priority Program 'Crystalline Non-Equilibrium Phases' (SPP 1415, grant no.: WI 3600 5-2).

References

1. S. L. James, C. J. Adams, C. Bolm, D. Braga, P. Collier, T. Friscic, F. Grepioni, K. D. Harris, G. Hyett, W. Jones, A. Krebs, J. Mack, L. Maini, A. G. Orpen, I. P. Parkin, W. C. Shearouse, J. W. Steed and D. C. Waddell, *Chem. Soc. Rev.*, 2012, **41**, 413-447.
2. V. Šepelák, A. Düvel, M. Wilkening, K. D. Becker and P. Heitjans, *Chem. Soc. Rev.*, 2013, **42**, 7507-7520.
3. P. Balaz, M. Achimovicova, M. Balaz, P. Billik, Z. Cherkezova-Zheleva, J. M. Criado, F. Delogu, E. Dutkova, E. Gaffet, F. J. Gotor, R. Kumar, I. Mitov, T. Rojac, M. Senna, A. Streletskii and K. Wieczorek-Ciurowa, *Chem. Soc. Rev.*, 2013, **42**, 7571-7637.
4. N. I. Sorokin and B. P. Sobolev, *Cryst. Reports*, **52**, 842-863.
5. R. A. Shakoob, S. Y. Lim, H. Kim, K.-W. Nam, J. K. Kang, K. Kang and J. W. Choi, *Solid State Ion.*, 2012, **218**, 35-40.
6. P. Liao, J. Li and J. R. Dahn, *J. Electrochem. Soc.*, 2010, **157**, A355-A361.
7. K. Minami, A. Hayashi and M. Tatsumisago, *J. Am. Ceram. Soc.*, 2011, **94**, 1779-1783.
8. D. Wohlmuth, V. Epp and M. Wilkening, *Chem. Phys. Chem.*, 2015, **16**, 2582-2593.
9. W. Jones and M. D. Eddleston, *Faraday Discuss.*, 2014, **170**, 9-34.
10. L. Takacs, *J. Mater. Sci.*, 2004, **39**, 4987-4993.
11. C. R. Hickenboth, J. S. Moore, S. R. White, N. R. Sottos, J. Baudry and S. R. Wilson, *Nature*, 2007, **446**, 423-427.

12. U. Hoffmann, C. Horst and U. Kunz, in *Integrated Chemical Processes*, eds. K. Sundmacher, A. Kienle and A. Seidel-Margenstern, Wiley, Weinheim, 2005, ch. 14, p. 409.
13. A. Chadwick and S. Savin, *Solid State Ion.*, 2006, **177**, 3001-3008.
14. P. Heitjans and M. Wilkening, *Mater. Res. Bull.*, 2009, **34**, 915-922.
15. P. Heitjans and S. Indris, *J. Phys.: Condens. Matter*, 2003, **15**, R1257-R1289.
16. S. Indris and P. Heitjans, *J. Non-Cryst. Solids*, 2002, **307**, 555-564.
17. M. Wilkening, S. Indris and P. Heitjans, *Phys. Chem. Chem. Phys.*, 2003, **5**, 2225-2231.
18. C. C. Liang, *J. Electrochem. Soc.*, 1973, **120**, 1289-1292.
19. N. Sata, K. Eberman, K. Eberl and J. Maier, *Nature*, 2000, **408**, 946-949.
20. J. Maier, *J. Phys. Chem. Solids*, 1985, **46**, 309-320.
21. J. Maier, *Prog. Solid State Chem.*, 1995, **23**, 171-263.
22. J. Maier, *Phys. Chem. Chem. Phys.*, 2009, **11**, 3011-3022.
23. J. Maier, *Nat. Mater.*, 2005, **4**, 805-815.
24. A. Düvel, J. Bednarcik, V. Šepelák and P. Heitjans, *J. Phys. Chem. C*, 2014, **118**, 7117-7129.
25. F. P. Bowden and D. Tabor, *The Friction and Lubrication of Solids*, Clarendon Press, Oxford, 1958.
26. F. P. Bowden and A. Yoffe, *Initiation and Growth of Explosion in Liquids and Solids*, Cambridge University Press, Cambridge, 1952.
27. F. P. Bowden and A. Yoffe, *Fast Reactions in Solids*, Butterworths, London, 1958.
28. P. A. Thiessen, M. K. and G. Heinicke, *Grundlagen der Tribochemie*, Akademie-Verlag Berlin, 1967.
29. F. Preishuber-Pflügl and M. Wilkening, *Dalton. Trans.*, 2014, **43**, 9901-9908.
30. M. Wilkening and P. Heitjans, *Chem. Phys. Chem.*, 2012, **13**, 53-65.
31. A. Kuhn, M. Kunze, P. Sreeraj, H. D. Wiemhöfer, V. Thangadurai, M. Wilkening and P. Heitjans, *Solid State Nucl. Magn. Reson.*, 2012, **42**, 2-8.
32. A. Kuhn, S. Narayanan, L. Spencer, G. Goward, V. Thangadurai and M. Wilkening, *Phys. Rev. B*, 2011, **83**, 094302
33. V. Epp and M. Wilkening, *Phys. Rev. B*, 2010, **82**, 020301.
34. A. Kuhn, P. Sreeraj, R. Pöttgen, H. D. Wiemhöfer, M. Wilkening and P. Heitjans, *J. Am. Chem. Soc.*, 2011, **133**, 11018-11021.
35. J. Schoonman, *J. Electrochem. Soc.*, 1976, **123**, 1772-1775.
36. M. Anji Reddy and M. Fichtner, *J. Mater. Chem.*, 2011, **21**, 17059-17062.
37. A. V. Chadwick, E.-S. Hammam, D. van der Putten and J. H. Strange, *Cryst. Latt. Def. and Amorph. Mat.*, 1987, **15**, 303-308.
38. L. N. Patro and K. Hariharan, *Solid State Ion.*, 2013, **239**, 41-49.
39. S. Chaudhuri, F. Wang and C. P. Grey, *J. Am. Chem. Soc.*, 2002, **124**, 11746-11757.
40. G. Dénès, T. Tyliszczak and P. Hitchcock, *J. Solid State Chem.*, 1991, **91**, 1-15.
41. G. Dénès, T. Birchall, M. Sayer and M. F. Bell, *Solid State Ion.*, 1984, **13**, 213-219.
42. G. Dénès, J. Hantash, A. Muntasar, P. Oldfield and A. Bartlett, *Hyperfine Interact.*, 2007, **170**, 145-158.
43. L. N. Patro and K. Hariharan, *Mater. Res. Bull.*, 2011, **46**, 732-737.
44. M. M. Ahmad and K. Yamada, *Appl. Phys. Lett.*, 2007, **91**, 052912.
45. M. M. Ahmad, Y. Yamane and K. Yamada, *J. Appl. Phys.*, 2009, **106**, 074106.
46. F. Preishuber-Pflügl, V. Epp, S. Nakhal, M. Lerch and M. Wilkening, *Phys. Status Sol. C*, 2015, **12**, 10-14.
47. L. N. Patro and K. Hariharan, *Mater. Lett.*, 2012, **80**, 26-28.
48. B. Ruprecht, M. Wilkening, S. Steuernagel and P. Heitjans, *J. Mater. Chem.*, 2008, **18**, 5412-5416.
49. C. Rongeat, M. A. Reddy, R. Witter and M. Fichtner, *J. Phys. Chem. C*, 2013, **117**, 4943-4950.
50. F. Preishuber-Pflügl, P. Bottke, V. Pregartner, B. Bitschnau and M. Wilkening, *Phys. Chem. Chem. Phys.*, 2014, **16**, 9580-9590.
51. H. Geiger, G. Schon and H. Stork, *Solid State Ionics*, 1985, **15**, 155-158.
52. A. Düvel, S. Wegner, K. Efimov, A. Feldhoff, P. Heitjans and M. Wilkening, *J. Mater. Chem.*, 2011, **21**, 6238-6250.
53. A. Düvel, B. Ruprecht, P. Heitjans and M. Wilkening, *J. Phys. Chem. C*, 2011, **115**, 23784-23789.
54. B. Ruprecht, M. Wilkening, A. Feldhoff, S. Steuernagel and P. Heitjans, *Phys. Chem. Chem. Phys.*, 2009, **11**, 3071-3081.
55. A. Düvel, M. Wilkening, R. Uecker, S. Wegner, V. Šepelák and P. Heitjans, *Phys. Chem. Chem. Phys.*, 2010, **12**, 11251-11262.
56. D. R. Figueroa, A. V. Chadwick and J. H. Strange, *Journal of Physics C: Solid State Physics*, 1977, **11**, 55-73.
57. C. V. Kannan, K. Shimamura, H. R. Zeng, H. Kimura, E. G. Villora and K. Kitamura, *J. Appl. Phys.*, 2008, **104**, 114113.
58. G. Scholz, S. Breitfeld, T. Krahl, A. Düvel, P. Heitjans and E. Kemnitz, *Solid State Sci*, 2015, **50**, 32-41.
59. R. Kanno, K. Ohno, H. Izumi, Y. Kawamoto, T. Kamiyama, H. Asano and F. Izumi, *Solid State Ion.*, 1994, **70**, 253-258.