

Green Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

COMMUNICATION

Ring Opening Metathesis Polymerisation of a New Bio-derived Monomer from Itaconic Anhydride and Furfuryl Alcohol

Yinjuan Bai,^{a,b} Mario De bruyn,^a James H. Clark,^a Jennifer R. Dodson,^a Thomas J. Farmer,^{a*} Mathilde Honore,^{a,c} Ian D. V. Ingram,^a Mohamed Naguib,^{a,d} Adrian C. Whitwood^a and Michael North^a

.Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

A new oxa-norbornene bio-based lactone obtained from the 100% atom economic reaction of furfuryl alcohol and itaconic anhydride via a tandem Diels-Alder addition and lactonisation is presented. Esterification of the resulting acid gives a monomer for the production of a bio-based polymer with low polydispersity and well controlled molecular weight via ring-opening metathesis polymerisation (ROMP).

Introduction

The development of novel functionalised bio-based molecules via facile, green synthetic routes is a major challenge of modern synthetic chemistry. There is interest in the use of furan-based compounds for the development of platform molecules and polymers due to their aromatic and dienic character, large structural variation and their easy accessibility from renewable resources.^{1,2} Furfural (2-furancarboxyaldehyde) is industrially produced (ca 200,000 tons/year) by the acid-catalysed dehydration of pentoses, with some being subsequently reduced to furfuryl alcohol **1**. However, these compounds can be unstable due to uncontrolled self-condensation reactions occurring in the presence of acids or heat. Itaconic acid is another bio-derived platform molecule with growing prevalence in the field of polymer synthesis and is particularly interesting due to its functionality, containing both a dicarboxylic acid and a carbon-carbon double bond.³⁻⁶ Production of itaconic acid by the fungal fermentation of glucose using *Aspergillus terreus* is

predicted to grow to 400,000 tons/yr by 2020.⁷⁻⁹ Radical polymerisation of itaconic acid and many of its esters is well known. However, as homopolymers the glass transition temperatures (T_g) of poly(itaconate alkyl esters) are often below room temperature,^{10,11} limiting their usefulness for many applications. To alleviate this problem copolymers of these monomers with conventional acrylates are often prepared.^{12,13} Poly(itaconic acid) and its salts are useful hydrophilic materials in commercial absorbents, as a co-monomer for styrene-butadiene rubber latexes, and in chelating agents.⁸ Unsurprisingly, the diacid functionality of itaconic acid, or its corresponding anhydride, has been used to make polyesters.¹⁴⁻¹⁶ However, few groups have studied the functionalisation of itaconic acid with more complex bio-based compounds, particularly furanic structures. This opens up the possibility for the development of new interesting fully bio-derived functionalised monomers and polymers.

Results and Discussion

As benzylic and other aromatic itaconate esters are known to produce polymers with higher T_g than their alkyl equivalents,¹⁷ we attempted to synthesise a bio-derived analogue of these by preparing itaconate esters with furfuryl alcohol **1**. However, when **1** was reacted with itaconic anhydride **2** (Scheme 1), at room temperature in acetonitrile solution for 24 hours, a crystalline solid formed that proved to be a novel oxa-norbornene structure **5** (61%), generated via a 100% atom economical tandem ring-opening and Diels-Alder addition, rather than the expected mono-esters **3a** or **3b**.

Although extensive work has previously been conducted on the reaction of maleic anhydride and furan derivatives, particularly for the formation of phthalic anhydrides via Diels-Alder addition and dehydration,¹⁸⁻²⁰ the reaction of **1** and **2** has not, to our knowledge, previously been studied.

Further tests showed that the reaction also occurred in the absence of solvent (68%), with the product **5** still precipitating direct from the neat reaction mixture. If necessary, the crude

^a Chemistry Department, University of York, Heslington, York, UK, YO10 5DD

^b Key Laboratory of Synthetic and Natural Functional Molecule Chemistry of Ministry of Education, College of Chemistry & Materials Science, Northwest University, Xi'an, Shaanxi 710127, PR China


^c Institut National des Sciences Appliquées, Avenue de l'Université, 76800 Saint-Étienne-du-Rouvray

^d Polymer & Pigments Department, National Research Centre, Cairo, Egypt.

* To whom correspondence should be addressed.

Email: thomas.farmer@york.ac.uk

product can be recrystallized from acetone or ethanol. Acid **5** was found to be extremely stable, showing no degradation over several weeks when stored under ambient conditions.

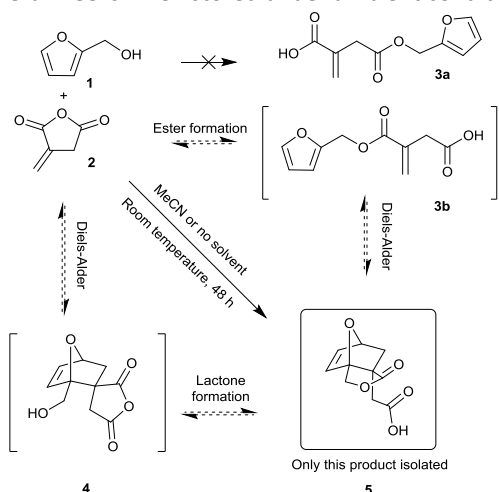

Scheme 1: Preparation of oxanorbornene-lactone monomer **5** via one-pot, tandem Diels-Alder and lactonisation reactions.

Analysis of the product by NMR spectroscopy clearly showed that the intended mono-ester **3a** was absent, as were starting materials **1** and **2**. However, both mass spectrometry and elemental analysis showed the product formed had the same molecular formula as **3a** and **3b**, leading us to consider other potential addition reactions.

Furans are well known dienes for Diels-Alder additions, including the reaction of maleic anhydride with **1**.^{18,19,21} Therefore, a combined Diels-Alder addition and ring-opening reaction to form tricyclic acid **5** was predicted to have occurred (figure S1) and was shown to fit the observed spectroscopic data. Detailed analysis by NMR spectroscopy of the crude, purified and recrystallised products indicated the formation of a single isomer (exo), with only minor by-products attributed to polymerised furfuryl alcohol. Single crystal X-ray diffraction unambiguously identified the product as **5** (Figure 1).[‡] The mechanism of this reaction is more interesting than it appears at first glance. Previous studies show that the reaction of itaconic anhydride with an alcohol regioselectively gives the ester furthest from the alkene functionality, in this case ester **3a**.²²⁻²⁴ However, the lactone present in **5** is the result of the esterification occurring at the carboxylic acid group adjacent to the alkene.


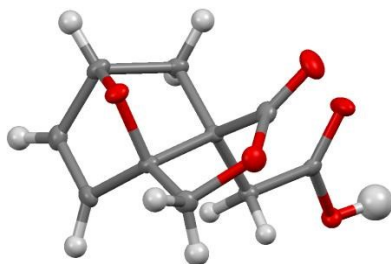


Figure 1: Single crystal X-ray structure of the isolated oxanorbornene acid **5**.


Presently it is not known whether the esterification reaction precedes the Diels-Alder cycloaddition, yielding intermediate **3b**, or whether the Diels-Alder cycloaddition occurs first, giving intermediate **4**, followed by the formation of a cyclic lactone **5**. A preliminary kinetic study proved inconclusive as neither of intermediates **3b** or **4** were observed as the reaction progressed. It would therefore seem likely that the driving force for the observed selectivity must be the crystallisation of this specific isomer from the reaction mixture. Interestingly, the formation of the intermolecular Diels-Alder adduct between maleic anhydride and various furfuryl alcohols to give an oxo-bicyclic product occurs under similar conditions to those used in this reaction.¹⁸ However, the retro-Diels-Alder addition is facile at elevated temperatures or under acidic conditions and the concurrent ring-opening of the anhydride requires either the addition of moisture or a multi-day reaction.^{18,21} In some instances oxo-norbornene derivatives are known to autoaromatise via elimination of water, though this is not possible in the case of compound **5** due to the presence of tetrasubstituted carbon atoms within the six-membered ring.

Oxo-norbornene derivatives formed from intramolecular Diels-Alder reactions of furans are known to be valuable intermediates for the production of biologically active compounds.²⁵⁻²⁹ Crucially, however, oxo-norbornenes are also capable of undergoing ring-opening metathesis polymerisation (ROMP). As obtained, acid **5** did not undergo ROMP in THF using any of the commercially available Grubbs catalysts (1st, 2nd or 3rd generations). Hence, protection of the carboxylic acid was carried out via esterification with methanol to give ester **6** (Scheme 2), with the product being purified via solvent extraction with water and either dichloromethane (77% yield) or ethyl acetate (62%).

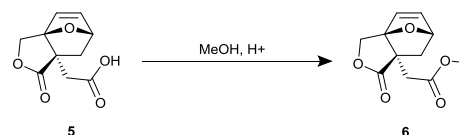

Scheme 2: Esterification of **5** with methanol to produce ROMP monomer **6**.

While Grubbs 1st generation catalyst was again found to be inactive when using **6**, the polymerisation did proceed successfully in dichloroethane (DCE) using both Grubbs 2nd generation and Hoveyda-Grubbs catalysts (H-G) (Scheme 3). To the best of our knowledge this is the first reported case of ROMP on a norbornene or oxo-norbornene molecule of this class where the bridgehead is substituted.

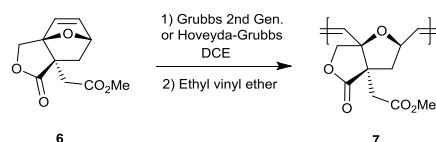

Scheme 3: ROMP of ester **6** to give homopolymer **7**


Table 1: Molecular weight and thermal analysis of random copolymers **9**.

| [6]:[8]:[i] | Reaction Time (h) | Conv. % | $M_{n(\text{calc.})}$ | $M_{n(\text{GPC})}$ | $M_{w(\text{GPC})}$ | PDI | T_g |
|-------------|-------------------|---------|-----------------------|---------------------|---------------------|------|-------|
| 25:25:1 | 16 | 100 | 10,850 | 9,500 | 11,000 | 1.15 | 158 |
| 50:50:1 | 24 | 100 | 21,700 | 21,500 | 23,700 | 1.11 | 159 |
| 100:100:1 | 48 | 97 | 42,000 | 45,200 | 53,200 | 1.17 | 161 |
| 200:200:1* | 48 | 95 | 82,500 | 63,200 | 80,800 | 1.27 | 163 |

The polymerization was carried out in 1,2-dichloroethane at room temperature, GPC was carried out in THF at 25 °C and calibrated relative to polystyrene standards.


* Reaction temperature 40 °C

Although homopolymerisation of monomer **6** occurred successfully under homogeneous conditions in DCE, with nearly full conversion, the polymer obtained (**7**) after end-capping with ethyl vinyl ether was insoluble in all solvents tested. Differential scanning calorimetry (DSC) analysis of **7** gave no detectable T_g while the temperature of 10% decomposition (TD_{10}) was determined as 358 °C (figure S10). To address the issue of solubility, copolymerisation of monomer **6** and commercially available dimethyl *endo-cis*-5-norbornene-2,3-dicarboxylate **8** was investigated and resulted in the formation of a soluble copolymers (Scheme 4). As the solubility of this copolymer hinges on the content of comonomer **8** it was subsequently established that a minimum content of 10 wt% is required to afford good solubility to the copolymer.

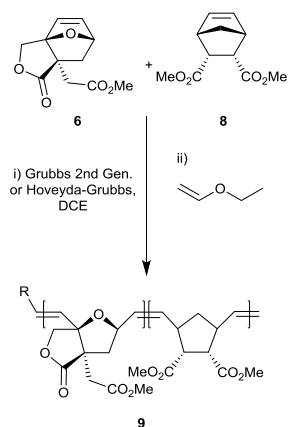Scheme 4: ROMP of monomer **6** and norbornene **8** to give copolymer **9**.

After polymerization, the fused lactone ring of **6** remained intact as elucidated by DRIFT and NMR spectroscopy.

GPC analysis showed that the soluble random copolymers have narrow molecular weight distributions indicative of a well-controlled polymerization process (see Table 1). As shown in Figure 2, there was a linear relationship between the copolymer molecular weight and the [catalyst]/[monomer] ratio which is denotive of a living polymerisation. DSC revealed that the polymers were amorphous and had glass transition temperatures ranging from 158 to 163 °C, while STA gave a TD_{10} of 370 °C (figure S10).

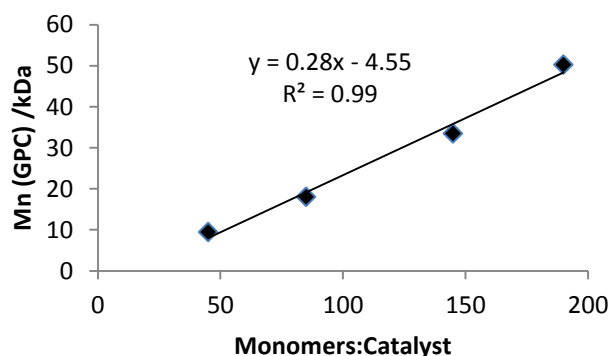Figure 2: Plot of the molecular weight versus the [monomers]/[catalyst] ratio for copolymers of **6** and **8**.

Although DCE has been a common solvent for this type of polymerisation, its current classification by sections of industry as highly hazardous and under REACH as a substance of very high concern makes future use as an industrial solvent very unlikely. Therefore, ROMP of monomer **6** was attempted using dimethyl carbonate (DMC), diethyl carbonate (DEC), tetrahydrofuran (THF) and ethyl acetate as the solvent. 2-Methyltetrahydrofuran, which is derivable from hemicellulose, was also investigated but proved to be a poor solvent for the monomer. As for the materials made in DCE, homopolymers prepared in these solvents were insoluble, therefore 50:50 copolymers were prepared. In each case, the molecular weight was very low (Table 2), with the partially formed polymer precipitating from solution in both ethyl acetate and THF. In DMC the polymer remained in solution during the reaction but only low molecular weight material ($M_n = 4000$ g/mol) was obtained. Results in DEC were somewhat more favourable, with the polymer reaching an M_n of 8500 g/mol, while extending the reaction time to 72 hours increased this further to 14200 g/mol. These results indicate that the carbonate solvent is likely coordinating to the ruthenium atom of the catalyst and slowing the rate of reaction relative to DCE.

Table 2: Molecular weights obtained for preparation of copolymer **9** in various solvents

| Solvent | M _n | M _w | PDI |
|---------------|----------------|----------------|------|
| Calculated | 21,700 | - | 1 |
| DCE | 21,500 | 23,700 | 1.11 |
| Ethyl Acetate | 2,300 | 2,400 | 1.08 |
| THF | 3,600 | 5,100 | 1.40 |
| DMC | 4,100 | 5,600 | 1.40 |
| DEC | 8,600 | 9,700 | 1.12 |
| DEC* | 14,200 | 15,700 | 1.11 |

The polymerization using a 50:50:1 molar ratio of monomers **6**:**8**:Grubbs 2nd generation catalyst was carried out at room temperature for 24 hours, molecular weights were obtained by GPC in THF at 25 °C and calibrated relative to polystyrene standards. *reaction time extended to 72 hours.

Conclusions

In this work we have demonstrated the unusual, 100% atom economic, tandem Diels-Alder cycloaddition and lactonisation reaction between itaconic anhydride **1** and furfuryl alcohol **2** to a versatile fused-ring oxa-norbornene derivative **5**. Moreover as itaconic acid and furfuryl alcohol are regarded as key platform molecules for the future bio-based chemical economy, this molecule can be considered fully bio-derivable. Additionally it is shown that the methyl ester **6** readily undergoes ROMP to produce a fully bio-derived and novel polymer, and can form copolymers with other suitable ROMP monomers.

Acknowledgements

M. Naguib would like to thank the Science & Technology Development Fund (STDF), the Egypt and the British Council, and the British Embassy for their financial support through the Newton-Mosharafa programme. Y. Bai would like to thank the State Scholarship Fund of China Scholarship Council for their support of her visiting fellowship at York (Scholarship No. 201508615069). The authors would also like to thank the Engineering and Physical Sciences Research Council (EPSRC) for funding this research through the grant EP/L017393/1.

Notes and references

‡ Crystallographic data for compound **5** has been submitted to CCDC and given code CCDC-1454993. All data used in the preparation of this manuscript is contained within this document, the electronic supplementary information or available via a depository (DOI: 10.15124ee9b6f2f-1409-4343-b855-bd5af8d97bc7).

1. J.-P. Lange, E. van der Heide, J. van Buijtenen and R. Price, *ChemSusChem*, 2012, **5**, 150-166.
2. C. Moreau, M. N. Belgacem and A. Gandini, *Topics in Catalysis*, 2004, **27**, 11-30.
3. L. Corici, A. Pellis, V. Ferrario, C. Ebert, S. Cantone and L. Gardossi, *Adv. Synth. Catal.*, 2015, **357**, 1763-1774.
4. A. Pellis, L. Corici, L. Sinigoi, N. D'Amelio, D. Fattor, V. Ferrario, C. Ebert and L. Gardossi, *Green Chem.*, 2015, **17**, 1756-1766.

5. J. Dai, S. Ma, X. Liu, L. Han, Y. Wu, X. Dai and J. Zhu, *Prog. Org. Coat.*, 2015, **78**, 49-54.
6. T. J. Farmer, J. H. Clark, D. J. Macquarrie, J. K. Ogunjobi and R. L. Castle, *Polym. Chem.*, 2016.
7. M. Okabe, D. Lies, S. Kanamasa and E. Y. Park, *Appl Microbiol Biotechnol*, 2009, **84**, 597-606.
8. Weastra, WP 8.1. *Determination of market potential for selected platform chemicals: Itaconic acid, Succinic acid, 2,5-Furandicarboxylic acid*, 2012.
9. T. Willke and K. D. Vorlop, *Appl. Microbiol. Biotechnol.*, 2001, **56**, 289-295.
10. A. Leon, L. Gargallo, A. Horta and D. Radić, *J. Polym. Sci., Part B: Polym. Phys.*, 1989, **27**, 2337-2345.
11. F. López-Carrasquero, A. Martínez de Ilarduya, M. Cárdenas, M. Carrillo, M. a. Luisa Arnal, E. Laredo, C. Torres, B. Méndez and A. J. Müller, *Polymer*, 2003, **44**, 4969-4979.
12. K. Satoh, D. H. Lee, K. Nagai and M. Kamigaito, *Macromol Rapid Commun*, 2014, **35**, 161-167.
13. E. Kassi, E. Loizou, L. Porcar and C. S. Patrickios, *Eur. Polym. J.*, 2011, **47**, 816-822.
14. A. Takasu, M. Ito, Y. Inai, T. Hirabayashi and Y. Nishimura, *Polym. J.*, 1999, **31**, 961-969.
15. T. Tang, T. Moyori and A. Takasu, *Macromolecules*, 2013, **46**, 5464-5472.
16. T. J. Farmer, R. L. Castle, J. H. Clark and D. J. Macquarrie, *Int. J. Mol. Sci.*, 2015, **16**, 14912-14932.
17. H.-z. Ma and G.-x. Ye, *Journal of Zhejiang University SCIENCE A*, 2007, **8**, 991-998.
18. S. Thiyagarajan, H. C. Genuino, M. Šliwa, J. C. van der Waal, E. de Jong, J. van Haveren, B. M. Weckhuysen, P. C. A. Bruijninx and D. S. van Es, *ChemSusChem*, 2015, **8**, 3052-3056.
19. E. Mahmoud, D. A. Watson and R. F. Lobo, *Green Chem.*, 2014, **16**, 167-175.
20. Y. Tachibana, S. Kimura and K.-i. Kasuya, *Sci. Rep.*, 2015, **5**, 8249.
21. A. Pelter and B. Singaram, *Tetrahedron Lett.*, 1982, **23**, 245-248.
22. E. Sagot, D. S. Pickering, X. Pu, M. Umberti, T. B. Stensbøl, B. Nielsen, M. Chapelet, J. Bolte, T. Gefflaut and L. Bunch, *J. Med. Chem.*, 2008, **51**, 4093-4103.
23. P. Ferraboschi, S. Casati, P. Grisenti and E. Santaniello, *Tetrahedron*, 1994, **50**, 3251-3258.
24. C. Kuheli, F. Cristina, N. Patrizia, P. Giuliana and V. Ennio, *Lett. Org. Chem.*, 2010, **7**, 245-248.
25. T. Butz and J. Sauer, *Tetrahedron: Asymmetry*, 1997, **8**, 703-714.
26. M. E. Jung and J. Gervay, *Tetrahedron Lett.*, 1988, **29**, 2429-2432.
27. O. Nieto-García and R. Alonso, *J. Org. Chem.*, 2013, **78**, 2564-2570.
28. F. I. Zubkov, E. V. Nikitina, T. R. Galeev, V. P. Zaytsev, V. N. Khrustalev, R. A. Novikov, D. N. Orlova and A. V. Varlamov, *Tetrahedron*, 2014, **70**, 1659-1690.
29. A. Padwa and A. C. Flick, in *Advances in Heterocyclic Chemistry, Vol 110*, ed. A. R. Katritzky, Elsevier Academic Press Inc, San Diego, 2013, vol. 110, pp. 1-41.

GRAPHICAL ABSTRACT

A 100% atom economic tandem Diels-Alder addition and lactonisation between bio-derivable itaconic anhydride and furfuryl alcohol can be used to prepare novel monomers for ROMP.

