

# Journal of Materials Chemistry C

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## Osmium-nitrido corroles as NIR indicators for oxygen sensors and triplet sensitizers for organic upconversion and singlet oxygen generation

Sergey M. Borisov,<sup>\*</sup><sup>1</sup> Abraham Alemayehu,<sup>2</sup> Abhik Ghosh<sup>\*</sup><sup>2</sup>

<sup>1</sup>Institute of Analytical Chemistry and Food Chemistry, NAWI Graz, Graz University of Technology, Stremayrgasse 9, 8010, Graz, Austria

<sup>2</sup>Department of Chemistry and Center for Theoretical and Computational Chemistry UiT – The Arctic University of Norway, 9037 Tromsø, Norway

**Abstract.** The photophysical properties of nitridoosmium(VI) corroles have been investigated. The complexes exhibit room temperature NIR phosphorescence ( $\lambda_{\text{max}}$  779-795 nm). Long decay times (110-150  $\mu\text{s}$  in solution and 136-183  $\mu\text{s}$  in polystyrene) are responsible for efficient quenching of the emission by oxygen. All the complexes act as efficient sensitizers of singlet oxygen (quantum yields of  $^1\text{O}_2$  0.76-0.95). Optical oxygen sensors prepared on the basis of nitridoosmium(VI) corroles exhibit high photostability and excellent sensitivity in the physiologically relevant range. The complexes have also been found to be promising sensitizers in triplet-triplet annihilation-based upconversion systems. Finally and not least, simple synthetic accessibility makes these dyes particularly attractive for application as optical materials.

\* Correspondence: sergey.borisov@tugraz.at (SMB); abhik.ghosh@uit.no (AG)

## Introduction

Dyes exhibiting room temperature phosphorescence find numerous applications, for example, as emitters in OLEDs,<sup>1,2</sup> as probes for sensing<sup>3</sup> and imaging,<sup>4-6</sup> and as sensitizers for triplet-triplet annihilation-based upconversion.<sup>7-10</sup> NIR phosphorescent dyes are of particular interest<sup>11</sup> and are used in NIR OLEDs,<sup>12-14</sup> and solar concentrators.<sup>15</sup> The combination of NIR emission with efficient absorption in the red part of the spectrum not only enables *in vivo* sensing and imaging of oxygen<sup>16-19</sup> and glucose,<sup>20</sup> but also makes the dyes promising for application in photon upconversion systems where harvesting of red light is of primary importance. Extended porphyrins, such as tetrabenzoporphyrins<sup>21,22</sup> and tetranaphthoporphyrins,<sup>23,24</sup> are probably the most common representatives of the dyes showing very strong NIR phosphorescence (phosphorescence quantum yields  $\Phi \sim 0.1-0.6$ ). Several new classes of NIR phosphorescent dyes such as Pt(II) and Pd(II) complexes with donor-acceptor Schiff bases<sup>25</sup> and Pt(II) hybrid complexes with BODIPY dyes<sup>26</sup> exhibit moderate phosphorescence quantum yields (1-11%). Other Pt(II) complexes with BODIPY dyes and naphthalene diimide chromophores coordinated via alkynyl linkages, however, exhibited even lower  $\Phi$  that were well below 1%.<sup>27-30</sup> Nevertheless, even in the absence of phosphorescent properties, dyes with high efficiency of inter-system crossing are very interesting as triplet sensitizers in photon upconversion and as singlet oxygen generators in photodynamic therapy.<sup>31,32</sup>

As porphyrin analogues with a rapidly unfolding chemistry, corroles are of considerable interest in this regard. A wide range of metallocorroles<sup>33-36</sup> have been synthesized in recent years and several have witnessed applications as catalysts,<sup>37,38</sup> in chemical sensing,<sup>39</sup> and in the biomedical arena.<sup>40</sup> Many of them exhibit bright fluorescence,<sup>41,42</sup> only a few, however, have been shown to possess NIR phosphorescence at room temperature. The latter class of complexes includes iridium corroles,<sup>43,44</sup> a gold(III)  $\beta$ -octabromocorrole,<sup>45</sup> and aluminium and gallium complexes of  $\beta$ -iodinated corroles.<sup>46</sup> A variety of other 5d metallocorroles, including rhenium,<sup>47</sup> osmium,<sup>48</sup> gold,<sup>49-51</sup> and platinum<sup>52</sup> corroles, which might be expected to exhibit NIR phosphorescence, have been synthesized in recent years. Given the steric mismatch of a large 5d metal and the constricted N4 cavity of a corrole, many of the syntheses are capricious and low-yielding. The nitridoosmium(VI) corroles, however, are accessible simply and in good yields, prompting us to examine their photophysical properties. Although they exhibit only moderate NIR phosphorescence, the OsN corroles are notable for their exceptional chemical and photochemical stability and

exhibit considerable promise as oxygen sensors, triplet sensitizers in upconversion systems, and as singlet oxygen photosensitizers.

## Experimental

### Materials

The osmium-nitrido corrole complexes were prepared according to a recently reported procedure.<sup>48</sup> The annihilators for upconversion experiments, perylene and solvent green 5 (= SG 5, diisobutyl 3,9-perylenedicarboxylate) were obtained from Fluka and ABCR (Karlsruhe, Germany), respectively. 9,10-Dimethylantracene and methylene blue were acquired from TCI Europe and Sigma-Aldrich, respectively.

### Preparation of oxygen sensors

The dye (1 mg), polystyrene (MW 250,000, 100 mg) and lipophilic titanium dioxide nanoparticles (P170, Kemira, 50 mg) were dissolved/dispersed in chloroform (1.35 g). The “cocktail” obtained was knife-coated onto a polyethylene terephthalate support (Melinex 505, Pütz, Taunusstein, Germany), yielding ~7- $\mu\text{m}$  thin films after evaporation of the solvent. For acquisition of absorption and emission spectra, a “cocktail” was prepared analogously but with no added titanium dioxide.

### Measurements

Absorption spectra were acquired on a Cary 50 UV-Vis spectrophotometer (Varian). Emission spectra were measured on a Fluorolog 3 fluorescence spectrometer from Horiba (Japan) equipped with a NIR-sensitive photomultiplier R2658 from Hamamatsu (Japan), all spectra being corrected for the sensitivity of the photomultiplier. The luminescence quantum yields in solution were measured relative to platinum(II) tetraphenyltetraabenzoporphyrin (PtTPTBP, QY 51%).<sup>53</sup> The solutions were placed in sealable quartz cells (Hellma Analytics, Mülheim, Germany) and deoxygenated by bubbling argon (5.0, Linde gas, Austria) for 15 min. Absolute quantum yields for the sensor foils were acquired in an integrating sphere from Horiba.

The photostability of the dyes was investigated by irradiating air-saturated dye solutions in toluene ( $1.4 \cdot 10^{-5}$  M) with the light of a high power orange LED array ( $\lambda_{\max}$  590 nm, www.led-tech.de) operated at 27 V and 0.6 A. The light was additionally focused through a lens (Edmunds Optics) to result in a photon flux density of  $\sim 10800 \mu\text{mol}\cdot\text{s}^{-1}\cdot\text{m}^{-2}$  or  $0.22 \text{ W/cm}^2$  as determined with a Li-250A light meter from Li-COR (www.licor.com). The cuvette with the solution was shaken after each irradiation period before absorbance measurement.

Luminescence decay times in deoxygenated toluene were measured in the frequency domain using a lock-in amplifier from PreSens (Regensburg, Germany). The solutions were excited with light from a 590-nm LED filtered through a NIR-blocking filter Calflex X (transmittance of 50% at 730 nm; Linos) and the emission was detected with a photodiode equipped with a long-pass RG 780 filter (transmittance of 50% at 780 nm; Schott). A modulation frequency of 916 Hz was used.

The oxygen sensors were characterized in the frequency domain with a two-phase lock-in amplifier (SR830, Stanford Research, Inc., USA). The excitation light was provided by a 455-nm LED (Roithner Lasertechnik, Austria). The light was sinusoidally modulated at 1150 Hz and filtered through a BG-12 band-pass filter (transmission range 300-520 nm; Schott). The emission light (filtered through an RG 780 filter) was recorded by a photomultiplier tube (H5701-02, Hamamatsu, Japan). Gas calibration mixtures were obtained from nitrogen and compressed air using a gas mixing device from MKS (Andover, MA, USA). The temperature was controlled with a ThermoHaake DC50 cryostat (Thermo Fisher Scientific, Inc).

Triplet-triplet annihilation upconversion was studied on Fluorolog 3 fluorescence spectrometer. The anoxic toluene solutions containing  $1 \cdot 10^{-4}$  M of an  $\text{Os}^{\text{VI}}\text{N}$  corrole and  $2.5 \cdot 10^{-4}$  M of the annihilator were excited at 595 nm (14 nm slits). The intensity dependency of the upconversion emission was acquired with neutral density filters from Schott (NG 11, NG 4, NG 3 and NG 9) with transmission at 595 nm of 77.8%, 34.3%, 9.4 % and 4.4%, respectively.


Singlet oxygen quantum yields were determined by a relative method using 9,10-dimethylanthracene (DMA) as singlet oxygen acceptor.<sup>54</sup> 2.5 mL of solution of DMA (7  $\mu\text{M}$ ) and a sensitizer ( $\sim 15 \mu\text{M}$ , adjusted for identical absorption of the corroles and the reference dye at the excitation wavelength) in EtOH:THF (9:1 v/v) were placed in a 1-cm screw-cap quartz cuvette which was irradiated with the light of a Xenon lamp using Fluorolog 3

spectrometer ( $\lambda_{\max}$  595 nm, 10 nm slit, photon flux  $\sim 175 \mu\text{mol}\cdot\text{s}^{-1}\cdot\text{m}^{-2}$ ). The solution was stirred during irradiation and the cuvette was shaken before acquisition of the absorption spectra. The curve was constructed as an average of 3 independent bleaching experiments. Quantum yields of singlet oxygen production  $\Phi_{\Delta}$  were determined from the slope of the curve (absorbance at 358 nm vs. time) using methylene blue as a standard ( $\Phi_{\Delta}$  of 0.48 which is the average value from the data reported by Gross et al.<sup>54</sup> and Usui et al.<sup>55</sup>

## Results and Discussion

### Photophysical properties of Os<sup>VI</sup>N corroles

The Os<sup>VI</sup>N corroles studied (see structures depicted in Fig. 1) exhibit strong absorption in the blue and orange parts of the electromagnetic spectrum and room-temperature phosphorescence in the NIR region (Fig.1, Table 1). Observe that the spectra are slightly susceptible to substituent effects. Thus, both the Q band maxima and the emission maxima slightly shift bathochromically with increasing electron-donating character of the para-substituent, i.e., Os[TpOCH<sub>3</sub>PC](N) > Os[TPC](N) > Os[TpCF<sub>3</sub>PC](N). Importantly for practical applications, the dyes can be excited with bright 590 nm and 605 nm LEDs.

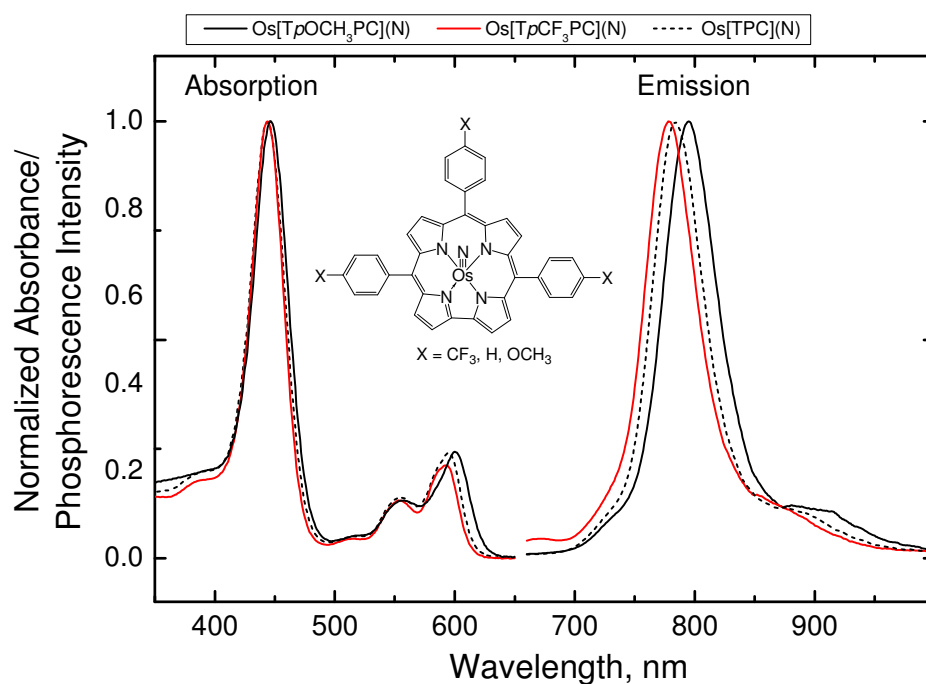

**Figure 1.** Absorption and emission spectra of Os<sup>VI</sup>N corroles in toluene (25 °C,  $\lambda_{\text{ex}}$  595 nm).

**Table 1.** Photophysical properties of Os<sup>VI</sup>N corroles in anoxic toluene solutions

Complex	$\lambda_{\max}$ (abs), nm	$\epsilon \times 10^{-4}$ , M <sup>-1</sup> cm <sup>-1</sup>	$\lambda_{\max}$ (em), nm	$\Phi$ , %	$\tau$ , 25°C, $\mu$ s
Os[ <i>Tp</i> OCH <sub>3</sub> PC](N)]	447, 558, 601	8.31, 1.18, 2.14	795	0.9	110
Os[ <i>Tp</i> PC](N)]	444, 555, 595	9.32, 1.28, 2.27	784	1.3	128
Os[ <i>Tp</i> CF <sub>3</sub> PC](N)]	444, 554, 593	8.02, 1.07, 1.73	779	1.3	150

The phosphorescence decay times for all the complexes are rather long (>100  $\mu$ s) and are intermediate between those of Pt(II) ( $\tau \sim 50$ -70  $\mu$ s) and Pd(II) porphyrins ( $\tau \sim 300$ -1000  $\mu$ s). The shortest phosphorescence lifetime is exhibited by Os[*Tp*OCH<sub>3</sub>PC](N) and the longest by Os[*Tp*CF<sub>3</sub>PC](N). This correlates well with the spectral properties of the dyes and the phosphorescence quantum yields. The quantum yields in solution are moderate, but nevertheless considerably higher than for the majority of phosphorescent iridium(III) corroles reported in the literature (<0.01%,<sup>43</sup> 0.033-1.2%<sup>44</sup>).

The photostability of dyes, a key parameter for all applications, was investigated via irradiation of  $1.4 \cdot 10^{-5}$  M solutions of the complexes in air-saturated toluene with the light of a high power orange LED array (photon flux density 10800  $\mu$ mol·s<sup>-1</sup>·m<sup>-2</sup>) whose emission wavelength ( $\lambda_{\max}$  590 nm) almost perfectly matched the the Q-bands of the dyes. No visible photodegradation was observed for Os[*Tp*CF<sub>3</sub>PC](N) (Fig. S1, ESI) and Os[*Tp*PC](N) after 30 min of continuous irradiation, indicating excellent photostability of these two dyes. Os[*Tp*OCH<sub>3</sub>PC](N) appeared to be slightly less photostable and ~1.1% dye degradation could be detected under the same conditions (Fig. S2, ESI), whereas after 6 h of irradiation bleaching of ~4.9% of the dye was observed. The lower photostability of Os[*Tp*OCH<sub>3</sub>PC](N) is presumably due to the electron-donating character of the methoxy groups in the *para*-position of the *meso*-phenyl substituents, which may favour oxidation of the dye by singlet oxygen.

### Oxygen sensing properties of the Os<sup>VI</sup>N corroles

The phosphorescence of the corroles is almost completely quenched by molecular oxygen in solutions of organic solvents, which makes them potentially suitable for application as oxygen-sensing materials. Accordingly, oxygen sensors were prepared by immobilizing the corroles into polystyrene (1% wt. of the indicator) along with TiO<sub>2</sub> nanoparticles used as a light-scattering material to increase brightness. Although many other polymers could be used, polystyrene was chosen for its high chemical stability, good compatibility with the indicator dyes, and for simple comparisons with state-of-the-art materials. The resulting planar sensors exhibit adequate brightness under excitation with a 590-nm orange LED. The positions of the absorption bands are not affected by immobilization and the phosphorescence spectra are also very similar to those obtained in the toluene solution (Figure S3, ESI; Table 2). The phosphorescent decay times are slightly higher in polystyrene relative to the solutions (Table 1 and 2), reflecting less efficient radiationless deactivation in a rigid matrix. The  $\Phi$  values are approximately 1% and are comparable to the values obtained in solution.

**Table 2.** Photophysical and sensing properties of the oxygen sensors based on Os<sup>VI</sup>N corroles corroles

Complex	$\lambda_{\max}$ abs, nm	$\lambda_{\max}$ em, nm	$\Phi$ , <sup>(a)</sup> %	$\tau_0$ at 25°C, $\mu$ s	$K_{SV}^{-1}$ at 25 °C, kPa <sup>-1(b)</sup>	$K_{SV}$ at 25 °C, kPa <sup>-1(c)</sup>	$k_q$ at 25 °C, Pa <sup>-1</sup> cm <sup>-1</sup> <sup>(c)</sup>	$d\tau_0/dT$ at 25 °C, %/K
Os[TP <sub>p</sub> OCH <sub>3</sub> PC](N)	447,557, 601	787	0.72	136	0.91	0.40	2.9	- 0.203
Os[TPC](N)	444, 554, 596	779	0.85	158	1.03	0.45	2.9	- 0.178
Os[TPCF <sub>3</sub> PC](N)	444,553, 593	771	0.95	183	1.38	0.56	3.0	- 0.136

(a) Anoxic conditions

(b) Decay time Stern-Volmer plots; fit parameters:  $m = 0.08$ ;  $f = 0.68$  for all optodes

(c) Intensity Stern-Volmer plots

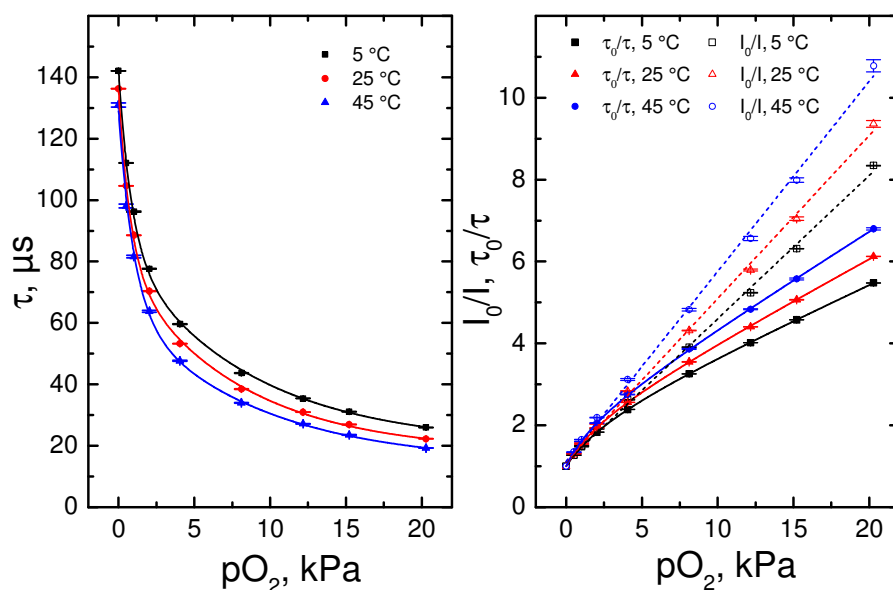


Fig. 2 shows a representative calibration plot obtained with phase fluorometry. Whereas the Stern-Volmer plots for fluorescence intensity are almost linear (correlation coefficient  $r^2$  0.998), the decay time plots deviate significantly from linearity. Such behaviour is in fact typical for oxygen sensors and very few matrices exhibit near-linear decay time plots. The nonlinear plots can be described with an equation derived from a so-called “two-site model” that assumes localization of the dye in two different environments:<sup>56</sup>

$$\frac{I}{I_0} = \frac{\tau}{\tau_0} = \frac{f}{1 + K_{SV}^1[O_2]} + \frac{1-f}{1 + K_{SV}^2[O_2]}, \quad (1)$$

where  $f$  is the fraction of the total emission for the first micro-environment, and  $K_{SV}^1$  and  $K_{SV}^2$  are the Stern-Volmer constants for each component.  $K_{SV}^2 = K_{SV}^1 * m$ .

Although the two-site model is physically meaningful only for the luminescence intensity, the decay time plots can also be almost perfectly fit with the above equation ( $r^2$  0.9999). The Stern-Volmer constants obtained from the fit are summarized in Table 2. Evidently, the sensors are promising for oxygen sensing from hypoxia to air saturation. Consistent with differences in luminescence decay times, the sensitivity is the highest for Os[TpCF<sub>3</sub>PC](N) and the lowest for Os[TpOCH<sub>3</sub>PC](N)-based sensors. The sensitivity of the sensor can thus be tailored to a specific application simply by varying the nature of the complex used. Obviously, much more substantial modulation of the sensitivity should be possible by substitution of polystyrene with a polymer with higher/lower oxygen permeability. Table 2 also shows that the bimolecular quenching constant  $k_q = K_{SV}/\tau_0$  is very similar for all the complexes examined.




**Figure 2.** Decay time (left) and Stern-Volmer plots (right) for the oxygen sensor based on Os[TpOCH<sub>3</sub>PC](N) in polystyrene. Eq. 1 was used to fit the decay time Stern-Volmer plots, whereas a linear fit was used in case of the intensity plots.

Fig. 2 evinces temperature cross-talk of the oxygen sensor, a well-known phenomenon that originates from two main factors: (i) thermal quenching of phosphorescence, which is the main error source at low pO<sub>2</sub> close to the limit of detection, and (ii) temperature-dependent diffusion and solubility of oxygen in the matrix polymer. Thermal quenching of the Os<sup>VI</sup>N complexes is relatively small as indicated by the temperature coefficients of  $\tau_0$  in the range from 0.13 to 0.20 %/K (Table 2). Notably, popular oxygen indicators such as Pd(II) porphyrins and particularly Ru(II) polypyridyl complexes show significantly higher temperature sensitivity of  $\tau_0$  ( $d\tau_0/dT \sim 0.33$  %/K<sup>57</sup> and  $\sim 0.5$  %/K,<sup>58</sup> respectively). Interestingly, thermal quenching is less efficient in case of Os[TpCF<sub>3</sub>PC](N) and is the highest for Os[TpOCH<sub>3</sub>PC](N). This correlates well with the phosphorescence quantum yields obtained at room temperature. As with other oxygen indicators in polystyrene, quenching becomes more efficient at higher temperatures (Fig. 2, Table S1, ESI). Despite that the Stern-Volmer constants  $K_{SV}$  are different for the three corroles, the bimolecular quenching constants  $k_q$  are very similar (Table S1, ESI).

The stability and reversibility of the sensors was investigated by continuous irradiation with a 455-nm LED (Fig. 3), which also reflects their photostability. Since the photostability

of the dyes may vary significantly for anoxic conditions and air saturation (due to generation of highly reactive singlet oxygen), we tested it under both conditions. Fig. 3 shows that stability of the optode based on the  $\text{Os}[\text{TpOCH}_3\text{PC}](\text{N})$  complex is excellent. In fact, the intensity decreases by only 4% after the first 2.5 h of irradiation, and by only 5 % after 6.5 h, indicating that bleaching is even slower after initial period. Also, no changes in the luminescence decay time were observed during the duration of the experiment. It may be noted that 1 h of continuous irradiation corresponds to about 200,000 measurement points under standard conditions (integration time 20 ms), emphasizing the suitability of the materials for prolonged measurements as well as for measurements at high light intensity (e.g., in microscopy). Analogously to the optode based on  $\text{Os}[\text{TpOCH}_3\text{PC}](\text{N})$ , the sensors based on the other  $\text{Os}^{\text{VI}}\text{N}$ -corroles also showed excellent stability.




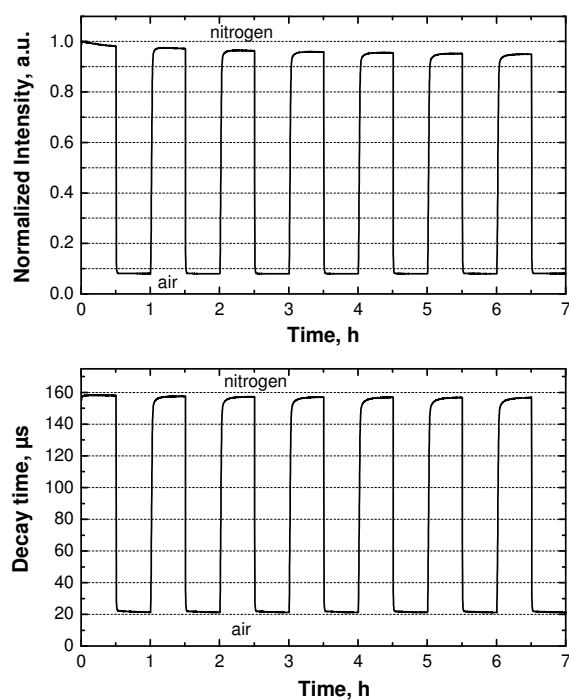


**Figure 3.** Intensity (above) and decay time (below) profiles for the oxygen sensor based on  $\text{Os}[\text{TpOCH}_3\text{PC}](\text{N})$  in polystyrene upon continuous excitation with a 455-nm LED (25 °C).

### $\text{Os}^{\text{VI}}\text{N}$ corroles as sensitizers in triplet-triplet annihilation-based upconversion


The room-temperature phosphorescence of the  $\text{Os}^{\text{VI}}\text{N}$  corroles and the relatively long phosphorescence decay times suggested that these dyes are potentially suitable as sensitizers in triplet-triplet-annihilation-based upconversion systems. Their absorption in the orange part

of the spectrum is particularly attractive, since the number of sensitizers available for this part of the spectrum is still limited. Anoxic toluene solutions containing  $1 \cdot 10^{-4}$  M of an Os<sup>VI</sup>N corrole as a sensitizer (**S**) and  $2.5 \cdot 10^{-4}$  M of an annihilator (**A**, perylene or SG 5) indeed exhibit intense upconverted emission from the annihilator, which is clearly visible even under excitation with a 590-nm LED (Fig. 4). Under excitation with orange light ( $\lambda_{\text{ex}}$  595 nm), the following processes occur:



Among the three corroles investigated, Os[TPC](N) exhibits the brightest upconverted emission (Fig. 5A). The quantum yields for the upconverted fluorescence were estimated to be 2.0, 0.9, and 0.8% for Os[TPC](N), Os[TpCF<sub>3</sub>PC](N) and Os[TpOCH<sub>3</sub>PC](N), respectively, when using SG 5 as the annihilator, and 0.51, 0.11 and 0.15%, with perylene as annihilator. The significantly lower upconversion quantum yields for perylene relative to SG 5 may be attributed to less efficient triplet-triplet energy transfer from the sensitizer to the annihilator as a result of the relatively high energy of the triplet state of the perylene. Indeed, residual phosphorescence from the sensitizer is visible when perylene is used as annihilator whereas it vanishes completely in case of SG 5 (Fig. 4A).

For comparison, the upconverted fluorescence quantum yield for the commonly used sensitizer Pt[TPTBP] were estimated to be 3.6 and 1.8%, when using SG 5 and perylene as annihilators, respectively. It should be noted that all the quantum yields are expected to be significantly higher at higher intensities of the excitation light, which were unfortunately not attainable with our experimental set-up. In fact, all the experimental points exhibit a quadratic dependency of the emission intensity on the intensity of the excitation light well below the saturation limit as indicated by the slope of the double logarithmic plots<sup>59</sup> close to 2.0 (Fig. 4B).

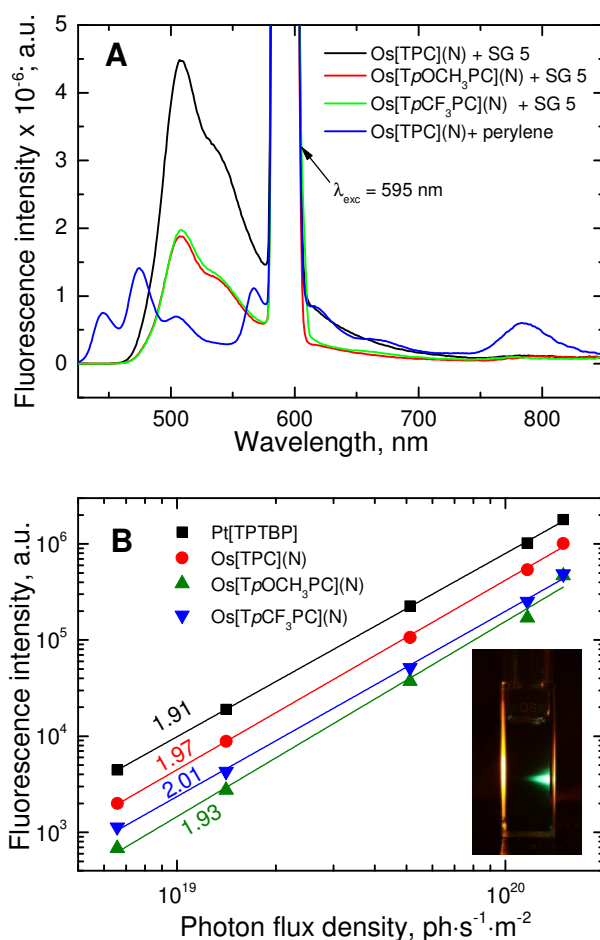


**Figure 4.** Panel A: Emission spectra of anoxic toluene solutions containing  $1 \cdot 10^{-4}$  M of an  $\text{Os}^{\text{VI}}\text{N}$  corrole and  $2.5 \cdot 10^{-4}$  M of annihilator ( $\lambda_{exc}$  595 nm). Panel B: Dependence of the intensity of upconverted fluorescence ( $\lambda = 505$  nm) on the power density of the excitation light with slopes of the curve indicated. The insert shows a photographic image of anoxic toluene solution containing  $1 \cdot 10^{-4}$  M of  $\text{Os}^{\text{VI}}[\text{TPC}](\text{N})$  and  $2.5 \cdot 10^{-4}$  M of annihilator SG 5 under excitation with a 590-nm LED.

### $\text{Os}^{\text{VI}}\text{N}$ corroles as singlet oxygen sensitizers

Singlet oxygen sensitizers are of high interest mostly due to their application in photodynamic therapy of cancer<sup>60</sup> but also as singlet oxygen generators for photocatalytic applications<sup>61,62</sup> and for disinfection purposes.<sup>63</sup>  $\text{Os}^{\text{VI}}\text{N}$  corroles might be attractive for these applications due to long-wavelength absorption and high stability. Fig. 5 illustrates the determination of singlet oxygen quantum yields  $\Phi_{\Delta}$  with a chemical method using 9,10-dimethylanthracene as a singlet oxygen acceptor.<sup>54</sup> Methylene blue ( $\Phi_{\Delta} = 0.48$ , an average value from the data

reported by Gross et al.<sup>54</sup> and Usui et al.<sup>55</sup>) was used as the reference dye. All three complexes were found to be efficient generators of singlet oxygen, with  $\Phi_{\Delta}$ 's of 0.95, 0.88 and 0.76 for Os[*Tp*OCH<sub>3</sub>PC](N), Os[*Tp*PC](N) and Os[*Tp*CF<sub>3</sub>PC](N), respectively. Interestingly, this trend is opposite to that observed for the phosphorescence quantum yields and decay times (Table 1). We may conclude that osmium-nitrido corroles show comparable or higher efficiency of <sup>1</sup>O<sub>2</sub> sensitization than the metal-free corroles and the respective Ga(III) complexes ( $\Phi_{\Delta}$  0.34-0.86;<sup>64</sup> 0.51-0.77<sup>65</sup>) and are much more powerful <sup>1</sup>O<sub>2</sub> generators than Ir(III) corroles ( $\Phi_{\Delta}$  0.09-0.15).<sup>43</sup>

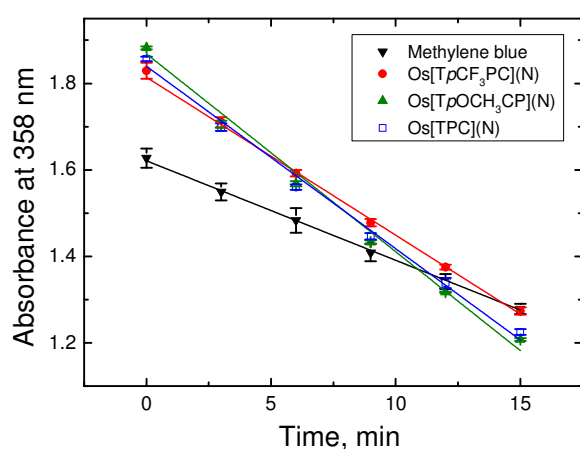

**Figure 5.** Degradation profiles of 9,10-dimethylanthracene (7  $\mu$ M) in an air-saturated solution (9:1 EtOH/THF) in presence of a sensitizer ( $\sim$  15  $\mu$ M) upon excitation with orange light (595 $\pm$ 5 nm; photon flux  $\sim$ 175  $\mu$ mol $\cdot$ s<sup>-1</sup> $\cdot$ m<sup>-2</sup>). Absorption spectra for all the systems are provided in ESI (Fig. S4-S7).

## Conclusions

Osmium(VI)-nitrido corroles represent a new class of NIR phosphorescent materials with relatively long decay times and high photostability. Although the luminescence quantum yields are moderate, they are significantly higher than those of the majority of phosphorescent corroles reported up to date. Furthermore, we have shown that Os<sup>VI</sup>N corroles can be used as indicators for optical oxygen sensors, as highly efficient singlet oxygen sensitizers, and as triplet sensitizers in organic upconversion systems, where high photostability of the dyes is of primary importance.

## Acknowledgements:

This project was partly supported by a FRINATEK project no. 231086 of the Research Council of Norway (AG). The authors thank Matthias Schwar (Graz University of Technology) for technical support.

## References

1. R. C. Evans, P. Douglas, C. J. Winscom, *Coord. Chem. Rev.*, 2006, **250**, 2093–2126.
2. J. Kalinowski, V. J. Kalinowski, V. Fattori, M. Cocchi, J. A. G. Williams, *Coord. Chem. Rev.*, 2011, **255**, 2401–2425
3. Q. Zhao, F. Li, C. Huang, *Chem. Soc. Rev.*, 2010, **39**, 3007–3030
4. M. Schäferling, *Angew. Chem. Int. Ed.*, **51**, 3532–3554.
5. Q. Zhao, C. Huang, F. Li, *Chem. Soc. Rev.*, 2011, **40**, 2508–2524.
6. D. B. Papkovsky, T. C. O’Riordan, *J. Fluoresc.*, 2005, **15**, 569–584.
7. T. N. Singh-Rachford, F. N. Castellano, *Coord. Chem. Rev.*, 2010, **254**, 2560–2573.
8. J. Zhao, S. Ji, and H. Guo, *RSC Adv.*, 2011, **1**, 937–950.
9. J. Zhou, Q. Liu, W. Feng, Y. Sun, F. Li, *Chem. Rev.*, 2015, **115**, 395–465.
10. J. Zhao, W. Wu, J. Sun, S. Guo, *Chem. Soc. Rev.*, 2013, **42**, 5323–5351
11. H. Xiang, J. Cheng, X. Ma, X. Zhou, J. J. Chruma, *Chem. Soc. Rev.*, 2013, **42**, 6128–6185.
12. C. Borek, K. Hanson, P. I. Djurovich, M. E. Thompson, K. Aznavour, R. Bau, Y. Sun, S. R. Forrest, J. Brooks, L. Michalski, J. Brown, *Angew. Chem. Int. Ed.*, 2007, **46**, 1109–1112.
13. J. R. Sommer, R. T. Farley, K. R. Graham, Y. Yang, J. R. Reynolds, J. Xue, K. S. Schanze, *ACS Appl. Mater. Interfaces*, 2009, **1**, 274–278.
14. K. R. Graham, Y. Yang, J. R. Sommer, A. H. Shelton, K. S. Schanze, J. Xue, J. R. Reynolds, *Chem. Mater.*, 2011, **23**, 5305–5312.
15. M. J. Currie, J. K. Mapel, T. D. Heidel, S. Goffri, M. A. Baldo, *Science*, 2008, **321**, 226–228.
16. E. Roussakis, Z. Li, A. J. Nichols, C. L. Evans, *Angew. Chem. Int. Ed.*, 2015, **54**, 8340–8362.
17. R. I. Dmitriev, D. B. Papkovsky, *Cellular and Molecular Life Sciences*, 2012, **69**, 2025–2039.
18. C. Staudinger, S. M. Borisov, *Methods Appl. Fluoresc.*, 2015, **3**, 042005.
19. A. Y. Lebedev, A. V. Cheprakov, S. Sakadžić, D. A. Boas, D. F. Wilson, S. A. Vinogradov, *ACS Appl. Mater. Interfaces*, 2009, **1**, 1292–1304.
20. B. Nacht, C. Larndorfer, S. Sax, S. M. Borisov, M. Hajnsek, F. Sinner, E. J. W. List-Kratochvil, I. Klimant, *Biosens. Bioelectron.*, 2015, **64**, 102–110.
21. S. A. Vinogradov, D. F. Wilson, *J. Chem. Soc., Perkin Trans. 2*, 1995, 103–111.
22. O. S. Finikova, A. V. Cheprakov, I. P. Beletskaya, P. J. Carroll, S. A. Vinogradov, *J. Org. Chem.*, 2004, **69**, 522–535.
23. V. V. Rozhkov, M. Khajehpour, S. A. Vinogradov, *Inorg. Chem.*, 2003, **42**, 4253–4255.
24. O. S. Finikova, A. V. Cheprakov, P. J. Carroll, S. A. Vinogradov, *J. Org. Chem.*, 2003, **68**, 7517–7520.
25. S. M. Borisov, R. Saf, R. Fischer, I. Klimant, *Inorg. Chem.*, 2013, **52**, 1206–1216.
26. W. Wu, J. Zhao, H. Guo, J. Sun, S. Ji, Z. Wang, *Chem. –Eur. J.*, 2012, **18**, 1961–1968.
27. W. Wu, L. Liu, X. Cui, C. Zhang, J. Zhao, *Dalton Transactions*, 2013, **42**, 14374–14379.
28. F. Zhong, A. Karatay, L. Zhao, J. Zhao, C. He, C. Zhang, H. G. Yaglioglu, A. Elmali, B. Küçüköz, M. Hayvali, *Inorg. Chem.*, 2015, **54**, 7803–7817.
29. Y. Liu, W. Wu, J. Zhao, X. Zhang, H. Guo, *Dalton Trans.* 2011, **40**, 9085–9089.
30. L. Liu, S. Guo, J. Ma, K. Xu, J. Zhao, T. Zhang, *Chem. Eur. J.*, 2014, **20**, 14282–14295.
31. A. Kamkaew, S. H. Lim, H. B. Lee, L. V. Kiew, L. Y. Chung, K. Burgess, *Chem. Soc. Rev.*, 2013, **42**, 77–88.
32. J. Zhao, K. Xu, W. Yang, Z. Wang, F. Zhong, *Chem. Soc. Rev.*, 2015, **44**, 8904–8939

33. I. Aviv, Z. Gross, *Chem. Commun.*, 2007, 1987–1999.
34. K. E. Thomas, A. B. Alemayehu, J. Conradie, C. M. Beavers, A. Ghosh, *Acc. Chem. Res.*, 2012, **45**, 1203–1214.
35. H. L. Buckley, J. Arnold, *Dalton Trans.*, 2015, **44**, 30–36.
36. J. H. Palmer, in *Molecular Electronic Structures of Transition Metal Complexes I*, Editors: D. M. P. Mingos, P. Day, J. P. Dahl, Springer Berlin Heidelberg, 2011, S. 49–89.
37. L. Simkhovich, Z. Gross, *Tetrahedron Lett.*, 2001, **42**, 8089–8092.
38. I. Aviv-Harel, Z. Gross, *Chem. Eur. J.*, 2009, **15**, 8382–8394.
39. L. Tortora, G. Pomarico, S. Nardis, E. Martinelli, A. Catini, A. D'Amico, C. Di Natale, R. Paolesse, *Sens. Actuators B*, 2013, **187**, 72–77.
40. I. Aviv-Harel, Z. Gross, *Coord. Chem. Rev.*, 2011, **255**, 717–736.
41. A. Ghosh, M. Ravikanth, *Chem. –Eur. J.*, 2012, **18**, 6386–6396.
42. J. J. Weaver, K. Sorasaene, M. Sheikh, R. Goldschmidt, E. Tkachenko, Z. Gross, H. B. Gray, *J. Porph. Phthalocyanines*, 2004, **08**, 76–81.
43. W. Sinha, L. Ravotto, P. Ceroni, S. Kar, *Dalton Trans.*, 2015, **44**, 17767–17773.
44. J. H. Palmer, A. C. Durrell, Z. Gross, J. R. Winkler, H. B. Gray, *J. Amer. Chem. Soc.*, 2010, **132**, 9230–9231.
45. E. Rabinovich, I. Goldberg, Z. Gross, *Chem. Eur. J.*, 2011, **17**, 12294–12301.
46. J. Vestfrid, I. Goldberg, Z. Gross, *Inorg. Chem.*, 2014, **53**, 10536–10542.
47. R. F. Einrem, K. J. Gagnon, A. B. Alemayehu, A. Ghosh, *Chem. Eur. J.*, 2016, **22**, 517–520.
48. A. B. Alemayehu, K. J. Gagnon, J. Turner, A. Ghosh, *Angew. Chem. Int. Ed.*, 2014, **53**, 14411–14414.
49. A. B. Alemayehu, A. Ghosh, *J. Porphyrins Phthalocyanines*, 2011, **15**, 106–110.
50. K. E. Thomas, A. B. Alemayehu, J. Conradie, C. Beavers, A. Ghosh, *Inorg. Chem.*, 2011, **50**, 12844–12851.
51. K. E. Thomas, C. M. Beavers, A. Ghosh, *Molecular Physics*, 2012, **110**, 2439–2444.
52. A. B. Alemayehu, H. Vazquez-Lima, C. M. Beavers, K. J. Gagnon, J. Bendix, A. Ghosh, *Chem. Commun.*, 2014, **50**, 11093–11096.
53. S. M. Borisov, G. Nuss, W. Haas, R. Saf, M. Schmuck, I. Klimant, *J. Photochem. Photobiol. A*, 2009, **201**, 128–135.
54. E. Gross, B. Ehrenberg, and F. M. Johnson, *Photochem. Photobiol.*, 1993, **57**, 808–813.
55. Y. Usui, H. Koike, and Y. Kurimura, *Bull. Chem. Soc. Jpn*, 1987, **60**, 3373–3378.
56. E. R. Carraway, J. N. Demas, B. A. DeGraff, J. R. Bacon, *Anal. Chem.*, 1991, **63**, 337–342.
57. S. M. Borisov, G. Nuss, I. Klimant, *Anal. Chem.*, 2008, **80**, 9435–9442.
58. S. M. Borisov I. Klimant, *Anal. Chem.*, 2007, **79**, 7501–7509.
59. A. Monguzzi, J. Mezyk, F. Scotognella, R. Tubino, and F. Meinardi, *Phys. Rev. B*, 2008, **78**, 195112
60. D. E. J. G. J. Dolmans, D. Fukumura, R. K. Jain, *Nat. Rev. Cancer*, 2003, **3**, 380–387
61. S. Hecht, J. M. J. Fréchet, *J. Am. Chem. Soc.*, 2001, **123**, 6959–6960
62. J. Sun, J. Zhao, H. Guo, W. Wu, *Chem. Commun.*, 2012, **48**, 4169–4171
63. L. Villén, F. Manjón, D. García-Fresnadillo, G. Orellana, *Appl. Catal. B*, 2006, **69**, 1–9
64. W. Shao, H. Wang, S. He, L. Shi, K. Peng, Y. Lin, L. Zhang, L. Ji, H. Liu, *J. Phys. Chem. B*, 2012, **116**, 14228–14234
65. B. Ventura, A. Degli Esposti, B. Koszarna, D. T. Gryko, and L. Flamigni, *New J. Chem.*, 2005, **29**, 1559–1566



## TOC text and figure

Readily accessible phosphorescent nitridoosmium(VI) corroles are promising sensitizers of singlet oxygen, triplet sensitizers for light upconversion and indicators for oxygen sensors

