



---

**Mechanism guided two-electron energy storage for redox-flow batteries using nickel bis(diphosphine) complexes**

Journal:	<i>ChemComm</i>
Manuscript ID	CC-COM-12-2024-006547.R1
Article Type:	Communication

**SCHOLARONE™**  
Manuscripts

## COMMUNICATION

## Mechanism guided two-electron energy storage for redox-flow batteries using nickel bis(diphosphine) complexes

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Md. Musharraf Hossain<sup>a</sup> and Byron H. Farnum <sup>\*a</sup>

**The storage of multiple electrons per molecule can greatly enhance the energy density of redox-flow batteries (RFBs). Here, we show that nickel bis(diphosphine) complexes efficiently store multiple electrons through either sequential  $1e^-$  redox waves or a concerted  $2e^-$  redox wave, depending on their coordination environment. Mechanistic studies comparing ligand sterics (-Me vs -Ph) and coordination of monodentate ligands (MeCN vs  $Cl^-$ ) allow for selective control of the electron transfer pathway, steering electron storage toward the more favorable  $2e^-$  wave. Continuous charge-discharge cycling experiments show more negative charge-discharge potentials and improved capacity retention in the presence of  $Cl^-$ , thus improving the energy storage of nickel bis(diphosphine) complexes as anolytes in RFBs. This work shows how mechanistic understanding of  $2e^-$  redox cycles for transition metal complexes can create new opportunities for multi-electron storage in RFBs.**

Renewable energy resources (i.e. solar and wind) are now prime targets to address the global energy crisis.<sup>1</sup> However, existing solar and wind power plants still have limited impact on grid systems because of their intermittent nature. Therefore, significant efforts are being made to develop efficient grid-scale energy storage (GSES) systems to improve grid flexibility.<sup>2</sup> Redox-flow batteries (RFBs) are among the best candidates to solve these challenges.

RFBs are regarded as one of the most practical options for energy storage applications on medium and large-scale.<sup>2-12</sup> Their unique architecture utilizes storage tanks filled with redox-active electrolytes wherein their power rating (kW) is a function of the electrode size and the number of cells in a stack while their energy storage capacity (kWh) is dependent on the

cell voltage and concentration of active species. The independent control of power and capacity provides design flexibility, ensuring long cycling and inherent safety for GSES applications.

Due to the inherently low energy density of RFBs, research efforts have focused on the storage of multiple electrons per redox-active molecule. This can be achieved either through sequential redox reactions of a molecule where each electron is stored at a unique potential, or through a concerted multi-electron redox reaction in which multiple electrons are stored at the same potential. The former can result in significant changes in the cell voltage of the RFB if the separation in potentials is large, whereas the latter strategy ensures that all electrons are stored equally, yielding a consistent cell voltage.


Achieving reversible multi-electron redox reactions, however, is challenging and requires intimate knowledge of electron transfer mechanisms. For organic molecules, reversible multi-electron reactions are often achieved through proton-coupled electron transfer (PCET) reactions where proton transfer is key to balancing charge and realizing a multi-electron path.<sup>10,11</sup> Inorganic transition metal complexes, however, require changes in the coordination environment to achieve multi-electron redox activity.<sup>13-16</sup> Known examples of this class use ligand coupled electron transfer (LCET) to cycle between complexes of higher coordination in the oxidized state and lower coordination in the reduced state.

Here, we report a mechanistic study on the  $2e^-$  redox cycle of Ni(II) bis(diphosphine) complexes, commonly explored as proton-reduction catalysts<sup>17-20</sup>, and show these molecules work effectively as anolytes for multi-electron storage RFBs. Furthermore, we show that the inclusion of  $Cl^-$  in the coordination environment around the nickel center allows for selective control of the multi-electron redox cycle, switching between sequential  $1e^-$  storage and concerted  $2e^-$  storage.

The chemical structures of  $[Ni(dmpe)_2]^{2+}$  and  $[Ni(dppe)_2]^{2+}$ , where dmpe is 1,2-bis(dimethylphosphino)ethane and dppe is 1,2-bis(diphenylphosphino)ethane are shown in **Fig. 1a,d** along

<sup>a</sup> Department of Chemistry and Biochemistry, Auburn University, Auburn, AL 36849, USA. Email: farnum@auburn.edu

† Electronic Supplementary Information (ESI) available: Experimental procedures, NMR, ESI-MS, UV-vis spectra, and cyclic voltammetry. See DOI: 10.1039/x0xx00000x

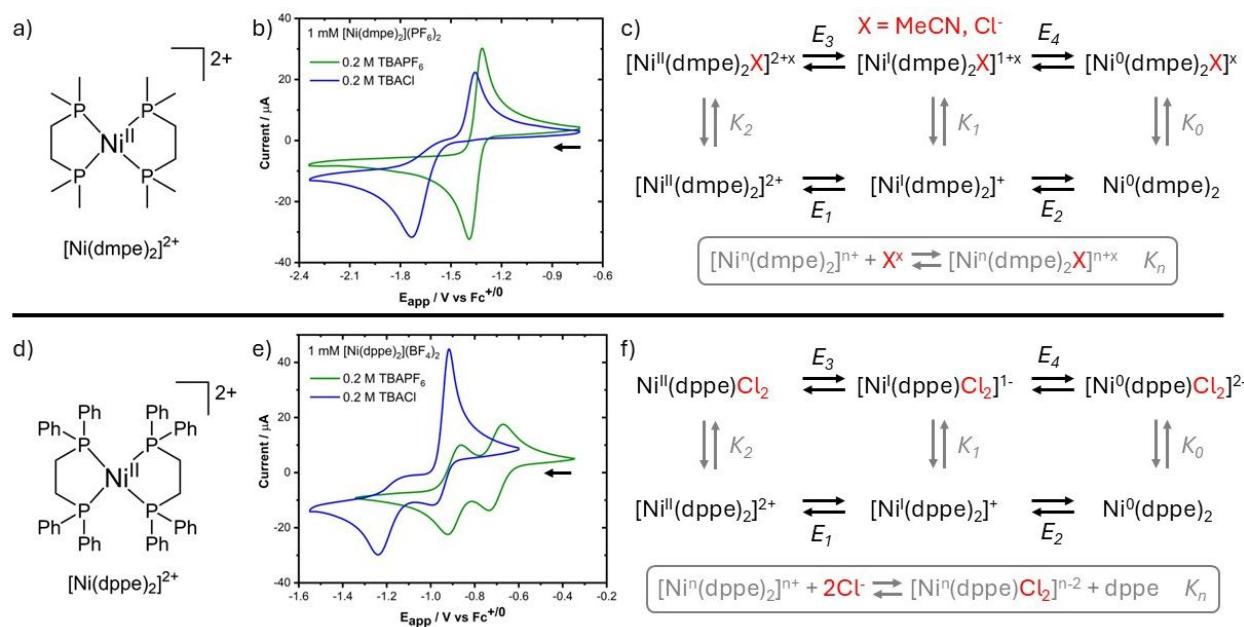

**Figure 1.** **a,d)** Chemical structures of  $[\text{Ni}(\text{dmpe})_2]^{2+}$  and  $[\text{Ni}(\text{dppe})_2]^{2+}$ . **b,e)** CV data obtained for 1 mM  $[\text{Ni}(\text{dmpe})_2](\text{PF}_6)_2$  or 1 mM  $[\text{Ni}(\text{dppe})_2](\text{BF}_4)_2$  in MeCN with different electrolytes: 0.2 M TBAPF<sub>6</sub> or 0.2 M TBACl (scan rate: 0.1 V/s, arrow indicates initial scanning direction). **c,f)** Thermochemical cycles describing the array of electron transfer and ligand transfer reactions which give rise to 2e<sup>-</sup> or 1e<sup>-</sup> redox activity.


with their corresponding cyclic voltammograms (CV) obtained in MeCN with 1 mM of each complex (**Fig. 1b,e**). Using 0.2 M TBAPF<sub>6</sub> electrolyte,  $[\text{Ni}(\text{dmpe})_2]^{2+}$  displays a single 2e<sup>-</sup> Ni(II/0) redox wave with  $E_{1/2} = -1.36$  V vs Fc<sup>+/-</sup>, while  $[\text{Ni}(\text{dppe})_2]^{2+}$  displays two sequential 1e<sup>-</sup> redox waves with  $E_{1/2} = -0.69$  V and  $-0.89$  V vs Fc<sup>+/-</sup> assigned to Ni(II/I) and Ni(I/0) redox couples. The 2e<sup>-</sup> behavior observed for  $[\text{Ni}(\text{dmpe})_2]^{2+}$  arises from the coordination of MeCN to Ni(II), thus forming  $[\text{Ni}(\text{dmpe})_2(\text{MeCN})]^{2+}$  in MeCN solution (**Fig. S12a, ESI**). This coordination pushes the Ni(II/I) reduction potential in a negative direction and generates a state of potential inversion between the Ni(II/I) and Ni(I/0) redox couples (i.e. Ni(II/I) < Ni(I/0), producing a 2e<sup>-</sup> redox wave in the CV. In the case of the  $[\text{Ni}(\text{dppe})_2]^{2+}$ , coordination of MeCN to Ni(II) does not occur (**Fig. S12b, ESI**) and thus the reduction of Ni(II) to Ni(0) occurs in a sequential fashion with the normal potential ordering of Ni(II/I) > Ni(I/0).

These redox mechanisms are summarized by the thermochemical cycles shown in **Fig. 1**. Reduction of  $[\text{Ni}(\text{dppe})_2]^{2+}$  occurs via a sequential 1e<sup>-</sup> path corresponding to reduction at  $E_1$  followed by reduction at  $E_2$  (**Fig. 1f**). However, the coordination of MeCN to  $[\text{Ni}(\text{dmpe})_2]^{2+}$  shifts the Ni(II/I) reduction potential according to the equilibrium constant  $K_2$ , resulting in a new value  $E_3$ . Following reduction to  $[\text{Ni}(\text{dmpe})_2(\text{MeCN})]^+$ , the MeCN ligand dissociates (1/ $K_1$ ), returning the structure to a four-coordinate environment where Ni(I) is reduced to Ni(0) at  $E_2$ . This reduction sequence ( $E_3 \rightarrow 1/K_1 \rightarrow E_2$ ) represents an ECE cycle where E is an electron transfer step and C is a chemical step (i.e. ligand transfer) and is common for 2e<sup>-</sup> transfer reactions. Oxidation of Ni(0) back to Ni(II) occurs in reverse order and yields a reversible CV wave.

The specific reason for the favorability of the ECE path in  $[\text{Ni}(\text{dmpe})_2]^{2+}$  lies in the ability to change its coordination environment as a function of oxidation state.  $[\text{Ni}(\text{dmpe})_2]^{2+}$  can be isolated as a square planar structure but adopts square pyramidal in solution due to MeCN coordination.<sup>17</sup> The d<sup>8</sup> Ni(II) center is able to accommodate the five-coordinate environment to yield an 18 electron complex, but reduction to the d<sup>9</sup> Ni(I) and d<sup>10</sup> Ni(0) strongly disfavors five-coordinate geometries due to the result of 19 and 20 electron complexes, respectively. Steric hindrance by the phenyl groups of  $[\text{Ni}(\text{dppe})_2]^{2+}$  disrupts MeCN coordination and prevents the 2e<sup>-</sup> ECE cycle from being observed.

Given the differences in CV data observed for the two complexes as a result of MeCN coordination (or lack thereof), electrochemical experiments were also performed in the presence of Cl<sup>-</sup> to further study the impact of monodentate coordination on their redox cycles. Overlaid in **Fig. 1b,e** are CVs collected in MeCN with 0.2 M TBACl as the electrolyte. In the case of  $[\text{Ni}(\text{dmpe})_2]^{2+}$ , the cathodic peak was shifted  $-330$  mV to  $E_{pc} = -1.73$  V while the anodic peak was relatively unchanged ( $E_{pa} = -1.35$  V) with respect to 0.2 M TBAPF<sub>6</sub> electrolyte (**Table S2, ESI**). For  $[\text{Ni}(\text{dppe})_2]^{2+}$ , the two cathodic peaks were shifted by  $-260$  mV and  $-330$  mV to  $E_{pc} = -0.98$  V and  $-1.25$  V, respectively. Furthermore, the anodic peaks were consolidated mostly into a single oxidation peak at  $E_{pa} = -0.92$  V with a much smaller peak observed at  $E_{pa} = -1.14$  V.

Changes observed for both complexes are ascribed to coordination and dissociation of Cl<sup>-</sup> as a function of oxidation state. UV-visible absorption studies showed Cl<sup>-</sup> coordination to both  $[\text{Ni}(\text{dmpe})_2]^{2+}$  and  $[\text{Ni}(\text{dppe})_2]^{2+}$  (**Fig. S13-S14, ESI**), however, with different resulting complexes. In the case of

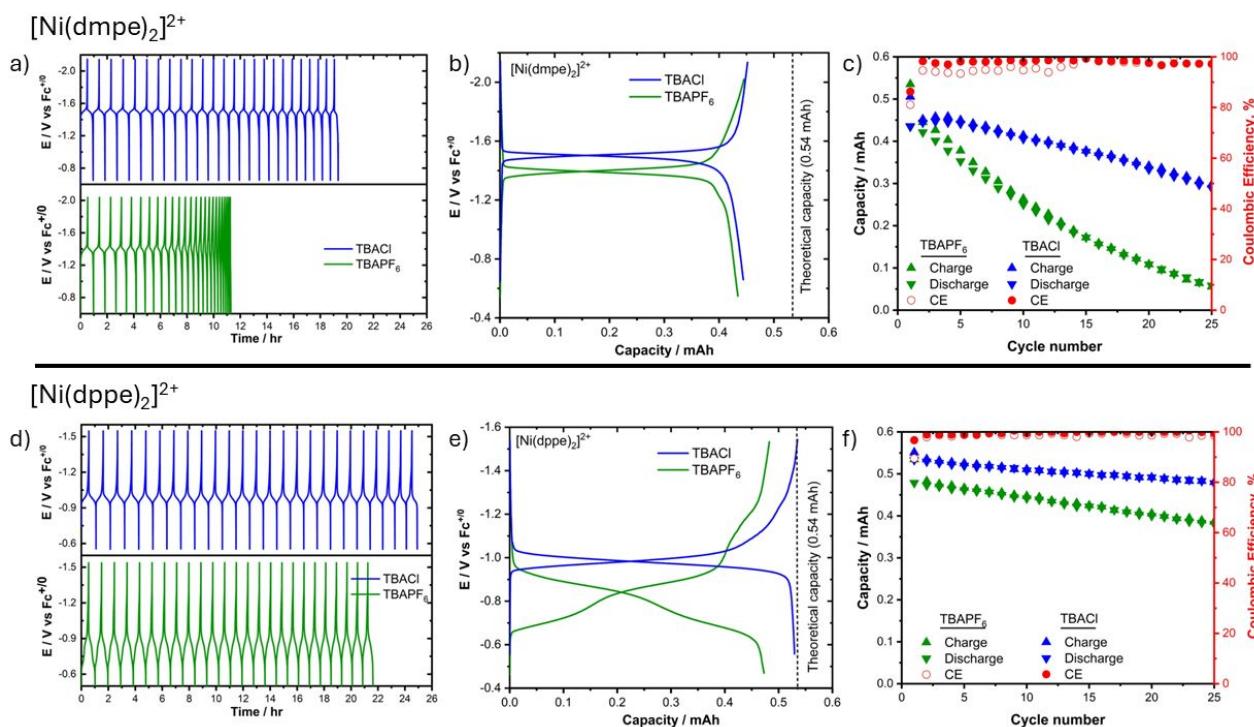

**Figure 2.** **a,d)** Representative charge-discharge voltage vs time data for either 1 mM  $[\text{Ni}(\text{dmpe})_2](\text{PF}_6)_2$  or 1 mM  $[\text{Ni}(\text{dppe})_2](\text{BF}_4)_2$  in MeCN with 0.2 M TBAPF<sub>6</sub> (green) or 0.2 M TBACI (blue) electrolyte. Charging current = discharging current = 1 mA. **b,e)** Comparison of the 2<sup>nd</sup> charge-discharge cycle for each complex in each electrolyte. **c,f)** Capacity and coulombic efficiency vs cycle number for each complex in each electrolyte.

$[\text{Ni}(\text{dmpe})_2]^{2+}$ , the coordination of  $\text{Cl}^-$  yields a 1:1 complex,  $[\text{Ni}(\text{dmpe})_2\text{Cl}]^+$ , and shifts the redox potentials further into an inverted state by increasing  $K_2$  (and thus shifting  $E_3$ ) resulting in the same ECE pathway for the reduction and oxidation processes observed in the absence in  $\text{Cl}^-$ .

Coordination of  $\text{Cl}^-$  to  $[\text{Ni}(\text{dppe})_2]^{2+}$ , however, results in a 2:1 complex,  $\text{Ni}(\text{dppe})\text{Cl}_2$ , wherein one dppe ligand is dissociated. UV-vis and electrochemical comparisons with independently obtained  $\text{Ni}(\text{dppe})\text{Cl}_2$  verified this result (Fig. S14 & S16, ESI). Using Fig. 1f as reference, the reduction of  $\text{Ni}(\text{II})$  to  $\text{Ni}(0)$  for the new  $\text{Ni}(\text{dppe})\text{Cl}_2$  starting complex occurs via  $E_3 \rightarrow E_4 \rightarrow 1/K_0$  (EEC) while oxidation of  $\text{Ni}(0)$  back to  $\text{Ni}(\text{II})$  occurs via  $E_2 \rightarrow K_1 \rightarrow E_3$  (ECE). These cycles can be gleaned from the appearance of two shifted cathodic waves corresponding to reduction at  $E_3$  and  $E_4$  while the oxidation process shows a single anodic peak. Notably, the  $\text{Ni}(0)$  complex is assigned to  $\text{Ni}(\text{dppe})_2$  in which the reaction  $1/K_0$  involves ligand exchange between  $\text{Cl}^-$  and dppe. We believe this is due to better stabilization of the  $\text{Ni}(0)$  state by the  $\pi$ -acceptor dppe ligand, rather than the  $\pi$ -donor  $\text{Cl}^-$ . Control experiments in which excess dppe ligand was added to a  $\text{Ni}(\text{dppe})\text{Cl}_2$  electrolyte solution found identical CV behavior as was obtained for excess  $\text{Cl}^-$  in  $[\text{Ni}(\text{dppe})_2]^{2+}$  solution (Fig. S6, ESI), thus confirming the formation of  $\text{Ni}(\text{dppe})_2$  at the  $\text{Ni}(0)$  state. The differing pathways for reduction and oxidation (EEC vs ECE) is due to the relatively slow kinetics for ligand transfer between  $\text{Cl}^-$  and dppe at the  $\text{Ni}(\text{I})$  state. This kinetic argument is supported by CVs which show that peak potentials and peak currents change as a function of scan rate, indicating that  $\text{Cl}^-$

/dppe ligand transfer occurs on the same time scale as the scan rate (Fig. S16, ESI).

To fully evaluate the suitability of  $[\text{Ni}(\text{dmpe})_2]^{2+}$  and  $[\text{Ni}(\text{dppe})_2]^{2+}$  as anolytes in RFBs, it is essential to investigate the complete charging and discharging of  $\text{Ni}(\text{II}/0)$  redox couples over an extended number of cycles. Extended CV cycling of nickel complexes in both electrolytes indicated no significant current loss, suggesting chemically reversible redox cycles. However, some nickel bis(diphosphine) complexes have been observed to decompose to nickel nanoparticles in the reduced state, resulting in chemically irreversible CVs following multiple cycles.<sup>19</sup> This observation was not found in the present molecules.

Charge-discharge cycling was performed for each complex for 25 cycles in a three-electrode electrochemical H-cell with carbon felt electrodes and 5 mM ferrocene in the catholyte chamber. Fig. 2a-b shows the complete charge-discharge cycling along with comparisons of the 2<sup>nd</sup> cycle for 1 mM  $[\text{Ni}(\text{dmpe})_2]^{2+}$  in MeCN with either 0.2 M TBAPF<sub>6</sub> or 0.2 M TBACI as the supporting electrolyte. Fig. 2c shows the capacity retention and coulombic efficiency measured for each cycle as a function of electrolyte conditions. In the case of 0.2 M TBAPF<sub>6</sub> electrolyte, the initial charge capacity was 0.53 mAh, corresponding to  $1.96\text{e}^-/\text{molecule}$ ; however, the capacity faded rapidly with increased cycle numbers, as seen by the compression of the data in time for Fig. 2a, losing 3.9%/cycle over the first 10 cycles and slowing to 2.3%/cycle for cycles 10-25. When TBACI was used as the supporting electrolyte, the initial capacity was the same as TBAPF<sub>6</sub> at 0.52 mAh ( $1.93\text{e}^-$

## COMMUNICATION

## ChemComm

/molecule), but the capacity fade rate decreased to 1.4%/cycle (**Fig. 2c**). We believe that the decrease in capacity fade is the result of more efficient conversion of  $[\text{Ni}(\text{dmpe})_2]^{2+}$  to  $\text{Ni}(\text{dmpe})_2\text{Cl}$ , resulting in a more complete ECE oxidation cycle. The charge-discharge potential also shifted negatively in the presence of  $\text{Cl}^-$ , from  $-1.39$  V with  $\text{TBAPF}_6$  to  $-1.50$  V with  $\text{TBACl}$ , matching our results from CV experiments. This change in potential results in a higher stored voltage when paired with the ferrocene catholyte in a two-electrode cell.

Chronopotentiometric cycling experiments performed using 1 mM  $[\text{Ni}(\text{dppe})_2]^{2+}$  in different electrolyte conditions (**Fig. 2d-f**) showed similar improvements to the capacity fade rate in the presence of  $\text{Cl}^-$ , decreasing from 0.76%/cycle in  $\text{TBAPF}_6$  to 0.38%/cycle in  $\text{TBACl}$ . Overall, the capacity fade rate was much lower for  $[\text{Ni}(\text{dppe})_2]^{2+}$  than  $[\text{Ni}(\text{dmpe})_2]^{2+}$  in both electrolytes, indicating higher stability despite the more complex ligand transfer steps. Most importantly, the presence of  $\text{Cl}^-$  consolidated the two distinct charging-discharge voltage plateaus observed in  $\text{TBAPF}_6$  into a single plateau consistent with a  $2\text{e}^-$  process. The new  $2\text{e}^-$  charge-discharge voltage was shifted  $-150$  mV with respect to the sequential  $1\text{e}^-$  path and achieved a higher charging capacity (0.54 mAh,  $2\text{e}^-$ /molecule). Both results represent an increase in the energy storage density in the context of an RFB.

The voltage observed in the presence of  $\text{Cl}^-$  is consistent with the first cathodic peak from CV experiments ( $E_{pc} = -0.98$  V). We therefore believe the  $2\text{e}^-$  charge-discharge behavior is due to efficient ligand transfer between  $\text{Cl}^-$  and dppe, converting  $[\text{Ni}(\text{dppe})\text{Cl}_2]^-$  to  $[\text{Ni}(\text{dppe})_2]^{2+}$  via the  $1/K_1$  chemical step. The efficiency of this step is likely a consequence of the relatively low charging current of 1 mA in which ample time is given for ligand transfer to occur. Further studies are underway to vary the applied current and understand the impacts of ligand transfer on RFB cycling.

Comparing the  $[\text{Ni}(\text{dmpe})_2]^{2+}$  and  $[\text{Ni}(\text{dppe})_2]^{2+}$  complexes in the context of an RFB, they both achieve  $2\text{e}^-$  storage at a single charge-discharge potential in the presence of  $\text{TBACl}$  electrolyte and both benefit from a negative voltage increase due to chloride coordination. The dmpe complex has a larger charge-discharge potential at  $-1.50$  V, compared to  $-0.98$  V for the dppe complex. However, the dppe complex is much more stable over multiple charge-discharge cycles. Both complexes exhibit moderate solubility in MeCN in the  $\text{Ni}(\text{II})$  oxidation states, 130 mM for  $[\text{Ni}(\text{dmpe})_2]^{2+}$  and 6 mM for  $[\text{Ni}(\text{dppe})_2]^{2+}$  with 0.2 M  $\text{TBAPF}_6$ . These solubilities increase to 320 mM and 10 mM with 0.2 M  $\text{TBACl}$ , respectively. Coupling these solubilities with the  $2\text{e}^-$  storage capabilities of both complexes, theoretical maximum charge densities of 17.2 Ah/L for  $[\text{Ni}(\text{dmpe})_2]^{2+}$  and 0.5 Ah/L for  $[\text{Ni}(\text{dppe})_2]^{2+}$  can be calculated.

The storage of  $2\text{e}^-$  at a single potential versus sequential  $1\text{e}^-$  redox events is an important distinction. The former offers the advantage of a consistent charge-discharge voltage profile and a greater energy efficiency by compressing the voltage profile over a narrower range. However, developing such redox couples with inorganic complexes requires ECE redox cycles which undergo coordination changes in their chemical steps. This can result in inefficiencies in the redox cycle or can invite

degradation pathways due to changes in coordination environment. Understanding and controlling mechanisms for two-electron redox cycles is therefore critically important to developing multi-electron inorganic redox-active molecules for applications in RFBs.

## Conflicts of interest

There are no conflicts to declare.

## Data availability

The data supporting this article have been included as part of the ESI.†

## References

- Zhu, Z.; Jiang, T.; Ali, M.; Meng, Y.; Jin, Y.; Cui, Y.; Chen, W. *Chem. Rev.* **2022**, *122* (22), 16610–16751.
- Gür, T. M. *Energy Environ. Sci.* **2018**, *11* (10), 2696–2767.
- Dunn, B.; Kamath, H.; Tarascon, J.-M. *Science* **2011**, *334*, 928–935.
- Yang, Z.; Zhang, J.; Kintner-Meyer, M. C. W.; Lu, X.; Choi, D.; Lemmon, J. P.; Liu, J. *Chem. Rev.* **2011**, *111* (5), 3577–3613.
- Li, L.; Kim, S.; Wang, W.; Vijayakumar, M.; Nie, Z.; Chen, B.; Zhang, J.; Xia, G.; Hu, J.; Graff, G.; Liu, J.; Yang, Z. *Adv. Energy Mater.* **2011**, *1* (3), 394–400.
- Noack, J.; Roznyatovskaya, N.; Herr, T.; Fischer, P. *Angew. Chem. Int. Ed.* **2015**, *54* (34), 9776–9809.
- Lopez-Atalaya, M.; Codina, G.; Perez, J. R.; Vazquez, J. L.; Aldaz, A. *J. Power Sources* **1992**, *39* (2), 147–154.
- Lourenssen, K.; Williams, J.; Ahmadpour, F.; Clemmer, R.; Tasnim, S. *J. Energy Storage* **2019**, *25*, 100844.
- Xie, C.; Duan, Y.; Xu, W.; Zhang, H.; Li, X. *Angew. Chem. Int. Ed.* **2017**, *56* (47), 14953–14957.
- Huskinson, B.; Marshak, M. P.; Suh, C.; Er, S.; Gerhardt, M. R.; Galvin, C. J.; Chen, X.; Aspuru-Guzik, A.; Gordon, R. G.; Aziz, M. J. *Nature* **2014**, *505* (7482), 195–198.
- Lin, K.; Chen, Q.; Gerhardt, M. R.; Tong, L.; Kim, S. B.; Eisenach, L.; Valle, A. W.; Hardee, D.; Gordon, R. G.; Aziz, M. J.; Marshak, M. P. *Science* **2015**, *349* (6255), 1529–1532.
- Shin, S.-H.; Yun, S.-H.; Moon, S.-H. *RSC Adv.* **2013**, *3* (24), 9095–9116.
- Mazumder, Md. M. R.; Dalpati, N.; Pokkuluri, P. R.; Farnum, B. H. *Inorg. Chem.* **2022**, *61* (48), 19039–19048.
- Jude, H.; Krause Bauer, J. A.; Connick, W. B. *J. Am. Chem. Soc.* **2003**, *125* (12), 3446–3447.
- Waldie, K. M.; Ramakrishnan, S.; Kim, S.-K.; McLaren, J. K.; Chidsey, C. E. D.; Waymouth, R. M. *J. Am. Chem. Soc.* **2017**, *139* (12), 4540–4550.
- Pierce, D. T.; Geiger, W. E. *J. Am. Chem. Soc.* **1989**, *111* (19), 7636–7638.
- Berning, D. E.; Noll, B. C.; DuBois, D. L. *J. Am. Chem. Soc.* **1999**, *121* (49), 11432–11447.
- McLaughlin, M. P.; McCormick, T. M.; Eisenberg, R.; Holland, P. L. *Chem. Commun.* **2011**, *47* (28), 7989–7991.
- J. Lee, K.; M. Lodaya, K.; T. Gruninger, C.; S. Rountree, E.; L. Dempsey, J. *Chem. Sci.* **2020**, *11* (36), 9836–9851.
- Gross, M. A.; Reynal, A.; Durrant, J. R.; Reisner, E. *J. Am. Chem. Soc.* **2014**, *136* (1), 356–366.

**Data Availability Statement:**

The data supporting this article have been included as part of the Supplementary Information.