

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Multi-stimuli Responsive Self-healing Metallo-Hydrogels: Tuning of the Gel Recovery Property

Shibaji Basak, Jayanta Nanda and Arindam Banerjee^{*a}

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

A series of amphiphilic tyrosine based self-healable, multi-stimuli responsive metallo-hydrogels have been discovered. Formation of these hydrogels is highly selective to Ni²⁺ ions. The self-healing property and the stiffness of these metallo-hydrogels can be tuned by varying the chain length of the corresponding gelator amphiphile.

Peptide/ amino acid based supramolecular gels¹ composed of low-molecular weight gelators are an important field of current research. These gelator molecules are self-assembled using various non-covalent interactions such as hydrogen bonding, π - π interaction, hydrophobic interaction and others to form a fibrillar network structure that is occupied by solvent molecules to form gels under a suitable condition. These non-covalent interactions are weak in nature and they can be broken and reformed in response to the various external stimuli² such as heat, pH of the medium, external chemicals, sonication, mechanical force and irradiation by light. Stimuli responsiveness of these soft gel materials with highly permeable network structure offers potential applicability^{1,3} in drug delivery, regenerative medicine, nanoparticle and nanoclusters synthesis and other fields. It is well known that peptides or amino acids form complexes with various transition metals.⁴ The side chain of tyrosine, plays a crucial role for the stability of the metal complex. This is due to the possibility of coordination of the hydroxyl group at the 4-position of aromatic ring in addition to the carboxylate and amino group. The hydrophobic surface of the phenyl ring also shields the attack of water molecules in aqueous medium.⁵ Sometimes metal ions triggered the self-assembly of peptides and amino acid derivatives to form supramolecular metallo-gels.⁶ Metallo-gelators belong to a special class of gelators due to their quick response to various stimuli. Diverse kind of molecules are found to form metallo-gels including cholesterol derivatives, pyridine complexes and various metal organic frameworks (MOFs). Moreover, self-healable supramolecular soft materials⁷ are one of the emerging field in advanced material research. Self-healing gels are able to partially or completely repair the damage imposed on them and the original structure can be restored. There are several examples of self-healing gels based on clay-composite, polymer and nano-composite and others. The modulation of the self-healing property in gels always remains to be a challenging task. However, none of the above mentioned

examples corresponds to multi-stimuli responsive metallo-hydrogel with self-healing property. So, there is a genuine need for the discovery of a common structural motif which shows multi-stimuli responsive metallo-gel formation with a self-healing property and tuning of the self-repairing property by the variation of the gelator structure keeping basic nature of the gelator molecules same.

In this report, a series of tyrosine based amphiphiles⁸ P₁–P₃ (Fig. 1a) have been found to form hydrogels in aqueous phosphate buffer solutions (pH 7.0 to 8.0) in presence of Ni²⁺ ions. These metallo-hydrogels exhibit remarkable self-healing property. The self-healing property of these hydrogels can be nicely tuned by varying the chain length of these amphiphiles. These metallo-hydrogels exhibit multi-stimuli responsiveness towards various stimuli including pH of the medium, temperature, mechanical forces and external chemicals.

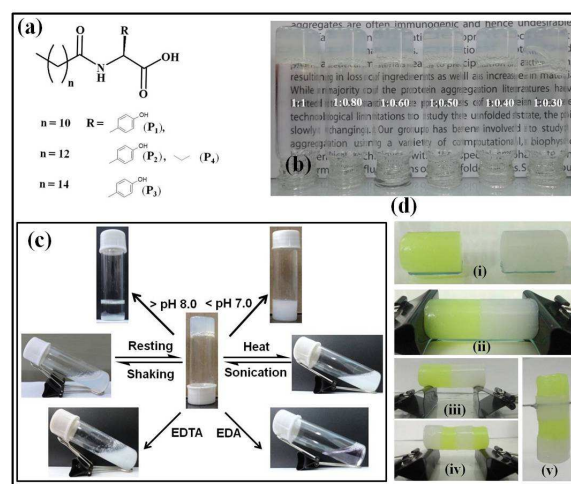


Figure 1. (a) Chemical structures of various amphiphiles (P₁–P₄). (b) Pictures of glass vials containing metallo-hydrogels obtained from different proportions of the P₃ and nickel salt (NiCl₂). (c) Multi-stimuli responsiveness shown by the hydrogel obtained from P₃. (d) Illustration of self-healing behavior (i–v) shown by the metallo-hydrogel obtained from P₃.

Amphiphiles P₁–P₃ are self-assembled in aqueous phosphate buffer solutions of pH ranging from 7.0 to 8.0 in

presence of Ni^{2+} ions to form translucent hydrogel. These amphiphiles were first dissolved in phosphate buffer solution by heating; then NiCl_2 was added concomitantly to this solution. It was turned into white coloured suspension upon the addition of NiCl_2 . These mixtures were then sonicated for a few minutes to produce a clear solution and kept at room temperature without any disturbance to form hydrogels. The amphiphile P_3 form gel within a few minutes. However, amphiphiles P_2 and P_1 form gel after 3 hr. and 18 hr. of standing respectively. These metallo-hydrogels are stable over several months. Without Ni^{2+} ions, on standing or on sonication all these amphiphiles get precipitate from the solution. To investigate the effective ratio of the gelator and Ni^{2+} ions for gelation, the Ni^{2+} ion concentration was systematically decreased keeping the concentration (10 mM) of the gelator P_3 fixed (Fig. 1b). By varying gelator: Ni^{2+} ion ratio it was observed that the gelation was taken place from 1: 1 to 1: 0.3 ratio of gelator: Ni^{2+} ions. The opacity of the metallo-gels increases by increasing the Ni^{2+} ion concentration. An increase in gelator: Ni^{2+} ion ratio above 1: 1 causes precipitation while the decrease of this ratio below 1: 0.3 results in a viscous solution with no gel formation. Other two gelators have also shown similar behaviour (not shown here). In order to examine further structural effect (regarding the substitution of the amino acid) on gelation, P_4 (Fig. 1a) was synthesized and tested for gelation. However, P_4 was unable to form any type of gel in similar conditions. All amphiphiles are unable to form any kind of hydrogel in presence of other metal ions such as Zn^{2+} , Cu^{2+} , Co^{2+} , Mn^{2+} , Fe^{2+} and Hg^{2+} . The gelation of these amphiphiles has also been studied by using NiSO_4 and $\text{Ni}(\text{ClO}_4)_2$ separately. However, no significant change in gel formation has been noticed. This precludes the possibility of anion effect in gelation. So, it can be stated that metallo-hydrogelation is very much selective and specific not only for the tyrosine based amphiphiles but also for the presence of Ni^{2+} . The minimum gelation concentration (MGC) of the metallo-hydrogels were found to be at 10 mM, 9 mM and 7 mM at 1: 0.5 ratio for P_1 , P_2 and P_3 respectively.

The morphological features of these metallo-hydrogels were investigated by TEM studies. TEM images (Fig. S13, ESI†) vividly indicate that these metallo-hydrogels form thick tape like nanofibrillar network structures with different widths for different hydrogels. Widths of these nanofibers are ranging from 60-80 nm, 60-70 nm and 120-150 nm for P_1 , P_2 and P_3 gelators respectively.

These hydrogels are highly sensitive to pH and stable within the pH range 7.0 to 8.0. Above pH 8.0 these gelators form solutions and after 3-4 hr. they are precipitated and below pH 7.0 these gelators form suspensions (Fig. 1c). The thermal behavior of these metallo-hydrogels have been studied by measuring the gel melting temperature (T_{gel}) at different ratio of gelators to Ni^{2+} ions (Fig. S14, ESI†). Above the T_{gel} , all these gels are turned into solution and the nickel hydroxide is precipitated out. Due to the least solubility of nickel hydroxide in water the whole solution is turned into a white colored suspension (Fig. 1c). This suspension is transformed into metallo-hydrogel by cooling it to room temperature (25

$^{\circ}\text{C}$) followed by sonication. However, below room temperature the gel phase remains intact (upto 5 $^{\circ}\text{C}$ was studied). The T_{gel} of the metallo-hydrogels increases with an increase in the concentration of Ni^{2+} ions upto a certain value, then it decreases upon further increase in Ni^{2+} ion concentration keeping the pH (7.46) constant. It is observed that the T_{gel} reaches to the maximum value at the ratio 1: 0.5 of gelator: Ni^{2+} ions. These metallo-hydrogels are sensitive to suitable metal chelating agents like ethylene diamine (EDA) or EDTA. Gel to sol transformation occur in presence of EDA while gel to precipitate occurs in presence of EDTA (Fig. 1c) indicates the chemical responsiveness of these metallo-hydrogels.

The gel-sol transformation can also be achieved by the application of mechanical force (Fig. 1c). These hydrogels are transformed into solution upon the application of mechanical forces such as vigorous shaking but regained by the complete withdrawal of the mechanical force and keeping the solution at room temperature without any disturbance. Interestingly, these metallo-hydrogels have shown significant self-healing property. These hydrogels can be recovered from any damage imposed on them. The time needed to recover the gel state is highly dependent on the chain length of the corresponding gelator amphiphiles. Thus self-healing property can be nicely tuned by changing the chain length of these amphiphiles. It was noticed that the hydrogel obtained from P_3 reform immediately (within 1 min.) after it was broke. Other two amphiphiles P_1 and P_2 reformed within 8 min. and 5 min. respectively. The self-healing property was explored (Fig. 1d) by cutting the gels into two round-shaped pieces with a razor and then these pieces were put together with a moderate press. It was found that after 25-30 min. these parts merged into a continuous block for all hydrogels. This fused block then could be suspended in air (Fig. 1d, iii-v) or can be stretched by pulling the two ends as shown in the fig. S15, ESI†. Similarly, the self-healing property of other two gels obtained from gelators P_1 and P_2 is illustrated in fig. S16, ESI†.

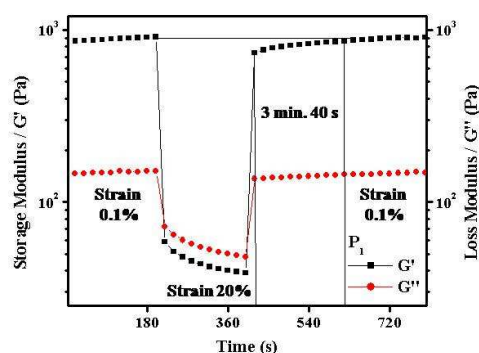


Figure 2. The step strain experiment data obtained from P_1 metallo-hydrogel. Concentration was maintained at 10 mM in 1:0.5 gelator and Ni^{2+} ratio respectively.

Fig. S17a shows the variations of G' and G'' against angular frequency (ω) of each gelator (10 mM). G' and G'' do not vary significantly with the range of applied angular frequency (ω)

and do not cross each other ($G' > G''$) throughout the experimental region. This indicates the presence of a stable and rigid gel phase material. Interestingly, the stiffness of these metallo-gels increases upon increasing the alkyl chain length of gelator molecules. It is evident from the rheological experiments (Fig. S17a, ESI†) that the rigidity of the metallo-gel is as follows: $P_1 < P_2 < P_3$. There are only a few reports on the control of stiffness of gels by incorporating of carbon based nanomaterial(s)⁷ into the native gels. However, controlling the gel stiffness by simply varying the alkyl chain length of amphiphile is not yet been reported.

Simple step strain experiment⁹ was performed for all these metallo-gels (10 mM) in several steps (Fig. 2 and S17, ESI†). At first gels were subjected to a constant strain of 0.1% (step 1). Then the strain was increased from 0.1% to 20% and was kept for a few minutes at 20% strain to break gels completely (step 2). Then the strain was decreased from 20% to 0.1% again and kept it for a few minutes at a 0.1% to observe the gel restoration kinetics (step 3). The angular frequency was kept constant at 1 rad/sec throughout the three steps of the entire experiment. It was observed that the loss modulus values (G'') were greater than the storage modulus (G') values when the constant strain was 20% indicating the sol-like nature of these gels during the second interval of the experiment. Immediately after removing the 20% strain, P_1 , P_2 and P_3 gels were recovered 80%, 80% and 83% of their original stiffness respectively (Fig. 2 and S17, ESI†). Interestingly, the complete recovery time was estimated to be 3 min. 40s for the P_1 hydrogel, while rest two metallo-gels obtained from P_2 and P_3 were 4 min. 40s and 6 min. respectively. The recovery time was calculated from the point of the withdrawal of 20% strain after the complete breakage of the gel till to the point the gel phase was repairing again and restores its 100% strength in the third interval of the step strain experiment.

Fourier transform infrared (FT-IR) spectra in non-gel state (without Ni^{2+} ions) and in gel state (in presence of Ni^{2+} ions) was almost identical except for the -OH stretching frequency of the side chain tyrosine moiety (Table S1). The -OH stretching frequency of the tyrosine moiety of P_3 appeared at 3440 cm^{-1} in non-gel state. However, in the gel state this peak was shifted to around 3400 cm^{-1} (Fig. S18, ESI†). The -OH stretching frequency for other two gelators P_1 and P_2 appeared at 3425 cm^{-1} and 3415 cm^{-1} respectively. These values indicate that the tyrosine -OH is involved in the hydrogen bond formation in the gel network.

The small angle X-ray scattering (SAXS) was performed to examine the molecular assembly in gel state. In SAXS (Figure S19a) peaks found at $2\theta = 4.35^\circ$, 3.9° and 3.4° with the corresponding d spacing values of 20.15 Å, 22.5 Å and 25.8 Å for gelators P_1 , P_2 and P_3 respectively. This values matches well with the calculated molecular length of these individual gelator molecules. In the wide angle region (Fig. S19b, ESI†) many sharp peaks were observed for all these gelators and each of these peaks were matches well with the pure nickel hydroxide X-ray diffraction pattern.¹⁰ Thus, it is evident from the XRD data that nickel hydroxide was formed in phosphate buffer medium (pH 7.46).

Results of XRD studies of all these amphiphiles (P_1 - P_3) indicate that the nickel hydroxide is formed after the addition of $NiCl_2$ salt into the buffer solution of these amphiphiles. FT-IR studies indicate that the tyrosine -OH is hydrogen bonded to the nickel complex in the gel state as it is evident from the significant red shift of the tyrosine -OH peak and in non-gel state this phenolic -OH of tyrosine residue remains unaffected. Other peaks of these gelator molecules remain unchanged in presence of Ni^{2+} ions. This study clearly suggests that the carboxylate oxygen and amide -NH of these gelators are not interacting with Ni^{2+} ions and it is the tyrosine -OH that is interacting with the hydrated nickel complex. A schematic representation for the self-assembly of these metallo-hydrogel formation is shown in the fig. S20, ESI† illustrating the stepwise assembly of the gelator molecules to form a tape like network structure.

In conclusion, a series of tyrosine based multi-stimuli responsive self-healing metallo-hydrogels have been discovered. These hydrogels have shown stimuli responsiveness towards heat, mechanical shaking, pH of the medium and external chemicals. Remarkably, these metallo-hydrogels exhibit self-healing property and the self-healing property has been successfully tuned by varying the alkyl chain length of these gelator molecules. In this study, we have not only identified the specific motif (tyrosine based amphiphiles with varied alkyl chain length) for metallo-hydrogelation but also modulated the self-healing property of these gels by changing the alkyl chain length of these gelators. This multi-stimuli responsive self-healable nickel containing hydrogels holds the future promise to make stimuli responsive self-healable smart materials.

Notes and references

- ^aDepartment of Biological Chemistry, Indian Association for the Cultivation of Science, Jadavpur, Kolkata - 700 032, India.
Fax: +91-332473-2805; Tel: +91-332473-4971;
E-mail: bcab@iacs.res.in
- ⁹† Electronic Supplementary Information (ESI) available: See DOI: 10.1039/b000000x/
- 1 I. W. Hamley, *Angew. Chem.* **2007**, *119*, 8274-8295; *Angew. Chem. Int. Ed.* **2007**, *46*, 8128-8147; V. Castelletto, G. Cheng and I. W. Hamley, *Chem. Commun.* **2011**, *47*, 12470-12472; C. A. Lagadec and D. K. Smith, *Chem. Commun.* **2012**, *48*, 7817-7819; J. Raeburn, T. O. McDonald and D. J. Adams, *Chem. Commun.* **2012**, *48*, 9355-9357; N. M. Sangeetha and U. Maitra, *Chem. Soc. Rev.* **2005**, *34*, 821-836; A. R. Hirst, B. Escuder, J. F. Miravet and D. K. Smith, *Angew. Chem. Int. Ed.* **2008**, *47*, 8002-8018; S. Bhattacharya, A. Srivastava and A. Pal, *Angew. Chem.* **2006**, *118*, 3000-3003; *Angew. Chem. Int. Ed.* **2006**, *45*, 2934-2937; A. Pal, B. S. Chhikara, A. Govindaraj, S. Bhattacharya and C. N. R. Rao, *J. Mater. Chem.* **2008**, *18*, 2593-2600.
 - 2 M. D. S-Maset, V. J. Nebot, J. F. Miravet and B. Escuder, *Chem. Soc. Rev.* **2013**, *42*, 7086-7098; L. Frkanec, M. Jokić, J. Makarević, K. Wolsperger and M. Žinić, *J. Am. Chem. Soc.* **2002**, *124*, 9716-9717; Z-X. Liu, Y. Feng, Z-C. Yan, Y-M. He, C-Y. Liu and Q-H. Fan, *Chem. Mater.* **2012**, *24*, 3751-3757.
 - 3 G. Liang, Z. Yang, R. Zhang, L. Li, Y. Fan, Y. Kuang, Y. Gao, T. Wang, W. W. Lu and B. Xu, *Langmuir* **2009**, *25*, 8419-8422; J. Naskar, G. Palui and A. Banerjee, *J. Phys. Chem. B*, **2009**, *113*, 11787-11792; J. Nanda and A. Banerjee, *Soft Matter* **2012**, *8*, 3380-3386; B. Adhikari and A. Banerjee, *Chem. Eur. J.* **2010**, *16*, 13698-13705; S. Basak, J. Nanda and A. Banerjee, *J. Mater. Chem.* **2012**, *22*, 11658-11664; J. Nanda, A. Biswas, B. Adhikari and A. Banerjee,

- Angew. Chem.* **2013**, *125*, 5145-5149; *Angew. Chem. Int. Ed.* **2013**, *52*, 5041-5045.
- 4 R. B. Martin, M. Chamberlin and J. T. Edsall, *J. Am. Chem. Soc.* **1960**, *82*, 495-498; H. C. Freeman, J. M. Guss and R. L. Sinclair, *Chem. Commun.* **1968**, 485-487; K. Severin, R. Bergs and W. Beck, *Angew. Chem. Int. Ed.* **1998**, *37*, 1634-1654.
- 5 O. Yamauchi and A. Odani, *J. Am. Chem. Soc.* **1985**, *107*, 5938-5945; S. Medici, M. Peana, V. M. Nurchi and M. A. Zoroddu, *Molecules* **2013**, *18*, 12396-12414.
- 10 6 A. Y-Y. Tam and V. W-W. Yam, *Chem. Soc. Rev.* **2013**, *42*, 1540-1567; A. Chakrabarty, U. Maitra and A. D. Das, *J. Mater. Chem.* **2012**, *22*, 18268-18274; S. Samai and K. Biradha, *Chem. Mater.* **2012**, *24*, 1165-1173; A. Mallick, E-M. Schön, T. Panda, K. Sreenivas, D. D. Díaz and R. Banerjee, *J. Mater. Chem.* **2012**, *22*, 14951-14963; C. M. Micklitsch, P. J. Knerr, M. C. Branco, R. Nagarkar, D. J. Pochan and J. P. Schneider, *Angew. Chem.* **2011**, *123*, 1615-1617; *Angew. Chem. Int. Ed.* **2011**, *50*, 1577-1579; S. Ray, A. K. Das and A. Banerjee, *Chem. Mater.* **2007**, *19*, 1633-1639; W. L. Leong, A. Y-Y. Tam, S. K. Batabyal, L. W. Koh, S. Kasapis, V. W-W. Yam and J. J. Vittal, *Chem. Commun.* **2008**, 3628-3630.
- 7 B.J. Blaiszik, N.R. Sottos and S.R. White, *Comp Sci Tech* **2008**, *68*, 978-986; C. J. Hansen, S. R. White, N. R. Sottos and J. A. Lewis, *Adv. Funct. Mater.* **2011**, *21*, 4320-4326; S. Neuser, V. Michaud and S.R. White, *Polymer* **2012**, *53*, 370-378; Q. Wang, J. L. Mynar, M. Yoshida, E. Lee, M. Lee, K. Okuro, K. Kinbara and T. Aida, *Nature* **2010**, *463*, 339-343; C. Hou, Y. Duan, Q. Zhang, H. Wang and Y. Li, *J. Mater. Chem.* **2012**, *22*, 14991-14996; A. Vidyasagar, K. Handore and K. M. Sureshan, *Angew. Chem.* **2011**, *123*, 8171-8174; *Angew. Chem. Int. Ed.* **2011**, *50*, 8021-8024; S. Roy, A. Baral and A. Banerjee, *Chem. Eur. J.* **2013**, *19*, 14950-14957; J. Yuan, X. Fang, L. Zhang, G. Hong, Y. Lin, Q. Zheng, Y. Xu, Y. Ruan, W. Weng, H. Xia and G. Chen, *J. Mater. Chem.* **2012**, *22*, 11515-11522.
- 8 E. Dinda, M. Biswas and T. K. Mandal, *J. Phys. Chem. C*, **2011**, *115*, 18518-18530.
- 35 9 N. T. Qazvini, S. Bolisetty, J. Adamcik and R. Mezzenga, *Biomacromolecules* **2012**, *13*, 2136-2147.
- 10 P. Oliva, J. Leonard and J. F. Laurent, *Journal of Power Sources* **1982**, *8*, 229-255; S. Chen, J. Duan, Y. Tang and S. Z. Qiao, *Chem. Eur. J.* **2013**, *19*, 7118-7124.
- 40