

PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Viologen based ionic liquid crystals: induction of a smectic A phase by dimerisation

Girolamo Casella^{a,†}, Valerio Causin^a, Federico Rastrelli^a, and Giacomo Saielli^{a,b}

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

The stability of thermotropic ionic liquid crystals is essentially due to micro-phase segregation between the ionic head and the long alkyl chains. Here we show, using newly synthesized viologen dimers, that the structure of the central core is another key parameter to play with in order to tune the mesomorphic behaviour.

Ionic liquid crystals (ILCs) have recently attracted the attention of the chemistry and materials science communities as systems with the potential to combine together the many applications and features of liquid crystals (LCs) and ionic liquids (ILs), see Ref.¹ for a comprehensive review and Refs.^{2,3} for more recent updates on the subject. ILCs are usually obtained from organic salts of quaternized nitrogen, the same class of compounds forming ILs, after a sufficient lengthening of the alkyl chain(s).^{4,5} In a recent paper, the role of the chains in driving the formation of imidazolium ILCs has been highlighted by MD simulations and the emergence of a smectic phase for chains longer than C12 was nicely reproduced.⁶ Since the driving force is believed to be the micro-segregation between the hydrophobic chains and the ionic layers, a smectic phase (for calamitic systems) is almost invariably obtained,⁷ though rare cases of ionic nematic phases have been reported.⁸⁻¹⁰

The modulation of the thermal range of stability and type of ILC phase is very important for the optimization of their performance, together with the tuning of properties like viscosity and conductivity. ILCs have been successfully tested recently for applications in the field of solar cells,¹¹ membranes for water desalination,¹² battery materials¹³ and electrochemical sensors.^{14,15} The conductive properties of the ionic mesophase have been found to have a significant impact on the performance of the ILC based devices compared to the analogous devices based on isotropic ILs. Recent MD simulations have highlighted the role played by pore-like defects in enhancing the diffusion, and therefore the conductivity, along the director in smectic ILCs.^{16,17} Nevertheless, our understanding of the properties of ILCs is still poor.

The design of novel ILCs with improved properties (notably lower viscosity and lower melting temperature) has, in most cases, regarded the exploration of the type of cationic head, length and type of chains and type of counter-anion but often remaining within the paradigm of an amphiphilic organic cation, with an ionic head and an alkyl chain, paired with a roughly spherical inorganic anion. Notable digressions with respect to this

route have been pursued by Ringstrand et al.¹⁰ and Laschat and co-workers¹⁸ who focussed on different kind of “mesogenic” anions.

In this work, starting from our previous investigations,¹⁹⁻²¹ we present a series of symmetric viologen dimers **n.m.n**, where *n* and *m* indicate the number of carbon atoms in the lateral and middle (spacer) alkyl chains, respectively, see Figure 1. We found that they exhibit a rich polymorphism including the ionic smectic A phase and an ordered smectic phase, SmX, which we believe to be characteristic of ionic liquid crystals with a polycationic core. Moreover, the viologen core is a key component to impart solvatochromic and red-ox properties in view of possible applications of these materials.²²




Fig. 1 Structure of the tetracationic viologen dimers investigated, **n.m.n**=nBPmBPn(Tf₂N)₄, where BP is the bipyridinium core. For *n*, *m* pairs see Table 1. Tf₂N⁻ is (CF₃SO₂)₂N⁻ (bistriflimide). Dicationic monomers, **n.m**, contain a single bipyridinium unit.

Table 1. Thermodynamic properties of the samples investigated. Transition temperatures T_n / °C (ΔH / kJ/mol). H: 1st Heating; C: 1st Cooling.

n.m.n		H T ₁ (ΔH ₁)		H T ₂ (ΔH ₂)		H T ₃ (ΔH ₃)	
		C T ₁ (ΔH ₁)		C T ₂ (ΔH ₂)		C T ₃ (ΔH ₃)	
14.2	Cr	71 (6.7)	Iso				
12.4.12	Cr	88 (23.6)	SmX	154 (17.7)	SmA	183 (7.3)	Iso
		24 (7.1)		148 (16.8)		174 (5.8)	
14.4.14	Cr	84 (23.2)	SmX	153 (20.0)	SmA	229 (10.0)	Iso
		19 (32.0)		143 (16.8)		209 (2.6)	
16.4.16	Cr	79 (20.6)	SmX	152 (18.2)	SmA	264 (6.8)	Iso
		19 (37.8)		143 (15.9)		248 (3.9)	
14.14	Cr	42 (49.1)	SmX	218 (15.2)	Iso		
		33 (30.3)		214 (13.2)			

Synthetic procedures are described in ESI. Two routes are available: *i*) first the central core is obtained by reacting an excess of α,ω-dihaloalkane with bipyridine; the intermediate is then dialkylated with the long-chain haloalkane; *ii*) first a monoalkylated bipyridine is made, which is then reacted with the α,ω-dihaloalkane to obtain the monomer; a second reaction with the monoalkylated bipyridine affords the final product. The latter route allows the synthesis of non-symmetric monomers. In Table 1 we report the thermodynamic data for the viologen dimers with a spacer of four carbons plus two monomers useful for a direct

comparison. In particular, **14.2** is formally the monomeric unit of the dimer **14.4.14**, while **14.14** is the analogous symmetric monomer with the same lateral chain. The histograms of the thermal range of stability of the phases are shown in Figure 2.

As noted already in Ref.²⁰ strongly non-symmetric monomeric viologen salts of bistriflimide do not exhibit any mesophase, rather they behave as ILs. This is the behaviour observed here for **14.2**, see the typical crystal textures in ESI (Fig. S27). In contrast, when the number of carbon atoms increased, an ordered smectic phase, SmX, was found that was not completely identified: POM, XRD²⁰ and solid-state NMR²¹ ruled out a smectic A phase and suggested an ordered, layered mesophase. This behaviour has been confirmed here for the sample **14.14** whose optical textures are of mosaic type and striated fan-shaped type (see ESI, Fig. S24),²³ thus suggesting an ordered smectic phase.

We now turn our attention to the dimeric viologen systems, particularly the **14.4.14** salt which can be directly compared with either its formal monomeric unit, **14.2** or the symmetric monomer with the same lateral alkyl chain length, **14.14**.

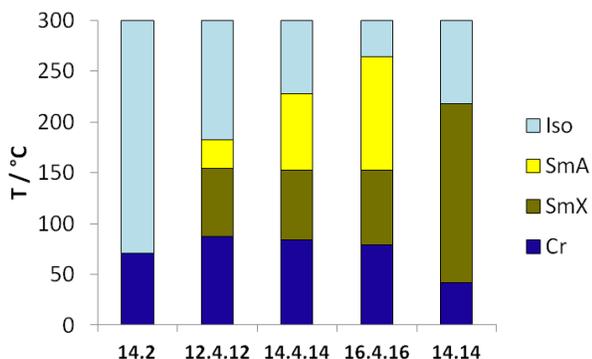


Fig. 2. Thermal range of stability of the systems investigated.

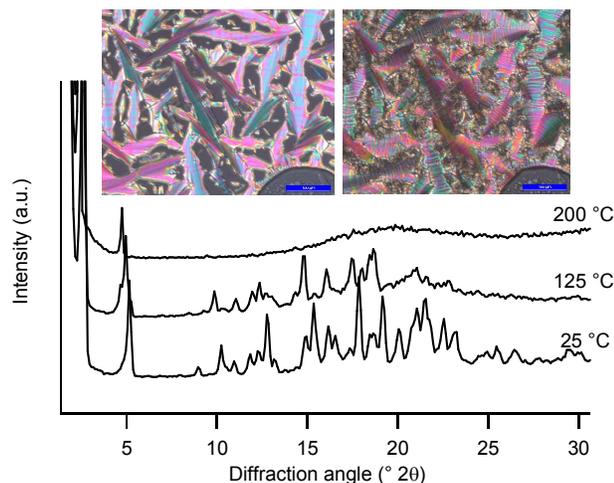


Fig. 3. XRD traces of **14.4.14** at three different temperatures corresponding to the Cr, SmA and SmX phases. Inset: left) fan-shaped textures of the SmA phase at 150 °C; right) striated fan-shaped textures of the ordered SmX phase at 120 °C. The blue bar is 100 μm.

In Figure 3 we show the XRD profiles at various temperatures corresponding to the three phases, except the liquid phase which only shows a broad halo around $2\theta \sim 20^\circ$. These traces indicate a crystal phase at room temperature; an ordered mesophase at 125 °C since, together with a broad halo around $2\theta \sim 20^\circ$, we have

several strong reflections indicating the coexistence of short range order;²⁴ a SmA phase at 200 °C since, apart from a first order peak and a weak second order one, there is only the broad halo indicating the lack of short range order. The small angle region of the first order peak due to the layered structure is clearly visible in Fig. S21 in ESI. The layer periodicity is found to be 33.3 Å, 34.6 Å and 37.6 Å, increasing as the system goes from the crystal phase into the SmX and finally into the high temperature SmA phase. The thickness is much smaller than the full elongation of the cation: for **14.4.14** the distance between the two methyl carbons in the all-trans arrangement is 51.6 Å (semiempirical PM3 calculations). Therefore a significant degree of interdigitation occurs in all the three phases.

The assignment of the SmA phase is confirmed by the fan-shaped textures observed on cooling from the melt (see Figure 3) and by the fluidity of the sample under the microscope, while no flow was observed after lowering the temperature below the SmA-SmX transition; moreover, the textures, once the sample cooled down into the SmX phase, changed into a striated fan-shaped type, as observed for **14.14**, which are typical of ordered smectic phases, with a higher degree of order than a SmB.²³ This would also explain the absence, in the XRD traces, of the typical sharp peak around $2\theta \sim 20^\circ$ expected in the hexagonal smectic B phase.

The XRD traces and POM images of **12.4.12** are shown in ESI (Fig. S23 and S25) and, again, clearly indicate a SmA phase at higher temperature and an ordered smectic phase at lower temperatures. Similarly to the former compound, the layer thickness is significantly shorter than the molecular length. An analogous behaviour is found for **16.4.16**.

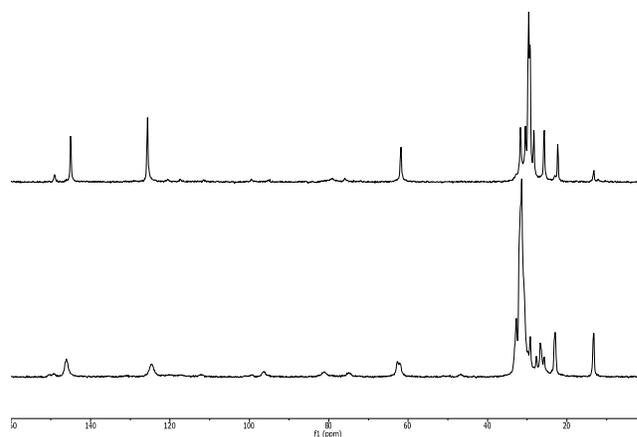


Fig. 4 SSNMR ^1H - ^{13}C CP-MAS spectra of **14.14** (100 MHz).

To get further insights on the structure of the SmX phase we acquired solid-state ^{13}C NMR spectra (SSNMR) of **14.14**, whose Cr-SmX transition occurs at sufficiently low temperature. They are reported in Figure 4. The spectra obtained just before and after the Cr-SmX transition (see full data in ESI, Figs. S5 and S6) show the same features seen in Ref.²¹ for the room temperature crystal and SmX phase of **8.8** and **7.10**, respectively. In the crystal phase we observe broad signals in the aromatic region and an almost unnoticeable signal of the CF_3 carbon of the anion; in the high temperature SmX phase the aromatic resonances are much sharper, indicating an enhanced mobility, though

anisotropic, and the two central lines of the 1:3:3:1 quartet of CF_3 at 118 ppm are now resolved, although weak; the increased mobility is also confirmed by the reduction of the intensity of the spinning side bands due to a partial averaging of the chemical shift anisotropy. Moreover, the intensity of the resonance of the methyl group at 13 ppm is strongly reduced, after the transition, suggesting an almost complete isotropic melting of the alkyl region. In fact the liquid-like phase of the alkyl region averages the C-H dipolar coupling responsible for the cross-polarisation of the methyl resonances. Despite this, the XRD traces of **14.14** (see Fig. S22 in ESI) clearly indicate that the smectic phase is not a SmA since short range order is present, together with the broad halo, in perfect agreement with the behaviour of the monomeric viologens studied in Ref. ²⁰; since the hydrophobic layers of the lateral alkyl chains are highly disordered, such order is likely due to a partial structure of the ionic layers.

The overall picture that emerges from these observations is of a rich mesomorphism exhibited by bistriflimide viologen salts which is summarised in the schematic representation of Figure 5.

Besides the low temperature crystal phase and high temperature isotropic phase, two smectic phases have been identified. For dimers, a SmA phase exists whose thermal range of stability grows into the isotropic phase region with increasing the length of the lateral chains, as usually observed for ILCs.

However, the lateral alkyl chains alone are not sufficient to stabilise a SmA phase: comparing the dimer **14.4.14** with the monomer **14.14** we note that the central poly-cationic and flexible core is necessary to induce a fluid SmA phase. An ordered smectic phase is observed for the dimer **14.4.14** at lower temperature, whose thermal range of stability has a very little dependence on the length of the alkyl chains. The long chain symmetric monomer **14.14** only exhibits the ordered smectic phase in a similar temperature range. This latter phase, in turn, is completely destabilized in favour of the isotropic liquid, if one of the chains is replaced by a short ethyl group, as in **14.2**.

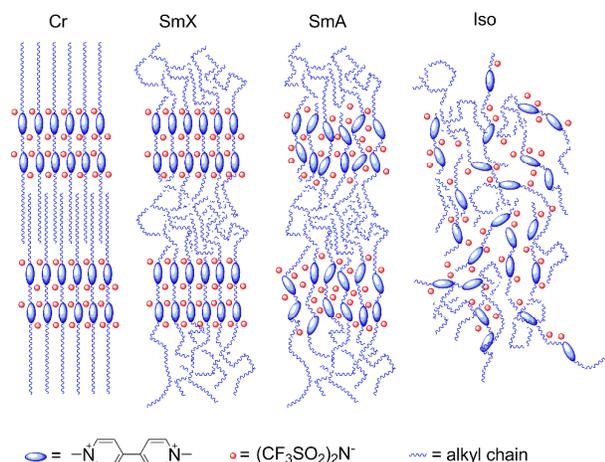


Fig. 5. Schematic representation of the four phases formed by viologen bistriflimide salts. The arrangement of the crystal phase and ionic layer of the SmX phase is purely qualitative.

The evidence we have collected indicates that the SmX phase is characterized by molten hydrophobic layers alternating with a ionic layers which still retain a relatively large degree of order. The packing of the ionic layers, which have, in poly-cationic

systems, a considerable thickness, is not a simple hexagonal packing as might be expected in a SmB phase, which is the ordered smectic phase usually found in non ionic LCs; rather a different lattice, depending on the type of quaternized nitrogen salt, will be formed giving rise to a complex XRD pattern. Striated-type textures support an ordered smectic phase. Remarkably, a similar sequence of high temperature SmA and low temperature ordered SmX phase was very recently reported for imidazolium trimers²⁴ suggesting that this might be a general behaviour for poly-cationic, symmetric ILCs.

Financial support from MIUR (PRIN 2010N3T9M4, FIRB RBAP11C58Y) and Fondazione CARIPARO (Progetti di Eccellenza "Nano-Mode" 2010, Varian 400 spectrometer) is gratefully acknowledged. We thank Moreno Lelli for helpful discussion and Renato Schiesari for help with SSNMR.

Notes and references

- ^a Dipartimento di Scienze Chimiche, Università di Padova, Via Marzolo, 1 – 35131 Padova, Italy.
- ^b Istituto per la Tecnologia delle Membrane del CNR (ITM-CNR), Unità di Padova, Via Marzolo, 1 – 35131 Padova, Italy. E-mail: giacomo.saielli@unipd.it
- † Electronic Supplementary Information (ESI) available: Full synthetic procedures and experimental and spectroscopic characterization. See DOI: 10.1039/b000000x/
- ‡ On leave of absence. Permanent address: Dipartimento di Scienze della Terra e del Mare (DiSTeM), Università di Palermo, Via Archirafi, 20 - 90123, Palermo (Italy).
- 1 K. Binnemans, *Chem. Rev.*, 2005, **105**, 4148-4204.
- 2 K. V. Axenov and S. Laschat, *Materials*, 2011, **4**, 206-259.
- 3 V. Causin and G. Saielli, in *Green Solvents II. Properties and Applications of Ionic Liquids*, ed. A. Mohammad and D. Inamuddin, Springer, UK, 2012, p. 79-118.
- 4 C. J. Bowlas, D. W. Bruce and K. R. Seddon, *Chem. Commun.*, 1996, , 1625-1626.
- 5 W. Dobbs, L. Douce, L. Allouche, A. Louati, F. Malbosc and R. Welter, *New J. Chem.*, 2006, **30**, 528-532.
- 6 Y. Ji, R. Shi, Y. Wang and G. Saielli, *J. Phys. Chem. B*, 2013, **117**, 1104-1109.
- 7 P. H. J. Kouwer and T. M. Swager, *J. Am. Chem. Soc.*, 2007, **129**, 14042-14052.
- 8 K. Goossens, P. Nockemann, K. Driesen, B. Goderis, C. Goerller-Walrand, K. Van Hecke, L. Van Meervelt, E. Pouzet, K. Binnemans and T. Cardinaels, *Chem. Mater.*, 2008, **20**, 157-168.
- 9 W. Li, J. Zhang, B. Li, M. Zhang and L. Wu, *Chem. Commun.*, 2009, , 5269-5271.
- 10 B. Ringstrand, A. Jankowiak, L. E. Johnson, P. Kaszynski, D. Pocięcha and E. Gorecka, *J. Mater. Chem.*, 2012, **22**, 4874-4880.
- 11 N. Yamanaka, R. Kawano, W. Kubo, N. Masaki, T. Kitamura, Y. Wada, M. Watanabe and S. Yanagida, *J. Phys. Chem. B*, 2007, **111**, 4763-4769.
- 12 M. Henmi, K. Nakatsuji, T. Ichikawa, H. Tomioka, T. Sakamoto, M. Yoshio and T. Kato, *Adv Mater*, 2012, **24**, 2238-2241.
- 13 M. Kagata, K. Hoshino, T. Mukai, H. Ohno and T. Kato, *J. Am. Chem. Soc.*, 2006, **128**, 5570-5577.
- 14 A. Safavi and M. Tohidi, *J. Phys. Chem. C*, 2010, **114**, 6132-6140.
- 15 N. V. Shvedene, O. A. Avramenko, V. E. Baulin, L. G. Tomilova and I. V. Pletnev, *Electroanalysis*, 2011, **23**, 1067-1072.
- 16 G. Saielli, G. A. Voth and Y. Wang, *Soft Matter*, 2013, **9**, 5716-5725.
- 17 G. Saielli, *Soft Matter*, 2012, **8**, 10279-10287.
- 18 M. Butschies, W. Frey and S. Laschat, *Chem. Eur. J.*, 2012, **18**, 3014-3022.
- 19 V. Causin and G. Saielli, *J. Mol. Liq.*, 2009, **145**, 41-47.
- 20 V. Causin and G. Saielli, *J. Mater. Chem.*, 2009, **19**, 9153-9162.
- 21 M. Bonchio, M. Carraro, G. Casella, V. Causin, F. Rastrelli and G. Saielli, *Phys. Chem. Chem. Phys.*, 2012, **14**, 2710-2717.

- 22 H. Q. N. Gunaratne, P. Nockemann, S. Olejarz, S. M. Reid, K. R. Seddon and G. Srinivasan, *Aust. J. Chem.*, 2013, **66**, 607-611.
- 23 I. Dierking, *Textures of Liquid Crystals*, Wiley-VCH, Weinheim, 2003.
- 24 M. R. Schenkel, R. Shao, L. A. Robertson, B. R. Wiesenauer, N. A. Clark and D. L. Gin, *Liq. Cryst.*, 2013, **40**, 1067-1081.