

Catalysis Science & Technology

Accepted Manuscript




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

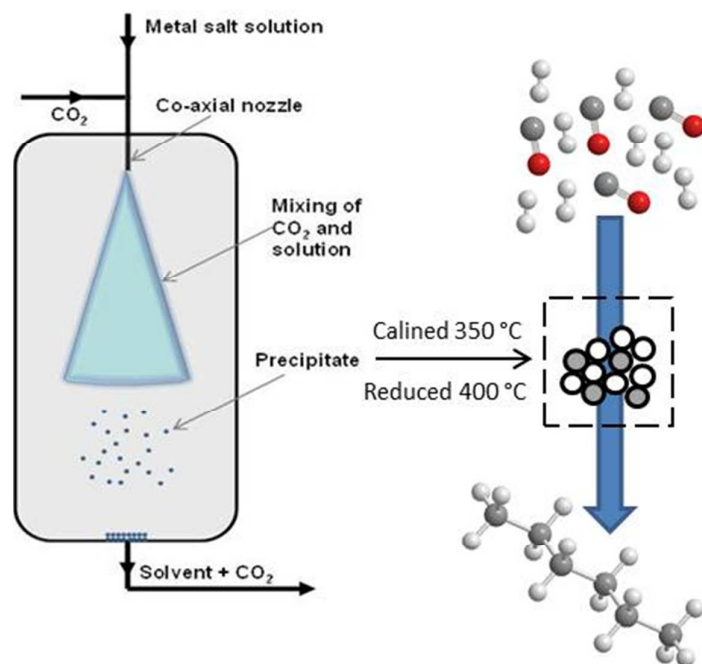

Novel Cobalt Zinc oxide Fischer–Tropsch catalysts synthesised
using supercritical anti-solvent precipitation

Raimon P. Marin,^{a,b} Simon A. Kondrat,^a Thomas E. Davies,^a David J. Morgan,^a Dan I.
Enache^b, Gary Combes,^b Stuart H. Taylor,^a Jonathan K. Bartley^a and Graham J.
Hutchings^{*a}

^aCardiff Catalyst Institute, School of Chemistry, Cardiff University, Park Place, Cardiff, CF10 3AT,
UK;

^bJohnson Matthey Plc., PO Box 1, Belasis Avenue, Billingham, Cleveland, TS23 1LB, UK

Abstract

Cobalt zinc oxide catalysts have been prepared by anti-solvent precipitation in supercritical CO₂ and investigated for CO hydrogenation. Here we show how the textural and catalytic properties of the catalyst can be tailored by the addition of water to the initial solution of cobalt and zinc acetates in methanol. Characterization of the catalysts by powder X-ray diffraction, infra-red and Raman spectroscopy showed that in the absence of water a high surface area mixed acetate was produced which upon calcination formed wurtzite type Zn_{1-x}Co_xO and spinel type Zn_xCo_{3-x}O₄. The addition of 5 vol.% water resulted in a phase separated Co₃O₄/ZnO catalyst and enhanced active cobalt surface area as a result of disruption of the solvent/CO₂ phase equilibrium during precipitation.

Introduction

The use of supercritical anti-solvent (SAS) precipitation as a method of catalyst synthesis offers a route to novel materials with properties intrinsic to the method of preparation. High diffusion and mass transfer rates possible within supercritical media mean that highly regular nanoparticulate materials can be synthesized with a narrow particle size distribution. Multi-element systems can be produced with an exceptional degree of nanoscale mixing between the relevant elements. In addition, the process offers a nitrate free route to catalyst synthesis through the use of a recycled CO₂ anti-solvent waste stream cutting out the need for expensive post treatment of waste.

SAS precipitation has been used extensively for the synthesis of explosives, polymers, semiconductor materials¹⁻⁶ and for membrane modification⁷ but it is only in the last ten years or so that the technique has been applied to the generation of catalytic materials. Previous studies have investigated the synthesis of single metal oxides for use as catalyst supports^{6,8} and catalysts⁹ as well as mixed metal oxides^{10,11}. We have previously shown that SAS prepared TiO₂⁸ and CeO₂¹² supports enhance the dispersion of active metals resulting in increased turnover rates.

The synthesis of binary metal oxides using this method can be challenging due to the varying precipitation rates and solubilities of the precursor compounds. However, the intimate mixing afforded, in combination with high surface area, mean that the SAS precipitation technique offers a clean, efficient and green method of accessing unique materials with enhanced catalytic activities. The intimate mixing can overcome the kinetic restrictions of metastable phase formation in solid-state reactions allowing access to new polymorphs with unique properties. Residue and

solvent free methods of catalyst preparation have been investigated previously employing nanocasting¹³, mechanochemical^{14, 15} and nanodispersion¹⁶ techniques. Methods such as these seek to overcome the kinetic limitation of forming these metastable compounds by ensuring effective mixing on the nanoscale. Supercritical anti-solvent precipitation is a superb method to obtain well-mixed precursor materials for mixed metal oxide catalysts, overcoming the limit of inter-diffusion over atomic distances. Furthermore, careful control of the precipitation parameters such as solvent composition, temperature, pressure, flow rates and nozzle size allows the product to be tuned towards a specific material product with desired properties.

Cobalt zinc oxide has traditionally been used in dyes and pigments^{17, 18}, as gas sensors and adsorbents for Cl₂, H₂O and H₂S^{19, 20}, semiconductors^{21, 22} and as a potential anode material in lithium ion batteries²³. Recently there has been interest in its potential as a catalyst for alcohol oxidation, ethanol reforming and Fischer-Tropsch (FT) synthesis. FT chemistry has been an important field since its inception in 1923 and is undergoing resurgence due to diminishing oil reserves and the development of alternative feedstocks such as biomass and natural gas. Cobalt is used as an FT catalyst because of its resistance to deactivation and efficiency for long chain hydrocarbon synthesis. However, the activity is strongly dependent upon a number of factors including particle size, dispersion, promoters, poisons and metal support interaction effects to name but a few. The most common supports are those based on refractory metal oxides such as TiO₂, SiO₂, Al₂O₃²⁴ and more recently carbon nanotubes²⁵ and activated carbon²⁶. The use of ZnO as a support has received little attention in the recent literature, although a number of patents do exist²⁷. Coville et al. have shown how Zn not only enhances the reducibility of the cobalt but also acts as a sulfur scavenger, increasing activity and selectivity in sulfur rich streams²⁸⁻³⁰.

In this work we have synthesized cobalt zinc oxide nanocomposites and shown how phase-separation can be induced by modification of the supercritical phase system with water, resulting in an increase in cobalt surface area relative to the standard co-precipitated material. These materials have then been tested as catalysts for CO hydrogenation.

Experimental

Catalyst precipitation was conducted using purpose built SAS equipment. The high pressure, stainless steel precipitation vessel (Jerguson gauge 13-R-32) was submerged in a water bath to control the temperature. A coaxial nozzle (CO₂ outer nozzle, i.d. 736 μm; solution inner nozzle, i.d. 250 μm) was used to deliver the CO₂ and solution to the precipitation vessel. CO₂ was pumped using air-driven pump (Haskel MS-71) and the solution pumped using a HPLC pump (Agilent Technologies series 1200) to maintain a molar ratio of CO₂:methanol equal to 40:1 at 120 bar and 40 °C. Three solutions were prepared with 7 mg ml⁻¹ (2.8x10⁻⁵ mol ml⁻¹) of Co(CH₃COO)₂·4H₂O and 35 mg ml⁻¹ (1.6x10⁻⁴ mol ml⁻¹) of Zn(CH₃COO)₂·2H₂O in 0, 5 and 15 vol.% H₂O/methanol. The CO₂ and solution were pumped concurrently for a period of 1.5 h, after which CO₂ alone was pumped for 0.5 h to remove any residual solvent. The resultant precursors prepared with differing amounts of H₂O, 0, 5 and 15 vol.% were designated SAS-0-P, SAS-5-P and SAS-15-P respectively and calcined at 350 °C and 500 °C prior to catalyst testing. These materials were designated SAS-0-350, SAS-5-350, SAS-15-350 or SAS-0-500, SAS-5-500, SAS-15-500 according to the calcination temperature used.

The SAS precipitated material was compared with a standard co-precipitated material. The initial nitrate metal solutions (Co(NO₃)₂·6 H₂O = 10 g L⁻¹ and

Zn(NO₃)₂·6 H₂O = 72 g L⁻¹) were pumped by peristaltic pumps at 1000 L h⁻¹ and an aqueous solution of NH₄CO₃ (NH₄CO₃ = 154 g L⁻¹) was delivered at the same flow rate. Both solutions were mixed inside a stirred vessel (300 r.p.m.) at pH 5.8 and 60 °C. The resultant material was washed with 1500 ml of deionised water five times and dried overnight at 120 °C followed by a final calcination at 350 °C or 500 °C. These materials were designated CP-P, CP-350 and CP-500, respectively.

X-ray diffraction studies were performed using a Panalytical X'pert Pro instrument using Ni filtered CuK_α radiation (40 kV and 40 mA). Scans were carried out over the range 10-120° 2θ. All patterns were matched using the ICDD database (International Centre for Diffraction Data, Pennsylvania, USA). H₂ chemisorption experiments were performed using a Micromeritics ASAP 2020. 0.5 g of catalyst was reduced *in situ* at 425 °C for 6 h under a 200 ml min⁻¹ flow of H₂ (BOC 99.99%) with a ramp rate of 3 °C min⁻¹. After reduction the sample was evacuated for 2 h at 450 °C to remove residual H₂. The H₂ chemisorption experiments were then carried out at 150 °C at 0.1-1 bar. The cobalt content of the materials was determined by atomic absorption spectroscopy (AAS) using a Varian SpectrAA 55B equipped with an air-acetylene flame. FTIR was carried out using a Jasco FT/IR 660 Plus spectrometer in transmission mode over the range 400-4000 cm⁻¹. Samples were diluted with anhydrous KBr and pressed into self-supporting discs prior to analysis. Thermogravimetric analysis (TGA) and differential temperature analysis (DTA) were performed using a Setaram Labsys. 10-30 mg of sample were loaded into an alumina crucible and heated to 550 °C at 20 °C min⁻¹ in air (BOC 99.99%). Scanning electron microscopy was carried out using a Carl Zeiss EVO 40 fitted with an Oxford Instruments EDX detector. Samples were mounted on Leit adhesive carbon discs and analysed uncoated. BET surface areas were measured by nitrogen physisorption using

a Micromeritics Gemini 2360. All samples were degassed at 120 °C for 2 h prior to analysis. Temperature programmed reduction (TPR) was performed using a Quantachrome Chembet 3000 equipped with a TCD detector, using a 10% H₂/Ar gas mixture at a flow rate of 20 ml min⁻¹. Catalysts were investigated over a temperature range of 50-900 °C with a ramp rate of 5 °C min⁻¹.

Catalyst testing was performed using six parallel fixed bed reactors consisting of ¼" o.d. stainless steel tubes housed in a brass block within a forced N₂ recirculating furnace. A thermocouple is in contact with the wall of the reactor at the level of the catalyst bed and the difference in temperature between the six reactors was 0.8 °C at 210 °C. The catalyst (0.13 g diluted with 0.5 g of SiC) was packed in the reactor and reduced *in situ* under flowing H₂ at 400 °C for 16 h. The reaction was performed at 20 bar, 210-250 °C. The syngas mixture Ar (3.5%) CO (32.17%) H₂ (64.33%) was fed at an initial GSVH = 13 L g_{cat}⁻¹ h⁻¹ to equilibrate the catalysts. After 24 hours the gas feed was adjusted to a GHSV value of 4.3 L g_{cat}⁻¹ h⁻¹. The reactors were then held under these conditions for 100 h. The temperature was then increased in 10°C increments and held at each temperature for 48 h, before increasing the temperature to the next point. After testing at 245 °C, the temperature was reduced to 210 °C to assess the deactivation of the catalyst. Liquid and wax traps were situated post reactor and the contents analysed by off-line gas chromatography, with the gaseous products analysed using on-line gas chromatography.

Results and discussion

Catalyst preparation and characterisation

FT-IR of the precursor materials (Fig. 1) was performed to investigate the effect of water addition on the chemical nature of the cobalt and zinc precipitated salts. The co-

precipitated material (CP-P) exhibited bands at *ca.* 1500, 1390 and 830 cm^{-1} associated with metal hydroxycarbonates^{31, 32}. SAS preparation without additional water (SAS-0-P) produced a spectra that could be assigned to metal acetates, due to the characteristic symmetric and asymmetric carbonyl bands at 1415 and 1560 cm^{-1} . The addition of water (SAS-5-P, SAS-15-P) resulted in the presence of distinct carbonate bands at 1500 and 830 cm^{-1} . Carbonate formation has been previously observed in SAS prepared CuMnO_x systems and is attributed to the reaction of the acetates with carbonic acid which is formed by the diffusion of CO_2 into the water containing precursor solution. However, even at 15 vol.% water addition (SAS-15-P), bands associated with acetates could still be observed in the CoZn system, indicating that anion exchange between acetate and carbonate was not complete.

TGA and DTA, shown in Figure 2, were performed on the SAS and co-precipitated materials to elucidate suitable calcination temperatures and to give greater insight to the composition of the precursors. The weight loss was observed to occur at <350 $^\circ\text{C}$ for all the SAS prepared materials with additional weight loss for the co-precipitated material observed at 350-500 $^\circ\text{C}$. Consequently, the SAS precipitated and co-precipitated materials were all calcined at both 350 and 500 $^\circ\text{C}$, with the lower temperature potentially affording greater retention of the fine structure provided by the SAS process. Two distinct TGA profiles were observed; one type for the SAS prepared materials and another for the co-precipitated material. The co-precipitated material had one principal weight loss centered *ca.* 280 $^\circ\text{C}$, which was endothermic in nature. The SAS prepared materials showed weight losses <120 $^\circ\text{C}$ were attributed to physisorbed water and methanol from the sample preparation and an endothermic weight loss *ca.* 150-225 $^\circ\text{C}$ attributed to the decomposition of hydroxycarbonates²⁰. The shift of this endothermic peak towards higher temperatures with increased water

content of the starting solution is attributed to the formation of crystalline species that need more thermal energy to decompose¹⁰. As observed in Figure 2a the total percentage weight loss attributed to this phase increased with higher amounts of water. The disrupted phase system emerging from introducing water as co-solvent could promote crystal growth, hence the formation of crystalline carbonates. The SAS prepared materials also had exothermic weight losses *ca.* 250-325 °C that can be assigned to the acetate decomposition. This confirms the findings from FT-IR analysis, that acetate anions are still present in all the SAS materials prepared with water as co-solvent. Gradual weight gains observed above 350 °C are due to a partial re-oxidation of the sample. It is known that metal acetates form a reducing atmosphere on thermal decomposition, leading to the reduction of the respective metals³³. This reduction is even apparent in oxygen containing atmospheres, although the metal quickly re-oxidises.

X-ray diffraction patterns of the freshly precipitated and the calcined cobalt zinc oxides are shown in Figures 3 and 4 respectively. The precursor precipitated by the SAS procedure without additional water (SAS-0-P) was amorphous, while the addition of water resulted in the formation of crystalline material. The degree of crystallinity was found to increase as the water concentration in the preparation was increased, as previously noted in SAS prepared CuMn_2O_4 ¹⁰. Calcination of the catalyst at 350 °C resulted in the formation of zinc oxide wurtzite (ZnO , ICDD 01-070-2551) and the expected cobalt product, a cubic spinel compound of ZnCo_2O_4 or Co_3O_4 , was not observed. The lack of observable Co_3O_4 phases could be also explained by the formation of a metastable cobalt substituted ZnO of the type $\text{Zn}_{1-x}\text{Co}_x\text{O}$ which has previously been synthesized from intimately mixed metal oxalates³⁴. However, determination of Co incorporation as a result of induced lattice strain in

ZnO is difficult due to the similar ionic radii of divalent Co (0.58Å) and divalent Zn (0.60Å) in tetrahedral coordination.

Calcination at 500 °C did not form different phases with the exception of SAS-5-500 which showed the presence of a cubic spinel phase. Significant overlap of the reflections makes it difficult to unequivocally assign the pattern to Co_3O_4 or ZnCo_2O_4 . This is consistent with work conducted by Baird *et al.* on co-precipitated Co/Zn/O catalysts which found the structure of the bulk to be monophasic ZnO at low Co concentrations with ZnCo_2O_4 prominent at the surface, whereas at higher Co concentrations a biphasic Co_3O_4 and ZnO system was formed³⁵.

Raman spectra of the calcined samples are shown in Figures 5 and 6, along with individual metal oxide standards prepared under the same conditions. The ZnO standard (Fig. 5a and 6a) shows the typical Raman modes for space group C^4_{6v} E_2 (high) at 439 cm^{-1} , A_1 (TO) at 382 cm^{-1} , E_2 (high)- E_2 (low) at 332 cm^{-1} . The Co_3O_4 standard (Fig. 5b and 6b) displays the theoretical Raman modes for a metal oxide spinel (space group $Fd3m$ (O_h^7)) (E_g at 484 cm^{-1} , F_{2g} at 523 cm^{-1} , F_{2g} at 622 cm^{-1} and A_{1g} at 693 cm^{-1})³⁶. In contrast to the XRD analysis the calcined materials prepared using the SAS process show only weak peaks from the ZnO component (E_2 (high) at 439 cm^{-1}) with the main vibrations attributed to the strongly scattering spinel phase. This demonstrates that Co_3O_4 or $\text{Zn}_x\text{Co}_{3-x}\text{O}_4$ is present in all samples, in a poorly crystalline state that is not observable by XRD. It was noted that the SAS and co-precipitated prepared materials had a significant blue shift in the spinel Raman bands, relative to the Co_3O_4 standard. This has previously been observed when Zn^{2+} is incorporated into the Co_3O_4 lattice^{17, 37, 38}. The most significant shift occurs for the A_{1g} mode corresponding to oxygen vibrations in the CoO_6 octahedral unit in Co_3O_4 . Recently Rubio-Marcus *et al.* synthesised ZnCo_2O_4

via a dry mixing method. They reported that temperatures of 500 °C and annealing times of up to 36 h were required to overcome the kinetic restriction of Zn diffusion through the lattice¹⁶. In this study, $Zn_xCo_{3-x}O_4$ was formed in all samples at temperatures as low as 350 °C after just 2 h calcination. However, weak peaks at *ca.* 689 cm^{-1} from residual Co_3O_4 are still visible, indicating incomplete formation of the mixed phase in CP-350 and SAS preparations with additional water. However, the lack of this band in SAS-0-350 indicates the intimate mixing of Co and Zn afforded by the SAS process aids the formation of the mixed metal oxide at much lower temperatures than traditional synthesis methods. The presence of phase separated metal oxides when water was added is due to a change in the phase system for the SAS process. Water addition limits the miscibility of CO_2 and methanol resulting in surface tension of the precursor solution droplet in the system. Consequently there will be a significant diffusion gradient as the CO_2 diffuses into the precursor solution. As the cobalt and zinc salts have differing solubilities in a CO_2 -solvent mixture, this diffusion gradient results in different nucleation rates of the respective salts and therefore a phase segregated material.

Calcination of the materials at 500 °C resulted in almost complete formation of $Zn_xCo_{3-x}O_4$, with minimal Co_3O_4 observed by Raman spectroscopy. Although a blue shift of the Raman bands was observed for the spinel phase in all samples, the extent of the shift was markedly less in the SS-5-500. This demonstrates that the addition of 5% water has a greater degree of Co and Zn phase separation, as confirmed by the observable spinel phase in XRD analysis.

The surface areas of the precursors and the calcined catalysts are presented in Table 1. Addition of 5 vol.% water to the methanol solution increased the surface area of the precursor from 28 to 100 $m^2 g^{-1}$ but this decreased to 37 $m^2 g^{-1}$ at higher water

concentration. It has previously been noted that high water concentrations (>10 vol.%) tend to result in a disruption of the CO₂-solvent phase equilibrium due to the poor miscibility between CO₂ and H₂O³⁹. This results in lower product yields, a broad particle size distribution, reduced surface area and particle agglomeration through wetting.


Calcination of the SAS precursors at 350 °C resulted in surface areas of *ca.* 45 m² g⁻¹ for all catalysts, whereas higher temperature calcination at 500 °C lowered the surface area to *ca.* 18 m² g⁻¹ which are comparable to the co-precipitated sample surface area. Previous studies by Baird *et al.* found the same total surface area values for low cobalt loaded samples (<20 at.%)²⁰. Previous catalyst preparations using SAS precipitation found that the addition of water during the synthesis prevented the decrease in surface area on calcination¹⁰. This was attributed to the formation of carbonic acid in the precipitation vessel, yielding metal carbonate products that decompose endothermically helping to maintain the surface area of the precursor. This effect was not observed in the current work, which is probably due to the significant presence of acetate in all samples, which was observed by IR spectroscopy.

Cobalt content of the catalysts was determined by AAS (Table 1) with all SAS samples having loadings between 14.5 and 18.5 wt.% Co, while the co-precipitated material had a lower loading of 10.4 wt.%. This lower loading in the co-precipitated sample could be due to the hygroscopic nature of cobalt nitrate resulting in a slightly lower Co concentration than targeted. The cobalt metal surface areas were determined using H₂ chemisorption and are presented in Table 1. The catalysts prepared using SAS precipitation and calcined at 350 °C all display higher active metal surface areas when compared to the standard co-precipitated material. The addition of water

resulted in an area increase from 3.7 (\pm 0.4) to 5.6 (\pm 0.6) $\text{m}^2 \text{g}^{-1}$ for which is over four times higher than the cobalt surface area of the co-precipitated material. The trend of SAS prepared catalysts having higher cobalt surface area was still retained when the data was normalized to Co mass. The XRD patterns of the catalysts calcined at 350 °C contained no reflections associated with cobalt metal. Calcination at 500 °C had the expected effect of lowering the active metal surface area through a combination of particle sintering and migration of Co into the ZnO bulk, forming a solid solution. These findings are consistent with the Raman and XRD data that showed an enhanced phase separation with 5 vol.% water addition.

Reducibility of the samples was determined by temperature programmed reduction and the results shown in Figure 7 and Table 3. The reduction profile of all catalysts was indicative of the two stage reduction of Co_3O_4 to CoO between 260-310 °C and CoO to Co between 400-500 °C⁴⁰. The lower temperature reduction at *ca.* 220-250 °C, observed in all catalysts calcined at 350 °C and SAS-0-500, could be attributable to decomposition of residual cobalt(II) acetate or carbonate species or reduction of a CoOOH species⁴¹. The presence of significant amounts of residual cobalt(II) salts are not apparent from the TGA data (Fig. 2), which shows no mass loss above 325 °C, though small amounts of surface stabilised cobalt(II) species may remain.

A clear difference in the reduction profile of the catalysts calcined at the different temperatures is observed. Theoretically pure Co_3O_4 would reduce to Co according to the two-step reaction shown in Equation 1 and 2.



This results in hydrogen consumption and water production at a ratio of 1:3 for the respective Co^{3+} and Co^{2+} reduction steps.. The catalysts calcined at 350 °C were found to have ratios of the low temperature (Co^{3+}) and high temperature (Co^{2+}) reduction peaks (Co_3O_4 reduction and the reduction peak at *ca.* 220-250 °C have been combined) of *ca.* 1:5. The variance from the theoretical value of 1:3 can be explained by the presence of an excess of Co^{2+} not in the Co_3O_4 , potentially as CoO. Catalysts calcined at 500 °C had far lower ratios, indicating more oxidised materials containing less Co^{2+} .

As reducibility of cobalt oxides is related to FT activity, since it is metallic Co that is the active phase, the final reduction temperature can give an indication of the potential of the FT catalyst. It was observed that the CoO reduction peak temperature for the 350 °C calcined materials increased with the water content in the catalyst preparation. This suggests that SAS-0-350 could be more active, though it does have the lowest Co surface area of the 350 °C calcined materials. Catalysts calcined at 500 °C all had similar CoO reduction temperatures at *ca.* 420 °C.

Catalyst testing

The materials were tested as FT catalysts using the standard procedure developed at Johnson Matthey and the data are presented in Table 2 and Figure 8. As small amounts of catalyst were tested conversions were relatively low, however a standard co-precipitated catalyst was also tested to benchmark the SAS precipitated materials performance. At low conversion the conversion appears to be $0\% \pm 0.25$. These should be considered to be no conversion and the deviation is due small fluctuations in the

peak areas used to calculate conversion and gives an indication of the error in the testing results.

It should be noted that no previous work has been reported in the literature for zinc oxide supported cobalt FT catalysts, as described here. Therefore, the observable formation of desired C_{5+} products demonstrates the potential of cobalt zinc oxide systems for FT synthesis without the presence of traditional support materials, such as Al_2O_3 , TiO_2 , SiO_2 and activated carbon.

It is clear from the results that both calcination temperature and the amount of water co-solvent are crucial to the performance of the SAS precipitated materials. The optimum calcination was found to be 350 °C with 5 vol.% water addition giving the most active catalysts. Calcination at 500 °C resulted in a decrease in the SAS prepared catalysts activity and in some cases loss of stability. This loss of activity on higher temperature calcination corresponds to the generally observed decrease in cobalt surface area on 500 °C calcination. The performance of the SAS precipitated materials compared favourably with the standard co-precipitated catalysts – particularly at low temperature. At higher temperature (245 °C) deactivation occurred, which was much faster for the catalysts calcined at high temperature and can be attributed to the reduction in both the bulk and cobalt surface areas. The minimal change in activity of the co-precipitated catalysts calcined at different temperatures correlated with a minimal change in surface area. Although the cobalt surface area is clearly important, the most active catalyst (SAS-5-350) has a comparable cobalt surface area to the less active SAS-15-350 and so it is not the only key parameter for these catalysts. Previously it has been shown that the hcp/fcc ratio of the Co is important⁴⁰, but this could not be determined from the XRD data in this study. It was noted in analysis of TPR data that SAS-5-350 was slightly more reducible than SAS-

15-350. Another important factor is the separation between cobalt and zinc phases. Evidence for this can be found in the Raman spectra of the SAS-5-350 catalyst, which shows an observable amount of non-blue shifted, pure Co_3O_4 . Further evidence of this phase separation can be inferred from Raman and XRD analysis of the 500 °C calcined material. The observed phase separation by XRD in SAS-5-500 catalyst would have been present in the lower temperature calcined material, but was made observable due to the sintering of the cobalt oxide.

Conclusions

Cobalt zinc oxide catalysts have been prepared by precipitation using supercritical CO_2 as an anti-solvent and characterized by XRD, TPR, SEM and FTIR. The SAS precipitated material prepared without additional water was amorphous and comprised a mixture of metal acetates. FTIR indicated that the addition of water to the supercritical phase facilitates the formation of carbonates through the generation of carbonic acid species, though exchange of acetate was not complete. The addition of water to the precursor solution altered the mixture critical point of the system changing the mechanism of precipitation promoting the formation of higher surface area precursors with spherical and needle-like particles morphologies. XRD analysis of the calcined catalyst found that the main phase present was ZnO with the presence of small amounts Co_3O_4 or a mixed ZnCo_2O_4 observable by Raman analysis. The degree of phase separation can be modified through altering the water concentration in the initial start solution, with the addition of 5 vol.% water resulted in a greater degree of separation. The water modified SAS precipitation facilitated the enhanced phase separation and high cobalt surface area of the catalysts, afforded by calcinations

at 350 °C, which was found to be favourable for the formation of C₅₊ products in the FT reaction.

Acknowledgments

The Cardiff Catalysis Institute would like to thank Johnson Matthey Plc for the catalyst testing and cobalt surface area analysis. Also we would like to thank the U.K Technology Strategy Board for funding.

References

1. D. Andreeva, I. Ivanov, L. Ilieva and M. V. Abrashev, *Applied Catalysis A: General*, 2006, **302**, 127-132.
2. P. M. Gallagher, M. P. Coffey, V. J. Krukonis, and N. Klasutis., *ACS Symposium Series*, 1989, **406**, 334-354.
3. D. J. Dixon, G. Luna-Bárcenas and K. P. Johnston, *Polymer*, 1994, **35**, 3998-4005.
4. A. O'Neil, C. Wilson, J. M. Webster, F. J. Allison, J. A. K. Howard and M. Poliakoff, *Angewandte Chemie International Edition*, 2002, **41**, 3796-3799.
5. C. N. Field, P. A. Hamley, J. M. Webster, D. H. Gregory, J. J. Titman and M. Poliakoff, *Journal of the American Chemical Society*, 2000, **122**, 2480-2488.
6. E. Reverchon, G. Della Porta, D. Sannino and P. Ciambelli, *Powder Technology*, 1999, **102**, 127-134.
7. Z. Xinli, H. Xiaoling, G. Ping and L. Guozheng, *The Journal of Supercritical Fluids*, 2009, **49**, 111-116.
8. Z.-R. Tang, J. K. Bartley, S. H. Taylor and G. J. Hutchings, *Studies in Surface Science and Catalysis*, 2006, **162**, 219-226.
9. E. Reverchon, G. D. Porta, D. Sannino, L. Lisi and P. Ciambelli, *Studies in Surface Science and Catalysis*, 1998, **118**, 349-358.
10. Z. R. Tang, S. A. Kondrat, C. Dickinson, J. K. Bartley, A. F. Carley, S. H. Taylor, T. E. Davies, M. Allix, M. J. Rosseinsky, J. B. Claridge, Z. Xu, S. Romani, M. J. Crudace and G. J. Hutchings, *Catalysis Science & Technology*, 2011, **1**, 740-746.
11. G. J. Hutchings, J. A. Lopez-Sanchez, J. K. Bartley, J. M. Webster, A. Burrows, C. J. Kiely, A. F. Carley, C. Rhodes, M. Hävecker, A. Knop-Gericke, R. W. Mayer, R. Schlögl, J. C. Volta and M. Poliakoff, *Journal of Catalysis*, 2002, **208**, 197-210.
12. P. J. Miedziak, Z. Tang, T. E. Davies, D. I. Enache, J. K. Bartley, A. F. Carley, A. A. Herzing, C. J. Kiely, S. H. Taylor and G. J. Hutchings, *Journal of Materials Chemistry*, 2009, **19**, 8619-8627.
13. A. H. Lu and F. Schüth, *Advanced Materials*, 2006, **18**, 1793-1805.
14. H. Yang, Y. Hu, X. Zhang and G. Qiu, *Materials Letters*, 2004, **58**, 387-389.
15. T. E. Davies, T. Garcia, B. Solsona and S. H. Taylor, *Chemical Communications*, 2006, 3417-3419.
16. F. Rubio-Marcos, V. Calvino-Casilda, M. A. Bañares and J. F. Fernandez, *Journal of Catalysis*, 2010, **275**, 288-293.
17. G. V. Bazuev and O. I. Gyrdasova, *Physica Status Solidi (b)*, 2008, **245**, 1184-1190.
18. C. Ai, M. Yin, C. Wang and J. Sun, *Journal of Materials Science*, 2004, **39**, 1077-1079.
19. X. Niu, W. Du and W. Du, *Sensors and Actuators B: Chemical*, 2004, **99**, 405-409.
20. T. Baird, K. C. Campbell, P. J. Holliman, R. W. Hoyle, D. Stirling, B. P. Williams and M. Morris, *Journal of Materials Chemistry*, 1997, **7**, 319-330.
21. M. Schumm, M. Koerdel, J. F. Morhange, Z. Golacki, K. Grasza, P. Skupinski, W. Szuszkiewicz, H. Zhou, V. Malik, H. Kalt, C. Klingshirn and J. Geurts, *Journal of Physics: Conference Series*, 2007, **92**, 012149.
22. N. H. Perry, T. O. Mason, C. Ma, A. Navrotsky, Y. Shi, J. S. Bettinger, M. F. Toney, T. R. Paudel, S. Lany and A. Zunger, *Journal of Solid State Chemistry*, 2012, **190**, 143-149.
23. W. Y. Li, L. N. Xu and J. Chen, *Advanced Functional Materials*, 2005, **15**, 851-857.
24. E. Iglesia, *Applied Catalysis A: General*, 1997, **161**, 59-78.
25. A. Tavasoli, R. M. M. Abbaslou, M. Trepanier and A. K. Dalai, *Applied Catalysis A: General*, 2008, **345**, 134-142.
26. W. P. Ma, Y. J. Ding and L. W. Lin, *Industrial & Engineering Chemistry Research*, 2004, **43**, 2391-2398.
27. C. R. Baijense, G. Johnson, A. Moini, *Core-shell catalyst, its preparation and use thereof for fischer-tropsch synthesis*, WO 2005/116167 A1 2009.
28. N. N. Madikizela and N. J. Coville, *Journal of Molecular Catalysis A: Chemical*, 2002, **181**, 129-136.
29. N. N. Madikizela-Mnqanqeni and N. J. Coville, *Applied Catalysis A: General*, 2004, **272**, 339-346.
30. N. N. Madikizela-Mnqanqeni and N. J. Coville, *Journal of Molecular Catalysis A: Chemical*, 2005, **225**, 137-142.
31. R. Wahab, S. G. Ansari, Y. S. Kim, M. A. Dar and H.-S. Shin, *Journal of Alloys and Compounds*, 2008, **461**, 66-71.
32. Z. Nickolov, G. Georgiev, D. Stoilova and I. Ivanov, *Journal of Molecular Structure*, 1995, **354**, 119-125.
33. S. A. Kondrat, T. E. Davies, Z. Zu, P. Boldrin, J. K. Bartley, A. F. Carley, S. H. Taylor, M. J. Rosseinsky and G. J. Hutchings, *Journal of Catalysis*, 2011, **281**, 279-289.

34. A. S. Risbud, N. A. Spaldin, Z. Q. Chen, S. Stemmer and R. Seshadri, *Physical Review B*, 2003, **68**, 205202.
35. T. Baird, K. C. Campbell, P. J. Holliman, R. W. Hoyle, M. Huxam, D. Stirling, B. Peter Williams and M. Morris, *Journal of Materials Chemistry*, 1999, **9**, 599-605.
36. V. G. Hadjiev, M. N. Iliev and I. V. Vergilov, *Journal of Physics C: Solid State Physics*, 1988, **21**, L199.
37. K. Samanta, P. Bhattacharya, R. S. Katiyar, W. Iwamoto, P. G. Pagliuso and C. Rettori, *Physical Review B*, 2006, **73**, 245213.
38. N. H. Perry, T. O. Mason, C. Ma, A. Narvrotsky, Y. Shi, J. S. Joanna, M. F. Toney, T. R. Tula, S. Lany, A. Zunger, *Journal of Solid State Chemistry*, 2012, **190**, 143.
39. C. Duarte, A. N. A. Aguiar-Ricardo, N. Ribeiro, T. Casimiro and M. N. Da Ponte, *Separation Science and Technology*, 2000, **35**, 2187-2201.
40. W. Chu, P. A. Chernavskii, L. Gengembre, G. A. Pankina, P. Fongarland, A. Y. Khodakov, *Journal of Catalysis*, 2007, **252**, 215-230.
41. J. van de Loosdrecht, S. Barradas, E.A. Caricato, N.G. Ngwenya, P.S. Nkwanyana, M.A.S. Rawat, B.H. Sigwebela, P.J. van Berge and J.L. Visagie, *Top. Catal.*, 2003, **26**, 121-127.

Legends for figures

Figure 1. FT-IR analysis of SAS and co-precipitated uncalcined precursors: (a) CP-P; (b) SAS-0-P; (c) SAS-5-P; (d) SAS-15-P.

Figure 2. Thermal analysis of the uncalcined cobalt zinc precursors: (a) TGA; (b) DTA. Dotted line CP-P; Solid line SAS-0-P; Dash line SAS-5-P; Dot-Dash line SAS-15-P.

Figure 3. X-ray diffraction patterns of the uncalcined cobalt zinc precursors: (a) CP-P; (b) SAS-0-P; (c) SAS-5-P; (d) SAS-15-P.

Figure 4. X-ray diffraction patterns of the cobalt zinc oxide catalysts: a) SAS-0-350; b) SAS-5-350; c) SAS-15-350; d) SAS-0-500; e) SAS-5-500; f) SAS-15-500. Inset: expanded view depicting spinel formation in SAS-5-500. (hkl) indices refer to wurtzite ZnO structure.

Figure 5. Raman spectra of the cobalt zinc oxide catalysts calcined at 350 °C: a) ZnO; b) Co₃O₄; c) CP-350; d) SAS-0-350; e) SAS-5-350; f) SAS-15-350.

Figure 6. Raman spectra of the cobalt zinc oxide catalysts calcined at 500 °C: a) ZnO; b) Co₃O₄; c) CP-500; d) SAS-0-500; e) SAS-5-500; f) SAS-15-500.

Figure 7. Temperature programmed reduction of SAS precipitated catalyst calcined at 350 and 500 °C. Top image: a) SAS-0-350 b) SAS-5-350; c) SAS-15-350. Bottom image: a) SAS-0-500; b) SAS-5-500; c) SAS-15-500.

Figure 8. Performance of the cobalt zinc oxide materials as Fischer Tropsch catalysts. Top: Catalysts calcined at 350 °C. ▼ CP-350; ■ SAS-0-350; ○ SAS-5-350; □ SAS-15-350. Bottom: Catalyst calcined 500 °C. ▼ CP-500; ■ SAS-0-500; ○ SAS-5-500; □ SAS-15-500

Table 1. Surface areas and Co:Zn ratios for uncalcined and calcined catalysts

Table 2. Performance of the cobalt zinc oxide materials as Fischer Tropsch catalysts.

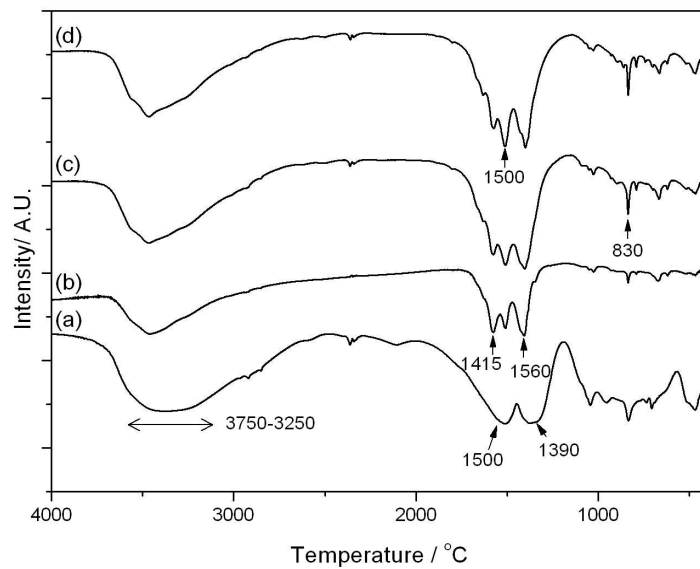


Figure 1. FT-IR analysis of the uncalcined cobalt zinc precursors: (a) CP-P; (b) SAS-0-P; (c) SAS-5-P; (d) SAS-15-P.

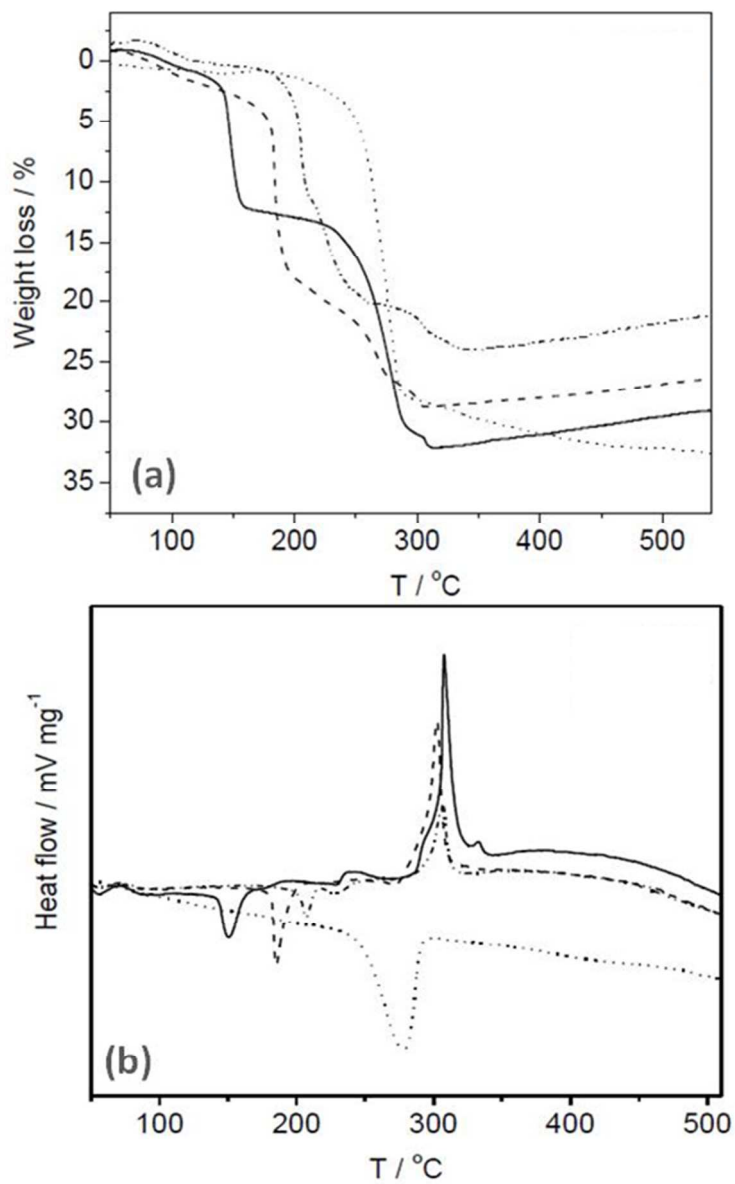


Figure 2. Thermal analysis of the uncalcined cobalt zinc precursors: (a) TGA; (b) DTA. Dotted line CP-P; Solid line SAS-0-P; Dash line SAS-5-P; Dot-Dash line SAS-15-P.

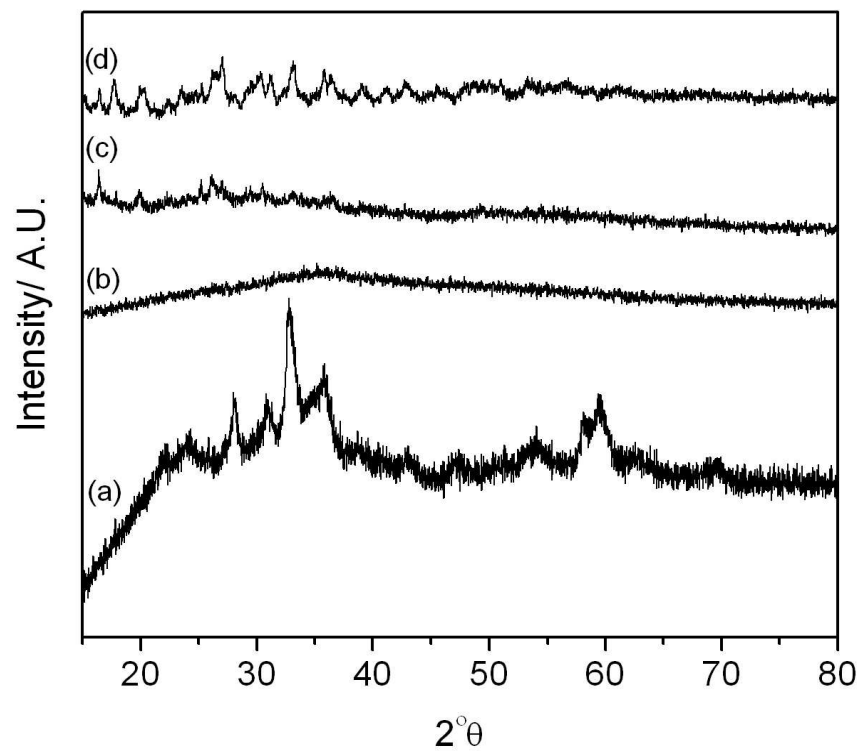


Figure 3. X-ray diffraction patterns of the uncalcined cobalt zinc precursors: (a) Cp-P; (b) SAS-0-P; (c) SAS-5-P; (d) SAS-15-P.

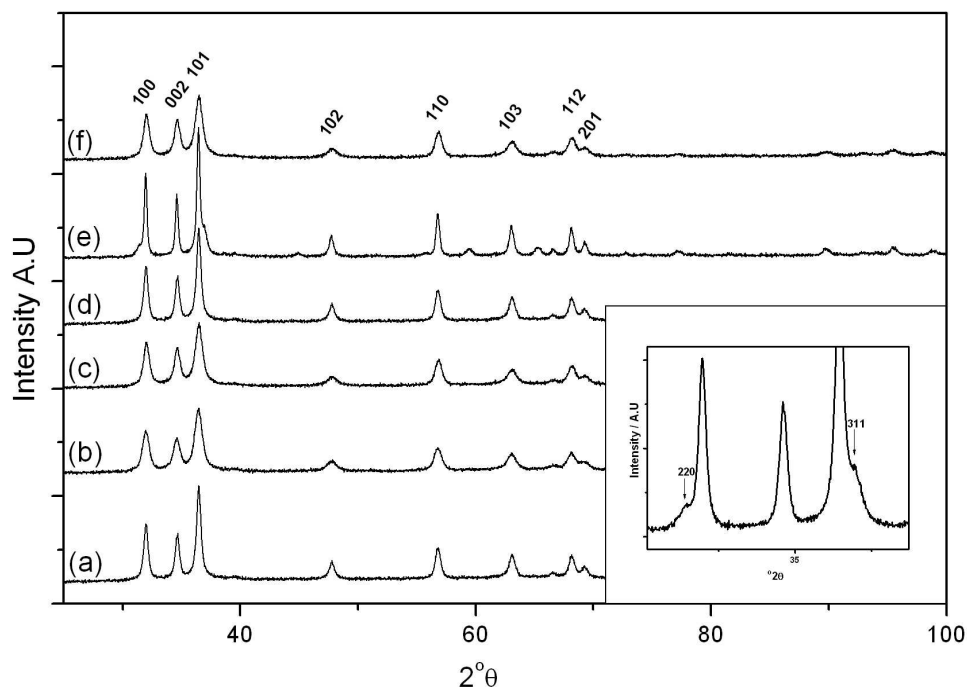


Figure 4. X-ray diffraction patterns of the cobalt zinc oxide catalysts: a) SAS-0-350; b) SAS-5-350; c) SAS-15-350; d) SAS-0-500; e) SAS-5-500; f) SAS-15-500. Inset: expanded view depicting spinel formation in SAS-5-500. (hkl) indices refer to wurtzite ZnO structure.

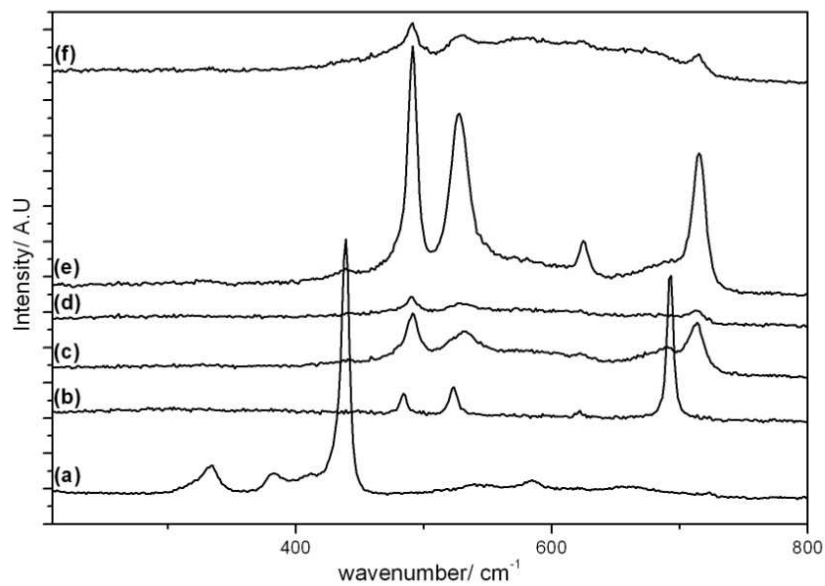


Figure 5. Raman spectra of the cobalt zinc oxide catalysts calcined at 350 °C: a) ZnO; b) Co_3O_4 ; c) CP-350; d) SAS-0-350; e) SAS-5-350; f) SAS-15-350.

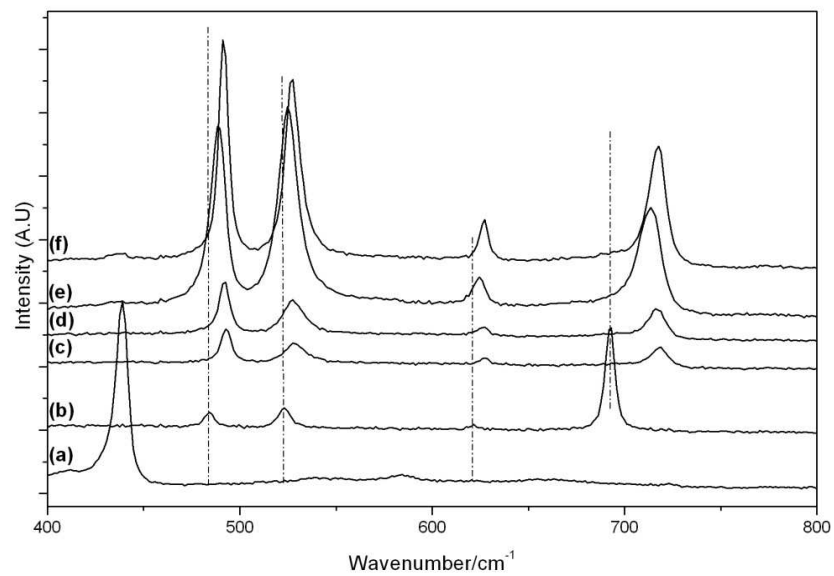


Figure 6. Raman spectra of the cobalt zinc oxide catalysts calcined at 500 °C: a) ZnO; b) Co₃O₄; c) CP-500; d) SAS-0-500; e) SAS-5-500; f) SAS-15-500.

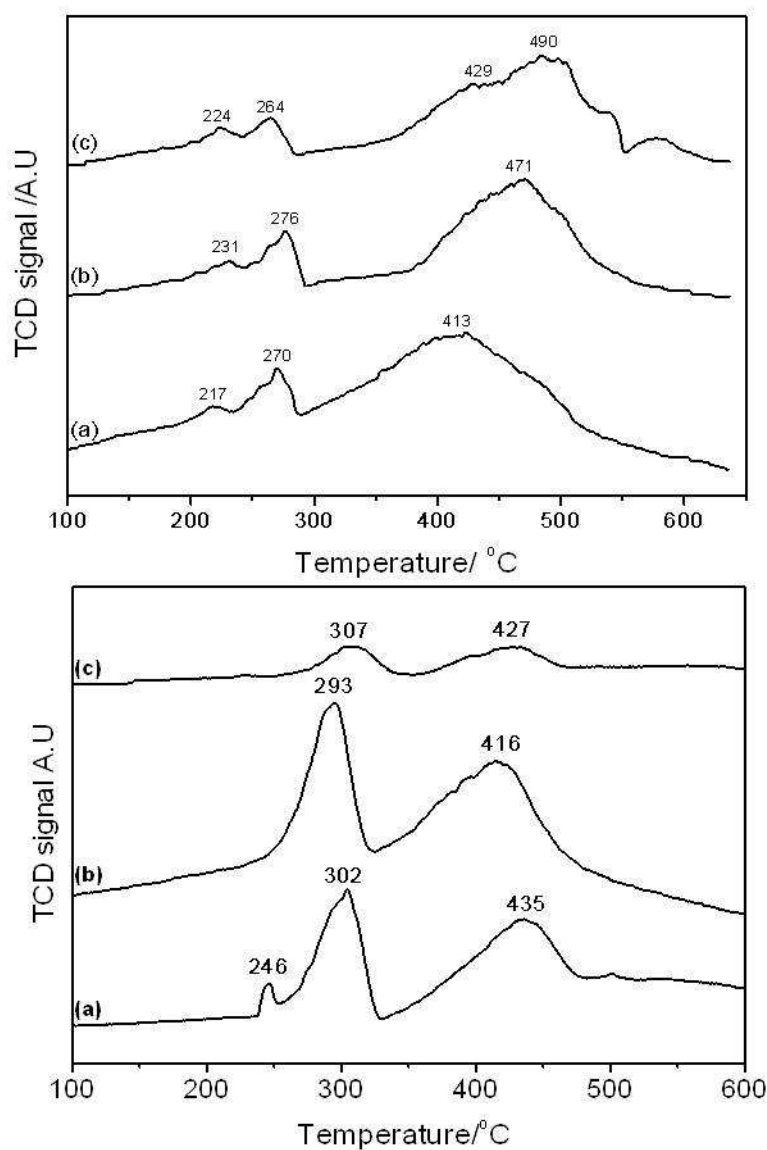


Figure 7. Temperature programmed reduction of SAS precipitated catalyst calcined at 350 and 500 °C. Top image: a) SAS-0-350 b) SAS-5-350; c) SAS-15-350. Bottom image: a) SAS-0-500; b) SAS-5-500; c) SAS-15-500.

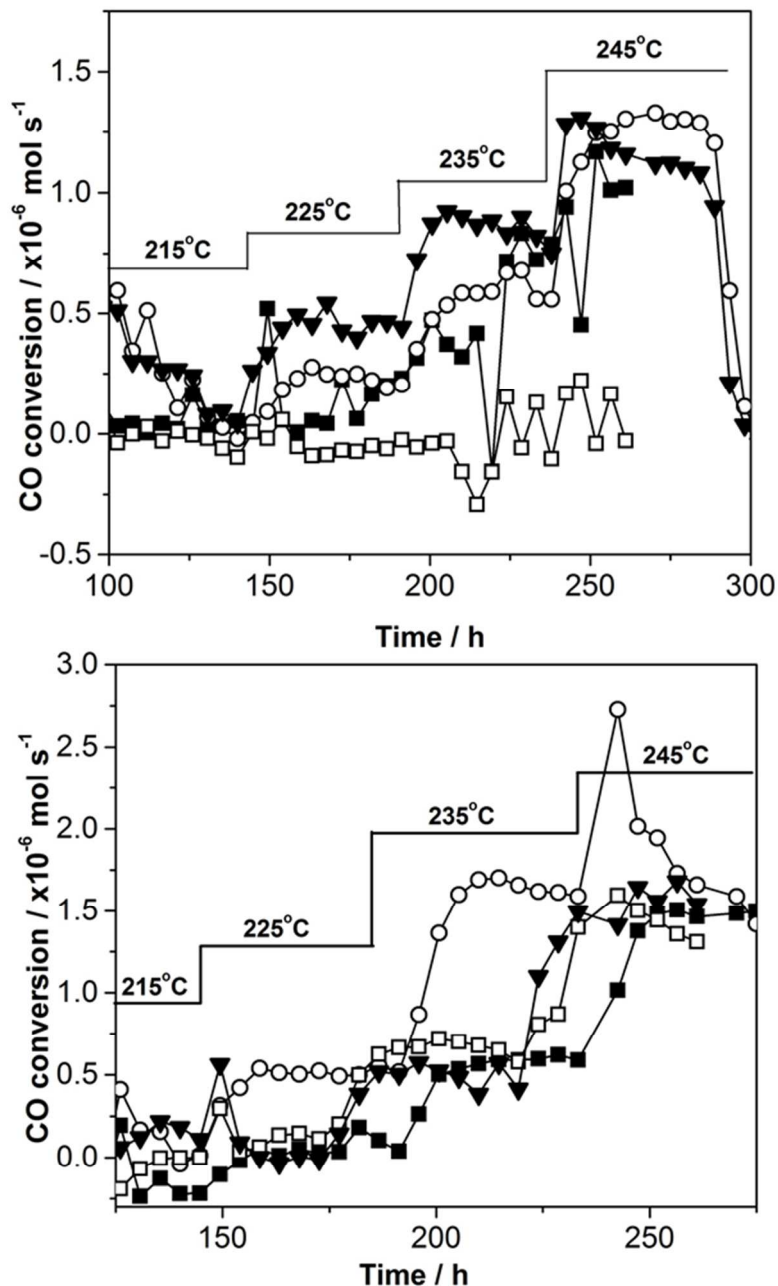


Figure 8. Performance of the cobalt zinc oxide materials as Fischer Tropsch catalysts. Top: Catalysts calcined at 350 °C. ▼ CP-350; ■ SAS-0-350; ○ SAS-5-350; □ SAS-15-350. Bottom: Catalyst calcined 500 °C. ▼ CP-500; ■ SAS-0-500; ○ SAS-5-500; □ SAS-15-500

Table 1. Surface areas and Co:Zn ratios for uncalcined and calcined catalysts

Catalyst	Co loading (wt.%)	BET surface area ($\text{m}^2 \text{g}^{-1}$) ^a		Co surface area ^b	
		Precursor	Calcined 350 °C	($\text{m}^2 \text{g}^{-1}$)	($\text{m}^2 \text{g}_{\text{Co}}^{-1}$)
SAS-0-350	18.5	28	44	3.7 (± 0.4)	21.2 (± 2.9)
SAS-0-500			17	1.7 (± 0.2)	9.7 (± 1.4)
SAS-5-350	17.1	101	46	5.6 (± 0.6)	32.8 (± 4.6)
SAS-5-500			18	2.5 (± 0.3)	14.6 (± 2.0)
SAS-15-350	14.5	37	47	5.6 (± 0.6)	38.5 (± 5.4)
SAS-15-500			18	1.7 (± 0.2)	11.7 (± 1.6)
CP-350	10.4	17	17	1.3 (± 0.1)	12.5 (± 1.8)
CP-500			19	1.5 (± 0.2)	14.4 (± 2.0)

^a Determined by N₂ physisorption at 77 K; ^b determined by H₂ chemisorption; ^c determined by atomic absorption spectroscopy

Table 2. Performance of the cobalt zinc oxide materials as Fischer Tropsch catalysts.

Catalyst	CO conversion (10^{-6} mol s $^{-1}$)			C $_{5+}$ selectivity (%)		
	225 °C	235 °C	245 °C	225 °C	235 °C	245 °C
SAS-0-350	0.01	0.57	1.46	-	61	69
SAS-5-350	0.51	1.70	1.66	62	76	54
SAS-15-350	0.13	0.68	1.31	70	74	63
CP-350	0	0.38	1.54	-	70	74
SAS-0-500	0.06	0.32	1.02	78	0	45
SAS-5-500	0.28	0.59	1.30	15	34	47
SAS-15-500	0	0	0	-	-	-
CP-500	0.46	0.90	1.16	0	0	34

Table 3. Temperature programmed reduction peak temperatures and area ratios

Sample	Co $^{3+}$ reduction to Co $^{2+}$	Co $^{2+}$ reduction to Co	Reduction peak ratio (Co $^{3+} \rightarrow$ Co $^{2+}$):(Co $^{2+} \rightarrow$ Co) *
	Temperature (°C)	Temperature (°C)	
SAS-0-350	224 and 264	413	1:3.3
SAS-0-500	231 and 276	471	1.1:1
SAS-5-350	217 and 270	429 and 490	1:5
SAS-5-500	246 and 302	435	1:1.5
SAS-15-350	293	416	1:5
SAS-15-050	307	427	1:1.1

*Theoretical value for pure Co $_3$ O $_4$ is 1:3